



COVER SHEET

This is the author version of article published as:

Frost, Ray L. and Bouzaid, Jocelyn M. and Martens, Wayde N. (2007) Thermal decomposition of the composite hydrotalcites of iowaite and woodallite. *Journal of Thermal Analysis and Calorimetry* 89(2):pp. 511-519.

Copyright 2007 Springer

Accessed from <http://eprints.qut.edu.au>

Thermal decomposition of the composite hydrotalcites of iowaite and woodallite

Jocelyn M. Bouzaid, Ray L. Frost,* and Wayde N. Martens

*Inorganic Materials Research Program, School of Physical and Chemical Sciences,
Queensland University of Technology, 2 George Street, Brisbane, GPO Box 2434,
Queensland 4001, Australia.*

Abstract

The thermal stability and thermal decomposition pathways for synthesized composite iowaite /woodallite have been determined using thermogravimetry analysis in conjunction with evolved gas mass spectrometry. Dehydration of the hydrotalcites occurred over a range of 56-70 °C. The first dehydroxylation step occurred at around 255 °C and, with the substitution of more iron (III) for chromium (III) this temperature increased to an upper limit of 312 °C. This trend was observed throughout all decomposition steps. The release of carbonate ions as carbon dioxide gas initialised at just above 300 °C and was always accompanied by loss of hydroxyl units as water molecules. The initial loss of the anion in this case the chloride ion was consistently observed to occur at about 450 °C with final traces evolved at 535 to 780 °C depending of the Fe:Cr ratio and was detected as HCl ($m/Z = 36$). Thus for this to occur, hydroxyl units must have been retained in the structure at temperatures upwards of 750 °C. Experimentally it was found difficult to keep CO₂ from reacting with the compounds and in this way the synthesized iowaite-woodallite series somewhat resembled the natural minerals.

Keywords: dehydration, dehydroxylation, hydrotalcite, iowaite, woodallite, thermogravimetric analysis

Introduction

There exists in nature a group of minerals based upon the brucite structure in which the divalent cation Mg²⁺ is replaced by a trivalent cation (Al³⁺, Fe³⁺, or Cr³⁺), resulting in a positive charge on the brucite-like surface. This positive charge is counterbalanced by anions held within the brucite layers. Hydrotalcites are layered double hydroxides (LDHs) and are fundamentally anionic clays. These clays are less well known than cationic clays like smectites. The structure of hydrotalcite can be derived from a brucite structure (Mg(OH)₂) in which e.g. Al³⁺ or Fe³⁺ (pyroaurite-sjögrenite) substitutes a part of the Mg²⁺. Further mixtures of these mineral phases with multiple anions in the interlayer are observed. When LDHs are synthesized any appropriate anion can be placed in the interlayer. This substitution creates a positive layer charge on the hydroxide layers, which is compensated by interlayer anions or anionic complexes [1, 2]. The hydrotalcite may be considered as a gigantic cation, which is counterbalanced by anions in the interlayer. In hydrotalcites a broad range of compositions are possible of the type $[M^{2+}_{1-x}M^{3+}_x(OH)_2][A^{n-}]_{x/n} \cdot yH_2O$, where M²⁺ and M³⁺ are the di- and trivalent cations in the octahedral positions within the hydroxide layers with x normally between 0.17 and 0.33. Aⁿ⁻ is an exchangeable interlayer anion [3].

* Author to whom correspondence should be addressed (r.frost@qut.edu.au)

In the hydrotalcites reevesite and pyroaurite, the divalent cations are Ni^{2+} and Mg^{2+} respectively with the trivalent cation being Fe^{3+} . For iowaite, the divalent cation is Mg^{2+} and the trivalent cation Fe^{3+} . Woodallite is like iowaite but simply has Cr^{3+} instead of Fe^{3+} . In these cases the chloride anion is the major interlayer counter anion. Of course when synthesizing hydrotalcites any anion may be used. Normally the hydrotalcite structure based upon takovite (Ni,Al) and hydrotalcite (Mg,Al) has basal spacings of $\sim 8.0 \text{ \AA}$ where the interlayer anion is carbonate. Slight differences in the d(003) spacing occurs when different anions are placed in the interlayer. In the case of iowaite and woodallite, the naturally occurring minerals contain carbonate as well as the chloride anions. These types of minerals are often formed as a result of the chemical degradation of crysotile. As such the minerals may be formed below the sea.

Thermal analysis using thermogravimetric techniques (TG) enables the mass loss steps, the temperature of the mass loss steps and the mechanism for the mass loss to be determined. Thermoanalytical methods provide a measure of the thermal stability of the hydrotalcite [4-6]. The iowaite-woodallite mineral series is of interest [7, 8]. Interest in the study of these hydrotalcites results from their potential use as catalysts, adsorbents and anion exchangers [9-13]. The reason for the potential application of hydrotalcites as catalysts rests with the ability to make mixed metal oxides at the atomic level, rather than at a particle level. Such mixed metal oxides are formed through the thermal decomposition of the hydrotalcite [14, 15]. One would expect that the potential application of hydrotalcites as catalysts will rest on reactions occurring on their surfaces. The significance of the formation of the mixed metal oxides is their importance as a transition material in the synthesis of catalysts. In this work we report the stability and thermal decomposition of the hydrotalcites iowaite and woodallite with chloride in the interlayer.

Experimental

Synthesis of hydrotalcite Minerals

Minerals such as iowaite and woodallite may be synthesized in the laboratory. The reason for using synthetic minerals as opposed to the natural minerals is that difficulties associate with multiple anions in the interlayer can be minimised. The Iowaite-Woodallite series was synthesized by the coprecipitation method. Two solutions were prepared using boiled ultra pure water: Solution 1 contained 2M NaOH while solution 2 contained 0.75M Mg^{2+} ($\text{MgCl}_2 \cdot 6\text{H}_2\text{O}$) and a combined 0.25M Fe^{3+} ($\text{FeCl}_3 \cdot 6\text{H}_2\text{O}$) and Cr^{3+} ($\text{CrCl}_3 \cdot 6\text{H}_2\text{O}$). That is, to synthesize $\text{Mg}_6(\text{Fe}_{0.5}\text{Cr}_{0.5})_2(\text{OH})_{16}\text{Cl}_2$, solution 2 contained 0.75M Mg^{2+} combined with 0.125M Fe^{3+} and 0.125M Cr^{3+} . Prior to the addition of the two solutions the sealed vessel was purged with nitrogen for 20 minutes. Solution 2 was added to solution 1 under vigorous stirring using a peristaltic pump set at $40\text{cm}^3 \text{ min}^{-1}$. The resulting gelatinous substance was again purged with nitrogen for a further 20 minutes and then washed three to four times via vacuum filtration with boiled ultra pure water at room temperature to remove residual salts. The composition of the minerals was checked using electron probe analysis, while the phase composition was verified using X-ray diffraction.

X-ray diffraction

X-Ray diffraction patterns were collected using a Philips X'pert wide angle X-Ray diffractometer, operating in step scan mode, with Co K_{α} radiation (1.78897 Å). Patterns were collected in the range 3 to 75° 2 θ with a step size of 0.02° and a rate of 1.2s per step. Samples were prepared in ethanol and placed on glass slides as thin films.

Thermal Analysis

Thermal decompositions of the hydrotalcites, woodallite and iowaite and their composite mixtures were carried out in a TA® Instruments incorporated high-resolution thermogravimetric analyzer (series Q500) in a flowing nitrogen atmosphere (80 cm³/min). Approximately 50mg of sample was heated in an open platinum crucible at a rate of 2.0 °C/min up to 1000°C. The TGA instrument was coupled to a Balzers (Pfeiffer) mass spectrometer for gas analysis. Several gases (and isotopic analogues) and their ionic fragments were analysed including: Cl₂, CO, CO₂, HCl and H₂O. Mass/charge ratios were measured for example H₂O is 18/1.

Results and discussion

X-ray diffraction

The XRD patterns of the iowaite-woodallite series are shown in Figure 1a as is the reference patterns of iowaite (020-0500) and woodallite (053-1185). The d(003) spacing generally increases with the inclusion of more chromium and hence less iron. However, interestingly the spacing for a pure iron sample is larger than the Fe_{0.8}Cr_{0.2} and similarly the pure chromium specimen has a spacing smaller than that of the Fe_{0.2}Cr_{0.8} mixture. This suggests that the trends exhibited by the mixtures are not simply an interpolation of the two end members but in fact, the inclusion of small amounts of iron and chromium introduce a new maximum and minimum outside the limits of the pure sample. For future work it would be interesting to synthesize mixtures with 5, 10, 15 % substitutions and hence observe the effects on the d(003) spacing.

The XRD of the thermal decomposition products along with the reference is shown in Figure 1b. This figure shows that all mixtures decompose into MgO (045-0946) and the spinel which in this case is a combination of MgFe₂O₄ (088-1942) and MgCr₂O₄ (010-0351). This conclusion correlates well with the decomposition mechanism for each mixture and is illustrated by a mixed spinel formula Mg(Fe_xCr_{1-x})O₄. Table 1 shows the calculations of the X-ray diffracting crystallite size as a function of composition. The size varies from 11.66 nm for iowaite to 3.73 nm for woodallite. The crystallite size is larger for those hydrotalcites with higher Fe content.

EDAX analysis

The results of the EDX analyses are summarised in Table 2. The Table shows the Fe/Cr ratios, the theoretical formula and the averaged results from EDX analyses. The calculated formula of the hydrotalcite is given in column 3. The formulae are

worked out in terms of charge balance with the reference point taken as 16 OH⁻ units. The remaining positive charge from the cations was then counterbalanced with Cl⁻ and CO₃²⁻ units using the EDX and thermal information.

Thermal analysis


Thermal analysis can provide fundamental understanding of the behaviour of hydrotalcites. In particular the temperature at which decomposition takes place and the measurement of the thermal stability of the decomposition products. This is illustrated in Figures 2a-5a which show the TG and DTG plots of the mixed hydrotalcites of iowaite and woodallite. The TG and DTG curves for iowaite-woodallite series with Fe:Cr = 0.2:0.8, 0.4:0.6, 0.6:0.4; 0.8:0.2 are shown. Typical ion current curves for the evolved gases are shown in Figures 2b-5b. Figures 2 show the results for an Fe:Cr ratio of 0.2:0.8; Figure 3 Fe:Cr ratio of 0.4:0.6; Figure 4 Fe:Cr ratio of 0.6:0.8; Figure 5 Fe:Cr ratio of 0.8:0.2.

All TG curves of the iowaite-woodallite compounds show a mass loss around 56-70 °C. Dehydroxylation occurred around 255 °C for the iron (III) rich LDHs and increased to 312 °C as more chromium (III) substituted the iron. This trend was observed throughout all decomposition steps, therefore indicating that iron (III) rich hydrotalcites were more stable than those with more chromium (III). The releases of carbonate ions as carbon dioxide gas ($m/Z = 44$) commenced at about 300 °C and was always accompanied by loss of hydroxyl units as water molecules ($m/Z = 17$ and $m/Z = 18$). Both isotopes of Cl⁻ ($m/Z = 35$ and $m/Z = 37$) were analysed and subsequently HCl ($m/Z = 36$ and $m/Z = 38$) was scouted. The initial loss of the interlayer anion (Cl⁻) was consistently observed to occur at about 450 °C with final traces evolved between 535 to 780 °C depending of the Fe:Cr ratio and was detected as predominately HCl ($m/Z = 36$). Thus for this to occur, hydroxyl units must have been retained in the structure at temperatures upwards of 750 °C.

Mechanism for the decomposition of iowaite-woodallite mixture with 0.2:0.8 ratio of Fe(III): Cr(III) with chloride anion in the interlayer


The following steps describe the thermal decomposition of the chloride-carbonate anions in the interlayer (Figure 2a and 2b).

Step 1 at 62 °C




This initial step shows a loss of water at 62 °C and is the only dehydration step for the decomposition. There is a 15.97 % mass loss at this step. This mass depletion is accounted for by the loss of 6.15 moles of water.

Step 2 at 312 °C




This step shows a 20.32% mass loss and represents the first of the dehydroxylation steps. At this temperature 14.2 moles of hydroxyl ions are lost in the form of 7.1 moles of water. Also at this stage the hydrotalcite changes to a higher oxidation state (i.e. the ratio of Mg/Cr decreases). This is caused by the commencement of the formation of the oxide (most likely MgO). This transition is expected for all the synthetic hydrotalcites discussed in this study and usually takes place between 250-320 °C. Unfortunately the exact proportion of MgO is not known but its formation at this temperature has been verified by X-ray diffraction .

Step 3 at 390-450 °C



This step represents another dehydroxylation step where at this temperature 0.29 moles of water are liberated. Traces of carbon dioxide are also lost in this step. This step accounts for the major loss of the chloride ions in the form of 0.89 moles of hydrogen chloride. This results from the carbonate impurity in the interlayer. There is a 5.58 % mass loss at this temperature.

Step 4 at 550 °C




This final step in the decomposition of synthetic iowaite-woodallite mixture and represents the loss of the rest of the chloride ions in the form of 0.33 moles of hydrogen chloride which, accounts for 1.71% mass loss. The products of the thermal decomposition are a spinel $0.94\text{Mg}(\text{Fe}_{0.2}\text{Cr}_{0.8})_2\text{O}_4$ and 5.18MgO . Thus the total mass loss equates to approximately 44% and occurred over 4 steps.

Mechanism for the decomposition of iowaite-woodallite mixture with 0.42:0.58 ratio of Fe(III): Cr(III) with chloride anion in the interlayer


The following steps describe the thermal decomposition of the chloride-carbonate anions in the interlayer (Figures 3a and 3b).

Step 1 at 67°C




Dehydration occurs at 67 °C with a 17.81% mass loss.

Step 2 at 265°C




At this temperature there is a 3.65% mass loss associated with dehydroxylation.

Step 3 at 311°C




At this temperature there is a 15.24% mass loss. This decomposition step is associated with dehydroxylation and loss of carbonate.

Step 4 at 370-500°C




This decomposition step is associated with loss of the interlayer anion which evolves as HCl with a 5.16% mass loss.

Step 5 at 615°C



There is a 2.03% mass loss at this step associated with the evolution of HCl

Step 6 at 780°C




At this temperature there is a 0.88% mass loss associated with the evolution of HCl. The final products are the spinel $0.88\text{Mg}(\text{Fe}_{0.42}\text{Cr}_{0.58})_2\text{O}_4$ and 5.37MgO . The total mass loss was 45% and took place over 6 steps.

Mechanism for the decomposition of iowaite-woodallite mixture with 0.6:0.4 ratio of Fe(III): Cr(III) with chloride anion in the interlayer


The following steps describe the thermal decomposition of the chloride-carbonate anions in the interlayer.

Step 1 at 65°C




For this hydrotalcite there is a 16.43% mass loss at 65 °C associated with dehydration.

Step 2 at 254°C




There is a 4.57% mass loss at 254 °C associated with dehydroxylation

Step 3 at 305°C




At 305 °C there is a 15.0% mass loss attributed to the loss of carbon dioxide and water from the hydroxyl units.

Step 4 at 371-490°C

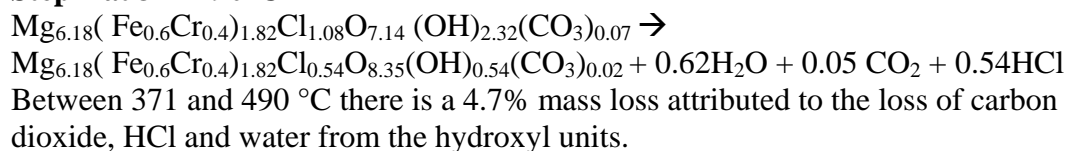


Step 5 at 575°C



At 575 °C there is a 1.7% mass loss attributed to the loss of carbon dioxide and HCl.

Step 6 at 760°C




There is a 1.22% mass loss associated with this step. The final products are the spinel $0.91\text{Mg}(\text{Fe}_{0.6}\text{Cr}_{0.4})_2\text{O}_4$ and 5.27MgO . The total mass loss was just under 44% and occurred over a series of 6 steps.

Mechanism for the decomposition of iowaite-woodallite mixture with 0.8:0.2 ratio of Fe(III): Cr(III) with chloride anion in the interlayer


The following steps describe the thermal decomposition of the chloride-carbonate anions in the interlayer (Figure 2a and 2b).

Step 1 at 59 °C




This initial step shows a loss of water at 59 °C and is the only dehydration step for the decomposition. There is a 15.17 % mass loss at this step. This mass depletion is accounted for by the loss of 5.84 moles of water.

Step 2 at 255 °C




This step shows a 5.05% mass loss and represents the first of the dehydroxylation steps. At this temperature 3.92 moles of hydroxyl ions are lost in the form of 1.96 moles of water.

Step 3 at 308 °C




This step represents another dehydroxylation step where at this temperature 1.07 moles of water are liberated. Traces of carbon dioxide are also lost in this step. This results from the carbonate impurity in the interlayer. There is a 3.70 % mass loss at this temperature.

Step 4 at 329 °C




At this temperature both carbon dioxide and hydroxide are liberated. In this step the last traces of carbon dioxide are lost. There is a total of 13.68% mass loss at this temperature.

Step 5 at 450 °C



At this temperature both water and hydrogen chloride are given off. It is here where the number of hydroxyl moles equals that of chloride ions. This step accounts for 2.23% mass loss.

Step 6 at 535 °C



This final step in the decomposition of synthetic iowaite-woodallite mixture and represents the loss of the rest of the chloride ions in the form of 0.56 moles of hydrogen chloride which, accounts for 2.89% mass loss. The products of the thermal decomposition are a spinel $\text{Mg}(\text{Fe}_{0.8}\text{Cr}_{0.2})_2\text{O}_4$ and 5.01MgO. It was found that the total mass loss for this mechanism was about 43% and occurred over 6 steps.

Conclusions

Thermogravimetry in conjunction with evolved gas mass spectrometry has been used to study the thermal decomposition of a series of a new intermediate compound of synthetic iowaite and woodallite. In this work a sample of the composite mineral with minimal carbonate was synthesized but was found to still contain small amounts of carbonate and therefore a less than expected number of chloride ions per unit cell. It was found that the total mass loss for all intermediates was about 43-45% and the decomposition product was periclase (MgO) and a mixed spinel of $\text{Mg}(\text{Fe}_x\text{Cr}_{1-x})_2\text{O}_4$. From these results it seems that the thermal stability of the synthetic mineral increased as the content of iron increased. This was evident in the rise in temperature of each step as the series progressed from high chromium to low chromium content. Furthermore the decomposition mechanism for the composite with the least iron was finalised in four steps while those with higher ratios of iron to chromium had a more complex mechanism with six steps.

Acknowledgements

The financial and infra-structure support of the Queensland University of Technology Inorganic Materials Research Program of the School of Physical and Chemical Sciences is gratefully acknowledged. The Australian Research Council (ARC) is thanked for funding the thermal analysis facility.

References

- [1]. R. M. Taylor, *Clay Minerals* 17 (1982) 369.
- [2]. H. F. W. Taylor, *Mineralogical Magazine and Journal of the Mineralogical Society (1876-1968)* 37 (1969) 338.
- [3]. H. C. B. Hansen and C. B. Koch, *Applied Clay Science* 10 (1995) 5.
- [4]. R. L. Frost and K. L. Erickson, *J. Therm. Anal. Calorim.* 76 (2004) 217.
- [5]. R. L. Frost and M. L. Weier, *Thermochim. Acta* 409 (2004) 79.
- [6]. R. L. Frost, M. L. Weier and K. L. Erickson, *J. Therm. Anal. Calorim.* 76 (2004) 1025.
- [7]. R. Allmann and J. D. H. Donnay, *American Mineralogist* 54 (1969) 296.
- [8]. T. Moroz, L. Razvorotneva, T. Grigorieva, M. Mazurov, D. Arkhipenko and V. Prugov, *Applied Clay Science* 18 (2001) 29.
- [9]. J. Theo Klopogge and R. L. Frost, *Applied Catalysis, A: General* 184 (1999) 61.
- [10]. A. Alejandre, F. Medina, X. Rodriguez, P. Salagre, Y. Cesteros and J. E. Sueiras, *Appl. Catal., B* 30 (2001) 195.
- [11]. J. Das and K. Parida, *React. Kinet. Catal. Lett.* 69 (2000) 223.
- [12]. S. H. Patel, M. Xanthos, J. Greci and P. B. Klepak, *J. Vinyl Addit. Technol.* 1 (1995) 201.
- [13]. V. Rives, F. M. Labajos, R. Trujillano, E. Romeo, C. Royo and A. Monzon, *Appl. Clay Sci.* 13 (1998) 363.
- [14]. F. Rey, V. Fornes and J. M. Rojo, *J. Chem. Soc., Faraday Trans.* 88 (1992) 2233.
- [15]. M. Valcheva-Traykova, N. Davidova and A. Weiss, *J. Mater. Sci.* 28 (1993) 2157.

List of Figures

Figure 1 X-ray diffraction patterns of iowaite-woodallite with Fe/Cr ratios of 1:0,0.8:0.2,0.6:0.4, 0.5:0.5, 0.4:0.6, 0.2:0.8 and 0.0:1.0

Figure 2a TG and DTG curves for the hydrotalcite of composition Fe/Cr 0.2:0.8

Figure 2b Ion current curves for the hydrotalcite of composition Fe/Cr 0.2:0.8

Figure 3a TG and DTG curves for the hydrotalcite of composition Fe/Cr 0.4:0.6

Figure 3b Ion current curves for the hydrotalcite of composition Fe/Cr 0.4:0.6

Figure 4a TG and DTG curves for the hydrotalcite of composition Fe/Cr 0.6:0.4

Figure 4b Ion current curves for the hydrotalcite of composition Fe/Cr 0.6:0.4

Figure 5a TG and DTG curves for the hydrotalcite of composition Fe/Cr 0.8:0.2

Figure 5b Ion current curves for the hydrotalcite of composition Fe/Cr 0.8:0.2

List of Tables

Table 1 Particle size as a function of composition of the iowaite-woodallite hydrotalcites

Table 2 EDX analyses of the iowaite-woodallite hydrotalcites

Table 3 Results of the thermal decomposition of iowaite-woodalite hydrotalcites

COMPOUND	CRYSTALLITE SIZE (nm)
IOWAITE	11.66
Fe_{0.8}Cr_{0.2}	6.68
Fe_{0.6}Cr_{0.4}	5.26
Fe_{0.4}Cr_{0.6}	3.90
Fe_{0.2}Cr_{0.8}	3.73
WOODALLITE	3.73

Table 1 Particle size as a function of composition of the iowaite-woodallite hydroxalcsites

Ratios from EDX averaged from two different sites.

COMPOUND	THEORETICAL FORMULA	CHARGE BALANCED FORMULA
IOWAITE	$\text{Mg}_6\text{Fe}_2\text{Cl}_2(\text{OH})_{16}$	$\text{Mg}_{6.27}\text{Fe}_{1.73}\text{Cl}_{1.07}(\text{OH})_{16}(\text{CO}_3)_{0.33}$
Fe0.8Cr0.2	$\text{Mg}_6(\text{Fe}_{0.8}\text{Cr}_{0.2})_2\text{Cl}_2(\text{OH})_{16}$	$\text{Mg}_{6.01}(\text{Fe}_{0.8}\text{Cr}_{0.2})_{1.99}\text{Cl}_{0.89}(\text{OH})_{16}(\text{CO}_3)_{0.55}$
Fe0.6Cr0.4	$\text{Mg}_6(\text{Fe}_{0.6}\text{Cr}_{0.4})_2\text{Cl}_2(\text{OH})_{16}$	$\text{Mg}_{6.18}(\text{Fe}_{0.6}\text{Cr}_{0.4})_{1.82}\text{Cl}_{1.08}(\text{OH})_{16}(\text{CO}_3)_{0.37}$
Fe0.4Cr0.6	$\text{Mg}_6(\text{Fe}_{0.4}\text{Cr}_{0.6})_2\text{Cl}_2(\text{OH})_{16}$	$\text{Mg}_{6.25}(\text{Fe}_{0.42}\text{Cr}_{0.58})_{1.75}\text{Cl}_{1.15}(\text{OH})_{16}(\text{CO}_3)_{0.30}$
Fe0.2Cr0.8	$\text{Mg}_6(\text{Fe}_{0.2}\text{Cr}_{0.8})_2\text{Cl}_2(\text{OH})_{16}$	$\text{Mg}_{6.12}(\text{Fe}_{0.2}\text{Cr}_{0.8})_{1.88}\text{Cl}_{1.22}(\text{OH})_{16}(\text{CO}_3)_{0.33}$
WOODALLITE	$\text{Mg}_6\text{Cr}_2\text{Cl}_2(\text{OH})_{16}$	$\text{Mg}_{6.28}\text{Cr}_{1.72}\text{Cl}(\text{OH})_{16}(\text{CO}_3)_{0.36}$

Table 2 Ratios from EDX averaged from two different sites.

	Step 1			Step 2			Step 3			Step 4			Step 5			Step 6		
Iowaite-Woodallite	% mass loss	Temp (°C)	Species Lost	% mass loss	Temp (°C)	Species Lost	% mass loss	Temp (°C)	Species Lost	% mass loss	Temp (°C)	Species Lost	% mass loss	Temp (°C)	Species Lost	% mass loss	Temp (°C)	Species Lost
Fe _{0.2} Cr _{0.8}	15.97	62	H ₂ O	20.32	312	OH ⁻ / CO ₃	5.58	390 - 450	OH ⁻ / CO ₃ /Cl ⁻	1.71	550	Cl ⁻ /OH ⁻	*	*	*	*	*	*
Fe _{0.42} Cr _{0.58}	17.81	67	H ₂ O	3.65	265	OH ⁻	15.24	311	OH ⁻ / CO ₃	5.16	370 - 500	OH ⁻ / CO ₃ /Cl ⁻	2.03	615	Cl ⁻ /OH ⁻	0.88	780	Cl ⁻ /OH ⁻
Fe _{0.6} Cr _{0.4}	16.43	65	H ₂ O	4.57	254	OH ⁻	15.00	305	OH ⁻ / CO ₃	4.70	371- 490	OH ⁻ / CO ₃ /Cl ⁻	1.70	575	OH ⁻ / CO ₃ /Cl ⁻	1.22	760	Cl ⁻ /OH ⁻
Fe _{0.8} Cr _{0.2}	15.17	59	H ₂ O	5.05	255	OH ⁻	3.70	308	OH ⁻ / CO ₃	13.68	329	OH ⁻ / CO ₃	2.23	450	Cl ⁻ /OH ⁻	2.89	535	Cl ⁻ /OH ⁻

Table 3 Results of the thermal decomposition of iowaite-woodalite hydrotalcites

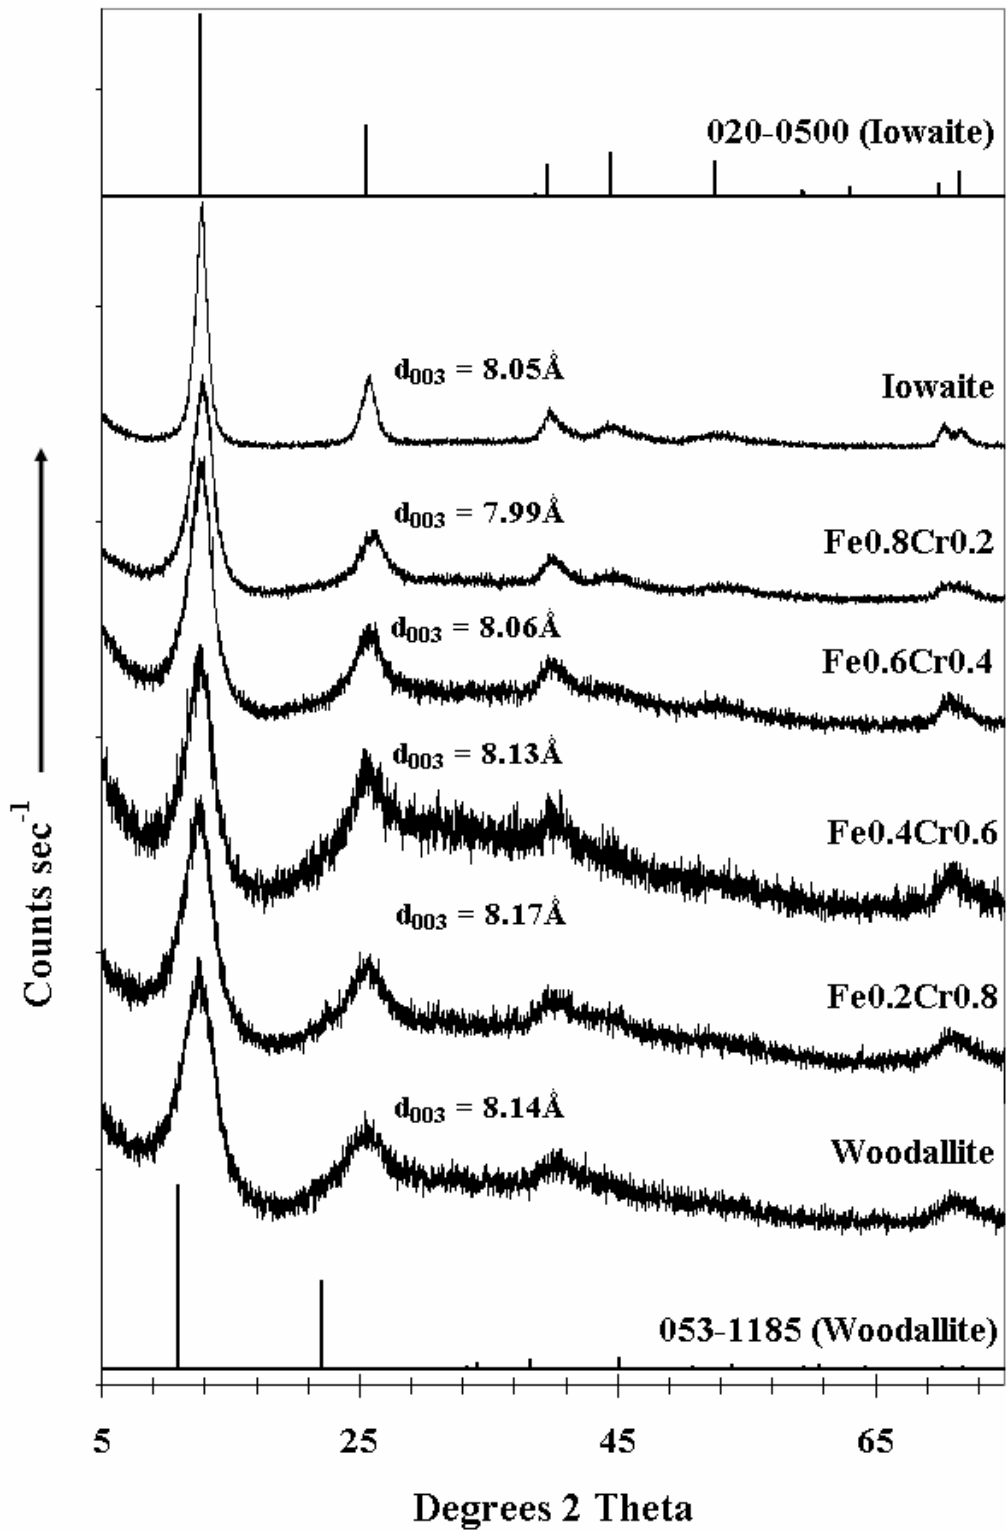


Figure 1a

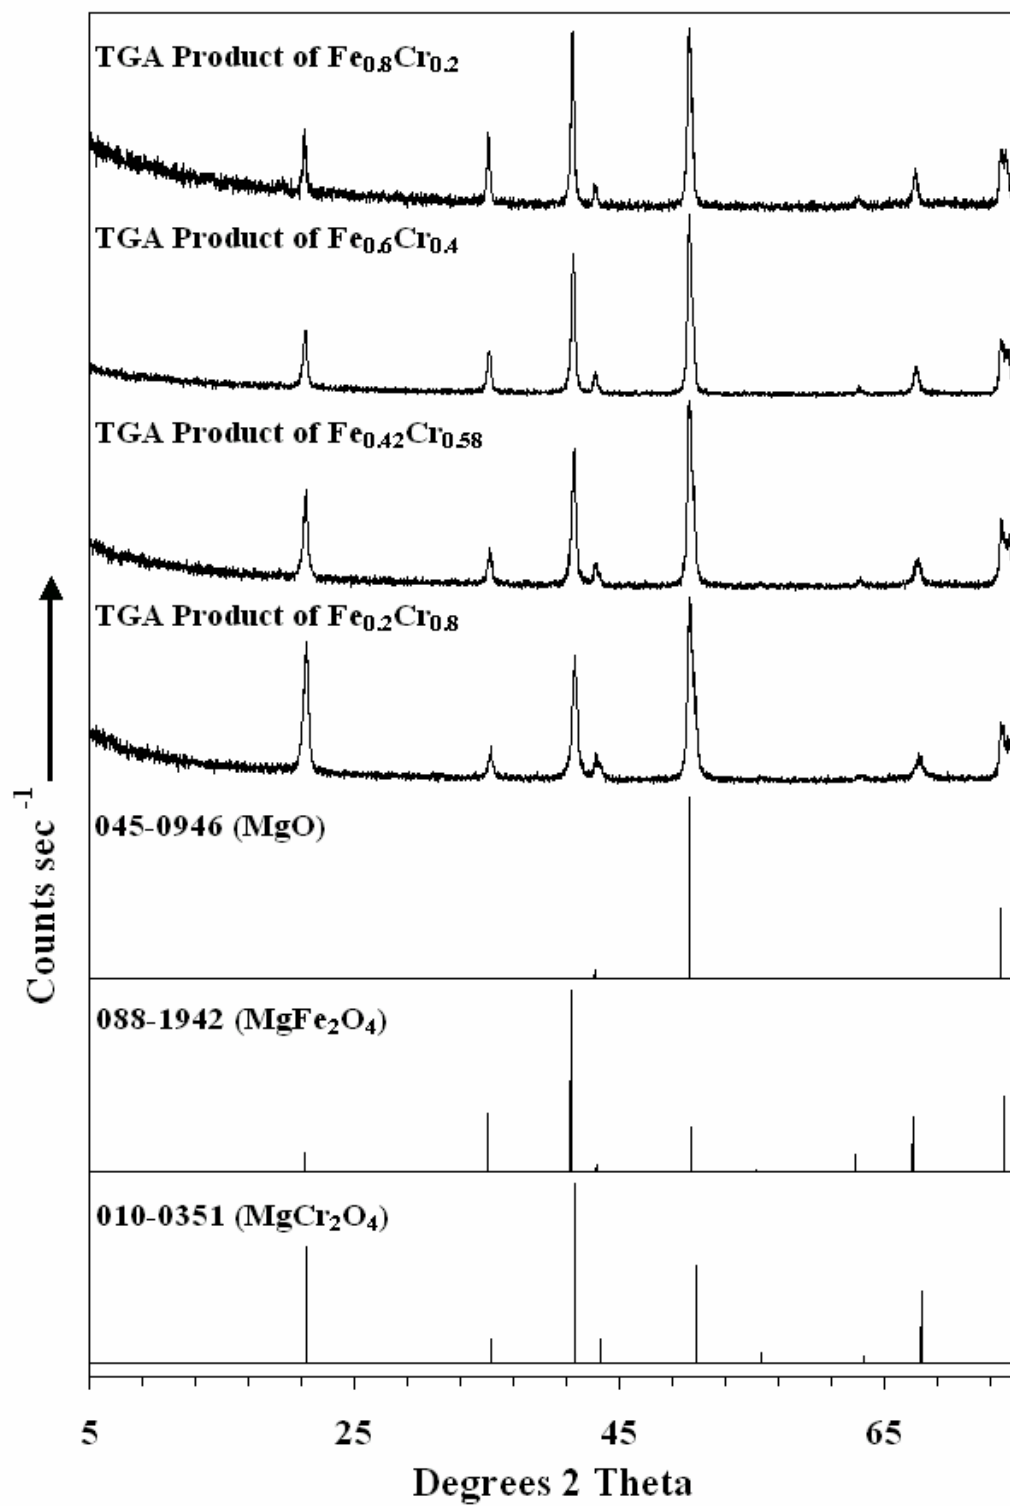


Figure 1b

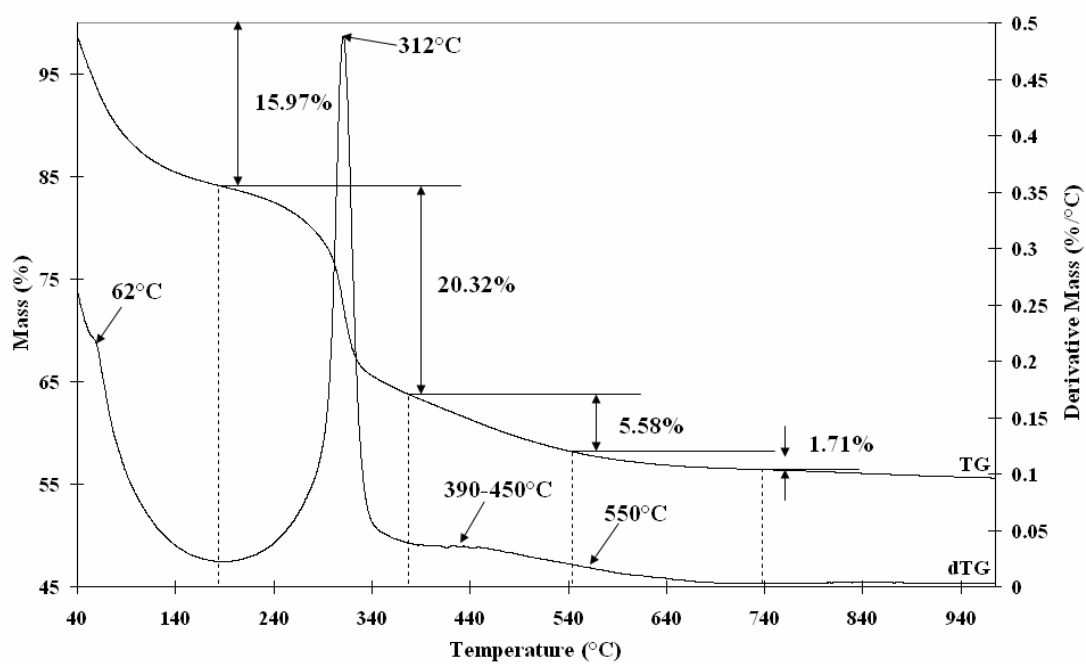


Figure 2a Fe₂Cr₈

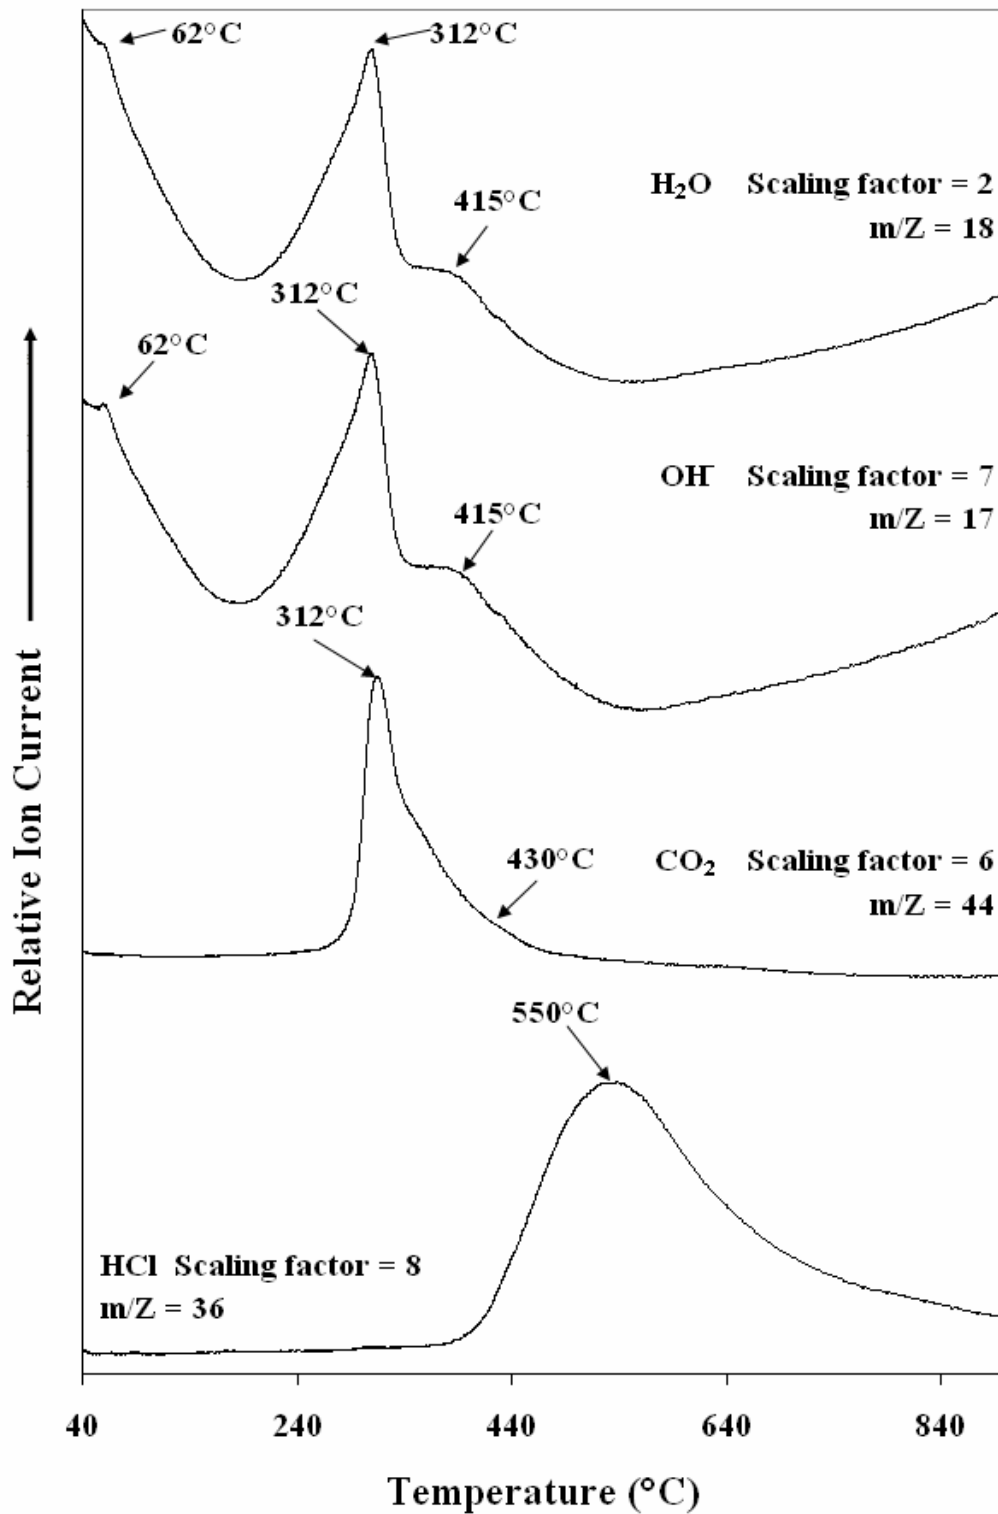


Figure 2b Fe₂Cr₈

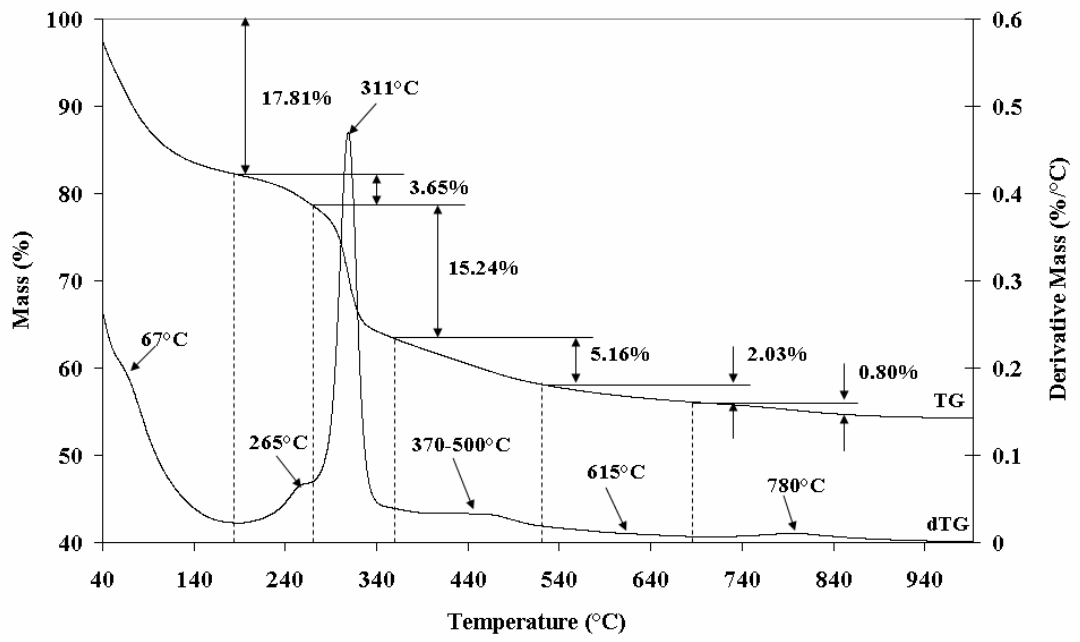


Figure 3a Fe₄Cr₆

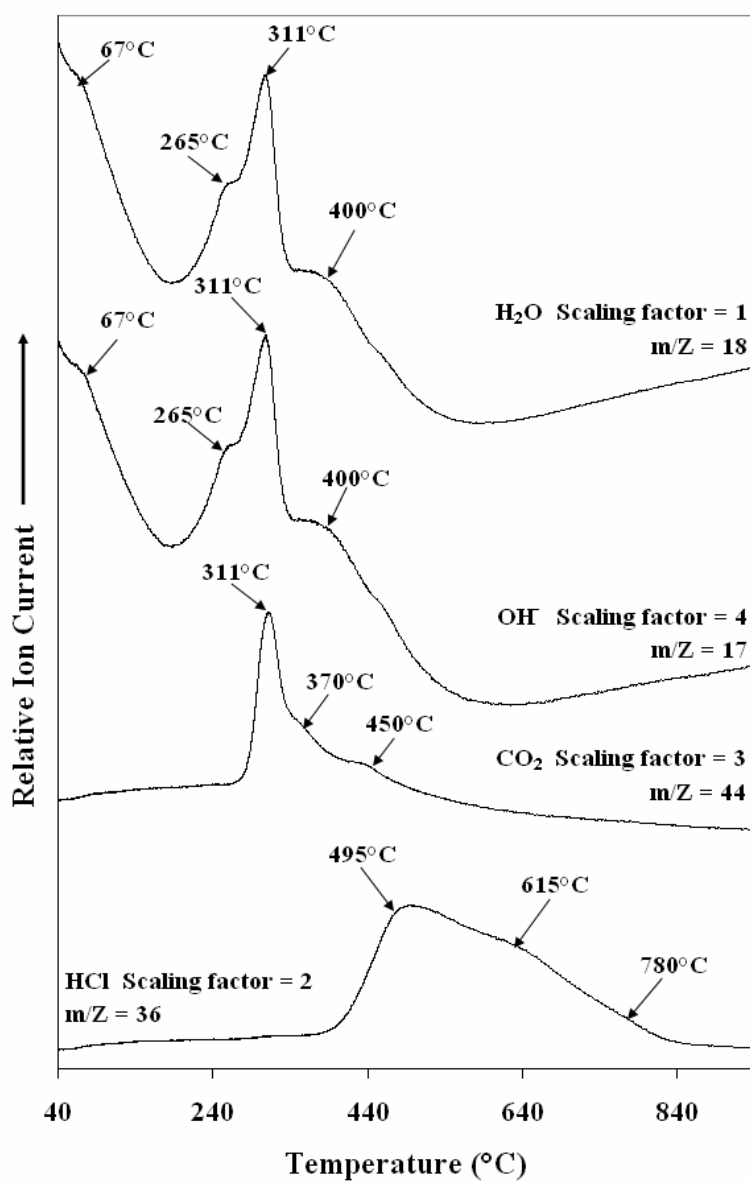


Figure 3b

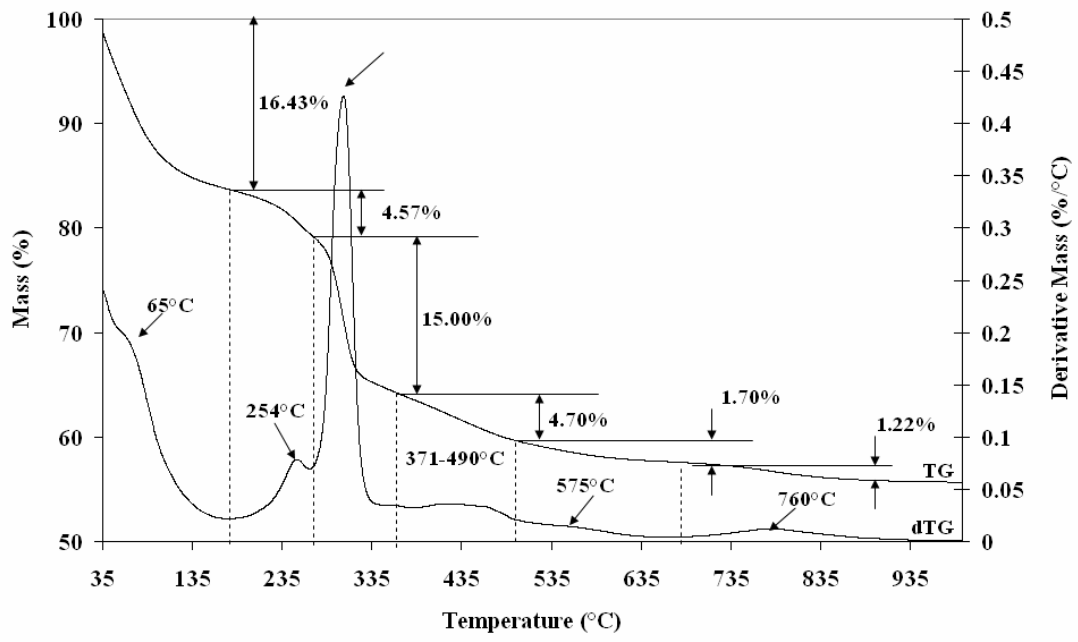


Figure 4a Fe₆Cr₄

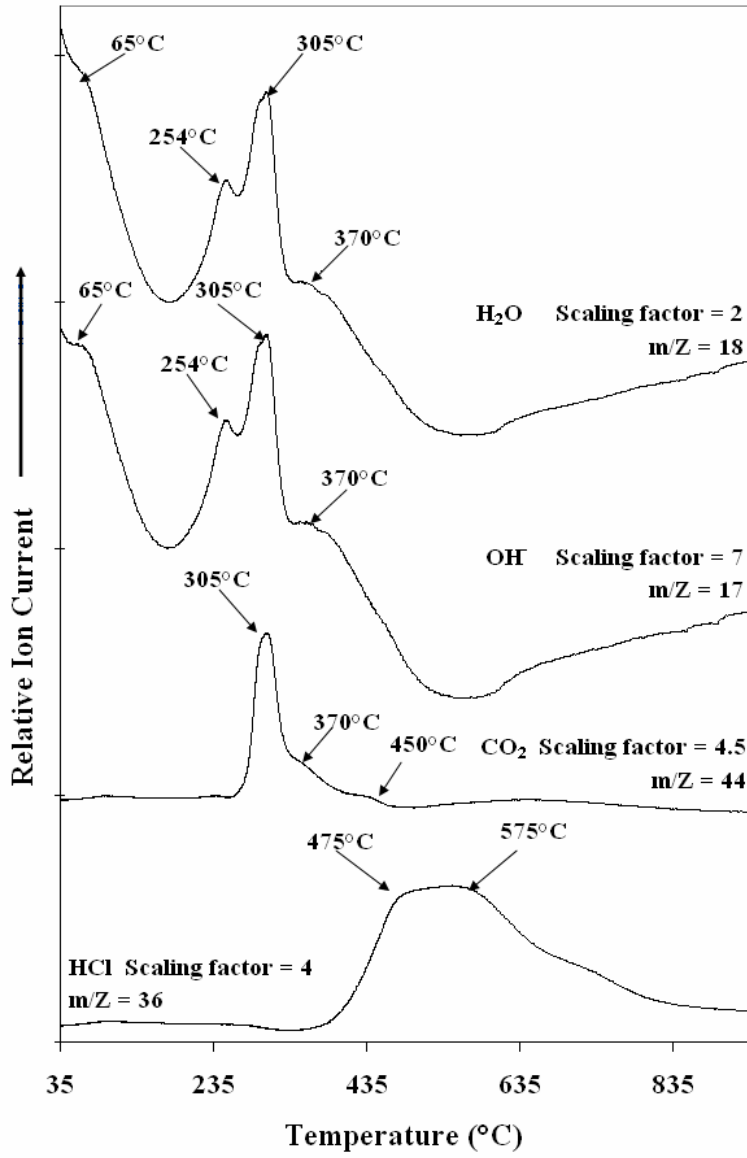


Figure 4b Fe6Cr4

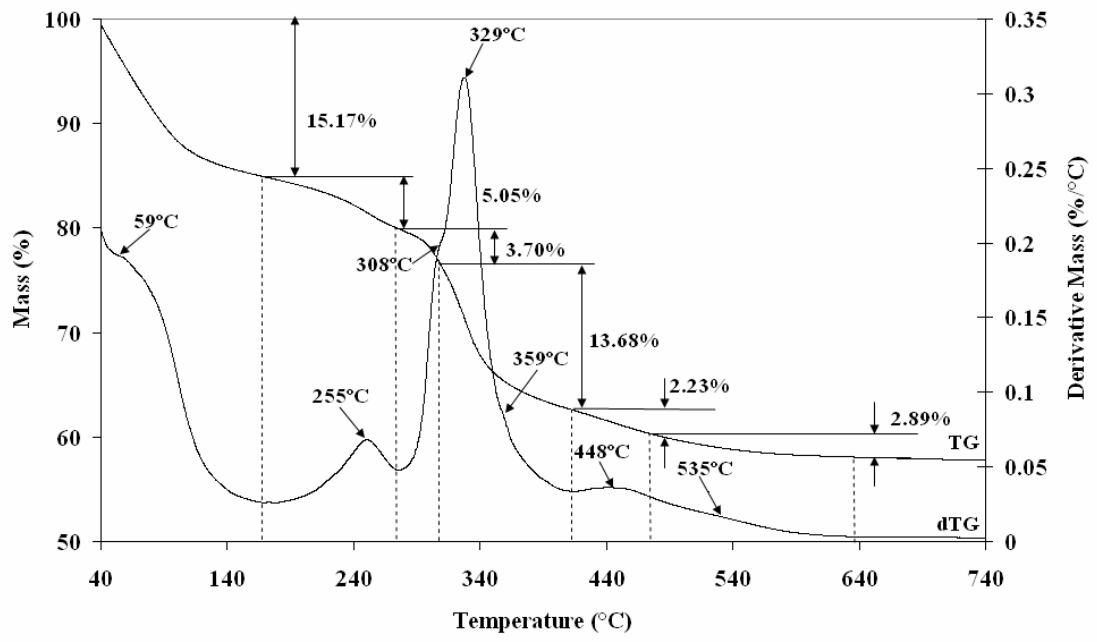


Figure 5a Fe₈Cr₂

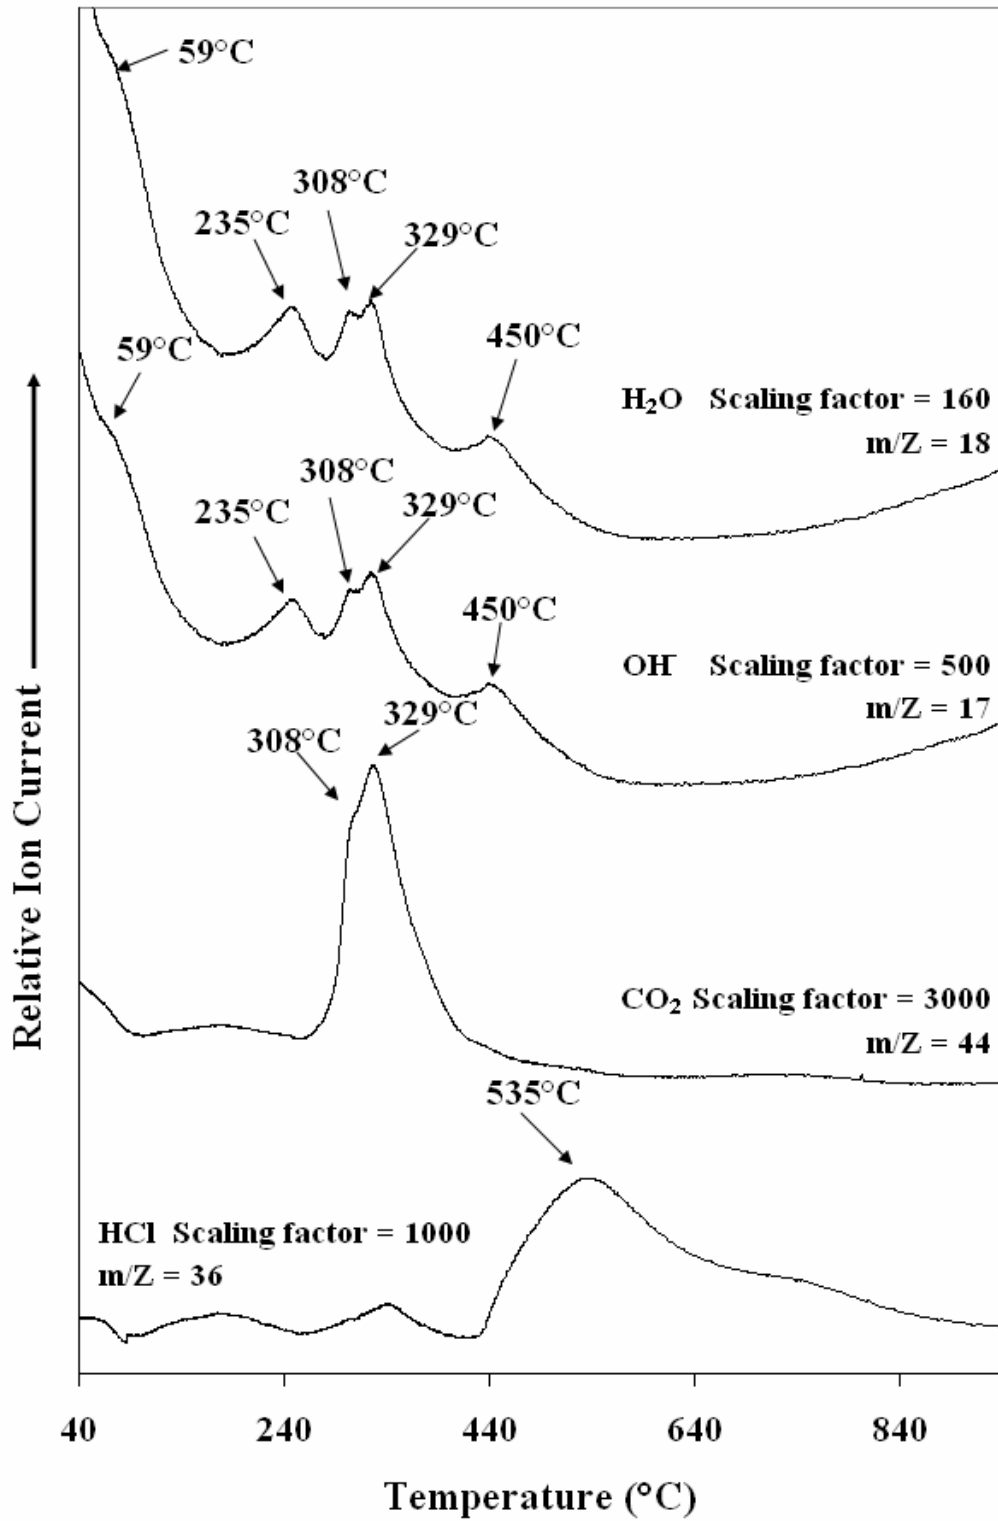


Figure 5b Fe₈Cr₂