

**ACCEPTED MANUSCRIPT**

# Thermal transport in epitaxial Si<sub>1-x</sub>Gex alloy nanowires with varying composition and morphology

To cite this article before publication: Alexandros El Sachat *et al* 2017 *Nanotechnology* in press <https://doi.org/10.1088/1361-6528/aa9497>

## Manuscript version: Accepted Manuscript

Accepted Manuscript is “the version of the article accepted for publication including all changes made as a result of the peer review process, and which may also include the addition to the article by IOP Publishing of a header, an article ID, a cover sheet and/or an ‘Accepted Manuscript’ watermark, but excluding any other editing, typesetting or other changes made by IOP Publishing and/or its licensors”

This Accepted Manuscript is © 2017 IOP Publishing Ltd.

During the embargo period (the 12 month period from the publication of the Version of Record of this article), the Accepted Manuscript is fully protected by copyright and cannot be reused or reposted elsewhere.

As the Version of Record of this article is going to be / has been published on a subscription basis, this Accepted Manuscript is available for reuse under a CC BY-NC-ND 3.0 licence after the 12 month embargo period.

After the embargo period, everyone is permitted to use copy and redistribute this article for non-commercial purposes only, provided that they adhere to all the terms of the licence <https://creativecommons.org/licenses/by-nc-nd/3.0>

Although reasonable endeavours have been taken to obtain all necessary permissions from third parties to include their copyrighted content within this article, their full citation and copyright line may not be present in this Accepted Manuscript version. Before using any content from this article, please refer to the Version of Record on IOPscience once published for full citation and copyright details, as permissions will likely be required. All third party content is fully copyright protected, unless specifically stated otherwise in the figure caption in the Version of Record.

View the [article online](#) for updates and enhancements.

# Thermal transport in epitaxial $\text{Si}_{1-x}\text{Ge}_x$ alloy nanowires with varying composition and morphology

A El Sachat<sup>1,2</sup>, J S Reparaz<sup>3</sup>, J Spiece<sup>4</sup>, M I Alonso<sup>3</sup>, A R Goñi<sup>3,5</sup>, M Garriga<sup>3</sup>, P O Vaccaro<sup>3</sup>, M R Wagner<sup>1</sup>, O V Kolosov<sup>4</sup>, C M Sotomayor Torres<sup>1,5</sup> and F Alzina<sup>1</sup>

<sup>1</sup>Catalan Institute of Nanoscience and Nanotechnology (ICN2), CSIC and BIST, Campus UAB, Bellaterra, 08193 Barcelona, Spain

<sup>2</sup>Dept. of Physics, Universitat Autònoma de Barcelona, Campus UAB, 08193 Bellaterra (Barcelona), Spain.

<sup>3</sup>Institut de Ciència de Materials de Barcelona (ICMAB-CSIC), Campus de la UAB, 08193 Bellaterra, Spain.

<sup>4</sup>Physics Department, Lancaster University, Lancaster, LA1 4YB, United Kingdom.

<sup>5</sup>ICREA, Passeig Lluís Companys 23, 08010 Barcelona, Spain.

E-mail: [alexandros.elsachat@icn2.cat](mailto:alexandros.elsachat@icn2.cat)

**Abstract.** We report on structural, compositional, and thermal characterization of self-assembled in-plane epitaxial  $\text{Si}_{1-x}\text{Ge}_x$  alloy nanowires grown by molecular beam epitaxy on Si (001) substrates. The thermal properties were studied by means of scanning thermal microscopy, while the microstructural characteristics, the spatial distribution of the elemental composition of the alloy nanowires and the sample surface were investigated by transmission electron microscopy and energy dispersive x-ray microanalysis. We provide new insights regarding the morphology of the in-plane nanostructures, their size-dependent gradient chemical composition, and the formation of a 5 nm thick wetting layer on the Si substrate surface. In addition, we directly probe heat transfer between a heated scanning probe sensor and  $\text{Si}_{1-x}\text{Ge}_x$  alloy nanowires of different morphological characteristics and we quantify their thermal resistance variations. We correlate the variations of the thermal signal to the dependence of the heat spreading with the cross-sectional geometry of the nanowires using finite element method simulations. With this method we determine the thermal conductivity of the nanowires with values in the range of 2-3  $\text{Wm}^{-1}\text{K}^{-1}$ . These results provide valuable information in growth processes and show the great capability of the scanning thermal microscopy technique in ambient environment for nanoscale thermal studies, otherwise not possible using conventional techniques.

**Keywords:**  $\text{Si}_{1-x}\text{Ge}_x$  nanowires, SThM, thermal properties, TEM-EDX, thermal imaging

## 1. Introduction

One-dimensional  $\text{Si}_{1-x}\text{Ge}_x$  semiconductor nanostructures have attracted enormous research interest due to their unique electronic properties and recently have been utilized in a wide range of applications, such as heterojunction bipolar transistors, strained Si com-

plementary metal-oxide-semiconductor (CMOS) devices [1, 2] nanoelectronics [2–5] and IR sensors [6]. Nanowire transistors with gate lengths of 5 nm have been produced in gate-all around configuration by scaling down the corresponding intrinsic nanowires (NWs) channel body [7, 8]. The continuous downscaling of semiconductor devices results in the

1 fabrication of devices with sub-micrometer feature  
2 sizes, where localized Joule heating becomes im-  
3 portant. The performance and the reliability of these  
4 devices are strongly connected to the efficient control  
5 of the thermal transport, thus, there is a need for a  
6 better understanding of the heat transfer mechanisms  
7 at the nanoscale. Towards this direction, new meas-  
8 urement techniques have been developed to character-  
9 ise thermally sub-micrometer features [9], while the  
10 key fabrication challenge to align and grow bottom-  
11 up NWs into complex patterns or structures still re-  
12 mains.

13  
14  
15 Recent studies reported new approaches to grow  
16 NWs with in-plane geometries into desired areas and  
17 along precise directions. The fabrication processes are  
18 performed either on metal substrates in arrays without  
19 using templates and catalysts [10, 11], or on semicon-  
20 ductor substrates [11–15] by adjusting the location of  
21 catalysts, offering the possibility of in situ fabrication  
22 of nanowire-based devices. In particular, in-plane  
23 assembled nanostructures target suitable geometry for  
24 integration on Si chips and CMOS architecture using  
25 planar microfabrication technology [16]. The compo-  
26 sition analysis of this kind of nanostructures is usually  
27 performed by micro-Raman spectroscopy [15, 17–19]  
28 and energy dispersive X-ray (EDX) analysis [20, 21].  
29 Although Raman spectroscopy is a fast and non-  
30 destructive technique to characterise nanostructures,  
31 there are some limitations, such as the lateral spatial  
32 resolution of about 300 nm, which does not allow  
33 discriminating composition inhomogeneities within,  
34 e.g. sub-300 nm nanostructures.

35  
36  
37  
38  
39  
40 Thermal transport in  $\text{Si}_{1-x}\text{Ge}_x$  NWs has been studied  
41 over the last decade both theoretically [22–29] and  
42 experimentally [25–28, 30, 31]. Most experimental  
43 studies focused on measuring the thermal conductivi-  
44 ty of individual  $\text{Si}_{1-x}\text{Ge}_x$  NWs with various Ge con-  
45 centrations and diameters using microfabricated sus-  
46 pended thermometer/heater platforms. Furthermore,  
47 recent studies even proved the existence of ballistic  
48 thermal conduction in  $\text{Si}_{1-x}\text{Ge}_x$  NWs with low thermal  
49 conductivity for a wide range of structural variations  
50 and alloy concentrations [32]. These results showed  
51 the significant potential of  $\text{Si}_{1-x}\text{Ge}_x$  NWs in thermoe-  
52 lectric applications. However, only few experimental  
53 studies have reported thermal transport on supported  
54  $\text{Si}_{1-x}\text{Ge}_x$  NWs or NWs embedded in a matrix material

55  
56  
57  
58  
59  
60  
[33, 34], which are more representative structures for  
many future NW-based applications. Here we report  
first a thorough investigation of structural, morpho-  
logical and chemical properties of in-plane epitaxial  
 $\text{Si}_{1-x}\text{Ge}_x$  alloy NWs by using high resolution trans-  
mission electron microscopy (TEM) measurements  
and EDX spectroscopy. Then, we report thermal  
transport results from the supported NWs using scan-  
ning thermal microscopy (SThM), by probing heat  
flux related signals between a heated scanning probe  
sensor and the investigated materials in contact with  
it. We estimate the dominant thermal resistive com-  
ponents contributing to the SThM signals during the  
heat exchange of the probe with the investigated  
nanostructures using finite element method (FEM)  
simulations and an analytical heat-spreading model,  
which allow us to determine the thermal conductivity  
of the NWs.

## 2. Materials and methods

### 2.1 Fabrication

The in-plane epitaxial  $\text{Si}_{1-x}\text{Ge}_x$  alloy NWs were grown  
by molecular beam epitaxy (MBE) on a Si (001) sub-  
strate using Au nanoparticles as catalyst. The growth  
method consists of a three-step process involving the  
deposition of 1 nm thick each Au and Si layers, the  
AuSi seeds formation by annealing these layers at 800  
°C and, finally, the formation of the  $\text{Si}_{1-x}\text{Ge}_x$  alloy by  
continuously supplying a Ge flux at 550 °C. More  
details about the fabrication process can be found  
elsewhere [13].

### 2.2 Morphology and composition

The sample surface was characterised ex situ by scan-  
ning electron microscopy (SEM) and atomic force  
microscopy (AFM), using a Quanta-200 ESEM-FEG  
and a MultiView SPM 4000 system from Nanonics,  
respectively. Then the cross-sectional morphology of  
 $\text{Si}_{1-x}\text{Ge}_x$  NWs was investigated using an Analytical  
Titan Low-base system in TEM and STEM modes.  
Ultra-high resolution images in scanning-transmission  
mode (HR-STEM) were also obtained. The elemental  
composition of the  $\text{Si}_{1-x}\text{Ge}_x$  alloy NWs and the sub-  
strate surface in a cross sectional plane was analysed  
using EDX elemental mapping, which provided spa-

tially resolved chemical composition variations within individual NWs and the substrate surface with 1 nm spatial resolution. A dual beam focused ion beam (FIB) (Dual Beam Helios 650 model) was used to prepare cross sections of specific NWs for TEM imaging by standard TEM lamella preparation [35].

### 2.3 Thermal analysis

The thermal measurements were performed using SThM in ambient environment (MultiView 4000 System, Nanonics). Our system is a multi-probe scanning probe microscopy (SPM) system, with an open architecture which allows flexible integration of different analytical tools. A platinum (Pt) dual wire resistive thermal probe in active mode was used for the thermal characterisation by applying high constant currents through the probe resistor to induce Joule heating. The thermal probe, which in this case is being used as the heater and thermometer, consists of two Pt wires stretched through a glass nanopipette (borosilicate glass) and fused together at their ends, creating a heating junction source. The mechanical interaction between the tip and the surface is controlled using a tuning fork in normal force mode with phase feedback, therefore, avoiding the laser-induced heating of the probe found in standard optical-based feedback systems. The principle of operation of SThM is based on the dependence of the electrical resistivity ( $\rho$ ) on temperature ( $T$ ), where the change in the electrical resistance is measured as a change in the output voltage ( $V_{out}$ ) across a Wheatstone bridge circuit. Therefore, changes in heat flux are monitored through the change of the probe resistance. More details regarding the experimental set-up and probe specifications can be found in the supporting information (SI).


## 3. Results and discussion

### 3.1 Morphology and composition

The surface morphology of the  $\text{Si}_{1-x}\text{Ge}_x$  alloy NWs was characterised by means of SEM, AFM and TEM. AFM images and topography profiles of the NW samples can be found in the SI. Figure 1(a) shows the SEM image of the AuSi clusters after annealing the 1 nm Au and Si films at 800 °C. A SEM image of as

grown  $\text{Si}_{1-x}\text{Ge}_x$  alloy NWs is presented in figure 1(b), where the variation of widths, heights and lengths is evident as well as the directional growth along the  $\langle 110 \rangle$  directions of the Si substrate. The width and length distribution of these NWs was measured to be  $w = (50 - 600) \text{ nm}$  and  $L = (0.3 - 4) \mu\text{m}$ , respectively.

Due to the excess Au content of the liquid SiGeAu droplets, Au rich particles at the end of the NWs are apparent after the MBE growth. These nanoparticles usually match the transversal size of the NWs, indicating that growth takes place following a vapour-liquid-solid (VLS) mechanism from the continuous supply of Ge flux at a fixed temperature of 550 °C. Previous investigations showed that at this temperature the diffusion length of Si atoms on the surface is quite small whereas for Ge atoms it is of the order of 1  $\mu\text{m}$  [15]. Initially, Ge atoms as supplied from the effusion cell are homogeneously distributed on the whole substrate surface. All atoms remain adsorbed (the sticking coefficient at 550 °C is 1 [36] and diffuse before they incorporate to the growing nanostructures. Most Ge atoms are preferentially collected by the liquid droplets and contribute to the NWs growth.

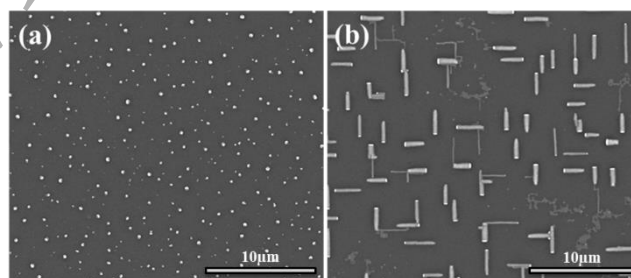

**Figure 1.** SEM images of (a) the AuSi seeds after 5 minutes annealing of the Au and Si layers at 800 °C and (b) the in plane epitaxial  $\text{Si}_{1-x}\text{Ge}_x$  alloy NWs after the Ge deposition by MBE.

Therefore, the fraction of atoms that does not reach a droplet must contribute to form a thin wetting layer (WL) on most of the substrate. Here, the term WL is used to denote rather planar growth morphology although its final characteristics are certainly influenced by the presence of Au. The existence of this WL could not be previously detected and is observed in the present work. The composition of individual NWs was found uniform along the length and non-uniform along the vertical cross section [13]. Even if the SiGe composition given by the VLS process should be well

determined, the behaviour of the diffusing Ge atoms obviously can modify both the average composition as well as the vertical composition profile, as is evaluated in this work.

The cross-sectional morphology and the chemical composition variations were investigated in four NWs of different dimensions by means of TEM-EDX. Figure 2 displays TEM images of the four  $\text{Si}_{1-x}\text{Ge}_x$  alloy NWs with decreasing width. From the TEM analysis, we found that the NWs have elongated shape, with the height ( $h$ ) roughly decreasing proportionally to the width ( $w$ ) according to a relation  $h(w) = \alpha \cdot w$ , where  $\alpha = (17 \pm 2.5)\%$ . This approximate geometrical relationship is related to the fact that the NWs are actually faceted with a  $\{001\}$  top facet and lateral sidewalls mostly consistent with  $\{115\}$  planes. The inclination of these planes is  $\Theta = 15.8$  degrees. Most of the width is given by the lateral sidewall geometry, that is, the proportionality constant  $\alpha$  is larger but close to  $(\tan \Theta)/2 = 0.14$ . In addition, we found that the NWs are partially buried with approximately half of the thickness embedded in the substrate. In fact, the NWs start to nucleate from droplets forming at dissolution pits. It was found that the droplets dissolve the substrate generating truncated inverted pyramids, with their lateral sides always oriented along  $\langle 110 \rangle$  directions of the substrate and sidewalls consistent with  $\{115\}$  planes, resulting in the approximate mirror-like appearance of the cross section and the preferential elongation direction of the NWs. Although the growth mode in these samples is not a purely epitaxial process of SiGe on Si, cross-sectional HR-STEM (see details in the SI) showed crystallinity and substrate dependent crystallographic orientation.

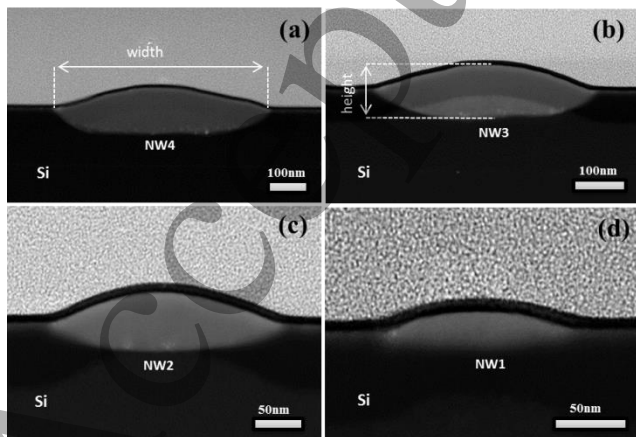


Figure 2. (a)-(d) Cross-section TEM images of the four


investigated  $\text{Si}_{1-x}\text{Ge}_x$  alloy NWs. Note that the scale bar is different in each image.

Table 1 summarizes the morphological characteristics of the four selected NWs. The perimeter/area ratio (P/A) accounts for the surface to volume ratio of the NWs. For the same NWs, we present in the next section SThM measurements which were performed before the composition analysis.

**Table 1.** Morphological characteristics of the four investigated  $\text{Si}_{1-x}\text{Ge}_x$  alloy NWs. The values inside the brackets represent the error of the measurement.

$\text{Si}_{1-x}\text{Ge}_x$	Width (nm)	Height (nm)	Length ( $\mu\text{m}$ )	P/A ( $\mu\text{m}^{-1}$ )
NW1	130 (5)	20(5)	1.30 (0.05)	0.14 (0.01)
NW2	225(5)	47(5)	1.35 (0.05)	0.057 (0.01)
NW3	420 (5)	82(5)	2.05(0.05)	0.032 (0.01)
NW4	585 (5)	105(5)	1.20 (0.05)	0.023 (0.01)

Having discussed the morphology of the NWs, we move to the chemical composition analysis of the sample. EDX spectra and elemental chemical maps revealed the existence of Si, Ge and Au both on the sample surface and inside the NWs in different concentrations. Figure 3(a) shows a cross-section TEM image in a flat region free of NWs of the sample surface, where the 5 nm WL is apparent. The rectangular box marks the selected region where the composition analysis was conducted. Figures 3(b), (c) illustrate the composition map of the WL and the corresponding 2D composition profile, respectively, showing clear evidence of an alloyed WL with continuous distribution of Si and Ge and trace amounts of Au. Different areas of the WL were analysed in order to confirm its homogeneity in the whole substrate surface. Figure 3(d) illustrates the composition profile obtained from the composition map by averaging in the lateral direction from the surface into the substrate.

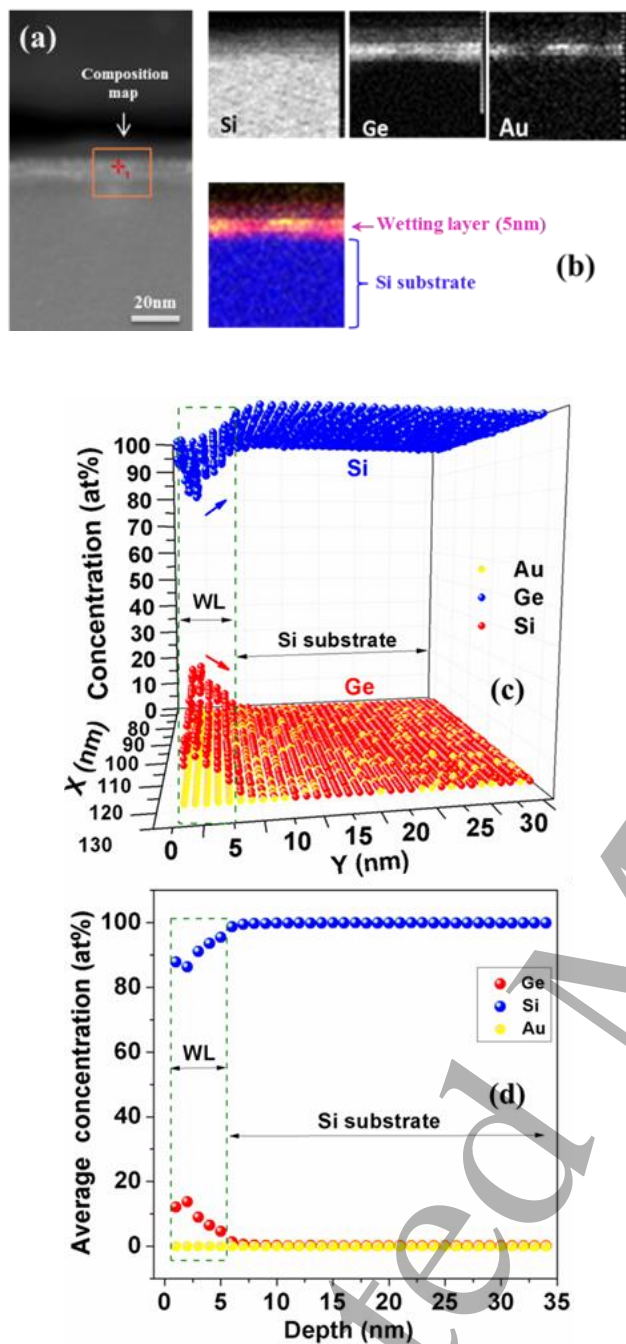

**Figure 3.** (a) TEM image of the sample surface where a 5 nm WL is formed, (b), (c) the corresponding composition map and composition profile, respectively, and (d) the average Si, Ge and Au concentration in depth. The spatial resolution of the EDX system is 1 nm.

Particularly, within the WL we found a vertical alloy composition gradient with a maximal Ge composition of 14.5 at% at the surface uppermost. The relative low Ge concentration on the WL indicates that Ge diffusion on the substrate towards the NW positions is very effective.

With regard to the composition maps and composition line scans obtained in the selected NWs, we found different vertical composition gradients depending on the NWs cross-section. As the latter decreases, the composition gradient becomes larger. Figure 4(a) illustrates the average atomic Si and Ge concentration of each NW as a function of its height. The composition profiles were obtained from composition maps throughout the NWs in the central region around the maximum height. The selected nanowire regions and the corresponding composition maps are shown in figure 4(c) (dark colour means absence of material). The average atomic Ge composition increases (from 50 to 82 %) as the width of the NWs decreases (from 585 to 130 nm). The existence of these composition gradients was expected due to the diffusive nature of the growth mechanism, as has been discussed in previous reports [13, 15], but the precise values of composition in the NWs core region were difficult to estimate by micro-Raman imaging [15].


Although it was not possible to discern the cross section dimensions of the NWs in the previous micro-Raman investigations, it was inferred that, in average, thinner NWs were richer in Ge, as is clearly shown here. The different vertical composition gradients most likely corroborate that diffusing Ge atoms on the substrate tend to incorporate preferentially at regions closer to the top of the NWs, giving the relative Ge concentration increase, which is larger in thin NWs. While the agreement with previous micro-Raman investigations is only qualitative, the results presented here also show that the uppermost regions of the NWs tend to be Ge-richer than the core and lowermost regions.

In addition, we found embedded clusters of Au within all the NWs volume, which indicates that the Au catalyst material was incorporated into the NWs during the growth process. The average atomic Au concentration decreases (from 8.5 to 0.5 %) as the width of the NWs decreases. Figure 4(b) shows the depth dependent average Au concentration for the four selected NWs. From the composition maps which are shown in figure 4(c), we found that the Au is mostly concentrated on the top part of the volume of the NWs. The precise determination of the Au concentration and distribution in the NWs is crucial, as the incorporation of the material catalyst within the

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

NWs volume might affect their electrical properties by creating deep traps in the band gap and changing the carrier mobility as has been discussed elsewhere [37].

Accepted Manuscript

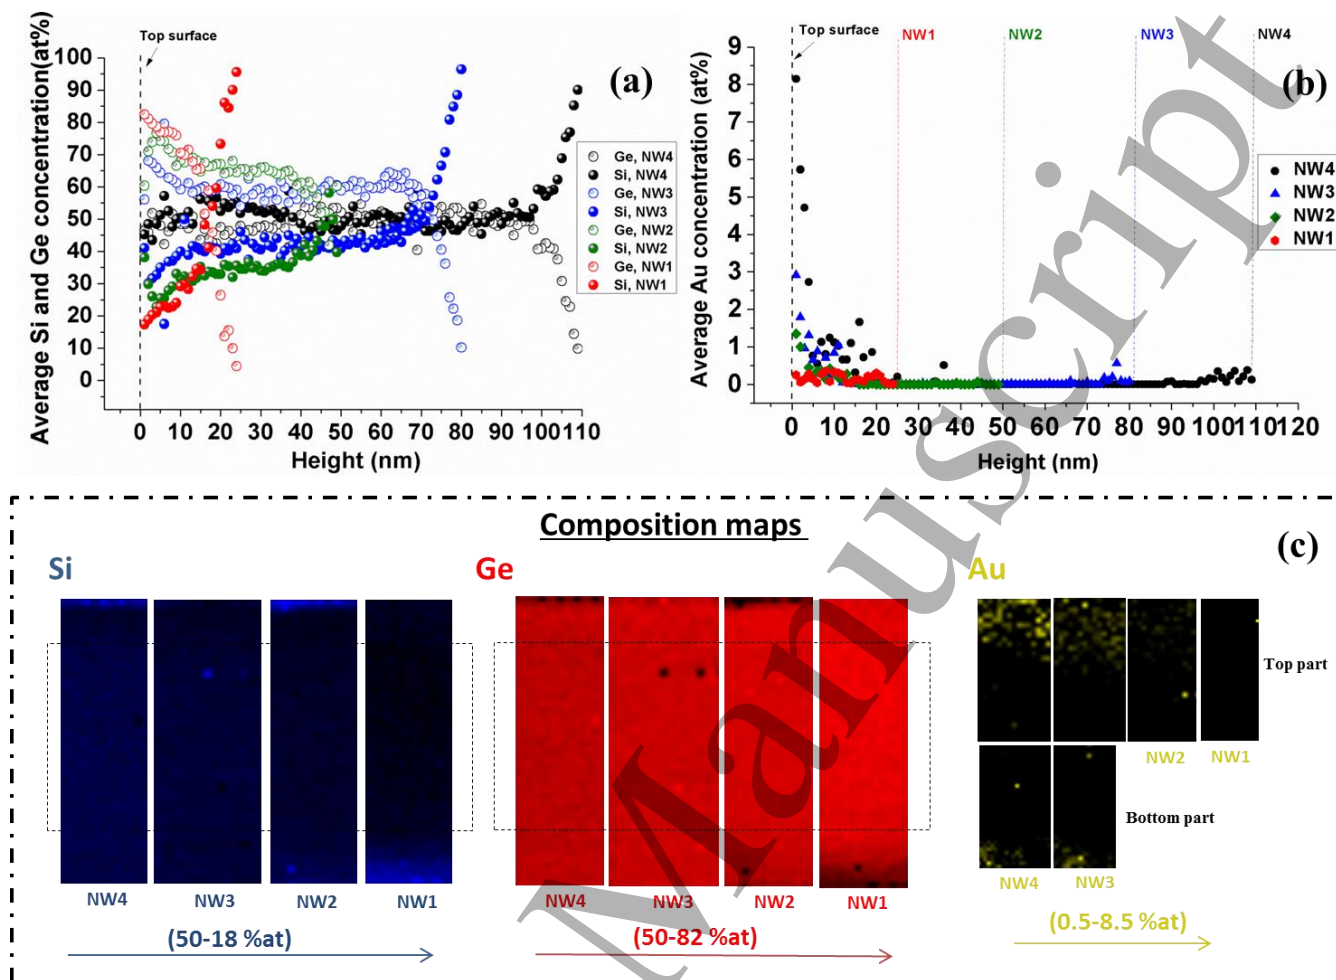1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

**Figure 4.** Average (a) Si, Ge and (b) Au concentration as a function of the height of the four supported  $\text{Si}_{1-x}\text{Ge}_x$  alloy NWs, and (c) the corresponding composition maps.


### 3.3 Thermal properties.

In this section, we present and discuss the study of the thermal transport across  $\text{Si}_{1-x}\text{Ge}_x$  alloy NWs of different morphological characteristics performed with the tip of a SThM. Sensitive probing of tip-sample effective thermal conductance or resistance variations was conducted by monitoring changes in heat flux related signals by the change of the probe electrical resistance. We consider the heated contact area as an isothermal circular heat source of radius  $r_c = (50 \pm 2)$  nm, as determined from SEM, whereas the low heat capacity ( $C_p = 133 \text{ kJ kg}^{-1}\text{K}^{-1}$ ) of the Pt wires makes the probe sensitive to thermal variations. Figures 5(a), (b) show SEM images of the cantilever where the heating Pt elements are exposed through a glass pipette, and a closer view of the Pt junction, respective-

ly. The thermal probe was used in the active SThM mode, where the probe resistive element is heated by the Joule effect. The thermal conductance between the thermal probe and the sample ( $G_{\text{th}}$ ) includes contributions due to radiation, the liquid meniscus and air, in addition to its dependence on the contact area [38–43]. Radiative heat transfer is generally assumed to be negligible as compared to the other mechanisms [41]. The values of the thermal conductance through the water meniscus have been found to be a few percent of the total contact thermal conductance [44]. Therefore, the thermal contact conductance is mainly dominated by the solid-solid contact and air conduction. Regardless of which of these two mechanisms dominate, the heat conduction through the air is independ-




ent of the surface material [45]. Moreover, since the measurements were performed in regions of smooth topography, we do not expect significant variations of the air heat transfer related to changes in the air gap between the tip and the sample surface.

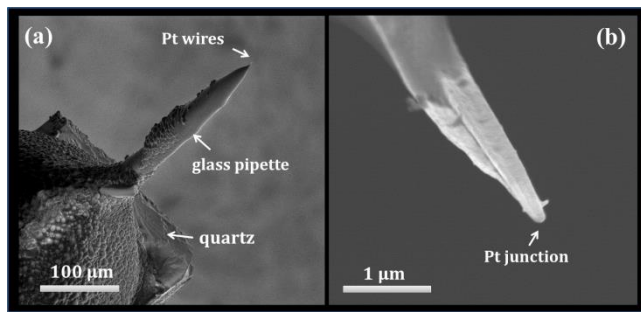

**Figure 5.** SEM images of (a) the SThM probe with the integrated Pt resistive elements and (b) the nanometer-scale junction in the Pt wires.

First, we obtained the 2D topography and thermal images of the NWs with different dimensions by simultaneous mapping the local variations in height (figure 6(a)) and tip-sample thermal resistance (figure 6(b)). The images consist of  $256 \times 256$  points. The integration time of about 30 ms at each point was long enough for the heated volume to reach thermal equilibrium. It is worth mentioning that the scanning probe environment was kept under well controlled conditions (ambient temperature and humidity). In the thermal image (see figure 6(b)), the darker regions correspond to signals acquired by the tip in contact with only the  $\text{Si}_{1-x}\text{Ge}_x$  NWs, and the brighter regions corresponds to areas where the scanning probe tip is in contact with the WL. In high thermally conductive regions, the increased heat flux from the tip to the sample results in a larger temperature drop of the probe at the heated junction, which, in turn, results in a lower probe electrical resistance ( $R_{\text{pr}}^{\text{el}}$ ). A Wheatstone bridge circuit was used to correlate changes of  $R_{\text{pr}}^{\text{el}}$  with the measured direct output voltage ( $V_{\text{out}}$ ). In our configuration, changes in the probe electrical resistance ( $\Delta R_{\text{pr}}^{\text{el}}$ ) produce proportional changes of the output voltage ( $\Delta V_{\text{out}} \propto \Delta R_{\text{pr}}^{\text{el}}$ ) (see details in the SI).

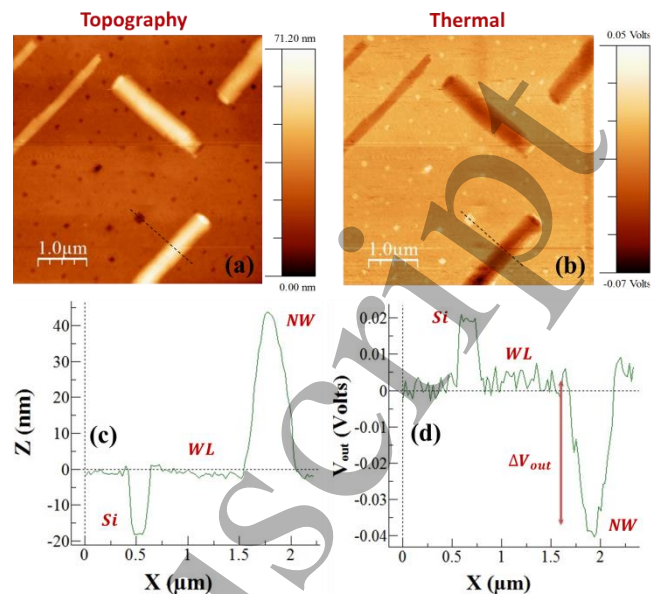

**Figure 6.** Examples of (a) topography and (b) thermal image of  $\text{Si}_{1-x}\text{Ge}_x$  alloy NWs with different dimensions. (c) Topography and (d) thermal signal profiles along the dashed lines in figure 6(a) and figure 6(b), respectively.


Before each thermal scan, the bridge was balanced with the probe in contact with the WL ( $V_{\text{out(WL)}}^{\text{rel}} \approx 0$  V). We then proceed to scan the sample surface and measured the off-balance bridge signal, i.e., the relative changes of the SThM signal ( $\Delta V_{\text{out}}^{\text{rel}}$ ) compared to the reference value in the WL. This procedure ensures an increased thermal image contrast and an accurate monitor of any signal variation. The relative variation of the thermal signal between the WL and a single NW can be directly observed in the thermal profile of figure 6(d), which is obtained from the line scan of the thermal image (dashed line in figure 6(b)). The 40 mV drop of the output voltage on top of the NW compared to the WL region indicates a drop of the heat conduction from the probe to the sample, i.e., an increase of the probe-sample thermal resistance.

Note that the probe-sample thermal resistance is composed of interfacial (Kapitza) thermal resistance and the spreading thermal resistance in the NW and the underlying Si substrate. For the four selected NWs, we found that the absolute value of the relative change of the SThM signal ( $\Delta V_{\text{out(NWS)}}^{\text{rel}}$ ) varies from -10 mV to -56 mV with increasing cross-sectional size of the NWs. Finally, the absolute thermal signals in the NWs are obtained taking into account the absolute response of the probe in the WL ( $V_{\text{out(NWS)}} =$

1  $V_{\text{out(WL)}} + \Delta V_{\text{out(NWS)}}^{\text{rel}}$ ). The absolute response of  
 2 the probe in the WL ( $V_{\text{out(WL)}} = 3.2 \text{ V}$ ) was meas-  
 3 ured by balancing the bridge far away from the sam-  
 4 ple surface and then bringing the probe in contact  
 5 with the WL. The surface topography indicates the  
 6 presence of square-like regions where the WL vanish-  
 7 es leaving holes of uncovered Si substrate. The ther-  
 8 mal profile in the uncovered Si (see figure 6(d)) dis-  
 9 plays an increase of the output voltage ( $\Delta V_{\text{out(Si)}}^{\text{rel}} =$   
 10  $20 \text{ mV}$ ), which is consistent with an increased heat  
 11 transfer compared to the WL. However, in non-  
 12 contacting regions ( $<100 \text{ nm}$ ), such as the Au parti-  
 13 cles in the NWs and few anti-dots in the WL (Figure  
 14 6(b)), the thermal contrast appears to be dominated by  
 15 the topography related changes of the tip-sample con-  
 16 tact geometry. Consequently, we measured mean val-  
 17 ues of the thermal response of the probe in different  
 18 NWs by taking into account only the thermal signals  
 19 derived from flat regions where topography induced  
 20 artifacts were not apparent.

21 Before we analyse the thermal response of our  
 22 probe in the four  $\text{Si}_{1-x}\text{Ge}_x$  NWs and in the WL, we  
 23 describe and estimate the thermal resistive compo-  
 24 nents, which contribute to the SThM signals during  
 25 the thermal exchange of the thermal probe with the  
 26 sample surface. Although the effect of heat transfer in  
 27 the ballistic regime might be considerable at length  
 28 scales comparable to phonon mean free paths (MFPs)  
 29 of the probe and the sample material, here we assume  
 30 the thermal transport as entirely diffusive. This as-  
 31 sumption is justified as long as the system is in the  
 32 steady state and the phonon MFPs in the NWs is  
 33 smaller than the contact area of the probe. This as-  
 34 sumption will be validated later when comparing the  
 35 experimental data and the results obtained using FEM  
 36 simulations in the diffusive regime.

37 The measured heat flux is considered as a function  
 38 of different thermal resistances, such as the thermal  
 39 resistance of the probe in air environment ( $R_{\text{pr}}$ ), the  
 40 thermal interface resistance between the probe and  
 41 materials in contact (thermal contact resistance) ( $R_{\text{c}}$ ),  
 42 and the thermal spreading resistance within the sam-  
 43 ple ( $R_{\text{spr}}$ ) that includes both NWs and underlying  
 44 substrate (see figure 7). Note that the contribution  
 45 of the interface resistance between the SiGe NWs and  
 46 the bottom Si substrate ( $r_{\text{int}}$ ) is discussed later in this  
 47 article.

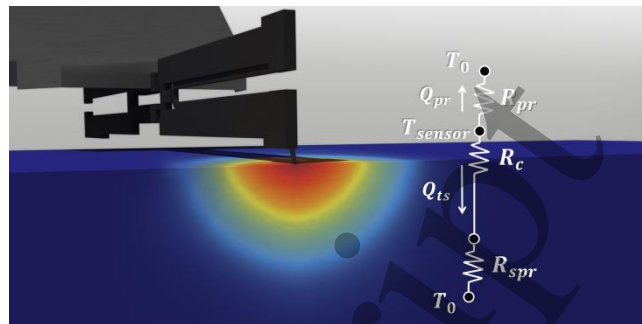

**Figure 7.** Schematic of the nanoscopic tip-sample contact and the equivalent thermal resistance circuit.

Therefore, we divide the total Joule heat generated by the current flowing through the sensor ( $Q_{\text{total}}$ ) into two pathways,  $Q_{\text{total}} = Q_{\text{ts}} + Q_{\text{pr}}$ , where  $Q_{\text{ts}}$ ,  $Q_{\text{pr}}$  are heat fluxes transferred from the probe tip to the sample and to the probe base, respectively. The equivalent thermal resistance ( $R_{\text{eq}}$ ) is given as follows [42, 46]:

$$\frac{Q_{\text{total}}}{T_{\text{sensor}} - T_0} = \frac{1}{R_{\text{eq}}} = \frac{1}{R_{\text{pr}}} + \frac{1}{R_{\text{c}} + R_{\text{spr}}} \quad (1)$$

where  $T_{\text{sensor}}$  is the heater temperature, and  $T_0$  is the ambient temperature. We determine each thermal resistance contribution to  $R_{\text{eq}}$  using FEM simulations (COMSOL Multiphysics) and analytical models reported elsewhere [43, 47, 48]. The full procedure is described in detail in the SI. FEM simulations were also used to calculate the temperature distribution in the thermal probe, taking into account the heat transfer from the probe to the surrounding air, and determine  $R_{\text{pr}}$ . The value provided by the FEM model was  $R_{\text{pr}} = 1.7 \times 10^6 \text{ K W}^{-1}$ .

Since the WL is homogeneously formed on the Si substrate we can estimate the spreading resistance when the thermal probe is in contact with the WL,  $R_{\text{spr(WL)}}$ , from the analytical thin-film approximation derived by Dryden [48]. This model describes the spreading of heat from a circular heat source into an isotropic structure in the case that the thickness of the film is significantly smaller than the contact radius of the heat source. The obtained value  $R_{\text{spr(WL)}} = 5.32 \times 10^5 \text{ KW}^{-1}$  is one order of magnitude larger than the spreading resistance in bulk Si ( $R_{\text{spr(Si)}} = 3.37 \times 10^4 \text{ KW}^{-1}$ ) due to the lower thermal conductivity of the SiGe alloy film forming the WL.

The magnitude of  $R_{spr}$  in the NWs is expected to vary with both, the geometrical scaling of the NWs and with possible variations of the thermal conductivity between NWs. We estimated the thermal spreading resistance variations at the probe-NWs contacts ( $R_{spr(NWs)}$ ) first by following the same analytical film approximation for the spreading resistance [48]. Assuming a perfect thermal contact between the thermal tip and the NWs, we estimated thermal spreading resistance variations from  $6.0 \times 10^5 \text{ KW}^{-1}$  to  $3.9 \times 10^6 \text{ KW}^{-1}$  in a thermal conductivity range from 1 to  $5 \text{ Wm}^{-1}\text{K}^{-1}$ . In order to validate the estimations of  $R_{spr}$  obtained from the thin film approximation, we performed FEM simulations to compute the thermal spreading resistance variations in the four investigated NWs taking into account their real morphology ( $R_{spr(NWs)}^{FEM}$ ). This procedure gave values of  $R_{spr}$  in the range  $4.3 \times 10^5 \text{ KW}^{-1}$  to  $4.4 \times 10^6 \text{ KW}^{-1}$ , similar to that derived from the analytical model.


Finally, the value of  $R_c$ , which represents the thermal resistance at the probe-sample interface, was estimated to be  $9.3 \times 10^7 \text{ KW}^{-1}$  both in the WL and the NWs. Despite the relatively high value of  $R_c$ , which limits the sensitivity of the method, it does not prevent the detection of small amplitude signal changes related to  $R_{spr}$  variations (see figure S7 in the SI). The determination of  $R_c$  was possible by combining our experimental data and the calculated thermal spreading resistance variations between the WL, the NWs and the bulk Si (see details in the SI). Nevertheless, we would expect  $R_c$  in the NWs and the WL to be similar since the two materials in contact were the same (Pt/SiGe contacts) during the thermal measurements and the amplitude of the contact force was kept approximately constant.

Following the identification of the heat transfer mechanisms between the thermal probe and the sample, as well as their relative weight, we discuss the variations observed in the SThM signal between different NWs. Considering that the probe Joule power dissipated into the sample is proportional to  $V_{out}$ , we correlate changes in  $V_{out}$  with variations of the effective thermal conductance ( $G_{th}$ ) between our heated tip and the sample surface (see details in the SI). The relation between the measured  $V_{out}$  and the estimated

thermal resistances is expressed by the ratio ( $g$ ) defined as follows:

$$g = \frac{V_{out(NWs)}}{V_{out(Si)}} = \frac{R_c^{Si} + R_{spr}^{Si} + R_{pr}}{R_c^{NWs} + R_{spr}^{NWs} + R_{pr}} \propto \frac{G_{th(NWs)}}{G_{th(Si)}} \quad (2)$$

where  $V_{out(NWs)}$  and  $V_{out(Si)}$  represent the absolute thermal signals obtained on the  $\text{Si}_{1-x}\text{Ge}_x$  NWs and the bulk Si, respectively. Figure 8 shows the ratio  $g$  (black spheres) obtained from the four investigated NWs, as a function of their surface to volume ratio. The observed trend reveals that the effective thermal conductance between the heated tip and the NWs ( $G_{th(NWs)}$ ), which scales proportional with the ratio  $g$ , increases in NWs with larger surface to volume ratio. Figure 8 also shows the effect of the 5 nm SiGe alloy WL on the SThM signal compared to the thermal signal measured in bulk Si. In the same graph, we have plotted the normalized thermal response of the probe ( $g_{FEM}$ ) obtained from the thermal spreading resistance values ( $R_{spr(NWs)}^{FEM}$ ), which were calculated for each NW for values of the thermal conductivity of  $k=2$  and  $k=3 \text{ Wm}^{-1}\text{K}^{-1}$  (red and green stars in figure 8).

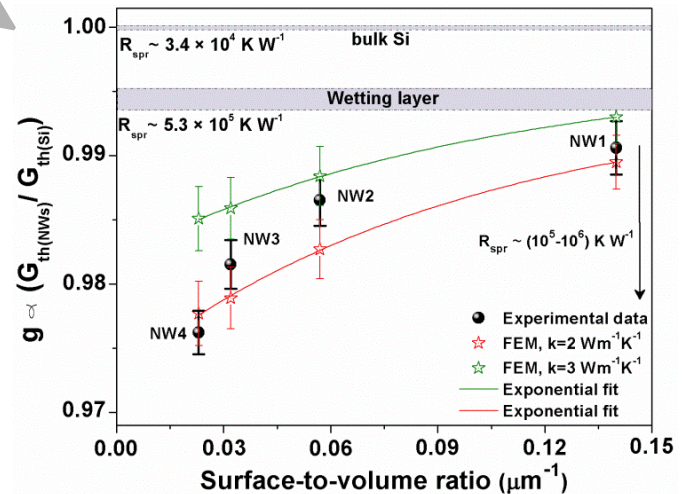

**Figure 8.** Plot of the experimental thermal ratio ( $g$ ) (black spheres) and the ratio obtained from the FEM simulations ( $g_{FEM}$ ) (red and green stars) versus the surface to volume ratio of the  $\text{Si}_{1-x}\text{Ge}_x$  NWs.

Based on the spreading resistance diffusive model, the obtained trend of increasing  $g$  ratio, i.e. thermal conductance, with increasing NW cross-section is attributed to the increasingly dissipated heat to the substrate, owing to the larger thermal conductivity of

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

Si. The comparison in figure 8 shows a quantitative agreement between the FEM simulations, which takes into account only  $R_{spr}$  variations, and our experimental results, confirming that, despite  $R_c$  is the dominant resistive component, the variations in the thermal response of the probe due to different NWs are associated with variations in  $R_{spr}$ . Further details on the comparison of the estimated variations of  $R_{spr}$  and  $R_c$  can be found in the SI (figure S6). The experimental data fall between the two calculations for  $k=2$  and  $k=3 \text{ Wm}^{-1} \text{ K}^{-1}$ , with values for NW3 and NW4 closer to the  $k=2 \text{ Wm}^{-1} \text{ K}^{-1}$ . These small deviations between the modelling and the experimental data can be attributed to composition variations in the NWs, which were not taken into account in the FEM simulations (e.g. presence of Au and SiGe composition).

Recalling the results from the composition analysis (figure 4(b)), it is interesting to note that NW3 and NW4 showed the highest Au concentration. The increased Au concentration in these cases generates a nanoscale disorder in the SiGe lattice, which increases the number of phonon scattering events. We consider the concentrated Au atoms as an additional thermal resistive layer, which potentially reduces the average phonon MFPs in the NWs and further suppress the heat dissipation perpendicular to the substrate. Recently, interfaces of different types have been reported to provide enhanced phonon scattering and phonon trapping at localized vibrational modes [49–53]. Moreover this mechanism can effectively suppress the transport of long-wavelength phonons and, therefore, the ballistic transport.

Refining the values of the thermal conductivity in the previous analysis, by better matching the calculated  $g_{FEM}$  to the experimental  $g$  value, we could estimate the thermal conductivity of NW3 and NW4 to be  $2.2 \pm 0.3 \text{ Wm}^{-1} \text{ K}^{-1}$  and of NW1 and NW2 to be  $2.7 \pm 0.3 \text{ Wm}^{-1} \text{ K}^{-1}$ , which are values almost four times lower than the bulk value [50]. This range is similar to the values expected in SiGe nanostructures of similar characteristic size and composition, where the reduction of the thermal conductivity has been attributed to phonon boundary scattering [30, 31, 54–56]. More importantly, our analysis indicates that even for nanometer scale heat sources and low conductive materials, heat dissipation can be consistently explained with a diffusive thermal spreading model.

Finally, in order to assess the effect of an interfacial thermal resistance,  $r_{int}$ , between the NWs and the substrate, we used an extension of the thin film approximation model, which accounts for the effect of an interface on the thermal spreading resistance [57]. Since the precise knowledge of  $r_{int}$  is difficult in the present samples, we used a wide range of values comprising those reported in SiGe based structures [49, 58, 59] and investigated its effect on the  $g$  ratio. Values of interfacial thermal resistance between 0 and  $1 \times 10^{-8} \text{ m}^2 \text{ KW}^{-1}$  were chosen and set in the analytical modelling. As expected, by introducing an interfacial thermal resistance the ratio  $g$  decreased. The variations were larger with decreasing NW height in the order of a 0.1% to 0.6% for NW4 and NW1, respectively, for a value of the thermal interface resistance of  $1 \times 10^{-8} \text{ m}^2 \text{ KW}^{-1}$ . These differences are within the experimental error and do not affect the values of the thermal conductivity of the NWs given previously. Moreover, a decreasing  $g$  ratio with increasing  $r_{int}$  supports the explanation in which the variations of the data with respect the model are more likely due to Ge composition variations and Au content.

### 3. Conclusions

In conclusion, we have performed a comprehensive experimental study of the structure and the composition of supported in-plane epitaxial  $\text{Si}_{1-x}\text{Ge}_x$  alloy NWs of different dimensions, which provides a deeper understanding of the bottom-up growth processes. We have presented new evidences regarding the morphology of the NWs, their size-dependent gradient composition and the formation of a 5 nm thick WL on the substrate surface. In addition, we have studied the thermal transport between the heated tip of a scanning thermal microscope and the sample surface. SThM has provided high resolution thermal contrast images of sub-micrometer structures on the sample surface with 100 nm lateral thermal resolution. By estimating all the major thermal resistive components contributing to the SThM signal at the probe-sample contact and determining the dominant mechanisms, we have been able to analyse the experimental thermal response. Particularly in the NWs, we found that the heat flux related signal are determined by thermal spreading resistance variations, revealing the relation between the measured SThM signal and the effective

thermal conductance. The results obtained using FEM simulations, which are in good agreement with the experimental results, allowed us to determine a range of thermal conductivities ( $2\text{--}3 \text{ Wm}^{-1} \text{ K}^{-1}$ ) for the investigated NWs. These results can provide essential guidance for the integration of epitaxial in-plane NWs in devices with varying composition in a controllable way and with improved heat management.

## Acknowledgements

The authors acknowledge the financial support from the EU FP7 project Quantiheat (Grant No 604668), the Spanish MINECO projects NanoTHERM (Grant No. CSD2010-589 0044) and PHENTOM (FIS2015-70862-P) and the program Severo Ochoa (Grants SEV-2013-0295 and SEV-2015-0496). We would like also to thank A. Ruiz and M. Alonso for the preparation of the Au films used as substrates, and M. Papan-dreou for the graphic illustrations.

## References

- [1] Paul D, Silicon-Germanium Strained Layer Materials in Microelectronics 1999 *Adv. Mater.* **11** 3
- [2] Amato M, Palumbo M, Rurali R, Ossicini S 2014 Silicon-germanium nanowires: chemistry and physics in play, from basic principles to advanced applications. *Chem. Rev.* **114** 1371–1412
- [3] Bean J C 1985 Strained-layer epitaxy of germanium-silicon alloys *Science* **230** 4722
- [4] Eneman G, Verheyen P, Rooyackers R, Nouri F, Schreutelkamp R, Moroz V, Smith L, Jurczak M, De Meyer K 2006 Scalability of the si/sub 1-x/ge/sub x/source/drain technology for the 45-nm technology node and beyond. *IEEE Trans. Electron Devices* **53** 7
- [5] Shih C C, Lee W Y, Chen W C 2016 Nanostructured materials for non-volatile organic transistor memory applications *Mater. Horiz.* **3** 294
- [6] Irrera A, Artoni P, Fioravanti V, Franzò G, Fazio B, Musumeci P, Boninelli S, Impellizzeri G, Terrasi A, Priolo F, Iacona F 2014 Visible and infrared emission from Si/Ge nanowires synthesized by metal-assisted wet etching. *Nanoscale Res. Lett.* **9** 74
- [7] Lu W, Xie P, Lieber C M 2008 Nanowire transistor performance limits and applications *IEEE Trans. Electron Devices* **55** 2859–2876
- [8] Sacchetto D, Ben-Jamaa M, De Micheli G, Leblebici, Y 2009 *Proc. ESSDERC* (Greece, 14-18 September 2009)
- [9] Cahill D G, Braun P V, Chen G, Clarke D R, Fan S, Goodson K E, Keblinski P, King W P, Mahan G D, Majumdar A, Maris H J, Phillpot S R, Pop E, Shi L 2014 Nanoscale thermal transport. II. 2003–2012. *Appl. Phys. Rev.* **1** 011305
- [10] Zhang W, Yang S 2009 In situ fabrication of inorganic nanowire arrays grown from and aligned on metal substrates *Acc. Chem. Res.* **42** 1617–1627
- [11] Kim W 2011 *Mater. Res. Innovations* **15** 377
- [12] Marcus I C, Berbezier I, Ronda A, Alonso M I, Garriga M, Goñi A R, Gomes E, Favre L, Delobbe A, Sudraud P 2011 In-plane epitaxial growth of self-assembled Ge nanowires on Si substrates patterned by a focused ion beam. *Cryst. Growth Des.* **11** 3190–3197
- [13] Alonso M I, Ruiz A, Alonso M, Bailo E, Garriga M, Molero A, Vaccaro P O, Goñi A R 2015 Growth and characterization of epitaxial in-plane SiGe alloy nanowires. *Mater. Today: Proceedings* **2** 548–556
- [14] Qi C, Goncher G, Solanki R, Jordan J 2007 SiGe nanowire growth and characterization *Nanotechnology* **18** 075302
- [15] Alonso M I, Bailo E, Garriga M, Molero A, Vaccaro, P O, Goñi A R, Ruiz A, Alonso M 2015 Composition and strain imaging of epitaxial in-plane SiGe alloy nanowires by micro-Raman spectroscopy *J. Phys. Chem. C* **119** 22154–22163
- [16] Schwartzman M, Tsivion D, Mahalu D, Raslin O, Joselevich E 2013 Self-integration of nanowires into circuits via guided growth *PNAS* **110** 38
- [17] Tiberj A, Camassel J 2012 Raman Imaging Techniques and Applications (*Springer series in Optical Sciences* vol 2) ed A Zoubir (Berlin Heidelberg) pp 386.
- [18] Picco A, Bonera E, Pezzoli F, Grilli E, Schmidt O G, Isa F, Cecchi S, Guzzi M 2012 Composition profiling of inhomogeneous SiGe nanostructures by Raman spectroscopy *Nanoscale Res. Lett.* **7** 633
- [19] Meduri P, Sumanasekera G U, Chen Z, Sunkara M K 2008 Composition controlled synthesis and Raman analysis of Ge-rich Si<sub>x</sub>Ge<sub>1-x</sub> nanowires. *J. Nanosci. Nanotechnol.* **8** 3153–3157
- [20] Bezuidenhout M, Kennedy T, Belochapkin S, Guo Y, Mullane E, Kiely P A, Ryan K M 2015 High density and patternable growth of silicon, germanium and alloyed SiGe nanowires by a rapid anneal protocol. *J. Mater. Chem. C* **3** 7455–7462
- [21] Chang H K, Lee Si C 2012 Morphology control and optical properties of SiGe nanostructures grown on glass substrate *Nanoscale Res. Lett.* **7** 155
- [22] Lebon G, Machrafi H 2015 Thermal conductivity of

- tubular nanowire composites based on a thermodynamical model. *Physica E* **71** 117–122
- [23] Li D, Wu Y, Fan R, Yang P, Majumdar A 2003 Thermal conductivity of Si/SiGe superlattice nanowires. *Appl. Phys. Lett.* **83** 15
- [24] Wingert M C, Chen Z C Y, Dechaumphai E, Moon J, Kim J H, Xiang J, Chen R 2011 Thermal conductivity of Ge and Ge–Si core–shell nanowires in the phonon confinement regime. *Nano Lett.* **11**, 5507–5513
- [25] Kwon S, Wingert M C, Zheng J, Xiang J, Chena R 2016 Thermal transport in Si and Ge nanostructures in the 'confinement' regime. *Nanoscale* **8** 13155
- [26] Kim H, Kim I, Choi H J, Kim W 2010 Thermal conductivities of Si<sub>1-x</sub>Ge<sub>x</sub> nanowires with different germanium concentrations and diameters *Appl. Phys. Lett.* **96** 233106-10190
- [27] Wang Z, Mingo N 2010 Diameter dependence of SiGe nanowire thermal conductivity *Appl. Phys. Lett.* **97** 101903
- [28] Shi L, Li D, Yu C, Jang W, Kim D, Yao Z, Kim P, Majumdar A 2003 Measuring thermal and thermoelectric properties of one-dimensional nanostructures using a microfabricated device *J. Heat transfer* **125** 881
- [29] Chen J, Zhang G, Li B 2009 Tunable thermal conductivity of Si<sub>1-x</sub>Ge<sub>x</sub> nanowires *Appl. Phys. Lett.* **95** 073117
- [30] Lee K E, Yin L, Lee, Y, Lee J W, Lee S J, Lee J, Nam Cha S, Whang D, Hwang G S, Hippalgaonkar K, Majumdar A, Yu C, Choi B L, Min Kim J, Kim K 2012 Large thermoelectric figure-of-merits from SiGe nanowires by simultaneously measuring electrical and thermal transport properties *Nano Lett.* **12** 2918–2923
- [31] Yin L, Kyung Lee E, Woon Lee J, Whang D, Lyong Choi B, Yu C 2012 The influence of phonon scatterings on the thermal conductivity of SiGe nanowires *Appl. Phys. Lett.* **101** 043114
- [32] Hsiao T K, Chang H K, Liou S C, Chu M W, Lee S C, Chang C W 2013 Observation of room-temperature ballistic thermal conduction persisting over 8.3 μm in SiGe nanowires *Nat. Nanotechnol.* **8** 534-538
- [33] Grauby S, Puyoo E, Rampnoux J M, Rouvière E, Dilhaire S 2013 Si and SiGe nanowires: fabrication process and thermal conductivity measurement by 3ω-scanning thermal microscopy. *J. Phys. Chem. C*, **117** 9025–9034
- [34] Persson A I, Koh Y K, Cahill D G, Samuelson L, Linke H 2009 Thermal conductance of InAs nanowire composites *Nano Lett.* **9** 4484
- [35] Liu Z, Elbert D, Chien C L, and Searson P C 2008 FIB/TEM characterization of the composition and structure of core/shell Cu-Ni nanowires *Nano Lett.* **8**, 2166
- [36] Greve D W 1998 Thin Films (Academic Press, vol 23) ed Francombe M H and Vossen J L (San Diego) pp 1
- [37] Kanungo P D, Wolfsteller A, Zakharov N D, Werner, P, Gosele U 2009 Enhanced electrical properties of nominally undoped Si/SiGe heterostructure nanowires grown by molecular beam epitaxy *Microelectron. J.* **40** 452–455
- [38] Menges F, Riel H, Stemmer A, Gotsmann B 2012 Quantitative thermometry of nanoscale hot spots *Nano Lett* **12** 596–601
- [39] Gomès S, Assy A, Chapuis P O 2015 Scanning thermal microscopy: A review. *Phys. Status Solidi A.* **3** 477–494
- [40] Chapuis P O, Greffet J J, Joulain K, Volz S 2006 Heat transfer between a nano-tip and a surface *Nanotechnology* **17** 2978–2981
- [41] Majumdar A 1999 Scanning thermal microscopy *Annu. Rev. Mater. Sci.* **29** 505–85
- [42] Shi L, Majumdar A 2014 *J. Heat transfer* **124** 329–337
- [43] Gotsmann B, Lantz M A, Knoll A, Dürig U 2010 *Nanotechnology Vol. 6 Nanoprobes* ed H Fuchs (Wiley-VCH, Weinheim)
- [44] Assy A and Gomès S 2015 Temperature-dependent capillary forces at nano-contacts for estimating the heat conduction through a water meniscus *Nanotechnology* **26** 355401
- [45] Prasher R 2005 Predicting the Thermal Resistance of Nanosized Constrictions *Nano Lett.* **5** (11) 2155–2159
- [46] Tovee P, Pumarol M, Zeze D, Kjoller K, Kolosov O V 2012 Nanoscale spatial resolution probes for scanning thermal microscopy of solid state materials *J. Appl. Phys.* **112** 114317
- [47] Yovanovich M M, Culham J R, Teertstra P 1998 Analytical modeling of spreading resistance in flux tubes, half spaces, and compound disks *IEEE Trans. Compon. Packag. Manuf. Technol.* **21** 1070–9886
- [48] Dryden J R 1993 The effect of a surface coating on the constriction resistance of a spot on an infinite half-plane. *ASME J. Heat Transf.* **105** 408–410
- [49] Pernot G, Stoffel M, Savic I, Pezzoli F, Chen P, Savelli G, Jacquot A, Schumann J, Denker U, Mönch I, Deneke C, Schmidt O G, Rampnoux J M, Wang S, Plissonnier M, Rastelli A, Dilhaire S, Mingo N 2010 Precise control of thermal conductivity at the nanoscale through individual phonon-scattering barriers

ers *Nat. Materials* **9** 491–495

- 1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60
- [50] Estreicher S K, Gibbons T M, Kang B, Bebek M B 2014 Phonons and defects in semiconductors and nanostructures: Phonon trapping, phonon scattering, and heat flow at heterojunctions *J. Appl. Phys.* **115** 012012
- [51] Pan Y, Hong G, Raja S N, Zimmermann S, Tiwari M K, Poulidakos D 2015 Significant thermal conductivity reduction of silicon nanowire forests through discrete surface doping of germanium *Appl. Phys. Lett.* **106** 093102
- [52] Uchida N, Maeda T, Lieten R R, Okajima S, Ohishi Y, Takase R, Ishimaru M and Locquet J P 2015 Carrier and heat transport properties of polycrystalline GeSn films on SiO<sub>2</sub> *Appl. Phys. Lett.* **107** 232105
- [53] Chen P, Katcho N A, Feser J P, Li W, Glaser M, Schmidt O G, Cahill D G, Mingo N, Rastelli A 2013 Role of surface-segregation-driven intermixing on the thermal transport through planar Si/Ge superlattices. *Phys. Rev. Lett.* **111** 115901.
- [54] Iskandar A, Abou-Khalil A, Kazan M, Kassem W, Volz S 2015 On the interplay between phonon-boundary scattering and phonon-point-defect scattering in SiGe thin films *J. Appl. Phys.* **117** 125102
- [55] Cheaito R, Duda J C, Beechem T E, Hattar K, Ihlefeld J F, Medlin D L, Rodriguez M A, Champion M J, Piekos E S, Hopkins P E 2012 Experimental investigation of size effects on the thermal conductivity of silicon-germanium alloy thin films *Phys. Rev. Lett.* **109** 195901
- [56] Xie G, Guo Y, Wei X, Zhang K, Sun L, Zhong J, Zhang G, Zhang Y W 2014 Phonon mean free path spectrum and thermal conductivity for Si<sub>1-x</sub>Ge<sub>x</sub> nanowires. *Appl. Phys. Lett.* **104** 233901
- [57] Fabian M, Heike R, Andreas S, Dimitrakopoulos C, and Gotsmann B 2013 Thermal Transport into Graphene through Nanoscopic Contacts *Phys. Rev. Lett.* **111**, 205901
- [58] Lee S M, Cahill D G, Venkatasubramanian R 1997 Thermal conductivity of Si-Ge superlattices *Appl. Phys. Lett.* **70** 2957–2959
- [59] Lee M L, Venkatasubramanian R 2008 Effect of nanodot areal density and period on thermal conductivity in Si Ge/Si nanodot superlattices *Appl. Phys. Lett.* **92** 053112

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

Accepted Manuscript