

Characterization of Heat and Momentum Transfer in Sintered Metal Foams

OLIVER REUTTER, JÖRG SAUERHERING,
THOMAS FEND, ROBERT PITZ-PAAL
*German Aerospace Center
Linder Hoehe
51143 Köln, Germany*

STEFANIE ANGEL
*University Aachen,
Department of Ferrous Metallurgy
52066 Aachen, Germany.*

ABSTRACT

In this study, metal foams made by the SlipReactionFoamSintering (SRFS)-process are investigated concerning their thermophysical and permeability properties. Since the foam is to be applied as a functional and structural element in the effusion air cooling system of a stationary gas turbine combustion chamber, these properties are of major interest for the calculation of the temperature distribution inside the combustion chamber walls, which may be critical for the employed materials. Experimental set-ups are presented, which are used to determine permeability, the volumetric heat transfer coefficient and the effective thermal conductivity. The results are presented for a wide range of foam materials. Porosity as well as the basic metal powder and the manufacturing parameters are varied. The influence of these parameters on the measured quantities is discussed. Thermal conductivity data are determined at temperatures of up to 1200 K. The obtained volumetric heat transfer coefficients are transferred to Nusselt-Reynolds plots, which allow generalization to the high temperature and high pressure regime. Correlations between the heat transfer properties and the permeability data are made. Using the acquired experimental data, a proposal is made for the calculation of the inner surface temperature of the combustion chamber as well as the temperature distribution inside the chamber wall, which consists of a structural element, the metal foam and a thermal barrier coating, equipped with laser drilled micro-holes.

1. INTRODUCTION

The foam investigated in this study is aimed to be applied as an open wall element of combustion chambers. This topic is investigated within the collaborative research center (SFB) 561 “Thermally Highly Loaded, Porous and Cooled Multi-Layer Systems for Combined Cycle Power

Plants”. It aims at increasing the efficiency of the gas turbine by raising the gas temperature. Within this research center, the present study was carried out. Increasing the temperature leads to the necessity of actively cooling the combustion chamber walls by effusion cooling, which means that cooling air is pressed through little holes into the chamber. The metallic foam is intended to be coated with a thermal barrier layer with laser drilled boreholes and to be used as a combustion chamber wall element [1] [2]. A sketch of the cooling principle is shown in Fig 1 (top). The knowledge of the temperature distribution inside the wall element (foam+coating) is important to predict the lifetime of the materials employed. To predict the temperature, flow through the wall element has to be characterized. For this, experimental data on the heat transfer characteristics, the thermal conductivity and the pressure drop characteristics is needed. Both, temperature prediction and determination of quantities is object of the present study.

2. INVESTIGATED MATERIALS

The foams investigated in the present study are produced by the SlipReactionFoamSintering (SRFS)-process. This is a promising method to produce metallic foams with an open, porous cell structure by a chemical reaction process. As this foaming is a rather new method there is not yet ready available data concerning the pore structure or the behavior to fluid flow. The foam structure is not similar to the foams made by casting using a polymer precursor as template or by metal deposition on cellular performs like polyurethane foams [3]. Therefore it was necessary to conduct a series of extensive experiments in order to characterize the SRFS foams. A first introduction and first results have been previously published [4]. The investigated samples for this study are made of Hastelloy B, Inconel 625 and NC-powder. The grain sizes range between 50 and 150 μm . The iron based samples (NC) were sintered at 1170°C, the nickel based samples (Inconel

625 and Hastelloy B) at 1200°C. After evacuating the furnace one time before starting the sintering process, the samples were sintered under a reducing atmosphere of 100% H₂.

Samples made only of the sintered slip without foaming show a porosity of about 50% (densities of 3.8-4.2 g/cm³) and are called *sintered powder samples* or *matrix material*. In comparison to these, the dense metals have densities of 7.87 g/m³ (NC), 9.24 g/m³ (Hastelloy B) and 8.44 g/m³ (Inconel 625). The *sintered powder samples* are taken as representing the material of the pore walls in the foams. The foams have a total porosity between 62 and 87% (densities of 1.2 – 3.7 g/cm³). The pores can be characterized as those which arise from the hydrogen foaming, called the *primary pores*, and those which are the spaces between adjacent grains of the sintered powder, called the *secondary pores* [5]. The secondary pores reach up to 0.3 mm diameter and the primary pores reach up to 3.5 mm. All densities were determined as gravimetric densities by weighing the foam samples and dividing this weight by the total volume of the foam sample. The total porosity was determined by using the density of the bulk material as the reference. The samples were produced at the Department of Ferrous Metallurgy at Aachen University. The samples are cylinders with diameters between 64 and 81 mm and the length was between 9 and 30 mm. The picture of a typical sample can be seen in Figure 1 (bottom left) together with an optical micrograph of the sample (bottom right). For measurements of anisotropy effects cubical samples were used with 45 mm side length.

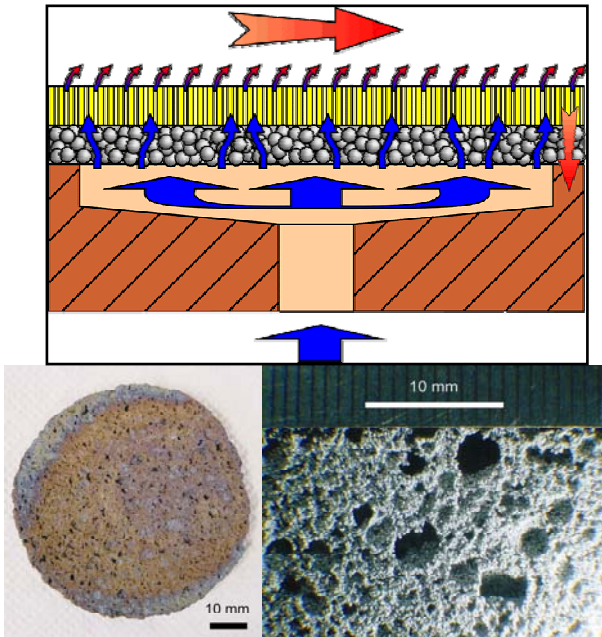


Figure 1: Cooling principle (top), picture of a sample of a Hastelloy B foam (bottom left) and a detailed view of the pore structure (bottom right)

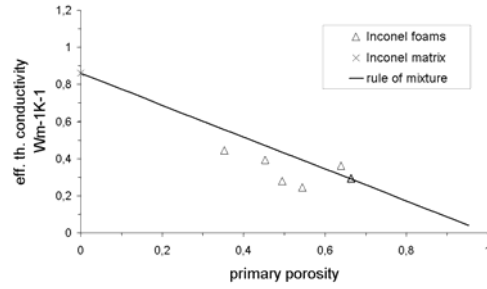


Figure 2: Effective thermal conductivity of selected Inconel foams as a function of their total porosity

3. EXPERIMENTALLY ACQUIRED MATERIAL DATA

3.1 Heat Conductivity

Effective heat conductivity λ_{EFF} has been determined with the Transient Heat Source Technique also called “Hot Disk”. This technique has been chosen, because the tested volume ($\approx 2\text{-}4 \text{ cm}^2$) is big enough to justify the assumption, that λ is a “volume averaged quantity”, which comprises all the micro-mechanisms like conductive heat transfer in the grains, convective heat transfer in the pores and radiation heat transfer from one pore wall to another. Basics of the experimental set-up have been previously reported [6]. The Inconel material without primary pores has been additionally measured with the Laser Flash method for comparison. It shows values of $\lambda_{\text{EFF}}=0.87 \text{ W/mK}$ at room temperature. This is only about 1/10 of the thermal conductivity of the dense metal ($\lambda=9.1 \text{ W/mK}$ at 25°C). The heat conductivity of the foams is even lower. As an example the results from the Inconel foams are shown in Fig. 2.

A simple rule of mixture holds, if only the primary porosity ε^* is considered:

$$\lambda_{\text{FOAM}} = \varepsilon^* \lambda_{\text{FLUID}} + (1 - \varepsilon^*) \cdot \lambda_{\text{MATRIX}} \quad (1)$$

The matrix thermal conductivity itself may be explained with models having been developed for packed beds [7].

3.2 Convective Heat Transfer Coefficients

The effective volumetric heat transfer coefficients αA_V (with α denoting the well known convective heat transfer coefficient and A_V the specific surface area participating in convective heat transfer usually measured in m^2/m^3) are considered as volume averaged quantities describing the solid to fluid heat transfer inside the porous material. They have been determined with a transient method after Viskanta and Younis [8]. An air flow of alternating temperature is directed through a porous sample, which

causes an amplitude decrease of the temperature wave (Fig. 3). From this, αA_V may be determined. To make use of the similarity theory, from αA_V more general Nusselt numbers (Nu) may be determined ($Nu = \alpha d / \lambda_{FLUID}$). For this, a characteristic channel diameter d is needed. Furthermore, the thermal conductivity of the fluid λ_{FLUID} . For those materials, of which the results are shown in Fig 4, this diameter has been determined to approximately 0.5mm by experiments observing the capillary flow of water into the pores. Reynolds numbers have been calculated from fluid flow velocity U_0 and fluid viscosity η by $Re = dU_0/\eta$. The results show, that the heat transfer increases with decreasing porosity. Imagining the pore structure as set of \varnothing 0.5 mm channels, a rough approximation of the specific surface A_V may be undertaken and Nusselt numbers may be determined directly. For the shown Hastelloy materials Nusselt numbers of $2.5 < Nu < 5$ were calculated. These values fit well to the empirical equations for the case of laminar flow inside a tube, which give Nu numbers of $Nu \approx 3.7$.

3.3 Permeability

Permeability of the foam was simply investigated by generating an air flow of various fluid velocities through the foam samples and measuring the pressure difference of the fluid before and behind the sample according to Fig. 5.

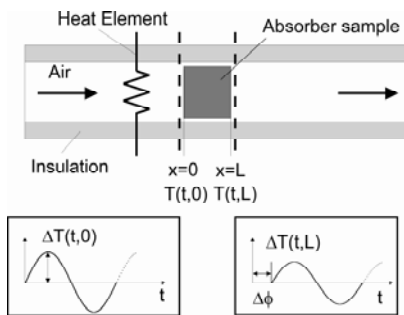


Figure 3: Principle of the set-up used for the convective heat transfer coefficient measurements

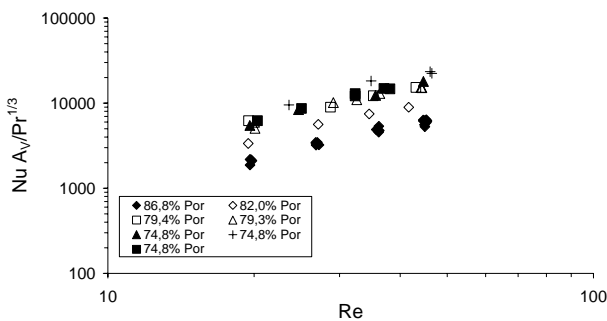


Figure 4: Principle of the set-up used for the convective heat transfer coefficient measurements

Pressure loss/air velocity plots were generated as can be seen in Fig. 6. The plots were fitted with the extended Darcy equation

$$\frac{\Delta p}{L} = \frac{\mu_{DYN}}{K_1} U_0 + \frac{\rho_F}{K_2} U_0^2 \quad (2)$$

in which Δp denotes pressure difference, L the length of the sample in the direction of flow, μ_{DYN} , ρ_F and U_0 the dynamic viscosity, the density and the velocity of the fluid respectively. From the plots and the fluid data, which is taken from the literature, K_1 and K_2 , the characteristic constants of the porous material are determined. Most frequently they are called the permeability and the inertial coefficient, because K_1 is the contribution of the viscous drag of the pores to permeability and K_2 the contribution of the acceleration of the fluid particles through the tortuous path of the flow through the material. The inertial coefficients determined are shown in Fig. 7 as a function of the total porosity of the foam samples. It can be clearly seen, that permeability increases significantly, when the porosity reaches approximately 70%. The obvious conclusion, that the primary pores form a network of channels is not yet proved by metallographic investigations.

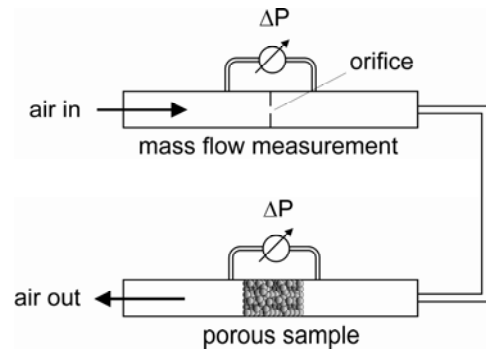


Figure 5: Set-up used to measure permeability of foams

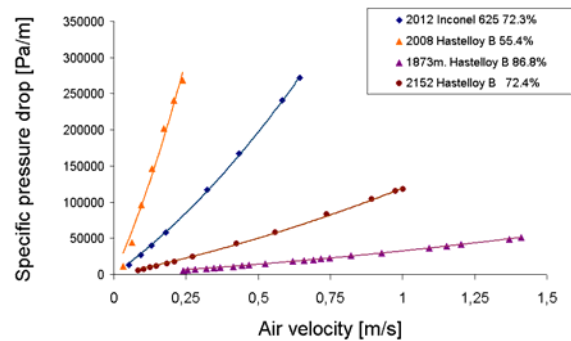


Figure 6: Pressure loss/Air velocity plots generated during permeability measurements

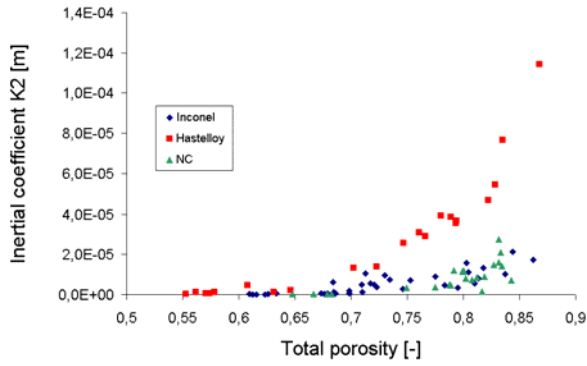


Figure 7: The inertial coefficient as function of the total porosity

4. ANALYTICAL RESULTS

Using the effective material data acquired in the chapters before, the heat flow balance equation for the solid and the fluid phase

$$\lambda_{eff} \frac{d^2 T_s}{dx^2} - \alpha A_v (T_s - T_L) = 0 \quad (3)$$

$$\dot{m} c_p \frac{dT_L}{dx} = -\alpha A_v (T_s - T_L) \quad (4)$$

can be solved analytically as a system of differential equations. Two mass flow rates \dot{m} have been compared under the assumption of a constant heat flow rate

$$\dot{q} = \lambda \frac{dT_s}{dx} = 1 \cdot 10^6 \left[\frac{W}{m^2} \right]$$

The result can be seen in Fig. 8. The surface temperature of 1300 K (for the $\dot{m} = 7 \text{ kg/m}^2\text{s}$ case) rapidly decreases, so that after 2 mm of foam already a constant temperature level is reached.

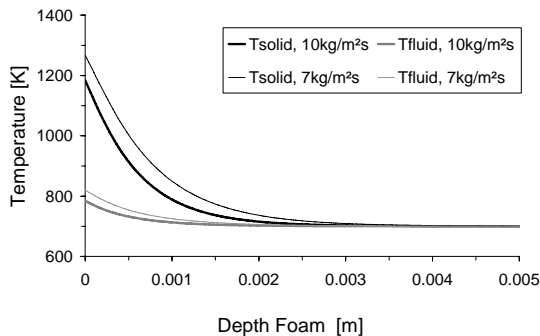


Figure 8: Temperature distribution inside the combustion chamber wall assuming a heat flux of 50 WM/m^2 (1D analytical solution)

5. CONCLUSIONS AND PROSPECTS

The 1D-solution of the heat transfer equation is a first approach to describe the temperature distribution inside the porous combustion chamber wall. However, the presence of large pores of up to 3 mm diameter leads to deviations from symmetry of the temperature field and thus to a non-satisfying accuracy of the 1D approach. To also take into account the local effect of a primary pore on the temperature field, a 2D or 3D calculation is necessary. In this case it has to be regarded, that due to dissipation effects the effective conductivity becomes anisotrope, it becomes larger in the direction perpendicular to the main flow direction. Moreover, this effect is dependent on the velocity of the fluid flow. At the moment an experimental technique to characterize the λ_{EFF} with flow is under development.

ACKNOWLEDEMENTS

The work of the whole research center SFB561 has been funded by the German Research Foundation (DFG). This support is gratefully acknowledged.

REFERENCES

1. D. Bohn. 2002. "New Materials and Cooling Systems for High Temperature, Highly Loaded Components in Advanced Combined Cycle Power Plants," presented at the 7th Liege Conference on Materials for Advanced Power Engineering, Sept. 30 - Oct. 02, 2002
2. D. Bohn, N. Moritz. 2001. "Numerical Investigation on Flow Field and Heat Transfer Phenomena in Multi-Hole Cooling Configurations" presented at the RTO-Symposium, May 2001
3. M.F. Ashby, A. Evans., N.A. Fleck, L.J. Gibson, J.W. Hutchinson, H.N.G. Wadley. 2000. *Metal Foams, a Design Guide*, Butterworth Heinemann, pp. 11-14.
4. Oliver Reutter, Joerg Sauerhering, Elena Smirnova, Thomas Fend, Stefanie Angel, Robert Pitz-Paal. 2006. "Experimental Investigation of Heat Transfer and Pressure Drop in Porous Metal Foams," presented at the 4. ASME ICNMM, June 19-21, 2006
5. S. Angel, W. Bleck, P.-F. Scholz and Th. Fend. 2004. "Influence of powder morphology and chemical composition on metallic foams produced by SlipReactionFoamSintering (SRFS)-process," *Steel Research Int.* **75**, 483-488
6. Th. Fend, D. Trimis, R. Pitz-Paal, B. Hoffschmidt and O. Reutter. 2005. "Thermal Properties", in: M. Scheffler and P. Colombo: "Cellular Ceramics", Wiley VCH.
7. J. Sauerhering, O. Reutter, Th. Fend, R. Pitz-Paal, S. Angel. 2006 "Temperature Dependency of the Effective Thermal Conductivity of Nickel Based Metal," presented at the 4. ASME ICNMM, June 19-21, 2006
8. R. Viskanta, L.B. Younis. 1993. *Int. J. Heat Mass Transfer*, **36**, 1425-1434