

THE JOURNAL OF PHYSICAL CHEMISTRY C

UEA
University of
East Anglia

Subscriber access provided by University of East Anglia Library

Article

An Environmental Friendly Nb-P-Si Solid Catalyst for Acid Demanding Reactions

Antonio Aronne, Martino Di Serio, Rosa Vitiello, Nigel J Clayden, Luciana Minieri, Claudio Imparato, Alessandro Piccolo, Pasquale Pernice, Paolo Carniti, and Antonella Gervasini

J. Phys. Chem. C, **Just Accepted Manuscript** • DOI: 10.1021/acs.jpcc.7b05886 • Publication Date (Web): 26 Jul 2017

Downloaded from <http://pubs.acs.org> on July 31, 2017

Just Accepted

“Just Accepted” manuscripts have been peer-reviewed and accepted for publication. They are posted online prior to technical editing, formatting for publication and author proofing. The American Chemical Society provides “Just Accepted” as a free service to the research community to expedite the dissemination of scientific material as soon as possible after acceptance. “Just Accepted” manuscripts appear in full in PDF format accompanied by an HTML abstract. “Just Accepted” manuscripts have been fully peer reviewed, but should not be considered the official version of record. They are accessible to all readers and citable by the Digital Object Identifier (DOI®). “Just Accepted” is an optional service offered to authors. Therefore, the “Just Accepted” Web site may not include all articles that will be published in the journal. After a manuscript is technically edited and formatted, it will be removed from the “Just Accepted” Web site and published as an ASAP article. Note that technical editing may introduce minor changes to the manuscript text and/or graphics which could affect content, and all legal disclaimers and ethical guidelines that apply to the journal pertain. ACS cannot be held responsible for errors or consequences arising from the use of information contained in these “Just Accepted” manuscripts.



ACS Publications

The Journal of Physical Chemistry C is published by the American Chemical Society, 1155 Sixteenth Street N.W., Washington, DC 20036
Published by American Chemical Society. Copyright © American Chemical Society. However, no copyright claim is made to original U.S. Government works, or works produced by employees of any Commonwealth realm Crown government in the course of their duties.

An Environmental Friendly Nb-P-Si Solid Catalyst for Acid Demanding Reactions

Antonio Aronne^{†*}, Martino Di Serio[‡], Rosa Vitiello[‡], Nigel J. Clayden^{fi}, Luciana Minieri[†], Claudio Imparato[†], Alessandro Piccolo[†], Pasquale Pernice[†], Paolo Carniti[§], and Antonella Gervasini^{§*}

[†] Dipartimento di Ingegneria Chimica, dei Materiali e della Produzione industriale, Università di Napoli Federico II, Piazzale Tecchio, 80, I-80125, Napoli (Italy).

[‡] Dipartimento di Chimica, Università di Napoli Federico II, Complesso Universitario M.te S. Angelo, Via Cintia, 4, I-80126, Napoli (Italy).

^{fi} School of Chemistry, University of East Anglia, Norwich, NR4 7TJ (UK)

[†] Dipartimento di Agraria, Università di Napoli Federico II and Centro Interdipartimentale di Ricerca sulla Risonanza Magnetica Nucleare per l'Ambiente, l'Agro-Alimentare ed i Nuovi Materiali (CERMANU), Università di Napoli Federico II, Via Università 100, I-80055, Portici (Italy).

[§] Dipartimento di Chimica, Università degli Studi di Milano, Via Camillo Golgi, 19, I-20133, Milano (Italy).

1
2
3 **ABSTRACT:** Here we report the structural characteristics, the surface properties and the catalyt-
4 ic performances of a Nb-P-Si ternary oxide material ($2.5\text{Nb}_2\text{O}_5 \cdot 2.5\text{P}_2\text{O}_5 \cdot 95\text{SiO}_2$, 2.5NbP) in two reac-
5 tions of importance for biomass valorisation and green industrial production: hydrolysis of inulin and es-
6 terification of oleic acid with polyalcohol for biolubricant production. High dispersion of the Nb centers,
7 ascertained by UV-vis-DRS, ^{29}Si , ^{31}P and ^1H solid state NMR spectroscopy, is the key-point for the suc-
8 cessful activity of 2.5NbP. *Intrinsic* and *effective* acidities of the sample were studied by FT-IR of ad-
9 sorbed pyridine in absence and presence of water and by volumetric titrations of the acid sites in cyclo-
10 hexane and in water, to enlighten the nature and amount of acid sites in different environment. For both
11 studied reactions, 2.5NbP catalyst exhibits *water tolerant* acidic sites, mainly Brønsted ones, giving
12 higher activity and better stability in the reaction medium than well-known niobium oxophosphate cata-
13 lyst, which is considered one of the best *water-tolerant* acid catalysts.
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

INTRODUCTION

Catalysis is a central science in the development of new, safer and greener chemical processes. Solid acid catalysts are among the most widely used catalysts in industrial chemical processes. Beside to the development of more efficient, safer, and more environmentally friendly acid-catalysts, a typical desired property of the new acid catalysts is tolerance to water. In particular, biorefinery reactions take place in environments where high amounts of water vapour are present, or directly in liquid water (sugar polymer and carbohydrates transformations). Niobium oxophosphate (NbOPO_4 , NbP) is an interesting solid acid catalyst ($\text{H}_0 < -8.2$) with a high ratio of Brønsted (BAS) to Lewis (LAS) acidic sites,¹⁻⁴ which has been used as water-tolerant solid acid catalyst for various reactions of interest in biorefining, such as esterification,⁵ hydrolysis,⁶ dehydration,^{4, 7-12} and alkylation.¹³ The advantages of NbP stem from the recognized stability of Nb-O-P bonds towards hydrolysis and the presence of both kinds of acid sites at the surface. Besides the commercial source from the Companhia Brasileira de Metalurgia e Mineração (CBMM), NbP solid is usually obtained either by impregnation of hydrated niobium oxide with diluted orthophosphoric acid,¹⁴ or by precipitation starting from niobium chloride using concentrated hydrochloric and orthophosphoric acid,¹⁵ or by hydrothermal approaches using neutral¹⁶ or cationic^{9, 16, 17} surfactants. Hydrothermal methods allow the synthesis of mesoporous solids characterized by a high surface area though at the cost of being energy and or time consuming to prepare, requiring procedures with multiple steps. All the synthetic methods listed above need a strictly controlled pH. The prospect of both extending the use of this catalyst with other acid catalyzed reactions and improving its performance has stimulated the preparation of new catalytic systems based on niobium, phosphorus, and silicon,¹⁸⁻¹⁹ as well as of multifunctional catalysts containing noble metals dispersed on NbP.²⁰⁻²² Performance improvements are aimed at modulating the distribution of acid sites and density at the surface by the addition of a third component (Si). So far the preparation of new catalytic systems based on niobium and

1
2
3 phosphorus has required the use of complex combined methods. Ziolk et al.¹⁸ have introduced niobium
4 and phosphorus into silicon mesoporous cellular foams, that were prepared by hydrothermal routes, ei-
5 ther by sol-gel or by post-synthesis impregnation realizing the following molar ratios: Si/Nb = 64, Si/P =
6 50; Si/Nb = 64, Si/P = 10. Choi et al.¹⁹ have prepared mesoporous niobium-phosphate-silicates charac-
7 terized by Nb/P atomic ratios equal to 0.5 and 1 by a solvothermal method combined with solvent evap-
8 oration. These processes are complicated, they need several steps at temperatures higher than room tem-
9 perature and they make use either of different precursors for P (orthophosphoric acid, triethylphosphate
10 and diethylphosphatoethyltriethoxysilane) and for Si (tetraethylorthosilicate and diethylphosphatoethyl-
11 triethoxysilane)¹⁹ or of toxic reactants such as 1,3,5-trimethylbenzene and toluene.¹⁸ Recently, some of
12 us have prepared amorphous niobium–phosphorus–silicon mixed oxide materials, with a molar ratio
13 P/Nb = 1 and an Si content ranging from 95 to 80 mol%, by an innovative hydrolytic sol-gel route from
14 phosphoryl chloride, niobium chloride and tetraethoxysilane, distinguished by the easy manipulation of
15 precursors and wholly performed at room temperature.²³ These solids were characterized by both a very
16 high degree of silicon crosslinking allowing phosphorus to be anchored through Nb-O-P bonds within
17 the framework, and a high content of OH groups even at temperatures higher than 500 °C, that are main-
18 ly linked to phosphorus, making them strong acid solids.

19
20 In this work, the catalytic performances of the solid with the highest silicon content and higher disper-
21 sion of Nb, whose nominal composition can be expressed as $2.5\text{Nb}_2\text{O}_5 \cdot 2.5\text{P}_2\text{O}_5 \cdot 95\text{SiO}_2$ (2.5NbP), were
22 exploited in two reactions of importance for biomass valorisation and green industrial production: hy-
23 drolysis of inulin and esterification of oleic acid with polyalcohols. It was shown that the catalyst exhib-
24 its intrinsic and effective acidities, measured both by FT-IR spectroscopy of pyridine adsorption in ab-
25 sence and presence of water and by acid-base titrations carried out in an apolar-aprotic solvent and in
26 water.²⁴⁻²⁶ The 2.5NbP structure was preserved after treatment in water giving only a partial removal of
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3 strong Brønsted acid sites and some P-leaching. 2.5NbP presents better catalytic performances than the
4 well-known acid catalyst NbP in both studied reactions proving its possible use as efficient water toler-
5 ant catalyst.
6
7
8
9

10 11 12 13 **EXPERIMENTAL SECTION**

14
15 **Catalyst Preparation.** The niobium-phosphorus-silicon mixed oxide **2.5NbP** material was prepared
16 according to a sol-gel procedure previously described,²³ starting from phosphoryl chloride, POCl₃ (99%,
17 Aldrich Chemical), niobium chloride, NbCl₅ (99%, Gelest), and tetraethoxysilane, Si(OC₂H₅)₄ (99%,
18 Gelest), as starting materials. Amorphous gel-derived catalyst was obtained by annealing the dried gel at
19 500 °C (**2.5NbP-500**). The sample was prepared by slow heating at 5 °C·min⁻¹ to the required tempera-
20 ture and held at this temperature for 1 h followed by quenching. To investigate the effective water toler-
21 ance of this sample, it was treated in water under vigorous stirring for 16 h at room temperature
22 (**2.5NbP-500w**). Further details are available in the Supporting Information.
23
24
25
26
27
28
29
30
31
32
33

34 **Catalyst Characterization.** The amorphous nature of the 2.5NbP-500 was investigated by X-ray dif-
35 fraction with a Philips X'PERT-PRO diffractometer by using monochromatized CuK α radiation (40 mA,
36 40 kV) with a step width of 0.013° 2 θ . Ultra-violet and visible light diffuse reflection (UV-vis-DRS)
37 spectra were recorded in the range of 190-800 nm on a double beam Jasco spectrophotometer. Barium
38 sulfate was used a reflectance standard. The measured intensity was expressed as the value of the Ku-
39 belka-Munk function F(R).
40
41
42
43
44
45
46
47

48 ²⁹Si-, ³¹P- and ¹H-NMR spectra were acquired by Direct Polarization (DP) Magic Angle Spinning
49 (MAS) technique with a Bruker AVANCE 300 (Bruker Biospin, Milan, Italy) magnet equipped with a
50 4-mm wide-bore MAS probe and operating at ²⁹Si, ³¹P and ¹H resonating frequencies of 59.6, 121.5 and
51 300.3 MHz, respectively.
52
53
54
55
56
57
58
59
60

1
2
3 Samples were packed in 4 mm zirconia rotors with Kel-F caps and spun at 10000 ± 1 Hz. ^{29}Si spec-
4 tra were acquired using 5352 data points, 1000 scans, a recycle delay of 180 s and a spectral width of
5 400 ppm (23809 Hz); ^{31}P spectra were acquired with 2914 data points, 500 scans, a recycle delay of 150
6 s and a spectral width of 400 ppm (48543 Hz); ^1H spectra were collected with 5352 data points, 16
7 scans, a recycle delay of 60 s and a spectral width of 333 ppm (99954 Hz). High power proton decou-
8 pling was applied with the ^{31}P acquisition only using a 30 ms long TPPM15 composite pulse (-0.5 dB
9 power attenuation), that led to signals enhancement owing to the minimization of long-range proton
10 coupling.
11
12
13
14
15
16
17
18
19
20
21

22 Each spectrum was processed using Bruker Topspin software (v.2.1). In particular, the free induc-
23 tion decays (FID) of ^{29}Si and ^{31}P spectra were Fourier Transformed (FT) by applying a 8 and 4 k zero
24 filling and adopting an exponential filter function, with a line broadening of 100 and 50 Hz, respective-
25 ly. No zero filling and apodization were applied during the FT of ^1H spectrum. Each spectrum was phase
26 and baseline corrected.
27
28
29
30
31
32
33

34 Morphologic characteristics of 2.5NbP-500 were studied by N_2 adsorption and desorption iso-
35 therms measured at liquid nitrogen temperature with an automatic surface area analyzer (Sorptomatic
36 1900 instrument). Prior to the measurements, thermal activation at 150°C for 16 h (overnight) was per-
37 formed under vacuum.
38
39
40
41
42

43 Lewis and Brønsted acid sites (LAS and BAS) of 2.5NbP-500 as well as their tolerance to water,
44 were investigated by Fourier Transform Infrared Spectroscopy (FT-IR) (Biorad FTS-60A) using pyri-
45 dine as probe molecule both in vapor phase and aqueous solution. The samples were pressed into 10-15
46 mg self-supporting disk (0.65 cm^2 geometrical area) and before each analysis they were activated at 150
47 $^\circ\text{C}$ for 2 h under air. After outgassing for 30 minutes in high vacuum, the sample was contacted with
48 pyridine vapors at room temperature for 10 minutes or, alternatively, a 1×10^{-3} M pyridine aqueous solu-
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3 tion was dropped on self-supporting disks under argon flow. After pyridine adsorption, the sample was
4
5 outgassed for 30 minutes in high vacuum at several temperatures (i.e. RT, 50, 100 °C) without the pos-
6
7 sibility to realize higher temperatures due to the violent evaporation of water that caused the rupture
8
9 disk. BAS and LAS concentration (expressed as $\text{meq g}_{\text{cat}}^{-1}$) was determined by integrating the peaks at
10
11 1540 and 1448 cm^{-1} , respectively, of the spectra collected after outgassing at 100 °C.
12
13
14

15 The amount of acid sites of 2.5NbP-500 was measured by using 2-phenylethylamine (PEA) as
16
17 basic probe in cyclohexane for the *intrinsic* acidity (I.A.) and in water for the *effective* acidity (E.A.) at
18
19 30 °C by working in an adsorption HPLC line specifically assembled for this purpose.^{4, 25, 26} Further de-
20
21 tails are available in the Supporting Information.
22
23
24

25 **Activity Tests.** The tests of the catalytic hydrolysis of inulin were performed in water in a glass
26
27 slurry batch reactor (Syrris, Atlas, UK) with magnetic stirrer at constant rate of 800 rpm under increas-
28
29 ing temperature from 50 to 90 °C ($0.12 \text{ °C} \cdot \text{min}^{-1}$, for a total of 6 h of reaction).
30
31

32 Inulin, in powder form, was a commercial pure product (Carlo Erba, RPE) with a number-
33
34 averaged degree of polymerization (DP_n) of 25, evaluated on the basis of the ratio of fructose to glucose
35
36 residues in inulin and considering that each molecule of inulin contains one glucose residual (at the
37
38 chain end point). The catalyst sample (ca. 0.3 g sieved between 20-80 mesh) was treated at 120 °C over-
39
40 night (ca. 16 h) in oven under air atmosphere. Inulin (1.5 g) was dissolved in 150 mL water (concentra-
41
42 tion, 55 mM). For each catalyst, two different catalytic tests were performed by using i) fresh and dried
43
44 catalyst samples and ii) catalyst sample stabilized in water overnight (at r.t.) to verify the activity of the
45
46 sample after water stabilization. In detail, the weighted and dried sample was put in the reactor filled
47
48 with water where it was maintained for 16 h (overnight) at room temperature under gentle stirring, then,
49
50 a weighted amount of inulin was added to obtain an inulin solution at the desired concentration; then, the
51
52 reaction started, while the temperature was allowed to increase (0.12 °C/min).
53
54
55
56
57
58
59
60

1
2
3 The yield to reducing sugars (corresponding to the extent of reaction and called *inulin conversion*
4 herein after below) was evaluated as the ratio between the reducing sugars produced and the reducing
5 sugars at complete hydrolysis of substrate. The selectivity to fructose and glucose was determined on the
6 basis of the ratio between fructose or glucose formed and the reducing sugars produced.
7
8
9
10
11

12 The reaction was followed by measuring the total reducing sugars by the classical colorimetric
13 Nelson-Somogyi method by using copper(II) sulfate pentahydrate ($\text{Cu}(\text{SO}_4) \cdot 5\text{H}_2\text{O}$, Carlo Erba, RPE)
14 and ammonium molybdate ($(\text{NH}_4)_6\text{MoO}_{14} \cdot 4\text{H}_2\text{O}$, Carlo Erba, RPE) salts. The blue complex formed was
15 analyzed and quantified at 520 nm. Moreover, the presence of glucose and fructose was determined by a
16 Boehringer enzymatic assay technique.
17
18
19
20
21
22
23

24 The kinetic coefficients at the average temperature T_m between two samplings (k_{T_m}) were calcu-
25 lated by the Eq. (1):
26
27

$$28 \quad k_{T_m} = (\Delta C / \Delta t) / C_m \quad \text{Eq. (1)}$$

29 where Δt is the time variation between two samplings ($\Delta t = 30$ min and $\Delta T = 5$ °C); ΔC is the variation
30 of bond concentration between two samplings; C_m is the average bond concentration between two sam-
31 plings.
32
33
34
35
36
37

38 The esterification reaction was carried out in a 100 mL glass reactor equipped with a magnetic
39 stirrer. Oleic acid and the catalyst (previously dried at 110 °C for 3h) were initially loaded into the reac-
40 tor. The reactor was heated to the desired temperature and then polyalcohol loaded into the reactor with
41 a constant flow of nitrogen (20 NL/h) for a continuous stripping of the water from the reactive mixture.
42 During each experimental run, samples were periodically withdrawn, in order to determine the evolution
43 of the reaction products composition during the time. The withdrawn samples of the reaction mixture
44 were analyzed by a standard acid–base titration procedure for the evaluation of the free residual acidity.
45 The operative conditions for all the esterification runs were: temperature 180 °C, alcohol: acid molar ra-
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3 tio 1: 2, catalyst concentration 1% wt (based on reaction mixture). The catalysts after the reaction were
4
5 recovered by centrifugation and in some cases were reused to study the stability to deactivation.
6
7
8
9

10 RESULTS AND DISCUSSION

11
12 **Structural Characteristics.** An amorphous gel-derived catalyst (2.5NbP-500) obtained by anneal-
13
14 ing the 2.5NbP dried gel at 500 °C for 1 h and the same catalyst treated at room temperature for 16 h in
15
16 water (2.5NbP-500w) were studied in order to verify its effective water tolerance.
17
18
19

20 The analysis of the powder X-ray diffraction (PXRD) pattern of 2.5NbP-500 clearly shows its
21
22 amorphous nature as well as the lack of any segregated crystalline phase (Figure 1).
23
24

25 UV-vis-DRS spectroscopy was used to determine the coordination geometry and chemical ar-
26
27 rangement of the niobium species on the surface of the investigated samples since the band gap energies
28
29 which can be derived from the spectra are known to depend on the coordination symmetry of the niobi-
30
31 um involved with the electronic transition. Figure 2 shows the UV-vis-DRS spectra of 2.5NbP-500 and
32
33 2.5NbP-500w along with the spectra of NbP and Nb₂O₅ reference samples, as well as the corresponding
34
35 Tauc equation plots.²⁷ Band gap energies (E_g) were found using these plots from the intercept of the ex-
36
37 trapolated linear absorption edge with the energy axis. The value found for Nb₂O₅ ($E_g = 3.14$ eV, 395
38
39 nm) is very close to the literature value reported for crystalline Nb₂O₅ having a structure formed by cor-
40
41 ner-sharing NbO₆ octahedra in which a large fraction of niobium atoms lies in sites characterized by
42
43 high coordination symmetry.²⁸ Therefore the above optical band gap is related to charge transfer (CT)
44
45 arising from excitation of an electron of the 2p oxygen valence band to the empty 4d niobium conduc-
46
47 tion band belonging to high symmetry NbO₆ octahedra.^{29, 30} CT involving niobium atoms belonging to
48
49 Nb polyhedra characterized by a lower symmetry, low distorted NbO₆ octahedra (i.e. edge-sharing NbO₆
50
51 octahedra), high distorted NbO₆ octahedra (i.e. face-sharing NbO₆ octahedra, disordered NbO₆ octahe-
52
53
54
55
56
57
58
59
60

1
2
3 dra), high symmetry NbO₄ tetrahedra (i.e. corner-sharing NbO₄ tetrahedra), distorted NbO₄ tetrahedra
4
5 (i.e. edge- or face-sharing NbO₄ tetrahedra, disordered NbO₄ tetrahedra), isolated NbO₄ tetrahedra, are
6
7 associated with progressively higher E_g values.^{29,30} Two optical band gaps were discovered for NbP (E_{g,1}
8
9 = 3.71 eV, E_{g,2} = 4.80 eV) indicating the presence in this sample both of low symmetry NbO₆ octahedra
10
11 and disordered NbO₄ tetrahedra as a consequence of its amorphous nature. The same E_g was observed
12
13 for 2.5NbP-500 and 2.5NbP-500w (E_g = 3.86 eV) demonstrating that the water treatment does not modi-
14
15 fy the distribution of surface Nb species.
16
17

18
19 The UV-vis spectrum of Nb₂O₅ shows the typical feature of a polycrystalline sample of niobium oxide
20
21 with absorptions at about 257, 310, and 350 nm that are related to NbO₆ octahedra with different sym-
22
23 metry: face-sharing, edge sharing and corner-sharing, respectively. The NbP spectrum reflects its amor-
24
25 phous nature with features at about 270 and 208 nm that are related to CT relating to NbO₆ octahedra
26
27 and NbO₄ tetrahedra, respectively. The residual absorption in the 300-350 nm range indicates the pres-
28
29 ence also of high symmetry NbO₆ octahedra.
30
31

32
33 Curves fitting of 2.5NbP-500 and 2.5NbP-500w spectra were performed (Figure S1 of Supporting In-
34
35 formation) for a better insight in their similarities confirming that the water treatment does not change
36
37 the distribution of surface NbO_x species and the results are summarized in Table 1. For each sample CT
38
39 transitions associated with isolated NbO₄ tetrahedra (~ 200 nm), low distorted NbO₄ tetrahedra (~ 230
40
41 nm), high distorted NbO₆ octahedra (~ 265 nm) and low distorted NbO₆ octahedra (~300 nm) are
42
43 seen.²⁸⁻³⁰ This assignment also agrees with the recent interpretation proposed by Tranca et al.³¹ for sili-
44
45 ca-supported niobium oxide catalysts. They, based on DFT calculations, assigned the UV band at about
46
47 260 nm to penta-coordinate niobium atoms, that indeed can be seen as high distorted NbO₆ octahedra.
48
49
50
51

52
53 A high degree of silicon cross-linking occurs in the siloxane network for both the 2.5NbP-500 ma-
54
55 terials as a consequence of the sol-gel procedure used, as revealed by the ²⁹Si NMR (Figure 3). Cluster-
56
57
58
59
60

1
2
3 ing of NbO₆ octahedra containing Nb-O-X (X = Si and/or P) bridges and of NbO₄ tetrahedra conse-
4
5 quently can occur. Notably, the formation of these bridges requires the occurrence of different kinds of
6
7 distorted NbO₆ octahedra, while the stabilization of the four-fold coordination of Nb⁵⁺ plays a key role
8
9 in realizing the interconnected network in which the cross-condensation between Nb- and P-units allows
10
11 the formation of P-O-X (X = Nb and/or P) bridges, in agreement with the UV-vis analysis.
12
13

14
15 ²⁹Si, ³¹P, and ¹H solid state NMR spectra of 2.5NbP-500 and 2.5NbP-500w are shown in Figures 3
16
17 a), 3b), and 3c) respectively. Prior to ¹H MAS NMR experiments, the samples were dehydrated at 100
18
19 °C for one day and then introduced into the sample holder using a glove-box. Distinct chemical shifts
20
21 ranges are seen in both the ²⁹Si and ³¹P NMR spectra for the various degrees of connectivity of the struc-
22
23 tural units as described by the Q_N notation^{32,33} where N is the number of bridging oxygen of the tetrahe-
24
25 dral unit.
26
27

28
29 Overall the ²⁹Si NMR data indicate extensive cross-linking with 70.0% Q₄ units and 25.0% Q₃
30
31 units for 2.5NbP-500 and 69.2% Q₄ units and 26.6% Q₃ units for 2.5NbP-500w. Consequently the ob-
32
33 servation of only minor differences between the ²⁹Si NMR spectra of the materials before and after ex-
34
35 posure to water indicates, as expected, the silicate network is essentially unaffected by the water expo-
36
37 sure. In contrast significant differences were observed in the ³¹P NMR spectra before and after exposure
38
39 to water as can be seen from the detailed curve fitted resonances, (Table 2) implying a modification in
40
41 the network connectivity. Notably there is a marked decrease in the relative intensity of the Q₁' reso-
42
43 nance at ~ -9 ppm which has been assigned to a terminal type phosphate.
44
45
46
47

48
49 First and foremost though it is important to recognize there remains significant intensity associated
50
51 with chain type phosphates with the Q₂' and Q₃' resonances. This is of particular importance as it estab-
52
53 lishes the majority of the phosphorus is still anchored into the silicate matrix. Unlike all previous sam-
54
55 ples of silico-phosphates which have shown the creation of monomeric phosphate, and hence detach-
56
57
58
59
60

1
2
3 ment from the silicate network upon long exposure to even atmospheric moisture. The decrease in the
4 amount of Q_1' can be understood either in terms of further cross-linking despite the hydrolytic condi-
5 tions or the loss of terminal phosphate groups through leaching. Of these explanations the latter is the
6 more plausible and assuming this is the only source of loss of phosphorus it can be estimated that 32 %
7 of the total phosphorus has been lost.
8

9
10 Owing to the chemical nature of the materials in question, ^1H NMR will highlight two types of en-
11 vironment in the sample, hydroxyl groups and bound water. The hydroxyl groups may be terminal or
12 bridging and associated with silicon, phosphorus or niobium (X-OH , $\text{X} = \text{Si}$, P and Nb ; X-O(H)-Y , with
13 X , $\text{Y} = \text{Si}$, P and Nb). Assignment of the resonances to a particular environment is fraught with difficul-
14 ty though generally terminal Si-OH are found around 2 ppm except inaccessible isolated ones may be
15 found as shielded as 1.1 ppm³⁴ while resonances around 5 ppm could be any bridging Si-O(H)-X ($\text{X} = \text{P}$,
16 Nb). Terminal X-OH ($\text{X} = \text{P}$, Nb) are expected to be more shielded and may be found in the range 0-1
17 ppm.³⁵ A further complication is that hydrogen bonding of terminal type hydroxyl will lead to deshield-
18 ing with the result ab initio calculations predict even Si-OH can be as deshielded as 5-11 ppm.³⁶ In view
19 of the uncertainty in the assignments any explanation for the changes in the ^1H NMR spectrum on ex-
20 posing the 2.5NbP material to water must be tentative. Nevertheless, the changes can be understood in
21 terms of the known hydrolytic instability of surface cross-linking bonds such as Si-O-P .
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42

43 Previous ^{29}Si and ^{31}P MAS NMR has established a structure for the 2.5 NbP-500 material based on
44 a silicate network with cross-linking between the phosphorus and niobium anchoring the phosphorus
45 through the niobium to this network P-O-Nb-O-Si . Some evidence was also found in the earlier work for
46 Si-O-P since small changes were seen in the ^{31}P NMR spectrum on exposure to atmospheric moisture. It
47 should be noted that the very fact these changes were small provided strong evidence for the indirect an-
48 choring of the phosphorus through the niobium. The silicate network is characterised, through terminal
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3 Si-OH, by the resonances seen at 2 ppm. Less clarity is afforded by the single broad resonance at 5.5
4
5 ppm. In all likelihood this represents a heterogeneous mix of environments involving the phosphorus
6
7 and niobium such as P-O(H)-Nb. These hydrogens would represent the source of the Brønsted acidity in
8
9 non-aqueous solvents. Indeed in the case of alumina impregnated with niobium oxide, it has been pro-
10
11 posed that a broad resonance at 8 ppm but 10 ppm wide corresponds to Nb-O(H)-Nb Brønsted acid sites.
12
13 Such a broad line would encompass the ^1H chemical shifts seen for 2.5 NbP-500.³⁷ Upon exposure to
14
15 water the resonance at 2 ppm remains unchanged, as expected given the inertness of silicate networks to
16
17 hydrolysis. However, new resonances appear around 1.8 ppm typical of terminal Si-OH. The most plau-
18
19 sible explanation of these is the hydrolysis of any Si-O-P formed during the synthesis. Changes in the
20
21 resonance at 5.5 ppm assigned to the hydrogen associated with the phosphorus and niobium must be re-
22
23 lated to hydrolytic instability of the cross-linking, however, it is clear from the ^{29}Si that bulk material is
24
25 largely unaltered. Again, it is probable that the broad resonance centered at 4 ppm will represent a varie-
26
27 ty of P-OH and Nb-OH environments while the observed increase in ^1H shielding is consistent with hy-
28
29 drolysis of X-O-Y (X, Y = P, Nb) giving rise to X-OH and Y-OH. Further support for this hydrolysis is
30
31 provided by the greater intensity seen for the 4 ppm resonance in the sample after exposure to water
32
33 compared with the 5.5 ppm resonance before water exposure.
34
35
36
37
38
39
40

41 **Morphologic Characteristics.** The isotherms of N_2 adsorption and desorption at 77 K collected
42
43 on 2.5NbP-500 indicate its porous character and high surface area (Figure 4).
44

45
46 The adsorption isotherm is a combination of type I (solid with micropores) and IV (solid with
47
48 mesopores), according to the IUPAC classification. The observed hysteresis loop at around $P/P^\circ=0.5$ is
49
50 characteristic for type H4 loop. Type H4 hysteresis is associated with particles containing small pores
51
52 including the micropores. In addition, the first part of the adsorption isotherm is typical of samples con-
53
54 taining micropores (< 2 nm), that is, high N_2 adsorption at very low P/P° values and sharp knee of the
55
56
57
58
59
60

1
2
3 isotherm (B point, which indicates the completion of the monomolecular N₂ layer). Thus it is apparent
4 that 2.5NbP-500 doesn't have a single pore type but instead a combination of micropores and meso-
5 pores. The surface area of 2.5NbP-500 was calculated by the classical 2-BET and 3-BET equations ob-
6 taining surface area values of 524 and 532 m²·g⁻¹, respectively. Positive value for the C_{BET} constants and
7 an average number of N₂ layers on the whole surface of 2.6 were obtained. The results suggest a pre-
8 dominantly mesoporous character for 2.5NbP-500, though with some micropores. The total porosity
9 evaluated by the Gurvich rule was 0.33 cm³·g⁻¹, that comprises interparticle and intraparticle porosity, of
10 this the mesopore volume determined by BJH model equation was 0.14 cm³·g⁻¹. The mesopore size is
11 centered at 3.20 nm (Figure 4 a') and the micropore volume is 0.12 cm³·g⁻¹, as determined by the Dubin-
12 in Raduskevich equation (Figure 4 a''). For sake of comparison, the N₂ isotherms of adsorption-
13 desorption of NbP together with its morphological properties are reported in Figure S2 of Supporting In-
14 formation.

15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32 **Acidity Determinations.** The acid properties of 2.5NbP-500 and of NbP, used as reference sam-
33 ple, were determined by two approaches: spectroscopic determination of the nature (BAS or LAS) of ac-
34 id sites by FT-IR of adsorbed pyridine and liquid-solid acid-base titrations using 2-phenyl-ethyl-amine
35 (PEA) as basic probe molecule. Figure 5 shows the FT-IR spectra of pyridine adsorption on 2.5NbP-500
36 recorded after pyridine desorption at 100°C in the interval 1700 to 1350 cm⁻¹. The two spectra refer to
37 pyridine adsorption in gas-phase and in aqueous solution (10⁻³ M). Both BAS and LAS could be ob-
38 served under the two different conditions, absence and presence of water. Table 3 reports the quantita-
39 tive results of the spectroscopic adsorption of pyridine on 2.5NbP-500 and comparatively on NbP. In ab-
40 sence of water, a similar amount of LAS were found for 2.5NbP-500 and NbP, despite that the nominal
41 content of Nb is much lower on 2.5NbP-500 than on NbP (about 7 and 47 Nb wt%, respectively). This
42 result can be related to a better dispersion and accessibility of Nb sites occurring in the studied catalyst
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3 than in NbP, as proved by the UV-vis characterization showing the presence of NbO₄ tetrahedra with a
4 low distortion degree (isolated) dispersed into the mixed Si-P framework of 2.5NbP-500. According to
5
6
7
8 ¹H MAS NMR analysis, the higher presence of BAS on 2.5NbP-500 than on NbP (LAS/BAS, 1.06 and
9
10 2.10 for 2.5NbP-500 and NbP, respectively) was expected as two types of environment were found for
11
12 2.5NbP-500: hydroxyl groups and bound water. The former is related to terminal X-OH, with X = Si, P
13
14 and Nb, the latter relates to bridging hydrogen X-O(H)-Y, with X, Y = Si, P and Nb, formed by H-
15
16 bonding between water and X-O-Y bridging oxygen. It is noteworthy that in this condition (absence of
17
18 water) there is a high contribution of Si-OH groups.
19
20
21

22 More interestingly, in the presence of water for 2.5NbP-500 both LAS and BAS concentrations
23
24 decrease but this trend is more pronounced for LAS giving a LAS/BAS ratio equal to 0.39. The strong
25
26 decrease of LAS occurring in 2.5NbP-500 in comparison with NbP can be related to the greater hydroly-
27
28 sis rate of NbO₄ tetrahedra with respect to the NbO₆ octahedra, producing Nb-OH terminal groups. Sup-
29
30 port for this hydrolysis is also provided by the comparison of ¹H NMR of the sample before and after
31
32 exposure to water. This phenomenon partially counteracts the missed contribution of the Si-OH groups
33
34 and the loss of P-OH terminal groups due to P leaching, which does not occur in the same extent for
35
36 NbP, giving a LAS/BAS four times greater than 2.5NbP-500. In other words, in the presence of water
37
38 the BAS concentration in 2.5NbP-500 is about twice the value for NbP.
39
40
41
42

43 Concerning the liquid-solid acid-base titrations, PEA was chosen for its high basicity and easy de-
44
45 tection in the UV-region ($\lambda_{\max} = 254$ nm). The titrations were carried out in two liquids with different
46
47 physical properties: cyclohexane with apolar and aprotic properties and water with polar, protic, and
48
49 solvating properties. Owing to the different characteristics of the two liquids, titrations in cyclohexane
50
51 allowed the determination of the so called *intrinsic* acidity of the samples. In contrast, titrations in water
52
53 gave the *effective* acidity of the samples, as water is able to have specific chemical interactions with giv-
54
55
56
57
58
59
60

1
2
3 en functional groups of the surface and to cause hydrolytic action.²⁴⁻²⁶ All the PEA adsorption isotherms
4 collected at 30 °C in the two liquids are shown in Figure 6. All the isotherms obtained were Langmuir in
5 type for both the solvents, the differences between the attained *plateau* of adsorption between the first
6 and second runs were due to the presence of higher or lower numbers of strong acid sites on the two
7 samples.
8
9

10 The acidity measured in cyclohexane was much higher on 2.5NbP-500 (0.600 mequiv·g⁻¹ of acid
11 sites) than on NbP (0.403 mequiv·g⁻¹ of acid sites), with a high and similar percentage of strong acid
12 sites in both samples (86%). Different results were obtained by titrating the sample acidity in water; the
13 number of acid sites titrated was greatly decreased on 2.5NbP-500 (0.126 mequiv·g⁻¹ of acid sites) and
14 only slightly on NbP (0.350 mequiv·g⁻¹ of acid sites), ca. 79 % and 13 % of acidity decrease, respective-
15 ly, in comparison with the titrations performed in cyclohexane. The *effective* acidity was higher on NbP
16 (31% of strong acid sites in water) than on 2.5NbP-500, which does not show any strong acidity in
17 agreement with the above trends of LAS/BAS ratio. In the presence of water a substantial reduction of
18 P-OH occurs for 2.5NbP-500 leaving on its surface weak BAS, mainly Si-OH and Nb-OH that are not
19 able to adsorb PEA because they are engaged with water coordination (H-bonding). Then, the lower av-
20 erage acid strength of 2.5NbP-500 surface in comparison with the acid surface of NbP could give bene-
21 fits for improving the catalyst stability in given catalytic reactions in which NbP has been already stud-
22 ied (fructose dehydration, cellobiose hydrolysis, etc.). The high acid strength of NbP surface provoked
23 irreversible adsorption of reagents/intermediates with formation of humic material responsible of a fast
24 catalyst deactivation.^{4,25}
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49

50 **Catalytic Activity Tests.** Inulin is a natural polysaccharide consisting of linear chains of fructose
51 residues linked by β-1,2 bonds and terminated with a sucrose residue; it acts as energy reserve in various
52 plants (e.g., chicory and Jerusalem artichoke) that can grow in hardly exploitable marginal areas. The
53
54
55
56
57
58
59
60

1
2
3 exploitation of such cultivations and the resulting inulin extraction make possible production of syrups
4 with higher fructose content than from other traditional processes, like glucose isomerization.³⁸⁻⁴⁰ The
5 reaction of inulin hydrolysis can be carried out by employing inorganic catalysts or biocatalysts (in-
6 ulinases). Among inorganic catalysts, protonic acid solid catalysts (with BAS sites) are promising. NbP
7 has long been used in several reactions aimed at improving the value of saccharides and polysaccha-
8 rides, thanks to its BAS and LAS at the surface. When NbP is used without any severe thermal treat-
9 ment, it is highly protonic acid and it can catalyze the same reactions of acid catalysts in homogeneous
10 liquid phase. Inulin hydrolysis can be easily followed by measuring the total reducing sugar concentra-
11 tion, formed by the breaking of the bonds between the monosaccharide units that form this organic pol-
12 ymer. The time course of the inulin hydrolysis was studied in water as a function of time/temperature in
13 the 50-90 °C interval by adding the dry catalyst samples in comparison with the samples stabilized in
14 water for long time before the reaction. In so doing, the intention was to control the stability of the sam-
15 ples to the hydrolytic action of water, i.e., the stability of the Nb-O-P bonds.
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33

34 Figure 7 shows the increasing trends in the formation of the total reducing sugars for both the NbP
35 (Figures 7 a, b, and c) and 2.5NbP-500 (Figures 7 a', b', and c') samples in the studied temperature in-
36 terval. Inulin hydrolysis started at ca. 67-70 °C (corresponding to 2.5-3 h of reaction) and reached more
37 than 80% using either of the fresh catalysts at the highest reaction temperature (90 °C corresponding to 6
38 h of reaction). It is noteworthy to observe that the curves of 2.5NbP-500 (fresh and water stabilized cata-
39 lysts, Figure 7 a') are perfectly superposed, indicating that the sample did not suffer any deactivation of
40 the catalytic sites by water. The same observation does not hold for NbP (Figure 7 a), in this case the
41 curve for the water stabilized NbP sample lies under that of the fresh NbP sample at each
42 time/temperature of reaction. In all likelihood, some hydrolytic effect of water on NbP has occurred that
43 has caused phosphorus leaching. Indeed, leaching experiments from aqueous solutions in the presence of
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3 NbP and 2.5NbP-500 have indicated the loss of phosphorus of ca. 15% for NbP (P nominal content, 6.94
4 wt%) and of 28% for 2.5NbP-500 (P nominal content, 2.30 wt%), with higher values in hot water. This
5 observation is in contrast with the known properties of NbP (stability and insolubility in water) and fur-
6 ther studies will be necessary in view of the real application of these materials in aqueous catalysis. The
7 total reducing sugars analyzed correspond to the monosaccharides, glucose and fructose, the increasing
8 inulin conversion led to higher selectivity towards these monosaccharides. Indeed, the molar ratio of
9 monosaccharides to total sugars produced at the highest inulin conversion attained was ≥ 0.9 for 2.5NbP-
10 500 (Figure 7 b') and between 0.8-0.9 for NbP (Figure 7 b). These figures depict unique trends in the ra-
11 tio of fructose plus glucose to reducing sugars for each catalyst regardless of the catalyst treatment (fresh
12 or water stabilized).

13
14
15
16
17
18
19
20
21
22
23
24
25
26
27 Moreover, the ratio of fructose to glucose (F/G) produced by the hydrolysis was much higher at
28 low inulin conversion and the ratio diminished with conversion, as expected. Activation parameters for
29 the two catalysts were determined from Arrhenius plots (Figures 7 c and 7 c') for NbP and 2.5NbP-500,
30 respectively) using the rate constants calculated at T_m (average temperature on 30 min of reaction) (Ta-
31 ble 4). Two distinct parallel lines can be seen for the fresh and water stabilized NbP catalyst, while a
32 single line can be fitted to the data for the fresh and water stabilized 2.5NbP-500 catalyst. The calculated
33 apparent activation energy values did not differ significantly for the two catalyst samples (E_a around 143
34 $\text{kJ}\cdot\text{mol}^{-1}$ and $\ln A$ around 47).

35
36
37
38
39
40
41
42
43
44
45
46 Esterification of fatty acids with high boiling polyalcohols is a potentially valuable reaction for in-
47 dustry because the esters formed can be used as biolubricants.⁴¹ Alternatively, esterification of fatty ac-
48 ids with methanol can be used to produce biodiesel. A great number of heterogeneous catalysts have
49 been proposed for these reactions.⁴²⁻⁴⁶ Recently, NbP has also been used as esterification catalyst for fat-
50 ty acids with alcohols (methanol, ethanol, 1-butanol).⁵ Here the esterification of oleic acid (OA) and
51
52
53
54
55
56
57
58
59
60

1
2
3 nonanoic acid (NA) with polyalcohols (1,3 propandiol (PD), trimethylolpropane (TMP), pentaerythritol
4 (PE)) by NbP and 2.5NbP-500 catalysts was studied. Nonanoic acid is not a natural fatty acid but it is
5
6 the coproduct of azelaic acid synthesis from oleic acid.⁴⁷
7
8

9
10 The conversion of OA and NA is reported in Figure 8 for both catalysed and non-catalysed runs.
11
12 One contribution to the difference in the reaction rate observed for the different substrates is the higher
13 concentration of fatty acids in the reaction mixture for TMP and PE in respect to PD because a stoichi-
14 ometric fatty acid/alcohol molar ratio was used. A higher concentration of fatty acids will favour an au-
15 to-catalytic mechanism, mainly at the beginning of the reaction. Although the activity of NbP is greater
16 than the activity of 2.5NbP-500 in every case, in agreement with the higher effective acidity of NbP, of
17 more importance is the greater stability of the 2.5NbP-500 catalyst. From Figure 8 d it is evident that the
18 recovered NbP has lower activity than the corresponding 2.5NbP-500 after the first use and the activity
19 of 2.5NbP-500 catalyst remains constant at least after 3 reuses (see Figure 8 e). Also in the case of ester-
20 ification the catalyst stability is favoured by the lower average acid strength of 2.5NbP-500 surface in
21 comparison with that of NbP. The lower acid strength of 2.5NbP-500 than that of NbP depends from its
22 structure, as it is not a mere dispersion of NbP in a silica matrix but it is a ternary system with Si-O-Nb-
23 O-P bridges, in which the components are uniformly dispersed at the molecular level.
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42

43 CONCLUSIONS

44
45 The studied Nb-P-Si ternary oxide material is characterised by a very high polymerization degree
46 giving a silicate matrix in which phosphate units are stably anchored by niobium bridges. Niobium can
47 then have high dispersion in the silicate matrix giving a high LAS concentration, despite the low niobi-
48 um content in the composition. The peculiar acidic properties of this solid, the high concentration of
49 both BAS and LAS sites, were for the most part preserved after treatment in water, especially concern-
50
51
52
53
54
55
56
57
58
59
60

1
2
3 ing BAS sites. Only a partial removal of strong BAS and some phosphorus leaching occur, leading to
4
5 some loss of the less polymerised Q₁' units. Despite these surface modifications after water contact, the
6
7 BAS concentration in the Nb-P-Si material remained about twice the value for NbP, showing the high
8
9 water-tolerance of the acid sites of the ternary oxide. On the other hand, the titrated *effective* acidity of
10
11 the Nb-P-Si material was lower than that of NbP because of the presence on its surface of weak BAS
12
13 sites, mainly Si-OH and Nb-OH. Consequently, it showed excellent catalytic performances in two im-
14
15 portant reactions which are known requiring acid sites: the hydrolysis of inulin and the esterification of
16
17 oleic acid with polyalcohols. Indeed, higher conversion and selectivity to monosaccharides (fructose and
18
19 glucose) were observed for the Nb-P-Si catalyst stabilized for long time in water with respect to NbP.
20
21 Moreover, the moderate acidity of the Nb-P-Si catalyst allows keeping alive its activity for more reuses
22
23 in the esterification of oleic acid with polyalcohols.
24
25
26
27
28

29 Therefore, this new ternary oxidic sample can be considered as an interesting material in the emerging
30
31 field of heterogeneous acid catalysis in water, or involving water or polar-protic species as solvent, rea-
32
33 gent, or product, in view of the development of new catalysts for *green* reactions.
34
35
36
37

38 ASSOCIATED CONTENT

39 Supporting Information

40
41 The Supporting Information is available free of charge on the ACS Publications website. Details con-
42
43 cerning the preparation procedure of the studied material, the characterization of its surface acidic prop-
44
45 erties, the curves fitting of 2.5NbP-500 and 2.5NbP-500w UV-vis DRS spectra, as well as the N₂ ad-
46
47 sorption-desorption isotherms of NbP and its main morphological data (PDF).
48
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3 **AUTHOR INFORMATION**
4

5 **Corresponding Authors**
6

7
8 *To whom correspondence should be addressed:
9

10 Antonio Aronne, Tel. +390817682556, E-mail: anaronne@unina.it;
11

12 Antonella Gervasini, Tel. +390250314254, E-mail: antonella.gervasini@unimi.it.
13
14

15 **Notes**
16

17 The authors declare no competing financial interest.
18
19
20
21
22
23

24 **ACKNOWLEDGMENTS**
25

26
27 The authors thank Dr. Pierluigi Mazzei and the Centro Interdipartimentale di Ricerca sulla Risonanza
28 Magnetica Nucleare per l'Ambiente, l'Agro-Alimentare ed i Nuovi Materiali (Università di Napoli
29 Federico II) for MAS NMR measurements. Dr. Filippo Bossola from Istituto di Scienze e Tecnologie
30 Molecolari (ISTM-CNR) of Milano is gratefully acknowledged for the FT-IR experiments.
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

REFERENCES

- (1) Martins, R. L.; Schitine, W. J.; Castro, F. R. Texture, surface acidic and catalytic properties of niobium phosphate. *Catal. Today* **1989**, *5*, 483-491.
- (2) Okuhara, T. Water-tolerant solid acid catalysts. *Chem. Rev.* **2002**, *102*, 3641-3666.
- (3) Ziolk, M. Niobium-containing catalysts - the state of the art. *Catal. Today* **2003**, *78*, 47-64.
- (4) Carniti, P.; Gervasini, A.; Biella, S.; Auroux, A. Niobic acid and niobium phosphate as highly acidic viable catalysts in aqueous medium: Fructose dehydration reaction. *Catal. Today* **2006**, *118*, 373-378.
- (5) Bassan, I. A. L.; Nascimento, D. R.; San Gil, R. A. S.; Pais da Silva, M. I.; Moreira, C. R.; Gonzalez, W. A.; Faro Jr., A. C.; Onfroy, T.; Lachter, E. R. Esterification of fatty acids with alcohols over niobium phosphate. *Fuel Process. Technol.* **2013**, *106*, 619-624.
- (6) Marzo, M.; Gervasini, A.; Carniti, P. Hydrolysis of disaccharides over solid acid catalysts under green conditions. *Carbohydr. Res.* **2012**, *347*, 23-31.
- (7) Rao, G. S.; Rajan, N. P.; Pavankumar, V.; Chary, K. V. R. Vapour phase dehydration of glycerol to acrolein over NbOPO₄ catalysts. *J. Chem. Technol. Biotechnol.* **2014**, *89*, 1890-1897.
- (8) Ordonsky, V. V.; Sushkevich, V. L.; Schouten, J. C.; van der Schaaf, J.; Nijhuis, T.A. Glucose dehydration to 5-hydroxymethylfurfural over phosphate catalysts. *J. Catal.* **2013**, *300*, 37-46.
- (9) Zhang, Y.; Wang, J.; Ren, J.; Liu, X.; Li, X.; Xia, Y.; Lu, G.; Wang, Y. Mesoporous niobium phosphate: an excellent solid acid for the dehydration of fructose to 5-hydroxymethylfurfural in water. *Catal. Sci. Technol.* **2012**, *2*, 2485-2491.
- (10) Armaroli, T.; Busca, G.; Carlini, C.; Giuttari, M.; Raspolli Galletti, A. M.; Sbrana, G. Acid sites characterization of niobium phosphate catalysts and their activity in fructose dehydration to 5-hydroxymethyl-2-furaldehyde. *J. Mol. Catal. A Chem.* **2000**, *151*, 233-243.

- 1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
- (11) West, R. M.; Braden, D. J.; Dumesic, J. A. Dehydration of butanol to butene over solid acid catalysts in high water environments. *J. Catal.* **2009**, *262*, 134-143.
- (12) de La Cruz, M. H. C.; Rocha, Â. S.; Lachter, E. R.; Forrester, A. M. S.; Castro Reis, M.; San Gil, R. A. S.; Caldarelli, S.; Farias, A. D.; Gonzalez, W. A. Investigation of the catalytic activity of niobium phosphates for liquid phase alkylation of anisole with benzyl chloride. *Appl. Catal. A Gen.* **2010**, *386*, 60-64.
- (13) de la Cruz, M. H. C.; da Silva, J. F.C.; Lachter, E. R. Catalytic activity of niobium phosphate in the Friedel–Crafts reaction of anisole with alcohols. *Catal. Today* **2006**, *118*, 379-384.
- (14) Okazaki, S.; Kurosaki, A. Acidic properties and catalytic activities of niobic acid treated with phosphoric acid. *Catal. Today* **1990**, *8*, 113-122.
- (15) Sørensen, D. R.; Nielsen, U. G.; Skou, E. M. Solid state ^{31}P MAS NMR spectroscopy and conductivity measurements on NbOPO_4 and H_3PO_4 composite materials. *J. Solid State Chem.* **2014**, *219*, 80-86.
- (16) Mal, N. K.; Fujiwara, M. Synthesis of hexagonal and cubic super-microporous niobium phosphates with anion exchange capacity and catalytic properties. *Chem. Commun.* **2002**, 2702-2703.
- (17) Sarkar, A.; Pramanik, P. Synthesis of mesoporous niobium oxophosphate using niobium tartrate precursor by soft templating method. *Micropor. Mesopor. Mat.* **2009**, *117*, 580-585.
- (18) Stawicka, K.; Trejda, M.; Ziolk, M. New phospho-silicate and niobo-phospho-silicate MCF materials modified with MPTMS – Structure, surface and catalytic properties. *Micropor. Mesopor. Mat.* **2013**, *181*, 88-98.

- 1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
- (19) Choi, Y. Park, D. S.; Yun, H. J.; Baek, J.; Yun, D.; Yi, J. Mesoporous siliconiobium phosphate as a pure Brønsted acid catalyst with excellent performance for the dehydration of glycerol to acrolein. *ChemSusChem* **2012**, *5*, 2460-2468.
- (20) Xi, J.; Xia, Q.; Shao, Y.; Ding, D.; Yang, P.; Liu, X.; Lu, G.; Wang, Y. Production of hexane from sorbitol in aqueous medium over Pt/NbOPO₄ catalyst. *Appl. Catal. B Environ.* **2016**, *181*, 699-706.
- (21) Sreekumar, S., Balakrishnan, M., Goulas, K.; Gunbas, G.; Gokhale, A. A.; Louie, L.; Grippo A.; Scown, C. D.; Bell, A. T.; Toste, F. D. Upgrading lignocellulosic products to drop-in biofuels via dehydrogenative cross-coupling and hydrodeoxygenation sequence. *ChemSusChem* **2015**, *8*, 2609-2614.
- (22) Xia, Q. Chen, Z.; Shao, Y.; Gong, X.; Wang, H.; Liu, X.; Parker, S. F.; Han X.; Yang, S.; Wang, Y. Direct hydrodeoxygenation of raw woody biomass into liquid alkanes. *Nat. Commun.* **2016**, *7*, 11162.
- (23) Clayden, N. J.; Accardo, G.; Mazzei, P.; Piccolo, A.; Pernice, P.; Vergara, A.; Ferone C.; Aronne, A. Phosphorus stably bonded to a silica gel matrix through niobium bridges. *J. Mater. Chem. A* **2015**, *3*, 15986-15995.
- (24) Carniti, P.; Gervasini, A.; Biella, S.; Auroux, A. Intrinsic and effective acidity study of niobic acid and niobium phosphate by a multitechnique approach. *Chem. Mater.* **2005**, *17*, 6128-6136.
- (25) Carniti, P.; Gervasini, A.; Marzo M. Silica–niobia oxides as viable acid catalysts in water: effective vs. intrinsic acidity. *Catal. Today* **2010**, *152*, 42-47.

- 1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
- (26) Carniti, P.; Gervasini, A. Liquid-solid adsorption properties: Measurement of the effective surface acidity of solid catalysts. *Calorimetry and Thermal Methods in Catalysis*. A. Auroux (Ed.), **2013**, *17*, Springer Series in Materials Science, 154.
- (27) Tauc, J.; Grigorovici, R.; Vancu, A. Optical properties and electronic structure of amorphous germanium. *Phys. Status Solidi B* **1966**, *15*, 627-637.
- (28) He, J., Li, Q.-J.; Fan, Y.-N. Dispersion states and acid properties of SiO₂-supported Nb₂O₅. *J. Solid State Chem.* **2013**, *202*, 121-127.
- (29) Zhu, H.; Zheng, Z.; Gao, X.; Huang, Y.; Yan, Z.; Zou, J.; Yin, H.; Zou, Q.; Kable, S. H.; Zhao, J.; et al. Structural evolution in a hydrothermal reaction between Nb₂O₅ and NaOH solution: from Nb₂O₅ grains to microporous Na₂Nb₂O₆·²/₃H₂O fibers and NaNbO₃ cubes. *J. Am. Chem. Soc.* **2006**, *128*, 2373-2384.
- (30) Nishimura, M.; Asakura, K.; Iwasawa, Y. New SiO₂-supported niobium monomer catalyst for dehydrogenation of ethanol. *J. Chem. Soc., Chem. Commun.* **1986**, 1660-1661.
- (31) Tranca, D. C.; Wojtaszek-Gurdak, A; Ziolk, M.; Tielens, F. Supported and inserted monomeric niobium oxide species on/in silica: a molecular picture. *Phys. Chem. Chem. Phys.* **2015**, *17*, 22402-22411.
- (32) Engelhardt, G.; Jancke, H.; Hoebbel, D.; Wieker, W. Strukturuntersuchungen an Silikationen in wäßriger Lösung mit Hilfe der ²⁹Si-NMR-Spektroskopie. *Z. Chem.*, **1974**, *14*, 109-110.
- (33) Clayden, N. J.; Esposito, S.; Pernice, P.; Aronne, A. Solid State ²⁹Si and ³¹P NMR study of gel derived phosphosilicate glasses. *J. Mater. Chem.* **2001**, *11*, 936-43.

- 1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
- (34) Hartmeyer, G.; Marichal, C.; Lebeau, B.; Rigolet, S.; Caullet, P.; Hernandez, J. Speciation of silanol groups in precipitated silica nanoparticles by ^1H MAS NMR spectroscopy. *J. Phys. Chem. C* **2007**, *111*, 9066-9071.
- (35) Fleischer, U.; Kutzelnigg, W.; Bleiber, A.; Sauer, J. Proton NMR chemical shift and intrinsic acidity of hydroxyl groups. Ab initio calculations on catalytically active sites and gas-phase molecules. *J. Amer. Chem. Soc.* **1993**, *115*, 7833-7838.
- (36) Xue, X.; Kanzaki, M. Ab initio calculation of the ^{17}O and ^1H NMR parameters for various OH groups: implications to the speciation and dynamics of dissolved water in silicate glasses. *J. Phys. Chem. B* **2001**, *105*, 3422-3434.
- (37) Papulovskiy, E.; Khabibulin, D. F.; Terskikh, V. V.; Paukshtis, E. A.; Bondareva, V. M.; Shubin, A. A.; Andreev, A. S.; Lapina, O. Effect of impregnation on the structure of niobium oxide/alumina catalysts studied by multinuclear Solid-State NMR, FTIR, and quantum chemical calculations. *J. Phys. Chem. C* **2015**, *119*, 10400 -10411.
- (38) Moreau, C.; Durand, R.; Roux, A.; Tichit, D. Isomerization of glucose into fructose in the presence of cation-exchanged zeolites and hydrotalcites. *Appl. Catal. A: Gen.* **2000**, *193*, 257-264.
- (39) Moreau, C.; Belgacem, M. N.; Gandini, A. Recent catalytic advances in the chemistry of substituted furans from carbohydrates and in the ensuing polymers. *Top. Catal.* **2004**, *27*, 1-30.
- (40) Román-Leshkov, Y.; Moliner, M.; Labinger, J. A.; Davis, M. E. Mechanism of glucose isomerization using a solid Lewis acid catalyst in water. *Angew. Chem., Int. Ed.* **2010**, *49*, 8954-8957.

- 1
2
3
4 (41) Abdulbari, H. A.; Akindoyo, E. O.; Mahmood, W. K. Renewable resource-based lubricating
5 greases from natural and synthetic sources: insights and future challenges. *Chem. Bio. Eng.*
6 *Rev.* **2015**, *2*, 406-422.
7
8
9
10 (42) Di Serio, M.; Tesser, R.; Pengmei, L.; Santacesaria, E. Heterogeneous catalysts for biodiesel
11 production. *Energ. Fuels* **2003**, *22*, 207-217.
12
13
14 (43) Borges, M. E.; Díaz, L. Recent developments on heterogeneous catalysts for biodiesel produc-
15 tion by oil esterification and transesterification reactions: a review. *Renew. Sust. Energ. Rev.*
16 **2012**, *16*, 2839-2849.
17
18
19
20
21 (44) Kuzminsk, M.; Backov, R.; Gaigneaux, E. M. Behavior of cation-exchange resins employed
22 as heterogeneous catalysts for esterification of oleic acid with trimethylolpropane. *Appl. Catal.*
23 *A: Gen.* **2015**, *504*, 11-16.
24
25
26
27
28 (45) Oh, J.; Yang, S.; Kim, C.; Choi, I.; Kim, J. H.; Lee, H. Synthesis of biolubricants using sulfat-
29 ed zirconia catalysts. *Appl. Catal. A: Gen.* **2013**, *455*, 164-171.
30
31
32
33 (46) Wu, Y.; Li, W.; Wang, X. Synthesis and properties of trimethylolpropane trioleate as lubricat-
34 ing base oil. *Lubrication Science* **2015**, *27*, 369-379.
35
36
37
38 (47) Santacesaria, E.; Ambrosio, M.; Sorrentino, A.; Tesser, R.; Di Serio M. Double bond oxida-
39 tive cleavage of monoenic fatty chains. *Catal. Today* **2003**, *79*, 59-65.
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

TABLES

Table 1. UV-vis-DRS curve fitting. Wavelength, λ (nm), estimated relative intensities, I, full width at half maximum, F_w (nm), calculated from line fitting of the UV-vis-DRS spectra. Standard errors are ± 1 nm in λ , ± 2 in the intensity, and ± 3 nm in the linewidth.

| Sample | λ (nm) | I | F_w (nm) |
|-------------|----------------|----|------------|
| 2.5NbP-500 | 196 | 30 | 65 |
| | 231 | 21 | 43 |
| | 266 | 31 | 45 |
| | 300 | 18 | 39 |
| 2.5NbP-500w | 199 | 23 | 44 |
| | 230 | 27 | 42 |
| | 264 | 31 | 41 |
| | 295 | 19 | 38 |

Table 2. ^{31}P curve fitting. Chemical shifts, δ (ppm), estimated relative intensities, I, and full width at half maximum, F_w (ppm), calculated from line fitting of the ^{31}P resonances. Standard errors are ± 0.25 ppm in δ , ± 1.0 in the intensity, and ± 0.25 ppm in the linewidth.

| Sample | δ (ppm) | I | F_w (ppm) |
|-------------|----------------|------|-------------|
| 2.5NbP-500 | -0.04 | 1.0 | 2.6 |
| | -8.9 | 46.0 | 8.8 |
| | -21.1 | 43.0 | 8.5 |
| | -35.1 | 10.0 | 7.8 |
| 2.5NbP-500w | -0.4 | 2.5 | 5.3 |
| | -9.6 | 19.8 | 7.4 |
| | -20.6 | 65.5 | 9.8 |
| | -36.4 | 12.2 | 7.6 |

Table 3. Determination of the nature of the acid sites determined by FT-IR with pyridine (Py) as probe molecule in absence and in presence of water. ^a

| Sample | Py _(vap) ^b | | | Py _(aq) ^c | | |
|-------------|----------------------------------|-------------------------------|---------|---------------------------------|-------------------------------|---------|
| | LAS (meq g ⁻¹) | BAS (meq g ⁻¹) | LAS/BAS | LAS (meq g ⁻¹) | BAS (meq g ⁻¹) | LAS/BAS |
| NbP | 0.082 | 0.039 | 2.10 | 0.061 | 0.036 | 1.69 |
| 2.5 NbP-500 | 0.088 | 0.083 | 1.06 | 0.027 | 0.069 | 0.39 |

^a All the values have been determined after thermal desorption of pyridine at 100 °C.

^b Pyridine contacted in vapor phase. ^c Pyridine contacted in aqueous solution.

Table 4. Kinetic coefficients evaluated at three representative temperatures and Arrhenius parameters for the catalytic hydrolysis of inulin.

| Sample | k _T (mequiv·g ⁻¹ ·min ⁻¹) | | | E _a (kJ·mol ⁻¹) | Ln A ^a |
|------------------|---|---------|---------|--|-------------------|
| | T=60 °C | T=70 °C | T=80 °C | | |
| NbP | <hr/> | | | | |
| fresh | 0.0124 | 0.0567 | 0.2370 | 144.1 ± 11.5 | 48.6 ± 3.9 |
| water stabilized | 0.00614 | 0.0278 | 0.1155 | 143.5 ± 4.4 | 46.7 ± 1.5 |
| 2.5NbP-500 | <hr/> | | | | |
| fresh | 0.0160 | 0.0712 | 0.2907 | 141.7 ± 8.2 | 47.0 ± 2.8 |
| water stabilized | | | | | |

^aA expressed in mequiv·g⁻¹·min⁻¹

FIGURES

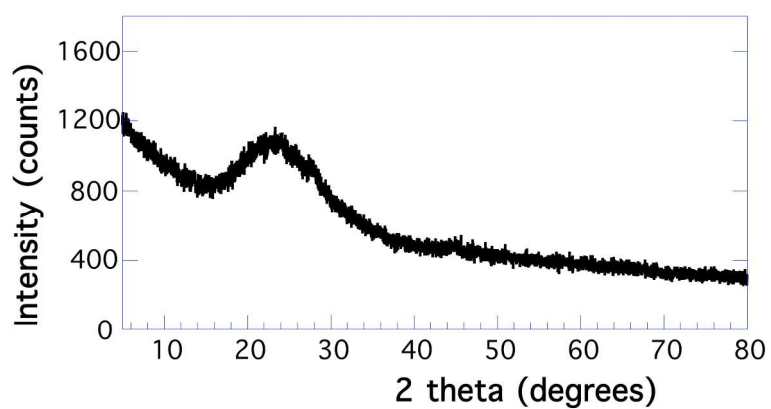


Figure 1. PXRD pattern of the 2.5NbP-500 sample.

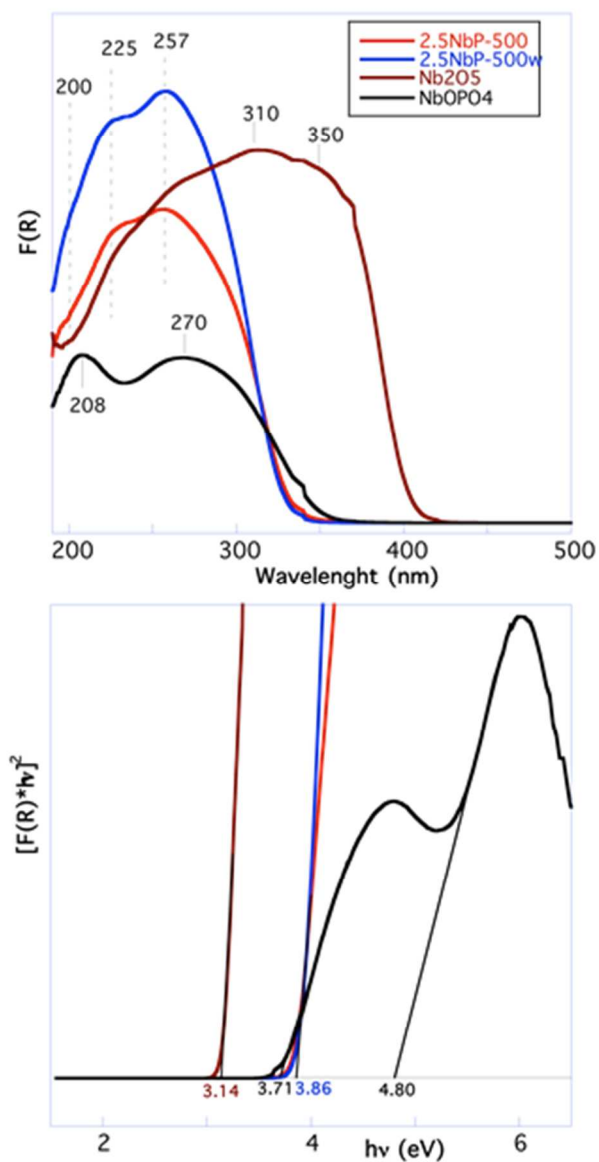


Figure 2. UV-Vis-DRS (top) and the corresponding Tauc plot (bottom) of the investigated samples. The same E_g was observed for 2.5NbP-500 and 2.5NbP-500w ($E_g = 3.86$ eV), demonstrating that the water treatment does not modify the distribution of surface Nb species

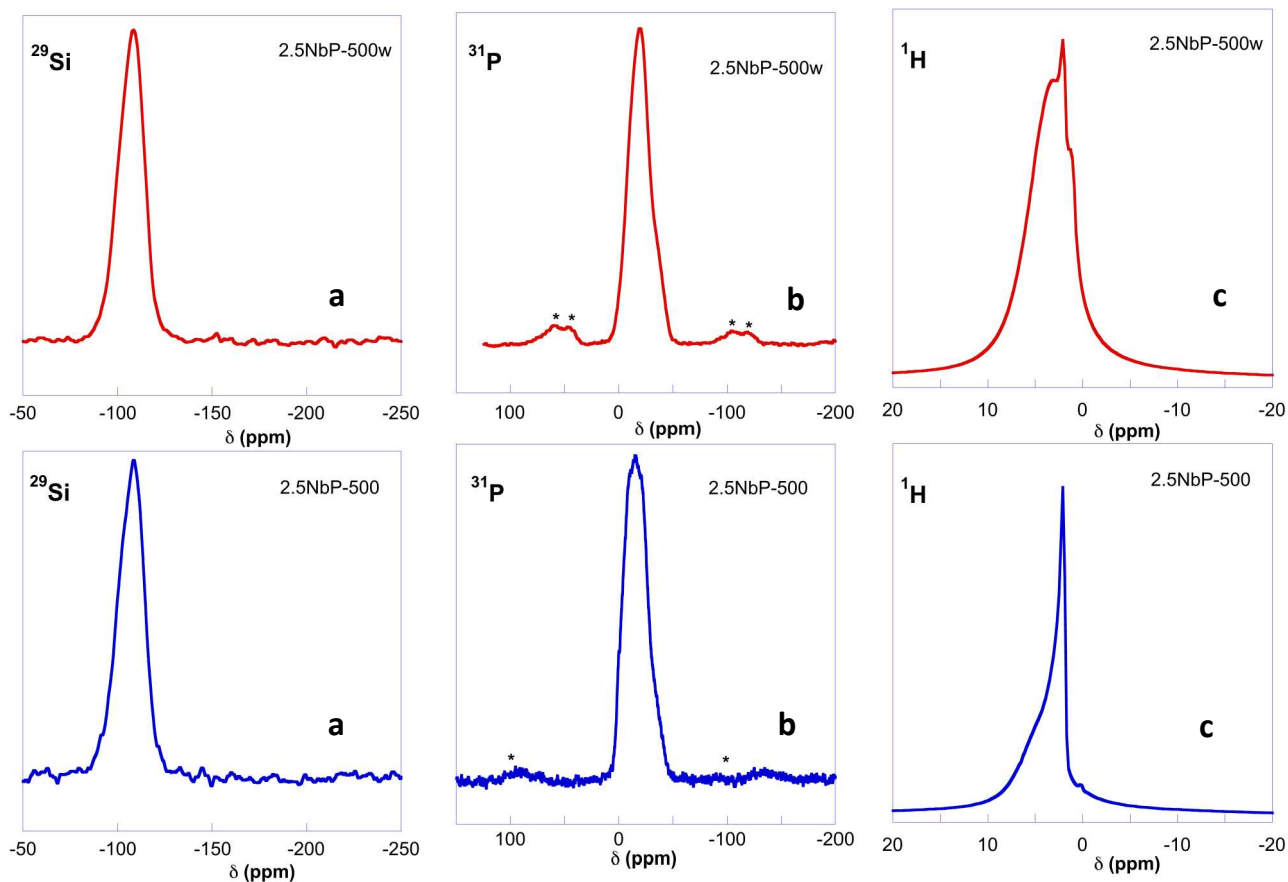


Figure 3. MAS NMR ^{29}Si (a), ^{31}P (b) and ^1H (c) of the investigated 2.5NbP-500w (top) and 2.5NbP-500 (bottom) samples. High stability in water is suggested by ^{29}Si spectra, changes are seen only in ^{31}P and ^1H spectra indicating the hydrolysis of few high reactive sites.

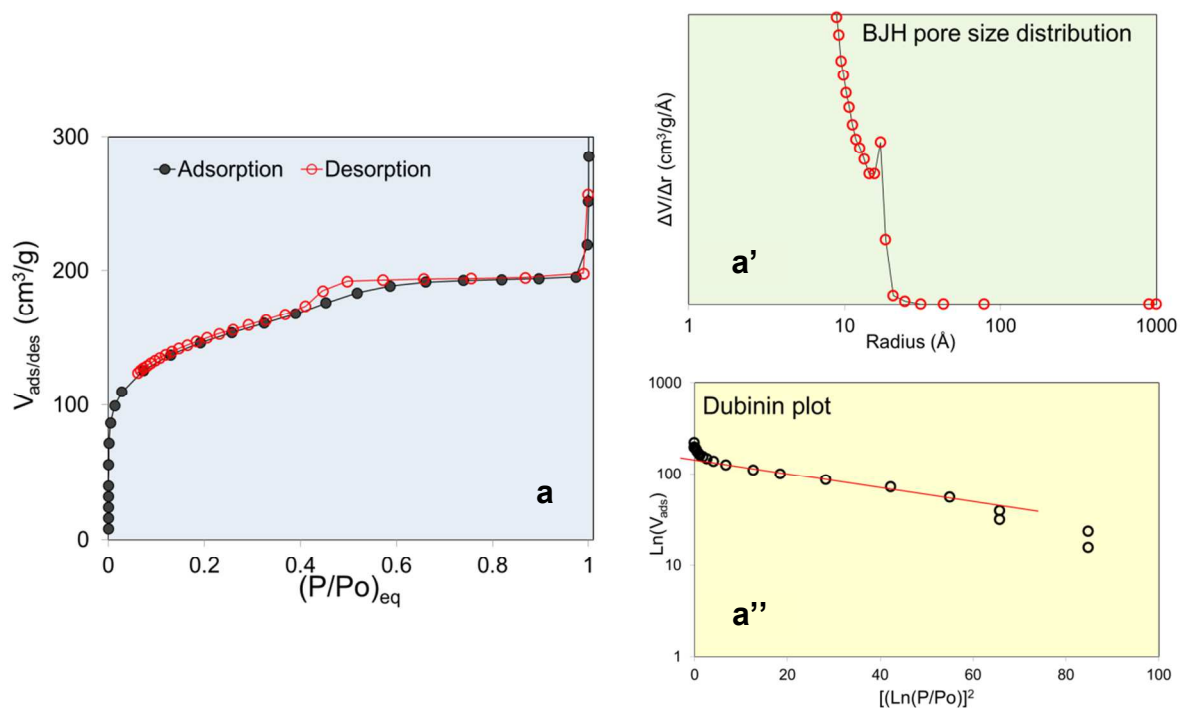


Figure 4. Morphologic characterization of 2.5NbP-500 sample. N₂ adsorption and desorption isotherms at -196 °C (a), pore size distribution determined by BJH model equation from the desorption branch of the N₂-isotherms (a'), and Dubinin plot for the determination of the micropore volume (a'').

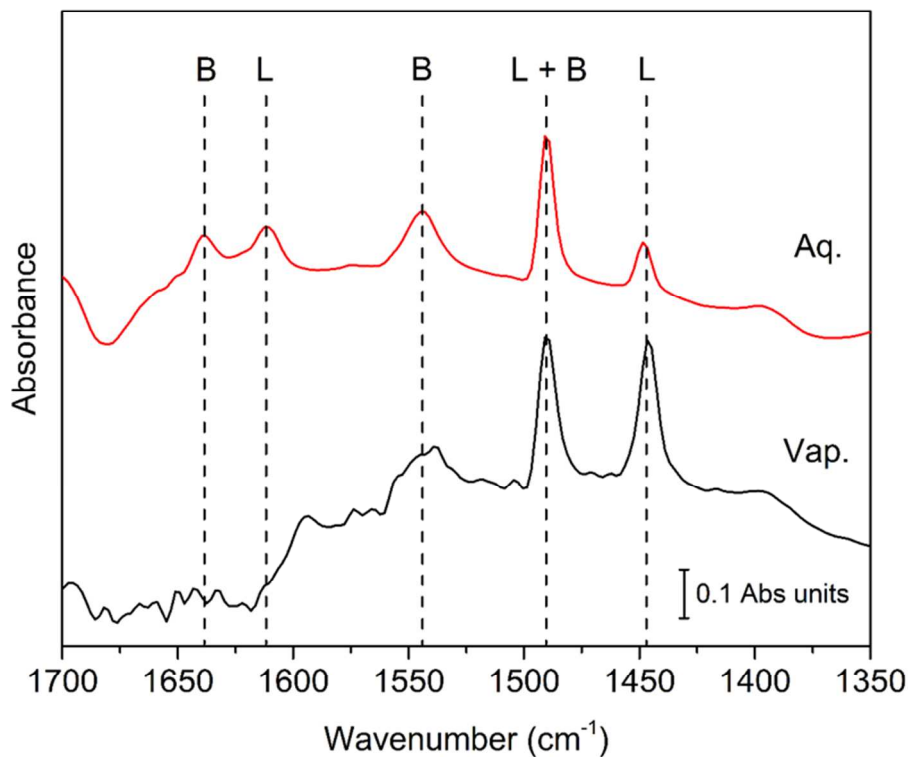


Figure 5. FT-IR desorption spectra of pyridine on 2.5NbP-500 sample at 100 °C with pyridine adsorbed in vapor phase (Vap.) and in aqueous solution (Aq.). Quantitative determinations of Brønsted (BAS) and Lewis (LAS) acid sites were made on the peaks at 1540 and 1448 cm⁻¹, respectively.

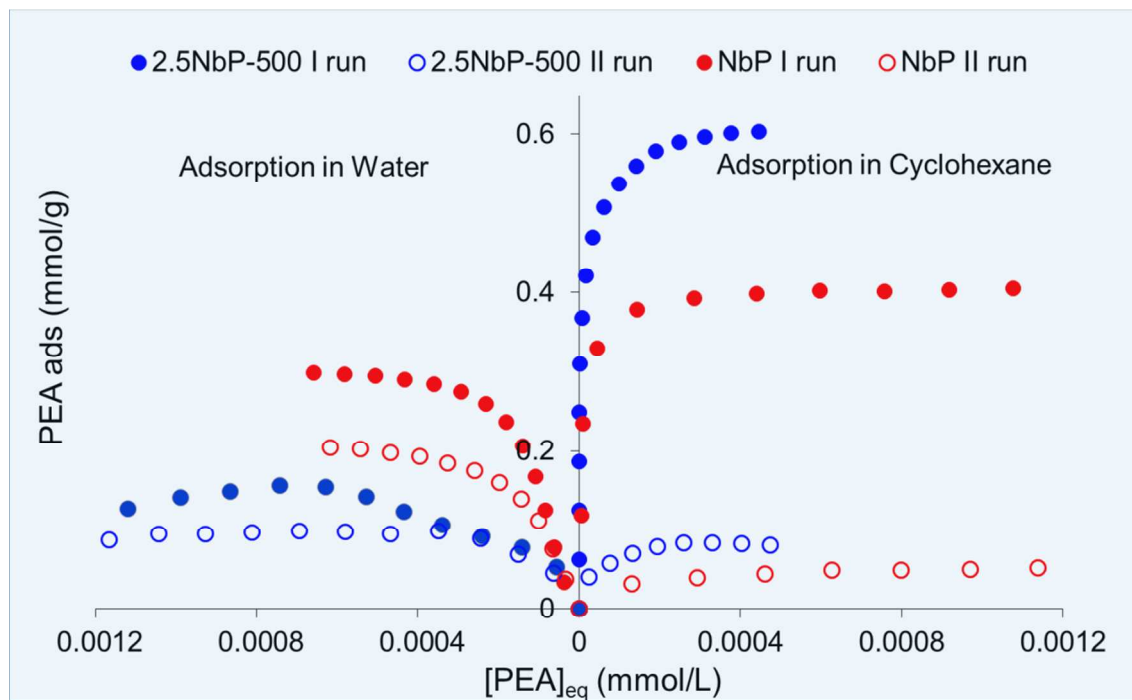


Figure 6. Surface acid characterization of the studied samples. Adsorption isotherms of phenylethylamine (PEA) at 30 °C on 2.5NbP-500 and NbP (reference sample), measured in two different liquids: cyclohexane for the *intrinsic* acidity determination and water for the *effective* acidity determination; first run (on the fresh sample) and second run (on the sample with PEA chemically adsorbed) are shown.

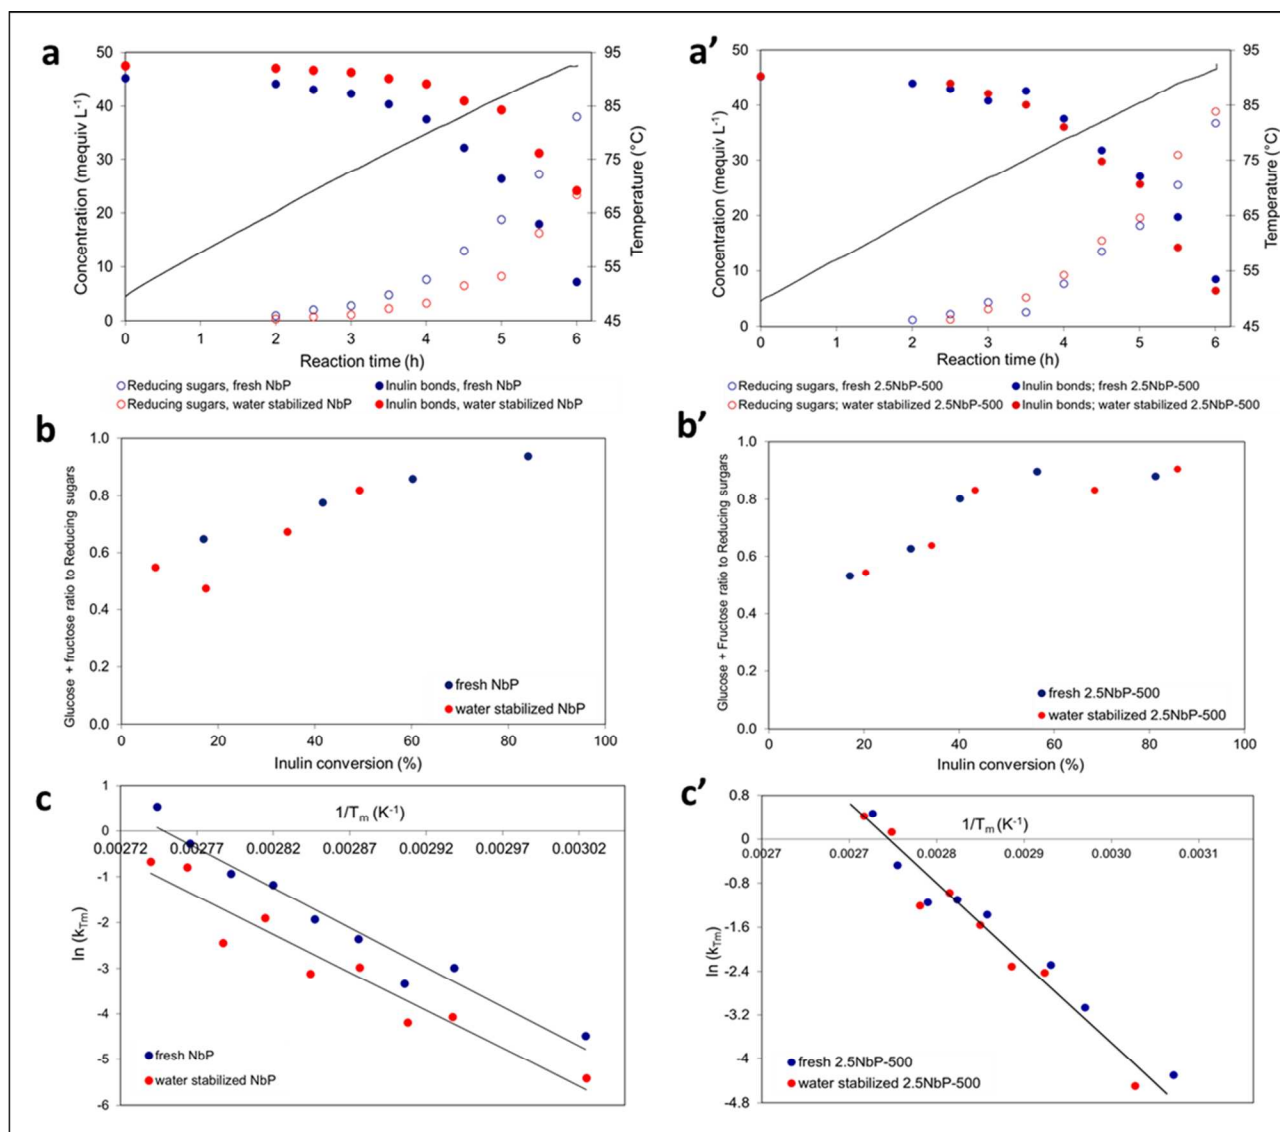


Figure 7. Catalytic performances of NbP and 2.5NbP-500 in the inulin hydrolysis. Concentration of total reducing sugars formed and of residual inulin bonds as a function of time and temperature (second axis) on fresh and water stabilized NbP (a) and 2.5NbP-500 (a'). Selectivity to monosaccharides: ratio between glucose plus fructose and total reducing sugars as a function of inulin conversion on fresh and water stabilized NbP (b) and 2.5NbP-500 (b'). Arrhenius plot for the reaction of inulin hydrolysis determined in the temperature range 50-90 °C on fresh and water stabilized NbP (c) and 2.5NbP-500 (c'); T_m represents the average temperature during ca. 30 min of reaction corresponding to ca. $\Delta T=5$ °C.

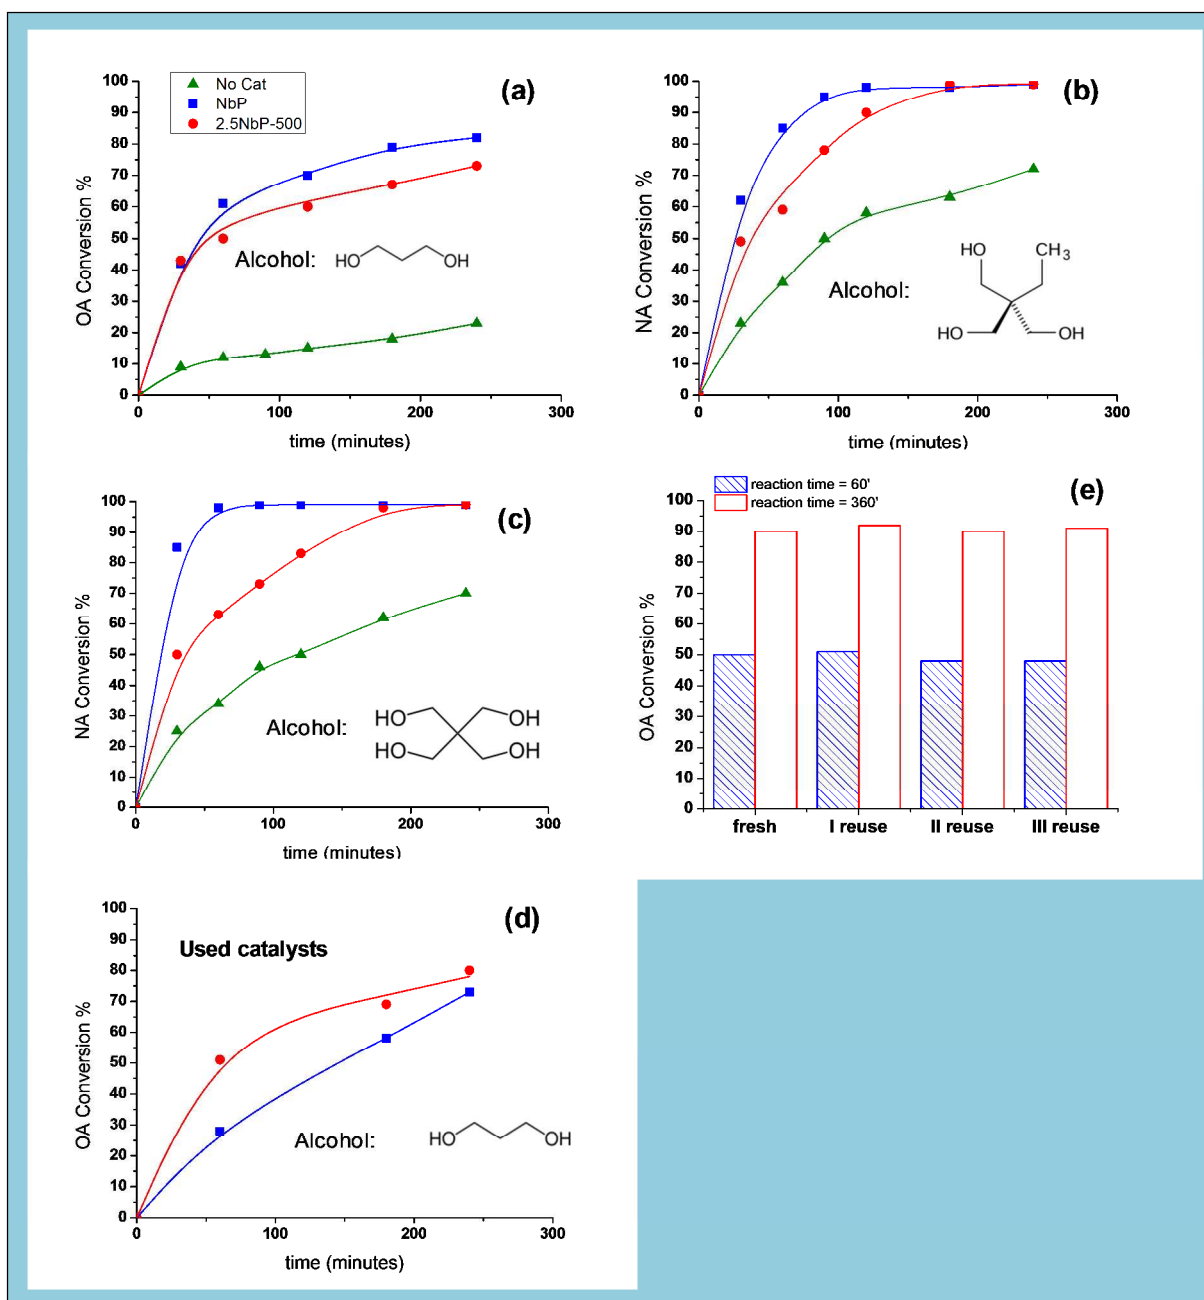


Figure 8. Catalytic performances of NbP and 2.5NbP-500 in the esterification reaction. Esterification runs, conversion of fatty acids. Reaction conditions: $T = 180^{\circ}\text{C}$, catalyst = 1% wt on reaction mixture, molar ratio fatty acid/alcohol = 2/1 (a), (d) and (e); 3/1 (b); 4/1 (c). Oleic Acid (OA), 1,3 propanediol, (a) and (d); nonanoic acid, trimethylolpropane (b); nonanoic acid, pentaerythritol (c). Results obtained in the I reuse of catalysts (d). Results obtained with fresh 2.5NbP-500 catalyst and in the successive 3 runs (Oleic Acid, 1,3 propanediol) (e).

TOC Graphic

