

Laboratory Studies to Examine the Properties of a Novel Cold-Asphalt Concrete Binder Course Mixture Containing Binary Blended Cementitious Filler (BBCF)

Anmar Dulaimi^{1,2}, Hassan Al Nageim³, Felicite Ruddock⁴ and Linda Seton⁵

¹ PhD student, Department of Civil Engineering, Liverpool John Moores University, Henry Cotton Building, Webster Street, Liverpool L3 2ET, UK, A.F.Dulaimi@2013.ljmu.ac.uk.

² Kerbala University, Kerbala, Iraq.

³ Professor of Structural Engineering, Head of the Liverpool Centre for Materials Technology, Department of Civil Engineering, Liverpool John Moores University, Peter Jost Centre, Byrom Street, Liverpool L3 3AF, UK, H.K.Alnageim@ljmu.ac.uk.

⁴ Programme Leader, Department of Civil Engineering, Liverpool John Moores University, Peter Jost Centre, Byrom Street, Liverpool L3 3AF, UK, F.M.Ruddock@ljmu.ac.uk.

⁵ Reader, School of Pharmacy and Biomolecular Science, Liverpool John Moores University, James Parsons Building, Byrom Street, Liverpool, L3 3AF, UK, L.Seton@ljmu.ac.uk.

Abstract

Conventional hot asphalt mixtures have an impact on global warming and CO₂ emissions contributing to debates on environmental issues which have been raised in recent years. As an alternative, cold emulsion asphalt mixtures (CBEMs) provide considerable benefits such as eco-friendliness, energy efficiency and cost effectiveness connected with safety. However, their weak early strength along with the need for longer curing times (usually 2-24 months) and higher moisture susceptibility compared to hot asphalt mixtures, have been cited as obstacles to their wider application. That said, the incorporation of waste materials in CBEM mixtures enhances sustainability by decreasing the amount of industrial waste materials needed and conserving natural resources. A new binary blended cement filler (BBCF) material generated from high calcium fly ash (HCFA) and fluid catalytic cracking catalyst (FC3R) was found to be very effective in providing microstructural integrity with a novel fast-curing cold asphalt concrete for the binder course (CACB) mixture. Laboratory performance tests included the stiffness modulus test by indirect tension to cylindrical samples, wheel-tracking tests and water sensitivity.

30 Regarding environmental issues, a toxicity characteristic leaching procedure (TCLP) test was
31 performed to analyse the leachate from various specimens comprising concentrations of heavy metal.
32 The findings of these tests have demonstrated that CACB performs extremely well compared to
33 traditional hot mixtures. The stiffness modulus of the BBCF treated mixture – 3730 MPa after 3 days –
34 is higher than the traditional hot mixture (100/150 pen). In addition, the BBCF treated mixture offered
35 a superior performance regarding rutting resistance, fatigue resistance and water susceptibility as well
36 as revealing a considerably lower thermal sensitivity. More significantly, the BBCF treated mixture was
37 found comparable to the traditional asphalt concrete binder course after a very short curing time (1 day).
38 Finally, the concentration of heavy metals in the specimens incorporating the BBCF was observed to
39 be less than the regulatory levels determined for hazardous materials and so requirements were satisfied.
40 Consequently, this BBCF treated mixture has significant potential with reference to its application as a
41 binder course in asphalt pavement.

42 **Keywords:** Cold bituminous emulsion mixtures, indirect tensile stiffness modulus, rutting, TCLP,
43 waste material and water susceptibility.

44 **Introduction**

45 Hot mix asphalt production is accountable for a great deal of energy consumption as a result of the need
46 to heat its constituent parts, aggregates and binder, meaning that greenhouse gas emissions are generated
47 from burning fossil fuels (Rubio et al., 2013). Cold mix asphalt is a technology by which the asphalt
48 mix is produced and laid at normal temperatures. One of the popular types of cold asphalt mixtures is
49 cold bitumen emulsion mixtures (CBEMs). The application of CBEMs in the construction of asphalt
50 pavements has attracted attention in the past few years as it can provide an alternative to traditional hot
51 mix asphalt. It has several advantages including environmental protection, economical benefits and
52 meeting health and safety requirements as these mixtures are characterised by production at ambient
53 temperature. Nevertheless, some disadvantages have resulted in cold mix asphalt being considered the
54 poorer option to hot mix asphalt (Thanaya et al., 2009). The long curing time required to achieve full
55 strength, which is generally between 2-24 months (Leech, 1994), weak early strength and possible early

56 distress due to rainfall water intrusion, are regarded as major disadvantages (Brown and Needham, 2000;
57 Thanaya et al., 2009).

58 CBEM technology has been applied in several countries including the USA; France has been using
59 CBEMs since the 1970s, annual manufacture in France reaching 1.5 million tonnes in 2014 (European
60 Asphalt Pavement Association (EAPA), 2014) . Nevertheless the use of cold emulsified asphalt as a
61 structural layer is very restricted as a result of the longer curing time essential for such materials to
62 reach their full strength after placing, and because of their high sensitivity to rainfall (mainly in the
63 UK) at the early stages of placement (Oruc et al., 2007).

64 Cold mix asphalt is termed as an evolutive material (Serfass et al., 2004), which means that after it has
65 been laid, this mixture passes through a number of stages in which binder cohesion, binder-aggregate
66 adhesion and mixture shear strength take place (Khalid and Monney, 2009). Enhancements of the
67 mechanical properties and moisture susceptibility of cold asphalt mixtures are limited by the use of
68 cement. An initial study performed by Terrel and Wang (1971) revealed that emulsion mixes treated
69 with the addition of cement resulted in an acceleration of the enhancement rate of the resilient modulus.
70 Head (1974) noted that when adding 1% Ordinary Portland Cement (OPC), the Marshall Stability of a
71 modified cold asphalt mix was superior (approximately three times better) in comparison to an
72 untreated mix. They also concluded that cement helped the modified mixture to cure under cold and
73 damp conditions. Cement-modified emulsion mixtures were studied by Brown and Needham (2000),
74 their main objective to assess the positive influence of adding OPC to the emulsified mixes. A granite
75 aggregate grading was used in the middle of 20mm dense bituminous macadam with a single slow-
76 setting emulsion. From the results, it was concluded that the addition of OPC improved the mechanical
77 properties, namely stiffness modulus, permanent deformation resistance and fatigue strength. Oruc et
78 al. (2007) also carried out laboratory investigations to assess the mechanical properties of emulsified
79 asphalt mixtures, including 0-6% OPC, replaced with mineral filler. They concluded that using a high
80 percentage of additional OPC resulted in a significant improvement suggesting that cement-modified
81 asphalt emulsion mixtures might be applied as a structural layer. A novel gap-graded Cold Rolled
82 Asphalt (CRA) was developed by Al-Hdabi et al. (2014) by utilising OPC instead of traditional

83 limestone mineral filler. They identified a substantial improvement in mechanical properties, namely
84 stiffness modulus, four-point load fatigue, uniaxial creep and semi-circular bending tests in addition to
85 an improvement in water sensitivity. However, Portland cement manufacture consumes a great deal of
86 resources and energy causing CO₂, SO₂ and NO_x emissions, this acid rain contributing to the
87 greenhouse effect. Consequently, there will be a significant environmental improvement if industrial
88 by-products can be utilised instead (Li et al., 2008).

89 Various waste and by-product materials have attracted attention due to their chemical composition as
90 the re-use of different kinds of waste materials in CBEMs is a growing research area promising
91 economic, technical and ecological advantages. The relatively low environmental impact connected
92 with CBEM manufacture can be further decreased while, at the same time, improvements to the quality
93 of CBEMs can be further improved with the application of industrial wastes. Ellis et al. (2004)
94 investigated a variety of storage grade macadams composed of recycled aggregates from many sources,
95 bound by bitumen emulsion and Ground Granulated Blastfurnace Slag (GGBS). Their results indicated
96 that stiffness and strength can develop when GGBS is added at high humidity. Thanaya et al. (2006)
97 performed laboratory investigations to assess the performance of a cold mix at full curing conditions by
98 using pulverised fly ash (PFA) as filler, finding that the cold mix stiffness was comparable to that of
99 hot mixes. Al Nageim et al. (2012) studied the addition of fly ash and OPC to cold bituminous emulsion
100 mixtures as a filler replacement to examine the development of the mechanical properties of CBEMs
101 and to investigate the possibility of replacing the OPC with fly ash. This new CBEM achieved
102 significant results in comparison to conventional CBEM with and without OPC addition. Al-Hdabi et
103 al. (2013) also investigated the mechanical characteristics and water susceptibility of cold-rolled asphalt
104 (CRA) by using cement as a filler replacement and waste bottom ash (WBA). They concluded that using
105 WBA as an additive enhanced the development of mechanical properties vis a vis stiffness modulus
106 and uniaxial creep tests in addition to water sensitivity.

107 Likewise, Thanaya et al. (2014) investigated the properties of cold asphalt emulsion mixtures (CAEMs)
108 including milled old road pavement, with and without the inclusion of cement and compaction delays.
109 They found that improved strength at an early age under tropical room temperatures was governed more

110 by the evaporation of water than by the inclusion of cement. Gómez-Meijide and Pérez (2014)
111 conducted a study looking to enhance the properties of cold asphalt mixtures in terms of the
112 environmental and economics, by using construction and demolition waste aggregates in such mixtures.
113 From the experimental results it was revealed that the indirect tensile strength, unconfined compression
114 strength, stiffness modulus and susceptibility to moisture were tolerable, not only in comparison to a
115 control mix with 100% natural aggregates (NA), but also with values provided by various standards and
116 recommendations.

117 Fluid catalytic cracking catalyst residue (FC3R) is an industrial by-product produced by the fluid
118 catalytic cracking processes in petrol refineries. Some studies have revealed that FC3R has the ability
119 to increase mechanical properties in mortars or concretes because of a densification of the cementitious
120 matrix generated by pozzolanic reaction. Pacewska et al. (1998) studied the hydration of cement paste
121 as a function of adding a spent catalyst to address catalytic cracking. Their research detailed the
122 pozzolanic nature of the spent catalyst. They found that the spent catalyst and microsilica had a similar
123 potential to be combined with $\text{Ca}(\text{OH})_2$, and that the hydration process was highly exothermic,
124 facilitating rapid setting of the cement paste. Payá et al. (1999) revealed that the substitution of cement
125 by FC3R in mortars created a significant increase in compressive strength, one that overcomes plain
126 cement mortar, possibly as a result of a pozzolanic reaction. Consequently, research indicates that FC3R
127 has the potential to be used as a supplementary cementitious material (SCM) which can be substituted
128 for cement.

129 Therefore, from the point of view of economics, environmental concerns and safety, CBEMs are useful
130 in the construction of asphalt pavements. However, the mechanical properties and water damage
131 resistance of material using waste materials has not been well documented. Only a few researchers have
132 examined the possibility of applying waste materials as filler replacement in CBEMs but there is no
133 research examining high calcium fly ash activation by fluid catalytic cracking catalyst (FC3R) in order
134 to produce a binary blended cement filler (BBCF). The current research aimed at developing fast-curing
135 cold emulsion asphalt mixtures for binder course materials in road pavements, with the goal of
136 decreasing the disposal of waste and raw materials and contributing to the improvement of sustainable,

137 cleaner production practices. Since the success of this technology is subject to performance, this study
138 aimed to assess the performance of CACB, with or without BBCF, when compared to the hot asphalt
139 concrete binder course mixtures. A laboratory programme covered the stiffness modulus, rutting
140 resistance, fatigue resistance and moisture damage resistance, assessed through indirect tensile stiffness
141 modulus tests on cylindrical specimens, wheel-track tests, four-point bending tests on prismatic shaped
142 samples and stiffness modulus ratio tests, respectively. Testing of waste material characteristics such as
143 morphology using a scanning electron microscope (SEM), chemical and mineralogical composition
144 utilising X-ray fluorescence (XRF) and X-ray diffraction (XRD) techniques, have been carried out.

145 **Materials and methods**

146 **Aggregates**

147 A commercial granite aggregate of coarse and fine fractions supplied by Carnsew Quarry at Mabe,
148 Penryn in the UK, was used in this research to manufacture all the hot and cold mixtures. As shown in
149 Figure 1, a dense gradation for binder course AC-20 mm was used. The aggregate gradation in this
150 research is based on EN 13108-1 (European Committee for Standardization, 2006), the common
151 properties of the aggregates presented in Table 1.

152 **Emulsion and binder**

153 The binder was a standard cationic bitumen emulsion (C60B5) (60% bitumen content) with 100/150
154 pen. This kind of emulsion is designed for use in road pavements and common maintenance applications.
155 Nikolaides (1994) confirmed that cationic emulsion is preferred because of its ability to coat aggregates
156 and to guarantee high adhesion between the particles of said aggregates. With reference to the
157 conventional hot asphalt mixture, a 40/60 and 100/150 penetration-grade bitumen was used. Tables 2
158 and 3 detail the primary properties of these binders.

159 **Fillers**

160 Two fillers which are considered industrial waste, were analysed in this research: high calcium fly ash
161 (HCFA) which is produced from power generation plants by combustion between 850°C and 1100°C
162 using the fluidised bed combustion (FBC) system, and fluid catalytic cracking catalyst (FC3R), which

163 is a by-product material produced in petrol refineries from the fluidised bed process. In addition, typical
164 traditional limestone filler (LF) was used for the reference cold mixture.

165 **Filler characterisation**

166 The chemical composition of the fillers was examined using X-ray fluorescence (XRF) while the
167 mineralogical properties were inspected using X-ray diffraction (XRD) techniques. Table 4 details the
168 chemical structure of the three fillers tested as revealed by the energy dispersive X-ray fluorescence
169 (EDXRF) spectrometer test while Figures 2 and 3 present the mineralogical composition from the XRD
170 test results. It can be seen from Table 4 that HCFA is composed of CaO with a suitable quantity of SiO₂
171 and Al₂O₃. Conversely, FC3R contains Al₂O₃ and SiO₂ as the main oxides. Lea (1970) reported that
172 soluble SiO₂ and Al₂O₃ present in the glass phase of pozzolanic materials, have an important role to
173 play in that they react with the Ca(OH)₂ released through the hydration of cements to form an extra
174 calcium silicate hydrate (CSH) gel that enhances the mechanical strength of the hardened concrete
175 structure.

176 The powder XRD pattern of HCFA in XRD shown in Figure 2 indicates that the HCFA is crystalline
177 as it contains sharp peaks without substantial noise in the background; the major crystal peaks identified
178 were lime (CaO), calcite (CaCO₃), mayenite (Ca₁₂Al₁₄O₃₃), merwinite (Ca₃Mg[SiO₄]) and gehlenite
179 (CaAl[Al,SiO₇]). The powder diffraction in XRD shown in Figure 3 indicates that FC3R has very low
180 crystalline peaks which are amorphous in nature. This means that it will demonstrate high reactivity
181 during the hydration process and can be used as a pozzolanic material, making this material a potential
182 precursor in the production of a new BBCF. The crystalline peaks identified comprised kyanite
183 (Al₂O₅Si), quartz (SiO₂), mullite (Al₆Si₂O₁₃) and dehydrated Ca-A zeolite (Al₉₆Ca₄₈O₃₈₄Si₁₉₆).

184

185 **Mixture production**

186 The Marshall Method for Emulsified Asphalt Aggregate Cold Mixture Design (MS-14) procedure, as
187 specified by the Asphalt Institute (1989), was used to design the cold asphalt concrete binder course
188 bituminous emulsion mixtures.

189 Various pre-wetting water contents (PWWC) were examined to select the lowest pre-water ratio and as
190 a result, adequate coating can be confirmed. Indirect tensile stiffness modulus tests were used to
191 determine the optimum emulsion content (OEC), while the mix density test was employed to define the
192 optimum total liquid content at compaction (OTLC). Consistent with this procedure, PWWC, OTLC
193 and optimum residual bitumen contents were 3.5%, 14% and 6.3%, respectively.

194 Incorporation of the HCFA was carried out with a partial substitution of the conventional mineral filler
195 with various proportions of HCFA (0%, 1.5%, 3%, 4.5% and 6%) by dry aggregate total mass, while
196 FC3R was used as the activator in four ratios (1%, 2%, 3% and 4%) by dry aggregate total mass to
197 replace the HCFA in order to generate a binary blended cement filler (BBCF).

198 The materials were mixed in a Hobart mixer where the aggregate, filler and PWWC were added and
199 mixed for 60 seconds at low speed. The bitumen emulsion was slowly introduced over the following 30
200 seconds of mixing, the mixing process continuing for the next 120 seconds at the same speed. Samples
201 were mixed and placed in moulds then compacted using a Marshall hammer with 50 blows per face.
202 The samples were left in their moulds at room temperature ($20\pm 1^\circ\text{C}$) for 24 hours then demoulded. The
203 samples were then cured at room temperature before they were used for ITSM tests.

204 The indirect tensile stiffness modulus test has been performed to investigate the influence of the
205 substitution of LF with HCFA and of FC3R inclusion, the results compared to a standard AC 20mm hot
206 dense binder course. Two types of hot binder course mix, namely AC 20mm dense binder course
207 100/150 and AC 20mm dense binder course 40/60, have been used throughout this research with the
208 same aggregate type and gradation. 4.6% optimum binder content by weight of aggregate was used
209 according to the PD 6691:2010 (European Committee for Standardization, 2015) for the AC 20mm
210 dense binder course. Specimens were fabricated and compacted at lab temperature (20°C), while the
211 100/150 and 40/60 hot mixtures were mixed at $150\text{--}160^\circ\text{C}$ and $160\text{--}170^\circ\text{C}$, respectively. In addition, a
212 cold asphalt concrete binder course containing limestone filler (LF) was used for the purpose of
213 comparison. Every indirect stiffness modulus test value is the average of 5 specimens to ensure the
214 reliability of the results.

215

216

217 **Laboratory testing programme**

218 The performance tests covered the stiffness modulus, temperature susceptibility, rutting resistance,
219 fatigue resistance and moisture susceptibility, assessed through the indirect tension of cylindrical
220 specimens, wheel-track tests, four-point bending tests and stiffness modulus ratio tests respectively.

221 **Indirect tensile stiffness modulus (ITSM) test**

222 Stiffness of bituminous mix is associated with the capacity of such material to distribute traffic loads,
223 meaning it can be considered as a synthetic indicator of their structural properties. The stiffness modulus
224 of asphalt mixtures is one of the most significant characteristics in the design of flexible pavements.
225 The test used here applied indirect tension to cylindrical samples in accordance with BS EN 12697-26
226 (European Committee for Standardization, 2012b), using a Cooper Research Technology HYD 25
227 testing machine, as shown in Figure 4, performed under the conditions given in Table 5. ITSM is
228 determined by applying 5 repeated loads, preceded by a pre-loading of 10 repetitions of load, which has
229 the function of correcting the load application system to the sample. All ITSM tests were conducted at
230 20°C, the samples conditioned for a 4-hour period to guarantee the test temperature as stipulated in the
231 above-mentioned standard EN 12697-26. Many researchers such as Monney et al. (2007); Al-Busaltan
232 et al. (2012); Nassar et al. (2016) and (Dulaimi et al., 2016) have used ITSM in order to assess the
233 stiffness modulus of CBEMs as this test is straightforward and can be executed quickly in comparison
234 to other conventional methods of testing (Oke, 2010). ITSM tests were performed at various testing
235 temperatures, 5, 20 and 45°C, to gain a measure of the temperature sensitivity of the CACB mixtures
236 and the control mixtures.

237 **Wheel-tracking test**

238 The wheel-tracking test has been utilised by numerous researchers to assess asphalt mixtures' resistance
239 to rutting (Bodin et al., 2009; Ma et al., 2015). In this study, wheel-tracking tests were conducted at
240 45°C to assess rutting resistance. The test slab specimen with a length of 400mm, width of 305mm and
241 thickness of 50mm was compacted by a roller compactor in accordance with BS EN 12697-33
242 (European Committee for Standardization, 2003b), as shown in Figure 5. Wheel-track tests were

243 conducted for all cold mixtures at full curing condition, which comprises two stages. The first stage
244 was completed by leaving the slabs in their moulds for 1 day at lab temperature, 20°C. Stage two
245 required the slab samples to be placed into a ventilated oven at 40°C for 14 days' curing to achieve their
246 constant mass as recommended by Thanaya (2003) and Al-Hdabi et al. (2014). The curing temperature
247 used is important as it needs to be below the softening point of the bitumen and thus stop the bitumen
248 from ageing (Cardone et al., 2014; Kuna, 2015). The slab samples were then cooled at lab temperature
249 before testing commenced.

250 In this test, a rubber tyre is moved back and forth in the centre of the slab sample at a speed of 42
251 passes/min., with a contact pressure of 700 N and contact width of 50mm. The vertical displacement of
252 the slab sample along the wheel path was measured by linear variable differential transformers (LVDTs),
253 the final vertical deformation an indicator of resistance to rutting. The wheel-track machine type HYCZ-
254 5 shown in Figure 6, is used by the Liverpool Centre for Materials Technology (LCMT) to perform the
255 tests following BS EN 12697-26 (European Committee for Standardization, 2003a). Table 6 details the
256 test conditions.

257 **Fatigue resistance**

258 Fatigue cracking is one of the main structural distress modes found in layers of bituminous road
259 pavement due to the repeated application of traffic-induced stresses which can lead to a substantial
260 decrease in the serviceability of flexible pavements. In this research, an investigation of fatigue
261 performance of the CACB mixtures and hot mixtures was performed using a four point bending test
262 following the standard BS EN 12697-24 (European Committee for Standardization, 2012a) at a test
263 temperature of 20°C using prismatic shaped samples (400 x 50 x 50mm) dimensions samples. Slab
264 specimens were prepared in accordance with the same mixing method detailed in Section 3.2, subject
265 to full curing conditions detailed earlier for wheel track samples after which five prismatic shaped
266 specimens were produced from each slab using a machine saw. The frequency was 10Hz under
267 sinusoidal loading with no rest period and 150 microstrain controlled strain as recommended by Al-
268 Hdabi et al. (2014).

269 Fatigue failure has been defined as cycles number (Nf), at which the initial stiffness is decreased by
270 50%. A Linear variable differential transformer (LVDT) located at the top of the beam was used to
271 measure the vertical deflection at the centre of the beam together with the applied load to determine
272 stresses and strains. The test set up is illustrated in Figure 7.

273 **Moisture damage resistance**

274 The presence of moisture in an asphalt mixture can result in deterioration of the bonds between the
275 aggregate and bitumen. This can lead to adhesive as well as cohesive weakening of the mixture which
276 in turn results in a reduction in its strength, load-carrying capacity and durability of the pavement.
277 Therefore, a water sensitivity assessment is essential because it is directly associated with the durability
278 performance of mixtures throughout the pavement life. Water sensitivity characterisation of the
279 bituminous mixtures followed the standard procedure in BS EN 12697-12 (European Committee for
280 Standardization, 2008). The production of cylindrical specimens consists of manufacturing a set of
281 samples which is divided into two equal subsets. The first subset is kept dry (dry samples) at a
282 temperature of 20°C for 7 days after 1 day inside the mould during preparation, whereas the other subset
283 is wet (wet samples). These specimens were left at 20°C for 4 days after 1 day in the mould. They were
284 then subjected to a vacuum at 20°C, left for 30 minutes under an absolute pressure of 6.7 kPa and then
285 left immersed for another 30 min. Following this, they were soaked and kept in water at 40°C for 3 days.
286 The two sets of samples underwent an ITSM test following EN 12697-26 (European Committee for
287 Standardization, 2012b). From these test results, the stiffness modulus ratio (SMR) was determined as
288 follows:

$$289 \text{ SMR} = (\text{wet stiffness} / \text{dry stiffness}) \times 100$$

290 **Effect on the environment – leaching of metals into water**

291 The two industrial wastes used, HCFA and FC3R, were measured using the toxic characteristic
292 leachability procedure (TCLP) standard in terms of the release of heavy metals by leaching. TCLP is
293 one of the major leaching procedure tests used to examine the risk of heavy metal leachability from
294 stabilised layers (Xue et al., 2009). In this research, a TCLP test was applied to measure the leached

295 concentrations of cadmium (Cd), chromium (Cr), lead (Pb), arsenic (As), barium (Ba), nickel (Ni),
296 copper (Cu) and zinc (Zn) from both the BBCF and HCFA treated mixtures. The tests were carried out
297 following the procedure adopted by Xue et al. (2009) and Modarres and Ayar (2014).

298 The BBCF and HCFA treated mixtures were prepared in the laboratory. A stock of TCLP leachant was
299 prepared by mixing stoichiometric amounts of deionised water and acetic acid (pH 2.88). Weighted
300 amounts (10 grams) of the crushed samples were placed in bottles containing 200 mL of the TCLP
301 leachant. These bottles were then shaken using a rotary extractor at 30 rpm for 18 hours. All experiments
302 were conducted at a temperature of 20°C. After the extraction process, the solutions were filtered using
303 a 47mm glass fibre filter then acidified using acetic acid to a pH below 2. The concentrations of heavy
304 metals were measured using an atomic adsorption spectrophotometer (type: Thermo, Model: ICE 3300),
305 as shown in Figure 8.

306 **Results and discussion**

307 **Performance in the indirect tensile stiffness modulus (ITSM) test**

308 This study examined the effects of HCFA and BBCF with cationic slow-setting bitumen emulsion on
309 the short- and long-term performance of binder course properties using laboratory mechanistic
310 assessment. The method used followed the European standard BS EN 12627-26 (European Committee
311 for Standardization, 2012b). Five specimens were prepared for each mixture type.

312 High calcium fly ash (HCFA) was included as a substitute for conventional limestone filler (LF) of
313 various proportions (0%, 1.5%, 3%, 4.5% and 6%) by total mass of dry aggregate for ITSM testing.

314 The results of these tests are illustrated in Figure 9 where it can be seen that the stiffness modulus of
315 the HCFA treated mixtures was higher than that of the cold emulsion mixture with 6% LF. Stiffness
316 levels depended on the HCFA percentage. The highest ITSM was 3181 MPa for 6% HCFA treated
317 mixture after 3 days, which is a 17 fold increase compared to the reference limestone treated mixture.
318 Comparing this with the hot asphalt concrete binder course mixture, it can be seen that using HCFA
319 gives a stiffness modulus 47.8% higher than that obtained for the traditional AC 20mm with 100/150
320 pen.

321 The improvements seen in the ITSM test are due to the consumption of trapped water and formation of
322 an additional binder from the process of hydration of HCFA. Using HCFA in CACB had a positive
323 effect on the stiffness modulus, particularly within the range of 4.5% to 6% filler replacement. When
324 the HCFA content was 6%, the influence on the stiffness modulus was more noticeable.

325 Waste material with a high aluminosilicate (FC3R) was included as the supplementary cementitious
326 material and worked as an activator in four proportions (1%, 2%, 3% and 4%) by dry aggregate weight
327 as a substitute for HCFA. FC3R is rich in pozzolanic particles which help to speed up the hydration of
328 the HCFA particles, leading to the production of more hydrated products. It can be noted from Figure
329 10 that the addition of FC3R to the HCFA improved both early as well as long-term strength. As
330 mentioned above, the FC3R pozzolanic particles reacted with the $\text{Ca}(\text{OH})_2$ released during the hydration
331 process resulting in an accelerated hydration of the HCFA particles. Consequently, more hydrated
332 products were formed. A balanced oxide composition was expected to be formed within the BBCF. The
333 new BBCF treated mixture was also found to have comparable ITSM to that of the conventional hot
334 asphalt concrete binder course mixture AC 20 mm with 100/150 pen, this in less than 1 day of curing.

335 The hydration of the HCFA particles were been accelerated by existence of the pozzolanic particles
336 provided by the FC3R which generated more hydrated products. The inclusion of pozzolanic materials
337 with a high silica material transformed the soluble calcium hydroxide (C-H) formed from the HCFA
338 hydration reaction, into a dense calcium silicate hydrate (C-S-H) through a pozzolanic reaction
339 (Lothenbach et al., 2011; Sadique et al., 2012). In addition, the formation of hydrous silicates was
340 accompanied by the formation of hydrous calcium aluminates in the pozzolanic materials which include
341 substantial amounts of Al_2O_3 (Morsy et al., 1998). These changes in the materials' structure led to
342 improvements in their mechanical strength (Chan and Xihuang, 1999).

343 It has been demonstrated that there is a considerable development in the stiffness modulus of the
344 specimens containing up to 2% FC3R replacement. This function uncovered its pozzolanic activity,
345 something which was reported by Payá et al. (1999). Therefore, a new binary blended cement filler
346 (BBCF) with 4.5% of HCFA and 1.5% of FC3R may be recommended. This BBCF mixture generated
347 more than a 17% increment in stiffness modulus compared with the HCFA treated mixture after 3 days.

348 However, increasing the percentages of FC3R more than 2% lead to a reduction in ITSM due to the
349 reduction in HCFA percentage and thus decreased the amount of $\text{Ca}(\text{OH})_2$ released as a function of the
350 hydration process which results in some of the FC3R particles showing no reaction.

351 Figure 11 shows that the treated BBCF mixture offers a substantial stiffness modulus in comparison to
352 the HCFA and cold limestone mixtures. Furthermore, the rate of stiffness modulus improvement was
353 clearly higher up to 7 days, when a reduction in this rate was detected. The target stiffness (2000 MPa)
354 can be achieved in 1 day's curing using the BBCF treated mixture, this meeting the British and European
355 requirements in terms of ITSM. Consequently, a new cementitious material made completely from
356 waste materials has been recommended for use in CBEMs.

357 **Temperature sensitivity performance**

358 Figure 12 presents the temperature susceptibility results of all the cold and hot mixtures. The slope of
359 the curve in a semi-logarithmic plane characterises temperature susceptibility where the greater the rate
360 of change, the more temperature sensitive the mixture. The results of ITSM for the LF treated mixture
361 depends significantly on the test temperature applied, which makes these mixtures fail immediately at
362 45°C. However, BBCF and HCFA treated mixtures revealed a considerable lower thermal sensitivity
363 than the two conventional hot asphalt concrete binder course mixtures.

364 **Rutting resistance performance**

365 The sensitivity of a bituminous material to rut is measured by a wheel-tracking test through a loaded
366 wheel making repeated passes at a fixed temperature, this simulating the effect of traffic. The BBCF
367 treated mixture, HCFA mixture, reference limestone mixture and hot asphalt concrete mixtures were
368 subjected to this test. As seen in Figure 13, the rutting resistance for the limestone reference mixture
369 dropped considerably; the cold limestone mixture is especially susceptible to rutting due to the long
370 time this mixture needs to achieve an acceptable performance. Nevertheless, when the BBCF filler was
371 used, the resistance to rutting increased notably to a level even greater than that of the hot asphalt
372 concrete mixture. In detail, the proportional depths of the mixtures' ruts after 10,000 cycles are 1.4%,
373 1.6%, 23.6 %, 5.3% and 6.7% for the BBCF, HCFA, LF, hot AC 20 40/60-pen and hot AC 100/150-

374 pen mixtures respectively. This shows that the rutting resistance of the HCFA treated mixture is
375 enhanced after the addition of FC3R. In terms of the rutting resistance required in practice, it is obvious
376 that the rutting resistance of the BBCF treated mixture is better than both the hot asphalt concrete
377 mixtures. The major reason for this is the higher stiffness of this mixture. Without the new BBCF or
378 even the HCFA, cold limestone is more prone to rutting. This can be attributed to the increase in
379 hydration products being generated by adding FC3R to the BBCF treated mixture.

380 **Fatigue performance**

381 The fatigue cracking resistance of the LF, HCFA, BBCF and the two reference hot mixtures were
382 achieved by using the four-point bending test following BS EN 12697-24 (European Committee for
383 Standardization, 2012a). Fatigue life is defined as the total amount of cycles which produce a 50%
384 reduction in initial stiffness. The results in Figure 14 show the significant variance in fatigue life
385 obtained from the 150 μ strain level at 20°C for both BBCF and LF which was analogous to the outcomes
386 for permanent deformation performance discussed earlier in section 4.3. The fatigue life values are
387 much higher than the corresponding two traditional hot mixtures; the inclusion of BBCF extends fatigue
388 life more than 19 times in comparison to the reference LF mixture, while HCFA extends fatigue life 14
389 times more in comparison to the control LF mixture. Consequently, including BBCF in CACB mixtures
390 considerably extends the fatigue life.

391 It was reported that the potential strain levels that might be experienced in a pavement structure are
392 below 200 microstrain (Brown and Needham, 2000) and they also stated that subgrade, stiffness of the
393 mixture, layer thickness and load represent the major factors affecting the actual strain value.

394 **Moisture damage resistance results**

395 The moisture susceptibility or moisture damage resistance assessment of the cold asphalt concrete
396 binder course mixtures in this research was performed through an indirect tensile stiffness ratio (SMR)
397 test, according to the standard BS EN 12697-12 (European Committee for Standardization, 2008) to
398 examine the impact of both BBCF and HCFA as replacements for the LF. The ITSM values for all types
399 of mixtures are illustrated in Figure 15 for both dry and conditioned samples. It is clearly seen that the

400 stiffness modulus ratio (SMR) for both the BBCF and HCAF treated mixtures is more than 100%; the
401 moisture susceptibility of these mixtures increasing after conditioning the specimens. These results
402 were greater than those for the hot asphalt concrete binder course specimens and reached the
403 requirements for bituminous mixtures. When BBCF was used, the stiffness modulus of both the dry and
404 wet specimens increased significantly. Conversely, it was observed that the cold mixture with limestone
405 filler had a lower stiffness modulus in both dry and wet conditions.

406 The results of the SMR test can be interpreted as follows. When the traditional mineral filler is fully
407 substituted by BBCF, this filler has a stronger bond than the mineral filler. Furthermore, because BBCF
408 contains hydration products, when it is immersed in water this activates the hydration process, resulting
409 in the mixture being less susceptible to moisture damage. In addition, the moisture susceptibility of the
410 BBCF mixture can further activate the hydration process after samples are conditioned at high
411 temperatures. Therefore, a BBCF treated mixture would perform well in terms of moisture susceptibility
412 and could satisfy specification requirements. It is evident that moisture damage is not an issue for the
413 mixes containing BBCF and HCFA, while in the case of the cold limestone mixture, the reduction in
414 stiffness is due to trapped water and the weak early strength of this mixture.

415 **Effect on the environment – leaching into water**

416 The results for the heavy metals, namely nickel (Ni), copper (Cu), lead (Pb), chromium (Cr), zinc (Zn),
417 strontium (Sr), barium (Ba) and cadmium (Cd), can be observed in Table 7, where it can be seen that
418 the concentrations of all the elements presented were zero, except for Cr and Sr, which had a very slight
419 increase as compared to the reference blank water. This means that adding HCFA and FC3R to CACB
420 does not have any negative impact on the environment. In addition, it is established that not did only
421 the application of HCFA and FC3R in CACB have technical benefits but this also reduced the
422 leachability of the waste and its harmful effects on the environment, meeting the requirements of the
423 standard limits and standing within regulatory levels (Modarres and Nosoudy, 2015; Modarres et al.,
424 2015).

425

426 **Conclusions**

427 A novel, fast-curing cold asphalt concrete for the binder course (CACB) mixture has been developed
428 which incorporates waste materials as the filler replacement. This mixture has benefits for the road
429 industry, in particular with regard to its contribution to sustainability, since this is an environmentally
430 friendly mixture. The main conclusions in this investigation are as follows:

- 431 • This research presents an environmentally friendly CACB mixture with substantial engineering
432 properties for use as a binder course in road pavements. It can be stated that the BBCF treated
433 mixture is a new technology with a mechanical performance comparable to traditional hot mix
434 asphalt binder course mixtures.
- 435 • A new binary blended cement filler (BBCF) comprising 4.5% HCFA and 1.5% FC3R was
436 created. A balanced oxide composition in the binary blend was responsible for the advanced
437 pozzolanic reactivity displayed. In addition, using FC3R as a pozzolanic material rapidly
438 enhanced the ITSM of the BBCF treated mixture.
- 439 • The BBCF treated mixture was found to have a higher stiffness modulus than the cold limestone
440 mixture and the relevant traditional hot asphalt concrete binder course AC 20mm with 100/150
441 pen. In addition, the BBCF treated mixture showed significant temperature susceptibility
442 resistance.
- 443 • The BBCF treated mixture can be used in the asphalt binder layer to offer significant rutting
444 resistance because of its high stiffness modulus as well as stability at high temperature.
- 445 • The BBCF mixture accomplished a significant improvement in fatigue life, extending fatigue
446 life more than 19 times that of the control LF mixture.
- 447 • In terms of water sensitivity, the BBCF treated mixture has an SMR of more than 100%, which
448 is higher than conventional hot mixtures and cold limestone mixture. Progressive curing with
449 the BBCF treated mixture accounted for higher resistance to water damage.
- 450 • The problems relating to carbon emissions (during production) and mixture temperature
451 maintenance (during transportation and laying) in the case of hot mix asphalt will be mitigated
452 by using this fast-curing CACB.

453 • An environmental investigation of the influence of using HCFA and FC3R in CACB mixtures
454 reveals that there are no negative impacts on the environment as the heavy metals will not leach
455 into the environment, thus there will be no pollution as a result of using this mixture. Analysis
456 of the TCLP demonstrates that these two wastes are non-hazardous and can therefore be
457 categorised as general industrial waste. This will encourage pavement and asphalt agencies to
458 promote their use.

459

460 **Acknowledgements**

461 The authors would like to acknowledge the financial support provided by the Ministry of Higher
462 Education in Iraq and Kerbala University. In addition, the authors wish to thank Jobling Purser, Colas
463 and Francis Flower for the bitumen emulsion, aggregate and limestone filler that were kindly provided
464 for the current research.

465 **References**

- 466 Al-Busaltan, S., Al Nageim, H., Atherton, W. & Sharples, G. (2012), Mechanical Properties of an Upgrading
467 Cold-Mix Asphalt Using Waste Materials, *Journal of materials in civil engineering* 24, 1484-91.
- 468 Al-Hdabi, A., Al Nageim, H., Ruddock, F. & Seton, L. (2013), Enhancing the Mechanical Properties of Gap
469 Graded Cold Asphalt Containing Cement Utilising By-Product Material, *Journal of Civil Engineering
470 and Architecture*, 7, 916-921.
- 471 Al-Hdabi, A., Al Nageim, H. & Seton, L. (2014), Performance of gap graded cold asphalt containing cement
472 treated filler, *Construction and Building Materials*, 69, 362-69.
- 473 Al Nageim, H., Al-Busaltan, S. F., Atherton, W. & Sharples, G. (2012), A comparative study for improving the
474 mechanical properties of cold bituminous emulsion mixtures with cement and waste materials,
475 *Construction and Building Materials*, 36, 743-748.
- 476 Bodin, D., Grenfell, J. R. & Collop, A. C. (2009), Comparison of Small and Large Scale Wheel Tracking
477 Devices, *Road Materials and Pavement Design*, 10, 295-325.
- 478 Brown, S. F. & Needham, D. (2000), A study of Cement Modified Bitumen Emulsion Mixtures. Association of
479 Asphalt Paving Technologists Conference Proceeding (AAPT), Reno, Nevada 92-121.
- 480 Cardone, F., Grilli, A., Bocci, M. & Graziani, A. (2014), Curing and temperature sensitivity of cement-bitumen
481 treated materials, *International Journal of Pavement Engineering*, 16, 868-880.
- 482 Chan, S. Y. N. & Xihuang, J. (1999), Comparative study of the initial surface absorption and chloride diffusion
483 of high performance zeolite, silica fume and PFA concretes, *Cement & Concrete Composites*, 21, 293-
484 300.
- 485 Dulaimi, A., Al Nageim, H., Hashim, K., Ruddock, F. & Seton, L. (2016), Investigation into the Stiffness
486 Improvement, Microstructure and Environmental Impact of A Novel Fast-Curing Cold Bituminous
487 Emulsion Mixture. *Eurasphalt & Eurobitume Congress*, Prague, Czech Republic.
- 488 Ellis, C., Zhao, B., Barnes, J. & Jones, N. (2004), Properties of GGBS-Bitumen Emulsion Systems with
489 Recycled Aggregates, *Road Materials and Pavement Design*, 5:3, 373-383.
- 490 European Asphalt Pavement Association (EAPA) (2014), *Asphalt in figures*, EAPA.
- 491 European Committee for Standardization (2003a), *BS EN 12697: Part 22*. Bituminous mixtures -Test methods
492 for hot mix asphalt - Wheel tracking test methods for hot mix asphalt London, UK: British Standards
493 Institution.

494 European Committee for Standardization (2003b), BS EN 12697: Part 33. Bituminous mixtures - Test methods
495 for hot mix asphalt - Specimen prepared by roller compactor, London, UK: British Standards
496 Institution.

497 European Committee for Standardization (2006), BS EN 13108: Part 1. Bituminous mixtures materials
498 specification-Asphalt Concrete, London, UK: British Standards Institution.

499 European Committee for Standardization (2008), BS EN 12697: Part 12. Bituminous mixtures-test methods for
500 hot mix asphalt-determination of the water sensitivity of bituminous specimens, London, UK: British
501 Standards Institution.

502 European Committee for Standardization (2012a), BS EN 12697-24. Bituminous mixtures-Test methods for hot
503 mix asphalt- Part 24: Resistance to fatigue, London, UK: British Standards Institution.

504 European Committee for Standardization (2012b), BS EN 12697: Part 26. Bituminous mixtures-test methods for
505 hot mix asphalt- stiffness, London, UK: British Standards Institution.

506 European Committee for Standardization (2015), PD 6691: Guidance on the use of BS EN 13108 Bituminous
507 mixtures – Material specifications, London, UK: British Standards Institution.

508 Gómez-Mejide, B. & Pérez, I. (2014), Effects of the use of construction and demolition waste aggregates in
509 cold asphalt mixtures, *Construction and Building Materials*, 51, 267-277.

510 Head, R. W. (1974), An informal report of cold mix research using emulsified asphalt as a binder. Association
511 of Asphalt Paving Technologists Conference Proceeding (AAPT), USA. 110-131.

512 Khalid, H. A. & Monney, O. K. (2009), Moisture damage potential of cold asphalt, *International Journal of*
513 *Pavement Engineering*, 10, 311-318.

514 Kuna, K. (2015), Mix design considerations and performance characteristics of foamed bitumen mixtures
515 (FBMs). Ph.D. Thesis, University of Nottingham, United Kingdom.

516 Lea, F. (1970), *The chemistry of cement and concrete*, London, Edward Arnold.

517 Leech, D. (1994), *Cold Asphalt Materials for Use in the Structural Layers of Roads*, Transport Research
518 Laboratory, Project Report 75, UK.

519 Li, D., Chen, Y., Shen, J., Su, J. & Wu, X. (2008), The influence of alkalinity on activation and microstructure
520 of fly ash, *Cement and Concrete Research*, 30, 881-86.

521 Lothenbach, B., Scrivener, K. & Hooton, R. D. (2011), Supplementary cementitious materials, *Cement and*
522 *Concrete Research*, 41, 1244-1256.

523 Ma, T., Wang, H., Huang, X., Wang, Z. & Xiao, F. (2015), Laboratory performance characteristics of high
524 modulus asphalt mixture with high-content RAP, *Construction and Building Materials*, 101, 975-982.

525 Modarres, A. & Ayar, P. (2014), Comparing the mechanical properties of cold recycled mixture containing coal
526 waste additive and ordinary Portland cement, *International Journal of Pavement Engineering*, 1-14.

527 Modarres, A. & Nosoudy, Y. M. (2015), Clay stabilization using coal waste and lime — Technical and
528 environmental impacts, *Applied Clay Science*, 116-117, 281-288.

529 Modarres, A., Ramyar, H. & Ayar, P. (2015), Effect of cement kiln dust on the low-temperature durability and
530 fatigue life of hot mix asphalt, *Cold Regions Science and Technology*, 110, 59-66.

531 Monney, O. K., Khalid, H. A. & Artamendi, I. (2007), Assessment of Fracture Properties of Emulsified Asphalt
532 Mixtures, *Road Materials and Pavement Design*, 8, 87-102.

533 Morsy, M. S., Galal, A. F. & Abo-El-Enein, S. A. (1998), Effect of temperature on phase composition and
534 microstructure of artificial pozzolana-cement pastes containing burnt kaolinite clay, *Cement and*
535 *Concrete Research*, 28, 1157-1163.

536 Nassar, A. I., Mohammed, M. K., Thom, N. & Parry, T. (2016), Mechanical, durability and microstructure
537 properties of Cold Asphalt Emulsion Mixtures with different types of filler, *Construction and Building*
538 *Materials*, 114, 352-363.

539 Nikolaidis, A. (1994), New design method for dense cold mixtures. , In: *Proceedings of the first European*
540 *symposium on performance and durability of bituminous materials*. University of Leeds.

541 Oke, O. (2010), A Study on the Development of Guidelines for the Production of Bitumen Emulsion Stabilised
542 RAPS for Roads in the Tropics. Ph.D. thesis, University of Nottingham.

543 Oruc, S., Celik, F. & Akpınar, V. (2007), Effect of cement on emulsified asphalt mixtures, *Journal of Materials*
544 *Engineering and Performance*, 16, 578-583.

545 Pacewska, B., Wilinska, I. & Kubissa, J. (1998), Use of spent catalyst from catalytic cracking in fluidized bed as a
546 new concrete additive, *Thermochimica Acta*, 322, 175-181.

547 Payá, J., Monzó, J. & Borrachero, M. V. (1999), Fluid catalytic cracking catalyst residue (FC3R) An excellent
548 mineral by-product for improving early-strength development of cement mixtures, *Cement and*
549 *Concrete Research*, 29, 1773-1779.

550 Rubio, M. D. C., Moreno, F., Martínez-Echevarría, M. J., Martínez, G. & Vázquez, J. M. (2013), Comparative
551 analysis of emissions from the manufacture and use of hot and half-warm mix asphalt, *Journal of*
552 *Cleaner Production*, 41, 1-6.

553 Sadique, M., Al Nageim, H., Atherton, W., Seton, L. & Dempster, N. (2012), *A new composite cementitious*
554 *material for construction*, Construction and Building Materials, 35, 846-55.
555 Terrel, R. L. & Wang, C. K. (1971), Early curing behavior of cement modified asphalt emulsion mixtures.
556 Association of Asphalt Paving Technologists Conference Proceeding (AAPT). 108-125.
557 Thanaya, I. N. A. (2003), Improving the performance of cold bituminous emulsion mixtures incorporating waste
558 materials. Ph.D. thesis, University of Leeds, UK.
559 Thanaya, I. N. A., Forth, J. P. & Zoorob, S. E. (2009), A laboratory study on cold-mix, cold-lay emulsion
560 mixtures, Proceedings of the ICE - Transport, 162, 47-55.
561 Thanaya, I. N. A., Negara, I. N. W. & Suarjana, I. P. (2014), Properties of Cold Asphalt Emulsion Mixtures
562 (CAEMs) Using Materials from Old Road Pavement Milling, Procedia Engineering, 95, 479-488.
563 Thanaya, I. N. A., Zoorob, S. E. & Forth, J. P. (2006), Utilisation of Coal Ashes in Hot and Cold Bituminous
564 Mixtures. International Coal Ash Technology Conference. The Birmingham Hippodrom Theatre,
565 Birmingham, West Midlands, UK.
566 Xue, Y., Hou, H., Zhu, S. & Zha, J. (2009), Utilization of municipal solid waste incineration ash in stone mastic
567 asphalt mixture: Pavement performance and environmental impact, Construction and Building
568 Materials, 23, 989-996.

569

570

571

572

573

574

575

576

577

578

579

580

581

582

583

584 Figure captions

Figure no.	Title
Figure 1	Gradation of aggregates
Figure 2	Powder XRD pattern of HCFA
Figure 3	Powder XRD pattern of FCER
Figure 4	ITSM Apparatus machine
Figure 5	Roller compactor machine
Figure 6	Wheel-tracking equipment used by LCMT lab
Figure 7	Test set up for the four point bending test
Figure 8	Atomic adsorption spectrophotometer
Figure 9	ITSM results for HCFA replacement after 3 days
Figure 10	Influence of substitution of HCFH with FC3R on ITSM after 3 days
Figure 11	Effect of curing time on ITSM of BBCF mixture
Figure 12	Temperature susceptibility results
Figure 13	Wheel-tracking test results
Figure 14	Four-point bending beam fatigue test results
Figure 15	ITSM test results in saturated and dry conditions

585
 586
 587
 588
 589
 590
 591
 592
 593
 594

595 List of tables

Table no.	Title
Table 1	Aggregate physical properties
Table 2	Properties of (C60B5) bitumen emulsion
Table 3	Properties of 40/60 and 100/150 bitumen binders
Table 4	EDXRF analysis of the chosen filler materials, %
Table 5	Conditions of the ITSM test
Table 6	Wheel-tracking test conditions
Table 7	Concentrations of heavy metals in leachate water, (mg/L)

596
 597
 598
 599
 600
 601
 602
 603
 604
 605
 606
 607
 608
 609
 610
 611
 612
 613
 614
 615

616

Table 1. Aggregate physical properties

Material	Property	Value
Coarse aggregate	Bulk particle density, Mg/m ³	2.62
	Apparent particle density, Mg/m ³	2.67
	Water absorption, %	0.8
Fine aggregate	Bulk particle density, Mg/ m ³	2.54
	Apparent particle density, Mg/ m ³	2.65
	Water absorption, %	1.7
Traditional mineral filler	Particle density, Mg/ m ³	2.57

617

618

619

620

621

622

623

624

625

626

627

628

629

630

631

632

633

634

635

636

637

638

639

640

Table 2. Properties of (C60B5) bitumen emulsion

Description	(C60B5) bitumen emulsion
Type	Cationic
Appearance	Black to dark brown liquid
Base bitumen	100/150 pen
Bitumen content, (%)	60
Particle surface electric charge	Positive
Boiling point, (°C)	100
Relative density at 15°C, (g/ml)	1.05

641

642

643

644

645

646

647

648

649

650

651

652

653

654

655

656

657

Table 3. Properties of 40/60 and 100/150 bitumen binders

Bituminous binder 40/60		Bituminous binder 100/150	
Property	Value	Property	Value
Appearance	Black	Appearance	Black
Penetration at 25°C, (0.1 mm)	49	Penetration at 25°C, (0.1 mm)	131
Softening point, (°C)	51.5	Softening point, (°C)	43.5
Density at 25°C, (g/cm ³)	1.02	Density at 25°C, (g/cm ³)	1.05

659

660

661

662

663

664

665

666

667

668

669

670

671

672

673

674

675

676

677

678

679

680

681

682

683

684

Table 4. EDXRF analysis of the chosen filler materials, %

Chemical composition	CaO	SiO ₂	Al ₂ O ₃	MgO	Fe ₂ O ₃	SO ₃	K ₂ O	TiO ₂	Na ₂ O
HCFA	67.057	24.762	2.430	2.845	0.000	0.340	0.266	0.473	1.826
FC3R	0.047	35.452	44.167	0.684	0.368	0	0.049	0	0
LF	76.36	16.703	0	0.981	0	0.096	0.348	0.185	2.258

685

686

687

688

689

690

691

692

693

694

695

696

697

698

699

700

701

702

703

704

705

706

707

708

709

710

711

712

Table 5. Conditions of the ITSM test

Item	Range
Specimen diameter, (mm)	100 ± 3
Rise time, (ms)	124 ± 4
Transient peak horizontal deformation, (µm)	5
Loading time, (s)	3–300
Poisson's ratio	0.35
No. of conditioning plus	5
No. of test plus	5
Test temperature, (°C)	20 ± 0.5
Specimen thickness, (mm)	63 ± 3
Compaction	Marshall 50 blows/face
Specimen temperature conditioning	4 h before testing

713

714

715

716

717

718

719

720

721

722

723

724

725

726

727

728

729

730

731

732

733

Table 6. Wheel-tracking test conditions

Item	Range
Tyre of outside diameter, (mm)	200-205
Tyre width, (mm)	50 ± 5
Trolley travel distance, (mm)	230 ± 10
Trolley travel speed, (s/min)	42 ± 1
Contact pressure, (MPa)	0.7 ± 0.05
Poisson's ratio	0.35
No. of conditioning cycles	5
No. of test passes	10000
Test temperature, (°C)	45
Compaction	Roller compactor
Specimen temperature conditioning	4hr before testing

734

735

736

737

738

739

740

741

742

743

744

745

746

747

748

749

750

751

752

753

754

Table 7. Concentrations of heavy metals in leachate water, (mg/L)

	Ba	Cu	Cd	Pb	Zn	Cr	Ni	Sr
Reference water quality	0.0	0.0	0.0	0.0	0.0	0.0	0.0	0.0
Leachate water (HCFA mix)	0.0	0.0	0.0	0.0	0.0	0.009	0.0	0.367
Leachate water (BBCF mix)	0.0	0.0	0.0	0.0	0.0	0.008	0.0	0.257
TCLP regulatory level	100	25	1	5	25	5	25	-

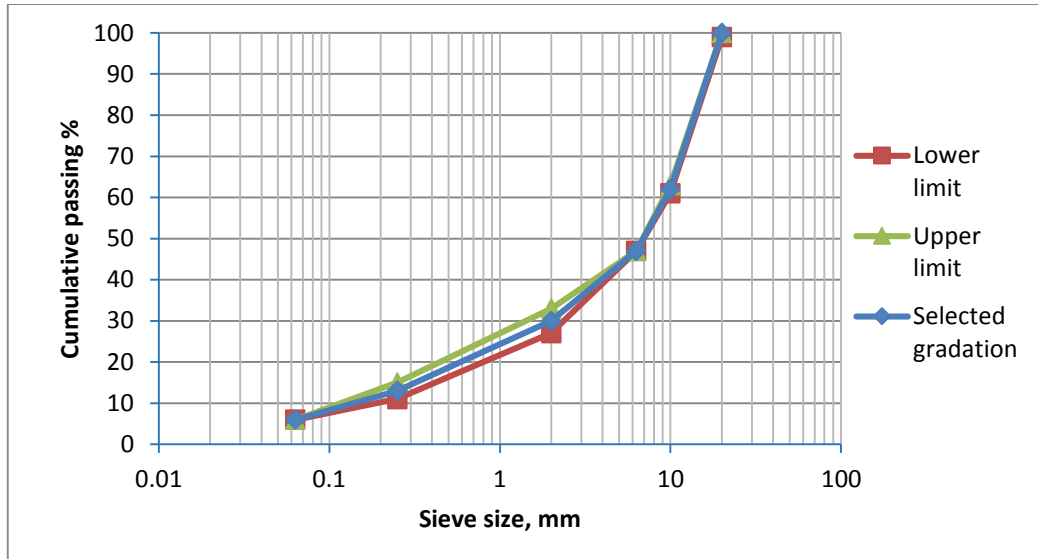


Figure 1. Gradation of aggregates

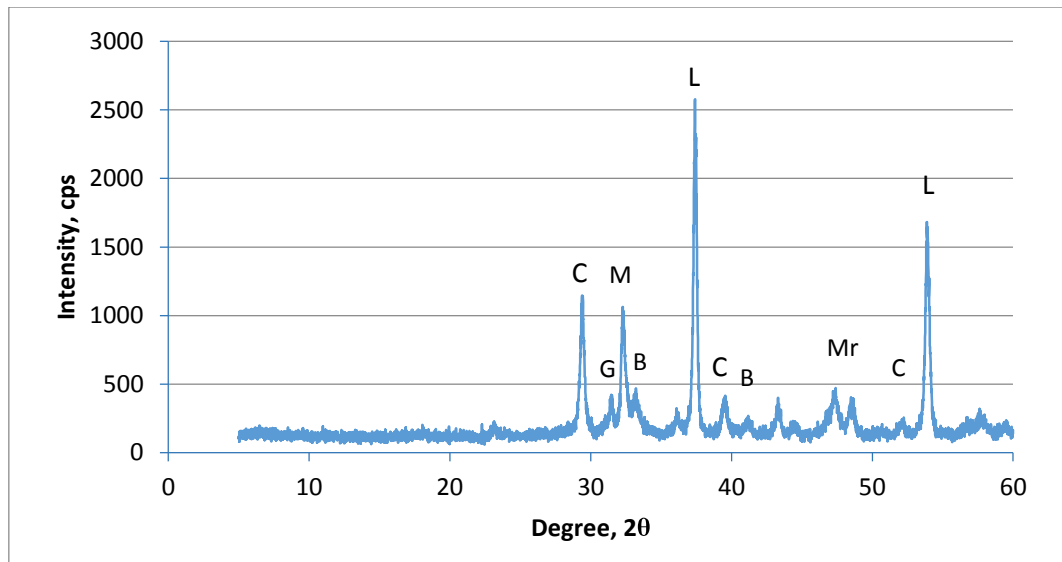


Figure 2. Powder XRD pattern of HCFA

(lime-L, calcite-C, gehlenite-G, belite-B, mayenite-M, merwinite-Mr)

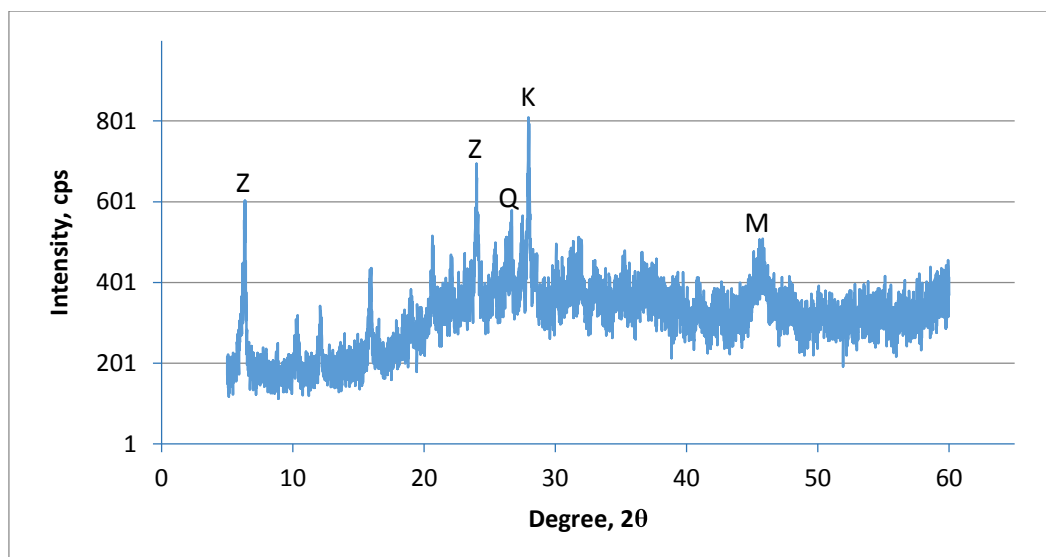


Figure 3. Powder XRD pattern of FCER

(K- kyanite ($\text{Al}_2\text{O}_3\text{Si}$), Q – quartz (SiO_2), M- mullite ($\text{Al}_6\text{Si}_2\text{O}_{13}$), Z- dehydrated Ca-A zeolite ($\text{Al}_{96}\text{Ca}_{48}\text{O}_{384}\text{Si}_{96}$))

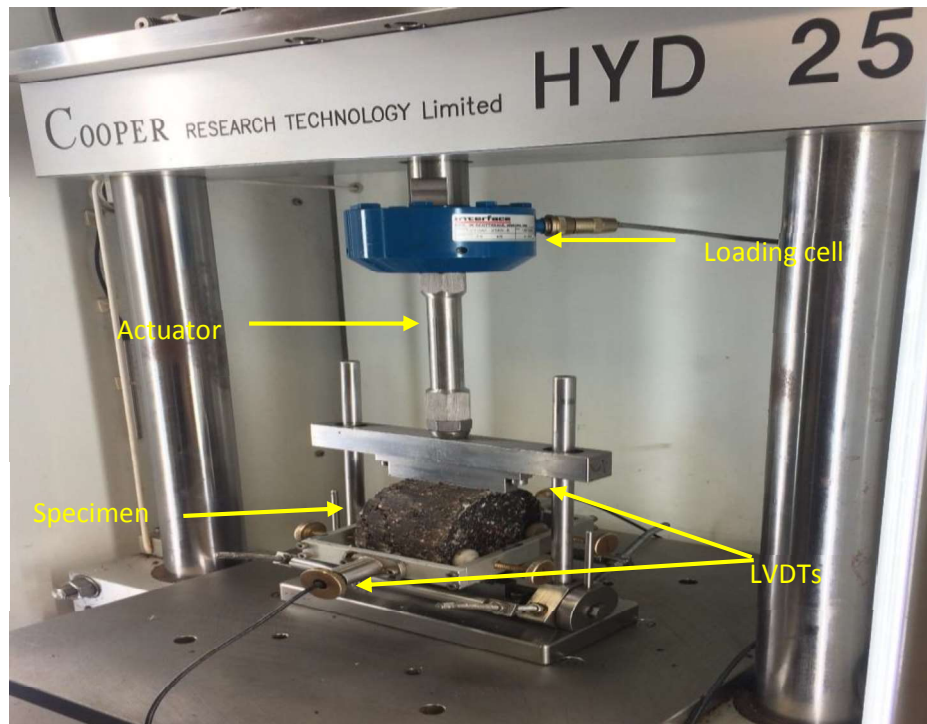


Figure 4. ITSM Apparatus machine



Figure 5. Roller compactor machine

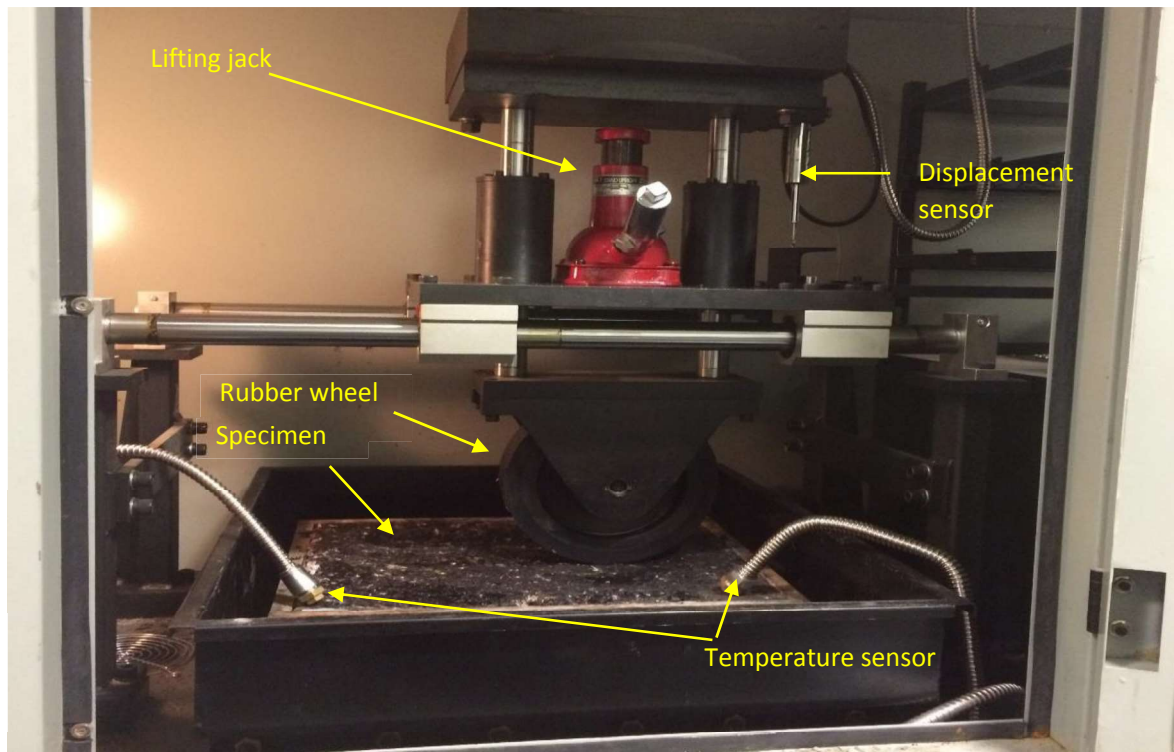


Figure 6. Wheel-tracking equipment used by LCMT lab

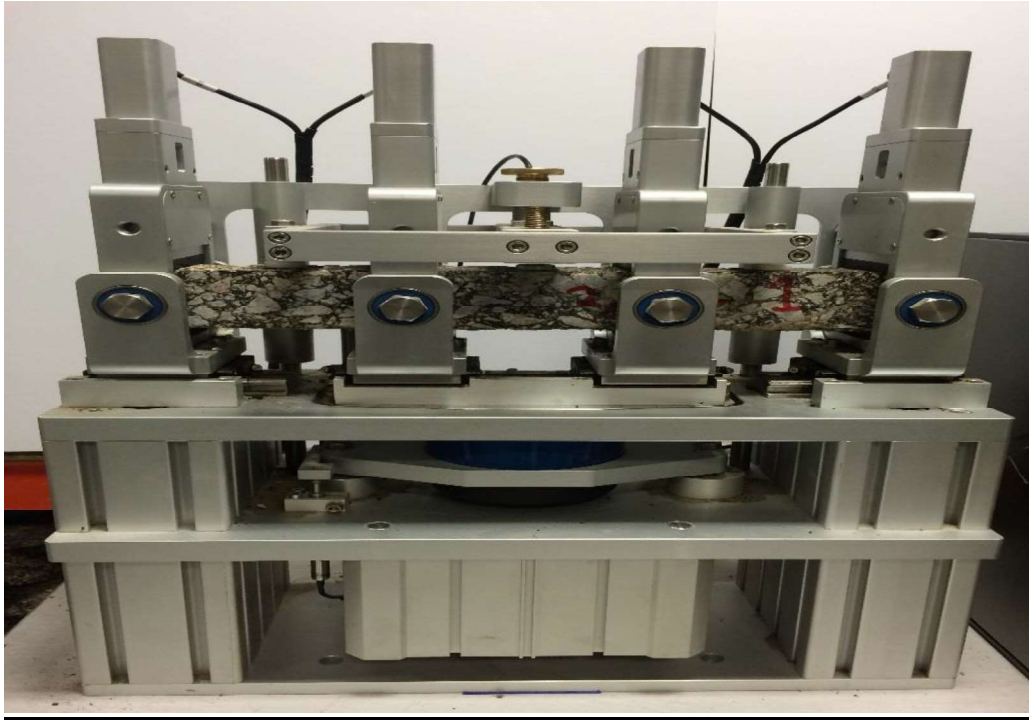


Figure 7. Test set up for the four point bending test

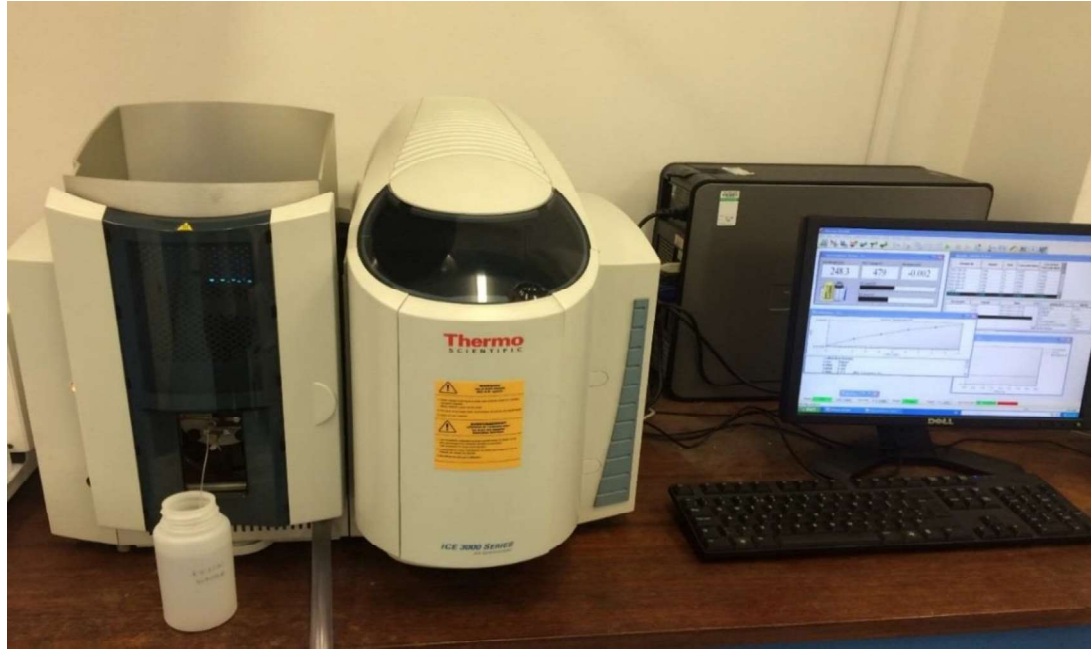


Figure 8. Atomic adsorption spectrophotometer

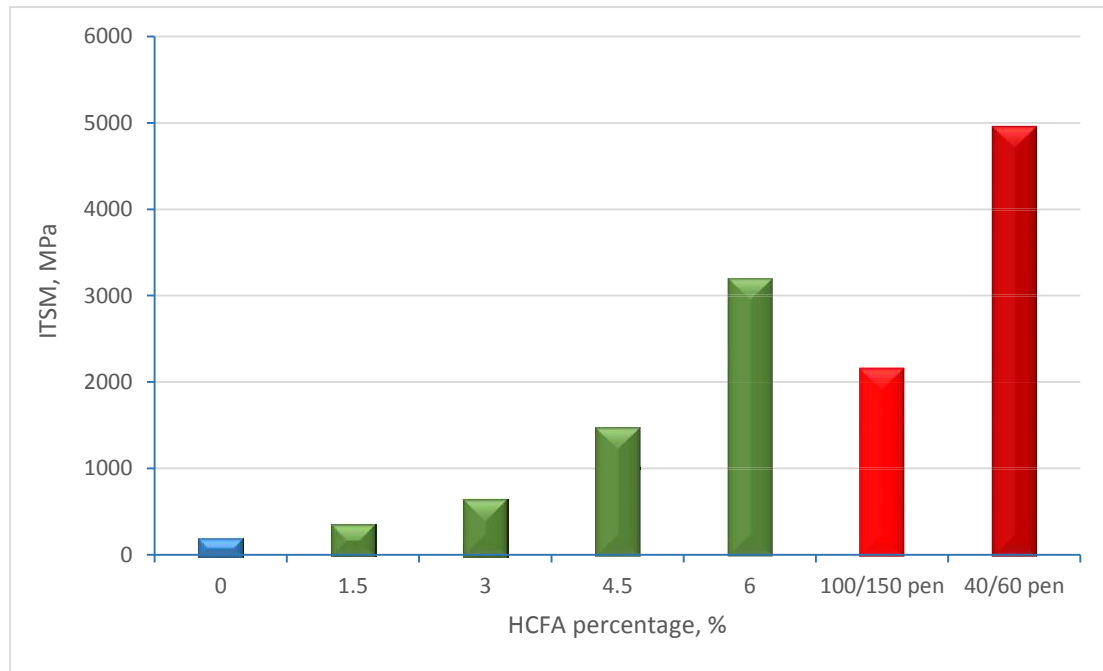


Figure 9. ITSM results for HCFA replacement after 3 days

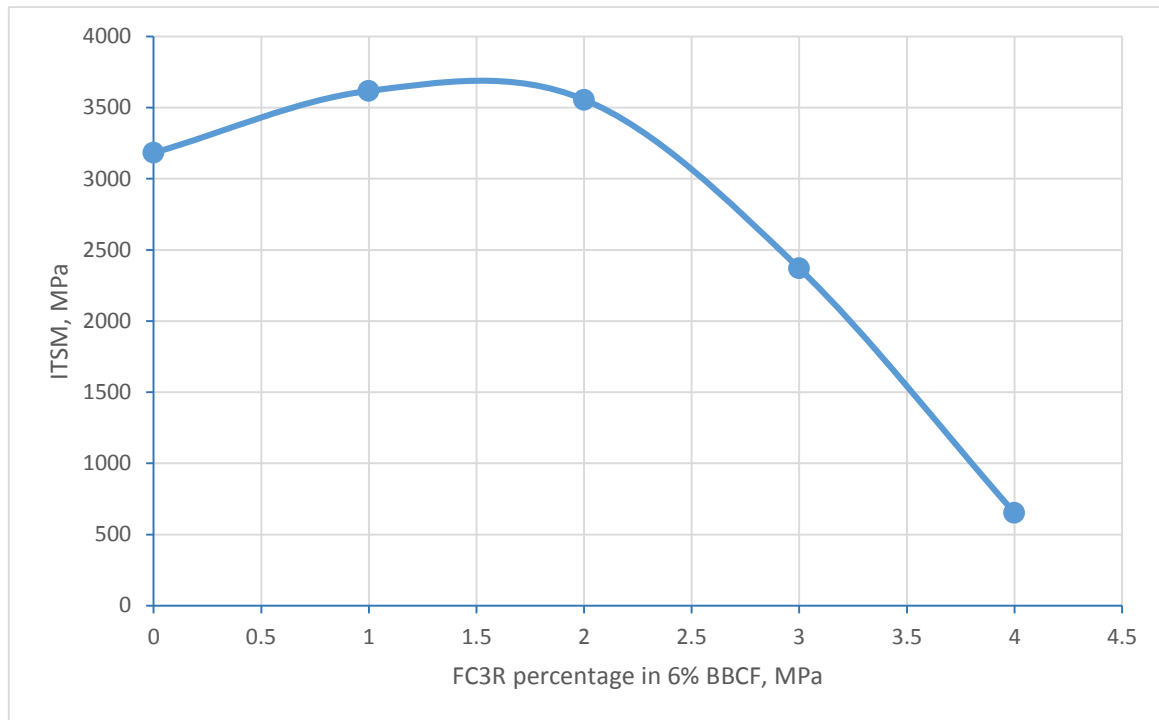


Figure 10. Influence of substitution of HCFH with FC3R on ITSM after 3 days

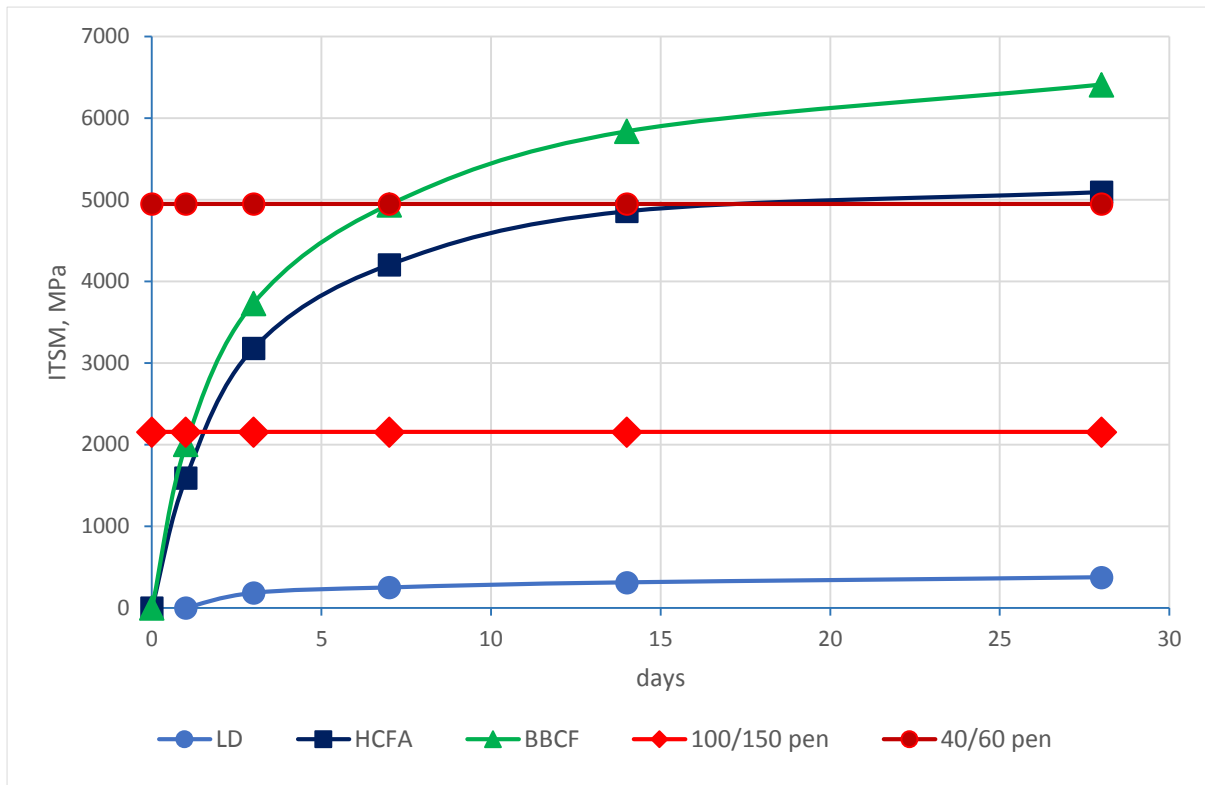


Figure 11. Effect of curing time on ITSM of BBCF mixture

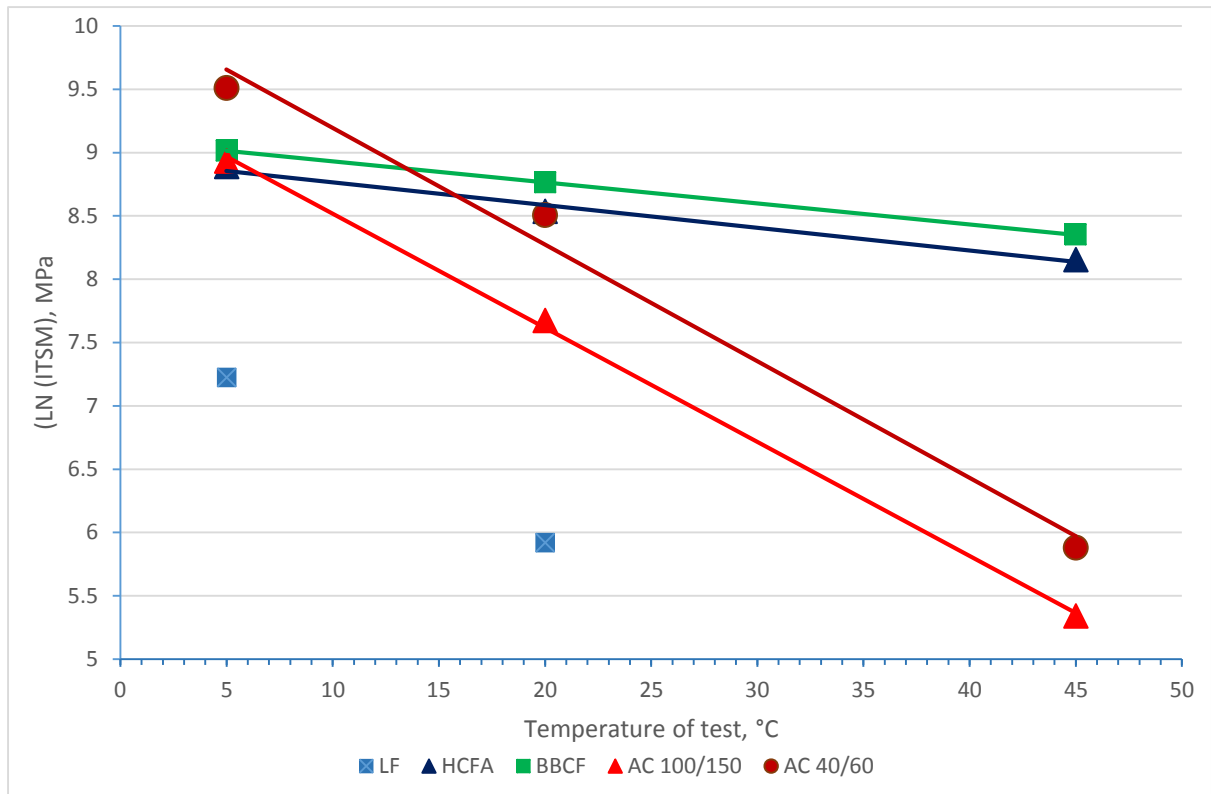


Figure 12. Temperature susceptibility results

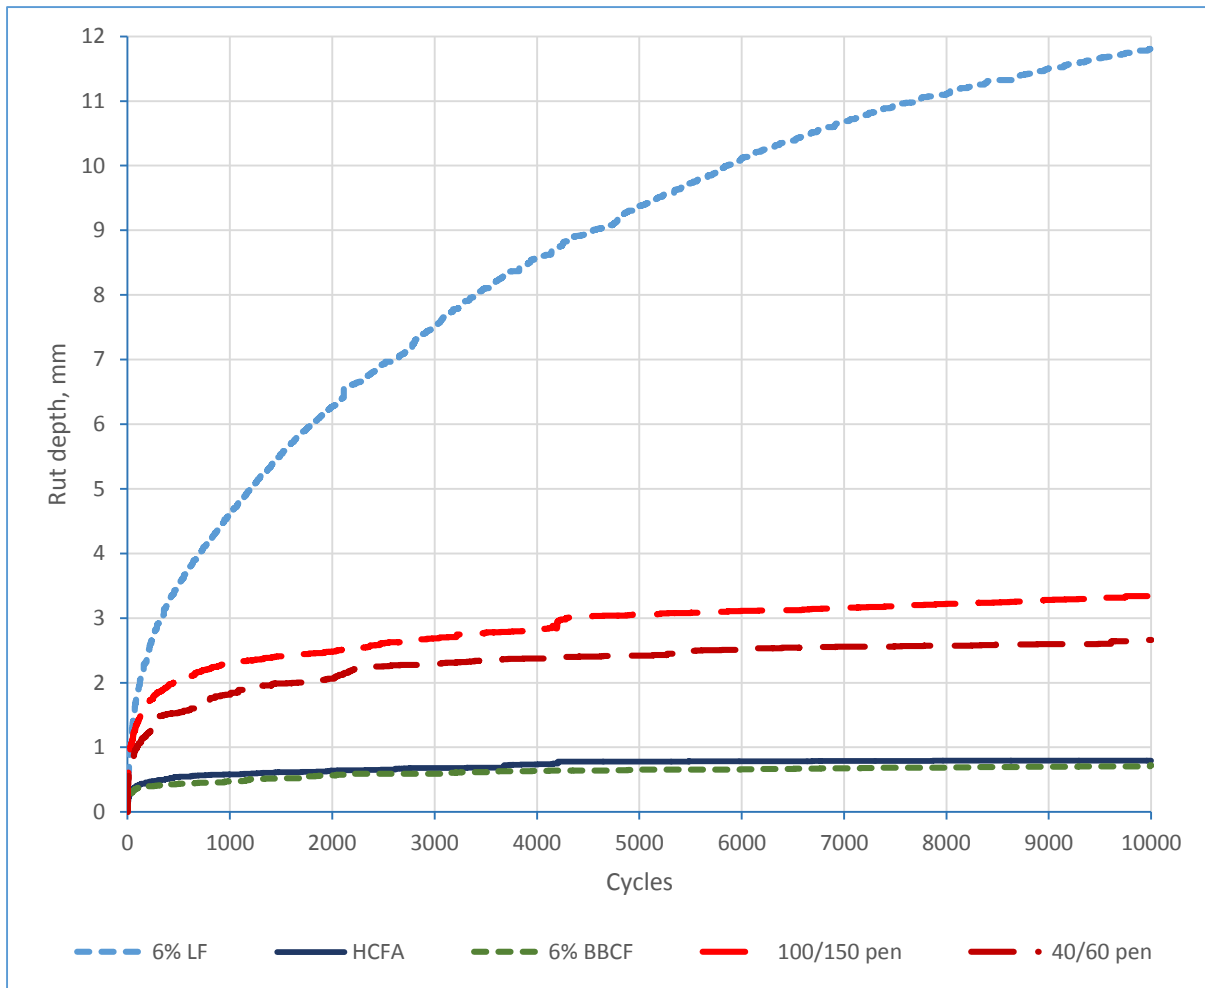


Figure 13. Wheel-tracking test results

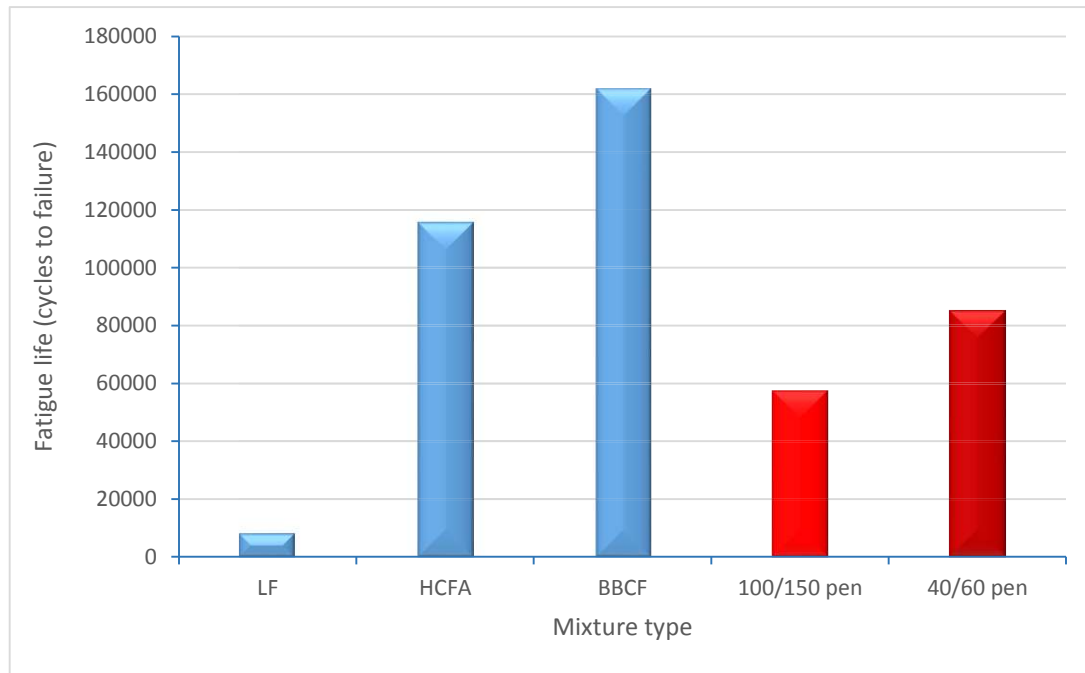


Figure 14. Four-point bending beam fatigue test results

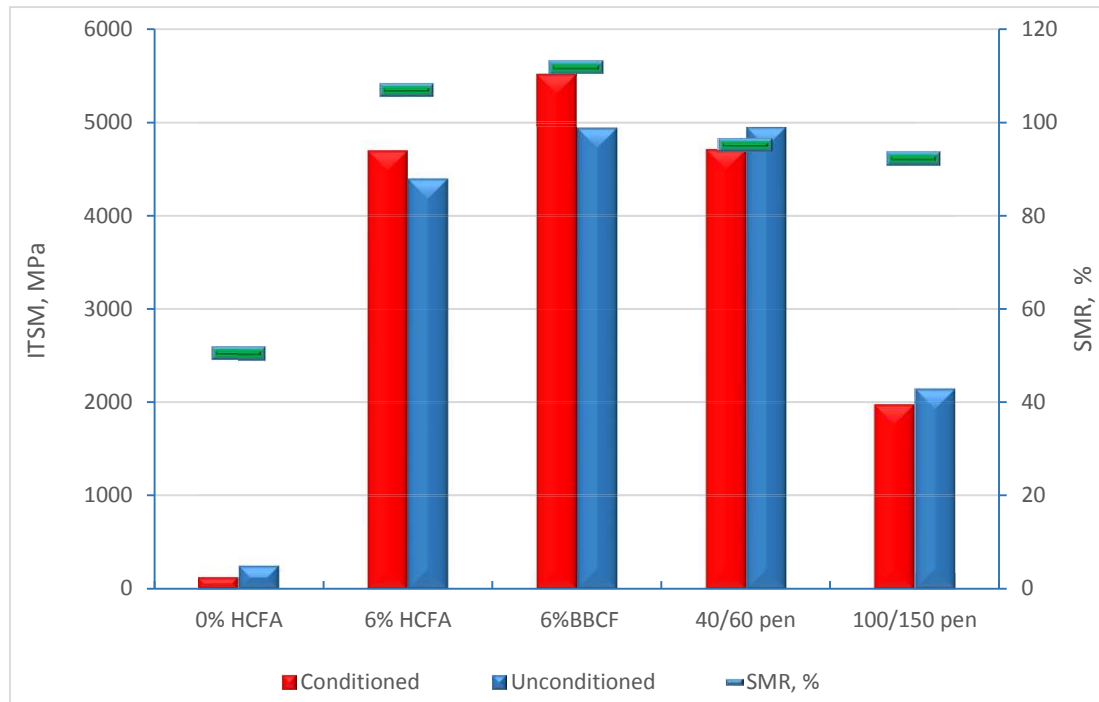


Figure 15. ITSM test results in saturated and dry conditions