

Technical University of Denmark



Spectroscopic analysis of LiTmF₄

Christensen, H.P.

Published in:
Physical Review B Condensed Matter

Link to article, DOI:
[10.1103/PhysRevB.19.6573](https://doi.org/10.1103/PhysRevB.19.6573)

Publication date:
1979

Document Version
Publisher's PDF, also known as Version of record

[Link back to DTU Orbit](#)

Citation (APA):
Christensen, H. P. (1979). Spectroscopic analysis of LiTmF₄. Physical Review B Condensed Matter, 19(12), 6573-6582. DOI: 10.1103/PhysRevB.19.6573

DTU Library

Technical Information Center of Denmark

General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

Spectroscopic analysis of LiTmF₄

H. P. Christensen

Department of Electrophysics, The Technical University of Denmark, DK-2800 Lyngby, Denmark

(Received 12 February 1979)

The absorption spectra of Tm³⁺ in LiTmF₄ have been measured at 2, 10, 30, and 50 K in the spectral interval 4000–25000 cm⁻¹. The energy levels of the ground-state configuration were calculated by diagonalizing the Hamiltonian of the electron-electron interaction, the spin-orbit coupling, and the crystal field in a basis of the whole configuration. The electrostatic parameter F_2 , the spin-orbit parameter ζ , and the crystal-field parameters B_{kq} were varied to obtain the best agreement with the experimentally observed levels. As the model does not account for configuration mixing and minor magnetic effects, it was necessary after optimizing F_2 and ζ to match the centers of gravity for the multiplets before the final adjustment of the B parameters. When this was done, the standard deviation was lowered from 170 to 12 cm⁻¹. The B parameters obtained for Tm³⁺ have been compared to those of Tb³⁺, Ho³⁺, and Er³⁺ in LiLnF₄, and they follow a common trend. The intensities of the transitions from the ground state were calculated in the Judd-Ofelt scheme, fitting six complex intensity parameters $A(kq\lambda)$ for best agreement with the experimentally observed intensities. The model was only able to give a rough estimate of the transition probabilities. The obtained relative standard deviation was 1.1. Contrary to what was found in the case of the energy calculations, it was important for the intensity calculations that the B parameters were allowed to take complex values. The imaginary part of the A parameters was not important to the intensities.

I. INTRODUCTION

This paper is the third and last in a series of papers reporting on spectroscopic investigation of dense LiLnF₄ crystals, where Ln—which is tripositive in LiLnF₄—is one of the heavier elements of the lanthanide group (the first series of rare earths).

The first paper was concerned with LiTbF₄,¹ the second with LiHoF₄ and LiErF₄,² and here the results for LiTmF₄ are given. Spectroscopic data for Tm³⁺ diluted in LiYF₄ have been reported by Jenssen *et al.*³

The chief purpose of this series of papers has been the experimental determination of the energy levels and the extraction of the crystal-field parameters for the Ln site in LiLnF₄. In order to exploit the information in the experimental data better, for LiTmF₄ it has also been tried to estimate the intensities of the optical transitions and compare them with those experimentally observed.

The theory for the energy and intensity calculations is summed up in Sec. II. The experimental data are presented in Sec. III, and the calculated values are given in Sec. IV. In Sec. V the results are discussed in connection with those obtained in the two preceding papers.

II. THEORY

Going up through the heavy Ln³⁺ ions, the ground-state configuration becomes increasingly simple and separated from excited configurations.

The ground configuration of Tm³⁺ is 4f¹², which is 91 times degenerate. The ground multiplet is ³H₆. Apart from the isolated ¹S level, which is situated around 78 000 cm⁻¹ above the ground level, the extension of the ground configuration is approximately 39 000 cm⁻¹. The distance from the ground level to the lowest level of the next configuration is approximately 60 000 cm⁻¹ (Dieke⁴).

A. Energy levels

The Hamiltonian for the system is given by

$$H = H_{ee} + H_{so} + H_{cf}, \quad (1)$$

where

$$H_{ee} = e^2 \sum_{i>j} \frac{1}{r_{ij}} \quad (2)$$

is the electron-electron interaction,

$$H_{so} = \zeta \sum_i (\vec{l}_i \cdot \vec{s}_i) \quad (3)$$

is the spin-orbit coupling, and

$$H_{cf} = \sum_{kq} B_{kq} \sum_i (C_i)_q^{(k)} \quad (4)$$

is the crystal field. The B parameters are given by

$$B_{kq} = \langle \gamma^k \rangle A_{kq}. \quad (5)$$

The expansion of the crystal field in terms of Legendre polynomials (which are equivalent to the

C operators) is only a formal way of introducing the symmetry of the crystal, since it has not been possible to set up a model for calculating the A parameters.

The matrix elements of H_{ee} may be expressed as linear combinations of the radial parameters F_2 , F_4 , and F_6 . For f electrons it is a good approximation to set $F_4 = 0.138 F_2$ and $F_6 = 0.0151 F_2$. Hence, there are only two free-ion parameters: F_2 and the spin-orbit parameter ξ .

For Ln ions heavier than Sm, LiLnF_4 crystallizes in the stable scheelite structure (space group $I4_1/a$). At the Ln site the point symmetry is S_4 . In this symmetry the only nonvanishing crystal-field parameters with k even influencing f electrons are A_{20} , A_{40} , A_{44} , A_{60} , and A_{64} , where the coordinate system may be chosen, so only the imaginary part of A_{64} differs from zero. The parameters with k odd give no contribution to the crystal-field splitting of the multiplets within a single configuration.

In S_4 symmetry the multiplets split up in non-degenerate levels, whose eigenfunctions transform according to the Γ_1 or Γ_2 representation of the point group and in two times degenerate levels transforming according to $\Gamma_3\Gamma_4$ (in the notation of Koster *et al.*⁵).

B. Transition probabilities

Electric-dipole (ED) transitions are to first order forbidden within a single configuration, since the ED operator is of odd parity. The magnetic-dipole (MD) operator is of even parity, but other selection rules restrict MD transitions to occur between multiplets for which J does not differ by more than one.

For Ln ions at sites without inversion symmetry (as in S_4 symmetry), transitions within the ground configuration are seen between most of the levels without the restriction $\Delta J \leq 1$. An explanation of these transitions were given by Judd⁶ and Ofelt,⁷ and the details for the present case will be sketched in the following.

1. Intensity model

Sites without inversion symmetry possess crystal-field terms with k odd, and these mix configurations of opposite parity into the ground configuration. ED transitions are now allowed between the new levels with mixed wave functions, which do not have a definite parity.

The ED operator is given by

$$\vec{H}_{ed} = -e \sum_i \vec{r}_i. \quad (6)$$

The integrated intensity I of a transition between

two states Ψ_1 and Ψ_2 is given by

$$I = c \Delta E \sum_p |\langle \Psi_1 | (H_T)_p^{(1)} | \Psi_2 \rangle|^2, \quad (7)$$

where c is a constant, ΔE is the energy difference between the levels, and $(H_{ed})_p^{(1)}$ is the p th component of the transition operator on tensor form.

For ED transitions $p = 0$ are related to π polarization and $|p| = 1$ to σ polarization. The matrix elements H_{12}^p of $(H_{ed})_p^{(1)}$ between two mixed states ψ'_1 and ψ'_2 are given by the expression

$$H_{12}^p = \sum_i [\langle \psi_1 | (H_{ed})_p^{(1)} | \phi_i \rangle \langle \phi_i | H_{ct} | \psi_2 \rangle / (E_2 - E_i) + \langle \psi_1 | H_{ct} | \phi_i \rangle \langle \phi_i | (H_{ed})_p^{(1)} | \psi_2 \rangle / (E_1 - E_i)], \quad (8)$$

where ψ_1 and ψ_2 are the pure wave functions of the ground configuration, and ϕ_i are wave functions of excited configurations of opposite parity. E_1 , E_2 , and E_i are the energies of the corresponding levels.

In the Judd-Ofelt model it is now assumed that $|E_1 - E_2| \ll |E_1 - E_i|$, i.e., $E_2 \approx E_1$, and that the excited configurations are completely degenerate. These approximations are unfortunately not always well fulfilled. After some algebraic manipulations one then arrives at the expression

$$H_{12}^p = \sum_{k\lambda} (-1)^{p+q} A_{kq} \Xi(k, \lambda) \begin{pmatrix} 1 & k & \lambda \\ -p & -q & p+q \end{pmatrix} \langle \psi_1 | U_{p+q}^{(\lambda)} | \psi_2 \rangle, \quad (9)$$

where the two last factors in the terms are a 3- j symbol and a matrix element of a unit tensor operator, respectively. For f electrons $\Xi(k, \lambda)$ is given by

$$\Xi(k, \lambda) = 2 \sum_{n_l} (-1)^{k+i} [f] [l] [\lambda] \frac{1}{E_1 - E_{n_l}} \begin{pmatrix} f & 1 & l \\ 0 & 0 & 0 \end{pmatrix} \begin{pmatrix} f & k & l \\ 0 & 0 & 0 \end{pmatrix} \times \langle 4f | r | n_l \rangle \langle 4f | r^k | n_l \rangle \begin{Bmatrix} 1 & k & \lambda \\ f & f & l \end{Bmatrix}, \quad (10)$$

where $[x] = 2x + 1$, $f = 3$, and the last factor in the terms is a 6- j symbol. The sum runs over excited configurations ϕ of the form $4f^{l_1} n_l$, where $l = f \pm 1$.

2. Intensity parameters

It is not possible to make correct *ab initio* calculations of $\Xi(k, \lambda)$, since it requires the knowledge of the energies and the radial part of the wave functions of excited configurations of parity opposite to that of the ground configuration.

One possibility for obtaining values for the $\Xi(k, \lambda)$ parameters is to exclude in the calculations all configurations but the few lowest. This approximation, however, is not good. Even if the mixing from the lower configurations is much stronger than from the higher, the density of the configurations grows so fast, as the continuum is approached, that the total effect from these configura-

rations is not negligible.

Another possibility is to treat $\Xi(k, \lambda)$ as adjustable parameters. For f electrons k may take the odd values 3, 5, and 7, and λ the values 2, 4, and 6. A triangle rule on the $6-j$ symbol limits the nonvanishing parameters to $\Xi(3, 2)$, $\Xi(3, 4)$, $\Xi(5, 4)$, $\Xi(5, 6)$, and $\Xi(7, 6)$. In S_4 symmetry the crystal-field parameters with k odd are A_{32} , A_{52} , A_{72} , and A_{76} , which may all be complex. As was the case for the even crystal-field parameters, the odd parameters cannot be calculated from first principles. Hence, the crystal-field parameters must also be treated as variable parameters.

To limit the number of free parameters, the $\Xi(k, \lambda)$ and A_{kq} parameters may be combined to new parameters:

$$A(kq\lambda) = A_{kq}\Xi(k, \lambda). \quad (11)$$

This gives six complex parameters: $A(322)$, $A(324)$, $A(524)$, $A(526)$, $A(726)$, and $A(766)$. There are, however, restrictions on some of these parameters:

$$\begin{aligned} \text{Im}A(324) &= \text{Im}A(322)[\text{Re}A(324)/\text{Re}A(322)], \\ \text{Im}A(526) &= \text{Im}A(524)[\text{Re}A(526)/\text{Re}A(524)], \end{aligned} \quad (12)$$

which reduce the number of free parameters to ten. According to Minhas and Sharma,⁸ further restrictions are valid for these parameters: $\text{Re}A(324)$ must have the same sign as $\text{Re}A(322)$, and $\text{Re}A(526)$ the same sign as $\text{Re}A(524)$.

III. EXPERIMENTS

A. Experimental setup

A single crystal of LiTmF₄ was oriented by x-ray technique, and a slab about 1 mm thick was cut with faces perpendicular to an a axis. Examination of the slab revealed some small blisters or grains in the crystal.

The absorption spectra were recorded using a modified Zeiss MM12 monochromator. A Glan prism was used as polarizer. The spectral resolution was better than 6 cm^{-1} . For low-temperature

measurements a simple glass-cryostat system was used, as described elsewhere.⁹

B. Experimental results

The absorption spectra for polarized light were recorded for LiTmF₄ in the region from 4000 to $25\,000 \text{ cm}^{-1}$ ($2.5\text{--}0.4 \mu\text{m}$) at 2, 10, 30, and 50 K. This spectral interval covers the transitions from the ground multiplet to the other multiplets of the three lowest terms (3H , 3F , and 1G).

1. Interpretation of the lines

At 2 K only transitions from the ground state may be seen. The wave function of the ground state transforms according to the Γ_2 representation of S_4 . $\Gamma_2 \rightarrow \Gamma_1$ ED transitions occur in π polarization, $\Gamma_2 \rightarrow \Gamma_3\Gamma_4$ in σ polarization, whereas $\Gamma_2 \rightarrow \Gamma_2$ transitions of ED nature are not allowed.

Thus at 2 K only lines corresponding to transitions to Γ_1 and $\Gamma_3\Gamma_4$ levels should occur. Actually, more lines were seen, but many of them were weak and broad. The broad lines were always situated at the high-energy side of strong and rather sharp lines. All the sharp lines could be interpreted as ED transitions to Γ_1 or $\Gamma_3\Gamma_4$ levels. A few of the expected lines were missing.

The lines of the sidebands must be due to phonon-assisted transitions. The experimental fact that the side lines always had higher energy than the zero-phonon line—i.e., phonons are emitted in the processes—is in accordance with the fact that at 2 K there are no phonons to be absorbed. A collection of energy differences from the sharp lines to the broad lines are plotted in Fig. 1.

The energies of the phonon modes in LiYF₄ are given by Miller *et al.*,¹⁰ and the energies of the phonon modes in LiTmF₄ should probably not deviate much from these. Although it looks like the energy differences in Fig. 1 are grouped around certain values, there is no similarity to the energy scheme for the phonon modes in LiYF₄. The previous examinations of LiLnF₄ crystals^{1,2} have also shown that the regular phonon modes in these crystals normally are rather inactive. The sidebands in LiTmF₄ may therefore involve local phonons due to lattice defects.

In order to determine the energy of the levels to which transitions were not seen at 2 K, the spectra were recorded at 10 K, 30 K, and 50 K. The warm-up spectra were consistent with additional transitions from a $\Gamma_3\Gamma_4$ level at 32 cm^{-1} and a Γ_1 level at 57 cm^{-1} .

To examine the temperature dependence of the transitions, the transitions to the $\Gamma_3\Gamma_4$ level at $21\,207 \text{ cm}^{-1}$ were followed to room temperature. The line position and linewidth are shown as a

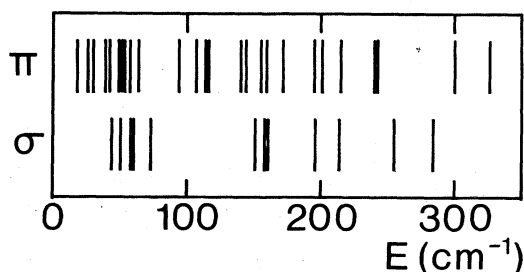


FIG. 1. Distance in energy at 2 K from the zero-phonon lines to the lines of the sidebands.

TABLE I. Experimental and calculated energies in cm^{-1} and calculated term composition of the wave functions for the levels of the lowest multiplets of Tm^{3+} in LiTmF_4 . Δc_{gs} gives the adjustment of the calculated centers of gravity for the multiplets. Experimental and calculated intensities of the transitions from the ground level to the other levels. "0" in the column of Expt. intens. indicates that the transition was not seen at 2 K, and " ∞ " that the absorption was too strong to be determined with the sample used.

J	Γ	Expt. energy	Calc. energy	Δc_{gs}	Wave funct.	pol.	Expt. intens.	Calc. intens.
6	2	0	0	...	99% 3H
	34	32	31		1% 1I	0.2
	1	57	62			0.1
	2	...	287			0
	2	...	316			0
	1	...	365			6
	34	...	382			51
	34	...	410			106
	1	...	421			1
	2	...	436			0
4	1	5585	5570	97	57% 3F	π	1	4
	34	5757	5746		34% 1G	σ	86	62
	1	5757	5762		9% 3H	π	35	94
	2	5828	5822			...	0	0
	1	5957	5976			π	29	19
	2	5961	5955			...	0	0
	34	5965	5983			σ	∞	922
	2	8270	8263	-138	99% 3H	...	0	0
5	34	8287	8278		+ $^3F, ^1G$	σ	34	23
	1	8287	8296			π	30	76
	34	8500	8490			σ	97	77
	1	8519	8532			π	61	1
	2	...	8533			...	0	0
	34	...	8541			...	0	14
	1	...	8555			...	0	158
	2	12595	12597	-130	58% 3H	...	0	0
4	1	12615	12616		29% 3F	π	5	21
	34	12650	12636		13% 1G	σ	54	76
	1	12740	12742			π	∞	29
	1	12805	12802			π	28	13
	34	12830	12839			σ	37	195
	2	...	12913			...	0	0
	34	14540	14531	-269	99% 3F	σ	31	35
	3	2	14557	14560		+ $^3H, ^1G$...	0
34		14600	14609			σ	34	37
2		...	14609			...	0	0
1		14625	14620			π	∞	856
2		15092	15096	-332	78% 3F	...	0	0
2	34	15210	15194		19% 1D	σ	31	38
	2	...	15218		2% 3P	...	0	0
	1	15255	15267		+ $^3H, ^1G$...	0	4
	4	1	20980	20999	102	53% 1G	π	1
4	34	21207	21207		37% 3H	σ	61	45
	2	21297	21297		10% 3F	...	0	0
	1	21320	21334			π	134	39
	2	21526	21513			...	0	0
	34	21575	21573			σ	∞	411
	1	21578	21556			π	21	6

function of the temperature in Fig. 2. It is seen that within the experimental accuracy the line position is temperature independent. The broadening with increasing temperature is moderate.

2. Line intensity

The transmission coefficient $T(E)$ for light with photon energy E through a crystal is approximately given by

$$T(E) \approx (1 - R)e^{-\alpha(E)d}, \quad (13)$$

where R is the reflection coefficient, $\alpha(E)$ is the loss coefficient of the crystal, and d is the thickness of the crystal. For energies which are equal to the difference between two energy levels, $\int \alpha(E) dE$ is approximately proportional to the intensity I [Eq. (7)] of the transition between these levels, if the lowest is completely populated.

If reflection is neglected, i.e., if the transmission coefficient between the lines is set equal to 1, the intensity of a transition may be determined from the experimental transmission in the following way:

$$I = \frac{c'}{d} \int \ln \frac{1}{T(E)} dE, \quad (14)$$

where c' is a constant.

For weak absorption ($T \approx 1$) $\ln[1/T(E)] \approx 1 - T(E)$, which means that

$$I \approx \frac{c'}{d} \int [1 - T(E)] dE \quad (15)$$

may be used for crystals with weak absorption, e.g., lightly doped crystals. For dense crystals this approximation is not valid. The intensity of the strong transitions would be estimated too low. Most important is that since $\ln[1/T(E)]$ tends towards infinity for $T(E)$ going towards zero, it is not possible to determine the intensity of lines with absorption near 100%.

The experimental intensities of the transitions at 2 K (for $c'/d \approx 1 \text{ cm}^{-1}$) are listed in Table I.

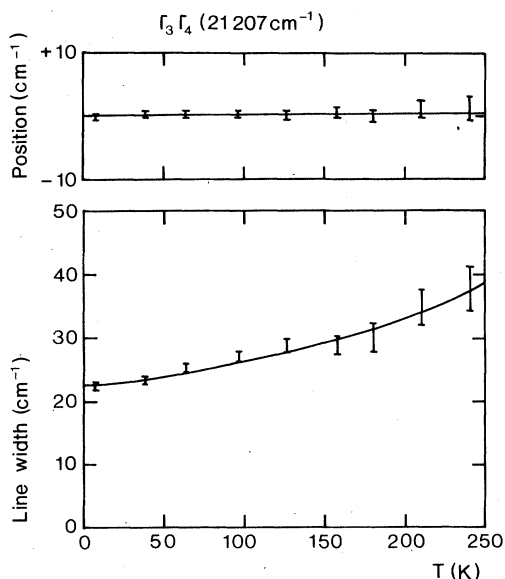


FIG. 2. Line position and linewidth of the transition from the ground level to the $\Gamma_3 \Gamma_4$ level at $21\,207 \text{ cm}^{-1}$ of Tm^{3+} in LiTmF_4 as a function of temperature.

IV. CALCULATIONS

The three lowest terms of $4f^{12}$ are heavily mixed via the $J = 4$ multiplets. This can be seen from the free-ion correlation diagram given in Fig. 3, in which the energies of the multiplets are plotted as function of the ratio of the spin-orbit parameter ζ to the electrostatic parameter F_2 . In this diagram pure multiplets will show up as straight lines. Due to the strong term mixing calculations within the ground term are of no use for Tm^{3+} . The Hamiltonian has to be diagonalized in a larger basis.

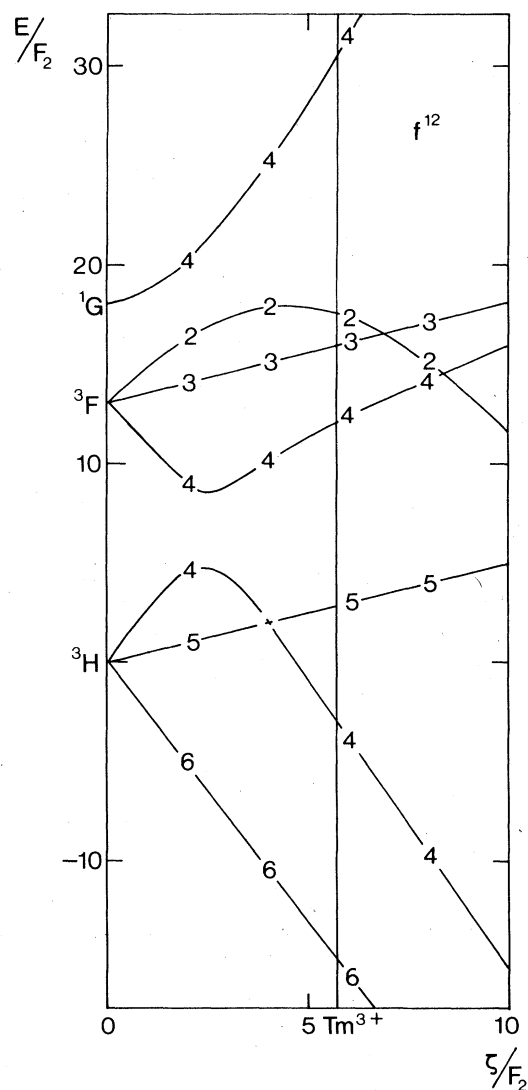


FIG. 3. Energy—normalized with respect to F_2 —of multiplets of free ions with f^{12} configuration as a function of the ratio of the spin-orbit parameter ζ to the electrostatic parameter F_2 . The multiplets are identified by their J number. The position of Tm^{3+} is indicated by the vertical line.

A. Energy levels

The energy levels of the ground configuration were calculated by diagonalizing the energy Hamiltonian described in Sec. IIA in a LS basis of the configuration. The F_2 parameter, the ζ parameter, and the six B parameters were varied until the best agreement was obtained with the 35 experimentally observed levels listed in Table I.

The standard deviation s of the energy fit is given by

$$s = \left(\sum_{i=1}^N \frac{(\Delta E_i)^2}{N-M} \right)^{1/2}, \quad (16)$$

where N is the number of levels, and M is the number of free parameters.

The fitting procedure gave an s of 170 cm^{-1} . A better agreement was not to be expected, since no attempt has been made to account for configuration mixing. If this mixing is omitted, it is not possible in the calculations to arrive at the right centers of gravity for the multiplets.

The standard deviation of 170 cm^{-1} was obtained with the F_2 and ζ values listed in Table II together with the free-ion values given by Wybourne.¹¹ It is important that the fitted values do not differ too much from the free-ion values—otherwise the model is unrealistic.

The way the configuration mixing is normally introduced in the calculations (see, e.g., Ref. 3) is not easily seen through, and may as well account for other inadequacies of the model. Instead of modifying the model, it was decided to fix F_2 and ζ on the values obtained, match the centers of gravity for each multiplet, and vary the B parameters only. In this way an s of 12 cm^{-1} was obtained. The B parameters of this fit are given in the second column of Table III.

The calculated energy levels and term composition of the wave functions are listed in Table I. The term composition of the wave functions do not differ from level to level within a multiplet. The adjustment of the center of gravity for each multiplet is also given in Table I.

TABLE II. Electron-electron and spin-orbit parameters in cm^{-1} for Tm^{3+} .

	In LiTmF_4	Free ion
F_2	469	451
F_4	(64.7) ^a	68.1
F_6	(7.1) ^a	7.4
ζ	2663	2656

^a Not allowed to vary freely.

Setting $\text{Im}B_{64}$ equal to zero and varying the five remaining B parameters only, gave an agreement just as good as when all six parameters were varied. The parameters obtained in this way are listed in the first column of Table III. The observation that $\text{Im}B_{64}$ has little influence on the energies of the levels is in agreement with the fact that on the Ln site in the scheelite structure the local symmetry is almost D_{2d} , in which all parameters are real. Although the wave functions are real in D_{2d} symmetry, their term composition does not differ from that of the complex S_4 wave function within the accuracy of the calculations.

B. Transition probabilities

The intensities of the ED transitions from the ground state to the other levels of the ground configuration were calculated using the model described in Sec. IIB1. The energies and the wave functions of the levels used in these calculations were those obtained from fitting to the energy levels. The intensities of the MD transitions were not considered, since they are only allowed to the 3H_5 multiplet, and there was no experimental evidence for their presence. This is in contrast to the case of LiHoF_4 and LiErF_4 ,² where MD transitions to the first excited multiplet were comparable in strength to the ED transitions.

The ten A parameters of Sec. IIB2 were varied until the best agreement with the experimental data was obtained. Of the 23 transitions observed at 2 K, only 19 were used in the fitting procedure, since four were so strong that it was not possible to get a realistic value for the intensity with the thickness of the sample used. As a measure of the discrepancy between experimental and calculated intensities the relative standard deviation σ was used. σ is given by

$$\sigma = \left(\sum_{i=1}^N \frac{[2(I_i^{\text{cal}} - I_i^{\text{ex}})/(I_i^{\text{cal}} + I_i^{\text{ex}})]^2}{N-M} \right)^{1/2}, \quad (17)$$

where N is the number of transitions, and M is the number of free parameters. The reason for

TABLE III. Crystal-field parameters in cm^{-1} for Tm^{3+} in LiTmF_4 . (i) $\text{Im}B_{64} = 0$; (ii) $\text{Im}B_{64}$ allowed to vary freely; (iii) $\text{Im}B_{64} = 320 \text{ cm}^{-1}$. The uncertainty on the parameters are $\pm 10 \text{ cm}^{-1}$.

	i	ii	iii
B_{20}	368	367	364
B_{40}	-717	-716	-711
B_{44}	919	918	884
B_{60}	-65	-64	-64
$\text{Re}B_{64}$	619	615	594
$ \text{Im}B_{64} $	0	118	320

using the relative standard deviation is to give all the transitions the same weight in the fitting procedure. Minhas and Sharma,⁸ who use the absolute deviation, fit actually to the strongest transitions only.

Contrary to what was the case for the energy fits, it was not possible to get rapid convergency towards a minimum for the intensity fits. It was difficult to find good starting values for the A parameters. Neither the parameters given for Nd³⁺ in PbMnO₄ by Minhas and Sharma,⁸ nor the parameters which could be calculated from the theoretical works of Morrison *et al.*¹² and Wortman *et al.*¹³ gave good results. The best convergence was obtained by starting with all the A parameters set equal to zero.

As stated in Sec. IV A, it is a usable approximation in the energy calculations to assume D_{2d} symmetry. In this symmetry Γ_1 of S_4 splits up in two different representations. In S_4 symmetry transitions from the ground state are allowed to both types of levels, whereas only transitions to one of the types are allowed in D_{2d} symmetry. Experimentally transitions to both types of levels are observed, even if many of the D_{2d} forbidden lines are weak. Therefore, it is not possible to use D_{2d} symmetry in the intensity calculations.

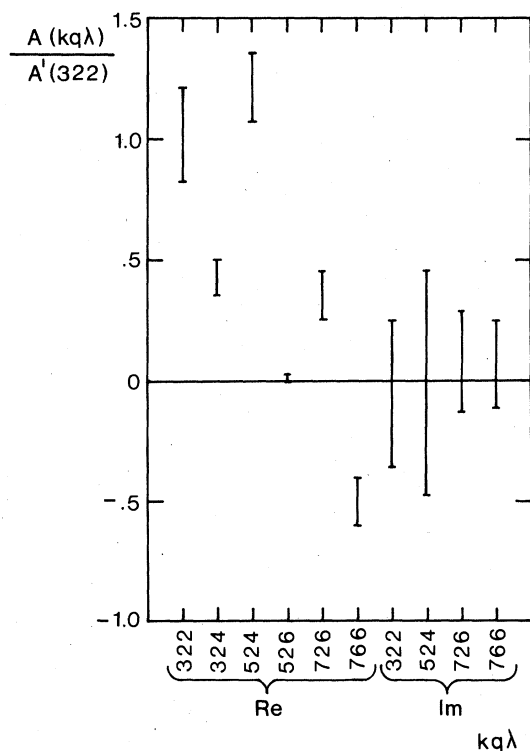


FIG. 4. Range in which the relative parameters $A(kq\lambda)$ may run without altering the relative standard deviation more than 10%.

Since it is not possible to get a good determination of $\text{Im}B_{64}$ from the energy fit, the intensity fits might be used to estimate the value of this parameter. The dependence of the intensities on this parameter was rather strong and peculiar. There was indeed a minimum in σ around the value 118 cm^{-1} obtained from the energy fit, but there was another and deeper minimum around 320 cm^{-1} . The minima were separated by a high sharp peak in the proximity of 200 cm^{-1} .

With $\text{Im}B_{64}$ fixed on 320 cm^{-1} , a new energy fit was carried out. The agreement obtained was as good as in the two previous fits with $\text{Im}B_{64}$ equal to zero or to 118 cm^{-1} , respectively. The new B parameters are listed in the last column of Table III. It is seen that changes in $\text{Im}B_{64}$ mostly affect the other nondiagonal parameters, B_{44} and $\text{Re}B_{64}$.

It is not possible to determine the sign of $\text{Im}B_{64}$, neither in the energy fit nor in the intensity fit. But the signs of the imaginary parts of the A parameters depend on the sign of $\text{Im}B_{64}$.

With the B parameters of the third column of Table III an intensity fit was obtained with $\sigma = 1.1$. The calculated intensities are given in Table I and the corresponding values of the A parameters normalized with respect to the real part of $A(322)$ are presented in the second column of Table IV. The absolute values of the A parameters have no meaning, since the parameters are fitted to relative intensities. The signs of the imaginary parts of the A parameters are those obtained for $\text{Im}B_{64} = +320 \text{ cm}^{-1}$.

The minimum of σ was not very sharp. In Fig. 4 the intervals in which each parameter may run without altering the relative standard deviation more than 10% are shown. It is seen that the imaginary parts of the parameters are very badly determined; they may run over both positive and negative values. With all the imaginary parts of the A parameters set equal to zero the real parameters listed in the first column of Table IV were

TABLE IV. Intensity parameters for Tm³⁺ in LiTmF₄. The parameters are normalized with respect to $\text{Re}A(322)$. $A(kq\lambda) = A_{kq}\Xi(k\lambda)$, where A_{kq} are crystal-field parameters and $\Xi(k\lambda)$ are parameters involving radial integrals.

	Real	Complex
$A(322)$	1	1 + $i0.16$
$A(324)$	0.45	0.46 + $i0.07$ ^a
$A(524)$	1.12	1.16 + $i0.36$
$A(526)$	0.02	0.00 + $i0.00$ ^a
$A(726)$	0.45	0.30 + $i0.24$
$A(766)$	-0.50	-0.55 - $i0.06$

^a Not allowed to vary freely.

obtained. The agreement was as good as when all the parameters were varied (σ was lowered to 0.9 due to the fewer variable parameters). That the imaginary parts of the A parameters have little influence on the intensities in the scheelite structure is in contrast to the conclusion of Minhas and Sharma.⁸

V. DISCUSSION

A. Energy levels

The difference between the experimental energy levels of Tm^{3+} in $LiTmF_4$ and in $LiYF_4$ (Ref. 3) are less than 20 cm^{-1} , which may partly be due to experimental inaccuracy. There is no systematic change in the crystal-field splittings of the multiplets when going from one host to the other. Thus there cannot be any substantial difference between the crystal-field potentials at the Ln site in these two crystals.

Jenssen *et al.*³ have calculated the energy levels of the ground configuration of Tm^{3+} in $LiYF_4$. They use a more complicated Hamiltonian than the one described in Sec. II A, but their agreement with the experimental levels is only slightly better than the agreement obtained in the present work. Refinements of the model do not have much influence on the splittings of the multiplets.

The crystal-field parameters for Tm^{3+} in $LiTmF_4$ are shown in Fig. 5 together with the parameters for Tb^{3+} , Ho^{3+} , and Er^{3+} in $LiLnF_4$.^{1,2} To indicate the variation through the series of Ln^{3+} ions, parabolas are drawn through the values for Tb^{3+} , Ho^{3+} , and Tm^{3+} . The values for Er^{3+} are not used in fixing these parabolas due to the difficulties in determining the parameters for this ion as described in Ref. 2. The points for Er^{3+} are, however, close to the parabolas. The values for Tb^{3+} , Ho^{3+} , and Er^{3+} are obtained by fitting to levels of the ground term only, whereas the values for Tm^{3+} are obtained by fitting to levels of the three lowest terms. The dependence of the parameters on the collection of levels to which they are fitted is, however, weak, if the levels under consideration possess correct wave functions (see Ref. 2).

Considering the uncertainties on the parameters, the parabolas should not be considered as more than a hint to the sizes of the parameters for the remaining ions. A further uncertainty is the possible temperature dependence of the parameters. Contrary to what was found for $LiTmF_4$, the parameters for $LiTbF_4$ (Ref. 1) were temperature dependent. (The values given for Tb^{3+} in Fig. 5 are for $T = 10\text{ K}$.)

If the extrapolated values for Eu^{3+} should turn out to be realistic, the crystal-field potential in $LiEuF_4$ would differ rather much from what is

found in other scheelites. Taken together with the observed temperature-dependent crystal field in $LiTbF_4$, one might speculate if the $LiLnF_4$ structure becomes increasingly unstable when going from $LiTmF_4$ to $LiEuF_4$ (in accordance with the

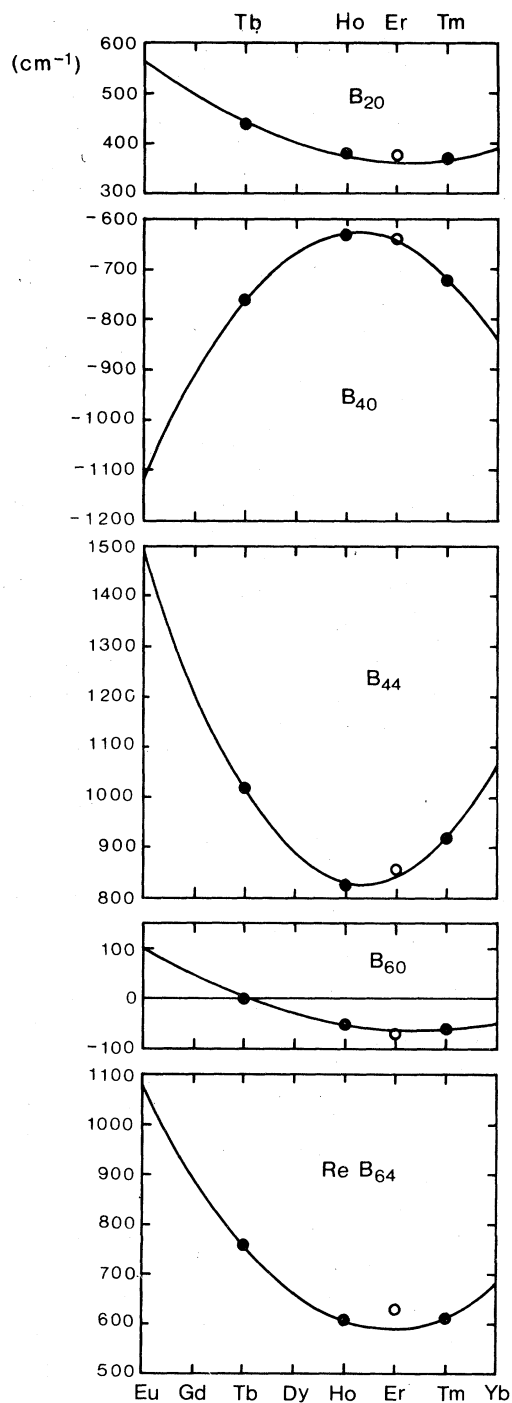


FIG. 5. Real crystal-field parameters at 10 K for Tb^{3+} , Ho^{3+} , Er^{3+} , and Tm^{3+} in $LiLnF_4$. Parabolas are drawn through the values for Tb^{3+} , Ho^{3+} , and Tm^{3+} .

circumstance that LiSmF₄ should not exist¹⁴). The spectra of LiEuF₄ would be interesting to investigate (LiGdF₄ have no transitions in the optical region), but we have not succeeded in growing crystals of LiEuF₄ by the method of spontaneous crystallization as described by Laursen and Holmes.¹⁵

Karayianis *et al.*¹⁶ give crystal-field parameters for Nd³⁺, Ho³⁺, Er³⁺, and Tm³⁺ in LiYF₄. The values for Ho³⁺ are in good agreement with those obtained in LiHoF₄. For Er³⁺ and Tm³⁺ the parameters differ up to 150 cm⁻¹. There are, however, no systematic change, so for the heavy Ln ions the crystal field does not seem to vary much from dense to diluted crystals; a statement in agreement with the conclusion for Tm³⁺ in the beginning of this section. Most of the parameters for Nd³⁺ follow the trends given by the parabolas in Fig. 2, but their numerical values are much smaller than extrapolations from the curves would give.

The calculated term composition of the wave functions showed—as could be predicted from Fig. 3—that multiplets with equal J quantum numbers were heavily mixed. The mixing of multiplets with different J values—which can take place only due to the crystal field—was very weak. This shows that it would be a good approximation to consider the crystal field as a perturbation within each multiplet, when the wave functions of these were determined. Since the wave functions of the ground multiplet of Tm³⁺ (due to the great distance to other multiplets with $J = 6$) are almost pure ³H, it should for this ion—in contrast to what was the case for Tb³⁺ (Ref. 1)—be a rather good approximation to do calculations only within the ground multiplet. The choice of basis set in a given situation may differ from one Ln ion to another because the relative strength of the three terms in Eq. (1) changes through the series of Lanthanides.

It must be emphasized that the wave functions belonging to a branch in the diagram of Fig. 3 outgoing from a given term do not necessarily maintain to be dominated by that term. The lowest multiplet with $J = 4$ originates from ³H, but the composition of the wave functions are for Tm³⁺ mostly ³F. Hence the multiplet could equally well be named ³H₄ or ³F₄.

B. Transition probabilities

The relative experimental intensities for Tm³⁺ in LiYF₄ (Ref. 3) differed somewhat from those

in LiTmF₄. Especially the strong transitions in the dense crystal were relatively weaker in the diluted crystal.

The intensity calculations gave only a rough estimate of the strength of the transitions. Except for a few lines the model was capable to point out the very strong and very weak lines. Even if the parameters were varied over a wide range, the model seldom failed in selecting strong and weak transitions. The intensity model was, however, not able to give quantitative good line intensities. The A parameters must only be considered as fitting parameters. As well as including the effect of configuration mixing due to the static crystal field, the parameters more or less include the effects of lattice vibrations.

As a minor point it should be mentioned that the intensity calculations indicated that the interpretation of the Γ_1 levels of the ³H₅ multiplet was somewhat ambiguous. The experimental π line at 8519 cm⁻¹ was interpreted as the Γ_1 line calculated to 8532 cm⁻¹. This line, however, had a very low calculated intensity, whereas the line calculated to 8555 cm⁻¹ had high intensity, and experimentally there was seen no π line with higher energy. If the experimental line at 8519 cm⁻¹ instead was interpreted as the 8555 cm⁻¹ line, it was possible to obtain an energy fit with an s of 14 cm⁻¹. However, when the modification did not improve the energy fit, it is unsafe to make a line assignment on the basis of the intensity calculations.

The theoretical intensities calculated by Wortman *et al.*¹³ for Tm³⁺ in LiYF₄ were not in agreement with the intensities for Tm³⁺ in LiTmF₄. Especially (and in contrast to the calculations reported here) the agreement was bad for σ transitions. Nor were the theoretical results in agreement with the experimental intensities for Tm³⁺ in LiYF₄,³ although the disagreement for σ polarization was less than when compared to the results for the dense crystal.

ACKNOWLEDGMENTS

The author is very grateful to Dr. R. Nevald and Professor V. Frank for helpful suggestions and discussions during the preparation of the manuscript.

- ¹H. P. Christensen, Phys. Rev. B 17, 4060 (1978).
²H. P. Christensen, Phys. Rev. B 19, 6564 (1979).
³H. P. Jenssen, A. Linz, R. P. Leavitt, C. A. Morrison, and D. E. Wortman, Phys. Rev. B 11, 92 (1975).
⁴G. H. Dieke, *Spectra and Energy Levels of Rare-Earth Ions in Crystals* (Wiley, New York, 1969).
⁵G. F. Koster, J. O. Dimmock, R. G. Wheeler, and H. Statz, *Properties of the Thirty-Two Point Groups* (MIT, Cambridge, Mass., 1963).
⁶B. R. Judd, Phys. Rev. 127, 750 (1962).
⁷G. S. Ofelt, J. Chem. Phys. 37, 511 (1962).
⁸I. S. Minhas and Kailash K. Sharma, Phys. Rev. B 14, 4124 (1976).
⁹H. P. Christensen, J. Phys. E 11, 742 (1978).
¹⁰S. A. Miller, H. E. Rost, and H. H. Caspers, J. Chem. Phys. 52, 4172 (1970).
¹¹B. G. Wyborne, *Spectroscopic Properties of the Rare Earth* (Interscience, New York, 1965).
¹²C. A. Morrison, N. Karayianis, and D. E. Wortman, Harry Diamond Laboratories Report No. TR-1816, 1977 (unpublished).
¹³D. E. Wortman, N. Karayianis, and C. A. Morrison, Harry Diamond Laboratories Report No. TR-1770, 1976 (unpublished).
¹⁴R. E. Thoma, G. D. Brunton, R. A. Penneman, and T. K. Keenan, Inorg. Chem. 9, 1096 (1970).
¹⁵I. Laursen and L. M. Holmes, J. Phys. C 7, 3765 (1974).
¹⁶N. Karayianis, D. E. Wortman, and H. P. Jenssen, J. Phys. Chem. Solids 47, 675 (1976).