

Novel Ultrathin Molecular Coating for Injection Molding Tools

Cech, Jiri; Taboryski, Rafael J.

Publication date:
2012

Document Version
Publisher's PDF, also known as Version of record

[Link back to DTU Orbit](#)

Citation (APA):

Cech, J., & Taboryski, R. J. (2012). Novel Ultrathin Molecular Coating for Injection Molding Tools. Poster session presented at The Pittsburgh Conference on Analytical Chemistry and Applied Spectroscopy Inc., Orlando, FL, United States.

DTU Library

Technical Information Center of Denmark

General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

Novel Ultrathin Molecular Coating for Injection Molding Tools

Jiri Cech, Rafael J. Taboryski

Motivation

Injection molding industry often employs **prototype molds** and mold inserts fabricated from Rapid Solidified Aluminum (RSA), specially for cutting edge mold applications in where quality is paramount, namely optics, photonics and microfluidics. Prototypes are also used for verification of mold filling.

Aluminum molds have substantially reduced lead time (days instead of weeks), lower manufacturing cost (30%) and excellent surface finish. Surface roughness (RMS) is often below 5 nm after diamond machining. Conventional coating with thickness of few microns may ruin small features.

We proposed perfluorinated trichloro-silane (FDTS) coating, realized it and tested stability in challenging conditions of injection molding, up to 200MPa and 250°C.

Method

FDTS monolayer coating was deposited in commercial MVD 100 system from Applied Microstructures using relevant multilayer recipe in presence water vapor at approximately 50°C.

Samples have been characterized by XPS and by Sessile Drop shape analysis on at least 3 locations of each sample at least 10 mm apart to account for possible surface heterogeneity.

Wear stability testing

- **Pristine** (uncoated control sample)
- **Coated** (fresh FDTS coating)
- **Post Injection molding** (500+ IM cycles with polystyrene (PS) and proprietary yellow ABS material)

Temporal stability testing

More than 7 months at ambient conditions prior to testing of post IM.

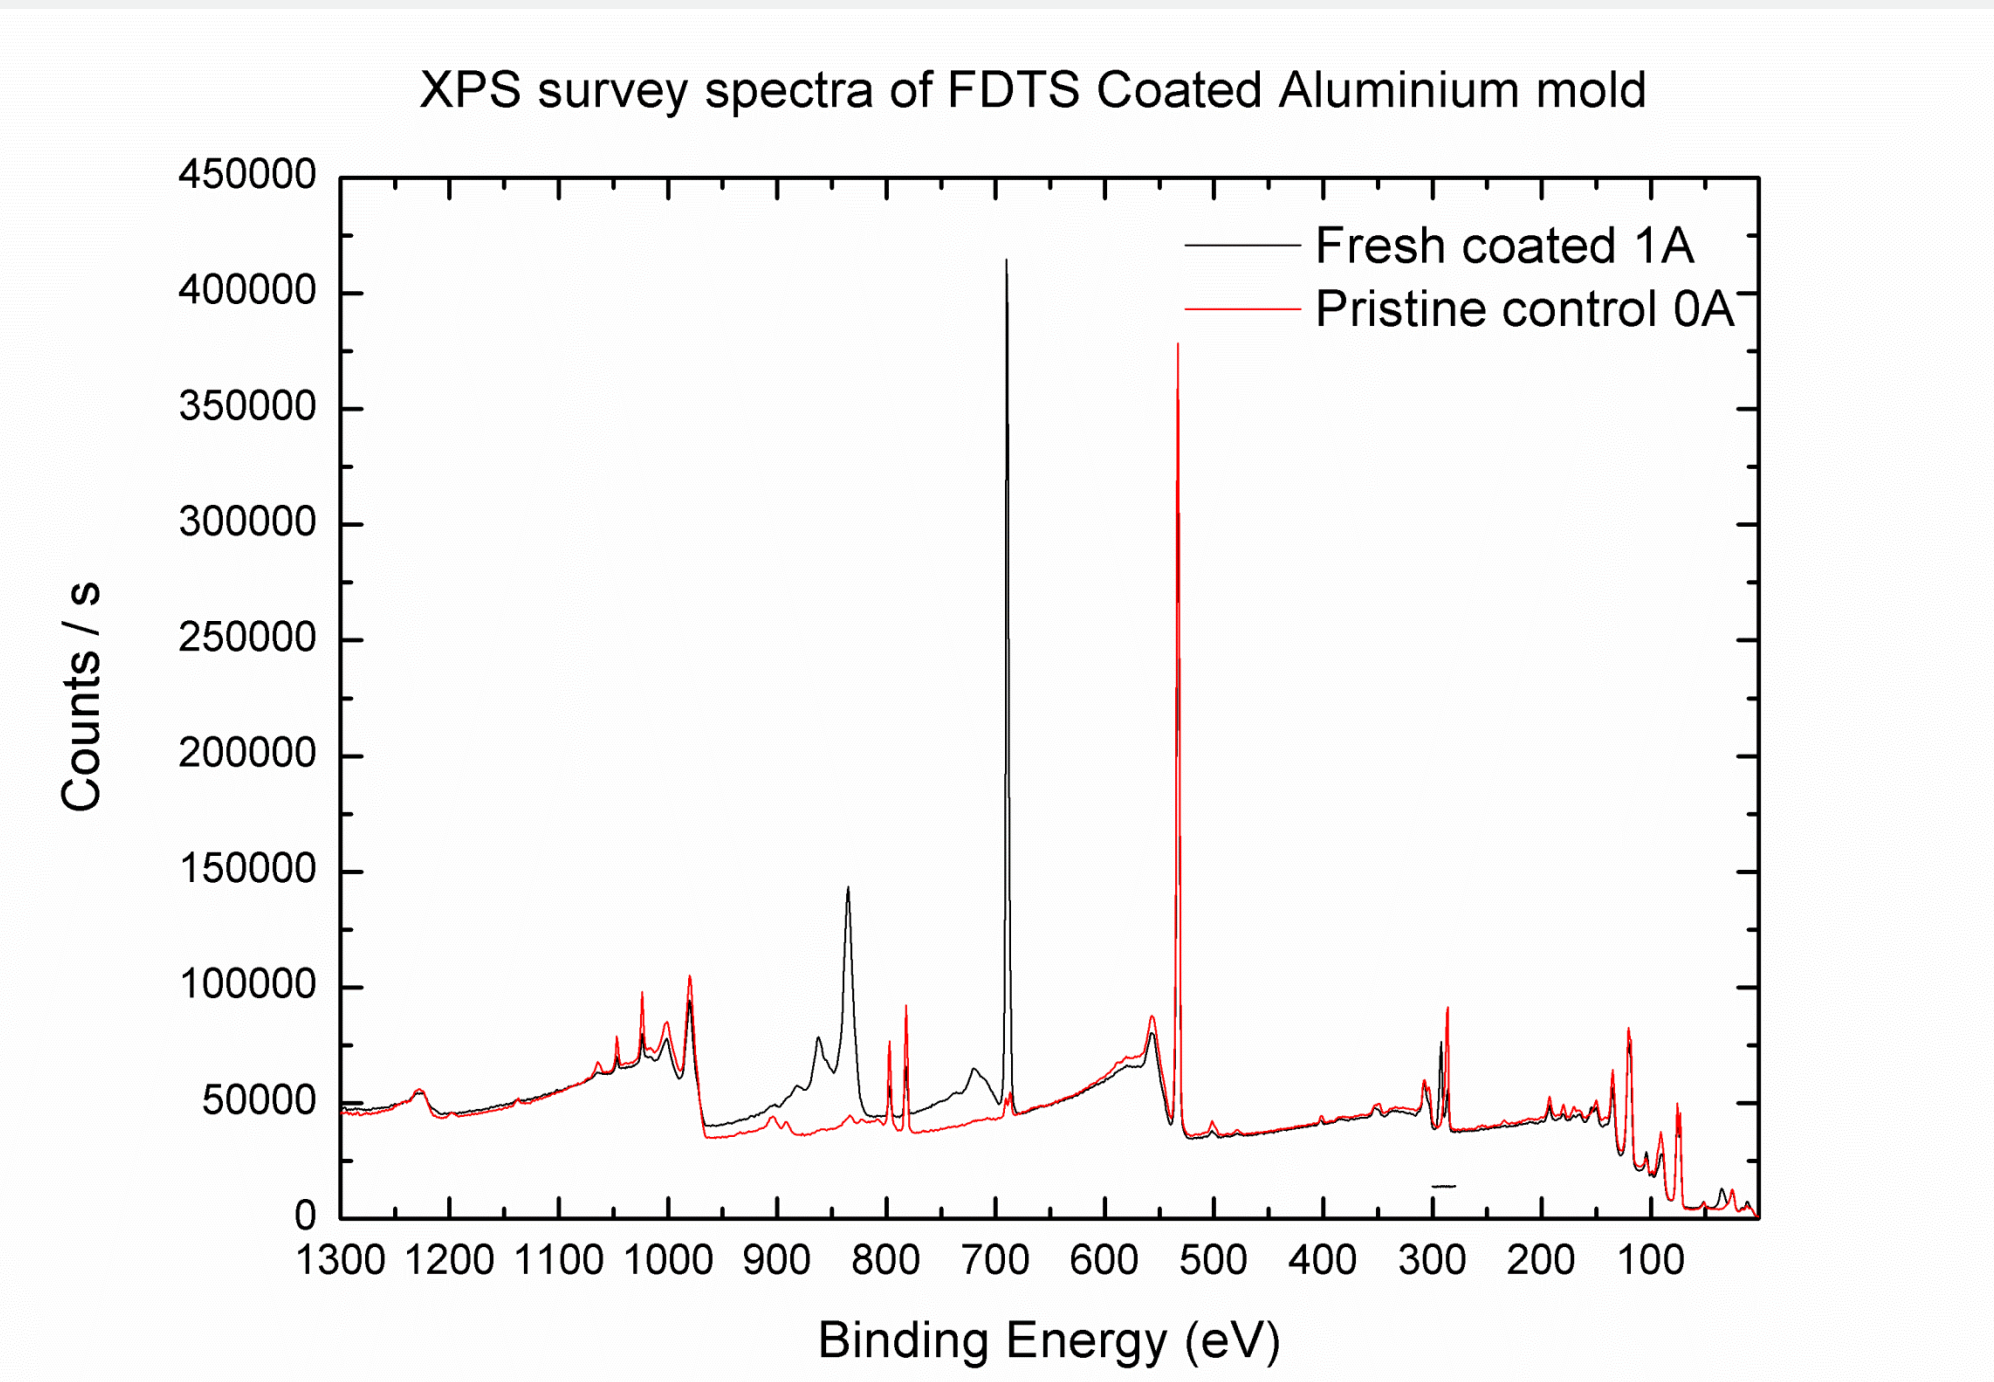


Figure 1. XPS Survey spectra shows distinct F1s peak near 690 eV.

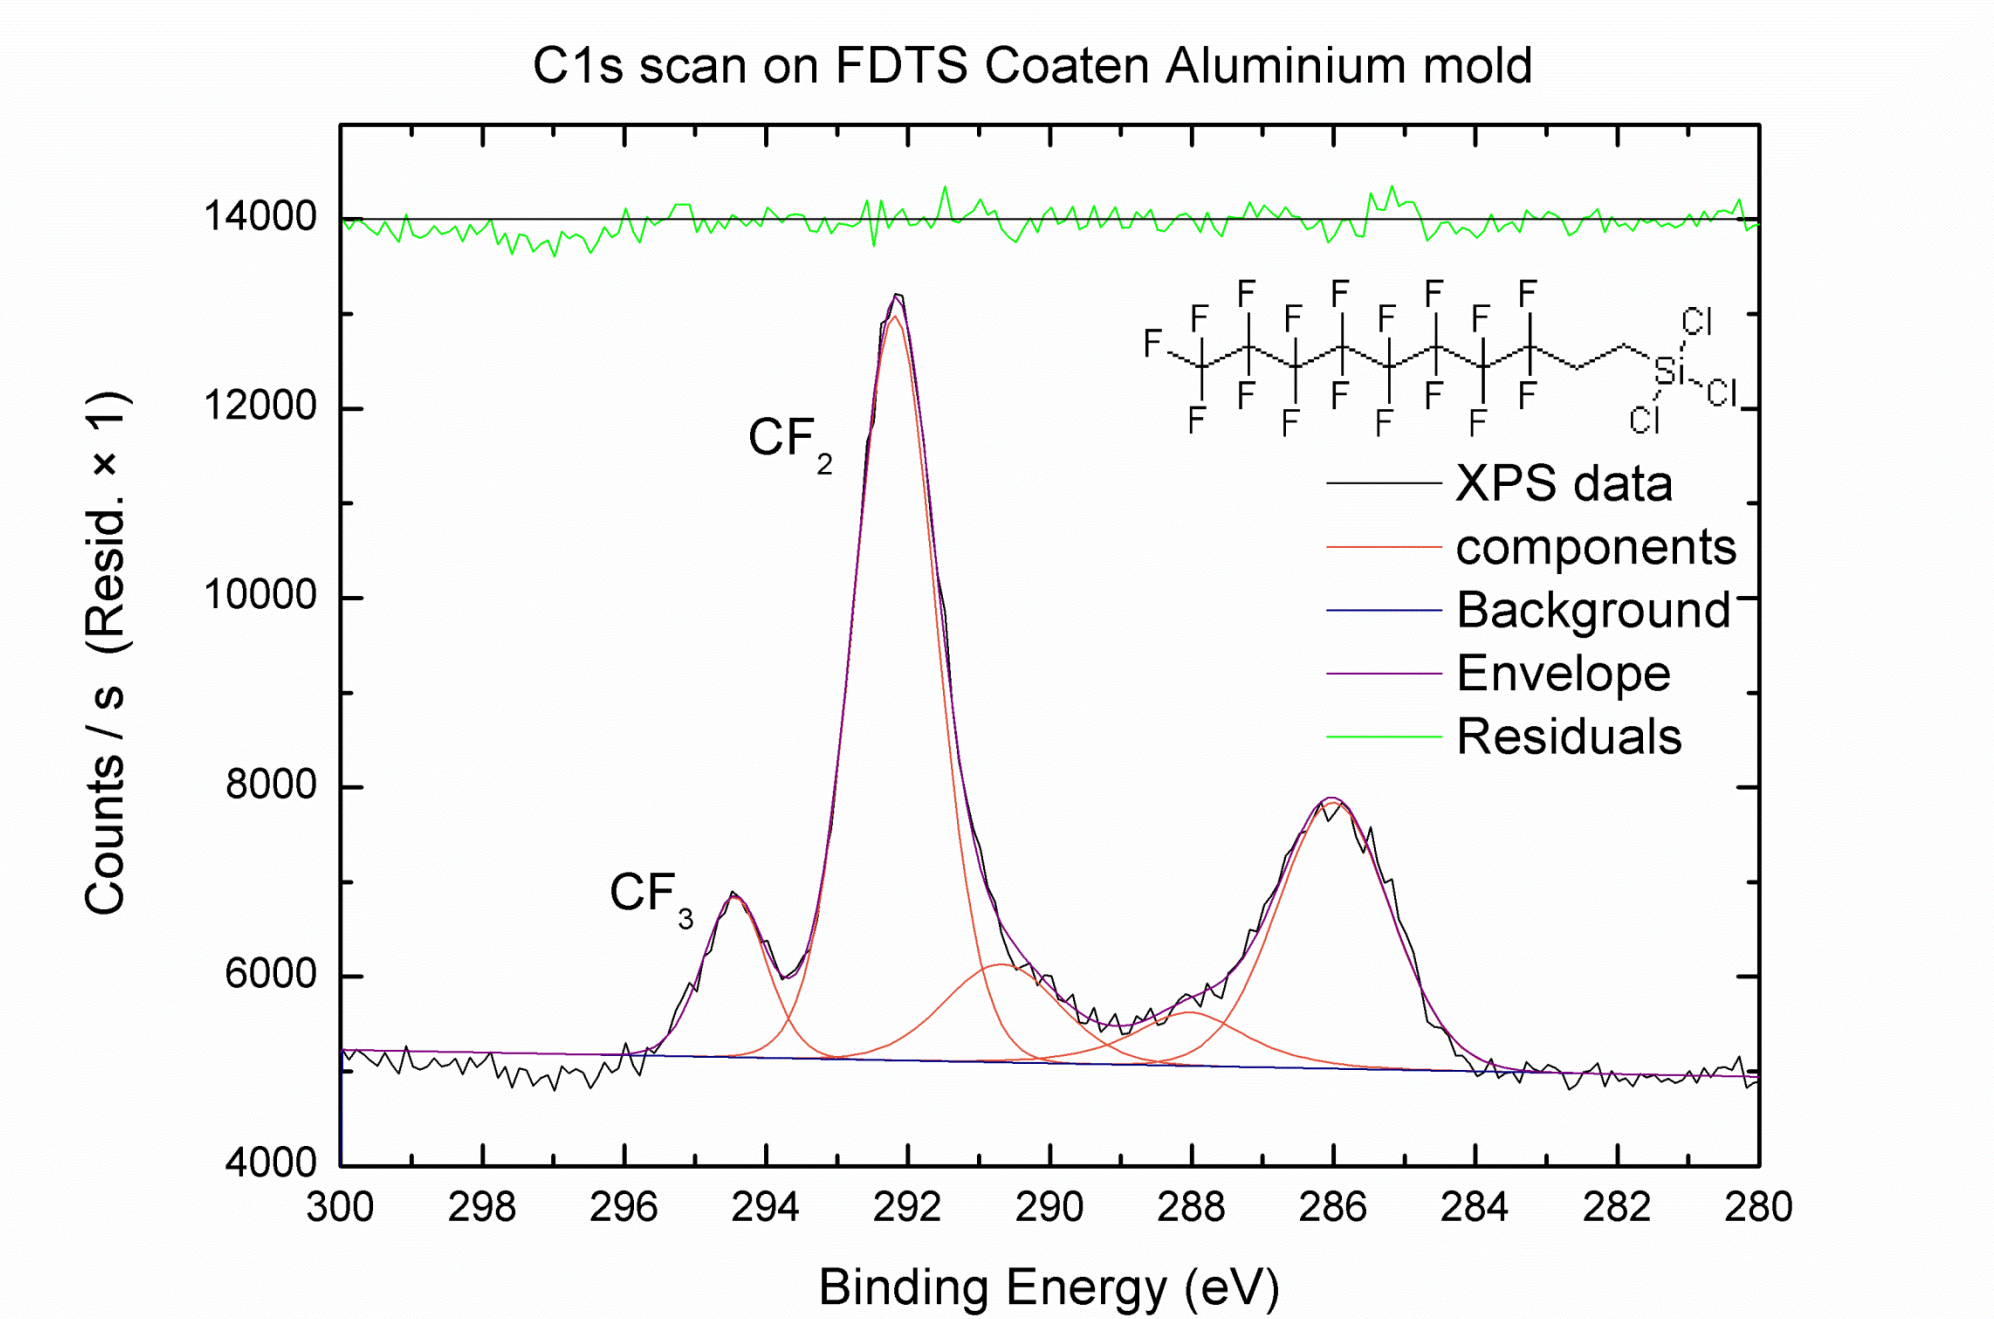


Figure 2. C1s spectrum, where the ratio of peaks corresponding to CF₂ to CF₃ is 6.89. This serves as a specific fingerprint of FDTS coating presence. Structure of a FDTS molecule is shown as insert.

Name	Peak BE	FWHM eV	At. %
O1s	531.04	3.34	44.6
Al2p	72.32	5.11	34.19
C1s	284.44	3.17	19.44
F1s	685.07	3.83	1.77

Name	Peak BE	FWHM eV	At. %
O1s	533.14	3.21	31.62
Al2p	75.54	5.09	26.78
C1s	292.17	2.72	11.78
F1s	689.76	2.95	29.82

Name	Peak BE	FWHM eV	At. %
O1s	534.01	3.23	29.25
Al2p	75.88	4.76	19.13
C1s	287.17	2.98	24.03
F1s	690.77	2.56	27.59

Tables 1-3. Pristine, Coated and Post IM surfaces (top to bottom).

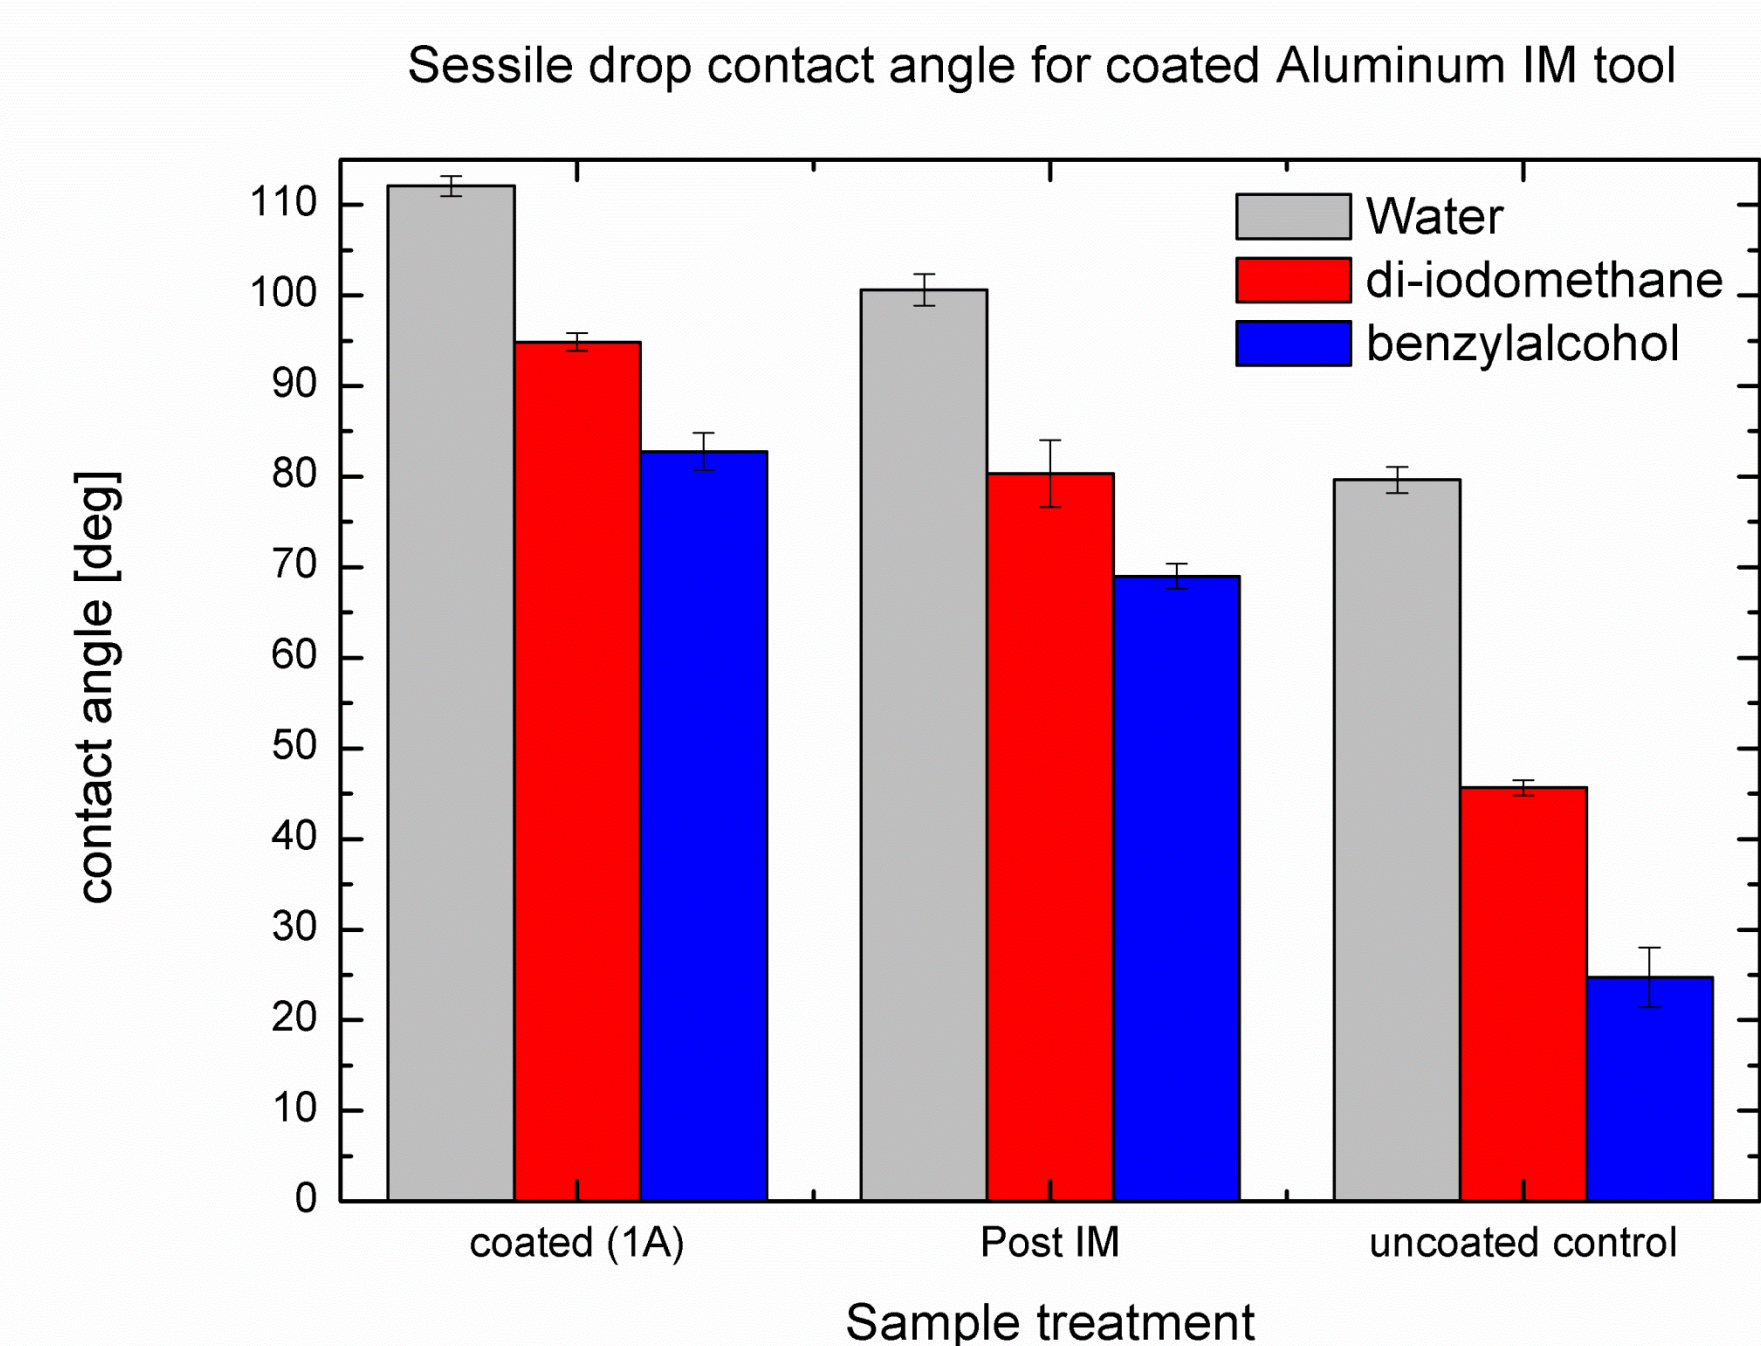


Figure 3. Contact Angle measurement results for different surface treatment and fluids.

Conclusion

XPS spectral survey data confidently shows presence of Fluorine in both coated and post IM samples and Carbon 1s spectra identify coating to be expected molecule. Covalently bonded coating molecules do prevail injection molding.

Surface energy is reduced 3 times by presented coating and this modification prevails over harsh IM cycling with enormous pressure and temperature loading. Temporal stability is excellent as well.

Predicted coating lifetime is at least 7700 shots and we expect much higher number. Deposition from gas phase is uncomplicated and affordable, suitable for prototype mold manufacturing workshops. Mold can be easily striped and re-coated if needed. This coating which is ultrathin, covalently bonded monolayer is reasonably durable, affordable, scalable to production and detectable on surface. It is especially suitable for rapid mold prototyping and mold geometry testing.

Presented result is commercially relevant, therefore nationally & internationally protected. It is available for licensing. Feel free to contact author for details.

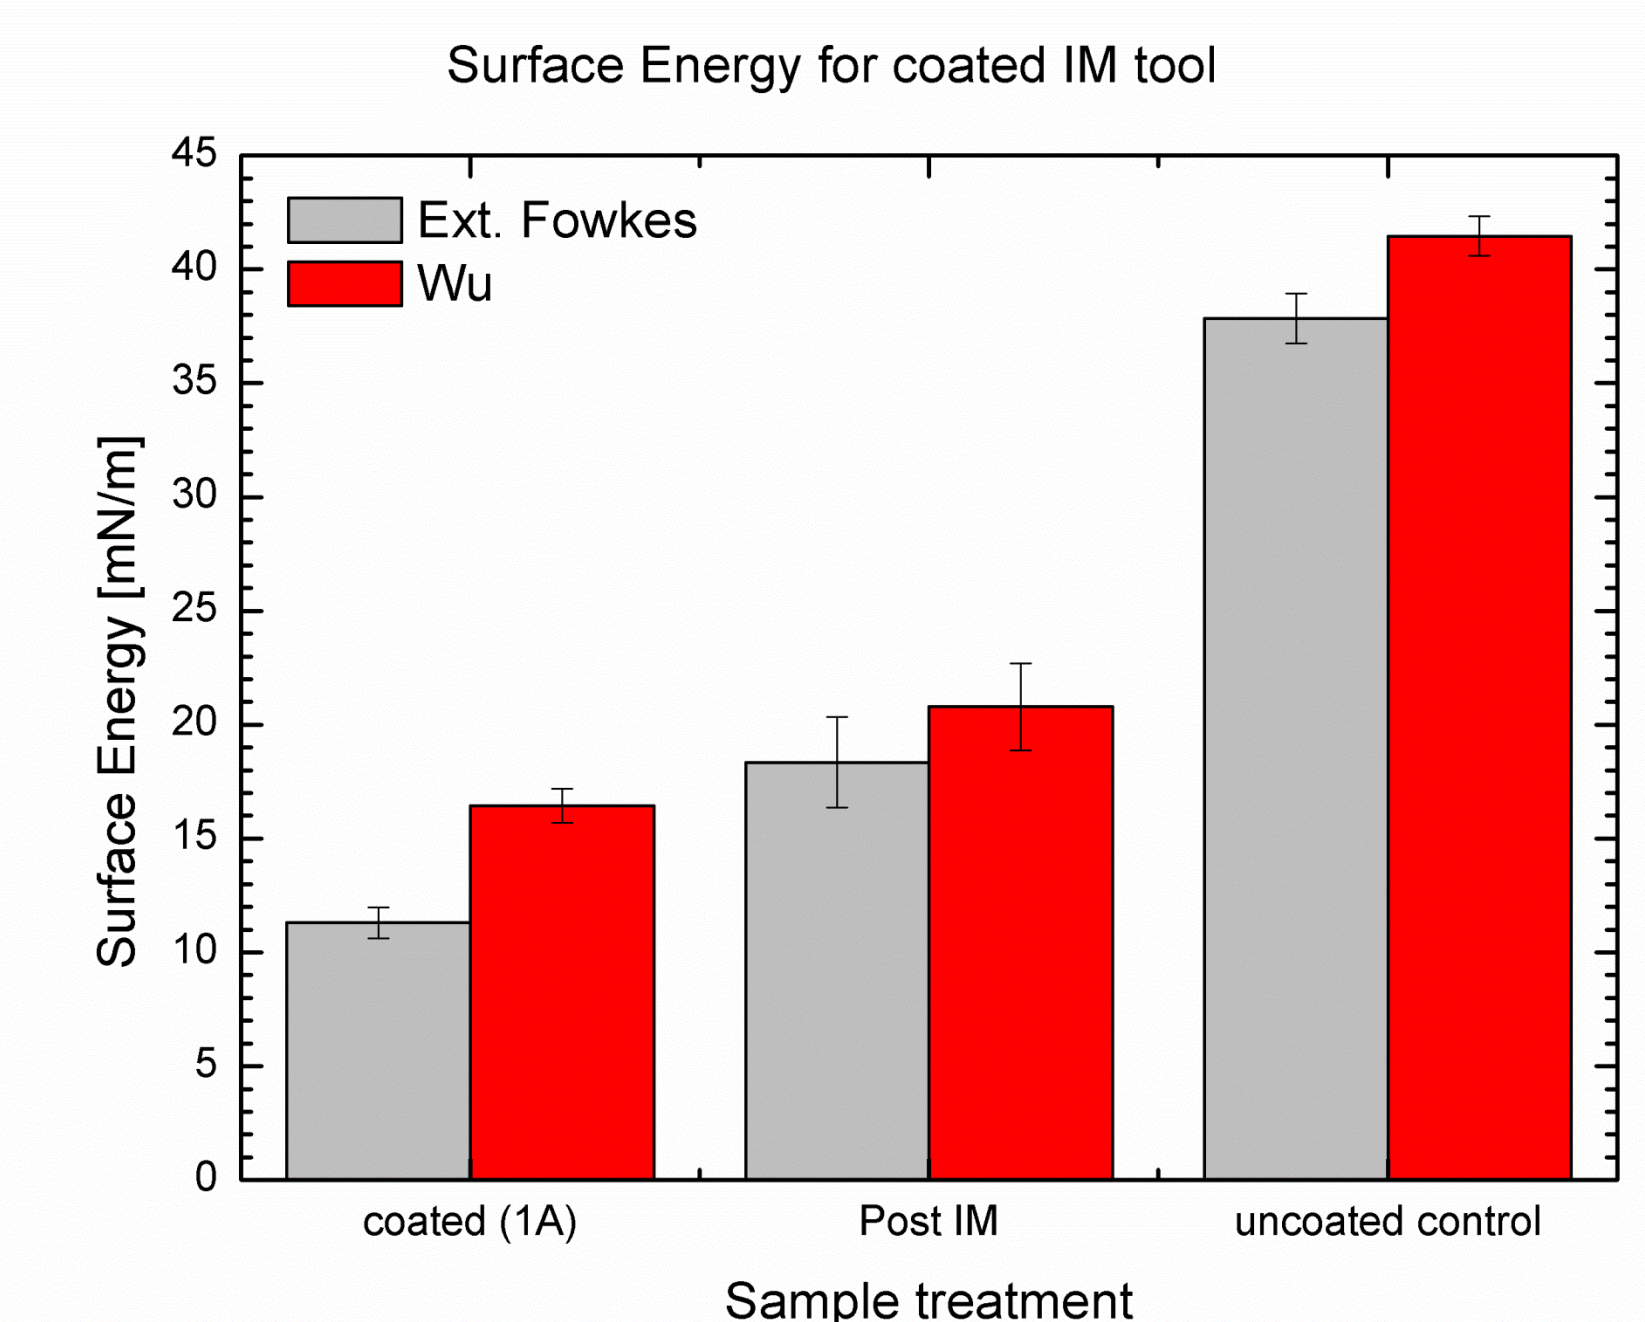


Figure 4. Aluminum Mold Surface Energy decreases ~3 times and stays decreased even after injection molding as shown above, where SE was calculated using different methods.

