

Technical University of Denmark



## Fiber Drawn 2D Polymeric Photonic Crystal THz Filters

**Stecher, Matthias; Jansen, Christian; Ahmadi-Boroujeni, Mehdi; Lwin, Richard; Stefani, Alessio ; Bang, Ole; Koch, Martin; Town, Graham**

*Published in:*  
CLEO Technical Digest

*Publication date:*  
2012

*Document Version*  
Publisher's PDF, also known as Version of record

[Link back to DTU Orbit](#)

*Citation (APA):*  
Stecher, M., Jansen, C., Ahmadi-Boroujeni, M., Lwin, R., Stefani, A., Bang, O., ... Town, G. (2012). Fiber Drawn 2D Polymeric Photonic Crystal THz Filters. In CLEO Technical Digest (pp. CM4J.2). Optical Society of America.

## DTU Library

Technical Information Center of Denmark

---

### General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

# Fiber Drawn 2D Polymeric Photonic Crystal THz Filters

Matthias Stecher,<sup>1,4</sup> Christian Jansen,<sup>1</sup> Mehdi Ahmadi-Boroujeni,<sup>1</sup> Richard Lwin,<sup>2</sup> Alessio Stefani,<sup>3</sup> Ole Bang,<sup>3</sup> Martin Koch,<sup>1</sup> and Graham Town<sup>4</sup>

1. AG Experimentelle Halbleiterphysik, Philipps-Universität Marburg, 35042 Marburg, Germany

2. Institute of Photonics and Optical Science (IPOS), School of Physics, A28 The University of Sydney, NSW 2006, Australia

3. DTU Fotonik, Department of Photonics Engineering, 2800 Kgs. Lyngby, Denmark

4. Department of Electronic Engineering, Macquarie University, NSW 2109, Australia.

Matthias.stecher@physik.uni-marburg.de

**Abstract:** In this paper, we report on different polymeric 2D photonic crystal filters for THz frequencies which are fabricated by a standard fiber drawing technique. The bandstop filters were simulated and designed by the generalized multipole technique (GMT). The frequency and angle dependent transmission characteristics of the photonic crystal structures were characterized in a pulsed terahertz (THz) time domain spectrometer.

**OCIS codes:** (000.0000) General; (000.0000) General

## 1. Introduction

Even though THz science and technology have been growing over the last 20 years, the lack of available passive components is one of the reasons that industrial and commercial THz systems are just emerging [1]. Especially frequency selective components like Bragg gratings and filters are necessary to realize cheap and versatile sensing systems for industrial applications. Typical filter concepts for the terahertz regime are close adaptations from either the optical or millimeter domain. The concepts from the RF field comprise metallic mesh designs and frequency selective surfaces, e.g. based on metamaterials [2]. Photonic crystal structures are the most promising optical concept for realizing THz filters. They have been fabricated by photo lithography [3], deep reactive-ion etching [4], laser based micromachining [5] or micro assembly [6].

In this paper we report on a fast and cheap method to fabricate scalable polymer based THz filters with mass production capability. First fabrication runs were performed in polycarbonate (PC) and in the Cyclic Olefin Copolymer (COC) TOPAS, which has low loss in the THz frequency regime [7]. The structures were simulated by a customized algorithm based on the Generalized Multipole Technique (GMT) [8]. A tube like preform (6 cm outer diameter (OD), 4.3 cm inner diameter (ID)) was loaded with several hundreds of small tubes (1 mm OD, 0.745 mm ID) and then drawn down in a standard fiber drawing tower (cf. Fig.1b). This provides a sufficient numbers of periods and a pronounced dip in transmission.

## 2. Results

The simulation result for a triangular lattice structure in polycarbonate (cf. Fig. 1a) with air hole diameter  $D_h = 260 \mu\text{m}$  and a pitch of  $D = 370 \mu\text{m}$  performed with the GMT is shown in Figure 1c. The simulations take the frequency dependent dielectric loss of the material into account. The solid and dotted line show the band diagrams for the first two horizontally polarized modes. For a fixed hole-diameter-to-pitch ratio of 0.745, the center stop band frequency versus the spacing of the holes is calculated.

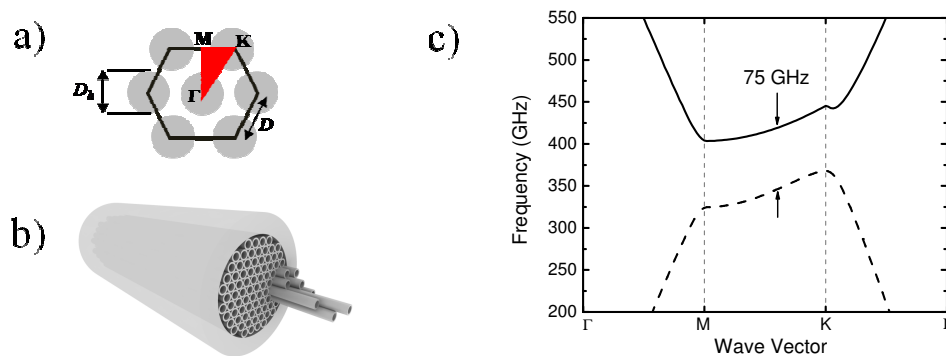


Fig. 1. a) The triangular photonic crystal structure b) Schematic of a stacked preform c) Band gap diagram for a polycarbonate 2D photonic crystal with  $370 \mu\text{m}$  hole spacing (hole diameter-to-pitch ( $D_h/D$ ) of 0.745).

To access feature sizes of 200  $\mu\text{m}$  and below a standard fiber drawing technique is used. Stacked tubes in a cylindrical preform are utilized to achieve the desired number of periods within the filter and to guarantee the optimal hole-diameter-to-pitch ratio. The pull ratio determines the final filter dimensions and therefore the resulting frequency characteristics. Thus, it is now possible to access a very broad range of frequencies, typically from three digit GHz frequencies up to several THz. The interstitial holes were closed by applying low pressure.

A standard THz time domain spectrometer with a bandwidth of more than 4 THz was used to analyze the polymer photonic crystal filters of approximately 1 cm length. The transmission spectrum of a polycarbonate filter with a hole spacing of 375  $\mu\text{m}$  and a TOPAS filter with a hole spacing of 55  $\mu\text{m}$  are shown in Figure 2a and b.

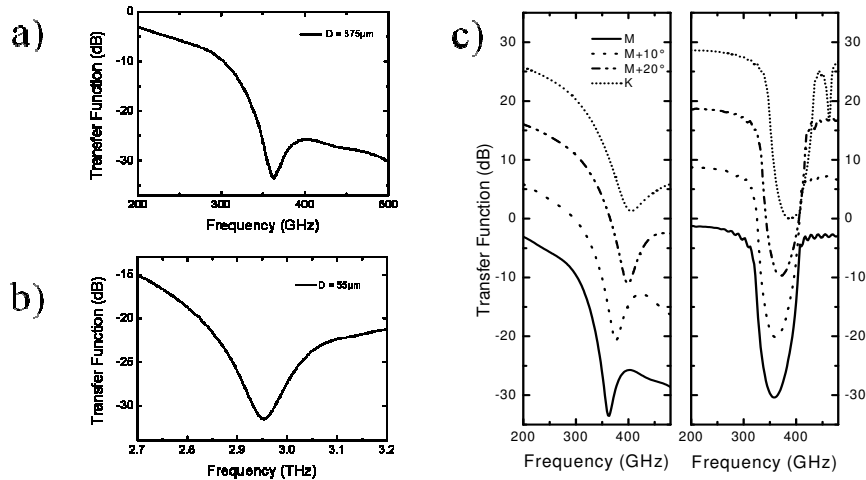


Fig. 2. Measured transfer function for a polycarbonate filter with (a) and a TOPAS filter with  $D = 55 \mu\text{m}$  (b). On the right hand side are measured and GMT simulated relative transmittance (c) at varying incident angles for a polycarbonate THz filter with a hole spacing of  $D = 375 \mu\text{m}$ . For clarity, the graphs are offset by 10 dB/10° with respect to the 0°-curve.

Placing the polycarbonate filter on a rotatable mount the angle dependent frequency characteristics have been investigated. A series of measurements from 0° (M-point) to 30° (K-point) in 10° steps confirm the predictions of the GMT simulations. In Figure 2c, the measured data is shown next to the simulation results (cf. right side of Figure 2c). The expected blue shift of the resonance frequency was observed for increasing angles of incidence

### 3. Conclusion

We present a first proof-of-concept experimental demonstration of polymeric 2D photonic crystal THz filters, fabricated by a standard fiber drawing technique. Angle and frequency dependent transmission measurements were performed in a pulsed THz time domain spectrometer confirming that the resonance frequency of the filter can be shifted by rotating the filter with respect to the incoming THz wave. The fabrication method relies on standard fiber drawing techniques and can therefore easily be used for mass production. Furthermore, adjusting the scaling factor enables the free scalability of the targeted resonance frequency using a single preform design.

The authors acknowledge technical support and use of equipment at University of Sydney founded through NCRIS and DTU Fotonik for their support and assistance in fabricating devices made out of TOPAS.

### 4. References

- [1] C. Jansen, S. Wietzke, O. Peters, M. Scheller, N. Vieweg, M. Salhi, N. Krumbholz, C. Jördens, T. Hochrein, and M. Koch, "Terahertz imaging: applications and perspectives," *Appl. Opt.*, vol. 49, pp. E48-E57, 2010.
- [2] C. Jansen, I. A. I. Al-Naib, N. Born, and M. Koch, "Terahertz metasurfaces with high Q-factors," *Applied Physics Letters*, vol. 98, pp. 051109-051109-3, 2011.
- [3] A. Bingham, Y. Zhao, and D. Grischkowsky, *THz parallel plate photonic waveguides* vol. 87: AIP, 2005.
- [4] N. Jukam and M. S. Sherwin, *Two-dimensional terahertz photonic crystals fabricated by deep reactive ion etching in Si* vol. 83: AIP, 2003.
- [5] E. Özbay, G. Tuttle, J. S. McCalmont, M. Sigalas, R. Biswas, C. M. Soukoulis, and K. M. Ho, *Laser/micromachined millimeter/wave photonic band/gap cavity structures* vol. 67: AIP, 1995.
- [6] S.-Y. Lin, V. M. Hietala, L. Wang, and E. D. Jones, "Highly dispersive photonic band-gap prism," *Opt. Lett.*, vol. 21, pp. 1771-1773, 1996.
- [7] K. Nielsen, H. K. Rasmussen, A. J. Adam, P. C. Planken, O. Bang, and P. U. Jepsen, "Bendable, low-loss Topas fibers for the terahertz frequency range," *Opt. Express*, vol. 17, pp. 8592-8601, 2009.
- [8] A. C. Ludwig, "The generalized multipole technique," *Computer Physics Communications*, vol. 68, pp. 306-314, 1991.