

Technical University of Denmark



Fundamental insight in soot oxidation over a Ag/Co₃O₄ catalyst by means of Environmental TEM

Gardini, Diego; Christiansen, J. M.; Jensen, Anker Degn; Damsgaard, Christian Danvad; Wagner, Jakob Birkedal

Publication date:
2013

Document Version
Publisher's PDF, also known as Version of record

[Link back to DTU Orbit](#)

Citation (APA):
Gardini, D., Christiansen, J. M., Jensen, A. D., Damsgaard, C. D., & Wagner, J. B. (2013). Fundamental insight in soot oxidation over a Ag/Co₃O₄ catalyst by means of Environmental TEM. Poster session presented at Scandem 2013 - Annual Meeting of the Nordic Microscopy Society, Copenhagen, Denmark.

DTU Library

Technical Information Center of Denmark

General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

Fundamental insight in soot oxidation over a $\text{Ag}/\text{Co}_3\text{O}_4$ catalyst by means of Environmental TEM

D. Gardini¹, J. M. Christiansen², A. Degn², C. D. Damsgaard^{1,3}, J. B. Wagner¹

¹ Center for Electron Nanoscopy, Technical University of Denmark, DK-2800 Lyngby, Denmark


² Department of Chemical and Biochemical Engineering, Technical University of Denmark, DK-2800 Lyngby, Denmark

³ CINF, Department of Physics, Technical University of Denmark, DK-2800 Lyngby, Denmark

Motivation: Soot emitted from diesel engine as typical solid particles has caused acute health problems to human beings. In modern vehicles, soot filters need to be regenerated periodically through a catalyzed high temperature oxidation process involving an extra fuel consumption. A dream catalyst would oxidize soot at a very low ignition temperature T_{ig} , ideally the temperature of the exhaust gas itself ($T_{ig} < 250\text{ }^\circ\text{C}$).

Choice of the materials:

Soot oxidation is a gas/solid/solid interaction. When catalyst and soot are crushed together (tight contact) the oxidation occurs at lower temperature, than when the two are stirred together with a spatula (loose contact).

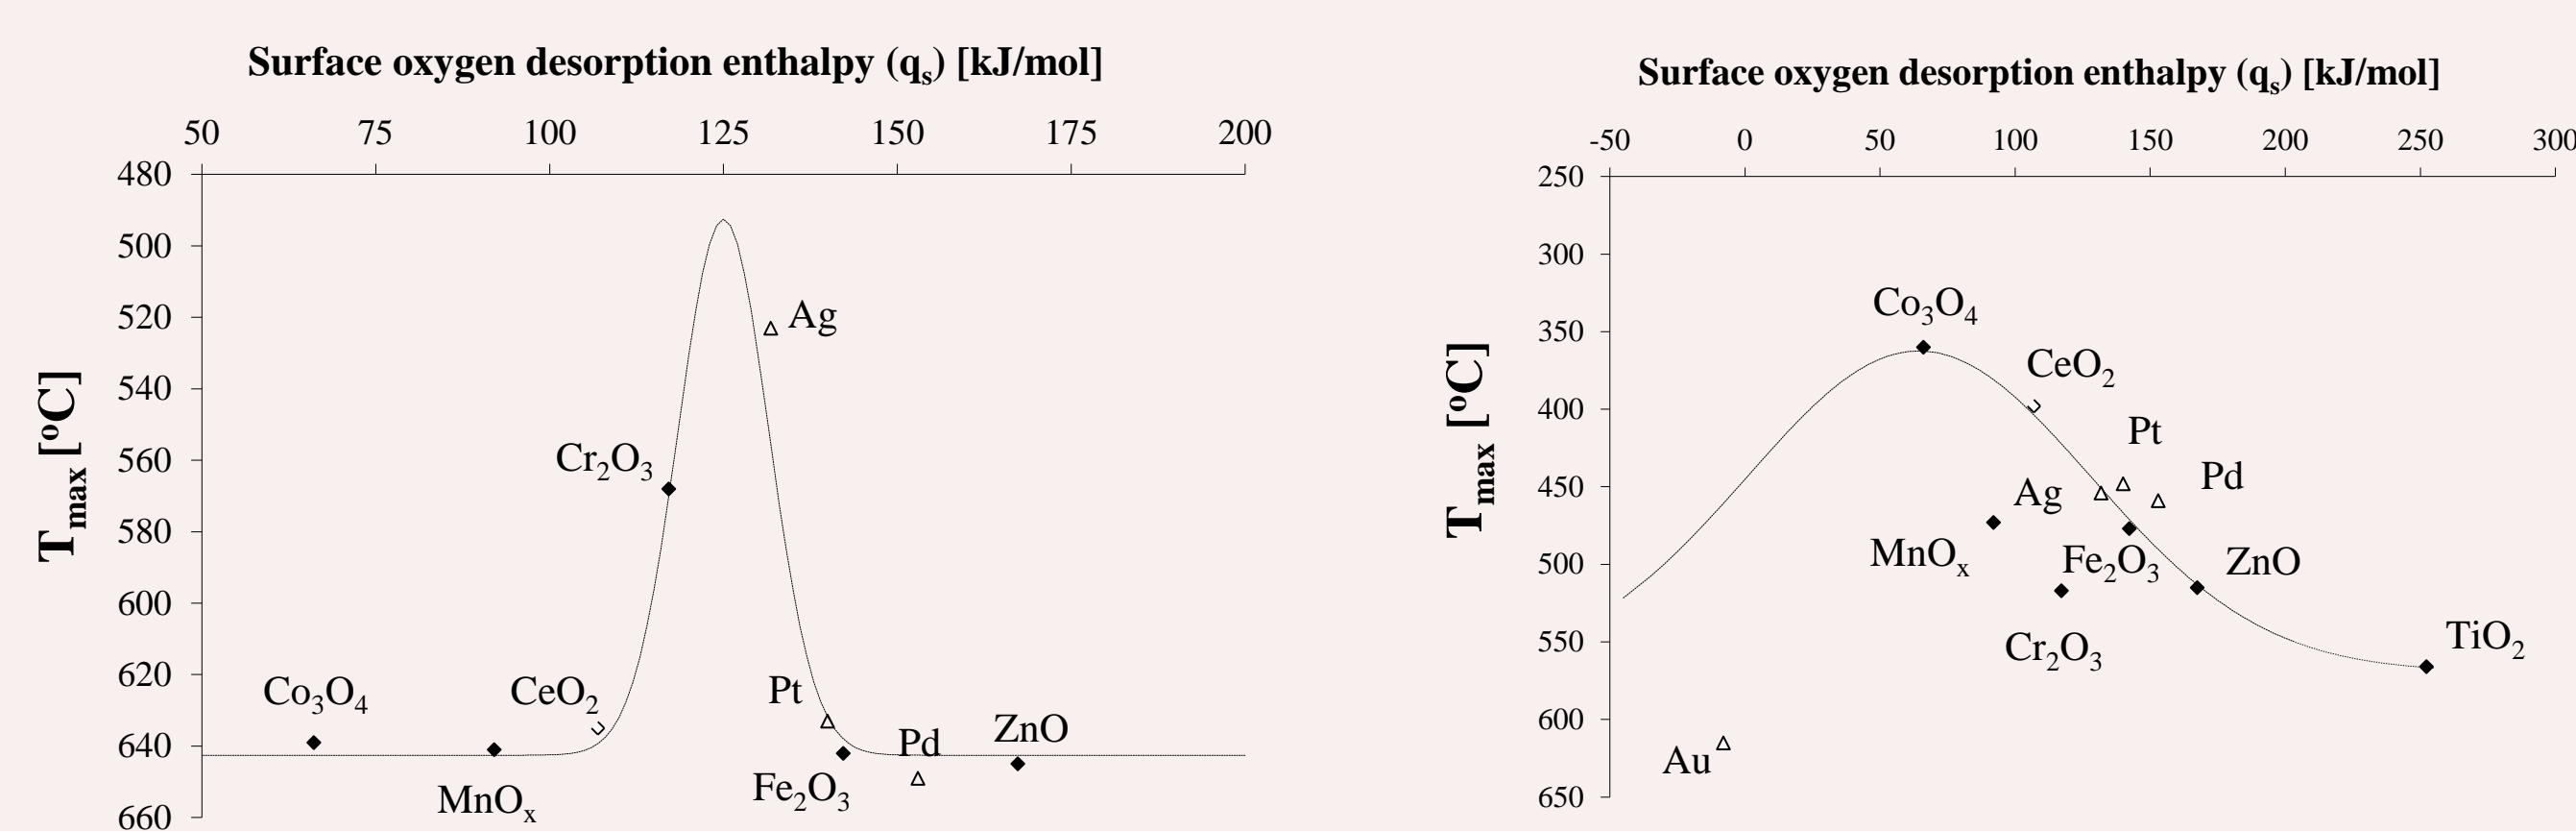


Catalytic test of $\text{Ag}/\text{Co}_3\text{O}_4$, Ag and Co_3O_4 :

Temperature programmed oxidation (TPO) in a flow reactor setup.

10-18 mg soot/catalyst mixture (ratio: 1/5 Wt/Wt).


1 NL/min flow of 10 vol% O_2 in N_2 . 100 to 750 $^\circ\text{C}$ at a rate 11 $^\circ\text{C}/\text{min}$.

CO and CO_2 concentrations in the effluent gas are measured with an ABB AO2020 continuous IR gas analyzer.

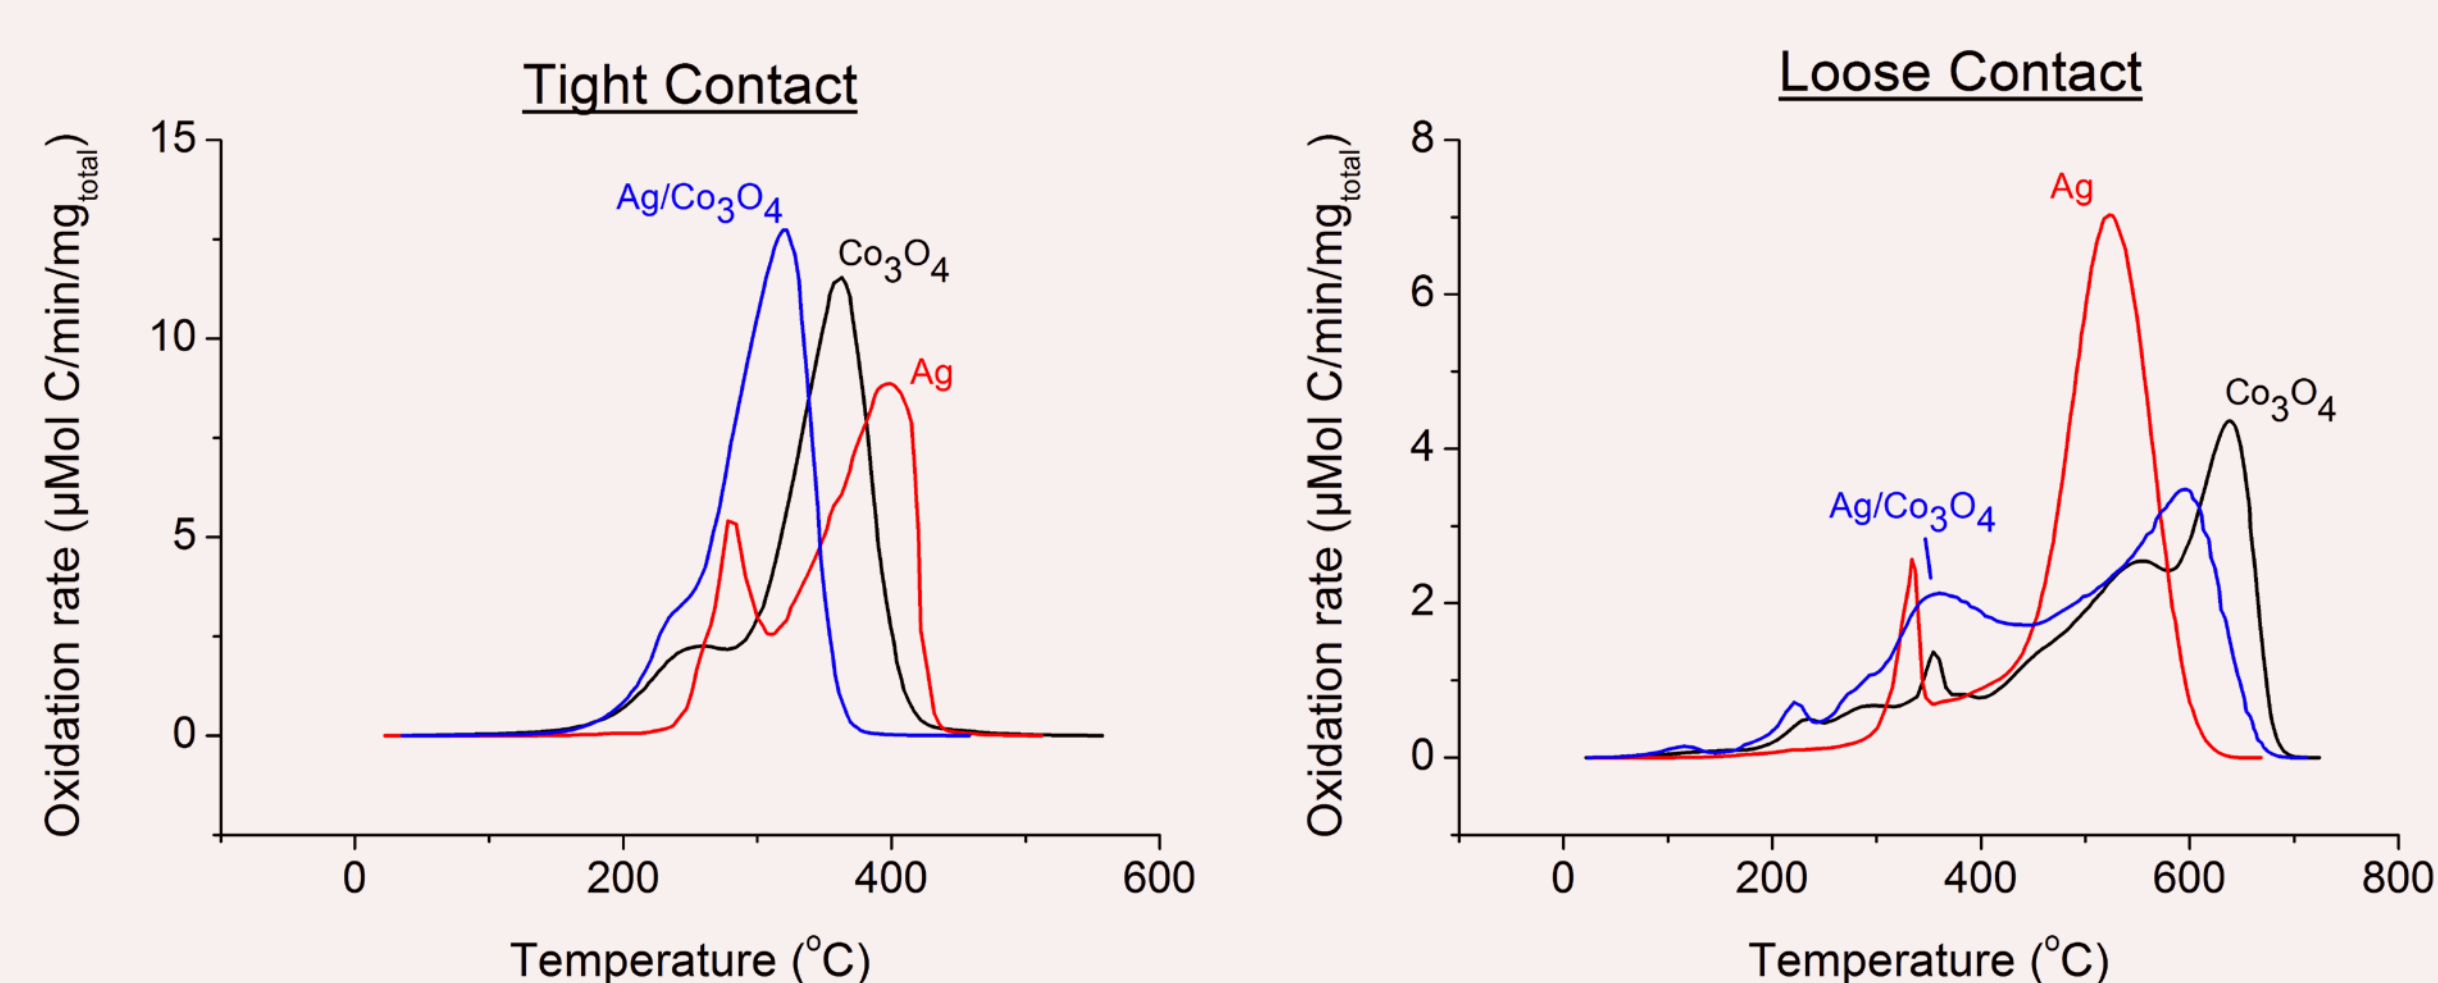


→ Performance of cosupported catalyst cannot be directly described in terms of the activity of the single Ag and Co_3O_4 components


Ex situ TEM analysis: TPO snapshots of Ag/soot system.

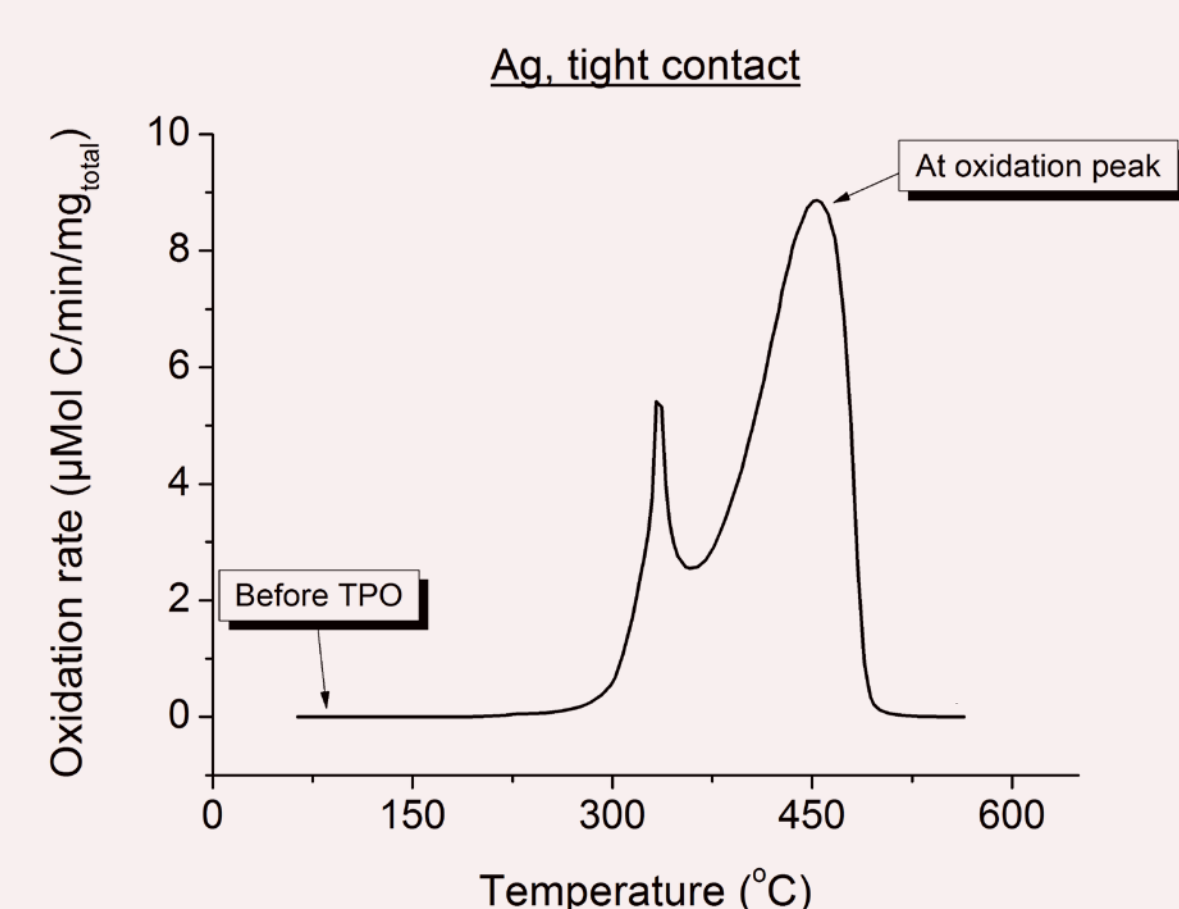

- Tapering of agglomerate's borders at oxidation peak
- Soot consumption

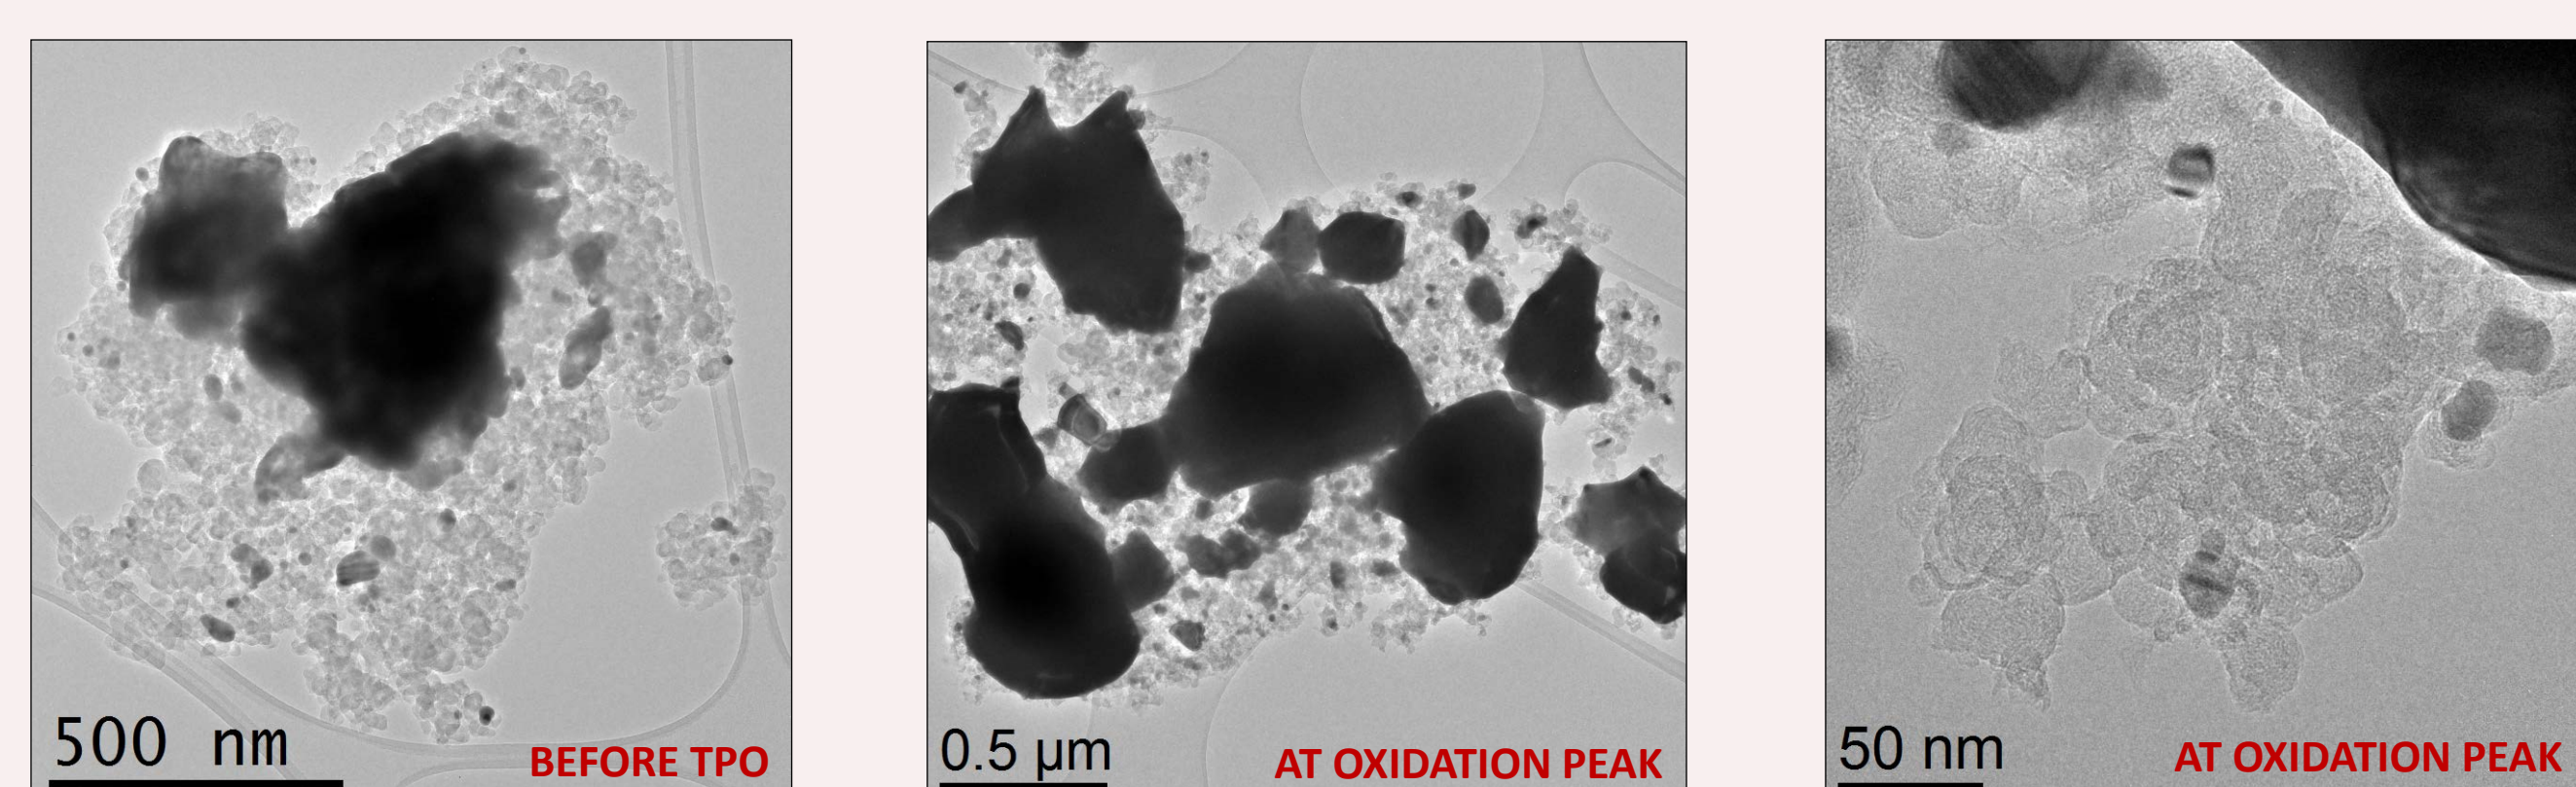

In situ TEM analysis:

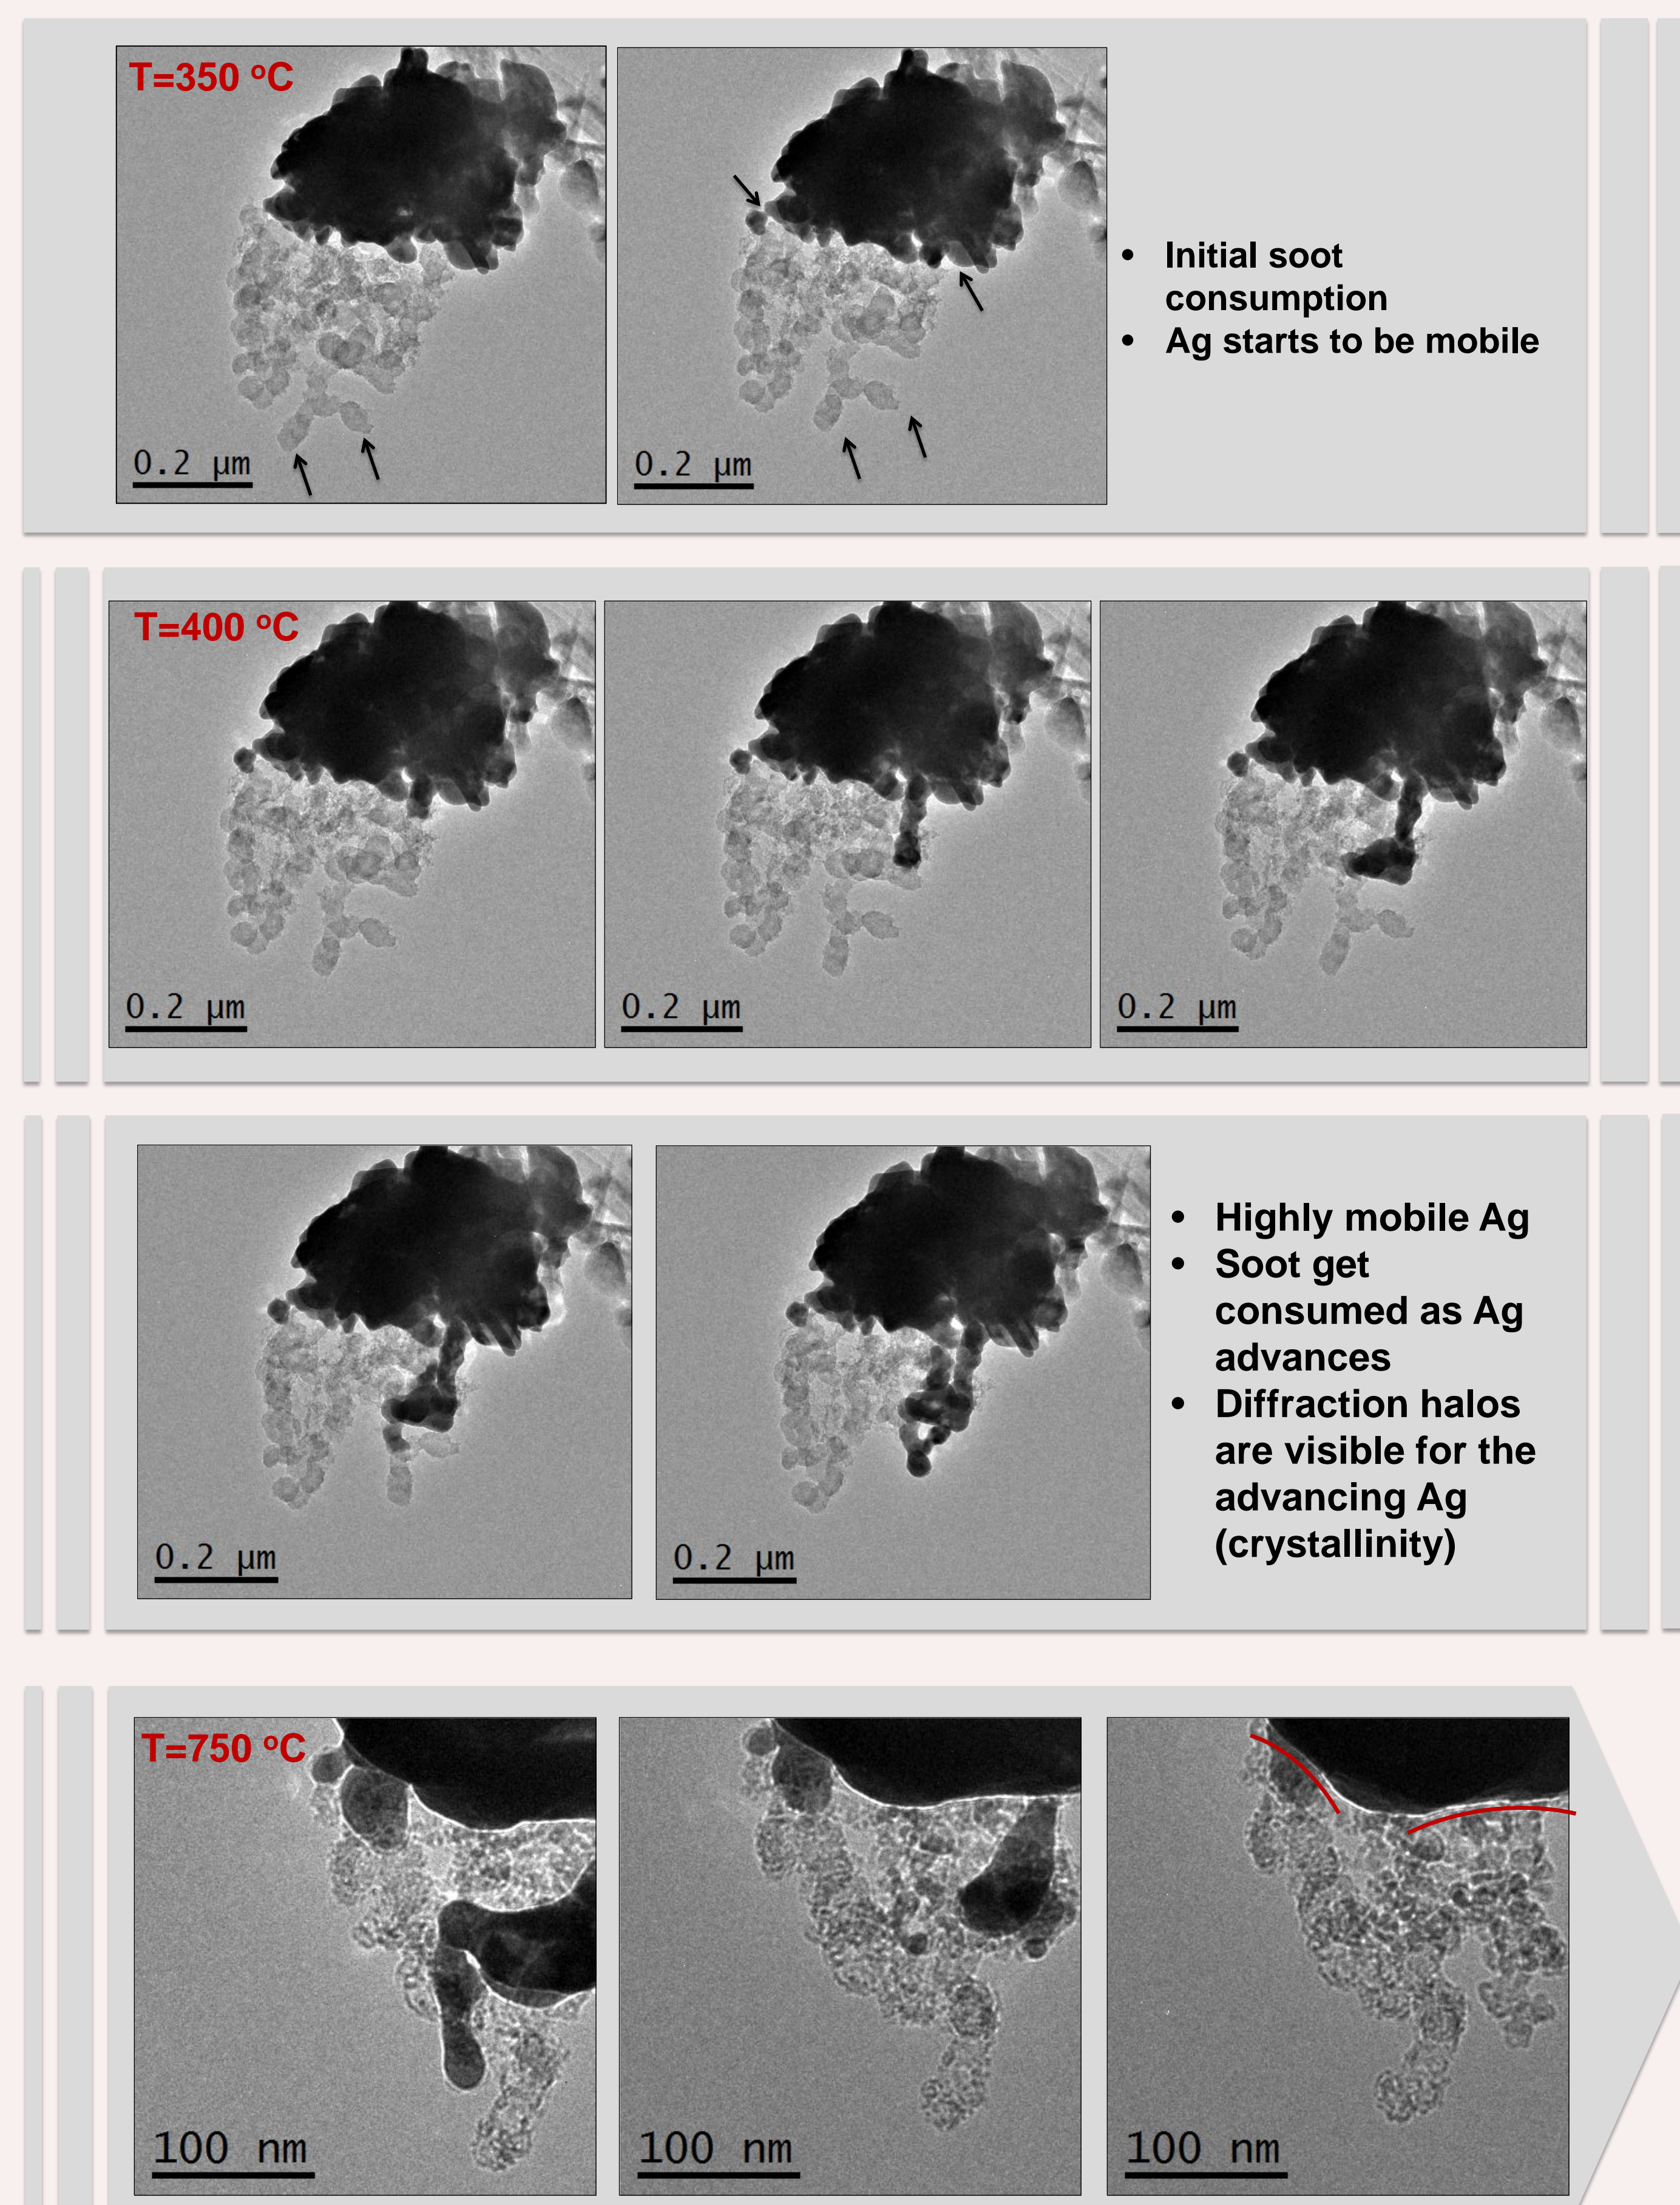

→ Soot oxidation is an exothermic process. Local heating could lead to melting of the advancing Ag (seen on metal nanoparticles in literature [1] for graphite oxidation). Once oxidation is over, Ag could solidify again.

→ At higher temperature, Ag agglomerates back leaving a soot "snake skin" and forming the tapered fronts.

References:

[1] J. R. Fryer, Nature (1968) 220, 1121-1122

Acknowledgements:

The A. P. Møller and Chastine Mc-Kinney Møller Foundation is gratefully acknowledged for its contribution towards the establishment of the Center for Electron Nanoscopy in the Technical University of Denmark. Part of this work is funded by The Danish Council for Strategic Research (DSF) under Grant No. 2106-08-0039.