



Strength recovery of concrete exposed to freezing-thawing by self-healing of cementitious materials using synthetic fiber

著者	CHOI Heesup, INOUE Masumi , SENGOKU Risa, CHANG Young-Cheol
journal or publication title	Advanced Materials Letters
volume	8
number	10
page range	993-998
year	2017-10
URL	http://hdl.handle.net/10258/00009508

doi: info:doi:10.5185/amlett.2017.1635

Strength recovery of concrete exposed to freezing-thawing by self-healing of cementitious materials using synthetic fiber

Heesup Choi^{1*}, Masumi Inoue¹, Risa Sengoku¹, Hyeonggil Choi²

¹Department of Civil and Environmental Engineering, Kitami Institute of Technology, Hokkaido, 090-8507, Japan

²Faculty of Environmental Technology, Muroran Institute of Technology, Hokkaido, 090-8585, Japan

*Corresponding author: E-mail: hs-choi@mail.kitami-it.ac.jp

Received: 23 January 2017, Revised: 18 February 2017 and Accepted: 09 April 2017

DOI: 10.5185/amlett.2017.1635

www.vbripress.com/aml

Abstract



In this study, it is possible to disperse effectively cracked using synthetic fiber, an examination of the most suitable self-healing conditions was performed on the above crack width 0.1mm. As a result, effective crack dispersion using polyvinyl alcohol (PVA) fibers with polar OH⁻ groups, as well as improved self-healing for cracks that are larger than 0.1 mm in width, posing concerns of CO₂ gas and Cl⁻ penetration, were observed. Also, CO₃²⁻ reacts with Ca²⁺ in the concrete crack, resulting in the precipitation of a carbonate compound, CaCO₃. Based on this, it is deemed possible for the recovery of effective water tightness and strength recovery through effective freezing-thawing resistance to be made from cracks that are larger than 0.1 mm in width. In addition, it was determined that, as for the most suitable self-healing conditions in the inside and surface of the cracks, calcium hydroxide (Ca(OH)₂) solution with CO₂ micro-bubble was more effective in promoting the self-healing capability than water with CO₂ micro-bubble. Copyright © 2017 VBRI Press.

Keywords: Freeze-thaw, micro-crack, PVA fiber, CO₂ micro-bubble, self-healing, water tightness, strength recovery.

Introduction

Concrete and cementitious building materials are essential in civil engineering for constructing buildings for the modern society. It is thought that in the near future, development of construction materials that can completely replace concrete will become exceptionally challenging. As concrete as a material has a lower tensile strength than compressive strength, the occurrence of cracks in concrete structures is inevitable. In Japan, as long as these cracks are smaller than the acceptable crack width, they are not considered as a major problem with respect to structural durability [1]. However, even if fine cracks do not immediately reduce the safety performance of a structure, degradation factors such as CO₂ and Cl⁻ can permeate into concrete through these fine cracks, and as these accumulate, water permeability, which is an evaluation index for the evaluation of durability, also increases [2]. As these deterioration factors continue to permeate deeper, the cracks widen, the degradation of concrete accelerates, and the possibility of the concrete structure being irreparably damaged rises. Therefore, it is essential to make an effort such that the occurrence of fine cracks in concrete structures can be prevented in its initial stages. In an environment where there is moisture, some of the cracks present in concrete can undergo a ‘filling-up’ or clogging phenomenon causing self-healing,

particularly when their width is sufficiently small. This is caused by rehydration reactions and the depositing of substances such as CaCO₃[3]. The latter repair mechanism involves the reaction between Ca²⁺ present in concrete and CO₃²⁻ dissolved in water to form CaCO₃, which helps in healing of the cracks [3]. The calcite crystal reactions are shown in Eqs.(1)-(3):



As a result of this self-healing phenomenon, the formation of cracks in concrete and the permeation of Cl⁻ and CO₂ can be delayed, which reduces a certain amount of the water permeability that results from the occurrence and development of these cracks [4]. Furthermore, it is possible to recover some of the dynamic modulus of elasticity of concrete, which had deteriorated because of freezing and thawing. This implies that the strength of concrete may be recovered to a certain extent [5]. Therefore, if cracks can be repaired autonomously through self-healing, this process may significantly contribute to reducing the burden of maintaining and prolonging the lifespan of concrete structures. Owing to this phenomenon, the early stages of deterioration, i.e.

when cracks are formed, can be checked. This can lead to an increase in the durability of concrete structures. In existing research pertaining to this self-healing phenomenon, it has been reported that standard concrete cracks of up to 0.1 mm in size can recover through self-healing [6]. Additionally, the cracks occurring in concrete can be dispersed by mixing synthetic fibers such as polyvinyl alcohol (PVA) and polypropylene (PE) into cementitious material. This method has been proposed as a means to efficiently promote self-healing by reducing the width of the cracks that have formed in concrete [7]. In particular, it has been shown that the use of PVA fibers, containing OH⁻ polar groups, results in an improved self-healing performance [8].

In this research, we conducted experiments pertaining to cementitious repair materials that are used for the recovery and reinforcement of the deteriorated concrete structures. We also investigated the use of synthetic fibers for effectively dispersing the cracks that are generated and expanded by freezing. In self-healing cracks that were 0.1 mm or larger, the penetration of degradation factors was suppressed in the portion containing recovery materials (Experiment 1). We also evaluated the recovery of strength of cementitious materials by self-healing that had been frozen and thawed (Experiment 2).

Table 1. Mixture proportions of the mortar.

Type	S/C (Wt.%)	W/C (Wt.%)	SP/C (Wt.%)	Fiber (vol.%)
PVA	0.4	0.3	0.25	1.2
PP				1.5

Experimental

Materials

As the experimental materials in this study, Portland cement (C, density: 3.16 g/cm³, mean diameter: 10 μm), quartz sand as the fine aggregate (S, surface-dry density: 2.61 g/cm³, mean diameter: 180 μm), and a high-performance water reducing agent as an admixture (SP, density: 1.05 g/cm³, main constituent: polycarboxylate-based superplasticizer) were used. As for the synthetic fibers, PVA (fiber diameter: 100 μm, fiber length: 12 mm, density: 1.3 g/cm³) and polypropylene (PP) (fiber diameter: 300 μm, fiber length: 12 mm, density: 0.91 g/cm³) were used. The mixture proportions of the mortar are summarized in **Table 1**. The properties of the employed fibers are presented in **Table 2**. The characteristic part of the chemical components of the employed synthetic fibers consists of polar groups

indicated by the circle in **Fig. 1**. PVA has the highest polarity strength owing to the OH radical, whereas PP has no polarity strength.

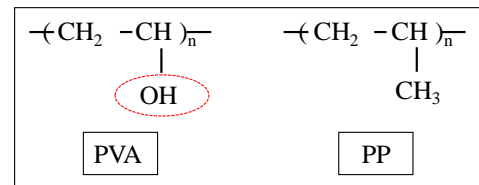


Fig. 1. Characteristic part of the chemical components of each fiber.

Evaluation of water tightness by fiber type and self-healing conditions (Experiment 1)

Experimental outline

In this experiment, the composite self-healing performance of the cementitious materials having PVA fibers incorporated into them was studied. Self-healing was observed in cracks having a width of 0.3 mm, which were introduced into the material through tensile loading. By using the coefficient of water permeability, self-healing performance was evaluated and optimal self-healing methods were also studied. Furthermore, the presence of self-healing substances was confirmed using Raman spectroscopic analysis.

Experiment and methods

In this TEST, the dimensions of the specimens were 85×80×30 mm (L×B×H). Two specimens were fabricated for each series. After mixing the mortar with the fibers, water curing was performed in a tank at 20°C for 28 days. A universal testing machine (UTM) was used to apply a tensile load at a speed of 0.2 mm/min, and the crack width was adjusted so that the displacement of the PI displacement transducer would be about 0.3mm. **Fig. 2(a)** and **(b)** show the mimetic diagram of the specimens, used in crack introduction, and the tensile load test.

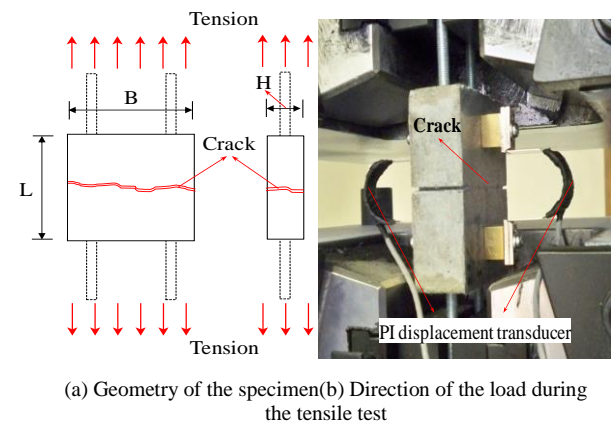


Fig. 2. Specimen overview.

Table 2. Properties of employed fibers.

Type	Type of Fiber	Density (g/cm ³)	Tensile Strength (GPa)	Length (mm)	Diameter (μm)
PVA	Polyvinyl alcohol	1.30	1.6	12	100
PP	Polypropylene	0.91	0.7	12	300

Table 3 summarizes the experimental procedure. In the first step (A), the coefficient of water permeability (K) was measured after introducing cracks in a tensile loading test. In the next step, K was measured after the test materials underwent self-healing (Step B). Self-healing performance was evaluated using both tap water and an aqueous solution (solubility: 0.82 g/L) of calcium hydroxide (hereafter $\text{Ca}(\text{OH})_2$), in a water tank that had a provision for introducing CO_2 micro-bubbles to each specimen, and for soaking the test materials in water (20°C). It has been reported that self-healing can be promoted by using saturated $\text{Ca}(\text{OH})_2$ aqueous solution as a source for calcium ions (Ca^{2+})[9], and CO_2 micro-bubbles also promote recovery owing to the increased supply of carbonate ions (CO_3^{2-}) during this process[10]. These methods were also adopted in this study to maximize self-healing. The self-healing period was set at 7 days with the temperature of water as 20°C, and the pH concentration was adjusted as given in **Table 3**. In Step C, the specimens that had previously undergone self-healing in Step B were subjected to repeated freezing and thawing, and cracks resulting from freezing damage were introduced. The freeze-thaw test was completed after 100 cycles according to JIS A 1148 and ASTM C 666, and the coefficient of water permeability was subsequently measured. Finally, in Step D, self-healing was performed using the same methods as in Step B, and the coefficient of water permeability was determined again. Next, to confirm the crystalline components of the substances resulting from the self-healing process, Raman spectroscopic analysis was performed on the cracked portion to which the self-healing substances had attached (Step D). The apparatus used in the water permeability tests in this study is shown in **Fig. 3**[11].

Evaluation of strength recovery from self-healing of cementitious materials that underwent freeze-thaw (experiment 2)

Experimental outline

In this experiment, the strength recovery of cementitious materials that underwent self-healing by the introduction of synthetic fibers after freeze-thaw damage was evaluated. The optimal self-healing method was selected based on the results of Experiment 1. The effectiveness of the strength recovery process was evaluated based on the change in the relative dynamic modulus of elasticity and flexural strength according to the time variation. In addition, the presence of self-healing substances on the surface of the fibers was confirmed by SEM (scanning electron microscopy) imaging.

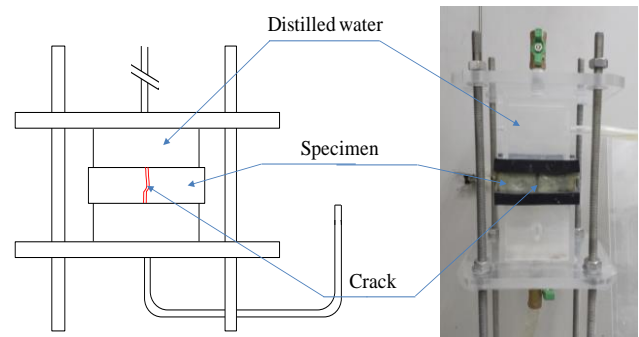


Fig. 3. Apparatus used in the water permeability tests [11].

Experiment and methods

The dimensions of the specimens used for testing the relative modulus of elasticity and the bending test were 100 x 100 x 400 mm (B x H x L) and 40 x 40 x 160 mm

Table 3. Experimental procedure (Experiment 1)

STEP	Experimental levels	Evaluation
A	Pre-crack by tensile loading	<ul style="list-style-type: none"> • Performance evaluation of self-healing by coefficient of water permeability (K) • Evaluation of self-healing substances by Raman spectroscopic analysis
B	First, self-healing	
C	Crack growth by freeze-thaw	
D	Second, self-healing	

Table 4. Experimental procedure (Experiment 2)

STEP	Experimental levels	Evaluation
E	Before freeze-thaw	<ul style="list-style-type: none"> • Evaluation of self-healing by relative dynamic modulus of elasticity and flexural strength • Evaluation of self-healing substances on the surface of the fibers by SEM imaging
F	After freezing and thawing	
G	After self-healing	

Table 5. Experimental factors and conditions (Experiment 1 and 2)

Experimental factors	Conditions		
Fiber	PVA, PP		
Self-healing	Water	W	pH 6.8
	$\text{Ca}(\text{OH})_2$	Ca	pH 12.0
	Water + CO_2 micro-bubble	W+MB	pH 6.0
	$\text{Ca}(\text{OH})_2$ + CO_2 micro-bubble	Ca+MB	pH 8.5
Temperature	20°C		
Crack	Tensile load, Freeze-thaw		
Period of self-healing	7 Days		

(B x H x L). They were cured in the same manner as used in Experiment 1, and cracks were introduced by repeated freezing and thawing.

Table 4 summarizes the experimental procedure. The experimental method employed was Method A of JIS A 1148, "Method of Freezing and Thawing Concrete". The relative dynamic modulus of elasticity and flexural strength were determined for each specimen before freeze-thaw (Step E), after 300 cycles of freeze-thaw (Step F), and after 7 days of self-healing (Step G). The self-healing method used in each case was terminated after 300 cycles of freeze-thaw, based on the results of Experiment 1. In order to increase the supply of calcium (Ca^{2+}) and carbonate (CO_3^{2-}) ions, the experiment was conducted with two cases (W+MB and Ca+MB) by micro CO_2 bubbles added and a $\text{Ca}(\text{OH})_2$ solution. Subsequently, SEM imaging was done to confirm the presence of substances, which had formed owing to presence of PVA fibers in the cracked part of the specimen that had been subjected to freeze-thaw (Step G). **Table 5** summarizes the experimental conditions of Experiments 1 and 2.

through the use of $\text{Ca}(\text{OH})_2$ solution, the specimen showed a greater tendency toward self-healing compared to when tap water was used [9]. Similarly, when micro CO_2 bubbles were added to water and $\text{Ca}(\text{OH})_2$ solution, PVA showed approximately 100-400 times more recovery of watertightness than PP. Furthermore, it was observed that the micro CO_2 bubbles promoted self-healing as the dispersion of fibers is better compared to the case where they were not present. This is due to the increase in the concentration of calcium (Ca^{2+}) and carbonate ions (CO_3^{2-}) in the $\text{Ca}(\text{OH})_2$ solution[10]. From these observations, it can be concluded that PVA always showed a better self-healing performance than PP, regardless of the amount of fiber that was mixed in the specimen. In particular, PVA with OH^- groups was very effective in its self-healing performance. Moreover, Ca + MB demonstrated an improved self-healing performance compared to W + MB. Based on these experimental results, the use of PVA fibers along with $\text{Ca}(\text{OH})_2$ solution and CO_2 micro-bubbles was judged to provide the most effective conditions for encouraging the production of self-healing substances for cracks with a width of 0.3 mm.

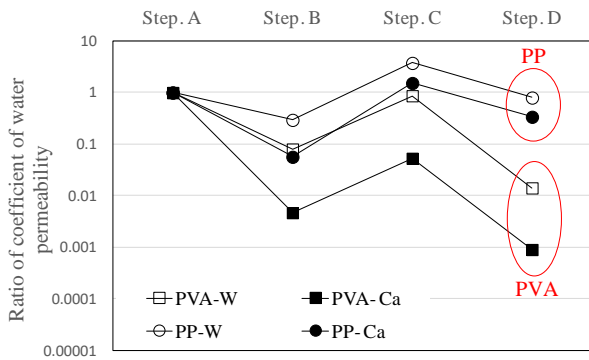


Fig. 4. W • Ca case (fiber 1.2%).

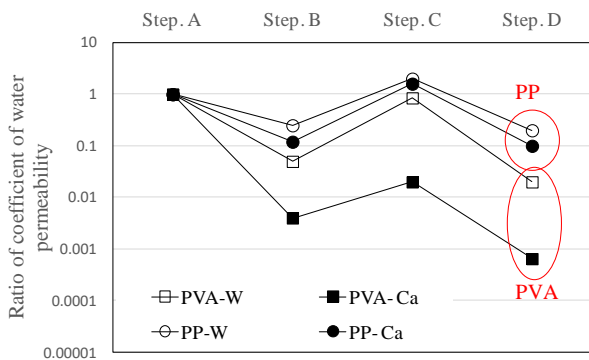


Fig. 5. W • Ca case (fiber 1.5%).

Results and discussion

Evaluation of water tightness by fiber type and self-healing conditions (experiment 1)

Figs. 4-7 show the water permeability coefficient ratio for each fiber series, calculated from the coefficient of water permeability as determined in Step A. In the case of self-healing using water and $\text{Ca}(\text{OH})_2$ solution, i.e. Step D, PVA showed approximately 60-400 times more recovery of watertightness than PP (**Figs 4 and 5**). Additionally,

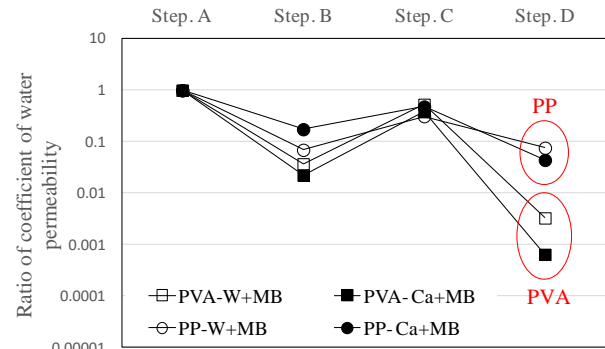


Fig. 6. W+MB • Ca+MB case (fiber 1.2%).


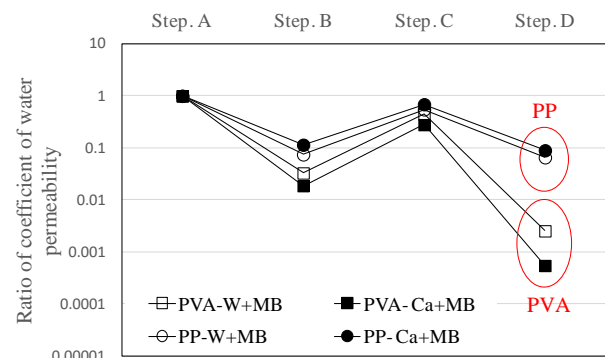



Fig. 7. W+MB • Ca+MB case (fiber 1.5%).

To confirm the nature of the crystalline components of the substances resulting from self-healing, Raman spectroscopic analysis was performed. The self-healing substances in the crack of PVA-Ca + MB (Fiber 1.5%, Step D) were obtained from the test specimen and irradiated with a laser, such that the positions of the wavelength peaks could be compared. **Fig. 8(a)** is a

photograph of the apparatus used, and 8(b) shows the results obtained from the Raman spectroscopic analysis. The wavelength of the cracked portion clearly matched with the wavelength peak in the spectrum of CaCO₃ powder. Thus, it was confirmed that the substances constituting the white substances that are formed after the self-healing process were predominantly CaCO₃.

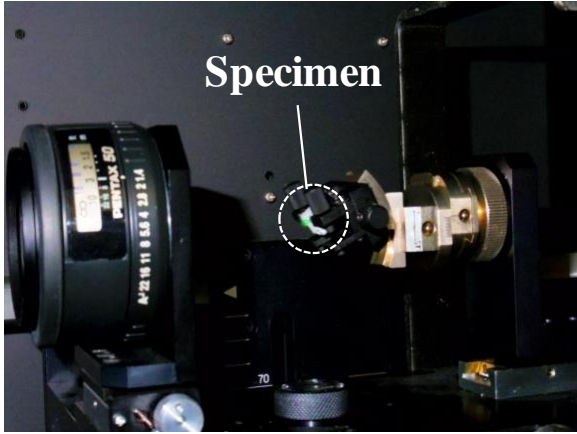

(a) Raman spectroscopy

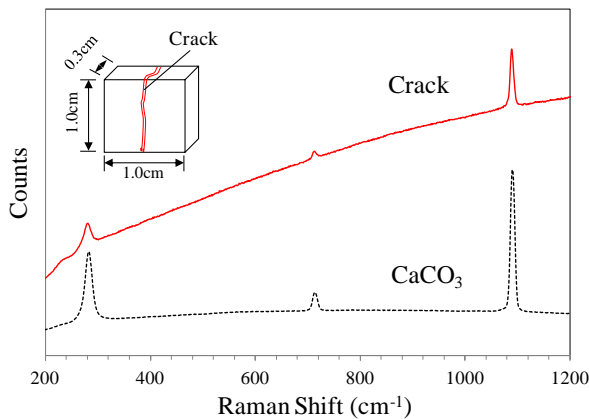

(b) PVA-Ca+MB (Fiber 1.5%, STEP D)

Fig. 8. Raman spectroscopy analysis.

Evaluation of strength recovery from self-healing of cementitious materials that underwent freeze-thaw (experiment 2)

Figs 9-12 show the relative dynamic modulus of elasticity and flexural strength ratio for each fiber series. In Fig. 9 and Fig. 10, from the time before (Step E) till after (Step F) the freeze-thaw, degradation of the relative dynamic modulus of elasticity was a result of the freeze-thaw process. In the case of W + MB (Fig. 9), after 300 freeze-thaw cycles (Step F) and 7 days of self-healing (Step G), there was hardly any change in the relative dynamic modulus of elasticity in the OPC and PP series. However, the relative dynamic modulus of elasticity tended to recover by ca. 10% for the PVA series, going from 70% in Step F to 80% in Step G. In the Ca +MB case (Fig. 10), case (Fig. 10), although the relative dynamic modulus of elasticity for the OPC and PP series increased only

slightly from Step F to Step G, there was an increase of ca. 8-10% for the PVA series. Fig. 11 and Fig. 12 show the results of the calculated flexural strength ratio based on the flexural strength before the freeze-thaw (Step E) for each fiber series. In the W + MB case (shown in Fig. 11), after 300 cycles of freeze-thaw (Step F) and 7 days of self-healing (Step G), the flexural strength of the OPC and PP series recovered ca. 20-25%, while the PVA series showed a tendency to recover more, ca. 35%. Furthermore, in the Ca + MB case (Fig. 12) from Step F to Step G, the flexural strength of the OPC and PP series recovered by about 25%, and the PVA series showed a tendency to recover its strength by nearly 50%. From the results of the relative dynamic modulus of elasticity and the flexural strength ratio, it can be concluded that the PVA series with OH⁻ groups demonstrates improved strength and effective self-healing when compared to the OPC and PP series. Furthermore, it was determined that the self-healing performance could be maximized by using PVA fibers having OH⁻ groups, along with the appropriate in the Ca + MB case that supplies the combination of Ca²⁺ and CO₃²⁻ necessary for self-healing.

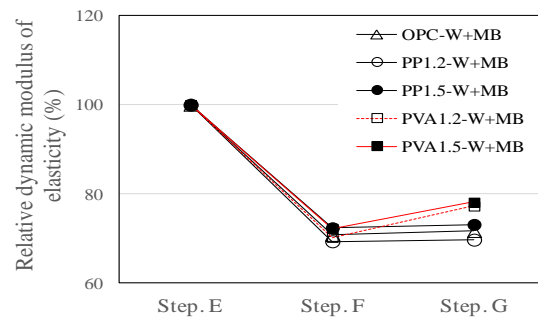


Fig. 9. W+MB case.

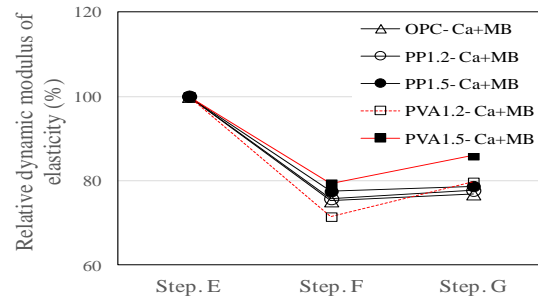


Fig. 10. Ca+MB case.

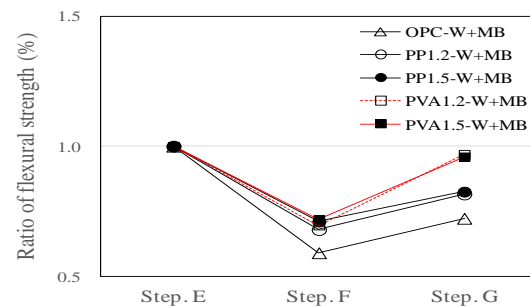


Fig. 11. W+MB case.

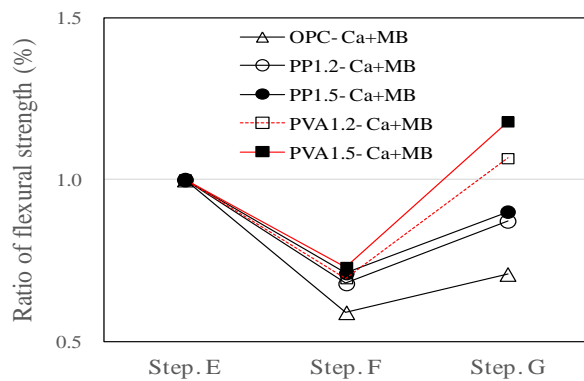


Fig. 12. Ca+MB case.

PVA fibers located in the cracked portion of the specimen that had been subjected to freezing and thawing (Step G) were studied using SEM. It was found that the self-healing substance was adhered to the surface of PVA fibers. This observation further confirmed that self-healing can be effectively promoted by using PVA fibers.

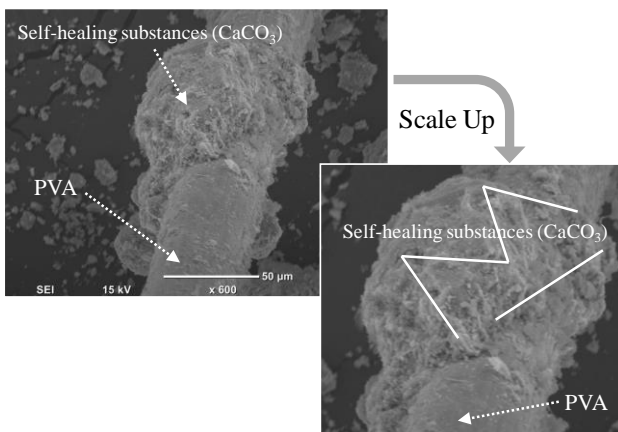


Fig. 13. Surface of a PVA fiber (SEM)

Conclusion

In this study, we examined cementitious materials that are used to repair and reinforce deteriorated concrete structures and aimed at evaluating the strength recovery of these repaired materials. We were able to suppress the penetration of degradation factors that arise owing to freezing and thawing of these materials. The self-healing process of cracks with a width of 0.1 mm or more was promoted by effectively dispersing and reducing the occurrence and development of cracks through fiber reinforcement. To that end, the self-healing performance of cracks was determined by evaluating the coefficient of water permeability and the relative dynamic modulus of elasticity and flexural strength. In addition, the nature of the self-healing substance was confirmed by Raman spectroscopic analysis and imaged using SEM. The results of this study are given below.


- Although it is possible to make repairs to cracks resulting from freezing damage using any type of

fiber, PVA allowed for a greater recovery than PP. The positive effects of using an aqueous solution of $\text{Ca}(\text{OH})_2$ and CO_2 micro-bubbles for promoting self-healing were confirmed.

- In addition to promoting composite self-healing, cementitious repair materials mixed with PVA fibers displayed a good performance in improving concrete strength.

References

1. Japan Concrete Institute; Practical Guideline for Investigation, Repair and Strengthening of Cracked Concrete Structure; Japan Concrete Institute, Tokyo, Japan, **2013**. (In Japanese)
2. Stefan, J.; Effect of cracking and healing on chloride transport in OPC concrete, *Cement and Concrete Research*, **1996**, 26, 6, pp.869.
3. Neville A.M.; Properties of Concrete, Person Education Limited, USA, **1995**.
4. Heesup, C.; Masumi, I.; Sukmin, K.; Hyeonggil, C.; Myungkwan, L.; Effective Crack Control of Concrete by Self-Healing of Cementitious Composites Using Synthetic Fiber, *Journal of the Materials*, **2016**, 9, 4, pp.1-14.
5. Stefan, J.; Self-healing of high strength concrete after deterioration by freeze/thaw, *Cement and Concrete Research*, **1996**, 26, 1, pp.55.
6. Edvardsen, C.; Water Permeability and Autogenous Healing of Cracks in Concrete, *ACI Materials Journal*, **1999**, 96, M56, pp.448.
7. Nishiwaki, T.; Koda, M.; Yamada, M.; Mihashi, H.; Kikuta, T.; Experimental study on self-healing capability of FRCC using different types of synthetic fibers, *Journal of Advanced Concrete Technology*, **2012**, 10, pp.195.
8. Heesup, C.; Masumi, I.; Hyeonggil, C.; Myungkwan, L.; Nishiwaki, T.; Shunzo, K.; The fundamental study of the crack control by self-healing of PVA fiber reinforced cementitious composites, *Journal of Civil Engineering and Architecture Research*, **2016**, 3, 9, pp.1680.
9. Haoliang, H.; Guang, Y.; Self-healing of cracks in cement paste affected by additional Ca^{2+} ions in the healing agent, *Journal of intelligent Material Systems and Structures*, **2014**, pp.1-12.
10. Hansic, K.; et al.; Fundamental Study on Recycling of Low-quality Recycled Fine Aggregate using Carbonated Nanobubble Water, Proceedings of first international Conference on concrete sustainability, *S3-1-4*, **2013**.
11. Homma, D.; Mihashi, H.; Nishiwaki, T.; Self-healing capability of fiber reinforced cementitious composites, *Journal of Advanced Concrete Technology*, **2009**, 7, 2, pp.217.



A Monthly Journal
ISSN 1938-0017

Publish your article in this journal

Advanced Materials Letters is an official international journal of International Association of Advanced Materials (IAAM, www.iaamonline.org) published monthly by VBRI Press AB from Sweden. The journal is intended to provide high-quality peer-review articles in the fascinating field of materials science and technology particularly in the area of structure, synthesis and processing, characterisation, advanced-state properties and applications of materials. All published articles are indexed in various databases and are available download for free. The manuscript management system is completely electronic and has fast and fair peer-review process. The journal includes review article, research article, notes, letter to editor and short communications.

Copyright © 2017 VBRI Press AB, Sweden

www.vbripress.com/aml