



Preparation, structure, and in vitro chemical durability of yttrium phosphate microspheres for intra-arterial radiotherapy

著者	Kawashita Masakazu, Matsui Naoko, Li Zhixia, Miyazaki Toshiki, Kanetaka Hiroyasu
journal or publication title	Journal of Biomedical Materials Research. Part B, Applied biomaterials
volume	99B
number	1
page range	45-50
year	2011-10-01
URL	http://hdl.handle.net/10228/6027

doi: [info:doi/10.1002/jbm.b.31870](https://doi.org/10.1002/jbm.b.31870)

1
2
3
4 **Preparation, structure, and *in vitro* chemical durability of yttrium**
5 **phosphate microspheres for intra-arterial radiotherapy**
6
7
8

9
10 **Masakazu Kawashita¹, Naoko Matsui¹, Zhixia Li¹, Toshiki Miyazaki², Hiroyasu**
11 **Kanetaka¹**
12

13
14 ¹Graduate School of Biomedical Engineering, Tohoku University, Aoba-ku, Sendai
15 980-8579, Japan
16
17

18 ²Graduate School of Life Science and Systems Engineering, Kyushu Institute of
19 Technology, Wakamatsu-ku, Kitakyushu 808-0196, Japan
20
21
22

23
24 **Correspondence to:** M. Kawashita; e-mail: m-kawa@ecei.tohoku.ac.jp
25
26
27

28 **Running head: Yttrium phosphate microspheres for intra-arterial radiotherapy**
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Abstract: Chemically durable microspheres containing yttrium and/or phosphorus are useful for intra-arterial radiotherapy. In the present study, we attempted to prepare yttrium phosphate (YPO_4) microspheres with high chemical durability. YPO_4 microspheres with smooth surfaces and diameters of around 25 μm were successfully obtained when gelatin droplets containing yttrium and phosphate ions were cooled and solidified in a water-in-oil emulsion and then heat-treated at 1100°C. The chemical durability of the heat-treated microspheres in a simulated body fluid at pH = 6 and 7 was high enough for clinical application of intra-arterial radiotherapy.

Keywords: yttrium phosphate; chemical durability; microspheres; intra-arterial radiotherapy

INTRODUCTION

Intra-arterial radiotherapy of malignant liver tumors has been performed using radioactive yttrium-containing microspheres.^{1,2} Yttrium-89 (^{89}Y) is a nonradioactive isotope with a natural abundance of 100%; neutron bombardment activates ^{89}Y to form the β -emitter ^{90}Y , which has a half-life of 64.1 h. When radioactive microspheres 20–35 μm in diameter are injected into a target organ, they are trapped inside small blood vessels in the tumor, blocking the nutritional supply to the tumor and delivering a large, localized dose of short-range, highly ionizing β -rays. The β -rays penetrate only about 2.5 mm in living tissue, thus causing little radiation damage to neighboring healthy tissues. These microspheres show high chemical durability, and the radioactive ^{90}Y remains essentially within the microspheres and does not affect neighboring healthy tissues. The radioactivity of ^{90}Y decays to a negligible level within 21 days after neutron bombardment. The microspheres therefore become inactive soon after the cancer treatment.

So far, Y_2O_3 – Al_2O_3 – SiO_2 (YAS) glass microspheres (TheraSphere[®])³⁻⁵ and yttrium-containing resin microspheres (SIR-Spheres[®])⁶⁻⁸ have yielded good results in clinical trials.⁹⁻¹² They have been used clinically to treat unresectable hepatocellular carcinoma in various countries including the USA, Canada, China, Australia, New Zealand and

Singapore.^{13–28} The Y_2O_3 content in TheraSpheres[®] is 17 mol%, and the yttrium content in SIR-Spheres[®] is around 2 mol%. The radioactivity of these microspheres decays significantly even before cancer treatment is started because of the short half-life. Therefore, the development of chemically durable microspheres having a higher yttrium content is desirable. We have developed dense Y_2O_3 microspheres,²⁹ hollow Y_2O_3 microspheres,³⁰ and porous Y_2O_3 microparticles³¹ with high chemical durability *in vitro*.

On the other hand, phosphorus-31 (³¹P), found at a natural abundance of 100%, can also be activated by neutron bombardment to form the β -emitter ³²P, which has a half-life of 14.3 days. Microspheres containing a high phosphorus content are therefore expected to be effective for cancer treatment, similar to yttrium-containing microspheres.^{32,33} Previously, we attempted to prepare yttrium phosphate (YPO₄) microspheres by a high-frequency induction thermal plasma melting method and found that they showed high chemical durability *in vitro*.²⁹ However, they lost a certain amount of phosphorus to form Y_2O_3 , and their surfaces were rather rough owing to the loss of phosphorus from volatilization at the higher synthesis temperatures (above 10,000°C). It is feared that the rough surfaces of the microspheres would damage blood vessels. In this study, we attempted to prepare YPO₄ microparticles with a smooth surface and investigated their structure and *in vitro* chemical durability in order to evaluate their potential as a radioactive source in intra-arterial radiotherapy.

MATERIALS AND METHODS

Sample preparation

A precursor precipitate containing yttrium and phosphate ions was obtained by the following solution precipitation process.³⁴ Equimolar (8.4 mM) amounts of yttrium nitrate (Y[NO₃]₃; Wako Pure Chemical Industries Ltd., Osaka, Japan) and phosphoric acid (H₃PO₄; Wako Pure Chemical Industries Ltd., Osaka, Japan) were dissolved in 300 mL of pure water. Aqueous NaOH solution (56 mM, 150 mL) was added to the Y(NO₃)₃–H₃PO₄ solution under stirring for 20 min, resulting in an opaque solution. This opaque solution was centrifuged at 4000 rpm for 5 min and decanted to obtain white precipitates. The precipitates were washed several times with pure water. Then, 2.5 mL of 0.1M nitric acid aqueous solution was added to 10 g

1
2
3
4 of the white precipitates to obtain a stable sol solution.³⁵ Gelatin (0.5 g; APH-250, Nitta
5 Gelatin Inc., Osaka, Japan) was dissolved in 5 mL of the sol solution. The resultant solution
6 was dropped into 50 mL of corn oil (Wako Pure Chemical Industries Ltd., Osaka, Japan) at
7
8 30°C and stirred at 1000 rpm for 10 min to obtain a water-in-oil emulsion. The emulsion was
9
10 cooled in an ice bath to solidify the gelatin-containing water droplets. The solidified droplets
11
12 were filtered and washed with cold ethanol and then freeze-dried for 6 h in a freeze dryer
13
14 (FD-1000; Tokyo Rikakikai Co. Ltd., Tokyo, Japan). Finally, the freeze-dried samples were
15
16 placed in an alumina boat, heated to various temperatures (700–1500°C) at a rate of
17
18 5°C·min⁻¹ in a SiC or MoSi₂ electric furnace, and kept at the given temperature for 1 h.
19
20
21
22
23
24

25 **Structural analysis**

26 The shapes of the microspheres were observed using a scanning electron microscope (SEM;
27 VE-8800, Keyence, Tokyo, Japan). The precipitated phase was examined with a powder
28 X-ray diffractometer (XRD; RINT-2200VL, Rigaku Co. Ltd., Tokyo, Japan) using the
29
30 following settings: X-ray source, Ni-filtered CuK α radiation; X-ray power, 40 kV, 40 mA;
31
32 scanning rate, $2\theta = 2^\circ \cdot \text{min}^{-1}$; and sampling angle, 0.02°. The structure of the heat-treated
33
34 microspheres before and after an *in vitro* chemical durability test was investigated by
35
36 Fourier-transform infrared spectroscopy (FT-IR; FT/IR-6200, JASCO, Tokyo, Japan) with a
37
38 diffusive reflection attachment (DR-PRO410M, JASCO, Tokyo, Japan). For the FT-IR
39
40 diffusive reflection spectroscopic measurement, potassium bromide (KBr) powder was mixed
41
42 with the samples. The sample content in KBr pellets was around 0.5 wt%.
43
44
45
46
47
48

49 ***In vitro* chemical durability test**

50 A simulated body fluid (SBF) with ion concentrations of Na⁺ 142.0, K⁺ 5.0, Mg²⁺ 1.5, Ca²⁺
51
52 2.5, Cl⁻ 147.8, HCO₃⁻ 4.2, HPO₄²⁻ 1.0, and SO₄²⁻ 0.5 mM was prepared by dissolving
53
54 reagent-grade NaCl, NaHCO₃, KCl, K₂HPO₄·3H₂O, MgCl₂·6H₂O, CaCl₂, and Na₂SO₄ (Nacali
55
56 Tesque Inc., Kyoto, Japan) in ultrapure water and buffering to pH 7.40 with
57
58 tris(hydroxymethyl) aminomethane ([CH₂OH]₃CNH₂) and 1M HCl (Nacali Tesque Inc.,
59
60 Kyoto, Japan) at 36.5°C.³⁶ Then, the pH value of the SBF was adjusted to 6 (SBF-6) or 7

(SBF-7) by further addition of 1M HCl.

The microspheres (0.025 g) heat-treated at 1100°C were soaked in 10 mL of SBF-6 or SBF-7 in a polypropylene bottle at 36.5°C for various periods up to 21 days. The pH value of a normal body fluid is maintained at around pH 7, but this value is liable to fall to around pH 6 near a cancer owing to the production of lactic acid.³⁷ The SBF was shaken at a rate of 120 strokes·min⁻¹ using a stroke length of 3 cm. The samples were soaked for up to 21 days, since the radioactivity of ⁹⁰Y decays to a negligible level after 21 days. An inductively coupled plasma (ICP) atomic emission spectrometer (Optima 2000DV, PerkinElmer Co., Ltd., Germany) was used to determine the concentrations of yttrium and phosphorus released from the microspheres into SBF-6 or SBF-7. The fraction of yttrium released from the microspheres was calculated using the following formula.

$$\text{Released fraction} = \frac{\text{Molar quantity of yttrium released from the microsphere into the SBF (mol)}}{\text{Total molar quantity of yttrium contained in the microsphere (mol)}}$$

RESULTS

Figure 1 shows XRD patterns of samples before and after heat treatment at different temperatures. The untreated sample exhibited a halo, indicating that its structure was amorphous. Several peaks of tetragonal YPO₄ with the xenotime structure (PDF File No. 11-0254) were clearly observed after heat treatment at temperatures above 700°C. With a further increase in heat treatment temperature to 1500°C, the structure of the sample remained dehydrated YPO₄ with tetragonal xenotime-type structure,³⁴ but the diffraction peaks became more intense and narrower, indicating crystal growth of YPO₄ with increasing heat treatment temperature.

Figure 2 shows SEM photographs of samples before and after heat treatment at different temperatures. Microspheres around 25 μm in diameter with smooth surfaces were successfully obtained by the present method, although their diameters ranged from 10 to 80 μm. The surface smoothness of the microspheres was improved slightly by heat treatment at 700°C or 1100°C. This might be attributed to partial sintering of YPO₄ by the heat treatment. With heat treatment at 1500°C, the surface of the microspheres became rather rough, and

1
2
3
4 remarkable aggregation of the microspheres occurred. It seems plausible that the
5
6 microspheres heat-treated at higher temperatures will show higher chemical durability in the
7
8 human body, since sintering of YPO_4 will proceed at higher temperatures. However, the rough
9
10 surface and aggregation of the microspheres are unfavorable for clinical application of
11
12 intra-arterial therapy. Therefore, we considered that the maximum useful heat treatment
13
14 temperature is 1100°C , and an *in vitro* chemical durability test was conducted for the
15
16 microspheres heat-treated at 1100°C in this study. Figure 3 shows SEM photographs of
17
18 cross-sections of these microspheres. Figures 2 and 3 show that both the inside and the outer
19
20 surface of the microspheres heat-treated at 1100°C were dense.
21

22
23 Figure 4 shows the concentrations of yttrium and phosphorus released from the
24
25 microspheres heat-treated at 1100°C into SBF-6 or SBF-7 after immersion for 21 days, in
26
27 comparison with those of the original SBF without soaking of the microspheres. The
28
29 concentrations of yttrium released from the microspheres into SBF-6 and SBF-7 were as low
30
31 as 0.3 mg/g , which is almost the same as the yttrium concentration of the original SBF
32
33 without microsphere soaking (Fig. 4[a]). It is interesting to note that the concentrations of
34
35 phosphorus in SBF-6 and SBF-7 in which the microspheres were soaked for 21 days were
36
37 slightly lower than those of the original SBF (Fig. 4[b]). This suggests that the microspheres
38
39 heat-treated at 1100°C released hardly any yttrium into either SBF-6 and SBF-7 after 21 days,
40
41 and a small amount of phosphorus might adsorb onto the surfaces of the microspheres.
42

43
44 Figure 5 shows the XRD patterns (a) and SEM photographs (b) of the microspheres
45
46 heat-treated at 1100°C before and after soaking in SBF-6 and SBF-7 for 21 days. No
47
48 appreciable change was observed in the XRD patterns and the SEM photographs of the
49
50 microspheres after soaking in either of the SBF solutions. Figure 6 shows the FT-IR diffusive
51
52 spectra of the microspheres heat-treated at 1100°C before and after soaking in SBF-6 and
53
54 SBF-7 for 21 days. The microspheres before soaking showed several bands assigned to
55
56 PO_4 .^{38,39} The bands at around 3500 cm^{-1} and 1630 cm^{-1} , which are assigned to H_2O ,^{38,39}
57
58 appeared after the microspheres were soaked in SBF-6 or SBF-7. This might be attributed to
59
60 partial hydration of the microspheres' surfaces due to the chemical durability test. The
intensity of the bands at around 1300 and 3000 cm^{-1} increased after the chemical durability

1
2
3
4 test. These two bands are assigned to PO_4 and CH_3 , respectively.³⁸⁻⁴⁰ This result suggests
5
6 adsorption of a small amount of phosphorus-containing organic compounds onto the surfaces
7
8 of the microspheres, although the detailed structure of the compounds is unclear. Also, it is
9
10 consistent with the results of the *in vitro* chemical durability test, indicating that the
11
12 concentrations of phosphorus in SBF-6 and SBF-7 in which the microspheres were soaked for
13
14 21 days were slightly lower than those of the original SBF (see Fig. 4). According to these
15
16 results, we can conclude that the present microspheres heat-treated at 1100°C are quite
17
18 chemically stable under acidic and neutral SBF solutions.
19
20
21

22 DISCUSSION

23
24
25 We examined the durability of the heat-treated microspheres by immersion for 21 days in
26
27 SBF (Fig. 4). Note, however, that the radioactivity of ^{32}P decays to a negligible level only
28
29 after 112 days, and hence it might be advisable to evaluate the chemical durability of the
30
31 microspheres for a longer period of 112 days. However, we can expect that the present YPO_4
32
33 microspheres would show high chemical durability for long periods such as 112 days because
34
35 we confirmed that microspheres consisting of YPO_4 and Y_2O_3 ($\text{YPO}_4\text{-Y}_2\text{O}_3$ microspheres)
36
37 showed excellent chemical durability for 112 days in saline with both $\text{pH} = 6$ and $\text{pH} = 7$ in
38
39 our previous study.²⁹ Moreover, the activity product of YPO_4 is reportedly as low as $10^{-24.76}$ at
40
41 $25 \pm 1^\circ\text{C}$.⁴¹
42

43
44 In Table 1, the fraction of yttrium released from the present YPO_4 microparticles is
45
46 compared with that of previously reported samples. The present YPO_4 microspheres showed
47
48 smaller released yttrium fractions than the previously reported samples, although the chemical
49
50 durability of some samples (dense Y_2O_3 microspheres, $\text{YPO}_4\text{-Y}_2\text{O}_3$ microspheres, and
51
52 $\text{Y}_2\text{O}_3\text{-Al}_2\text{O}_3\text{-SiO}_2$ [TheraSphere[®]-type] glass) was evaluated in saline solutions buffered at
53
54 $\text{pH} = 6$ or 7. In particular, we noted that the fraction of yttrium released from the present
55
56 YPO_4 microspheres was much smaller than that from TheraSphere[®]-type glass and dense
57
58 Y_2O_3 microspheres, which showed no acute toxicity in animal tests,⁴² indicating that the
59
60 chemical durability of the present YPO_4 microspheres is high enough for clinical application
in intra-arterial radiotherapy.

CONCLUSIONS

YPO₄ microspheres around 25 μm in diameter with smooth surfaces were successfully obtained by cooling and solidifying gelatin droplets containing yttrium phosphate precursor precipitates in a water-in-oil emulsion and then heat-treating them at 1100°C. The *in vitro* chemical durability of the heat-treated microspheres in a simulated body fluid at pH = 6 and 7 was high enough for clinical application of intra-arterial radiotherapy. We believe that the present YPO₄ microspheres are useful for intra-arterial radiotherapy of cancer, since they have smooth surfaces and can be activated to β-emitters by neutron bombardment.

ACKNOWLEDGMENTS

This work was supported by Funds for Promoting Science and Technology under the Program for Exploring Advanced Interdisciplinary Frontiers, The Ministry of Education, Culture, Sports, Science and Technology, Japan, and by a Grant-in-Aid for Scientific Research (B), Japan Society for the Promotion of Science (No. 22300613), The Ministry of Education, Culture, Sports, Science and Technology, Japan.

REFERENCES

1. Nicolay NH, Berry DP, Sharma RA. Liver metastases from colorectal cancer: Radioembolization with systemic therapy. *NatureRevClinOncol* 2009;6:687–697.
2. Kerr SH, Kerr DJ. Novel treatments for hepatocellular cancer. *CancerLett* 2009;286:114–120.
3. Hyatt MJ, Day DE. Glass properties in the yttria-alumina-silica system. *JAmCeramSoc* 1987;70:283–287.
4. Ehrhardt GJ, Day DE. Therapeutic use of ⁹⁰Y microspheres. *JNuclMed* 1987;14:233–242.
5. Erbe EM, Day DE. Chemical durability of Y₂O₃-Al₂O₃-SiO₂ glasses for the *in vivo* delivery of beta radiation. *JBiomedMaterRes* 1993;27:1301–1308.
6. Meade VM, Burton MA, Gray BN, Self GW. Distribution of different sized

- 1
2
3
4 microspheres in experimental hepatic tumors. *EurJCancerClinOncol*
5
6 1987;23:37–41.
7
8 7. Burton MA, Gray BN, Klemp PF, Kelleher DK, Hardy N. Selective internal radiation
9
10 therapy: Distribution of radiation in the liver. *EurJCancerClinOncol*
11
12 1989;25:1487–1491.
13
14 8. Gray BN, Anderson JE, Burton MA, Vanhazel G, Codde J, Morgan C, Klemp P.
15
16 Regression of liver metastases following treatment with Y-90 microspheres.
17
18 *AustNewZealJSurg* 1992;62:105–110.
19
20 9. Shepherd FA, Rotstein LE, Houle S, Yip TCK, Paul K, Sniderman KW. A phase-I
21
22 dose escalation trial of Y-90 microspheres in the treatment of primary
23
24 hepatocellular-carcinoma. *Cancer* 1992;70:2250–2254.
25
26 10. Lau WY, Leung WT, Ho S, Leung NWY, Chan M, Lin J, Metreweli C, Johnson P, Li
27
28 AKC. Treatment of inoperable hepatocellular carcinoma with intrahepatic arterial
29
30 Y-90 microspheres: A phase-I and phase-II study. *BrJCancer* 1994;70:994–999.
31
32 11. Lau WY, Ho S, Leung TWT, Chan M, Ho R, Johnson PJ, Li AKC. Selective internal
33
34 radiation therapy for nonresectable hepatocellular carcinoma with intraarterial
35
36 infusion of ⁹⁰yttrium microspheres. *IntJRadiatOncolBiolPhys* 1998;40:583–592.
37
38 12. Campbell AM, Bailey IH, Burton MA. Analysis of the distribution of intra-arterial
39
40 microspheres in human liver following hepatic yttrium-90 microsphere therapy.
41
42 *PhysMedBiol* 2000;45:1023–1033.
43
44 13. Stubbs RS, Cannan RJ, Mitchell AW. Selective internal radiation therapy with
45
46 ⁹⁰yttrium microspheres for extensive colorectal liver metastases. *JGastroSurg*
47
48 2001;5:294–302.
49
50 14. Gray B, Van Hazel G, Hope M, Burton M, Moroz P, Anderson J, Gebski V.
51
52 Randomised trial of SIR-Spheres[®] plus chemotherapy vs. chemotherapy alone for
53
54 treating patients with liver metastases from primary large bowel cancer. *AnnOncol*
55
56 2001;12:1711–1720.
57
58 15. Salem R, Thurston KG, Carr BI, Goin JE, Geschwind JFH. Yttrium-90
59
60 microspheres: Radiation therapy for unresectable liver cancer. *JVascIntervRadiol*

- 1
2
3
4 2002;13:S223–S229.
- 5
6 16. Kennedy AS, Nutting C, Coldwell D, Gaiser J, Drachenberg C. Pathologic
7 response and microdosimetry of Y-90 microspheres in man: Review of four
8 explanted whole livers. *InterJRadiatOncolBiolPhys* 2004;60:1552–1563.
- 9
10
11
12 17. Geschwind JFH, Salem R, Carr BI, Soulen MC, Thurston KG, Goin KA, Van
13 Buskirk M, Roberts CA, Goin JE. Yttrium-90 microspheres for the treatment of
14 hepatocellular carcinoma. *Gastroenterology* 2004;127:S194–S205.
- 15
16
17
18 18. Salem R, Lewandowski R, Roberts C, Goin J, Thurston K, Abouljoud M, Courtney
19 A. Use of yttrium-90 glass microspheres (TheraSphere) for the treatment of
20 unresectable hepatocellular carcinoma in patients with portal vein thrombosis.
21 *JVascIntervRadiol* 2004;15:335–345.
- 22
23
24
25
26 19. Salem R, Lewandowski RJ, Atassi B, Gordon SC, Gates VL, Barakat O, Sergie Z,
27 Wong CYO, Thurston KG. Treatment of unresectable hepatocellular carcinoma
28 with use of Y-90 microspheres (TheraSphere): Safety, tumor response, and
29 survival. *JVascIntervRadiol* 2005;16:1627–1639.
- 30
31
32
33
34 20. Murthy R, Nunez R, Szklaruk J, Erwin W, Madoff DC, Gupta S, Ahrar K, Wallace
35 MJ, Cohen A, Coldwell DM, Kennedy AS, Hicks ME. Yttrium-90 microsphere
36 therapy for hepatic malignancy: Devices, indications, technical considerations,
37 and potential complications. *Radiographics* 2005;25:S41–S56.
- 38
39
40
41
42 21. Murthy R, Xiong H, Nunez R, Cohen AC, Barron B, Szklaruk J, Madoff DC, Gupta
43 S, Wallace MJ, Ahrar K, Hicks ME. Yttrium 90 resin microspheres for the
44 treatment of unresectable colorectal hepatic metastases after failure of multiple
45 chemotherapy regimens: Preliminary results. *JVascIntervRadiol*
46 2005;16:937–945.
- 47
48
49
50
51 22. Avila MA, Berasain C, Sangro B, Prieto J. New therapies for hepatocellular
52 carcinoma. *Oncogene* 2006;25:3866–3884.
- 53
54
55
56
57 23. Salem R, Thurston KG. Radioembolization with ⁹⁰Yttrium microspheres: A
58 state-of-the-art brachytherapy treatment for primary and secondary liver
59 malignancies: Part 1: Technical and methodologic considerations.
60

- JVasIntervRadiol 2006;17:1251–1278.
24. Salem R, Thurston KG. Radioembolization with ⁹⁰Yttrium microspheres: A state-of-the-art brachytherapy treatment for primary and secondary liver malignancies: Part 2: Special topics. JVasIntervRadiol 2006;17:1425–1439.
25. Salem R, Thurston KG. Radioembolization with yttrium-90 microspheres: A state-of-the-art brachytherapy treatment for primary and secondary liver malignancies: Part 3: Comprehensive literature review and future direction. JVasIntervRadiol 2006;17:1571–1593.
26. Kennedy AS, Coldwell D, Nutting C, Murthy R, Wertman DE, Loehr SP, Overton C, Meranze S, Niedzwiecki J, Sailer S. Resin Y-90-microsphere brachytherapy for unresectable colorectal liver metastases: Modern USA experience. InterJRadiatOncolBiolPhys 2006;65:412–425.
27. Kennedy A, Nag S, Salem R, Murthy R, McEwan AJ, Nutting C, Benson A, Espat J, Bilbao JI, Sharma RA, Thomas JP, Coldwell D. Recommendations for radioembolization of hepatic malignancies using yttrium-90 microsphere brachytherapy: A consensus panel report from the Radioembolization Brachytherapy Oncology Consortium. IntJRadiatOncolBiolPhys 2007;68:13–23.
28. Hilgard P, Hamami M, El Fouly A, Scherag A, Muller S, Ertle J, Heusner T, Cicinnati VR, Paul A, Bockisch A, Gerken G, Antoch G. Radioembolization with yttrium-90 glass microspheres in hepatocellular carcinoma: European experience on safety and long-term survival. Hepatology 2010;52:1741–1749.
29. Kawashita M, Shineha R, Kim HM, Kokubo T, Inoue Y, Araki N, Nagata Y, Hiraoka M, Sawada Y. Preparation of ceramic microspheres for in situ radiotherapy of deep-seated cancer. Biomaterials 2003;24:2955–2963.
30. Kawashita M, Takayama Y, Kokubo T, Takaoka GH, Araki N, Hiraoka M. Enzymatic preparation of hollow yttrium oxide microspheres for in situ radiotherapy of deep-seated cancer. JAmCeramSoc 2006;89:1347–1351.
31. Kawashita M, Matsui N, Li Z, Miyazaki T. Preparation of porous yttrium oxide microparticles by gelation of ammonium alginate in aqueous solution containing

- yttrium ions. *J Mater Sci Mater Med* 2010;21:1837–1843.
32. Gao W, Liu L, Teng GJ, Feng GS, Tong GS, Gao NR. Internal radiotherapy using ^{32}P colloid or microsphere for refractory solid tumors. *Ann Nucl Med* 2008;22:653–660.
33. Wang XM, Yin ZY, Yu RX, Peng YY, Liu PG, Wu GY. Preventive effect of regional radiotherapy with phosphorus-32 glass microspheres in hepatocellular carcinoma recurrence after hepatectomy. *World J Gastroenterol* 2008;14:518–523.
34. Di W, Wang X, Chen B, Lu S, Zhao X. Effect of OH^- on the luminescent efficiency and lifetime of Tb^{3+} -doped yttrium orthophosphate synthesized by solution precipitation. *J Phys Chem B* 2005;109:13154–13158.
35. Miyazaki T, Kai T, Ishida E, Kawashita M, Hiraoka M. Fabrication of yttria microcapsules for radiotherapy from water/oil emulsion. *J Ceram Soc Jpn* 2010;118:479–482.
36. Cho SB, Nakanishi K, Kokubo T, Soga N, Ohtsuki C, Nakamura T, Kitsugi T, Yamamuro T. Dependence of apatite formation on silica gel on its structure: Effect of heat treatment. *J Am Ceram Soc* 1995;78:1769–1774.
37. Hiraoka M, Hahn GM. Comparison between tumor pH and cell sensitivity to heat in RIF-1 tumors. *Cancer Res* 1989;49:3734–3736.
38. Hezel A, Ros SD. Forbidden transitions in the infra-red spectra of tetrahedral anions—III. Spectra-structure correlations in perchlorates, sulphates and phosphates of the formula MXO_4 . *Spectrochim Acta* 1966;22:1949–1961.
39. Lucas S, Champion E, Bregiroux D, Bernache-Assollant D, Audubert F. Rare earth phosphate powders $\text{RePO}_4 \cdot n\text{H}_2\text{O}$ ($\text{Re}=\text{La}, \text{Ce}$ or Y)—Part I. Synthesis and characterization. *J Solid State Chem* 2004;177:1302–1311.
40. Briche S, Zambon D, Chadeyron G, Boyer D, Dubois M, Mahiou R. Comparison of yttrium polyphosphate $\text{Y}(\text{PO}_3)_3$ prepared by sol-gel process and solid state synthesis. *J Sol-Gel Sci Technol* 2010;55:41–51.
41. Firsching FH, Brune SN. Solubility products of the trivalent rare-earth phosphates. *J Chem Eng Data* 1991;36:93–95.

1
2
3
4 42. Kawashita M. Ceramic microspheres for biomedical applications.
5
6 IntJApplCeramTech 2005;2:173–183.
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Table legends and figure captions

- 1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
- Table 1 Fraction of yttrium released from the samples into SBF-6, SBF-7, and saline solutions buffered at pH = 6 or 7 at 36.5°C for 21 days.
- Figure 1 XRD patterns of samples before and after heat treatment at different temperatures.
- Figure 2 SEM photographs of samples before and after heat treatment at different temperatures.
- Figure 3 SEM photographs of cross-sections of samples after heat treatment at 1100°C.
- Figure 4 Concentrations of yttrium and phosphorus released from the microspheres heat-treated at 1100°C into SBF-6 or SBF-7 after 21 days, in comparison with those of the original SBF without soaking of the microspheres.
- Figure 5 XRD patterns (a) and SEM photographs (b) of the microspheres heat-treated at 1100°C before and after soaking in SBF-6 or SBF-7 for 21 days.
- Figure 6 FT-IR diffusive spectra of samples before and after soaking in SBF-6 or SBF-7 for 21 days.

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

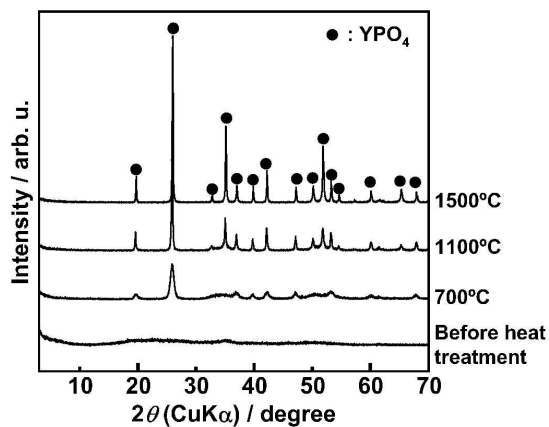


Figure 1 M. Kawashita *et al.*

205x292mm (600 x 600 DPI)

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

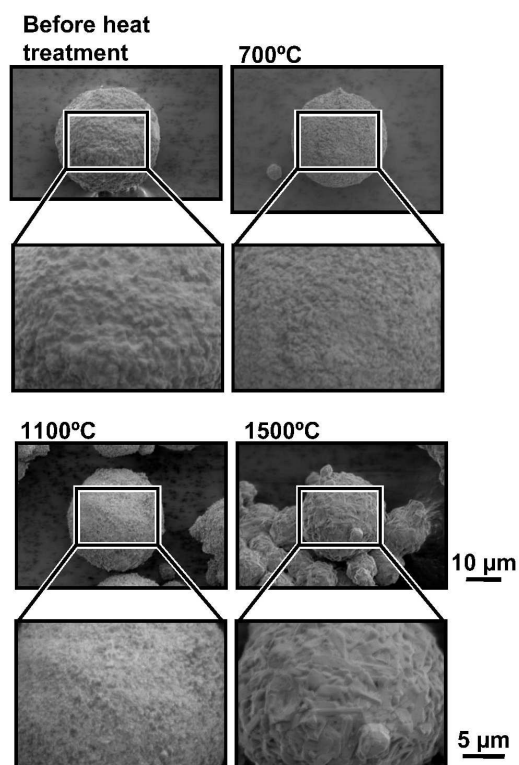


Figure 2 M. Kawashita *et al.*

205x292mm (600 x 600 DPI)

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

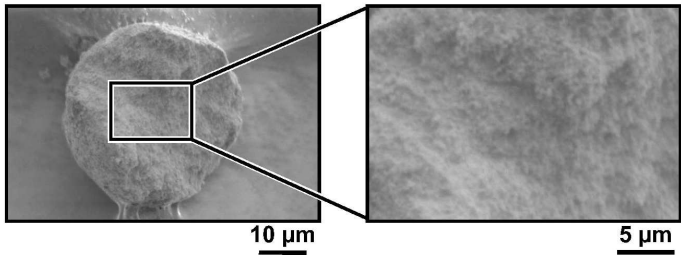


Figure 3 M. Kawashita *et al.*

205x292mm (600 x 600 DPI)

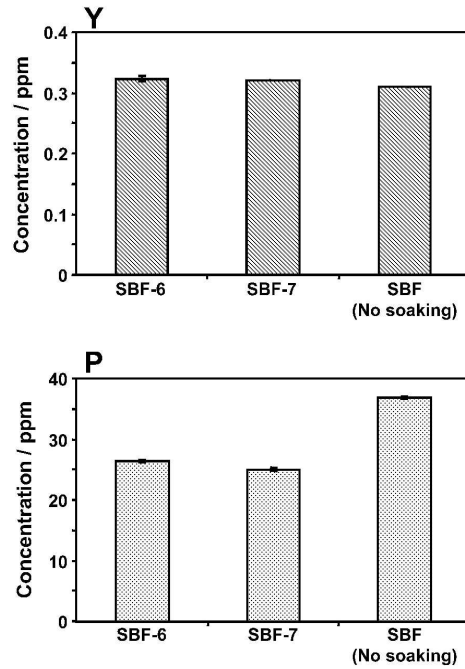
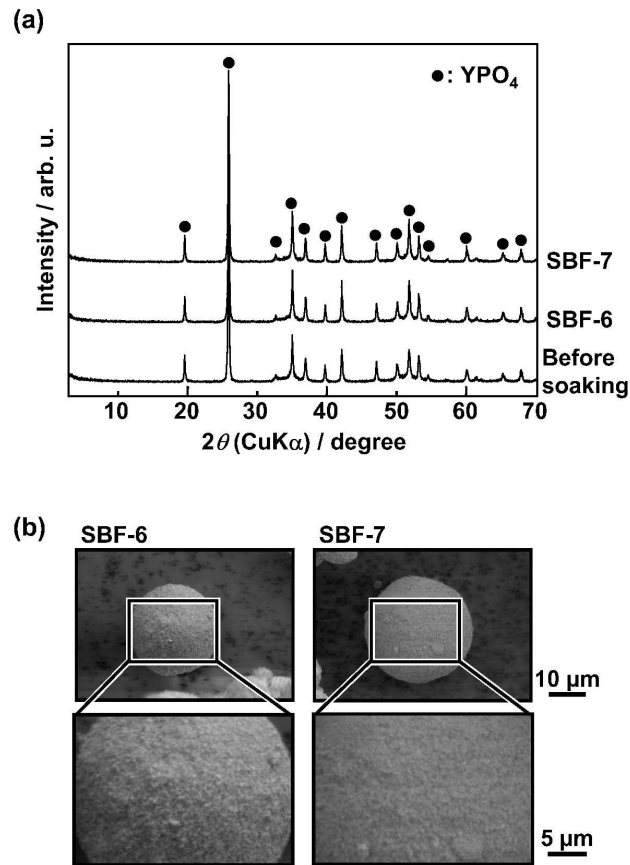


Figure 4 M. Kawashita *et al.*

205x292mm (600 x 600 DPI)

Figure 5 M. Kawashita *et al.*

205x292mm (600 x 600 DPI)

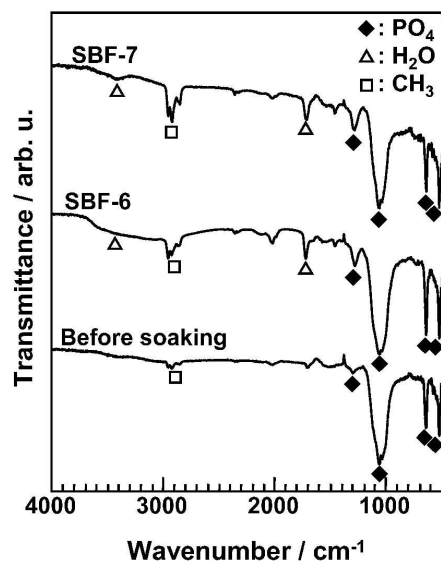


Figure 6 M. Kawashita *et al.*

205x292mm (600 x 600 DPI)

Table 1 Fraction of yttrium released from the samples into SBF-6, SBF-7, and saline solutions buffered at pH = 6 or 7 at 36.5°C for 21 days.

Sample	Immersion fluid	
	SBF-6	SBF-7
Present YPO ₄ microspheres	2.5×10^{-5}	2.5×10^{-5}
Hollow Y ₂ O ₃ microspheres ³⁰⁾	1.8×10^{-3}	1.3×10^{-3}
Porous Y ₂ O ₃ microparticles ³¹⁾	5.6×10^{-3}	5.2×10^{-3}
	Saline solutions buffered at pH = 6	Saline solutions buffered at pH = 7
Dense Y ₂ O ₃ microspheres ²⁹⁾	4×10^{-3}	2×10^{-3}
YPO ₄ -Y ₂ O ₃ microspheres ²⁹⁾	2.5×10^{-3}	undetectable level
Y ₂ O ₃ -Al ₂ O ₃ -SiO ₂ (TheraSphere [®] -type) glass ²⁹⁾	9×10^{-3}	3×10^{-3}