

Nonlinear magnetic response in ruthenocuprates

I. Živković^{1,2,a}, V.P.S. Awana³, and H. Berger⁴¹ Institute of Physics, POB 304, 10000 Zagreb, Croatia² LQM, IPMC, EPFL, 1015 Lausanne, Switzerland³ National Physical Laboratory, Dr. K.S. Krishnan Marg, New Delhi-110012, India⁴ LPRX, IPMC, EPFL, 1015 Lausanne, Switzerland

Received 19 September 2007 / Received in final form 10 April 2008

Published online 22 May 2008 – © EDP Sciences, Società Italiana di Fisica, Springer-Verlag 2008

Abstract. We have performed an investigation of the nonlinear magnetic response in ruthenocuprates. A negative, diverging-like peak at the main magnetic transition T_N in $\text{RuSr}_2\text{RECu}_2\text{O}_8$ ($\text{RE} = \text{Gd}, \text{Y}$) indicates a possible canted antiferromagnetic order. Another well defined feature above T_N points to a blocking of superparamagnetic particles through the T^{-3} dependence of the third harmonic at higher temperatures. Below T_N a nondiverging peak appears, which is strongly affected by the addition of 10% of Cu ions in the RuO_2 planes. In $\text{RuSr}_2\text{RE}_{2-x}\text{Ce}_x\text{Cu}_2\text{O}_{10}$ the main magnetic transition T_M is accompanied by two characteristic temperatures in the third harmonic of the ac susceptibility, in agreement with recent studies from μSR and Mössbauer spectroscopy. We find that the spin-spin correlation temperature is the same in both families of ruthenocuprates.

PACS. 75.20.-g Diamagnetism, paramagnetism, and superparamagnetism – 75.30.Cr Saturation moments and magnetic susceptibilities – 75.40.Gb Dynamic properties (dynamic susceptibility, spin waves, spin diffusion, dynamic scaling, etc.) – 64.75.+g Solubility, segregation, and mixing; phase separation

1 Introduction

A possibility of coexistence of superconducting and ferromagnetic order on the microscopic scale has attracted a lot of attention to ruthenocuprates. Although a respectable amount of experimental work has been published so far, a complete and detailed description of the magnetic properties of the ruthenocuprates is still lacking. The ruthenocuprate family of materials consists of two well investigated phases, $\text{RuSr}_2\text{RECu}_2\text{O}_8$ (Ru1212) and $\text{RuSr}_2\text{RE}_{2-x}\text{Ce}_x\text{Cu}_2\text{O}_{10}$ (Ru1222) and $\text{RuSr}_2\text{RECe}_2\text{Cu}_2\text{O}_{12}$ (Ru1232) ($\text{RE} = \text{rare-earth}$) recently synthesized through a high-pressure-high-temperature (HPHT) procedure [1] with a composition $\text{RuSr}_2\text{RECe}_2\text{Cu}_2\text{O}_{12}$ (Ru1232) ($\text{RE} = \text{rare-earth}$). All ruthenocuprates have similar planar structure with RuO_2 planes responsible for the magnetic ordering and CuO_2 planes for the superconductivity. Between the two CuO_2 planes there is a RE layer (as in $\text{YBa}_2\text{Cu}_3\text{O}_7$, where RuO_2 planes are replaced with CuO chains), a $\text{RE}_{2-x}\text{Ce}_x\text{O}_2$ block or a RECe_2O_4 block for Ru1212, Ru1222 and Ru1232, respectively. Due to the presence of the $\text{RE}_{2-x}\text{Ce}_x\text{O}_2$ block, the Ru1222 system has adjacent Ru ions shifted along the c -axis by $(a+b)/2$ and the unit cell is doubled.

On general grounds, the Ru1212 system shows one magnetic transition around $T_N = 130$ K while the Ru1222

system is characterized by two: one around $T_M^F = 180$ K and the second one around $T_M = 100$ K (depends slightly on the RE/Ce ratio). Although early reports have suggested a ferromagnetic order in Ru1212 [2] and Ru1222 [3], neutron scattering results have indicated the presence of antiferromagnetism [4–6] with an upper limit of $0.1\mu_B$ for a ferromagnetic component. Moreover, the direction of the magnetic moment has been determined to be along the c -axis, contradicting the μSR [2], EPR [7] and NMR [8] measurements where it was concluded that the moments lie in the ab -plane.

To reconcile the proposed hypotheses, a weak ferromagnetism [5,9], a phase separation [10], a combination of two [11] and a spin-glass scenario [12] have been suggested. Recently, a μSR study [13] on the Ru1222 system has shown that at T_M^F only 15% of the material gets ordered. This finding has been confirmed in a Mössbauer study [11]. The rest of the sample orders at T_M . As for the Ru1212 system, Xue and coworkers [10] have showed that substituting the Ru ions with the Cu ions leads to a separation of the ferromagnetic and the antiferromagnetic ordering temperatures. Moreover, a recent investigation of the nonlinear dynamics and the magnetization decay on the Ru1212 ($\text{RE} = \text{Gd}$) composition [14] has revealed an existence of ferromagnetic clusters with an ordering temperature only few Kelvins above the T_N , the antiferromagnetic ordering temperature. A similar observation has

^a e-mail: zivkovic@ifs.hr

been found on the Ru1212Y composition [15], although with a different sign of the third harmonic around T_N , which will be discussed later.

In this paper we extend our investigation of the nonlinear magnetic behavior in ruthenocuprates. We confirm our previous claim that the Ru1212 system, for $RE = \text{Gd}, \text{Y}$, shows a negative third harmonic in the ac susceptibility which is not compatible with a simple AFM ordering of Ru ions. Through a detailed study of the ac field dependence of the ac susceptibility we show that at the main magnetic transition T_N the third harmonic shows diverging-like behavior, where in simple AFM system, no divergence is observed both above and below T_N . Additional features are visible in both pure and doped Ru1212 systems which can be ascribed to a superparamagnetic behavior. The third harmonic for different RE/Ce ratios in the Ru1222 system is qualitatively the same. Two characteristic temperatures around T_M are found which indicates that a long-range ordering sets in at T_M .

2 Experimental details

We have performed the measurements on the following compositions: RuSr₂GdCu₂O₈ (Ru1212Gd), Ru_{0.9}Sr₂YCu_{2.1}O_{7.9} (Ru1212Y) and RuSr₂RE_{2-x}Ce_xCu₂O₁₀ (Ru1222Eu) with x ranging from 0.6 to 1.0. The polycrystalline samples used in this study have been measured previously, see references [3,16,17]. Ac susceptibility measurements were performed using the commercial CryoBIND system with the frequency of the driving field equal to 990 Hz.

Nonlinear susceptibilities can be defined through the expansion of the magnetization M in the power series of the magnetic field H

$$M = M_0 + \chi_1 H + \chi_2 H^2 + \chi_3 H^3 + \dots, \quad (1)$$

where χ_1 is the linear (or a first order) susceptibility and χ_2 and χ_3 are the second and the third order susceptibilities, respectively. Although usually much smaller than the linear component, χ_2 and χ_3 often provide additional information about the investigated system. It has been shown that the divergence of χ_3 characterizes the spin-glass transition [18]. It has been used to distinguish spin-glasses from superparamagnets [19–21], both showing similar behavior in the linear component χ_1 . For long-range-ordered systems χ_3 shows divergence on both sides of T_C in ferromagnets [18,22–24], while for antiferromagnets χ_3 has a nondiverging, asymmetric shape at the transition with a positive sign of χ_3 below T_N [18,25–27].

Even order susceptibilities vanish when the magnetization has inversion symmetry with respect to the magnetic field applied. χ_2 has been used to provide the evidence of the coexistence of the ferromagnetic and glassy behavior in reentrant spin-glass systems [28] and doped cobalt-based perovskites [29].

When an ac field $H = H_0 \cos \omega t$ with a frequency ω is applied, an induced voltage in the coils detected with a

lock-in amplifier involves higher harmonic terms in addition to the first harmonic:

$$\Delta V \propto -\frac{dM}{dt} \propto \omega H_0 \left[\chi_1^{exp} \sin \omega t + \chi_2^{exp} H_0 \sin 2\omega t + \frac{3}{4} \chi_3^{exp} H_0^2 \sin 3\omega t + \dots \right]. \quad (2)$$

The harmonics are related to the higher-order susceptibilities through the following relations:

$$\begin{aligned} \chi_1^{exp} &= \chi_1 + \frac{3}{4} \chi_3 H_0^2 + \frac{5}{8} \chi_5 H_0^4 + \dots, \\ \chi_2^{exp} H_0 &= \chi_2 H_0 + \chi_4 H_0^3 + \frac{15}{16} \chi_6 H_0^5 + \dots, \\ \frac{3}{4} \chi_3^{exp} H_0^2 &= \frac{3}{4} \chi_3 H_0^2 + \frac{15}{16} \chi_5 H_0^4 + \frac{63}{64} \chi_7 H_0^6 + \dots \end{aligned} \quad (3)$$

For small amplitudes H_0 we can put $\chi_1 = \chi_1^{exp}$, $\chi_2 = \chi_2^{exp}$ and $\chi_3 = \chi_3^{exp}$. There are no general rules as how large H_0 is allowed to be before higher order terms should be taken into account. The best option is to use as small H_0 as possible.

As explained above, the sign of the third harmonic is often more important in determining the qualitative aspects of the material under investigation than the absolute magnitude of the signal. Therefore, we have checked the sign of χ_3 by measuring the triangular wave as an input signal for the lock-in amplifier [22]. In addition to that, the sign is also verified by observing the response from the superparamagnetic particles which should always be negative (see the following section).

Measurements for the ac field dependence of the third harmonic (Fig. 3) have been performed by measuring the signal in a temperature window around the peak since the maximum shift as the ac field is increased.

3 Results and discussion

3.1 Ru1212

We have investigated the Ru1212 system containing two rare-earth elements, Gd and Y. The real part of the ac susceptibility for the two systems is shown in Figure 1a. Ru1212Gd shows a somewhat larger susceptibility than Ru1212Y with a peak positioned at $T_N = 135$ K. For Ru1212Y the peak is more rounded with a maximum value around 140 K. The imaginary part of the ac susceptibility is displayed in the inset of Figure 1a. A sharp peak is seen for Ru1212Gd system, while for Ru1212Y there are two broad maximums located around 110 K and 180 K, with a kink at 140 K where χ_1' has a maximum.

Figure 1b shows the nonlinear susceptibility for Ru1212Gd measured in various ac fields. Three distinct features can be noticed, which occur at $T_1 = 152$ K, $T_2 = 137$ K and $T_3 = 131$ K. In the inset of Figure 1b the peak at T_1 is shown enlarged. For small fields T_1 is barely visible and for larger fields it gets smeared out due to the growth of the peaks at T_2 and T_3 . The peak at T_2 is

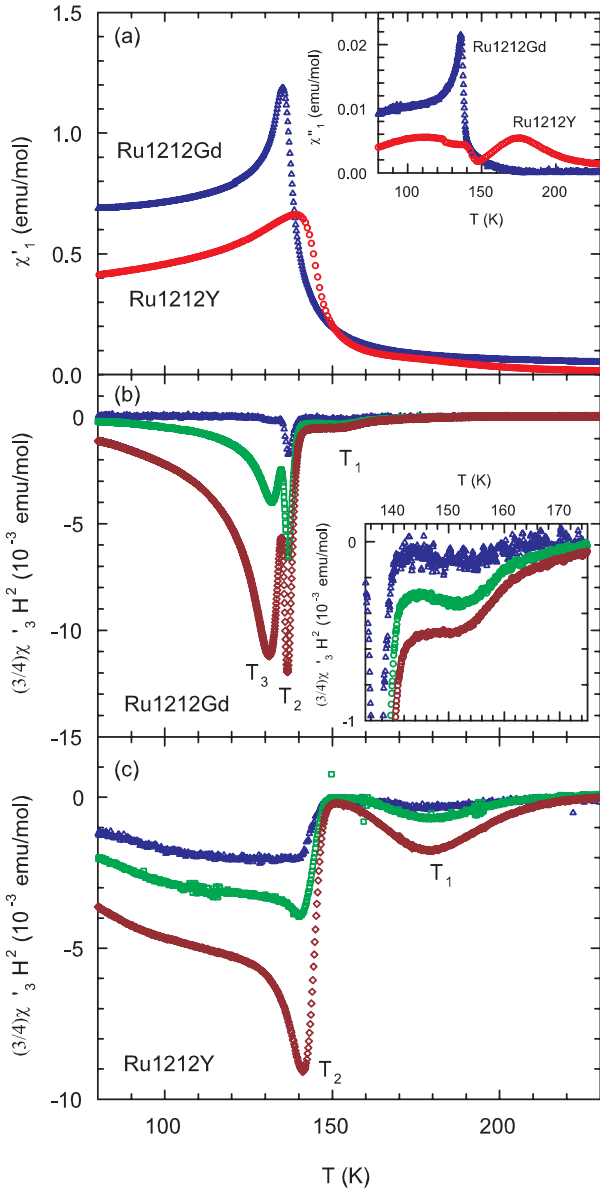


Fig. 1. (Color online) (a) Temperature dependence of the real part of the ac susceptibility for Ru1212Gd and Ru1212Y systems measured with $H_{AC} = 1$ Oe. The inset shows the imaginary part. (b) Temperature dependence of the third harmonic of the ac susceptibility for the Ru1212Gd system. From top to bottom $H_{AC} = 3, 10, 20$ Oe. Inset: enlarged view around T_1 . (c) Temperature dependence of the third harmonic for the Ru1212Y system. From top to bottom $H_{AC} = 5, 10, 20$ Oe.

very sharp for all the fields applied but it overlaps with the feature at T_3 as the field increases. T_3 peak shows a rapid growth as the field is increased, with a long tail below the temperature where the minimum occurs.

In Figure 1c the third harmonic for the Ru1212Y system is presented. A broad maximum around 180 K has been attributed to the formation of the superparamagnetic particles [15]. This feature leaves a visible imprint in the first harmonic as well (Fig. 1a). On the other hand, in Ru1212Gd neither χ'_1 nor χ''_1 show visible deviation at T_1 .

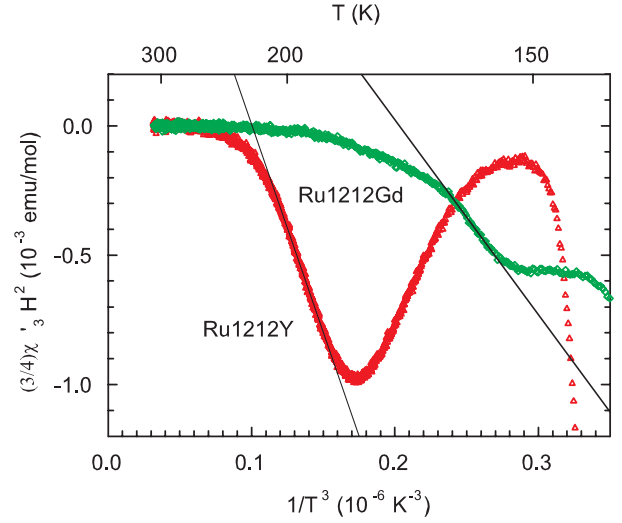


Fig. 2. (Color online) T^{-3} dependence of χ'_3 for Ru1212Y and Ru1212Gd measured in 10 Oe and 20 Oe, respectively. Solid lines represent the best fit to Wohlfarth's model (see text).

Below 150 K χ'_3 starts to grow (in negative values) with a kink at 140 K (where a maximum in χ'_1 is located) for small fields. As the field is increased, a peak develops at a temperature slightly above 140 K with a tail for lower T . No T_3 peak is observed in the Ru1212Y system. Taking into account that the RuO₂ planes in the Ru1212Y system investigated in this paper are slightly disordered due to the doping with extra Cu ions, it is naturally to conclude that the features observed at T_1 and T_3 are intrinsic to Ru1212 ruthenocuprate (as seen for the Ru1212Gd composition).

It has been shown [20] that the existence of the superparamagnetic particles can be verified through the T^{-3} dependence of χ'_3 . According to the Wohlfarth's superparamagnetic blocking model [30], χ'_1 of the assembly of superparamagnetic particles follows a Curie law above the blocking temperature T_B while χ'_3 shows negative T^{-3} dependence,

$$\chi'_1 = \frac{n \langle \mu \rangle}{3} \frac{\langle \mu \rangle}{k_B T} \quad (4)$$

$$\chi'_3 = -\frac{n \langle \mu \rangle}{45} \left(\frac{\langle \mu \rangle}{k_B T} \right)^3, \quad (5)$$

where n is the number of particles per unit volume, $\langle \mu \rangle$ is the average magnetic moment of the single particle and k_B is the Boltzmann constant. In Figure 2 we show appropriate plots for Ru1212Gd and Ru1212Y. The linear dependence of χ'_3 on T^{-3} is found only in a small temperature interval: between 188 K and 203 K for Ru1212Y and between 156 K and 161 K for Ru1212Gd. Although in conventional superparamagnetic systems the particle's internal spin-spin correlation temperature is much higher than the blocking temperature T_B [19,31], it has been shown recently [32] that for Li_{0.5}Ni_{0.5}O a similar behavior occurs with a 10 K wide temperature interval where the third harmonic is linear in T^{-3} . We are aware that a 5 K interval observed in the Ru1212 system is probably too small

and it can serve only as an indication. What is important is that a doped system Ru1212Y shows qualitatively the same behavior as a pure system ($RE = \text{Gd}$) corroborating the hypothesis that these features are intrinsic to material and that they are not the consequence of the existence of impurities.

From equations (4, 5) one can extract the average magnetic moment of the superparamagnetic particle [19]. However, due to the presence of the ordering at T_N and the paramagnetic contribution from the Gd ions (in the Ru1212Gd system), it was in this case not possible to extract the magnetic moment.

It is indicative that for the Ru1212Y composition, for which 10% of Ru ions have been replaced by Cu ions, T_1 peak is larger than in the stoichiometric Ru1212Gd composition and has shifted to higher temperatures. The same happens for the first harmonic of Ru1212Y (see Fig. 1). This suggests that the incorporation of Cu ions in the RuO₂ plane enhances the formation of superparamagnetic particles. It doesn't affect the main transition since T_2 shows the same behavior for both compositions.

χ'_3 gradually vanishes at higher temperatures (≈ 250 – 280 K). This applies for both investigated Ru1212 systems, indicating a common mechanism behind the build-up of correlations.

In both Ru1212 RE systems ($RE = \text{Gd}, \text{Y}$) investigated here, the third harmonic remains negative, contrary to the report of Cimberle and coworkers [14]. In reference [14] two positive peaks have been observed with the interpretation that there are one positive and one negative peak, the negative one following the positive peak. The positive peak has been ascribed to an AFM order while the negative peak has been attributed to the blocking of the superparamagnetic particles [14]. The close inspection reveals that the only difference between reference [14] and our results lies in the sign of the third harmonic, since the two peaks from reference [14] are the T_2 and T_3 peaks from Figure 1b.

The detailed ac field dependence (Figs. 3a, 3b) shows that the T_2 and T_3 peaks have substantially different behavior in the small field regime, which has not been probed in reference [14]. T_2 shows a divergent-like behavior, while T_3 starts to decrease below ≈ 8 Oe and is not observable below 2 Oe. Similar ac field dependence has been observed in reference [14] (for fields above 7 Oe), except for the sign, but interpreted as a negative peak following the positive one. We have checked our setup applying the triangular wave to the lock-in amplifier to confirm the correct sign of the third harmonic. In addition, the existence of T_1 in the Ru1212 system with a T^{-3} dependence indicates an occurrence of superparamagnetic particles. There is no doubt that this results in a *negative* χ_3 (Eq. (5)), as reproduced in our measurements. T_1 is a natural explanation for the occurrence of blocked superparamagnetic particles which gives rise to time relaxations of magnetization [14]. We may assume that the phase of the third harmonic in reference [14] was simply changed by 180 degrees, either before the measurement or during the data analysis.

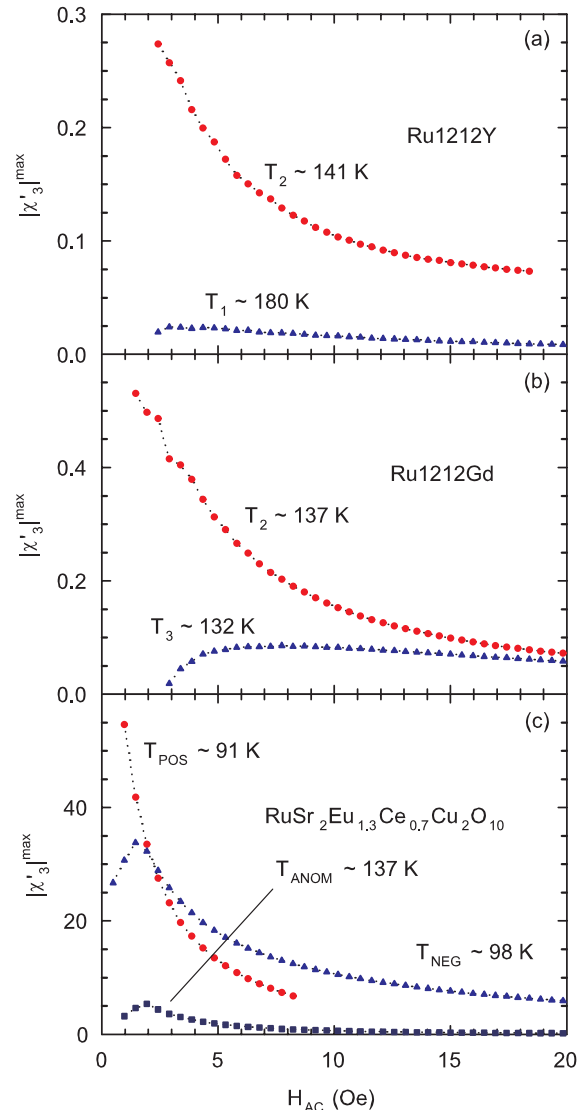


Fig. 3. (Color online) ac field dependence of the amplitude of the peaks in χ_3 for various ruthenocuprates. The peaks shift in temperature as the ac field is increased and the labels correspond to the low-field value. Dotted lines are guides for the eye.

The main magnetic transition in the Ru1212 system is characterized by a negative, diverging peak at T_2 for both compositions investigated. Due to the presence of the adjacent peaks and relatively small signal, we were unable to perform the critical analysis which would allow us to determine to which class this transition belongs. Divergence in the limit of $H_{AC} \rightarrow 0$ indicates a long-range ordered magnetic state. This line of reasoning has been used before to discriminate between a spin-glass and a superparamagnetic system [21,33]. Also, investigation of ferromagnets in the limit of $H_{AC} \rightarrow 0$ showed [24] divergence on both sides of T_C . The negative character of T_2 peak is in disagreement with the proposed C-type AFM system [4] for which it is expected to show a positive, nondiverging third harmonic for $T < T_N$ and vanishingly small signal for $T > T_N$ [18,27]. On the other hand, it

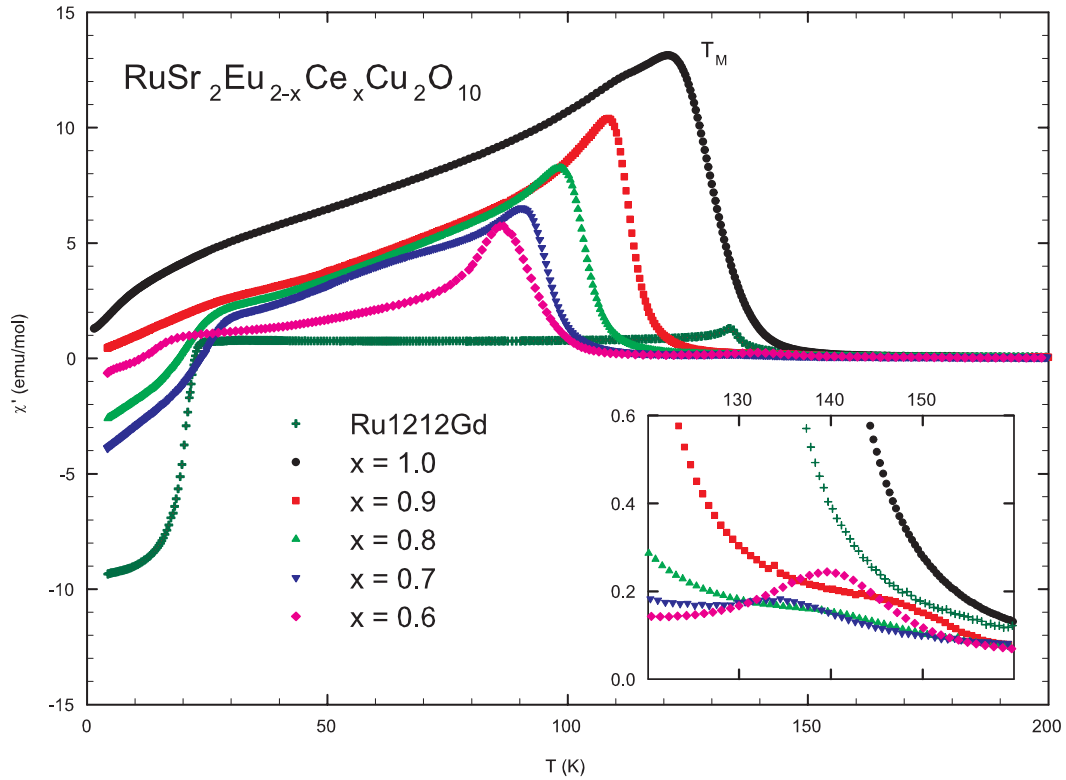


Fig. 4. (Color online) The first harmonic for Ru1222Eu and Ru1212Gd compositions. Inset: enlarged temperature window where the anomaly for the Ru1222 system occurs. No systematic behavior has been observed, either in the temperature or in the size of the anomaly.

has been shown [27] that canted AFM systems diverge negatively on both sides of the transition. In addition, another well defined peak has been observed in [27] below the transition, which has been ascribed to an interaction of domain walls with an external field. We also see the appearance of a peak at T_3 for larger fields. Based on this experimental evidence, we suggest a canted AFM ordering to occur in the Ru1212 system.

Canted AFM structure has been previously proposed for the Ru1212 system [5]. Calculations of the local spin-density approximation of Nakamura and Freeman [34] showed that canted AFM has a slightly lower energy than c-type ordering seen in the neutron scattering. Investigation of ac susceptibility in dc-bias field [35] revealed a metamagnetic transition which was suggested to be between the canted AFM state for fields below the critical field and FM state above.

Since an upper limit for a ferromagnetic component at $0.1 \mu_B$ has been obtained [4], it was hard to accommodate large canting angles to explain three times larger magnetic moment revealed from the magnetization measurements [36]. Xue and coworkers [10] suggested a phase separation into an AFM matrix and FM particles which eliminates the need for a large canting angles of the AFM matrix. This scenario is also supported by our measurements.

The largest difference between the two Ru1212 compositions investigated in this work is revealed below the main

transition. In the Gd-based compound there is another well-defined peak T_3 with a strong ac field dependence while the Y-based compound shows only a broad feature with a modest field dependence. T_3 peak shows nondiverging behavior while the broad feature in Ru1212Y is visible even for smallest measuring fields. Very similar observation has been reported in the case of a canted AFM system [27]. The appearance of a peak below the main transition has been attributed to the effect of the external field on magnetic domains formed by weak ferromagnetic moments. Taking into account the fact that the T_3 peak is missing in Ru1212Y where Cu ions to some extent alter the genuine magnetic order in RuO_2 planes, we conclude that it is intrinsic to the magnetic order in Ru1212.

3.2 Ru1222

The first harmonic in the Ru1222Eu system for the concentrations ranging from $x = 1.0$ to $x = 0.6$, along with Ru1212Gd data, is presented in Figure 4. In general, susceptibility of the Ru1222 system is approximately an order of magnitude larger than for the Ru1212 system. As x decreases both the temperature T_M and the size of the peak decrease, from 121 K for $x = 1.0$ to 85 K for $x = 0.6$. For concentrations with $x \leq 0.8$ there is a kink around 30 K indicating an onset of the superconductivity. Similar results have been obtained through the dc susceptibility measurements [37].

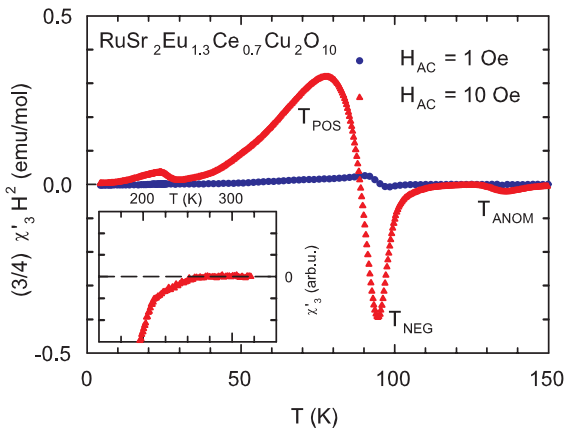


Fig. 5. (Color online) The third harmonic for the Ru1222Eu system with $x = 0.7$ in two different ac fields. The high temperature part is shown in the inset.

In addition, there is an anomaly in the susceptibility curve which occurs between $120 \text{ K} < T_{ANOM} < 140 \text{ K}$, shown in the inset of Figure 4. No correlation has been observed between either the size of the anomaly or the temperature at which anomaly occurs with respect to the nominal Eu/Ce ratio, in agreement with [38]. In μSR study [13], conducted on the $x = 0.6$ composition, it was concluded that the anomaly does not represent a bulk transition. Although all the compositions were prepared at the same time and in the same laboratory, $x = 0.6$ shows particularly strong signal. Also, an overall shape for this concentration is somewhat different from other curves. On the other hand, $x = 1.0$ composition shows monotonic behavior without the apparent anomaly. We will show below that the anomaly is also present for this concentration but can be only observed in the third harmonic, while in the first harmonic it overlaps with the peak at T_M .

The third harmonic for the $\text{RuSr}_2\text{Eu}_{1.3}\text{Ce}_{0.7}\text{Cu}_2\text{O}_{10}$ ($x = 0.7$) composition measured in 1 and 10 Oe is shown in Figure 5. Three distinct magnetic features can be discerned in larger fields: a small negative peak around the temperature where the anomaly in χ_1 has been observed (T_{ANOM}), a negative peak above T_M and a positive peak below T_M . On lowering the temperature the signal becomes smaller, until the superconducting order sets in below 30 K. The third harmonic measurements have been recently used to prove the coexistence of ferromagnetic and superconducting order parameters [39]. For other concentrations the results are very similar, with T_{POS} and T_{NEG} shifting in temperature according to the shift in T_M . In the inset there is an enlarged view of the high temperature part for $H_{AC} = 10 \text{ Oe}$ where we show the disappearance of the third harmonic in the same temperature range as for the Ru1212 system (Fig. 2).

As we have mentioned in the introduction, it is very important to measure the higher order harmonics in as small a field as possible, to be able to use the approximation $\chi_3 = \chi_3^{exp}$ (see Eq. (3)). In Figure 6 we show all the investigated concentrations of the Ru1222Eu system measured in 1 Oe. All the curves show a similar pattern:

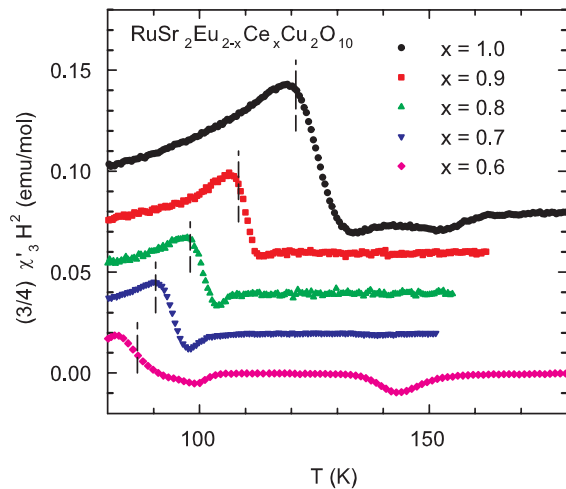


Fig. 6. (Color online) The third harmonic for the Ru1222Eu system measured with 1 Oe. The curves have been vertically displaced for clarity. The vertical dashed lines mark T_M , the maximum in χ_1 .

a positive peak below T_M (vertical dashed lines) and a small negative dip above T_M . This is a strong indication that T_{POS} and T_{NEG} are related to the main magnetic transition T_M . For $x = 0.6$ and $x = 1.0$ T_{ANOM} is already observed for $H_{AC} = 1 \text{ Oe}$.

The occurrence of two characteristic temperatures around the main magnetic transition in the Ru1222 system has been reported in recent investigations by μSR [13] and Mössbauer spectroscopy [11]. These reports showed the existence of two internal magnetic fields appearing around the main magnetic transition T_M . In addition, the existence of the ordering just above T_M has been indicated in our previous reports [40,41]. A temperature dependence of the time relaxations of the ac susceptibility [40] and the peculiar inverted hysteresis [41] has shown that these phenomena originate at a slightly higher temperature than T_M and fully develop below T_M .

With respect to the occurrence of the anomaly, all compositions show the same behavior, even the parent compound ($x = 1.0$). This is important to stress since a recent report [38] indicated that $x = 1.0$ does not show the anomaly. We suggest that the anomaly is not visible in the first harmonic of the ac susceptibility and magnetization due to the higher magnetic transition at T_M for $x = 1.0$. It has been suggested that for $x < 1.0$ the reduction of the Ce content leads to oxygen depletion. Ru^{5+} ions surrounded by oxygen holes reduce to Ru^{4+} , which has been assumed to be related to the occurrence of the anomaly. Our measurements show that if the clustering of Ru^{4+} ions is related to this feature, it is not the Ce content that drives the reduction from Ru^{5+} to Ru^{4+} ions, since the $\text{RuSr}_2\text{EuCeCu}_2\text{O}_{10}$ ($x = 1.0$) compound is stoichiometric. NMR experiments on Ru1212 [8], which is also stoichiometric, indicated the coexistence of Ru^{5+} and Ru^{4+} ions which has been associated with the transfer of electrons from CuO_2 to RuO_2 planes and the occurrence of superconductivity in this compound. We propose that a

similar mechanism might also be present in the Ru1222 system. The transfer of electrons must be weaker than in the Ru1212 system, since $x = 1.0$ and $x = 0.9$ are not superconducting. With further substitution of Eu^{3+} for Ce^{4+} ions additional holes are introduced to CuO_2 planes which induces superconductivity for $x \leq 0.8$.

It is instructive to look at the ac field dependence of characteristic peaks for the Ru1222 system, T_{POS} , T_{NEG} and T_{ANOM} . We have only shown the results for the Ru1222Eu $x = 0.7$ composition but other compositions, including $x = 1.0$, reveal qualitatively similar results. Figure 3c shows that T_{POS} has a diverging character, while T_{NEG} and T_{ANOM} are nondiverging, although this is only evident in fields smaller than 2 Oe, which indicates the importance of the small-field measurements. A very similar observation in an amorphous ferromagnet, $\text{Fe}_5\text{Co}_{50}\text{Ni}_{17-x}\text{Cr}_x\text{B}_{16}\text{Si}_{12}$ with $x = 5$ [24], has been explained invoking a clusterization above the main transition, before the full FM order sets in. This resulted in a negative, nondiverging third harmonic above T_C and a positive, diverging harmonic below T_C . We propose that a similar situation occurs in the Ru1222 system. As shown by μSR study [13], just above T_M a majority of the volume orders and from our results it seems clear that there is no long-range order. Eventually at T_M , where the rest of the sample gets ordered [13], χ_3 diverges indicating a long-range order. This is to be contrasted with recent neutron scattering results on Ru1222, $x = 0.8$ where no long-range order could be measured for the main magnetic phase [42]. Moreover, it is claimed [42] that the ordering at T_M is actually related to the impurity phase of unknown origin and that Ru ions incorporated in the Ru1222 phase do not contribute significantly to the observed magnetic behavior in the Ru1222 system. The systematic change of characteristic temperatures with x in linear and nonlinear magnetic dynamics presented in this report and in previous investigations, with various dopants for Ru ions [38] suggest an intrinsic scenario behind the magnetism in the Ru1222 system. More experiments are needed in order to elucidate the microscopic nature of magnetic ordering in this material.

Some features are not visible in small fields (~ 1 Oe). We show in Figure 7 measurements performed with $H_{AC} = 10$ Oe. The anomaly is now clearly visible for all the concentrations, with the $x = 0.6$ concentration showing the largest signal. For the $x = 1.0$ composition T_{ANOM} overlaps with a large, negative peak at T_{NEG} . Above T_{ANOM} there is another deviation, $170 \text{ K} < T^* < 180 \text{ K}$, which for some concentrations develops into a peak and for others creates only a barely visible shoulder. The most pronounced peak is again seen for the $x = 0.6$ composition. Around the same temperature a formation of superparamagnetic clusters has been proposed from nonlinear magnetization measurements [10] and μSR [13] showed the existence of magnetic order in 15% of the sample below T^* . The weak, negative sign of the third harmonic supports the hypothesis of a minor volume fraction ordering locally and giving rise to magnetism above the main magnetic transition T_M . Due to the small signal and large

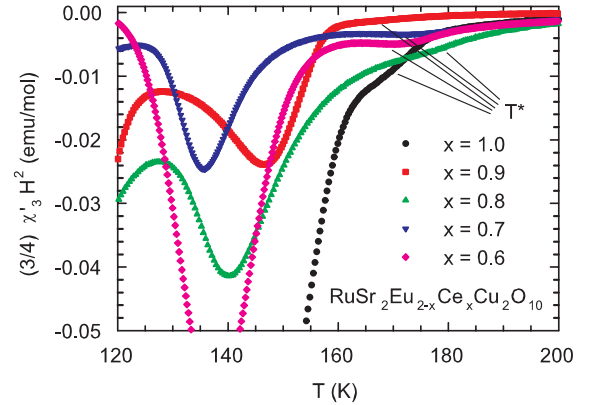


Fig. 7. (Color online) Measurement of the third harmonic with $H_{AC} = 10$ Oe for all the investigated concentrations of the Ru1222Eu system. T_{ANOM} is developed for all the concentrations. $x = 1.0$ has T_{ANOM} and T_{NEG} overlapped.

background from other peaks, we were unable to find an appropriate temperature interval with a T^{-3} dependence, as we have shown for the Ru1212 system (see Fig. 2). The Wohlfarth's model, which predicts a T^{-3} dependence, assumes a constant average moment of the particle (see Eqs. (4, 5)). As suggested in reference [43], due to the different temperature dependence of the FM and AFM interactions inside the clusters, the average magnetic moment is temperature dependent. This implies a nondiverging third harmonic with a temperature dependent slope in the χ_3 versus T^{-3} plot, as in our case.

The origin of the high-temperature ordering continues to be a subject of debate. Except for the obvious intrinsic scenario, an impurity-based explanation has been proposed [38] with Sr-Ru-Cu-O₃ phase showing similar temperature dependence of the coercive field as the Ru1222 system. Cu^{2+} ions are thought to be inhomogeneously distributed in both Ru and Sr sites which causes Sr-Ru-Cu-O₃ phase to act as an independent particle inside the Ru^{5+} matrix. This study has been conducted on a system with a long-range ferromagnetic order where magnetic domains and domain walls play a dominant role in the mechanism behind the coercivity. On the other hand, nanosized particles incorporated in the Ru1222 matrix can be considered as monodomain structures, with a superparamagnetic blocking as the main mechanism generating the coercive field. Although an anisotropy (K) is involved in both processes, a temperature dependence of the coercive field in a bulk system should not be taken as an indicator for nanosized particles. This leaves the intrinsic scenario as a probable mechanism, but we are still missing the microscopic explanation of it.

Other features observed in this report are also unlikely to be related to the presence of impurities. The Ru1212 system has been investigated before [14] and, apart from the sign of the third harmonic, the same features have been observed. Furthermore, through the investigation of $\text{Ru}_{0.9}\text{Sr}_2\text{YCu}_{2.1}\text{O}_{7.9}$ (Ru1212Y) we have shown that upon introduction of a structural disorder due to the incorporation of Cu ions into the RuO_2 planes, the Ru1212

system's predominant ordering at T_2 does not change. On the other hand, the peak at T_2 , which presumably reflects the interaction of domain walls in the canted AFM state with the external field, is strongly influenced with the imposed disorder, indicating that the magnetic response from the Ru1212Gd compound is intrinsic to the Ru1212 system.

In the Ru1222 system all the different RE/Ce ratios show consistent behavior between the first and the third harmonic. T_{POS} and T_{NEG} change in accordance with the change in T_M and in the μ SR experiment [13] it has been shown that this involves more than 90% of the sample's volume. The detection limit of X-ray diffraction measurements for our samples indicates <3% of impurities [3,16,17], confirming that T_{POS} and T_{NEG} are intrinsic to the Ru1222 system. The anomaly around 120 K has been observed in all previously investigated Ru1222 samples and has been linked to the high temperature transition around 180 K [38,43]. Substitution of Ru ions with Mo ions [38] showed that while the main magnetic transition is shifted, the anomaly remains unchanged. If the anomaly is related to some sort of impurities in the Ru1222 system, one would expect drastic changes in position and intensity, which has not been observed. In addition, the higher harmonics are orders of magnitude weaker than the first harmonic and we have shown that the anomaly appears even for the smallest fields used. This strongly implies that the anomaly is intrinsic to the Ru1222 system.

4 Conclusions

Several novel features have been observed in our study of the nonlinear susceptibility of ruthenocuprates. In Ru1212 we have found a negative third harmonic of the ac susceptibility, with a clear separation between the main magnetic transition and the formation of superparamagnetic particles. The divergent-like behavior of the third harmonic at the main magnetic transition indicates a long-range ordered state. Previous reports favored a canonical AFM state with magnetic moments pointing along the c -axis. Our results contradict this hypothesis since canonical AFM systems are expected to show a nondiverging positive third harmonic. We propose that the majority of magnetic moments order in a canted AFM state, in accordance with the neutron diffraction results. The dominant ferromagnetic response comes from the separated, short-range ordered particles which are blocked below a temperature slightly higher than the temperature of the main magnetic transition. The peak appearing below T_N for larger magnetic fields has been ascribed to an interaction between domains of weak ferromagnetic moments and the applied field.

Nonlinear response in the Ru1222 system revealed two characteristic temperatures around T_M , in line with μ SR and Mössbauer results. The characteristic lower temperature T_{POS} coincides with the main magnetic transition T_M seen in the linear response. The divergence of the third harmonic at T_{POS} is an indication of the onset of a long-range order. We have observed a small negative feature in

χ_3 around 180 K for all compositions. This is a possible signature of a minority phase ordering into superparamagnetic particles.

In both ruthenocuprate systems the third harmonic starts to show in the temperature range ≈ 250 – 280 K. Below this temperature short-range correlations bind individual spins into larger clusters giving rise to an observed nonlinearity. It is important to notice that when the third harmonic starts to show a deviation from the Curie-Weiss behavior occurs, which can be crucial when determining a paramagnetic moment from the Curie-Weiss plot.

This work was supported by Croatian Ministry of Science, Education and Sport, project 035-0352843-2845, the funds of a SCOPES from Swiss National Science Foundation and by the Israeli Ministry of Science under the mutual India (DST) – Israel (MST) grant. I. Ž. is grateful to M. Prester, D. Drobac and M.R. Cimberle for fruitful discussions and to I. Felner for providing the samples and reading the manuscript.

References

1. V.P.S. Awana H. Kishan, T. Kawashima, E. Takayama-Muromachi, C.A. Cardoso, J. Appl. Phys. **97**, 10B111 (2005)
2. C. Bernhard, J.L. Tallon, Ch. Niedermayer, Th. Blasius, A. Golnik, E. Brücher, R.K. Kremer, D.R. Noakes, C.E. Stronach, E.J. Ansaldo, Phys. Rev. B **59**, 14099 (1999)
3. I. Felner, U. Asaf, Y. Levi, O. Millo, Phys. Rev. B **55**, R3374 (1999)
4. J.W. Lynn, B. Keimer, C. Ulrich, C. Bernhard, J.L. Tallon, Phys. Rev. B **61**, R14964 (2000)
5. J.D. Jorgensen, O. Chmaissem, H. Shaked, S. Short, P.W. Klamut, B. Dabrowski, J.L. Tallon, Phys. Rev. B **63**, 054440 (2001)
6. A.C. McLaughlin, F. Sher, J.P. Attfield, Nature **436**, 829 (2005); this article has been retracted (A.C. McLaughlin, F. Sher, J.P. Attfield, Nature **437**, 1057 (2005)) but the magnetic structure has been confirmed to be correct as published
7. A. Fainstein, E. Winkler, A. Butera, J.L. Tallon, Phys. Rev. B **60**, R12597 (1999)
8. Y. Tokunaga, H. Kotegawa, K. Ishida, Y. Kitaoka, H. Takagiwa, J. Akimitsu, Phys. Rev. Lett. **86**, 5767 (2001)
9. I. Felner, E. Galstyan, V.P.S. Awana, E. Takayama-Muromachi, Physica C **408-410**, 161 (2004)
10. Y.Y. Xue, B. Lorenz, D.H. Cao, C.W. Chu, Phys. Rev. B **67**, 184507 (2003); Y.Y. Xue, F. Chen, J. Cmaidalka, R.L. Meng, C.W. Chu, Phys. Rev. B **67**, 224511 (2003)
11. I. Felner, E. Galstyan, R.H. Herber, I. Nowik, Phys. Rev. B **70**, 094504 (2004)
12. C.A. Cardoso, F.M. Araujo-Moreira, V.P.S. Awana, E. Takayama-Muromachi, O.F. de Lima, H. Yamauchi, M. Karppinen, Phys. Rev. B **67**, 020407(R) (2003)
13. A. Shengelaya, R. Khasanov, D.G. Eschenko, I. Felner, U. Asaf, I.M. Savić, H. Keller, K.A. Müller, Phys. Rev. B **69**, 024517 (2004)
14. M.R. Cimberle, R. Masini, F. Canepa, G. Costa, A. Vecchione, M. Polichetti, R. Ciancio, Phys. Rev. B **73**, 214424 (2006)

15. I. Živković, V.P.S. Awana, H. Kishan, S. Balamurugan, E. Takayama-Muromachi, I. Felner, *J. Appl. Phys.*, accepted
16. V.P.S. Awana, T. Kawashima, E. Takayama-Muromachi, *Phys. Rev. B* **67**, 172502 (2003)
17. I. Živković, D. Drobac, D. Ariosa, H. Berger, D. Pavuna, M. Prester, *EuroPhys. Lett.* **60**, 917 (2002)
18. S. Fujiki, S. Katsura, *Prog. Theor. Phys.* **58**, 1130 (1981)
19. T. Bitoh, K. Ohba, M. Takamatsu, T. Shirane, S. Chikazawa, *J. Phys. Soc. Jpn* **62**, 2583 (1993)
20. T. Bitoh, K. Ohba, M. Takamatsu, T. Shirane, S. Chikazawa, *J. Magn. Magn. Mater.* **154**, 59 (1996)
21. A. Bajpai, A. Banerjee, *J. Phys.: Condens. Matter* **13**, 637 (2001)
22. T. Sato, Y. Miyako, *J. Phys. Soc. Jpn* **51**, 1394 (1981)
23. T. Bitoh, T. Shirane, S. Chikazawa, *J. Phys. Soc. Jpn* **62**, 2837 (1993)
24. S. Nair, A. Banerjee, *Phys. Rev. B* **68**, 094408 (2003)
25. A.P. Ramirez, P. Coleman, P. Chandra, E. Brück, A.A. Menovsky, Z. Fisk, E. Bucher, *Phys. Rev. Lett.* **68**, 2680 (1992)
26. J. Kushauer, W. Kleemann, *J. Phys.: Condens. Matter* **7**, L1 (1995)
27. N. Narita, I. Yamada, *J. Phys. Soc. Jpn* **65**, 4054 (1996)
28. A. Chakravarti, R. Ranganathan, *Solid State Commun.* **82**, 591 (1992)
29. J. Androulakis, N. Katsarakis, J. Giapintzakis, *J. Appl. Phys.* **91**, 9952 (2002)
30. E.P. Wohlfarth, *Phys. Lett. A* **70**, 489 (1979)
31. W. Luo, S.R. Nagel, T.F. Rosenbaum, R.E. Rosensweig, *Phys. Rev. Lett.* **67**, 2721 (1991)
32. A. Bajpai, A. Banerjee, *Phys. Rev. B* **62**, 8996 (2000)
33. A. Bajpai, A. Banerjee, *Phys. Rev. B* **55**, 12439 (1997)
34. K. Nakamura, A.J. Freeman, *Phys. Rev. B* **66**, 140405(R) (2002)
35. P. Mandal, A. Hassen, J. Hemberger, A. Krimmel, A. Loidl, *Phys. Rev. B* **65**, 144506 (2002)
36. A. Butera, A. Fainstein, E. Winkler, J. Tallon, *Phys. Rev. B* **63**, 054442 (2001)
37. I. Felner, U. Asaf, E. Galstyan, *Phys. Rev. B* **66**, 024503 (2002)
38. I. Felner, E. Galstyan, I. Nowik, *Phys. Rev. B* **71**, 064510 (2005)
39. G.I. Leviev, M.I. Tsindlekht, E.B. Sonin, I. Felner, *Phys. Rev. B* **70**, 212503 (2004)
40. I. Živković, Y. Hirai, B.H. Frazer, M. Prester, D. Drobac, D. Ariosa, H. Berger, D. Pavuna, G. Margaritondo, I. Felner, M. Onellion, *Phys. Rev. B* **65**, 144420 (2002)
41. I. Živković, D. Drobac, M. Prester, *Physica C* **433**, 234 (2006)
42. J.W. Lynn, Y. Chen, Q. Huang, S.K. Goh, G.V.M. Williams, *Phys. Rev. B* **65**, 144420 (2002)
43. S. Garcia, L. Ghivelder, S. Soriano, I. Felner, *Eur. Phys. J. B* **53** 307 (2006)