


# INKJET-PRINTED CONDUCTIVE POLYMER ELECTRODES FOR AC ELECTRO-OSMOSIS


Luca Ribetto, Jérôme Courbat, Alexandra Homsy, Danick Briand, Nico F. de Rooij

Ecole Polytechnique Fédérale de Lausanne (EPFL), Sensors, Actuators and Microsystems Laboratory, Rue Jaquet-Droz 1, 2000 Neuchâtel, Switzerland

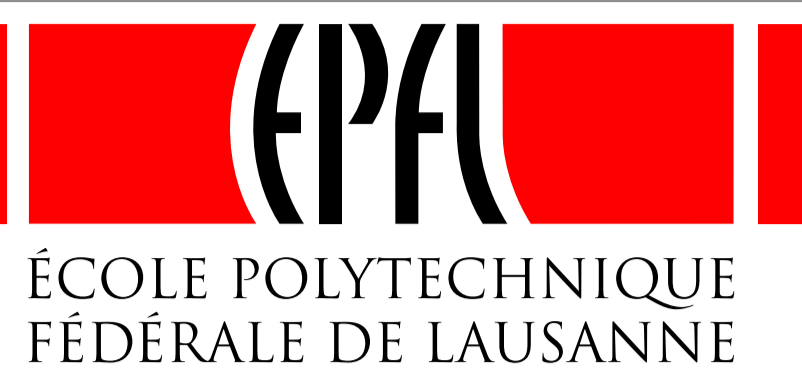

## AC Electro-osmosis

Standalone integrated microfluidic systems require pumping elements. Electro-osmosis (EO) is an effective method of actuating liquids [1,2]. ACEO exploits much lower potentials and, by using alternating fields, overcomes the issues of electrolysis and gas generation [3].

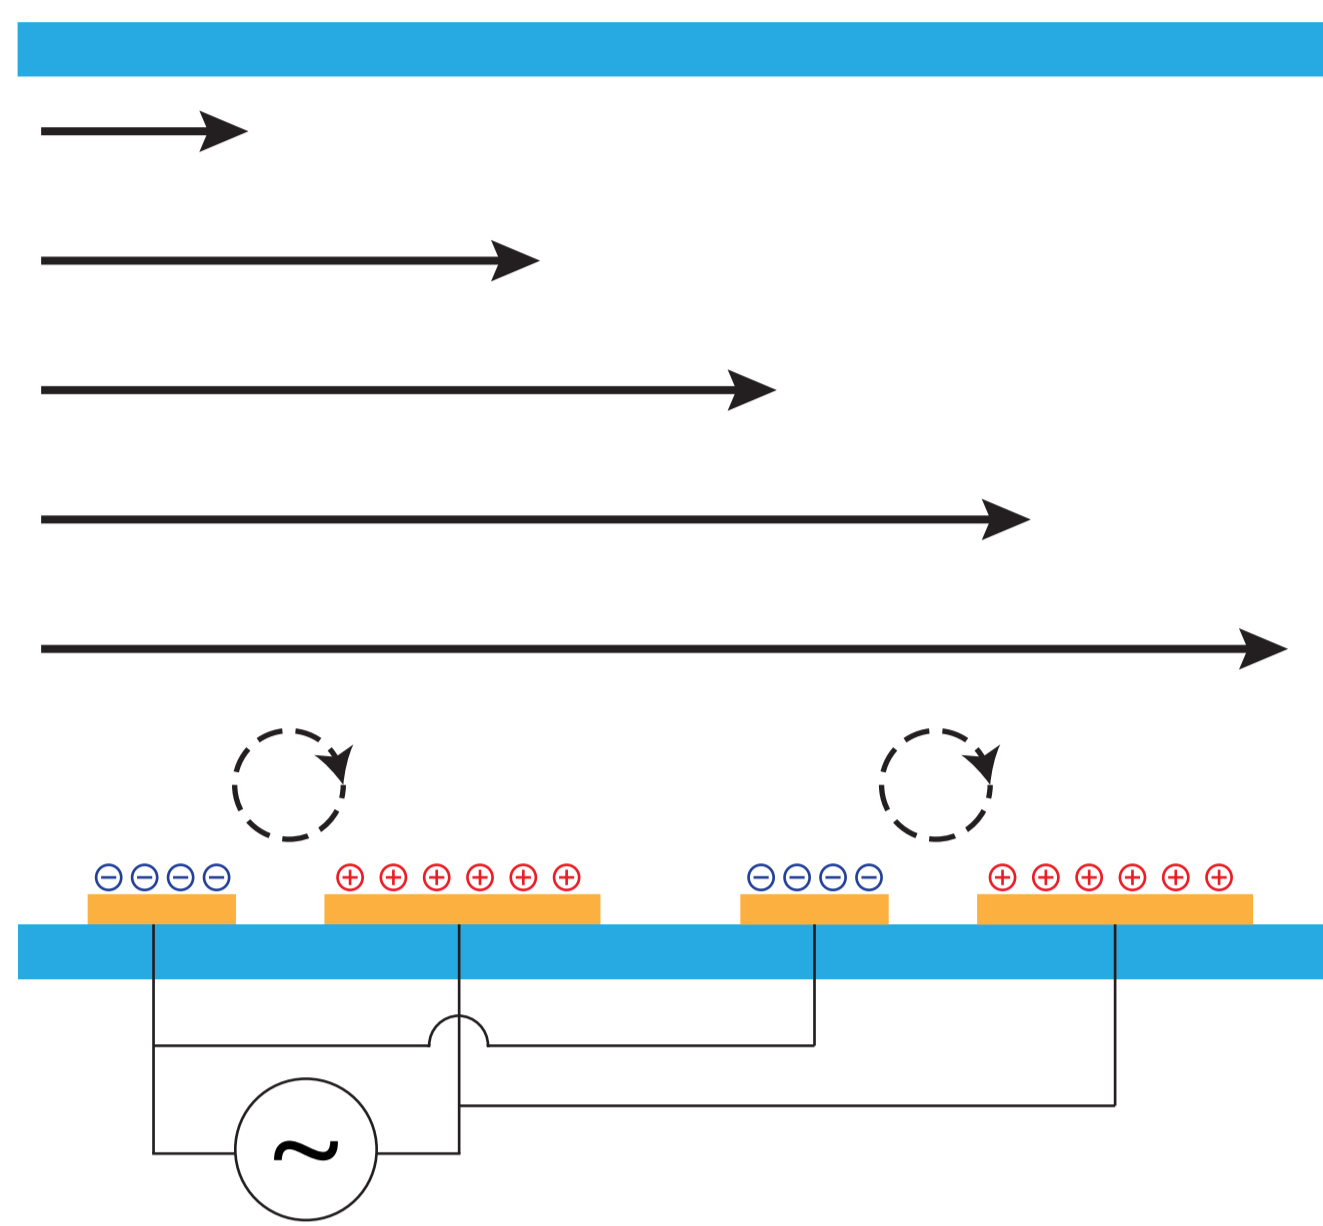

Low-voltage

No gas generation


Good velocity

$$v_{aceo} \sim \int V^2 \frac{(\omega/\omega_0)^2}{(1 + (\omega/\omega_0)^2)^2}$$

PROBLEM: electrolysis at very low frequencies and/or high voltages [4]

## Why using PEDOT electrodes?

Poly(3,4-ethylenedioxythiophene)-poly(styrenesulfonate) (PEDOT:PSS) can withstand DC voltages as high as 100 V without electrolysis [5]. ACEO works fine with micromachined arrays of PEDOT electrodes [6].

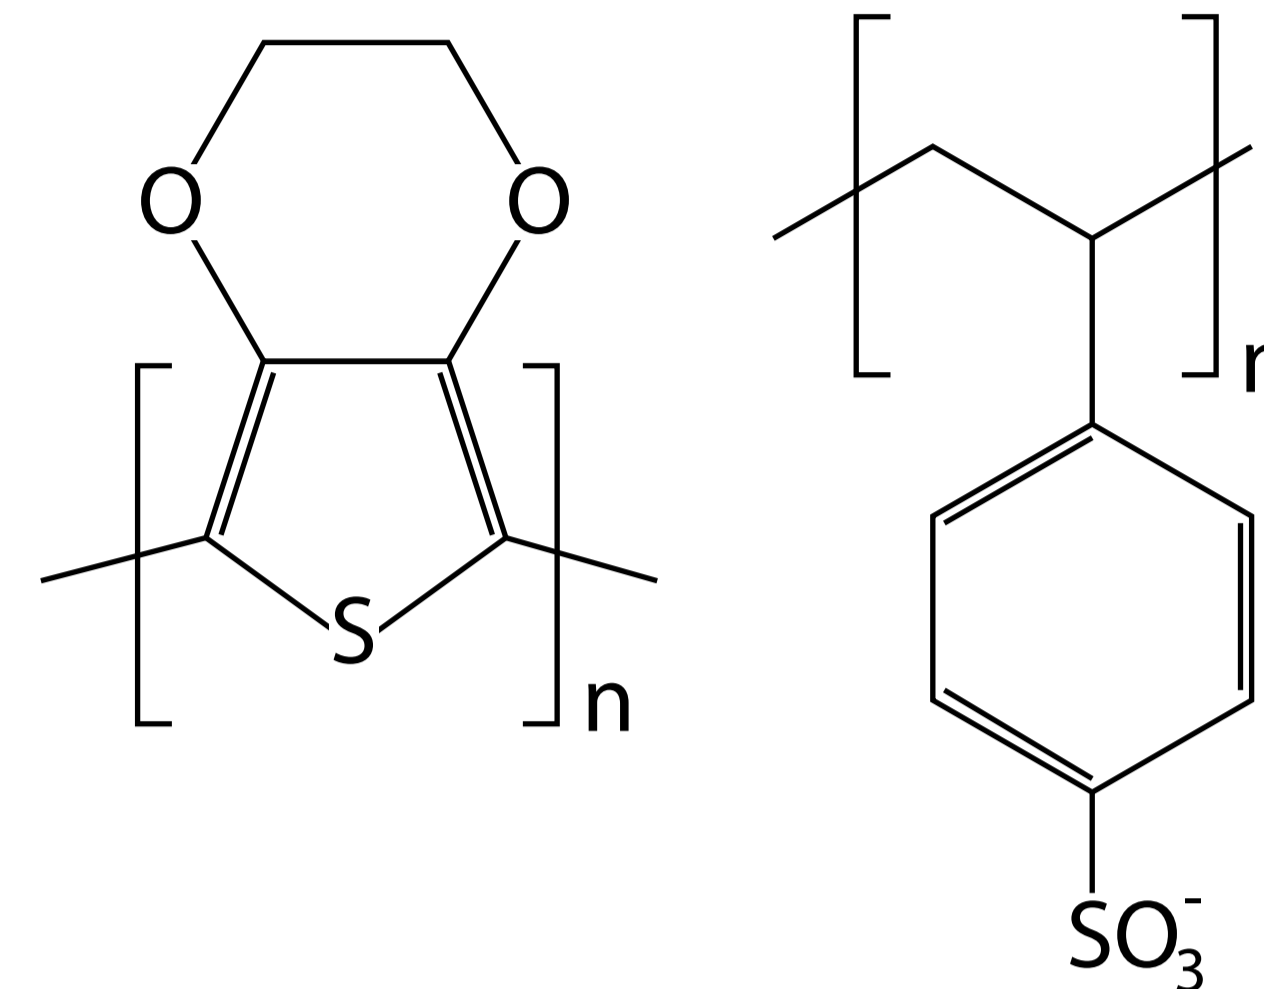


Resists high voltages

Avoids electrolysis

Can be used for ACEO



Printable on plastics

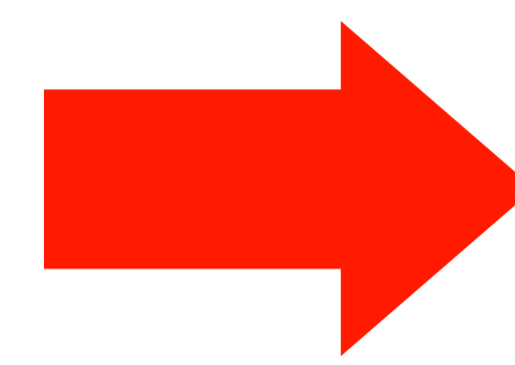

LOW-COST  
GOOD POTENTIAL FOR ACEO


## Inkjet-printing of PEDOT electrodes

### Parallel to print direction (8 layers)

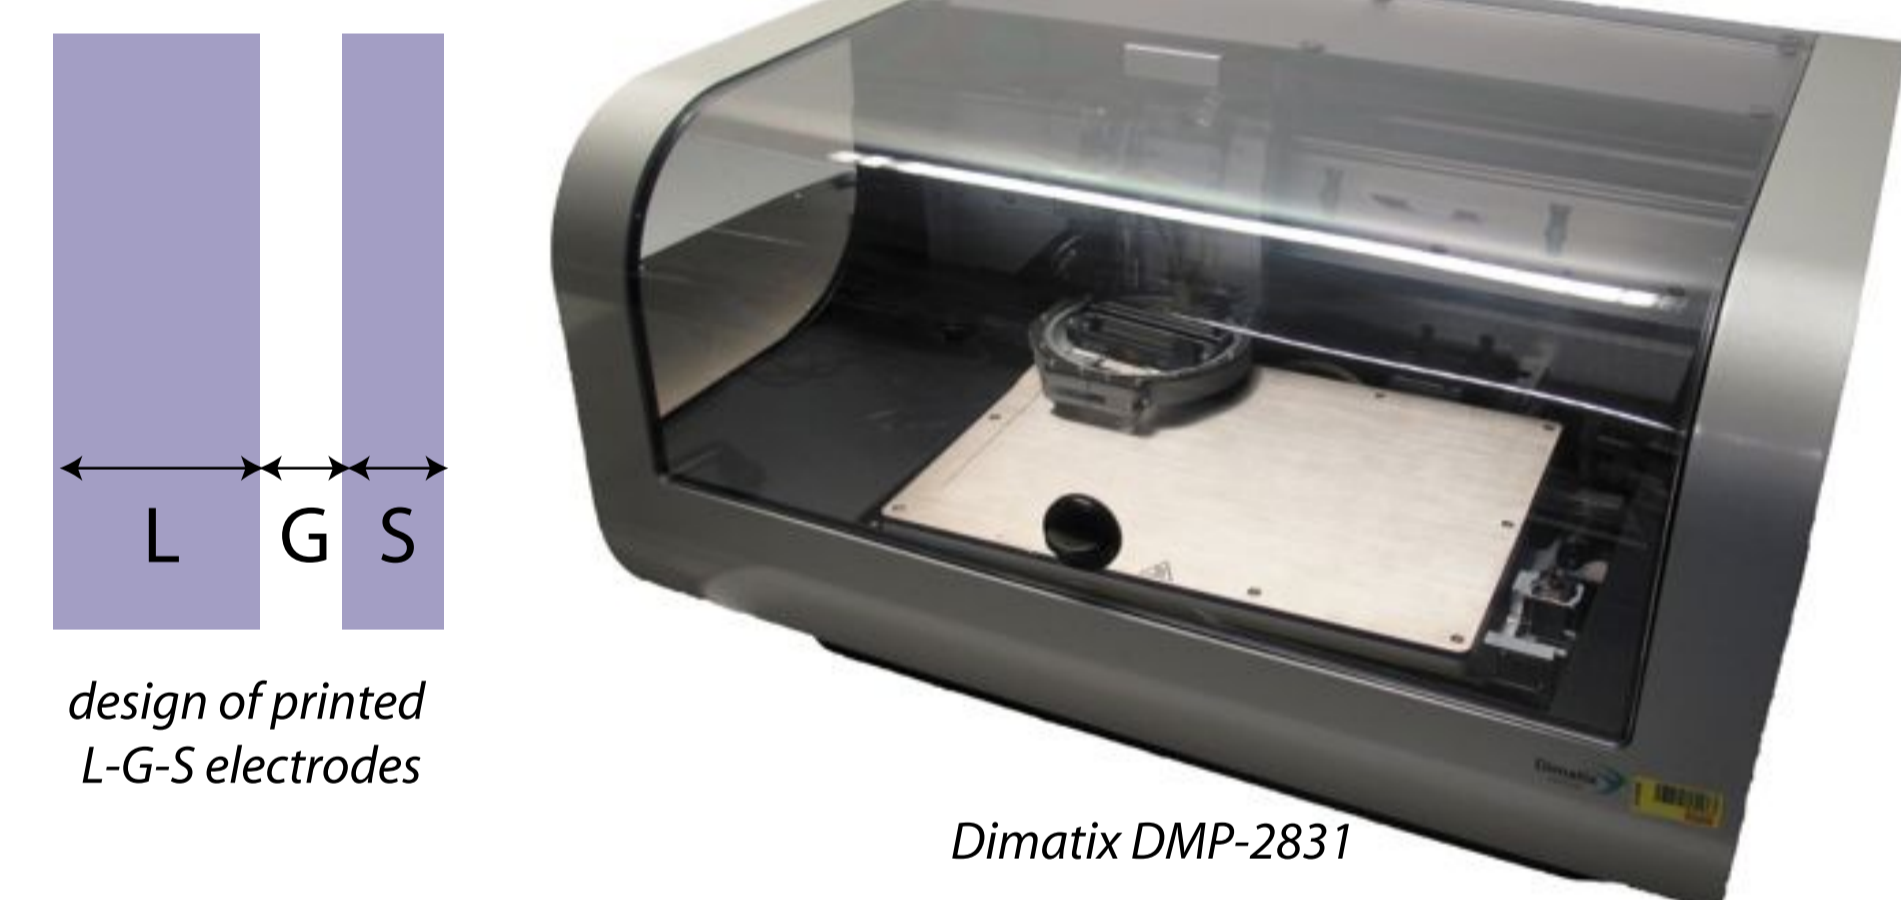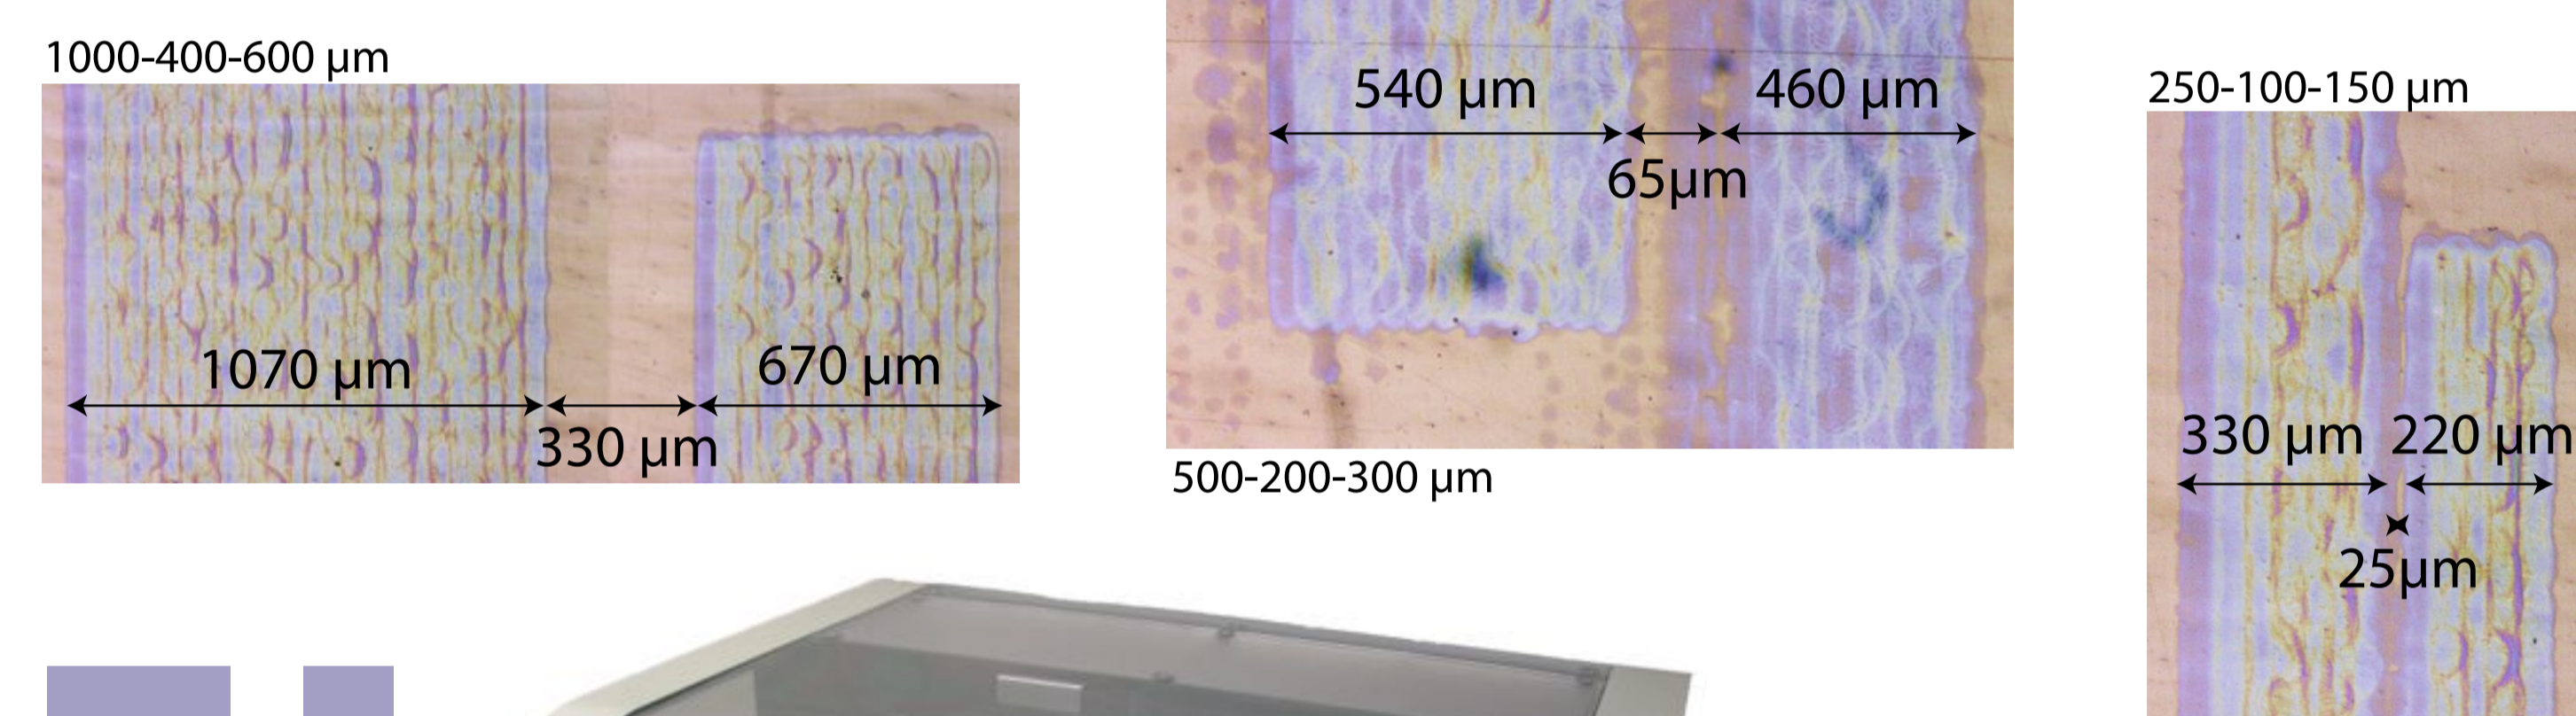


Substrate temperature 40 °C Ink Temperature 30 °C  
Jetting voltage 19.5 V Jetting frequency 5 kHz

### Perpendicular to print direction (8 layers)

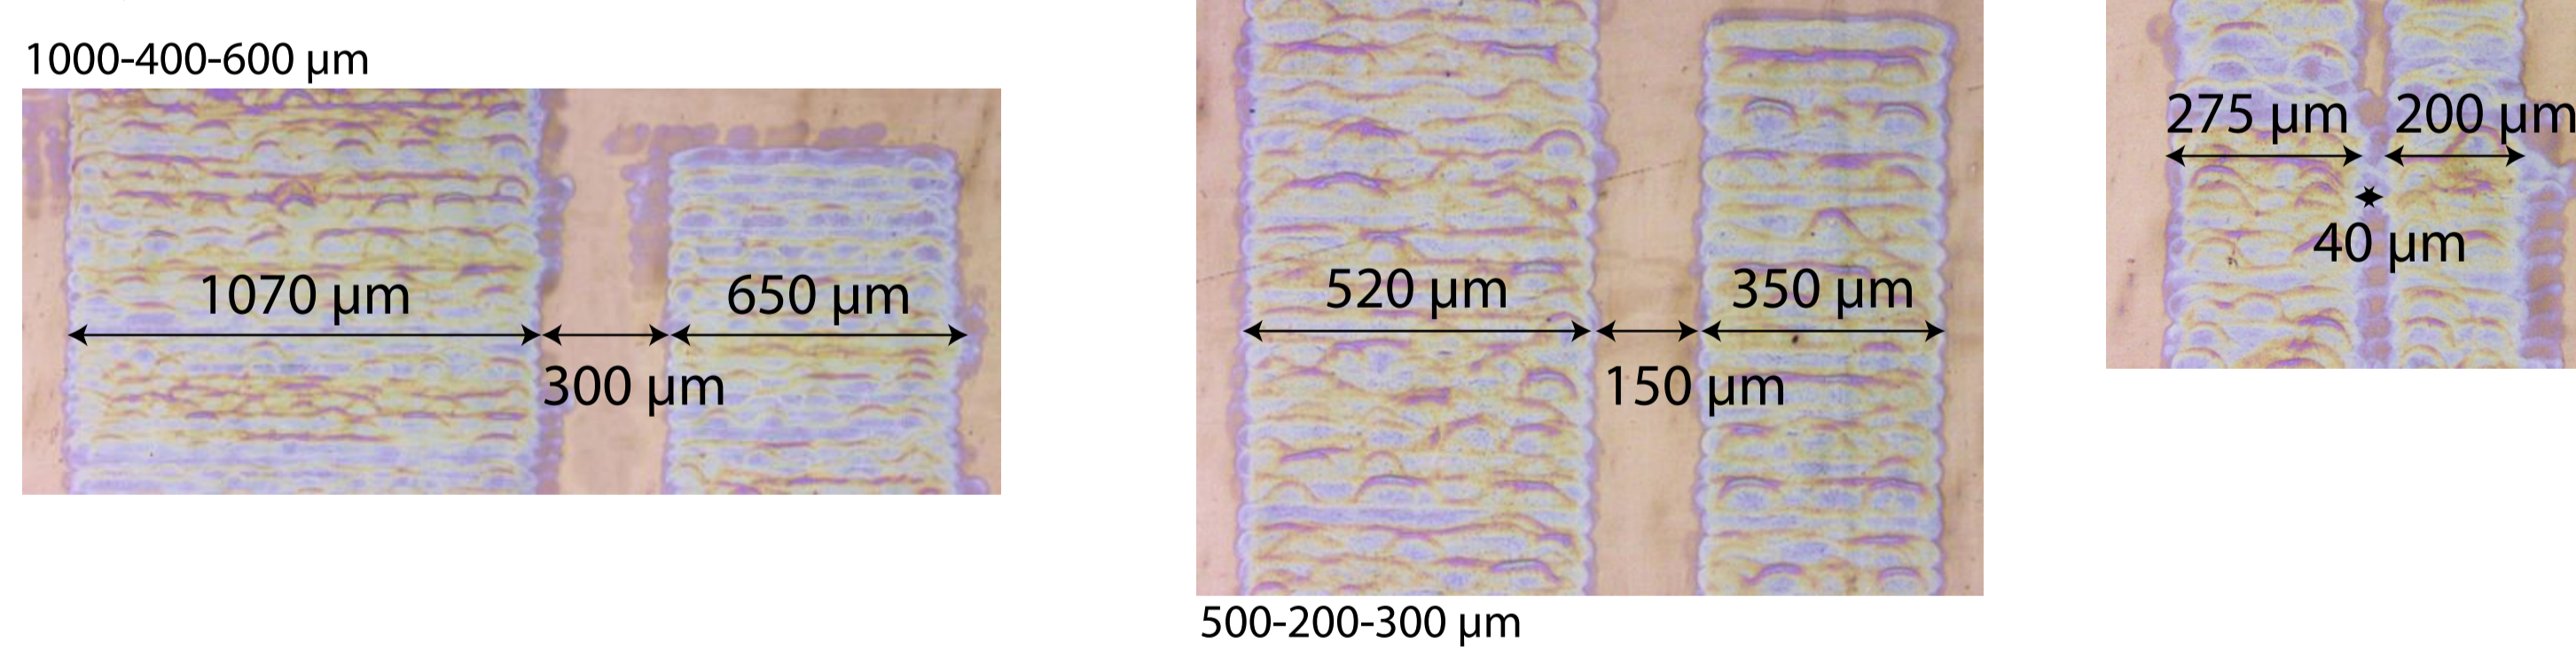


### Profile of 8 printed layers (white light interferometry)

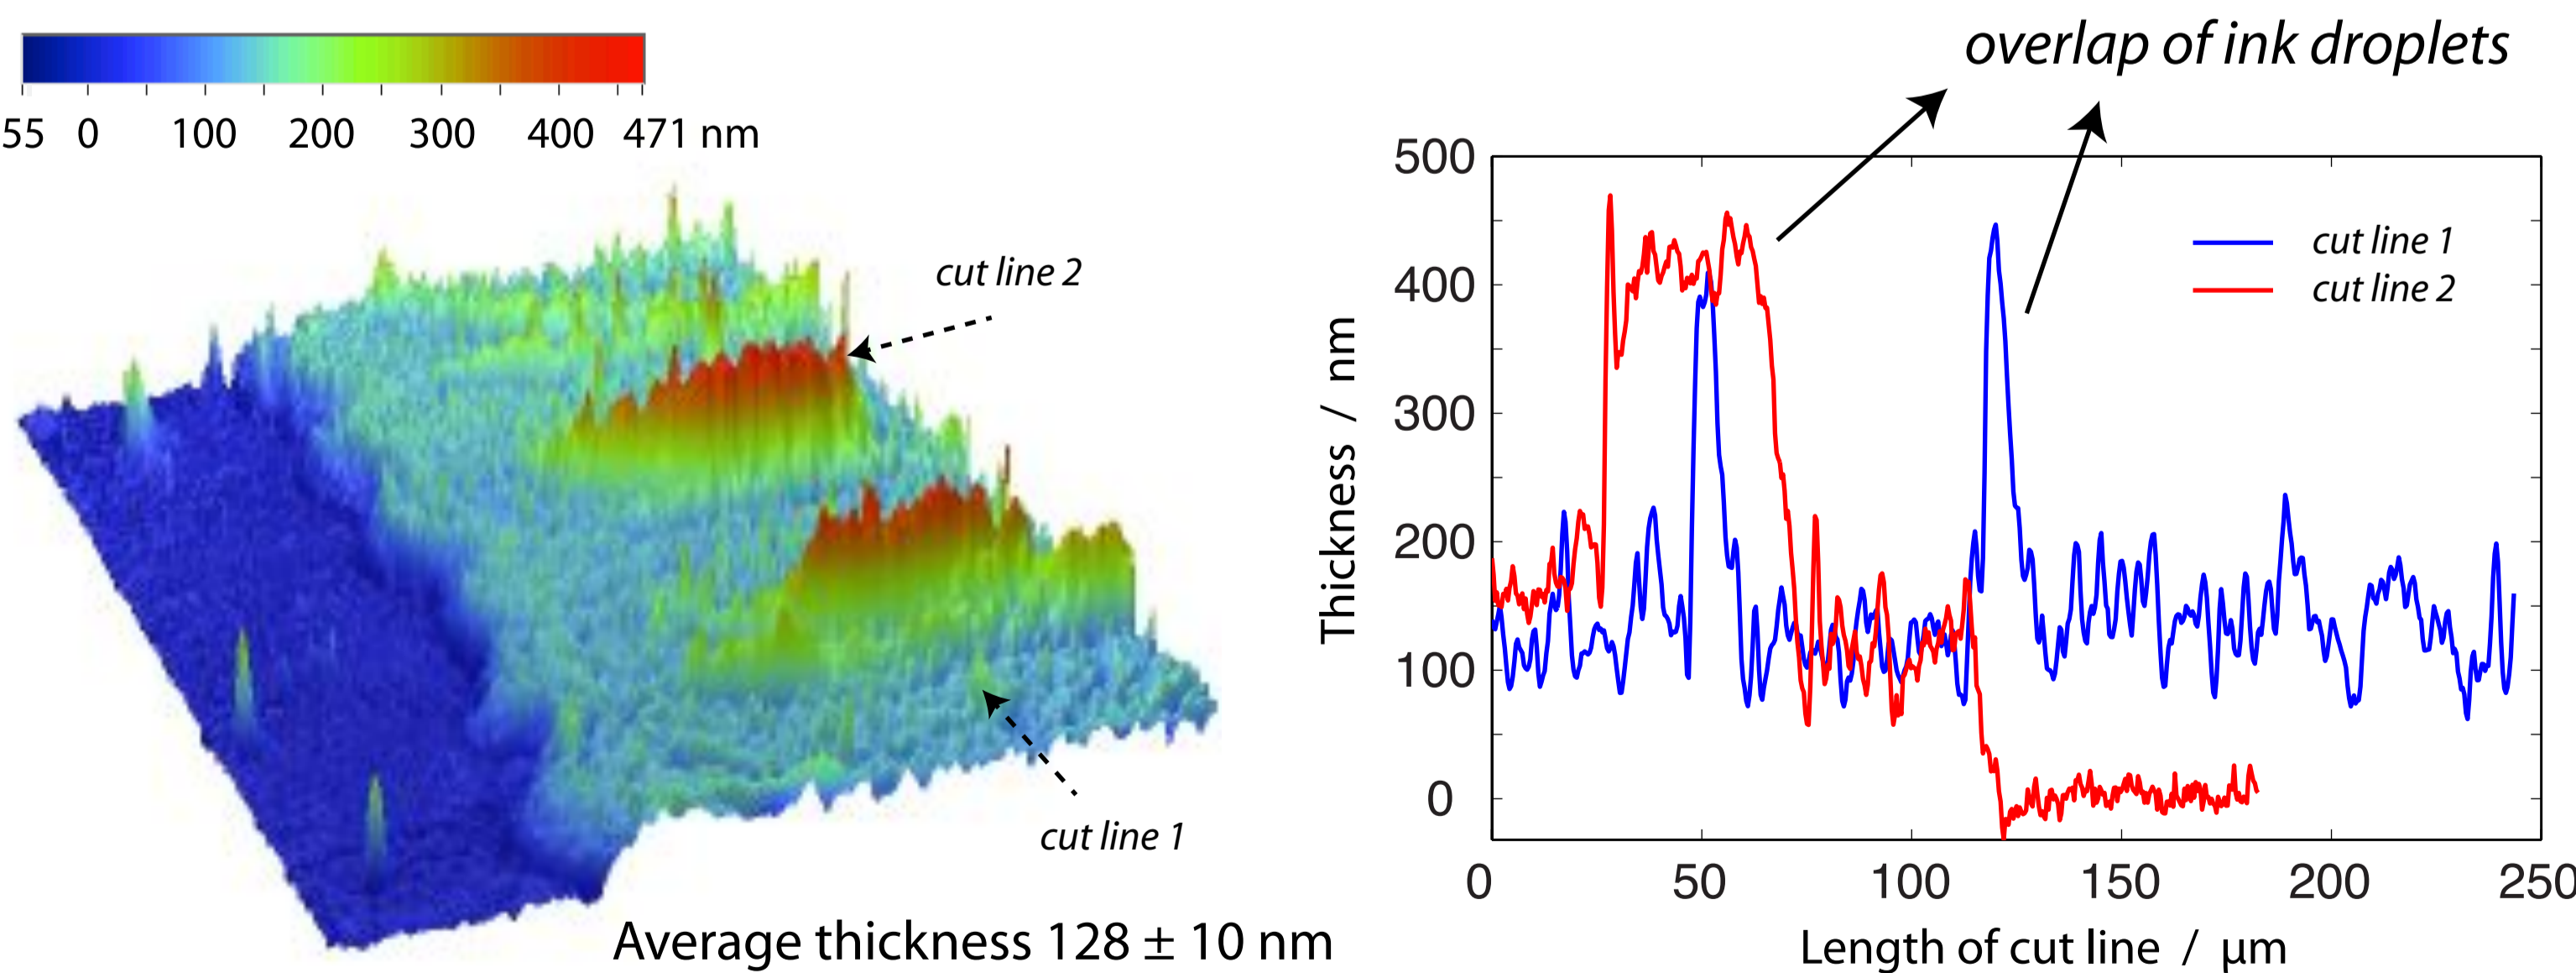

## A qualitatively good impedance

### Comparison of printed polymer with evaporated Pt

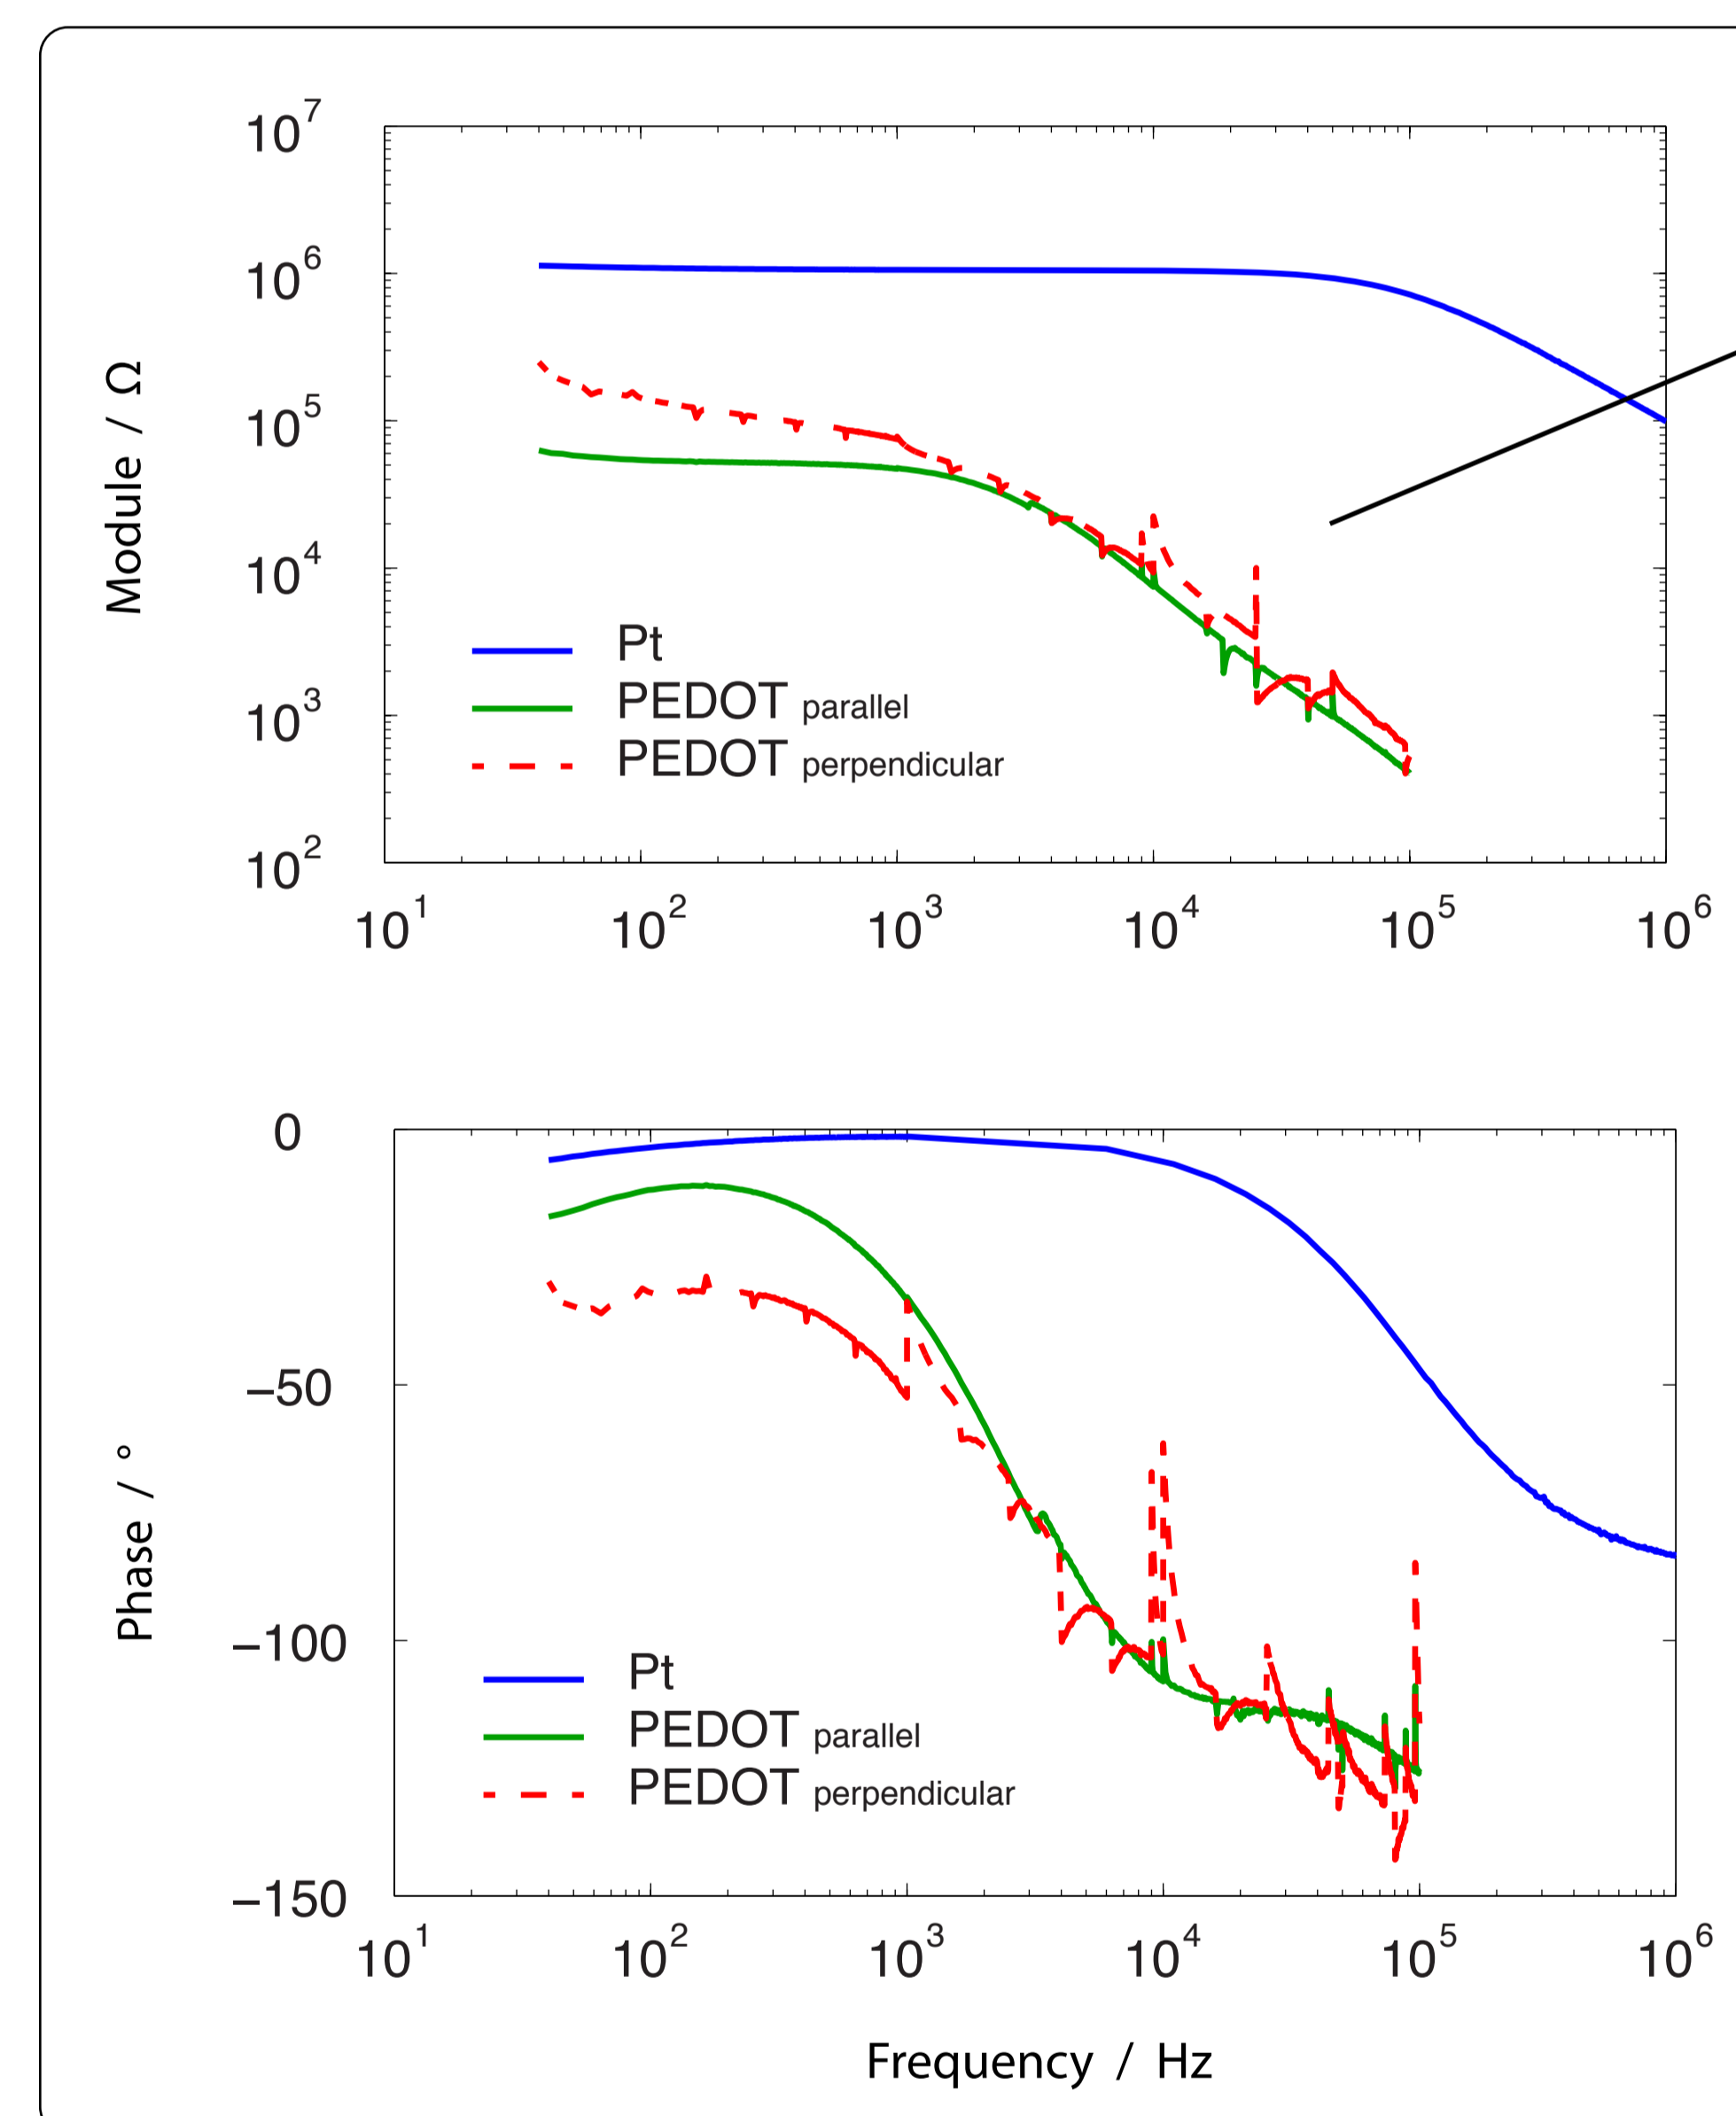


PEDOT:PSS has lower impedance, due to a printed electrode gap smaller than designed

#### Sheet resistance

PEDOT:PSS on PET  
1.88 ± 0.33 kΩ/sq.

Pt lift-off on PET (120nm)  
3.20 ± 0.58 Ω/sq.

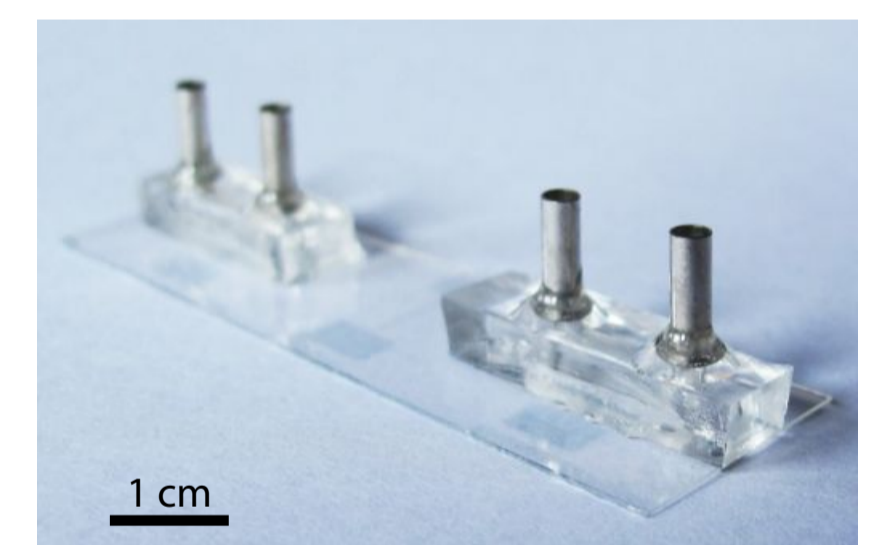

500-200-300 μm electrode patterns

measured with KCl 0.01mM

## Conclusion

PEDOT:PSS impedance has a comparable shape to that of Pt electrodes and both correspond well to theoretical predictions [8]. Inkjet-printed electrodes can be used for ACEO.

Impedance OK, but need smaller sizes for effective velocity generation

CHALLENGE for the future

Improve definition (need structures < 100 μm)

## References

- [1] Laser *et al.*, *J. Micromech. Microeng.* 14 (2004) R35
- [2] Hermes *et al.*, *Microsys. Tech.* 12 (2006) 436
- [3] Brown *et al.*, *Phys. Rev. E* 63 (2001) 016305
- [4] Castellanos *et al.*, *J. Phys. D: Appl. Phys.* 36 (2003) 2584
- [5] Erlandsson *et al.*, *Electrophoresis* 32 (2011) 784
- [6] Hansen *et al.*, *J. Micromech. Microeng.* 17 (2007) 860
- [7] Vig *et al.*, *J. Micromech. Microeng.* 21 (2011) 035006
- [8] Gregersen *et al.*, *Phys. Rev. E* 76 (2007) 056305

## Acknowledgements

This research was funded by Tronics Microsystems (Crolles, France)