

The Importance of the Interaction Radius Between Cr and Self-interstitial Fe in Object Kinetic Monte Carlo Calculations of Irradiated FeCr Diluted Alloys

L. Gámez¹, B. Gámez¹, M.J. Caturla², D. Terentyev³, J.M. Perlado¹

¹Instituto de Fusion Nuclear, UPM, Madrid, Spain linarejos.gomez@upm.es

²Departamento de Física Aplicada, Universidad de Alicante, Alicante, Spain

³SCK·CEN, Mol, Belgium

We have studied electron irradiation and annealing of FeCr alloys in the dilute limit (less than 1% Cr) using Object Kinetic Monte Carlo (OKMC) with input from density functional theory calculations and empirical potentials. The results are compared to experimental measurements of electric resistivity for different Cr concentrations. We analyse the dependence of Cr on the first two observed peaks: ID2 and IE and the influence of parameters such as the interaction radius between Cr and an Fe self-interstitial.

Parameters for OKMC model

Migrating species:

I up to size 4, V up to size 4

ICr 0.23 eV

I₂Cr 0.30 eV

ICr₂, I₂Cr₂ do not migrate

Dissociation of clusters

ICr → I + Cr 0.08 + 0.34 = 0.42 eV

ICr₂ → ICr + Cr 0.08 + 0.23 = 0.31 eV

I + Cr₂ 0.394 + 0.34 = 0.73 eV

I₂Cr → ICr + I 0.65 + 0.23 = 0.88 eV

I₂ + Cr 0.02 + 0.43 = 0.45 eV

I₂Cr₂ → I₂Cr + Cr 0.062 + 0.30 = 0.362 eV

And others of higher energies



Simulation conditions

Electron irradiation at 77 K

Isochronal anneal from 77 to 200K, Heating rate 3K/3min





Pure Fe & FeCr at 0.019 at.%, 0.047 at.% & 0.095 at.%

Experimental results from Abe & Kuramoto [1]

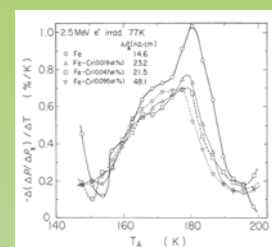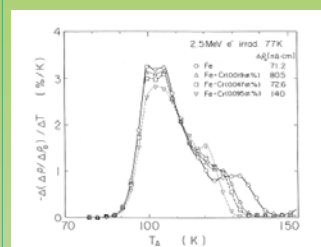

- Shift of stage IE to lower temperatures in FeCr
- Decreases in temperature and increases in amplitude with increasing Cr concentration
- Peak at 180K does not depend on solute concentration

Simulation results

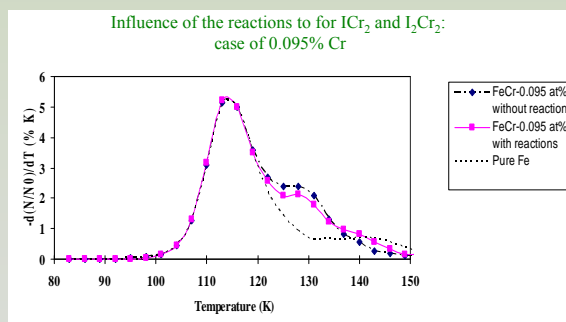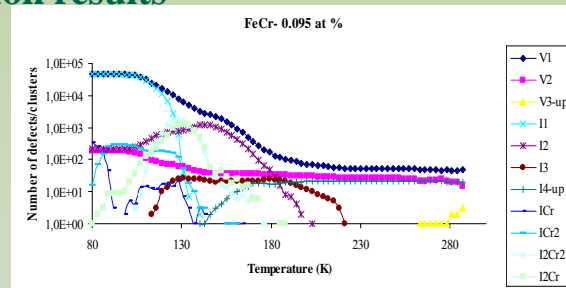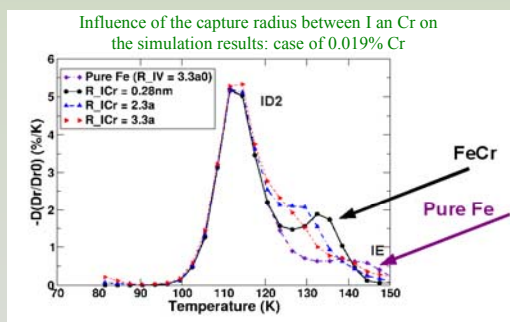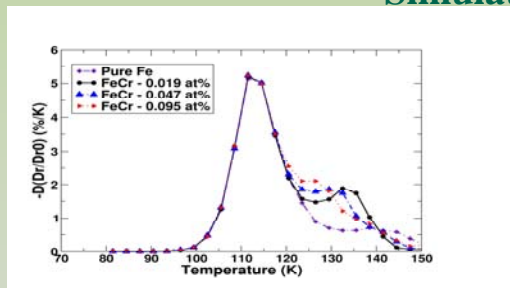

Conclusions: The model reproduces the shift of stage IE towards lower temperatures when Cr concentration increases. This peak is related to the formation of ICr and ICr₂ clusters. ICr migrates and recombines with V while ICr₂ dissociates into ICr and Cr. Since ICr migrates faster than an Fe interstitial the shift towards lower temperatures is reproduced. The position of the IE peak depends strongly on the ICr capture radius, with a capture radius of 0.28nm providing the best agreement with the experimental measurements. There is not a significant difference in the results when the I₂Cr and I₂Cr₂ reactions are not included. Further work is underway to study the behaviour at higher temperatures.

References.-

- [1] H. Abe & E. Kuramoto, J. Nuclear Materials 271-272 (1999) 209-213
- [2] F. Maury, P. Lucasson, A. Lucasson, F. Fudot, J. Bigot, J. Phys. F: Met. Phys. 17 (1987) 1143-1165
- [3] C. C. Fu, J. Dalla Torre, F. Willaime, J.-L. Bouquet, A. Barbu, Nature Materials (2004)
- [4] D. Terentyev et al., Comp. Mat. Sci. Doi:10.1016/j.commatsci.2008.03.013
- [5] P. Olsson, J. Nucl. Mater., accepted within ICFRM 2007.
- [6] P. Olsson, C. Domain, J. Wallenius, Phys. Rev. B75 (2007) 014110

Acknowledgements.-

We thank P. Olsson for providing information about defect energies from DFT and L. Malerba for fruitful discussions. This work has been funded by the FPVII projects FEMAS and GETMAT and by the MAT-REMEV task of EFDA.