

**STUDIES ON THE DURABILITY OF *Acacia*
HYBRID WOODS THROUGH ENVIRONMENTAL
FRIENDLY OIL-HEAT TREATMENT PROCESS**

FARAH WAHIDA BINTI AYOB


PERPUSTAKAAN
UNIVERSITI MALAYSIA SABAH

**THESIS SUBMITTED IN FULFILLMENT
FOR THE DEGREE OF MASTER OF SCIENCE**

**SCHOOL OF INTERNATIONAL TROPICAL
FORESTRY
UNIVERSITI MALAYSIA SABAH
2009**



A

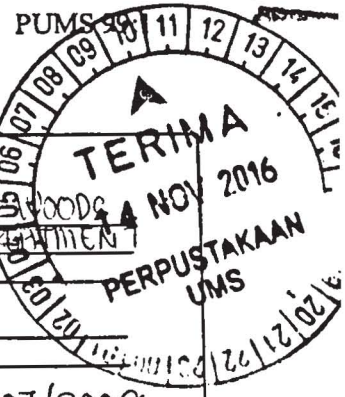

UNIVERSITI MALAYSIA SABAH

BORANG PENGESAHAN STATUS TESIS

JUDUL: STUDIES ON THE DURABILITY OF ACACIA HYBRID WOODS THROUGH ENVIRONMENTAL FRIENDLY OIL-HEAT TREATMENT PROCESS

IJAZAH: SARJANA SAINS PERHUTANAN

SAYA: FARAH WAHIDA BINTI AYUB SESI PENGAJIAN: 2007/2008
(HURUF BESAR)

Mengaku membenarkan tesis *(LPSM/Sarjana/Doktor Falsafah) ini disimpan di Perpustakaan Universiti Malaysia Sabah dengan syarat-syarat kegunaan seperti berikut:-

1. Tesis adalah hakmilik Universiti Malaysia Sabah.
2. Perpustakaan Universiti Malaysia Sabah dibenarkan membuat salinan untuk tujuan pengajian sahaja.
3. Perpustakaan dibenarkan membuat salinan tesis ini sebagai bahan pertukaran antara institusi pengajian tinggi.
4. Sila tandakan (/)

UNIVERSITI MALAYSIA SABAH

- SULIT (Mengandungi maklumat yang berdarjah keselamatan atau kepentingan Malaysia seperti yang termaktub di AKTA RAHSIA RASMI 1972)
- TERHAD (Mengandungi maklumat TERHAD yang telah ditentukan oleh organisasi/badan di mana Penyelidikan dijalankan)
- TIDAK TERHAD

(TANDATANGAN PENULIS)

Disahkan oleh:

(TANDATANGAN PUSTAKAWAN)

Alamat tetap: A25, JLN PERMAI 7, TAMAN SERTI PERMAI, FASA 2, BATU 3, JLN LANGGAR 05600, ALOR SETAR KEDAH

PROF. MADYA DR MAHMUD HJ SUDAN
NAMA PENYELIA

Tarikh: 26 OGOS 2010

Tarikh: 11 OCT 2010

Catatan :-

- * Potong yang tidak berkenaan.
- * Jika tesis ini SULIT atau TERHAD, sila lampirkan surat daripada pihak berkuasa/organisasi berkenaan dengan menyatakan sekali sebab dan tempoh tesis ini perlu dikelaskan sebagai SULIT dan TERHAD.
- * Tesis dimaksudkan sebagai tesis bagi Ijazah Doktor Falsafah dan Sarjana Secara penyelidikan atau disertai bagi pengajian secara kerja kursus dan Laporan Projek Sarjana Muda (LPSM)

PERPUSTAKAAN UMS




UMS
UNIVERSITI MALAYSIA SABAH

DECLARATION

I hereby declare that the materials in this thesis are of my own except for quotations, excerpts, equations, summaries and references, which have been duly acknowledged.

22 APRIL 2009



Farah Wahida Ayob
PF 2007-8229

PERPUSTAKAAN
UNIVERSITI MALAYSIA SABAH

CERTIFICATION

Name : **FARAH WAHIDA BT. AYOB**

Matric No. : **PF 2007 – 8229**

Title : **STUDIES ON THE DURABILITY OF *Acacia* HYBRID
WOODS THROUGH ENVIRONMENTAL FRIENDLY OIL-
HEAT TREATMENT PROCESS**


Degree : **MASTER OF SCIENCE (FORESTRY)**

VIVA Date : **14th AUGUST 2009**

DECLARED BY

SUPERVISOR

ASSOC. PROF. DR. MAHMUD SUDIN

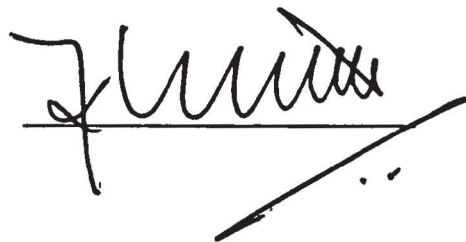

ACKNOWLEDGEMENT

I wish to express my deepest gratitude and appreciation to my supervisor, Associate Professor Dr Mahmud Sudin of the School of International Tropical Forestry, University Malaysia Sabah who has been patient enough to advise, guide and supervise me throughout the past few years. His continuous encouragement provided me the necessary impetus to complete the research and publish this thesis.

My special sense of gratitude to Sabah Forestry Development Authority (SAFODA), Mycology Laboratory of Forest Research Institute of Malaysia (FRIM) and School of International Tropical Forestry (SITF), University Malaysia Sabah for supplying the samples of wood, fungi and provide the equipments needed. My sincere appreciation to the Science Fund from Ministry of Science and Technology (MOSTI) for funding this research project (SCF0037-IND-1/2007 – Enhancing Finish Product Appearances and durability of Sapwood from Cultivated *Acacia Hybrid* and *Tectona grandis* through Environmentally Friendly Heat treatment Process)

Last but not least, appreciation to my parents, Mr Ayob Salleh and Mrs Rohaya Othman, my husband Mr. Mohd Faniezal Ismail and family for their support and encouragement.

Farah Wahida Ayob

28 February 2010

ABSTRACT

STUDIES ON THE DURABILITY OF *Acacia* HYBRID WOODS THROUGH ENVIRONMENTAL FRIENDLY OIL-HEAT TREATMENT PROCESS

The durability of oil-heat treated *Acacia* hybrid wood, an important plantation species in Sabah, was tested using *in-vitro* techniques against three different wood decay fungi (*P. sanguineus*, *C. versicolor* and *G. trabeum*). To determine the effectiveness of the treatments, 900 wood blocks of *Acacia* hybrid (~1.0 x 2.5 x 2.5 cm) were soaked into boiling palm oil with different temperature range between 180°C - 220°C and period between 30 – 90 min before exposed to the fungal cultures for 12 weeks. Results from the *in-vitro* tests showed that massive colonization by fungi on woodblocks affected the weight loss of samples from top, middle and bottom portion of trees, with a range of 2.89 – 10.59%, 4.67-20.33% and 4.27-20.55% (*P.sanguineus*); 3.26-15.42%, 3.88-16.84% and 4.69-18.79% (*C.versicolor*) and 0.88-4.94%, 1.22-5.29% and 1.22-4.89% (*G. trabeum*). The percentage of moisture contents of the oil heat treated *Acacia* hybrid wood had decreased in relation to the treatment given (5.96%, 5.61% and 4.40%) compared to untreated samples (12.04%, 13% and 13.48%) for top, middle and bottom portion respectively. A lesser amount of weight loss indicated greater durability of woods in relation to the treatment given, subsequently implied the potential of the heat treatment in improving resistance of *Acacia* hybrid woods against wood decay fungi.

ABSTRAK

*Ketahanan kayu Acacia hybrid yang diberi pemanasan minyak, yang mana Acacia hybrid merupakan spesies perladangan yang penting di Sabah, telah diuji dengan teknik in-vitro terhadap tiga fungi pereput kayu (*P. sanguineus*, *C. versicolor* dan *G. trabeum*) Untuk menentukan keberkesanan rawatan-rawatan, 900 blok-blok kayu Acacia hybrid (~ 1.0 x 2.5 x 2.5 cm) telah di rendam di dalam minyak kelapa sawit yang mendidih pada julat suhu antara 180°C - 220°C dan tempoh masa 30 – 60 min sebelum didedahkan kepada kultur fungi pereput kayu selama 12 minggu. Keputusan daripada ujian in-vitro menunjukkan kolonisasi yang banyak mempengaruhi kehilangan berat sampel-sampel dari bahagian atas, tengah dan bawah pokok , dengan julat 3.26-15.42%, 3.88-16.84% and 4.69-18.79% (*C.versicolor*) and 0.88-4.94%, 1.22-5.29% and 1.22-4.89% (*G. trabeum*). Peratusan kandungan air di dalam sampel Acacia hybrid yang diberi pemanasan minyak menurun sehubungan rawatan yang diberikan (5.96%, 5.61% and 4.40%) berbanding tanpa pemanasan (12.04%, 13% and 13.48%) untuk masing-masing bahagian atas, tengah dan bawah. Kehilangan berat yang rendah menunjukkan semakin meningkatnya ketahanan kayu setelah diberikan rawatan. Dan seterusnya juga menunjukkan potensi rawatan haba dalam meningkatkan ketahanan kayu Acacia hybrid terhadap fungi pereput kayu.*

TABLE OF CONTENTS

	Page
DECLARATION	ii
CERTIFICATION	iii
ACKNOWLEDGEMENT	iv
ABSTRACT	v
ABSTRAK	vi
LIST OF TABLES	ix
LIST OF FIGURES	x
LISTT OF APPENDICES	xiii
CHAPTER 1: INTRODUCTION	
1.1 <i>Acacia</i> sp. in Asia	1
1.2 <i>Acacia</i> sp. in Sabah	2
1.3 Objectives	4
CHAPTER 2: LITERATURE REVIEWS	
2.1 <i>Acacia</i> hybrid	5
2.2 Durability	6
2.3 Heat Treatment	8
2.4 Wood Decay Fungus	13
2.4.1 Brown Rot Fungi	17
2.4.2 White Rot Fungi	17
2.4.3 Soft Rot Fungi	18
2.5 Physical Properties of Wood	18
2.5.1 Moisture Content	18
2.5.2 Basic Density	21
CHAPTER 3: MATERIALS AND METHOD	
3.1 Effect of Different Oil-Heat Treatment on <i>Acacia</i> Hybrid Wood's Durability	22
3.1.1 Wood Samples Preparation	22
3.1.2 Oil-Heat Treatment Process	23
3.1.3 Effect of Different Fungi on Oil-Heat Treated <i>Acacia</i> Hybrid Woods	25
3.1.3.1 Preparation of Culture Media	25
3.1.3.2 Preparation of Fungal Culture	26
3.1.3.3 Preparation of Test Blocks	27
3.1.3.4 Measurement of Weight Loss	29
3.2 Physical Properties of Oil-Heat Treated and	29

Untreated <i>Acacia</i> Hybrid Wood	
3.2.1 Moisture Content	29
3.2.2 Basic Density	30
3.3 Micromorphology of Colonized <i>Acacia</i> Hybrid Woods	30
3.4 Statistical Analysis	30
CHAPTER 4: RESULTS AND DISCUSSION	
4.1 Effect of Different Oil-Heat Treatment on <i>Acacia</i> Hybrid Wood's Durability	32
<i>Treatments</i>	36
<i>Fungi</i>	38
<i>Portion</i>	41
4.2 Physical Properties of Oil-Heat Treated and Untreated <i>Acacia</i> Hybrid Wood	41
<i>Moisture Content</i>	45
<i>Basic Density</i>	50
4.3 Micromorphology of Colonized <i>Acacia</i> Hybrid Woods	57
CHAPTER 5: CONCLUSION	62
REFERENCES	63
APPENDIX 1	73
APPENDIX 2	88

LIST OF TABLES

	Page	
Table 2.1:	Natural durability classes for temperate and tropical exposure and laboratory exposure	6
Table 2.2:	Test fungi used in natural durability tests by BRE, UK	7
Table 2.3:	Restricted use pesticides	10
Table 2.4:	Examples of some commonly occurring brown rot and white rot decay fungi	16
Table 2.5:	Equilibrium moisture content of wood at various temperatures and relative humidity	20
Table 3.1:	Oil-Heat Treatments at different temperature and duration using palm oil as the medium to test the durability of <i>Acacia</i> hybrid wood blocks. Blocks that were not heated serves as the Control	24
Table 4.1:	Mean weight loss (%) of <i>Acacia</i> hybrid wood blocks for top, middle and bottom portion following 12 weeks exposure to cultures of <i>P. sanguineus</i> , <i>C. versicolor</i> and <i>G. trabeum</i>	33
Table 4.2:	General Linear Model of the weight loss of <i>Acacia</i> hybrid wood blocks given oil-heated treatments and tested against wood decay fungi for 12 weeks	34
Table 4.3:	Mean moisture content (%) of <i>Acacia</i> hybrid wood blocks for top, middle and bottom portion given oil-heated treatments	46
Table 4.4:	General Linear Model of the moisture content of <i>Acacia</i> hybrid wood blocks given oil-heated treatments.	48
Table 4.5:	Mean basic density of <i>Acacia</i> hybrid wood blocks for top, middle and bottom portion given oil-heated treatments	52
Table 4.6:	General Linear Model of the basic density of <i>Acacia</i> hybrid wood blocks given oil-heated treatments.	54

LIST OF FIGURES

		Page
Figure 3.1:	Location of Kinarut, Sabah where the sampling of <i>Acacia</i> hybrid were carried	22
Figure 3.2:	Portion of healthy stem of <i>Acacia</i> hybrid samples (1 m) from top, middle ad bottom portion were peeled off (a) and cut (b) into blocks	23
Figure 3.3	Wood blocks of <i>Acacia</i> hybrid (55 x 10 x 3 cm) soaked into palm oil in a heating tank to test treatment effects on wood durability	25
Figure 3.4:	Malt Extract Agar (MEA) in Duran bottles (250 ml) in the canister of the autoclave machine	26
Figure 3.5:	Culture media (MEA) with feeder strips of <i>Acacia</i> hybrid woods and mycelia plugs of the test fungi, <i>P. sanguineus</i> (arrows) in 250 ml Duran bottle (a) was fully covered by mycelia after 3 weeks incubation (b) at 26.7 °C and 70 % RH in darkness	27
Figure 3.6	Oil-heat treated and untreated of <i>Acacia</i> hybrid wood blocks (2.5 x 2.5 x 0.9 cm) were exposed to the decay fungi (<i>C. versicolor</i> , a) and the mycelium (arrow) was covered the wood blocks after 12 weeks testing period (b)	28
Figure 3.7:	Oil-heat treated and untreated of <i>Acacia</i> hybrid wood blocks were exposed to decay fungi incubated at 26.7 °C and 70 % RH for 12 in darkness	28
Figure 4.1:	Differing in colonization by a test fungal isolate (<i>C.versicolor</i> on oil-heat treated (a) and untreated (b) wood blocks of <i>Acacia</i> hybrid after 12 weeks incubation at 25°C in darkness	32
Figure 4.2	Mean weight loss of <i>Acacia</i> hybrid wood blocks for each Treatment after exposed to fungi for 12 weeks	35
Figure 4.3	Box plots of weight loss of <i>Acacia</i> hybrid wood blocks for each Treatment after exposed to fungi for 12 weeks	37

Figure 4.4	Box plots of weight loss of <i>Acacia</i> hybrid wood blocks for each fungi after exposed to fungi for 12 weeks	40
Figure 4.5	Box plots of weight loss of <i>Acacia</i> hybrid wood blocks for each portion after exposed to fungi for 12 weeks	42
Figure 4.6	Mean of moisture content of <i>Acacia</i> hybrid wood blocks for each portion before and after oil-heat treated	47
Figure 4.7	Box plots of moisture content of <i>Acacia</i> hybrid wood blocks for each portion before and after oil-heat treated.	48
Figure 4.8	Mean of basic density of <i>Acacia</i> hybrid wood blocks for each portion before and after oil-heat treated	53
Figure 4.9	Box plots of basic density of <i>Acacia</i> hybrid wood blocks for each portion before and after oil-heat treated	54
Figure 4.10:	Scanning electron micrographs (transverse sections) of <i>Acacia</i> hybrid woods sampled from top (a, b), middle (c, d) and bottom (e, f) portion colonized by <i>P. sanguineus</i> after 12 weeks incubation period. A more prolific mycelia (arrows) permeating and filling the lumen of vessels of untreated wood (a, c & e) was observed as compared to wood experienced Treatment 9 (b, d & f). Bars represent magnification scale in μm .	58
Figure 4.11:	Scanning electron micrographs (transverse sections) of <i>Acacia</i> hybrid woods sampled from top (a, b), middle (c, d) and bottom (e, f) portion colonized by <i>G. trabeum</i> after 12 weeks incubation period. A more prolific mycelia (arrows) permeating and filling the lumen of vessels of untreated wood (a, c & e) was observed as compared to wood experienced Treatment 9 (b, d & f). Bars represent magnification scale in μm	59
Figure 4.12:	Scanning electron micrographs (transverse sections) of <i>Acacia</i> hybrid woods sampled from top (a, b), middle (c, d) and bottom (e, f) portions colonized by <i>C. versicolor</i> after 12 weeks incubation period. A more	60

prolific mycelia (arrows) permeating and filling the lumen of vessels of untreated wood (a, c & e) was observed as compared to wood experienced Treatment 9 (b, d & f). Bars represent magnification scale in μm

LIST OF APPENDICES

Appendix 1	Weight loss of each replicate of the wood blocks taken from the top, middle and bottom portions of the sampled <i>Acacia</i> hybrid trees, after 12 weeks exposure to fungal isolates of <i>P. sanguineus</i> , <i>C. versicolor</i> and <i>G. trabeum</i> .	73
Appendix 2	Statistical analysis on the weight loss of the <i>Acacia</i> hybrid wood blocks receiving oil heat treatments and were subjected to 12 weeks exposure to fungal isolates of <i>P. sanguineus</i> , <i>C. versicolor</i> and <i>G. trabeum</i> .	88

CHAPTER 1

INTRODUCTION

1.1 *Acacia* sp. in Asia

Acacia is a well known tree genus in the Family: Mimosaceae and it contain more than 1200 species in tropical and subtropical regions (Simmons, 1987). Several of these species which is widely used as plantation species are *Acacia mangium* and *Acacia auriculiformis*. They were selected because of their less site selective and fast growing characteristics, besides the quality of the timber. *Acacias* grew well in other parts of the tropical forests despite it originated from Australia (Ramatoulaye *et.al*, 2007), although Boland *et al.* (1990) reported that some species of the genus like *A. mangium* and *A. auriculiformis* are also natural in Papua New Guinea and Indonesia. The species were then introduced and hence widespread to other countries such as Vietnam, Bangladesh and also Malaysia (Le, 2001 and Latif, 1994).

Many tropical countries considered these species as an important fast growing species including the hybrid between these two species (Nguyen *et.al*, 2008b) and for that, the plantation area of these species has steadily increased over time, especially in Asia. Arif *et al.* (2004) mentioned that in Indonesia, there are more than 800,000 hectares of *A. mangium* plantation established. Similar pattern i.e extensive plantation establishment of *Acacias* has developed in Southeast Asia, again this was encouraged by its fast growth, good form and the utilization potentials of the wood (Sabri *et al.*, 1993). Martin (2004) also informed that the tree plantations such as with this species could help reduce the greenhouse gas in addition to providing pulps and fire wood. Hence, it contributes in the mitigation of global warming through greening or increased reforestation; which will stocks more carbon and thus help keep a healthy environment.

1.2 *Acacia* sp. in Sabah

The endeavor towards enterprising the forest plantations in Sabah has begun in the 1960s, especially with the inception of Forest Plantation Section by the Forestry Department to establish trials to demonstrate the capability of selected trees especially those of fast growing species. *Acacias* was one of the genus that had been chosen following the excellent growth performance of *A. mangium*, which was first introduced from Australia and planted in Ulu Kukut as fire break buffer in 1966 (Koichi, 2003). Some other *Acacias* were also planted including *A. auriculiformis* which was noticed to have less mortality. Conscious of these different valuable properties in both species, the breeding using the two *Acacias* was carried out to gain the best product (species) which genetically have good qualities from both parent trees; the result, a new seedlings known as *Acacia* hybrid, was obtained in Malaysia in 1972 (Nguyen *et al.*, 2008b). This 'new' species then was observed to be equally good as its parents in terms of rapid growth, wood quality and adaptation to many soil types, thus were also widely planted, as addition to *A.mangium* and *A.auriculiformis* (Le. 2001).

Currently, *Acacia* hybrid (*A.mangium* x *A.auriculiformis*) is one of the plantation species in Sabah which has higher density and straight tree shape (Toshiaki, 2008). The height and diameter of this species also more higher than its parents (Nguyen, 2008a). Latif (1994) reported that the female parent of this *Acacia* hybrid was *A.mangium* while the male parent was *A.auriculiformis*. Regarding to these properties (fast growing and straight shape), the demand for *Acacia* hybrid products such as pulpwood for domestic paper mills, raw material for manufacturing medium-density fiberboard and woodchips for the export market had increased (Martin, 2004). Plantation area of this species also developing to 55 000 hectares in sabah since 1985 and expected to increase (Udarbe and Hepburn, 1987; Yamamoto, 1998).

The economic value of this species of course relies also on its wood properties. This aspect have the subject of various studies for the *Acacia* hybrid encompassing wood durability and resistance against wood decay fungi. Kevin *et.al* (2009) reported that the durability of wood is a very vulnerable property because of many microorganisms including fungi, insects and bacteria can cause severe degradation on the wood under suitable environment conditions. So, as for any other tree species, durability of the wood could be enhanced by applying treatments on it. However some treatments especially involve the use of chemicals are hazardous and high costs. Another alternative which is widely used is heat treatment (Muss *et al.*, 2006). In Europe, several heat treatment processes have been developed in order to enhance the durability of wood (Momohara, 2003). Wang and Cooper (2005) reported that in Europe, thermal modification of wood have successfully been carried out using steam, nitrogen or oil as the heat transfer and oxygen excluding medium.

In Finland, Thermo Wood process using steams was used (Syrjänen and Kangas, 2000), whilst in France nitrogen was used in Retification process (Dirol and Guyonnet, 1993). In the Netherlands, Plato process was also used (Boonstra *et al.*, 1998; Tjeerdsma *et al.*, 1998, 2000; Militz and Tjeerdsma, 2001) and In Germany, heat treatment process by using oil (Sailer *et al.*, 2000; Rapp and Sailer, 2001) was reported. To augment high durability to wood, hydrothermolysis have also been recently assessed by Syrjanen and Kangas (2000) which aimed at stabilizes the timber as similar to the used of high temperature drying process by Shuichi *et al.*, (2005). However, that treatment process considered complicated for large scale production due to high temperature needed to get good biological durability (Saila and Pertti, 2001); however but the effect of this treatment – i.e. heat treatment - was already known which is it could increase the durability of wood.

Oil-heat treatment is one of the methods that could be carried out by using palm oil which is only need a low cost than other treatments. Another factor is that, among the vegetables oils, palm oil is high in saturated fatty acids thus it could be in semi-solid state at ambient temperature (Wand and Cooper, 2005). Due to this and therefore the heat treatment, could reduce fungus and termites resistance because of the effect of the high temperature on wood durability (Kurisaki *et al.*, 2001).

Additionally, the durability of *Acacia* hybrid wood can be assessed in three ways; service use, field trials and/or from laboratory testing (Curling, S.F. and Murphy, R.J., 1999). In this study, the focus was on laboratory testing (in-vitro test).

1.3 Objectives

The general objective of this study was to study the effectiveness of heat treatment process on the durability of *Acacia* hybrid woods against selected wood decay fungi. This was achieved through several specific objectives as below:

1. To study the durability of oil-heat treated *Acacia* hybrid woods through accelerated laboratory tests;
2. To examine changes in the physical properties of oil-heat treated *Acacia* hybrid woods; and
3. To observe changes in the microstructure of oil-heat treated *Acacia* hybrid woods through Scanning Electron Microscope.

CHAPTER 2

LITERATURE REVIEW

2.1 *Acacia* hybrid

The *Acacia* hybrid is a cross breed between *A. mangium* and *A. auriculiformis* (Chiai, 1993; Nguyen *et al.*, 2008). Both of these parental species are natural to Australia - *A. mangium* mainly in Queensland whilst *A. auriculiformis* in Darwin (Lee *et al.*, 1993). *Acacia* hybrid, which inherit the genetic traits of fast growing (from *A. mangium*) and straighter shape (from *A. auriculiformis*) was considered to have a promising potential for plantation use since it has been noted to be more vigorous and adaptable to various soil types (Chiai, 1993; Pinyopusarerk, 1993; Nguyen *et al.*, 2008). This has made it as one of a major fast growing species in a many regions such as Australia, Malaysia, and Thailand (Yoshiyuki *et al.*, 2002). Additionally, another important characteristic is that *Acacia* hybrid was reported to be less susceptible to disease than its parental species (Nguyen *et al.*, 2008). This quality has stimulate the establishment of *Acacia* hybrid planting in Malaysia, particularly Sabah.

In Sabah, biconal orchards for mass production of the seeds of *Acacia* hybrid were established and more than 55,000 hectares had been planted (Jiwarawat *et al.*, 1996). Vietnam had also taken similar initiative where *Acacia* hybrid had been chosen as one of the forest tree species. In 2001, a total of 2.6 million hectares was planted (Martin, 2004). A huge plantation of a species would certainly attract various studies.

Bueren (2004) reported that *Acacia* hybrid had almost double in terms of growth rate as compared to its parental species (*A. mangium* and *A. auriculiformis*). At the same time, despite the vigorous growth increment, the wood quality is good for pulping as well as for particleboards and medium density fiberboard production (Nguyen, 2002; Nguyen, 2004). Being harvestable at a shorter rotation and with significant yields higher than their parental species, has make *Acacia* hybrid a species of high demand in the market (Nguyen *et al.*, 2009).

2.2 Durability

European Standard (EN350-1) has defined the natural durability of wood as an inherent resistance against wood destroying organisms (Acker *et al.*, 2003). Bailleres and Durand (2000) added that the natural durability may vary enormously whether between trees or within the same tree individuals.

Table 2.1: Natural durability classes for temperate and tropical exposure and laboratory exposure

Durability Class	Service life under			(% weight loss) ^a
	Temperate conditions (years)	Tropical conditions (years) ^b	Laboratory conditions	
Perishable	< 5	< 2 ^b	> 30	
Non-durable	5 – 10	2 – 5 ^b	10 – 30	
Moderately durable	10 – 15	Not given	5 – 10	
Durable	15 – 25	5 – 10	1 – 5	
Very durable	25 +	10 +	< 1	

^a 16 weeks incubation at 22°C test fungi listed in Table 2.2

^b In some tropical countries the term perishable is not used and non-durable is used to describe this class; in this case moderately durable is used to describe 2-5 years service life.

Source: (Findlay, 1966)

Natural durability of wood was also categorized in relation to the environmental conditions that they were in for example temperate, tropical or *in vitro* (Table 2.1). Such categories however was only applied to basidiomycete decay fungi such as brown and white rot (Table 2.2) under high decay risk, and may not apply to other situation or biodeterioagens (Eaton & Hale, 1993).

Table 2.2: Test fungi used in natural durability tests by BRE, UK

Serpula lacrymans

Gloeophyllum trabeum

Coniophora puteana

Trametes (Coriolus) versicolor

Antrodia (Fibroporia) vailantii

Pycnoporus (Polystictis) sanguineus

Kokutse (2006) asserted that durability of wood was depending on several factors such as genetic of the origin tree, silvicultural prescription, climate and environmental conditions. However, the durability of wood against decay fungi (*eg.* In Table 2.2) could be increased through heat treatment as during the process chemical properties of wood and other components like carbohydrate could be transformed and changed (Baechler, 1959; Highley, 1970). However, a decline of decay durability is also possible due to the likely generation of low molecular weight sugar fragments from the hydrothermal

changes of hemicelluloses during the drying process including the steam treatment, although a different result were obtained between different fungi (Sehlstedt, 1995).

2.3 Heat Treatment

Woods, for the purpose of extending its durability, can be treated in various ways and one of them is 'heat treatment'. In Finland, for example, eight heat treatment plants were established to deal with a production of around 35,000 m³ per year (at least in 2000). These treatment plants did not use chemical but put a high pressure to replace the heat and water vapor in the wood (Tuula and Kestopuu, 2001). It is an environmental friendly treatment which is not hazardous to both people and the environment. Some countries used pesticides (*eg.* In Table 2.3) for preservation of wood. In certain regions such as Japan, Australia, USA and Southern EU, have given due attention to termite durability as well as decay durability when heat treated wood materials are used for building and exterior construction (Shuichi *et al.*, 2005).

Different heat treatments need different range of temperature. Tjeerdsma *et al.* (1998) reported that suitable temperature for Plato process ranged between 160°C to 190°C while for Ratification process and Bios procedure needs a temperature range between 200°C to 240 °C (Kamdem *et al.*, 2002). Rapp and Sailer (2000) suggested that temperature range for oil-heat treatment is between 180°C to 220°C.

According to Weiland & Guyomet (2003), heat treatment at a very high temperature (over 150°C) should be an effective method as an alternative to improve the durability

of wood. Reinprecht (1999) suggested that high temperature rendered the wood a high resistance to fungi and thus a range from 150°C and 240°C can be used. Conversely, duration of treatment is also important. Salla and Pertti (2001) reckoned that the properties of heat treated wood are depending on temperature and duration of which the former has the greater effect on many properties than the later.

Many reports had appeared on the evaluation of the effect of high temperature on wood properties (Kubojima *et al.*, 2002). However, the methods of using high temperature on wood become the subject and arguments of many studies as wood be dried upon extreme heating. But the European process suggested that high temperature wood drying process could increase wood durability if the process keeps wood at a high temperature enough (Momohara *et al.*, 2003).

REFERENCES

- Acker, J.V., Stevens, M., Carey, J., Sierra-Alvarez, R., Miltz, H., Bayon, I.L., Kleist, G. and Peek, R.D. 2003. Biological Durability of Wood in Relation to End-Use. *Holz als Roh-und Werkstoff* **61**: 35-45.
- Adzo, D.K., Alexia, S., Henri, B., Kouami, K. and Christine, B. 2006. Decay Resistance of Togolese Teak (*Tectona grandis* L.f) Heartwood and Relationship with Colour, *Holz als Roh-und Werkstoff* **20**: 219-223
- American Institute of Timber Construction (AITC). 2000. Designing Structural Glued Laminated Timber for Permanence, AITC Technical Note 12.
- American Society for Testing Materials (ASTM). 1998. Standard Test Method for Fungicides for Controlling Sapstain and Mold on Unseasoned Lumber (Laboratory Method), Standard D 4445091. Annual Book of ASTM Standards **4.10**: 497-500
- Andreas, O.R. and Michael, S. 2001. Oil Heat Treatment of Wood in Germany – State of the Art. In: *Review on Heat Treatments of Wood: Proceedings of Special Seminar*, France.
- Anonymous. 2000. Preservation and Maintenance of Log Structures. *National Association of Home Builders*.
- Arif, N., Budi, L., Susumu, K. and Susumu, S. 2004. Realized Genetic Gain Observed in Second Generation Seedling Seed Orchards of *Acacia mangium* in South Kalimantan, Indonesia. *Journal Forest Research* **9**: 265-269
- Baechler, R.H. 1959. Improving Wood's Durability through Chemical Modifications. *Forest Product Journal* **9**: 166-171



- Bhat, K.M., Thulasidas, P.K., Maria F.E.J. and Jayaraman, K. 2005. Wood Durability of Home-Garden Teak against Brown Rot and White Rot Fungi. *Trees* **19**: 654-660.
- Boonstra, M.J., Acker, V.J., Kegel, E. and Stevens, M. 2007. Optimization of a Two Stage Heat Treatment Process: Durability Aspects. *Wood Science Technology* **41**: 31-57
- Boonstra, M.J., Tjeerdsma, B.F., Groeneveld, H.A.C. 1998. Thermal Modification of Wood. *International Research Group on Wood Preservation IRG/WP* 98-40123
- Callum, A.S.H. 2006. Wood Modification Chemical, Thermal and Other Processes. John Wiley & Sons Ltd. England.
- Carol, A.C. and Vina, Y. 2007. Protecting Wood from Mould, Decay and Termites with Multi-Component Biocide Systems. *International Biodeterioration & Biodegradation* **59**: 20-24
- Chia, E. 1993. Recent Development in *Acacia* Improvement at Sabah Softwoods. In: Kamis, A. and Taylor, D.A. *Acacias for Rural Industrial and Environmental Developments: Proceeding of the 2nd Meeting of the Consultative Group for Research and Development of Acacias*. Thailand
- Clausen, C.A. 2002. Recognize, Remove and Remediate Mold and Mildew. In: *Proceedings of the Second Annual Conference on Durability and Disaster Mitigation in Wood Frame Housing, Forest Products Society*. 231-234

- Cowling, E.B. 1961. Comparative Biochemistry of the Decay of Sweetgum Sapwood by White Rot and Brown Rot Fungi, *Technical Bulletin No. 1258*, Department of Agriculture, Washington DC.
- Cullen, D. and Kersten, P.J. 1994. *Enzymology and Molecular Biology of Lignin Degradation*. In: *The Mycota III, Biochemistry and Molecular Biology*, Springer Berlin. 295-312pp
- Curling, S.F. and Murphy, R.J. 1999. The Effect of Artificial Ageing on the Durability of Wood-Based Board Materials Against Basidiomycete Decay Fungi. *Wood Science and Technology* **33**: 245-257
- Daniel, G. 2003. *Microview of Wood Under Degradation by Bacteria and Fungi*. In: Goodell, Nicholas, Schultz. *Wood Deterioration and Preservation Advances in Our Changing World*. American Chemical Society Press 34-72
- Eaton, R.A. and Hale, M.D.C. 1993. *Wood, Decay, Pests and Prevention*. Chapman & Hall, London
- EN 350-1. 1994. Durability of Wood and Wood Based Products- Natural Durability of Solid Wood. Part 1: Guide to the Principle of Testing and Classification of the Natural Durability of Wood. *European Committee for Standardization (CEN)*. Belgium
- Eriksson, K.E. 1981. Fungal Degradation of Wood Components. *Pure and Applied Chemistry* **53**: 33-43
- Findlay, W.P.K. 1966. *Ecology of Wood Destroying and Wood Inhabiting Fungi*. Holz und Organismen. International Symposium Berlin. 199-212

- Frederick, G. and Terry, L.H. 1997. Mechanism of Brown Rot Decay: Paradigm or Paradox. *International Biodeterioration and Biodegradation*. **39** (2-3): 113-124
- Highley, T.L. 1970. Decay Resistance of Four Woods Treated to Destroy Thiamine. *Phytopathology* **60**: 1660-1661
- Highley, T.L., Clausen, C.A., Croan, S.C., Green, F., Illman, B.L. and Micales, J.A. 1992. Research on Biodeterioration of Wood. *United States Department of Agriculture Forest Products Laboratory Research Paper FPL-RP-529*
- Ishengoma, R.C., Gillah, P.R., Amartey, S.A. and Kitojo, D.H. 2004. Physical, Mechanical and Natural Decay Resistance Properties of Lesser Known and Lesser Utilized *Diospyros mespiliformis*, *Tyrachylobium verrucosum* and *Newtonia paucijuga* Timber Species from Tanzania. *Holz Roh Werkst* **62**: 387-389.
- Jerrold, E.W. 1994. Wood Properties. In: Arntzen, Charles, J., (ed), *Encyclopedia of Agricultural Science*. *Academic Press* **4**: 549-561
- Jiwarawat, P., Luangviriyaseng, V. and Woo, K.C. 1996. Hybrid Seeds of *Acacia Mangium* in Tree Important for Sustainable Tropical Forestry. QFRI-IUFRO 234-237
- Kamdem, D.P., Pizzi, A. and Jermannaud, A. 2002. Durability of Heat Treated Wood. *Holz als Roh und Werkstoff* **60**: 1-6.

- Kevin, M., Laurie, C. and Damian, S. 2009. Natural Durability of Six Eucalypt Species from Low Rainfall Farm Forestry. *Rural Industries Research and Development Corporation*. RIRDC 08/161
- Koichi, Y., Othman, S., Crispin, K., Ling, W.C. and Nguyen, T.N. 2003. Moisture Distribution in Stems of *Acacia Mangium* and *Acacia Auriculiformis* and Hybrid *Acacia* Tress. *JARQ* 37 (3): 207-212
- Kubojima, Y., Suzuki, Y. and Tonosaki, M. 2002. Real-Time Measurement of Vibrational Properties of Green Wood at High Temperature. *Wood and Fiber Science* 34: 643-650
- Kurisasi, H., Tsukamoto, E. and Mizumoto, K. 2001. Durability of Sugi (*Cryptomeria japonica* D. Don) Heartwood Dried at High Temperature against the Brown Rot Fungus, *Fomitopsis palustris* (in Japanese). *Wood Preservation* 27:6 – 66
- Latif, M.A. and Habib, M.A. 1994. Biomass Tables for *Acacia mangium* Grown in the Plantation in Bangladesh. *Journal Tropical Forest Science* 7 (2):296-302
- Le Dinh Kha. 2001. Studies on the Use of Natural Hybrids between *Acacia mangium* and *Acacia Auriculiformis* in Vietnam, Hanoi. Agriculture Publishing House.
- Lee, D.K., Nguyen, D.H. and Nguyen, V.T. 1993. Natural Hybrid between *Acacia mangium* and *Acacia auriculiformis* (in Vietnamase). *Forest Rev* 7:18-19
- Llewellyn, G.C., Dashek, W.V. and O'Rear, C.E. 1994. *Biodeterioration Research 4: Mycotoxin, Wood Decay, Plant Stress, Biocorrosion and General Biodeterioration*. Proceedings of 4th Meeting of the Pan American Biodeterioration Society. Aug: 20-25, 1994.

- Maria, L.L., Monica, A.M., Gabriel, D.K. and Marcelo, E.O. 2004. Patterns of Decay Caused by *Pycnoporus sanguineus* and *Ganoderma lucidum* (Aphyllophorales) in Poplar Wood. *IAWA Journal* **25**:425-433
- Martin, V.B. 2004. *Acacia Hybrids in Vietnam*, ACIAR Project FST/1986/030. Centre for International Economics. Canberra and Sydney, 44pp
- Militz, H. and Tjeerdsma, B. 2000. *Heat Treatment of Wood by the Plato Process*. Proceeding of Seminar on 'Production and Development of Heat Treated Wood in Europe. Oslo
- Momohara, I., Ohmura, W., Kato, H. and Kubojima, Y. 2003. *Effect of High-Temperature Treatment on Wood Durability against the Brown Rot Fungus Fomitopsis palustris and the Termite Coptotermes formosanus*. 8th International IUFRO Wood Drying Conference
- Nguyen, T.K., Junji, M., Kazuyuki, O. and Nguyen, V.C. 2009. Possibility if Improvement in Fundamental Properties of Wood of *Acacia* Hybrid by Artificial Hybridization. *Journal Wood Science* **55**:8-12
- Nguyen, T.K., Mikiko, O., Junji, M. and Kazuyuki, O. 2008. Variation in Wood Properties of Six Natural *Acacia* Hybrid Clones in Northern Vietnam. *Journal Wood Science* **54**:436-442
- Nguyen, T.N. and Nguyen, D.H. 2004. Growth Features and Wood Density of *Acacia mangium*, *Acacia auriculiformis* and *Acacia* hybrid in Dong Ha-Quang. *Tropical Forest Research* **4**:48-53
- Nguyen, V.T. 2002. Research on Structure Characteristic and Major Properties of *Acacia mangium* and *Acacia auriculiformis* at 8-9 Years of Age and

- Recommendation on How to Use It Effectively in Processing. *Journal Agriculture Rural Development* **11**:964-967
- Pinyopusarerk, K. 1993. Genetic Resources of Fifteen Tropical *Acacia*. In: Kamis, A. and Taylor, D.A. *Acacias for Rural Industrial and Environmental Developments*: Proceeding of the 2nd Meeting of the Consultative Group for Research and Development of Acacias. Thailand
- Rapp, A.O. and Sailer, M. 2000. *Heat Treatment in Germany*. Proceeding of Seminar 'Production and Development of Heat Treated Wood in Europe. Oslo
- Reinprecht, L. 1999. Changed Susceptibility of the Chemically and Thermally Degraded Spruce Wood to Its Attack by the Dry Rot Fungus *Serpula lacrymans*. *International Research Group on Wood Preservation IRG/WP* 99-10322
- Saila, J. and Pertti, V. 2001. Heat Treatment of Wood – Better Durability without Chemicals. In: *Review on Heat Treatments of Wood*. Proceedings of Special Seminar, France
- Sandra, L.B. and Micheal, L.R. 2005. Plant Water Relations and the Fiber Saturation Point. *New Phytologist* **168**:25-37
- Sehlstedt, P. 1995. High Temperature Drying of Scots Pine; A Comparison Between High Temperature and Low Temperature Drying. *Holz Roh Werkst* **53**:95-99.
- Shuichi, D., Masakazu, A., Shigeru, Y. and Yasuji, K. 2005. Changes of Decay and Termite Durability of Japanese larch (*Larix leptolepis*) Wood due to High-Temperature Kiln Drying Processes. *Journal Wood Science* **51**:526 – 530

- Simmons, M.H. 1987. The genus *Acacia*. In: MH Simmons (ed) *Acacias of Australia* 1:7–10. *Nelson Publishers*
- Sinclair, W.A., Lyon, H.H., Johnson, W.T. 1987. Diseases of Trees and Shrubs. *Cornell University Press*, Ithaca, New York
- Stephen, B.P., Marilen, M.P. and Kevin D.H. 2003. Production of Wood Decay Enzymes, Mass Loss and Lignin Solubilization in Wood by Tropical *Xylariaceae*. *Mycology Research*. 107 (2):231-235
- Syrjanen, T., Jamsa, S. and Viitaniemi, P. 2000. Heat *Treatment of Wood in Finland*. Proceeding of Seminar 'Production and Development of Heat Treated Wood in Europe. Oslo
- Thomasson, G., Capizzi, J., Dost, F., Morrell, J. and Miller, D. 1998. Wood Preservation and Wood Products Treatment Training Manual. *Oregon State University Extension Service*
- Tjeerdsma, B.F., Boonstra, M., Militz, H., 1998. Thermal Modification of Non-Durable Wood Species Part 2. Improved Wood Properties of Thermally Treated Wood. *International Research Group on Wood Preservation IRG/WP 98-40124*
- Tuula, S. and Kestopuu, O. 2001. Production and Classification of Heat Treated Wood in Finland. In: *Review on Heat Treatments of Wood, Proceedings of Special Seminar*. France
- Udarbe, M.P. and Hepburn, A.J. 1987. Development of *Acacia mangium* as a Plantation Species in Sabah. In: Turnbull JW (ed) *Australian Acacias in Developing Countries*. *ACIAR Proceedings* 16:157–159

- Venmalar, D. and Nagaveni, H.C. 2005. Evaluation of Copperised Cashew Nut Shell Liquid and Neem Oil as Wood Preservatives. *International Research Group on Wood Preservation* **IRG/WP 05-30368**
- Wang, J.Y. and Cooper, P.A. 2005. Effect of Oil Type, Temperature and Time on Moisture Properties of Hot Oil-Treated Wood. *Journal of Holz als Roh und Werkstoff* **63**:417-422.
- Weiland, J.J. and Guyonnet, R., 2003, Study on Chemical Modification and Fungi Degradation of Thermally Modified Wood using DRIFT Spectroscopy, *Journal of Holz als Roh und Werkstoff* **61**: 216-220.
- Wilkinson, J.G. 1979. Industrial Timber Preservation. *Associated Business Press*. London
- Yamamoto, K., 1998, Wood Quality of Planted *Acacia mangium*, **Mokuzai Kogyo** **53**: 350-355
- Yoshiyuki, O., Tadashi, N., Minoru, F. and Mohammed, H.S. 2002. A Synchronous Wood Formation in Young *Acacia mangium* Planted In Malaysia. *Journal of Wood Science* **48**:89-94
- Zabel, R.A. and Morrell, J.J. 1982. Wood Microbiology: Decay and its Prevention between Different Accelerated Test Methods for the Determination of the Natural Durability of Wood. *International Research Group on Wood Preservation* **IRG/WP 96-20099**
- Zohar, K., Kenneth, A.J. and Kenneth E.H. 1999. Biodegradative Mechanism of the Brown Rot Basidiomycete *Gloeophyllum trabeum*. *Evidence for an*

Extracellular Hydroquinone-Driven Fenton Reaction. Federation of European Biochemical Societies