



# The University of Bradford Institutional Repository

<http://bradscholars.brad.ac.uk>

This work is made available online in accordance with publisher policies. Please refer to the repository record for this item and our Policy Document available from the repository home page for further information.

To see the final version of this work please visit the publisher's website. Available access to the published online version may require a subscription.

**Link to publisher's version:** <http://dx.doi.org/10.1007/s11947-013-1210-9>

**Citation:** Contini C, Katsikogianni MG, O'Neill FT, O'Sullivan M, Boland F, Dowling DP and Monahan FJ (2014) Storage stability of an antioxidant active packaging coated with Citrus extract following a plasma jet pre-treatment. *Food and Bioprocess Technology*. 7(8): 2228-2240.

**Copyright statement:** © 2014 Springer. Reproduced in accordance with the publisher's self-archiving policy. The final publication is available at Springer via <http://dx.doi.org/10.1007/s11947-013-1210-9>.

1 **Storage stability of an antioxidant active packaging coated with Citrus extract following a**  
2 **plasma jet pre-treatment**

3  
4 C. Contini<sup>a</sup>, M.G. Katsikogianni<sup>b</sup>, F.T. O'Neill<sup>b</sup>, M. O'Sullivan<sup>a</sup>, F. Boland<sup>c</sup>, D.P. Dowling<sup>b</sup> and F.J.  
5 Monahan<sup>a</sup>

6  
7 <sup>a</sup> UCD School of Agriculture and Food Science, University College Dublin, Belfield, Dublin 4,  
8 Ireland

9 <sup>b</sup> UCD School of Mechanical and Materials Engineering, University College Dublin, Belfield, Dublin  
10 4, Ireland

11 <sup>c</sup> UCD School of Mathematical Sciences, University College Dublin, Belfield, Dublin 4, Ireland

12  
13 Contact: Frank Monahan, UCD School of Agriculture and Food Science, University College Dublin,  
14 Belfield, Dublin 4, Ireland (Tel.: +353 1 716 2842; e-mail: [frank.monahan@ucd.ie](mailto:frank.monahan@ucd.ie))

15  
16  
17 **ABSTRACT**

18  
19 Antioxidant active packaging was prepared by coating a Citrus extract on the surface of  
20 polyethylene terephthalate trays after plasma pre-treatment and compared with trays coated without  
21 plasma pre-treatment. Plasma pre-treatment increased coating density, thickness, and roughness, and  
22 oxygenated functional groups at the polymer surface, whereas water contact angle decreased. The  
23 stability of the active packaging was measured under three storage conditions over 24 weeks: room  
24 temperature, 0% relative humidity (RH) or 50 °C. Trays stored at room temperature did not lose their  
25 antioxidant efficacy over 24 weeks and plasma pre-treatment enhanced the efficacy from week 8  
26 onwards. Analysis of weight of the coating revealed a loss of antioxidant compounds only after 16  
27 weeks. Trays stored at 0% RH lost coating from week 1 onwards with lower loss in plasma pre-treated  
28 trays. Loss of coating was highest at 50 °C with lower loss in plasma pre-treated trays only after 24  
29 weeks.

30  
31 *Keywords:*

32 Active packaging; atmospheric pressure plasma jet; Citrus extract; lipid oxidation, turkey meat

33

## 34 INTRODUCTION

35

36 The shelf-life of lipid-containing foods, such as meat and meat products, is reduced by  
37 degradative processes like lipid oxidation that adversely affect organoleptic properties (Ladikos &  
38 Lougovois, 1990; Ruban, 2009). Among the different strategies that can be adopted to increase shelf  
39 life, the use of active packaging has received considerable attention in recent years (Suppakul, et al.,  
40 2003; Kerry et al., 2006).

41 Active packaging systems can be classified as either scavenging or releasing systems (De  
42 Kruijf et al., 2002). The former prevent food degradation and preserve organoleptic properties by  
43 adsorbing compounds like oxygen, moisture or taints, while the latter release compounds such as  
44 water, antioxidants or preservatives into the food (Vermeiren et al., 1999). Polyolefin films containing  
45 substances with antimicrobial or antioxidant properties have been developed by incorporating the  
46 compounds into the resin before the formation of the plastic film (Chen et al., 2012; Jin et al., 2009)  
47 or in the food contact layer of multilayer packaging materials, so that they can migrate into the food  
48 (van Aardt e al., 2007; Wessling et al., 2000).

49 Despite the availability of synthetic compounds with antioxidant activity, natural extracts  
50 from herbs, fruits, plants and spices have been widely studied as alternative additives for the  
51 preservation of food. Specifically, the addition of rosemary, oregano, olive, grape seed, or Citrus  
52 extracts has been shown to retard oxidation processes in meat (Murphy et al., 1998; Georgantelis et  
53 al., 2007; DeJong & Lanari, 2009; Contini et al., 2012). The use of natural extracts for the  
54 development of active packaging is therefore of interest.

55 Innovative approaches for surface modification of plastic materials offer the potential to  
56 significantly extend the range of new packaging methods for food preservation. By incorporating  
57 specific functional groups, the polymer surface can be altered to improve important characteristics  
58 such as wettability, sealability, printability and adhesion. Cold plasma treatments results in a surface  
59 modification that presents advantages over other surface treatment techniques, due to its speed of  
60 treatment, in addition to its ability to involve a very limited surface layer. A plasma is a partially  
61 ionized gas that consists of excited and ionized particles, photons and radicals. It is produced by  
62 means of an electrical discharge, it induces chemical reactions on the treated surface through complex  
63 mechanisms where active species in the plasma play a predominant role (Borcia et al., 2004 a, Borcia  
64 et al., 2004 b). As such, the gas used for plasma treatment largely affects the nature of the  
65 modifications to the polymer structure (Placinta et al., 1997), but also the cost of the process.

66 Due to their ease of application, there is considerable interest in the use of atmospheric  
67 pressure plasma jets (APPJs) for the activation of polymers (Foest et al., 2007, Bismarck et al., 2008;

68 Sun et al., 2010). The PlasmaTreat system is an example of APPJ which generates plasma in air and,  
69 due to its low cost and high efficiency, has been used extensively to activate polymers prior to  
70 adhesive bonding (Lommatzsch et al., 2007, Dowling et al., 2011). In this study, the use of this air  
71 plasma system as a pre-treatment of polyethylene terephthalate (PET) food trays, prior to the  
72 application of a Citrus extract, is investigated. The objective is to evaluate the antioxidant  
73 performance of the natural extract on both plasma activated and unactivated PET. To date, no plasma  
74 treatments have been reported in the preparation of an active packaging with antioxidant properties.

75 A previous study showed the effectiveness of an active packaging prepared by coating a Citrus  
76 extract on the surface of PET trays in reducing lipid oxidation in cooked turkey meat (Contini et al.,  
77 2012). The aim of the present study was twofold. Firstly, the study assessed the effects of plasma  
78 treatment on the morphology and retention characteristics of the Citrus extract coating on the PET  
79 surface and on the antioxidant efficacy of the Citrus-coated active packaging in reducing lipid  
80 oxidation in cooked turkey meat. Secondly, we evaluated the stability of the Citrus extract coating on  
81 the packaging under different environmental condition, by storing the Citrus coated trays for up to 24  
82 weeks at room temperature, 0% relative humidity (RH) or 50 °C, and then measuring their efficacy  
83 in reducing lipid oxidation in cooked meat.

84

## 85 **2. MATERIALS AND METHODS**

### 86 **2.1 Chemicals**

87 A commercially available natural Citrus extract in powder form containing carboxylic acids  
88 and flavanones was provided by Citrox Biosciences, Kimbolton, Cambridgeshire, England.  
89 Hydrochloric acid (37% w/w), 2-thiobarbituric acid (TBA, 98%), 1,1,3,3-tetraethoxypropane (TEP,  
90  $\geq 96\%$ ) and acetic acid ( $\geq 99\%$ ) were purchased from Sigma-Aldrich Ltd., Dublin, Ireland. Recycled  
91 polyethylene terephthalate (PET) trays (100 × 150 × 25 mm) were supplied by Holfeld Plastics  
92 Wicklow, Ireland. Low-density polyvinylchloride (PVC) catering film (thickness: 7.0  $\mu\text{m}$ ;  $\text{O}_2$   
93 transmission:  $2.000 \text{ cm}^3 \text{ m}^{-2} \text{ D}^{-1} \text{ bar}^{-1}$ ) was supplied by Western Plastic Ltd., Galway, Ireland.

94

### 95 **2.2 Preparation of the active packaging**

96 Plasma activated PET trays (PET-PA) were prepared by activating the surface of uncoated  
97 PET trays with an APPJ plasma system (PlasmaTreat GmbH, Steinhagen, Germany) as described  
98 previously (Dowling et al. 2011). The plasma treatment was applied using compressed air as working  
99 gas with an inlet pressure at 300 kPa. Following an iterative study, the system parameters used to

100 activate the PET samples were as follows: voltage of 5 kV, frequency of 20 kHz, plasma cycle time  
101 of 50% and nozzle speed of 250 mm s<sup>-1</sup>. The distance between the nozzle and the PET tray samples  
102 was 15.5 mm and one pass of plasma was used to activate the PET surface. The plasma was ‘flushed’  
103 through the jet nozzle mounted onto a cncGraf computer numerical control system (Boenigk  
104 Electronics, Bonn, Germany).

105 Citrus extract (10% w/v methanol solution) was deposited on the inner surface of both the  
106 untreated (PET) and the plasma pre-treated (PET-PA) trays through a Mira Mist high pressure  
107 nebuliser (Burgener Research Inc., Ontario, Canada), following a procedure described by Contini et  
108 al. (2012). The uncoated trays without (PET) and with (PET-PA) plasma pre-treatment were used as  
109 controls in subsequent comparisons with Citrus extract coated trays, PET-CIT and PET-PA-CIT,  
110 respectively.

111

## 112 **2.3 Surface characterization of PET and plasma treated PET**

### 113 **2.3.1 X-ray photoelectron spectroscopy and surface chemical composition**

114 The analysis of the elemental composition of the PET and PET-PA was carried out using the  
115 x-ray photoelectron spectrometer (XPS) technique (Fadley, 2010). This analysis was performed on  
116 square pieces (1×1 cm) cut from PET and PET-PA trays. The instrument used was a Kratos AXIS  
117 165 with a monochromated Al K $\alpha$  radiation at energy of 1486.6 eV. Survey spectra at pass energy of  
118 160 eV were acquired before and after the plasma pre-treatment of the PET surface. High resolution  
119 spectra of C 1s and O 1s were recorded at the surface and binding energies were determined using C  
120 1s peak at 284.8 eV as charge reference. For constructing and fitting the synthetic peaks of high  
121 resolution spectra a mixed Gaussian-Lorentzian function with a Shirley type background subtraction  
122 was used (Fadley, 1978).

123

### 124 **2.3.2 Surface wettability**

125 Surface wettability was examined by measuring the water contact angle (WCA) on square  
126 pieces (1×1 cm) cut from PET and PET-PA trays. The measurements were performed with the sessile  
127 drop technique at room temperature using the optical contact angle measuring instrument OCA 20  
128 (Dataphysics Instruments GmbH, Filderstadt, Germany). The average value of 6 measurements was  
129 determined. Measurements were carried out within one hour of plasma activation.

130

## 131 **2.4 Morphology of Citrus extract coating**

132 The surface roughness and film thickness of the Citrus extract coatings were measured using  
133 an optical profilometer (Wyko, NT1100) operating in vertical scanning interferometry mode. The  
134 instrument calculates the average surface roughness (Ra) as the arithmetic mean of the departures  
135 (peaks and valleys) from the centerline over the sampling length. From the variations in coating  
136 thickness an average thickness was estimated over the scanned surface at an instrumental resolution  
137 of approximately 5 nm. Each surface characterization measurement was repeated three times on each  
138 substrate for the statistical evaluation of the morphology parameters. Surface and cross sectional  
139 images of the deposited coatings were obtained using a FEI Quanta 3D FEG DaulBeam™ (FEI Ltd,  
140 Hillsboro, OR, USA) focused ion beam/scanning electron microscope (FIB/SEM) system.

141

## 142 **2.5 Assessment of antioxidant activity of trays**

143 Cooked turkey breast meat was used for the evaluation of the antioxidant activity of the trays.  
144 The meat was cooked and cut into slices using a procedure previously described by Contini et al.  
145 (2012). Nine meat slices (30 × 30 × 5.5 mm) per tray, were placed in direct contact with tray surface;  
146 the tray was then immediately overwrapped with a PVC catering film and placed in refrigerator at  
147 4 °C. After 0, 1 and 2 days of storage, the level of lipid oxidation was determined in 3 meat slices for  
148 each time using the TBARS distillation procedure described by Contini et al. (2012).

149

## 150 **2.6 Evaluation of the stability of the active packaging under different storage conditions**

151 To assess the stability of the antioxidant activity, the PET-CIT and PET-PA-CIT trays were  
152 stored under three different environmental conditions. A set of trays were stored at room temperature  
153 (approximately 20 °C and relative humidity (RH) of ~50%) and analyzed immediately after  
154 preparation and then after 2, 4, 8, 16, 24 weeks. Other sets of trays were placed in a desiccator  
155 (approximately 20 °C and RH of 0%) to understand the effects of a dry environment on the antioxidant  
156 efficacy. A final set of trays was placed in an oven at 50 °C to determine the influence of high storage  
157 temperatures. The trays stored at 0% RH and 50 °C were evaluated for their antioxidant efficacy only  
158 after 2 and 4 weeks. For each storage time considered, the antioxidant activity of PET-CIT trays and  
159 PET-PA-CIT trays was measured in triplicate and compared to that of the uncoated PET and PET-  
160 PA trays, respectively.

161

## 162 **2.7 Weight change of Citrus extract coatings on PET and plasma treated PET under different** 163 **storage conditions**

164 Changes in weight of the coated PET during storage were determined gravimetrically using a  
165 Sartorius CP225D analytical balance with a resolution of 0.01 mg. Discs of 34 mm diameter were cut  
166 from uncoated PET trays using a stainless steel punch. The discs were submitted to four the different  
167 treatments described in section 2.2: untreated (PET disc), plasma pretreated (PET-PA disc), Citrus  
168 extract coated without plasma pre-treatment (PET-CIT disc) and Citrus extract coated after plasma  
169 pre-treatment (PET-PA-CIT disc). The quantity of Citrus extract coated on PET discs was calculated  
170 as the difference in weight before and after the coating procedure. The value obtained after 3  
171 consecutive weighing differing by less than 0.2 mg was recorded as the initial weight of each disc  
172 (weight at time 0). For each treatment three discs were then stored under the three different  
173 environmental conditions (room temperature; 0% RH at room temperature; 50 °C). Changes in disc  
174 weight were monitored after 1, 2, 4, 8, 16 and 24 weeks following the same weighing procedure as at  
175 time 0. The weight change across the treatments and storage conditions was calculated as follows:

$$176$$
$$177 \quad W^c (\text{PET-CIT disc}) = W^t (\text{PET-CIT disc}) - W^0 (\text{PET-CIT disc})$$
$$178 \quad W^c (\text{PET disc}) = W^t (\text{PET disc}) - W^0 (\text{PET disc})$$

179

180 where  $W^0$ = weight of discs at time 0;  $W^t$ = weight of discs at time t;  $W^c$ = weight change of discs

181

182 The change in weight of Citrus extract coating ( $W^{cc}$ ) from the different types of disc treatments,  
183 corrected for change in weight of the PET disc, was then calculated as follows:

$$184$$
$$185 \quad W^{cc} (\text{PET-CIT disc}) = W^c (\text{PET-CIT disc}) - W^c (\text{PET disc})$$

186

187 The same calculation was applied to determine the weight change of Citrus extract in PET-PA-CIT  
188 discs.

189

## 190 **2.8 Statistical analysis**

191 Each experiment was conducted in triplicate and results were expressed as the mean  $\pm$   
192 standard deviation of the three replicates. Statistical analysis of the data was performed using one-  
193 way analysis of variance (ANOVA) and Bonferroni's test by SPSS (version 18) statistical software  
194 (IBM Inc. Chicago, IL, USA).

195

## 196 **3. RESULTS**

197

### 198 **3.1 Effect of plasma pre-treatment on chemical composition and wettability of the PET surface**

199 The chemical composition of the PET surface was determined by analysing the high resolution  
200 XPS spectra. The deconvolution of the C 1s and O 1s peaks revealed the binding energies of carbon  
201 and oxygen, which are indicative of the nature of the chemical bonds of these two elements on the  
202 PET surface. For untreated PET, the C 1s spectrum was fitted with three peaks (Figure 1a) at 284.8  
203 eV, 286.6 eV and 288.8 eV, which correspond to bonds typical of a benzene ring (C-C, C=C),  
204 methylene carbon singly bound to oxygen (-C-O-) and ester carbon atoms (O-C=O), respectively  
205 (Gupta et al., 2002; Jie-Rong et al., 1999). The additional small broad peak at approximately 292 eV  
206 corresponds to  $\pi$ - $\pi^*$  shake up satellites in phenyl groups (Placinta et al., 1997). The O 1s spectrum,  
207 on the other hand, showed two peaks at 531.9 eV and 533.5 eV (Table 1), which can be attributed to  
208 the carbonyl oxygen (O=C) and singly bonded oxygen atoms in the ester groups (O-C) (Girardeaux  
209 et al., 1996).

210 The XPS analysis of the PET-PA samples revealed significant modifications in the chemical  
211 structure of the PET surface induced by the plasma pre-treatment (Figure 1b). The decrease in C=C/C-  
212 C together with an increase in -C-O- bonds (Table 1) indicates the substitution of hydrogen of  
213 aromatic rings by hydroxyl groups (Riccardi et al., 2003). Another evident modification in the  
214 polymer structure is the appearance of a new carbon peak with a binding energy of 287.6 eV,  
215 suggesting the introduction of carbonyl groups (Girardeaux et al., 1996; Cueff et al., 1997; Choi et  
216 al., 2004) Besides, the broadening of the peaks after plasma treatment, expressed by the larger full  
217 width at half height maximum (Table 1), further suggests the presence of other species too close in  
218 binding energies to be discriminated from the existing peaks, such as hydroxyl and hydroperoxide  
219 groups at 286.4 eV and carboxylic groups at 288.8 eV (Cueff et al., 1997; Gupta et al., 2002). The  
220 existence of these new oxygen reactive sites in the plasma-treated polymer structure was also  
221 confirmed by an increase in the intensity of the two peaks obtained from the deconvolution of oxygen  
222 and by the increase in the O 1s/C 1s ratio from 0.27 to 0.59 (Table 1).

223 The changes in chemical composition with the introduction of these new chemical groups  
224 resulted in an increase of hydrophilicity of the polymer surface, as indicated by the results of WCA  
225 measurement, which showed a decrease in WCA from  $84.0 \pm 4.5^\circ$  for PET (control) to  $33.7 \pm 3.6^\circ$  for  
226 PET-PA samples.

227

### 228 **3.2 Effect of storage conditions and plasma pre-treatment on the morphology of Citrus extract** 229 **coating**



230 The optical profilometer results revealed the morphology of the Citrus extract coating on the  
231 PET surface, the effect of the plasma pre-treatment and the effect of the three different storage  
232 conditions. The plasma pre-treatment resulted in the adhesion of a significantly thicker Citrus coating  
233 on the PET surface. In fact, the initial values of coating thickness were  $1.70\pm 0.61\ \mu\text{m}$  for the PET-  
234 CIT discs (Figure 2a), while after treatment the PET-PA-CIT discs exhibited a thickness of  $4.41\pm 0.42$   
235  $\mu\text{m}$  (Figure 2b). The Citrus extract layer deposited using both processes was found to exhibit a  
236 decrease in thickness with storage time. The reduction in thickness was the lowest at 0% RH storage  
237 conditions (Figure 2a). The most pronounced loss in coating thickness was observed for storage at  
238  $50\ ^\circ\text{C}$ , resulting in lower values compared to the other treatments at week 1 and week 2. The coating  
239 thickness on the PET-PA-CIT discs remained significantly higher ( $p<0.01$ ) than that on the PET-CIT  
240 discs for all storage conditions and times ( $p<0.01$ ) (Figure 2a and 2b).

241 The optical profilometry examination demonstrated that the PET-PA-CIT coatings exhibited  
242 significantly higher roughness (Ra) values (Figure 3). The Ra for the PET-CIT discs was  $1.13\pm 0.18$   
243  $\mu\text{m}$  while that for the PET-PA-CIT discs was  $3.34\pm 1.52\ \mu\text{m}$  for (Figure 3a and 3b). The roughness  
244 values of PET-CIT discs remained significantly lower ( $p<0.01$ ) than those of the PET-PA-CIT discs  
245 for all the storage conditions and times. For both treatments, the roughness of samples stored at room  
246 temperature and 0% RH were similar, while the decrease in roughness at  $50\ ^\circ\text{C}$  was much greater  
247 with significantly lower values at week 1 and week 2 for PET-CIT discs ( $p<0.01$ ) and at week 1, 2, 4  
248 and week 8 for PET-PA-CIT discs ( $p<0.01$ ). The tribology results were further supported by SEM  
249 which shows a thicker, rougher coating on the plasma pre-treated PET surface, compared to the  
250 unactivated control (Figure 4).

251

### 252 **3.3 Effect of storage conditions and plasma pre-treatment on the weight of Citrus extract** 253 **coating**

254 The initial amount of Citrus extract coating deposited was calculated as  $4.14\pm 0.72\ \text{mg}$  for  
255 PET-CIT discs and  $7.08\pm 0.06\ \text{mg}$  for PET-PA-CIT discs. The weight change of the Citrus extract  
256 coated on trays stored at room temperature, expressed as mg of coating weight loss, showed a very  
257 low decreasing trend up to week 8 for both PET-CIT and PET-PA-CIT discs (Figure 5a). A more  
258 pronounced weight loss was observed at week 16 and week 24, to reach maximum loss values of  
259  $1.25\pm 0.03\ \text{mg}$  for PET-CIT discs and  $1.29\pm 0.16\ \text{mg}$  for PET-PA-CIT discs. This represented  
260  $30.17\pm 0.86\ \%$  and  $18.28\pm 2.58\ \%$  of the initial coating deposited on the PET-CIT and PET-PA-CIT  
261 trays, respectively. Differences between the two types of discs were not significant at any storage  
262 time. The results for the discs stored at 0% RH revealed more pronounced differences in weight loss  
263 between PET-CIT and PET-PA-CIT discs. The untreated coated discs exhibited a significantly higher

264 rate of weight loss ( $p<0.01$ ) from week 1 onwards ( $p<0.01$ , except for week 16) compared with the  
265 discs that had been subjected to the plasma pre-treatment. The total weight loss of  $1.34\pm 0.06$  mg,  
266 obtained at week 24 (Figure 5b), represented  $32.29\pm 1.05\%$  of the initial coating deposited. For the  
267 PET-PA-CIT discs, in contrast, the weight loss trend was more similar to that obtained at room  
268 temperature, with a slow weight loss during the first 8 weeks followed by a higher loss at week 16  
269 and week 24, up to a final value of  $0.86\pm 0.02$  mg ( $12.10\pm 1.22\%$  of the initial coating deposited).  
270 Storage at 50 °C had a much higher impact on the loss of coating weight for both types of discs,  
271 resulting in a decrease of coating weight after one week of  $1.65\pm 0.06$  and  $1.97\pm 0.10$  for PET-CIT  
272 and PET-PA-CIT discs, respectively. Hence, the loss in weight after one week at 50 °C was  
273 significantly higher ( $p<0.01$ ) than the maximum weight loss for the other storage conditions during  
274 the whole experimental period (Figure 5c). After the rapid and pronounced initial decrease, the  
275 coating weight remained stable and similar for the two treatments until week 16. For the plasma  
276 treated discs no further weight loss was detected at week 24, whereas the untreated discs showed a  
277 loss of coating of  $4.15\pm 0.413$  mg by the end of storage period, a value significantly higher than that  
278 observed for the PET-PA-CIT discs ( $p<0.01$ ).

279

### 280 **3.4 Effect of storage conditions and plasma pre-treatment on the antioxidant activity of the** 281 **active packaging**

282 The antioxidant activity of the Citrus extract coating was evaluated by the % reduction in  
283 TBARS values measured in the meat stored on PET-CIT and PET-PA-CIT trays compared to meat  
284 stored on uncoated PET and PET-PA trays, respectively. The trays stored at room temperature  
285 showed a reduction in lipid oxidation at week 0 of  $36.7\pm 11.8\%$  and  $49.1\pm 11.1\%$  for PET-CIT and  
286 PET-PA-CIT trays, respectively (Figure 5). During the experiment the reduction of TBARS values  
287 remained almost unchanged in time, with the exception of the meat measured at week 8, for which  
288 the antioxidant effects were higher for both treatments. This likely relates to the lower initial oxidation  
289 of the meat used at week 8 compared to the other times periods (Table 2). A possible explanation  
290 could be a shorter cooking time due to the smaller size of the turkey breast used at week 8, which  
291 may have resulted in lower initial oxidation levels (Peiretti et al., 2012). Throughout the 24 weeks of  
292 the study the oxidation levels in the meat stored on both the PET-CIT and PET-PA-CIT trays were  
293 significantly lower ( $p<0.01$ ) than those of the corresponding controls (PET and PET-PA,  
294 respectively) (Table 2), indicating that the antioxidant activity of the packaging was stable over 24  
295 weeks of storage. The reduction in TBARS values in meat samples stored on PET-PA-CIT trays was

296 more pronounced than for those stored on PET-CIT trays at all weeks, but the differences between  
297 the two treatments were statistically significant only from week 8 onwards ( $p < 0.01$ ).

298 The antioxidant activity for the trays stored at 0% RH was slightly lower compared to storage  
299 at room temperature, with % reduction in lipid oxidation values of  $21.99 \pm 10.8\%$  for PET-CIT trays  
300 and  $38.7 \pm 8.0\%$  for PET-PA-CIT trays at week 4 (Figure 6). The differences between the two  
301 treatments (PET-CIT vs PET-PA-CIT), however, were not statistically significant. Moreover, all the  
302 trays stored at 0% RH maintained their antioxidant efficiency, as revealed by the significant lower  
303 TBARS values ( $p < 0.05$ ) than those of the controls (Table 2). The loss of antioxidant efficiency with  
304 storage was most pronounced for the trays stored at 50 °C, with TBARS reductions of  $8.71 \pm 15.5\%$   
305 and  $27.3 \pm 20.3\%$  for the PET-CIT and PET-PA-CIT trays at week 4, respectively (Figure 6). Under  
306 these storage conditions, the PET-CIT trays lost their antioxidant activity even after 2 weeks of  
307 storage, as indicated by the lack of a significant difference compared to uncoated control (Table 2).  
308 The results also show a large variability, as indicated by the high error bars. This is likely due to the  
309 degradation of the antioxidant coating with increasing temperature, reducing the interaction between  
310 the active substances and the meat. The results for trays stored at 50 °C further confirmed the  
311 enhancement of the stability of the Citrus extract coating provided by the plasma pre-treatment,  
312 expressed by the significantly lower TBARS values ( $p < 0.05$ ) compared to the control (Table 2).

313

#### 314 4. DISCUSSION

315 The initial weight of Citrus extract coatings on the surface of PET-CIT and PET-PA-CIT discs  
316 ( $4.14 \pm 0.72$  mg vs  $7.08 \pm 0.06$  mg) clearly suggests that the modification of the PET surface induced  
317 by the plasma pre-treatment was effective in increasing the amount of the extract coating adhering to  
318 the polymer surface. This effect was confirmed by the higher coating thickness value of  $4.41 \pm 0.42$   
319  $\mu\text{m}$  for PET-PA-CIT discs compared to  $1.70 \pm 0.61$   $\mu\text{m}$  for PET-CIT discs. Other studies on the effect  
320 of plasma treatments of PET polymers have also shown an increase of PET surface roughness due to  
321 the removal of additives, processing aids or fragments of the polymer by etching effects (Gupta et al.,  
322 2002; Yang et al., 2009). Therefore, the higher polymer surface available for the adhesion of the  
323 Citrus extract constituents due to the increased PET roughness, could in part explain the higher  
324 amount of coating found in the PET-PA-CIT discs.

325 The adhesion of the coating on the PET surface is also determined by the chemical affinity  
326 between Citrus extract components and the polymer. In our previous study the Citrus extract coating  
327 appeared hydrophilic with a WCA of  $22 \pm 0.6^\circ$  (Contini *et al.*, 2012) due possibly to the flavanones  
328 contained in the extract which are rich in oxygenated functional groups such as hydroxyl and keto

329 groups (Yanishlieva et al., 2006; Belitz et al., 2009), while citric and salicylic acid contain carboxyl  
330 groups. Therefore, during the deposition of the extract, polar interactions could take place between  
331 its components to form a layer on the polymer surface. The establishment of polar interactions  
332 between the Citrus extract coating and the oxygenated functional groups of the plasma pre-treated  
333 PET surface could further enhance the stability of the antioxidant coating. In that respect, the higher  
334 hydrophilicity of the polymer surface after plasma pre-treatment, indicated by the decrease in WCA  
335 value, could have contributed to the enhancement in Citrus extract deposition. In fact, dipole  
336 interactions and hydrogen bonds could take place between the carbonyl, hydroxyl, hydroperoxide and  
337 carboxyl groups, formed on the PET surface after plasma treatment, as confirmed by XPS, and the  
338 antioxidant molecules. Besides, reactions between hydroperoxides on the plasma pre-treated PET  
339 surface and carboxyl groups of citric and salicylic acid could induce the formation of covalent bonds,  
340 in a similar way to that observed in grafting processes of acrylic acid on PET polymers (Ying et al.,  
341 2003).

342 The higher roughness of the Citrus extract coating observed in the PET-PA-CIT discs  
343 compared to PET-CIT discs ( $3.34\pm 1.52\ \mu\text{m}$  vs  $1.13\pm 0.18\ \mu\text{m}$ ) could be a consequence of the higher  
344 amount of Citrus extract coated on the discs surface, amplifying a 'cluttered' disposition of the  
345 antioxidant molecules during the coating process. Nevertheless, it could also be a consequence of the  
346 higher surface roughness of the polymer induced by the plasma pre-treatment that was reflected in  
347 the coating morphology.

348 The measurement of the weight loss of the coated discs stored at room temperature indicated  
349 that the antioxidant coating exhibited a high degree of stability up to week 8, with a final loss of  
350  $30.17\pm 0.86\%$  of the initial coating weight in the case of PET-CIT. This weight loss however did not  
351 have a significant effect on the antioxidant properties of the active packaging, which remained  
352 remarkably constant throughout the storage period. This suggests that either the components lost did  
353 not contribute to the antioxidant effect or the amount lost was not sufficient to reduce the efficacy of  
354 the packaging. In addition, the decrease in coating thickness, observed during the first 4 weeks of  
355 storage (Figure 2a), resulted from a rearrangement of the molecule disposition on the surface without  
356 a loss of components. Modifications in surface roughness were minor with a slight decrease in  
357 accordance with the loss of coating components (Figure 3a). The effect of plasma pre-treatment  
358 enhanced the adhesion of the antioxidant substances, resulting in a final loss in active substances of  
359 only  $18.28\pm 2.58\%$  of the initial value. This may explain the significantly higher reduction of TBARS  
360 values compared to PET-CIT trays from week 8 onwards (Figure 6).

361 The results for storage at 0% RH suggest an influence of the air humidity on the stability of  
362 the Citrus extract coating, with a higher weight loss throughout the whole storage period, compared  
363 to the results observed for the discs stored at room temperature (Figure 5b). The beneficial effect of  
364 plasma pre-treatment on the stability of the antioxidant coating was further confirmed by the lower  
365 coating weight loss observed in PET-PA-CIT discs. It is interesting to note that, even if the weight  
366 loss observed at 0% RH at week 4 was lower than that observed at room temperature at week 24  
367 (Figure 5a and 5b), the TBARS reduction obtained at week 4 (Figure 7) was lower than that obtained  
368 at week 24 for the trays stored at room temperature (Figure 6). This may indicate that the Citrus  
369 extract constituents lost at 0% RH were different from those lost at room temperature. Another  
370 possible explanation is that the lower decrease in film thickness compared to that observed at room  
371 temperature (Figure 2a) may suggest a different rearrangement of the molecules of the coating  
372 induced by the lack of air humidity, which decreased the antioxidant effect.

373 An immediate and noticeable decrease in all the physical parameters indicated a loss of the  
374 coating at 50 °C, which was also observed visually. Presumably, the higher temperature weakened  
375 the adhesion of the Citrus extract components, with a loss of arguably the more volatile components  
376 of the coating. The degradation of the coating explains the loss of the antioxidant activity of the PET-  
377 CIT trays already apparent at week 2 (Figure 7). Although the reduction of lipid oxidation decreased  
378 also for the PET-PA-CIT trays, the plasma pre-treatment facilitated superior Citrus extract coating  
379 performance, with antioxidant activity maintained until week 4.

380

## 381 **Conclusions**

382 The study on the effect of plasma pre-treatment and storage conditions on the effectiveness  
383 of PET packaging coated with Citrus extract showed that the antioxidant effect of the active  
384 packaging exhibited good stability even after storage for a period of up to 24 weeks. The antioxidant  
385 performance was further enhanced by the plasma pre-treatment of the trays, which resulted in the  
386 incorporation of oxygenated functional groups onto the plasma activated surface. Under given spray  
387 deposition conditions, significantly enhanced levels of Citrus extract were obtained on the plasma  
388 pre-treated PET surface, possibly due to its more hydrophilic chemistry. This thicker and more  
389 adherent coating (based on weight loss studies), exhibited superior antioxidant effect, compared to  
390 the Citrus coating deposited onto the unactivated polymer. The storage of the PET at 0% RH and  
391 particularly at 50 °C accelerated the degradation of the coating, reducing the antioxidant properties  
392 of the packaging, although the plasma pre-treatment still enhanced stability. These promising results

393 indicate the suitability of the active packaging with plasma pre-treatment for commercial use because  
394 of its potential to preserve meat products from oxidative degradation.

395

396 Note: This work was undertaken within the Precision Strategic Research Cluster supported by Science

397 Foundation Ireland grant 08/SRC/I1411.

398

399 **References**

400

401 Belitz H-D, Grosch W & Schieberle P (2009) Fruits and fruit products. In Food Chemistry, pp 807-  
402 861). Springer, Berlin, Heidelberg.

403

404 Bismarck A, Brostow W, Chiu R, Lobland H-E-H & Ho K-K-C (2008) Effects of surface plasma  
405 treatment on tribology of thermoplastic polymers. Polymer Engineering and Science, 1971-1976.

406

407 Borcia C, Anderson C-A & Brown N-M-D (2004a) The surface oxidation of selected polymers using  
408 at atmospheric pressure air dielectric barrier discharge. Part I. Journal of Applied Surface Science,  
409 221, 203-214.

410

411 Borcia C, Anderson C-A & Brown N-M-D (2004b) The surface oxidation of selected polymers using  
412 at atmospheric pressure air dielectric barrier discharge. Part II. Journal of Applied Surface Science,  
413 225, 186-197.

414

415 Chen X, Lee D-S, Zhu X & Yam K-L (2012). Release kinetics of tocopherol and quercetin from  
416 binary antioxidant controlled-release packaging films. Journal of Agricultural and Food Chemistry,  
417 60, 3492-3497.

418

419 Choi H-S, Kim Y-S, Zhang Y, Tang S, Myung S-W & Shin B-C (2004) Plasma-induced graft co-  
420 polymerization of acrylic acid onto the polyurethane surface. Surface & Coating Technology, 182,  
421 55-64.

422

423 Contini C, Katsikogianni M-G, O'Neill F-T, O'Sullivan M, Dowling D-P & Monahan F-J (2012)  
424 PET trays coated with Citrus extract exhibit antioxidant activity with cooked turkey meat. Food  
425 Science and Technology, 47, 471-477.

426

427 Cuff R, Band G, Benmalek M, Besse J-P, Butruille J-R & Jaquet M (1997) X-ray photoelectron  
428 spectroscopy studies of plasma-modified PET surface and alumina/PET interface. Journal of Applied  
429 Polymer Science, 115, 292-298.

430

431 DeJong S & Lanari M-C (2009) Extracts of olive polyphenols improve lipid stability in cooked beef  
432 and pork: contribution of individual phenolics to the antioxidant activity of the extract. *Food*  
433 *Chemistry*, 116, 892-897.

434

435 Dowling D-P, O'Neill F-T, Langlais S-J & Law V-J (2011) Influence of dc pulsed atmospheric  
436 pressure plasma jet processing conditions on polymer activation. *Plasma Processes and Polymers*, 8  
437 (8), 718-727.

438

439 Fadley C-S (1978) Basic Concepts of X-ray Photoelectron Spectroscopy. In C. R. Brundle, A. D.  
440 Baker (Eds.), *Electron Spectroscopy: Theory, Techniques and Applications*, pp 2-145. Academic  
441 Press, London . New York . San Francisco.

442

443 Fadley C-S (2010) X-ray photoelectron spectroscopy: progress and perspectives. *Journal of Electron*  
444 *Spectroscopy and Related Phenomena*, 178-179, 2-32.

445

446 De Kruijf N, Van Beest M, Rijk R, Sipiläinen-Malm T, Paseiro Losada P & De Meulenaer B (2002)  
447 Active and intelligent packaging: applications and regulatory aspects. *Food Additives and*  
448 *Contaminants*, 19, 144-162.

449

450 Foest R, Bindemann T, Brandenburg R, Kindel E, Lange H, Stieber M & Weltmann K-D (2007) On  
451 the vacuum ultraviolet radiation of a miniaturized non-thermal atmospheric pressure plasma jet.  
452 *Plasma Processes and Polymers*, 4, 460-464.

453

454 Georgantelis D, Ambrosiadis I, Katikou P, Blekas G & Georgakis S-A (2007) Effect of rosemary  
455 extract, chitosan and tocopherol on microbiological parameters and lipid oxidation of fresh pork  
456 sausages stored at 4 °C. *Meat Science*, 7, 172-181.

457

458 Girardeaux C, Zammattéo N, Art M, Gillon B., Pireaux J-J & Caudano R (1996) Animation of  
459 poly(ethylene terephthalate) polymer surface for biomedical application. *Plasmas and Polymers*, 1(4),  
460 327-346.

461



462 Gupta B, Plummer C, Bisson I, Frey P & Hilborn J (2002) Plasma-induced graft polymerization of  
463 acrylic acid onto poly (ethylene terephthalate) film: characterization and human smooth muscle cell  
464 growth on grafted film. *Biomaterials*, 23(3), 863-871.

465

466 Jie-Rong C, Xue-Yan W & Tomiji W (1999) Wettability of poly(ethylene terephthalate) film treated  
467 with low-temperature plasma and their surface analysis by ESCA. *Journal of Applied Surface  
468 Science*, 72(10), 1327-1334.

469

470 Jin X, Zumbrennen D-A, Balasubramanian A & Yam K (2009) Tailored additive release rates in  
471 extruded plastic films produced with smart blending machines. *Journal of Plastic Film and Sheeting*,  
472 425, 115-140.

473

474 Kerry J-P, O'Grady M-N & Hogan S-A (2006) Past, current and potential utilization of active and  
475 intelligent packaging systems for meat and muscle-based products: A review. *Meat Science*, 74, 113-  
476 130.

477

478 Ladikos D & Lougovois V (1990) Lipid oxidation in muscle food: A Review. *Food Chemistry*, 35,  
479 295-314.

480

481 Lommatzsch U, Pasedag D, Baalman A & Ellinghorst G (2007) Atmospheric pressure plasma jet  
482 treatment of polyethylene surfaces for adhesion improvement. *Plasma Processes and Polymers*, 4,  
483 1041-1045.

484

485 Murphy A, Kerry J-P, Buckley J & Gray I. (1998) The antioxidative properties of rosemary oleoresin  
486 and inhibition of off-flavours in precooked roast beef slices. *Journal of Science and Food Agriculture*,  
487 77, 235-243.

488

489 Peiretti P-G, Medana C, Visentin S, Dal Bello F & Meineri G (2012) Effect of cooking method on  
490 carnosine and its homologues, pentosidine and thiobarbituric acid reactive substance contents in beef  
491 and turkey meat. *Food Chemistry*, 132, 80-85.

492

493 Placinta G, Arefi-khonsari F, Gheorghiu M, Amouroux J & Popa G (1997) Surface properties and the  
494 stability of poly(ethylene terephthalate) films treated in plasmas of helium-oxygen mixtures. *Journal  
495 of Applied Polymer Science*, 66, 1367-1375.

496  
497 Riccardi C, Barni R, Selli E, Mazzone G, Massafranca M-R, Marcandalli B & Poletti G (2003).  
498 Surface modification of poly (ethylene terephthalate) fibers induced by radio frequency air plasma  
499 treatment. *Journal of Applied Surface Science*, 211, 386-397.  
500  
501 Ruban S-W (2009). Lipid peroxidation in muscle food - An overview. *Global Veterinaria*, 3(6), 509-  
502 513.  
503  
504 Sun J, Yao L, Gao Z, Peng S, Wang C, & Qiu Y (2010) Surface modification of PET films by  
505 atmospheric pressure plasma-induced acrylic acid inverse emulsion graft polymetization. *Surface &*  
506 *Coating Technology*, 204, 4101-4106.  
507  
508 Suppakul P, Miltz J, Sonneveld K & Bigger S-W (2003) Active packaging technologies with an  
509 emphasis on antimicrobial packaging and its applications. *Journal of Food Science*, 68(2), 408-420.  
510  
511 van Aardt M, Duncan S-E, Marcy J-E, Long T-E, O'Keefe SF & Sims S-R (2007) Release of  
512 antioxidants from poly(lactide-co-glycolide) films into dry milk products and food simulating liquids.  
513 *International Journal of Food Science and Technology*, 42(11), 1327-1337.  
514  
515 Vermeiren L, Devlieghere F, Debevere J, Smolander M, Hurme E, Ahvenainen R, Van Beest M-D &  
516 Rijk, M-A-H (1999) An in-depth review of technologies, legislation, market and consumer needs and  
517 trends in active and intelligent packaging in relation to current European food packaging regulations.  
518 Literature review of FAIR-project Actipak (CT 98-4170), October, 55p.  
519  
520 Wessling C, Nielsen T & Giacini J-R (2000) Antioxidant ability of BHT- and  $\alpha$ -tocopherol-  
521 impregnated LDPE film in packaging of oatmeal. *Journal of the Science of Food and Agriculture*, 81,  
522 194-20.  
523  
524 Yang L, Chen J, Guo Y & Zhang Z (2009) Surface modification of a biomedical polyethylene  
525 terephthalate (PET) by air plasma. *Applied Surface Science*, 255, 4446-4451.  
526  
527 Yanishlieva N-V, Marinova E & Pokorný J (2006) Natural antioxidants from herbs and spices.  
528 *European Journal of Lipid Science and Technology*, 108, 776-793.

529

530 Ying L, Yin C, Zhuo R-X, Leong K-W, Mao H-Q, Kang T-E & Neoh K-G (2003) Immobilization of  
531 galactose ligands on acrylic acid graft-copolymerized poly(ethylene terephthalate) film and its  
532 application to hepatocyte culture. *Biomacromolecules*, 4, 157-165.

533

534

535 **Figure 1.** XPS spectra of PET samples: C 1s spectrum analysis of (a) virgin PET and (b) plasma  
536 activated PET (PET-PA).

537

538 **Figure 2.** Coating thickness of (a) PET-CIT discs and (b) PET-PA-CIT discs stored at room  
539 temperature (open circle), discs stored at 0% RH (open square), discs stored at 50 °C (open triangle).  
540 <sup>a,b,c</sup> Within each storage time, points with different letters are significantly different due to the  
541 treatment ( $p < 0.01$ ). <sup>x,y,z</sup> Within each treatment, points with different letters are significantly different  
542 due to the storage time ( $p < 0.01$ ).

543

544 **Figure 3.** Coating roughness of (a) PET-CIT discs and (b) PET-PA-CIT discs stored at room  
545 temperature (open circle), discs stored at 0% RH (open square), discs stored at 50 °C (open triangle).  
546 <sup>a,b</sup> Within each storage time, points with different letters are significantly different due to the treatment  
547 ( $p < 0.01$ ). <sup>x,y,z</sup> Within each treatment, points with different letters are significantly different due to the  
548 storage time ( $p < 0.01$ ).

549

550 **Figure 4.** SEM images of PET trays coated with Citrus extract; PET-CIT (a) and PET-  
551 PA-CIT (b).

552

553 **Figure 5.** Coating weight loss of Citrus extract from PET-CIT discs (filled circle) and PET-PA-CIT  
554 discs (open circle). The discs were stored (a) at room temperature (b) at 0% RH and (c) at 50 °C for  
555 periods of up to 24 weeks. <sup>a,b</sup> Within each storage time, points with different letters are significantly  
556 different due to the treatment ( $p < 0.01$ ). <sup>x,y,z</sup> Within each treatment, points with different letters are  
557 significantly different due to the storage time ( $p < 0.01$ ).

558

559 **Figure 6.** Percentage reduction in TBARS values of cooked turkey meat after 2 days storage at 4 °C  
560 on PET-CIT trays (black columns) and PET-PA-CIT trays (grey columns) previously stored for

561 periods of up to 24 weeks at room temperature. <sup>a,b</sup> Within each storage time, bars with different letters  
562 are significantly different due to the treatment ( $p<0.01$ ). <sup>y,z</sup> Within each treatment, bars with different  
563 letters are significantly different due to the storage time ( $p<0.01$ ).

564

565 **Figure 7.** Percentage reduction in TBARS values of cooked turkey meat after 2 days storage at 4 °C  
566 on PET-CIT trays (black column) and PET-PA-CIT trays (dark grey column) previously stored for  
567 up to 4 weeks at 0% RH, and on PET-CIT trays (white column) and PET-PA-CIT trays (light grey  
568 column) previously stored for up to 4 weeks at 50 °C. <sup>a</sup> Within each storage time, bars with similar  
569 letters are not significantly different due to the treatment ( $p<0.05$ ). <sup>z</sup> Within each treatment, bars with  
570 similar letters are not significantly different due to the storage time ( $p<0.05$ ).

571

572 **Table 1.** Relative composition (%) of the different chemical groups detected with the deconvolution  
 573 of C 1s and O 1s spectra (in parenthesis, full width at half maximum height values expressed as  
 574 eV).  
 575

	C 1s				O 1s		O 1s/C 1s
Peaks deconvolution	C1	C2	C3	C4	O1	O2	
Functional groups	C-C, C=C	-C-O-	O-C=O	-C=O	O=C	O-C	
Binding energy (eV)	284.8	286.4	288.8	287.6	531.9	535.5	
<b>PET</b>	59.5 (1.1)	9.5 (1.0)	8.0 (0.8)	0	12.1 (1.1)	9.1 (1.3)	0.27
<b>PET-PA</b>	33.0 (1.1)	15.4 (1.2)	8.6 (1.0)	3.8 (1.0)	21.0 (1.5)	15.3 (1.6)	0.59


576

577 **Table 2.** TBARS values of cooked turkey meat after 2 days storage at 4 °C on trays previously stored  
 578 at room temperature, 0% relative humidity or 50 °C for periods of up to 24 weeks. <sup>a,b,c</sup> Within each  
 579 storage period, values with different letters are significantly different (p<0.05) due to the treatment.  
 580  
 581  
 582


Room temperature				
Week	PET	PET-CIT	PET-PA	PET-PA-CIT
0	6.25±0.71 <sup>b</sup>	3.92±0.73 <sup>a</sup>	6.45±0.65 <sup>b</sup>	3.23±0.45 <sup>a</sup>
2	5.75±0.20 <sup>b</sup>	3.93±0.06 <sup>a</sup>	5.73±0.17 <sup>b</sup>	3.34±0.13 <sup>a</sup>
4	5.60±0.75 <sup>b</sup>	3.75±0.42 <sup>a</sup>	5.68±0.86 <sup>b</sup>	2.93±0.35 <sup>a</sup>
8	3.33±0.19 <sup>c</sup>	1.40±0.22 <sup>b</sup>	3.36±0.05 <sup>c</sup>	0.93±0.03 <sup>a</sup>
16	5.72±0.22 <sup>c</sup>	3.86±0.16 <sup>b</sup>	5.56±0.08 <sup>c</sup>	2.88±0.32 <sup>a</sup>
24	5.61±0.28 <sup>c</sup>	3.36±0.20 <sup>b</sup>	5.49±0.05 <sup>c</sup>	2.79±0.36 <sup>a</sup>
0% RH				
Week	PET	PET-CIT	PET-PA	PET-PA-CIT
2	5.75±0.20 <sup>b</sup>	3.92±0.33 <sup>a</sup>	5.55±0.53 <sup>b</sup>	3.56±0.26 <sup>a</sup>
4	5.89±0.16 <sup>b</sup>	3.84±0.38 <sup>a</sup>	5.81±0.63 <sup>b</sup>	3.51±0.79 <sup>a</sup>
50 °C				
Week	PET	PET-CIT	PET-PA	PET-PA-CIT
2	3.62±0.07 <sup>a</sup>	3.96±1.14 <sup>a</sup>	5.51±0.46 <sup>b</sup>	3.73±0.43 <sup>a</sup>
4	5.68±0.86 <sup>a</sup>	5.14±0.79 <sup>a</sup>	6.79±0.15 <sup>b</sup>	4.70±0.69 <sup>a</sup>

600

601 **Figure 1** Contini et al.

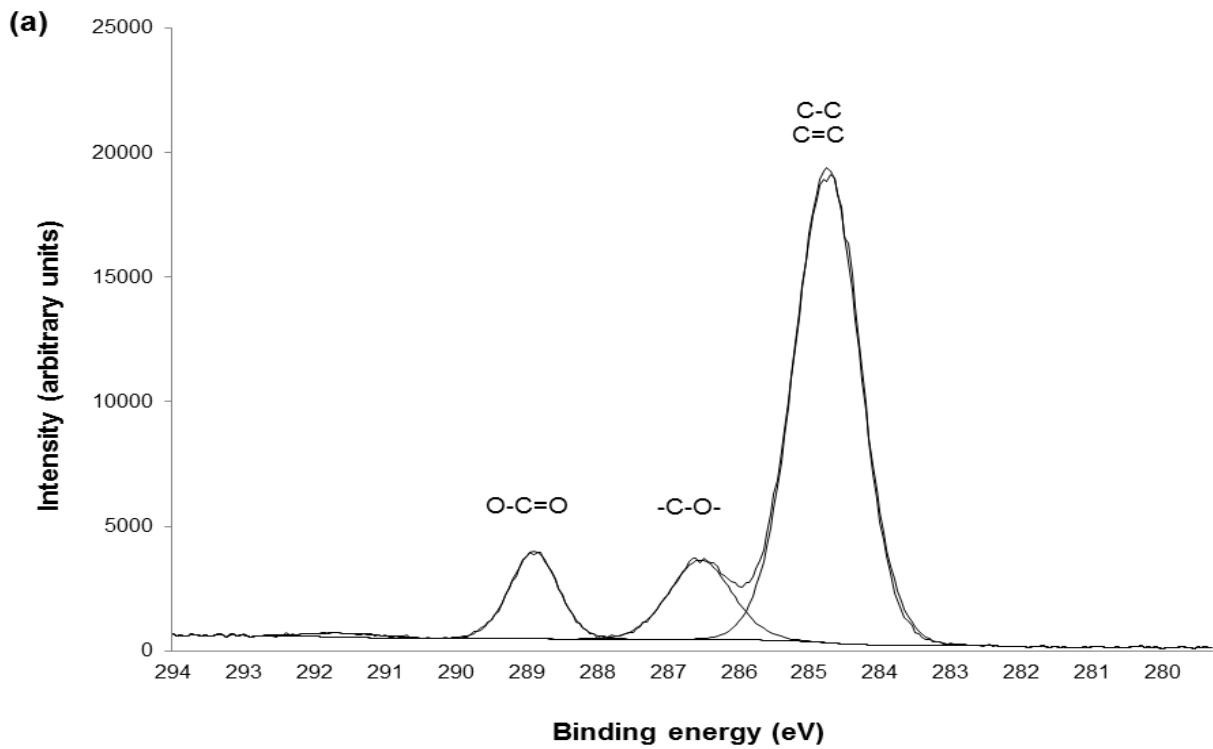



602


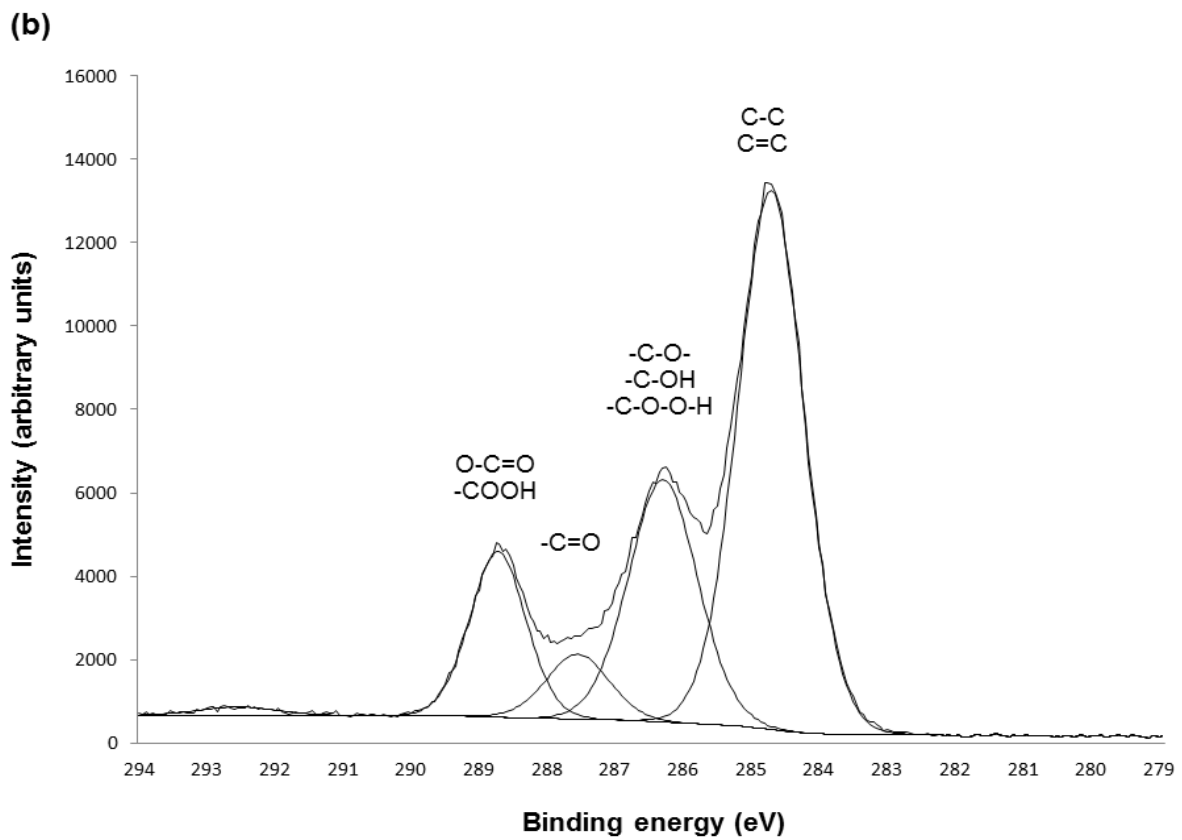


603



604



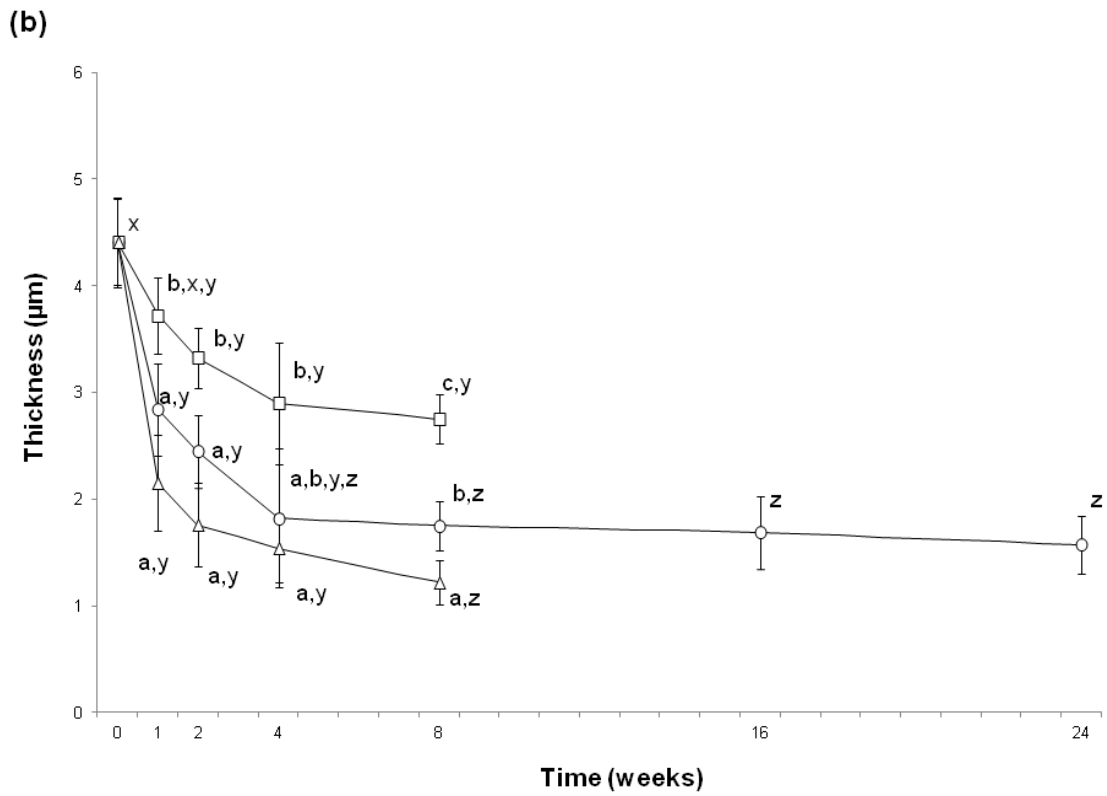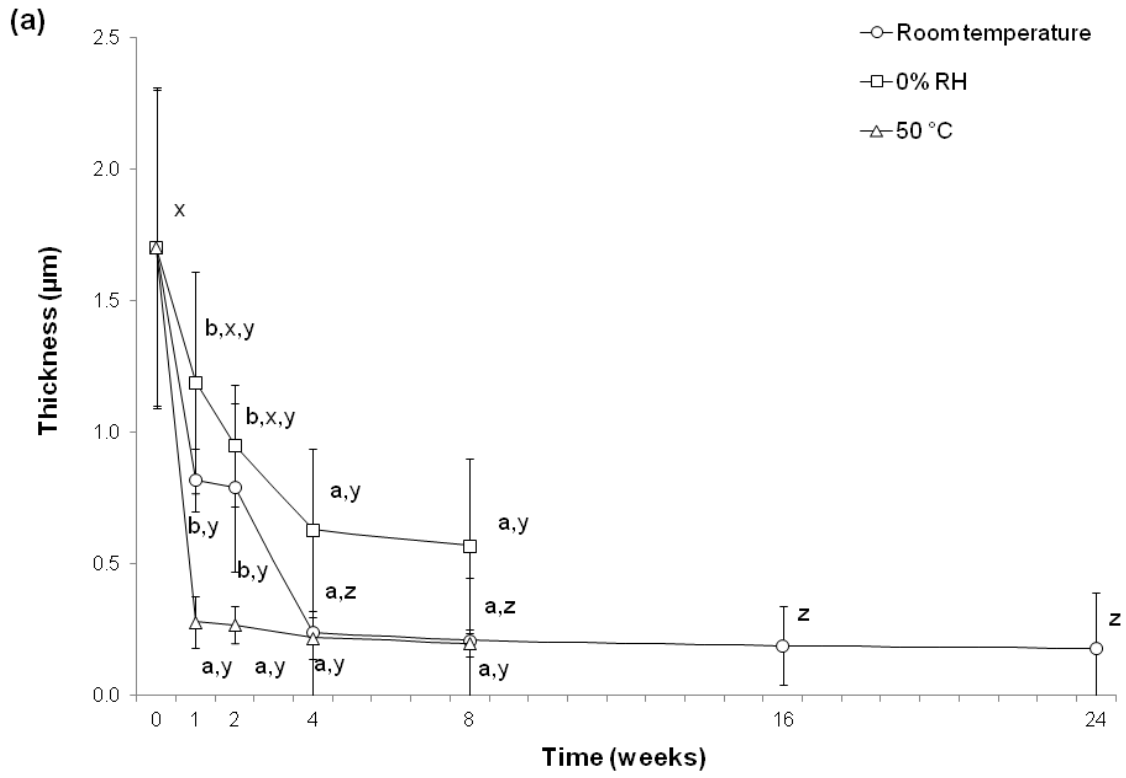

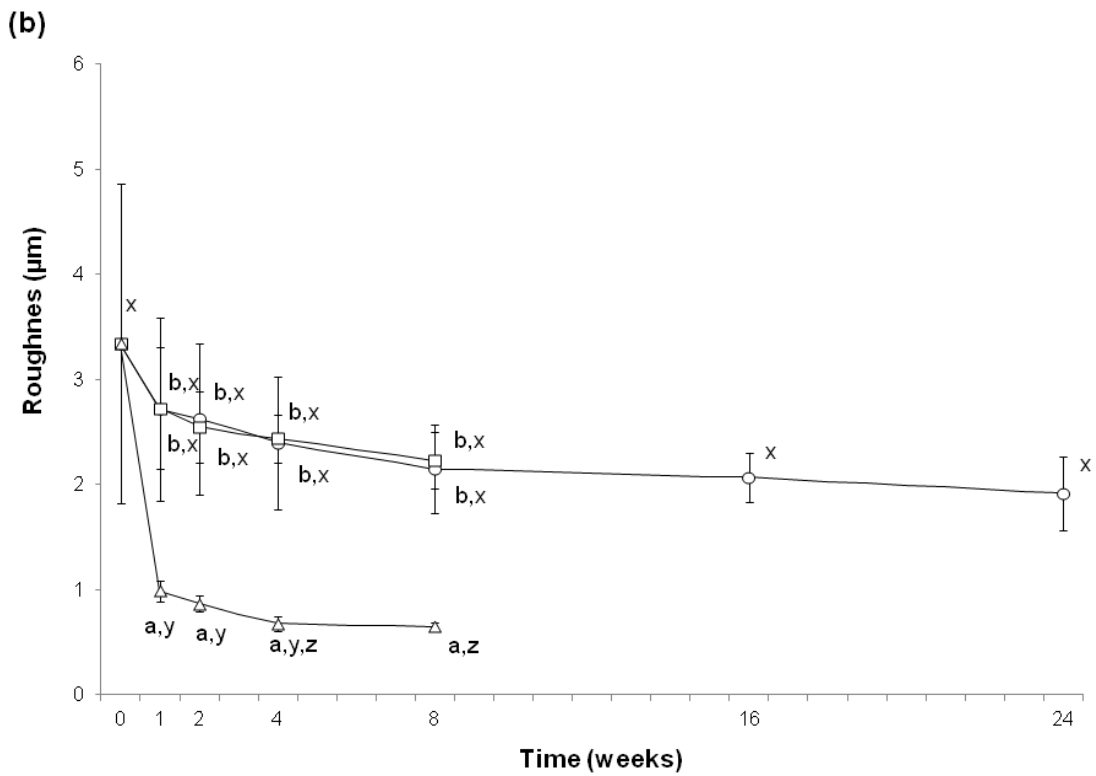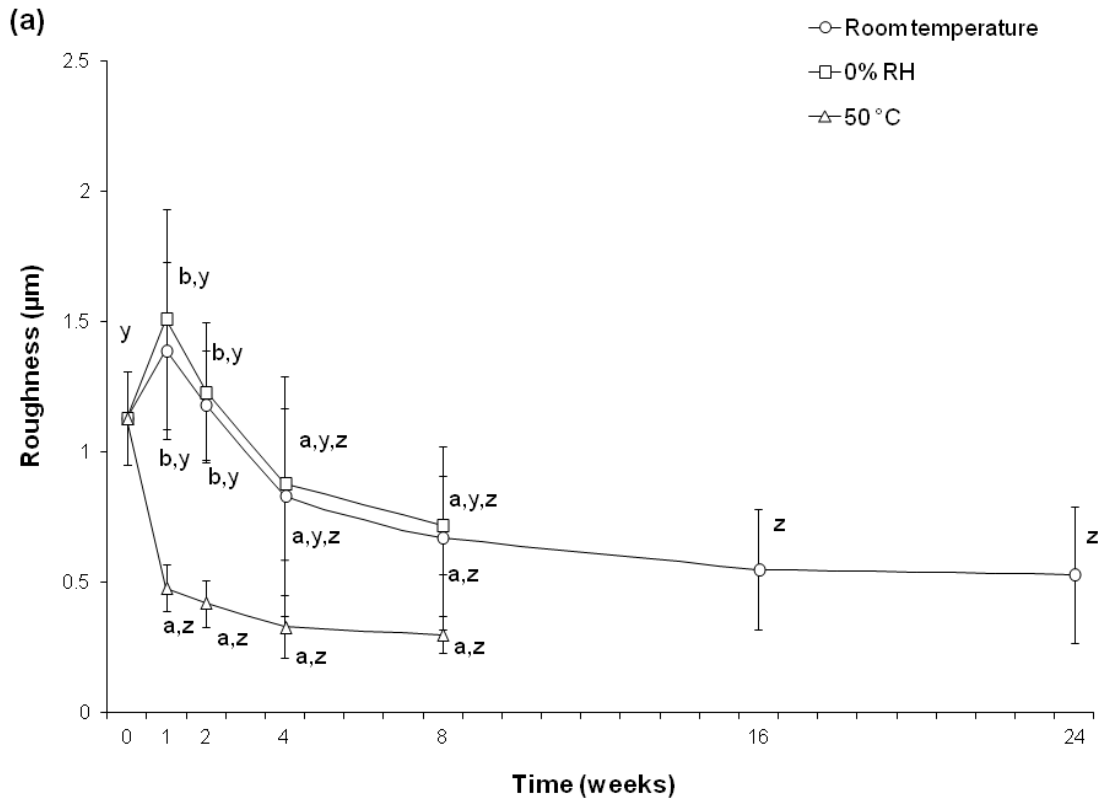

611 **Figure 4 Contini et al.**

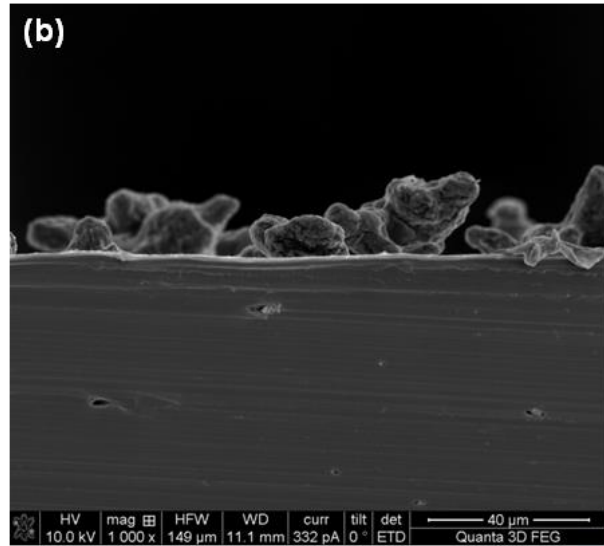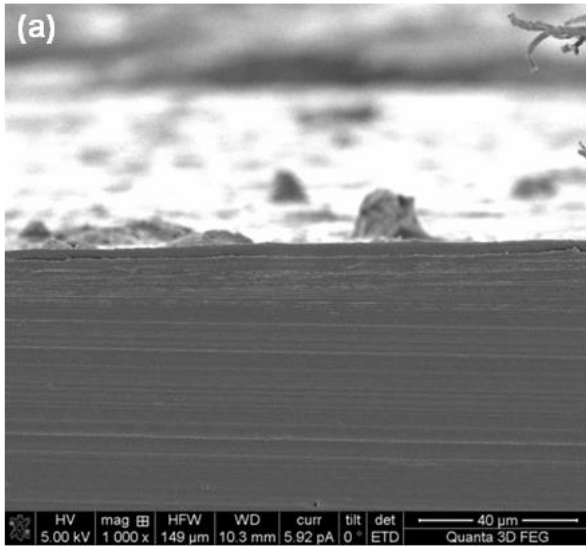


612


613

614


615 **Figure 5 Contini et al.**

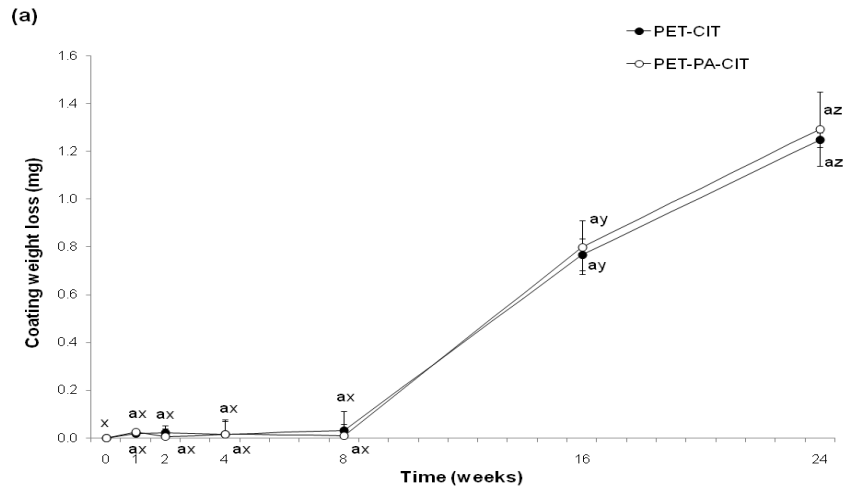

616

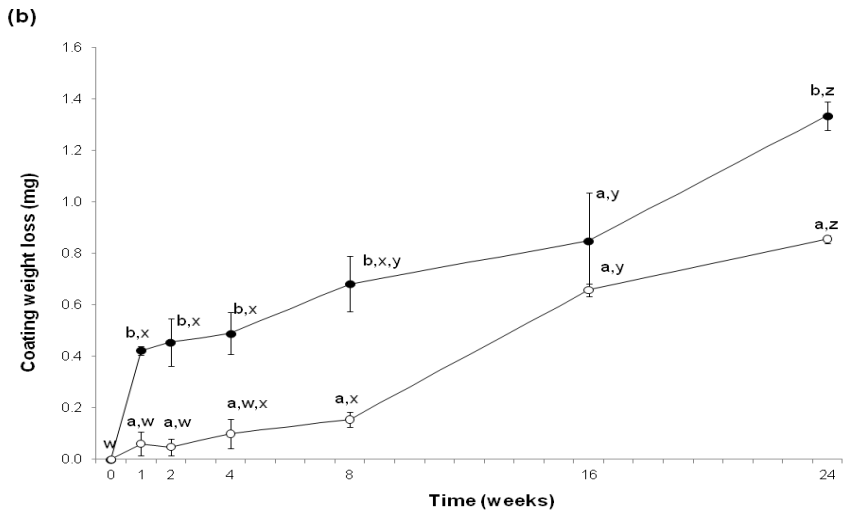

617

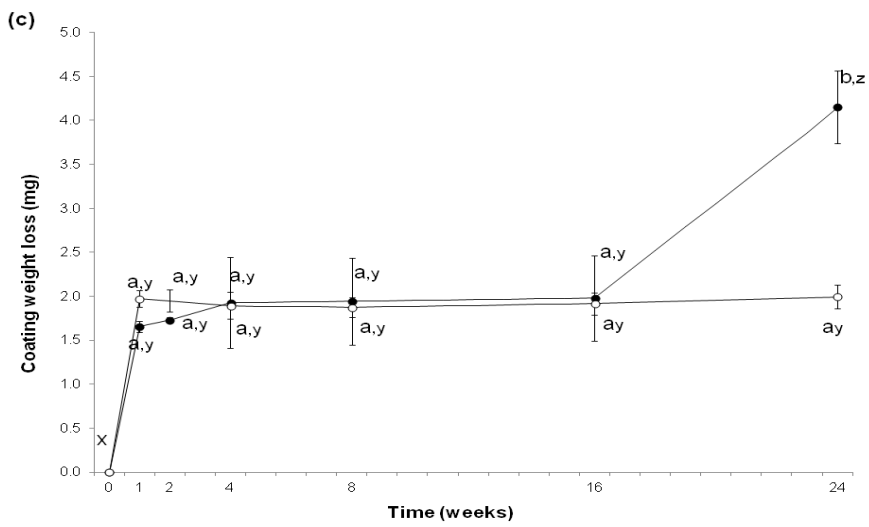


618

619

620

Figure 6 Contini et al.

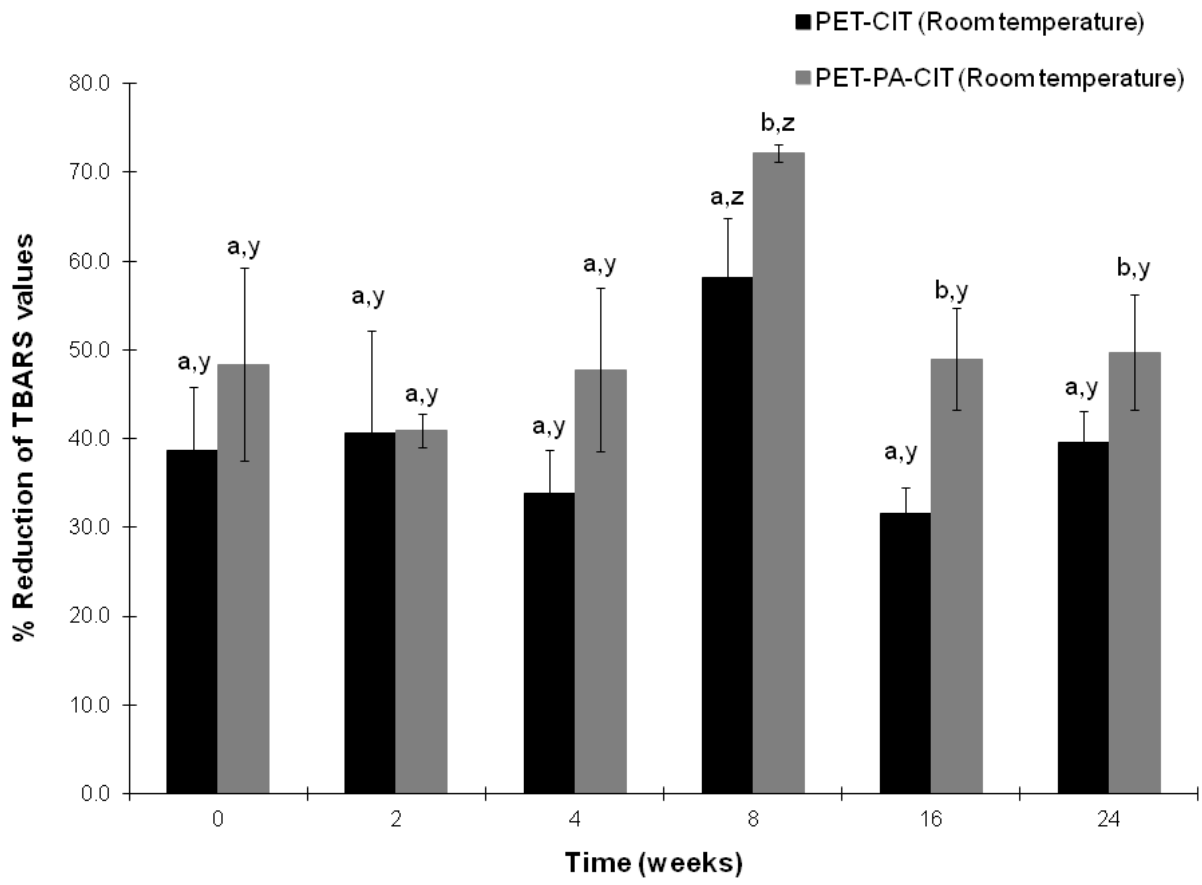


621

622

623 **Figure 7 Contini et al.**

624

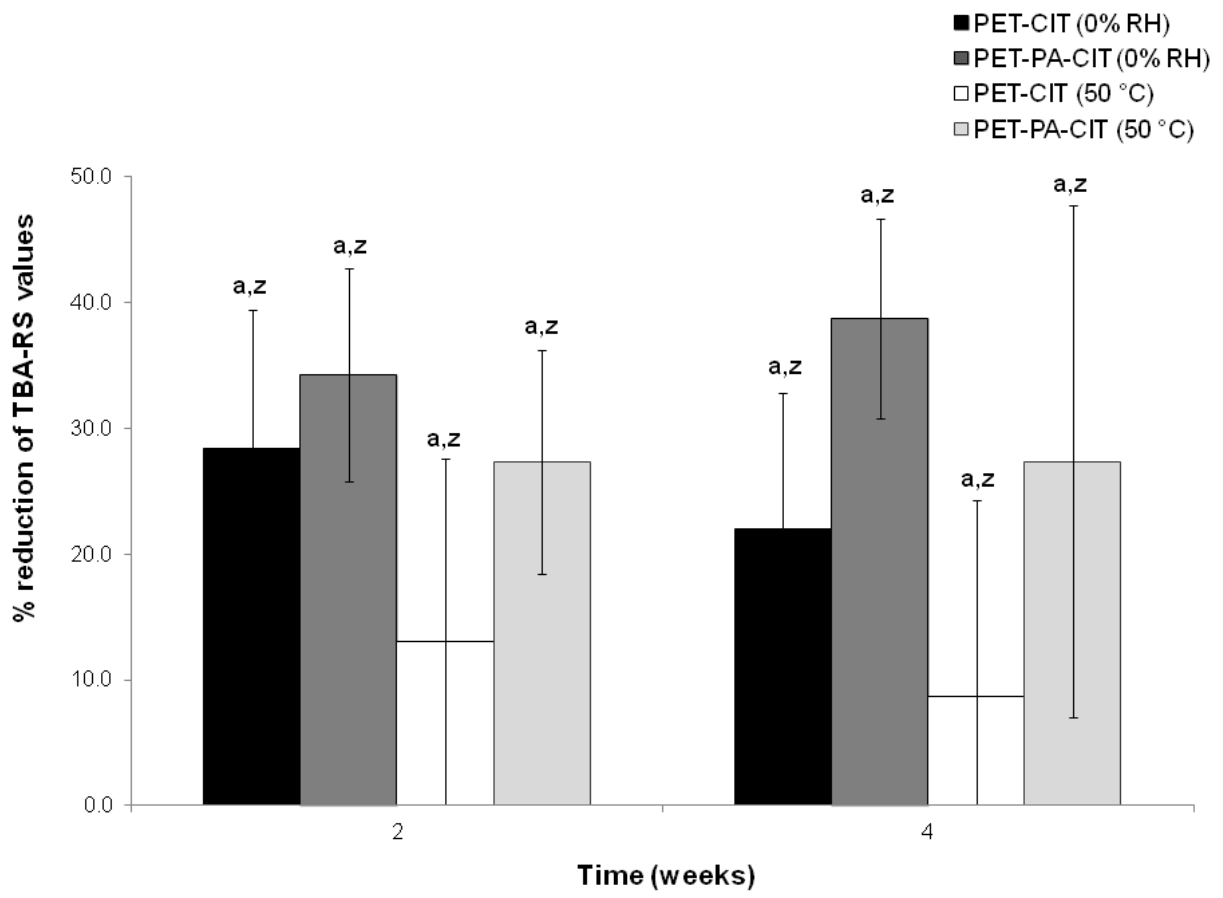

625

626

627

628