



Selective Oxidative Carbonylation of Aniline to Diphenylurea with Ionic Liquids

Zahrtmann, Nanette; Claver, Carmen; Godard, Cyril; Riisager, Anders; Garcia Suárez, Eduardo José

Published in:
ChemCatChem

Link to article, DOI:
[10.1002/cctc.201800004](https://doi.org/10.1002/cctc.201800004)

Publication date:
2018

Document Version
Peer reviewed version

[Link back to DTU Orbit](#)

Citation (APA):
Zahrtmann, N., Claver, C., Godard, C., Riisager, A., & Garcia Suárez, E. J. (2018). Selective Oxidative Carbonylation of Aniline to Diphenylurea with Ionic Liquids. *ChemCatChem*, 20, 2450-2457. DOI: 10.1002/cctc.201800004

General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

Heterogeneous & Homogeneous & Bio- & Nano-

CHEMCATCHEM

CATALYSIS

Accepted Article

Title: Selective Oxidative Carbonylation of Aniline to Diphenylurea with Ionic Liquids

Authors: Nanette Zahrtmann, Carmen Claver, Cyril Godard, Anders Riisager, and Eduardo José Garcia-Suárez

This manuscript has been accepted after peer review and appears as an Accepted Article online prior to editing, proofing, and formal publication of the final Version of Record (VoR). This work is currently citable by using the Digital Object Identifier (DOI) given below. The VoR will be published online in Early View as soon as possible and may be different to this Accepted Article as a result of editing. Readers should obtain the VoR from the journal website shown below when it is published to ensure accuracy of information. The authors are responsible for the content of this Accepted Article.

To be cited as: *ChemCatChem* 10.1002/cctc.201800004

Link to VoR: <http://dx.doi.org/10.1002/cctc.201800004>

FULL PAPER


Selective Oxidative Carbonylation of Aniline to Diphenylurea with Ionic Liquids

N. Zahrtmann,^[a,b] C. Claver,^[a] C. Godard,^{[a]*} A. Riisager,^{[b]*} and E.J. Garcia-Suarez^[b,c,d]

Abstract: A catalytic system for the selective oxidative carbonylation of aniline to diphenylurea based on Pd complexes in combination with imidazolium ionic liquids is presented. Both oxidants, Pd complexes and ionic liquids affect the activity of the reaction while the choice of oxidant determines the selectivity of the reaction. Together they allow the reaction to proceed under comparatively mild conditions without loss of activity. *In-situ* NMR examination of the reaction led to the observation of a previously suggested intermediate supporting the proposed mechanism.

Introduction

Ureas are commonly found in the structures of a large number of biologically active compounds. Moreover, ureic derivatives have a wide spectrum of biological activity and have been extensively applied as agrochemicals, dyes, antioxidants or resin precursors as well as key intermediates in organic synthesis, e.g. in the production of isocyanates.^[1] In this context, the oxidative carbonylation of amines to obtain ureas (Scheme 1) has received much interest over the past 50 years^[2] as alternative to the traditional phosgenation process.^[3] The reaction is carried out in the presence of a metal catalyst or organo-catalyst, an oxidizing agent such as I₂^[1,4] or O₂/Air^[5] and CO pressure. Among the transition metals and organo-catalysts Mn,^[2] Pd,^[4c,5h-q,6] Cu,^[5a,7] Au,^[5b-c] Co,^[5d-e] W^[1,4a-b] Ni,^[5f] Rh,^[5g] Ru,^[5h] S^[8] and Se^[9] can be pointed out. Usually, a non-nucleophilic solvent is required in order to avoid the formation of carbamates.^[5h,10] The best result reported to date in terms of turn-over-frequency (TOF) was achieved with a catalytic system comprising Pd(OAc)₂ and 3-butyl-1,2-methylimidazolium iodide as co-catalyst in the presence of O₂ (17,368 h⁻¹). However, the reaction was carried out under explosive CO/O₂ gas mixture requiring extraordinary safety precautions.^[5f]



Scheme 1. General reaction scheme for the oxidative carbonylation of amines to ureas.


[a] Dr. N. Zahrtmann, Prof. C. Claver and Prof. Cyril Godard
Department of Physical and Inorganic Chemistry, Universitat Rovira i Virgili, C/Marcel·lí Domingo s/n, Campus Sescelades, 43007 Tarragona (Spain), E-mail: cyril.godard@urv.cat

[b] Dr. N. Zahrtmann, Prof. A. Riisager and Dr. E.J. García-Suárez
Centre for Catalysis and Sustainable Chemistry, Department of Chemistry, Technical University of Denmark, DK-2800 Kgs. Lyngby (Denmark), E-mail: ar@kemi.dtu.dk

[c] Tecnalia. Energy and Environment Division. Parque Tecnológico de Álava, Leonardo Da Vinci, 11, 01510 Miñano, Spain.

[d] IKERBASQUE, Basque Foundation for Science, Maria Diaz de Haro 3, 48013 Bilbao, Spain

The mechanism of the Pd-catalysed oxidative carbonylation of amines have been studied by Hiwatari *et al.*^[6d] using I₂ as oxidant (Scheme 2). The authors suggested that the reaction proceeds through a Pd²⁺/Pd⁰-cycle via a Pd-carbamoyl intermediate, where the active species is a Pd²⁺ complex (I) that reacts with CO and 2 equivalents of amine to form a Pd-carbamoyl complex (II) and an ammonium salt. Reaction of an amine molecule at the carbonyl of Pd intermediate (II) provides the corresponding isocyanate that reacts *in-situ* to form urea as final product and Pd⁰ species (III) that are reoxidized to the active Pd²⁺ species (I).

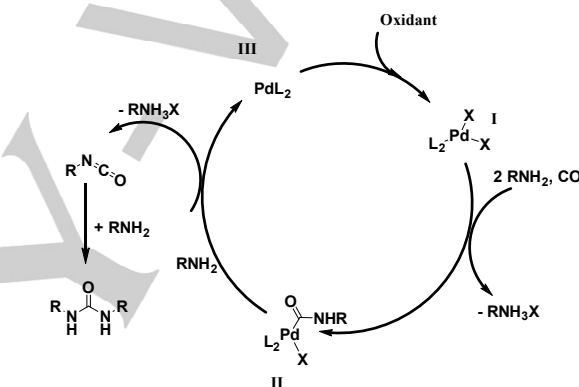

Scheme 2. Mechanism proposed by Hiwatari and co-workers for the Pd-catalysed oxidative carbonylation of amines.^[6d]

The basis of the mechanism suggested by Hiwatari *et al.* is the observation, that the isolated *N*-propylcarbamoyl-Pd complex reacts with primary and secondary amines yielding *N,N*-dialkylurea and *N,N,N*-trialkylurea, respectively, while the reaction with a tertiary amine forms the free isocyanate (Scheme 2). The selectivity of the reaction supports the mechanism as the reaction step II to III can be promoted by primary, secondary and tertiary amines alike although isocyanate can only be formed from a primary amine and the formation of the urea from isocyanate requires a primary or a secondary amine. The repeated observation that *N,N,N,N*-tetrasubstituted ureas cannot be generated with CO and secondary amines as the only substrates^[5l-o] supports this mechanism. On the other hand, a different mechanism must be accredited for the observations published first by Pri-Bar *et al.*^[4c] and later by others^[4d-f] who prepared *N,N,N,N*-tetrasubstituted ureas in I₂-oxidised systems. Giannoccaro *et al.*^[4d,5q] prepared Pd-carbamoyl complexes of both primary and secondary aliphatic amines from various Pd(L-L)Cl₂ precursors and isolated the Pd-complexes along with ammonium chlorides supporting the mechanistic proposal by Hiwatari *et al.*^[6d] The Pd-carbamoyl complexes were subsequently treated with Cl₂, I₂ and CuCl₂ yielding various elimination products along with the Pd²⁺ precursors.^[4d,5q] The elimination products were found to be more dependant of the amine substitution than the halide source as secondary

FULL PAPER

carbamoyl halides and primary isocyanates was formed regardless of halide source. Giannoccaro *et al.*^[5q] summarized their observations in a proposed mechanism which is largely in agreement with the proposal made by Hiwatari *et al.*,^[6d] although they disagree on whether or not the ammonium halides reenter the cycle. The formation of secondary carbamoyl halides would explain the observation of *N,N,N,N*-tetraalkylureas in reactions where I₂ have been used as oxidant as the reaction of carbamoyl halides with nucleophiles is well known.^[11] Further support for the proposed mechanisms has been provided by Didgikar *et al.*^[5m] and Gabriele *et al.*^[5k-1,5n-m] who both studied the oxidative carbonylation of amines with Pd²⁺/I⁻ catalytic systems using O₂ as oxidant, and reported a correlation between the nucleophilicity and the reactivity of the substrate.

Ionic liquids (ILs) have been employed as reaction media in the oxidative carbonylation of amines generating biphasic systems.^[5i,5k] In these reactions, the catalytic systems were constituted by a Pd²⁺ catalysts, an IL - and in the case of Mancuso *et al.* - an iodide salt as additive.^[5k] ILs constitute a special class of compounds that exhibit interesting physical and chemical properties for application in catalysis, biomass processing, electrochemistry etc.^[12] In catalysis, ILs can be used as both reaction media and catalysts and provide beneficial effects such as, e.g. high stability towards oxidation by O₂.^[12c] In addition, ILs can be easily functionalized for specific catalytic applications.^[12c-e]

In this work, we report the use of Pd-based catalysts bearing N- or P-donor ligands for the selective oxidative carbonylation of aniline into diphenylurea in the presence of IL as reaction media. The roles of the IL ions, ligands, oxidants as well as the effect of catalyst loading were investigated and optimized. Introduction of a highly active catalytic system, even under comparatively mild conditions, and observation of the Pd-carbamoyl intermediate previously suggested by Hiwatari and Giannoccaro *et al.* (*vide supra*) by *in-situ* NMR spectroscopy, along with a TOF of 15,000 under optimized conditions, are prominent results obtained in the reported study.

Results and Discussion

Influence of oxidant, catalyst loading and reaction time

The influence of the oxidant is important for oxidative carbonylation. O₂ is preferred as a green oxidant but some safety issues have to be considered, i.e. choice of organic solvent due to peroxide formation (e.g. THF or 1,4-dioxane) and concentration of O₂ in the CO/O₂ mixtures to avoid potential explosive hazards.^[12e] With this in mind, O₂, I₂ and 1,4-benzoquinone (BQ) were selected as oxidants in the study. Noteworthy, BQ was used as oxidant for the first time for this reaction type although it has been employed in other well-known Pd-catalyzed processes such as olefins carbonylation.^[13] The reaction was initially carried out in a biphasic mixture of toluene and 1-butyl-3-methylimidazolium chloride ([BMIM][Cl]) at 140 °C under 10 bar of CO using 0.1 mol% of Pd(PPh₃)₂Cl₂ as catalyst. The results are displayed in Table 1.

After 4 h of reaction, full conversion aniline was achieved with BQ and I₂ as oxidants while only 79% conversion was obtained with O₂ (Table 1, entries 1-4). The lower conversion in the case of O₂ was attributed to the poor solubility of the gas in the reaction media.^[14] Concerning the selectivity, more than 99% diphenylurea was formed with BQ and O₂ as oxidants (entries 3 and 4). In contrast, no urea product was obtained when I₂ was used without additional additives instead only anilinium chloride formed (entry 1). The absence of urea product with I₂ as oxidant was most likely due to the insolubility of the anilinium chloride species formed from *in-situ* generated anilinium iodide^[5m] and [BMIM][Cl] during the reaction in the IL phase containing the catalyst, thus hampering the catalytic performance. Similar results were previously reported when I₂ was used as oxidant in the absence of additional base.^[4c-d,5k] When the reaction was performed in the presence of K₂CO₃ (1 equivalent), the conversion decreased to 66% but resulted in >99% selectivity towards urea product (entry 2) as the base scavange HI which would otherwise be formed in stoichiometric amount with respect to urea.

Table 1. Influence of the oxidant, catalyst loading and reaction time.^[a]


Entry	Catalyst (mol%)	Oxidant	Time (h)	TOF ^[b] (h ⁻¹)	Conv. ^[c] (%)	Selec. ^[d] (%)
1	0.1	I ₂	4	248	99	0
2 ^[e]	0.1	I ₂	4	165	66	>99
3	0.1	O ₂	4	198	79	>99
4	0.1	BQ	4	250	100	>99
5	-	BQ	1	0	0	-
6	0.001	BQ	1	11,000	11	>99
7	0.005	BQ	1	7,200	36	>99
8	0.01	BQ	1	5,200	52	>99
9	0.1	BQ	1	1,000	100	>99
10	0.01	BQ	0.25	15,600	39	>99
11	0.01	BQ	2	2,350	47	>99
12	0.01	BQ	4	1,100	44	>99

[a] Reaction conditions: Aniline (6 mmol), Pd(PPh₃)₂Cl₂, BQ (benzoquinone) (6 mmol), I₂ (6 mmol), O₂ (6 mmol), CO (0.1 mol), 10 bar total pressure, [BMIM][Cl] (7.5 mmol), mesitylene as internal standard (0.6 mmol), toluene (10.5 mL), 140 °C, 1000 rpm. [b] Turn-over-frequency as mmol aniline converted per mmol Pd per hour. [c] Conversion of aniline. [d] Selectivity to diphenylurea. [e] Using K₂CO₃ as additive (6 mmol).

Based on the initial results, BQ was selected as oxidant to study the catalyst loading and reaction time effect. When the catalyst loading was progressively decreased from 0.1 to 0.001 mol%, a decrease from full conversion to 11% was observed while the selectivity towards diphenylurea remained unchanged at

FULL PAPER

>99% (Table 1, entries 6-9). Similarly, the catalyst turn-over-frequency (TOF) increased significantly with the lower catalyst loadings suggesting that only under these conditions was the catalyst inventory utilized efficiently. The influence of the reaction time was also studied at 0.01 mol% catalyst loading (Table 1, entries 8 and 10-12). After 1 h reaction time, a maximum conversion of 52% was achieved whereas longer reaction time resulted in decreased conversions of 47 and 44% after 2 and 4 h, respectively. These results are possibly explained by partly decomposition of the formed diphenylurea into aniline and phenylisocyanate followed by further decomposition into aniline and CO₂ in the presence of water (Scheme 3).^[15] It is worth to point out that the studied catalytic system composed of [BMIM]Cl/Pd-PPh₃/BQ is, to the best of our knowledge, among the most active reported in the literature^[51-] with a TOF of 15,600 h⁻¹ after 15 min reaction (Table 1, entry 10).

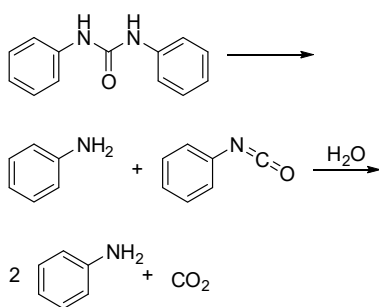

Scheme 3. Diphenylurea decomposition to aniline.^[55]

Influence of the ligand

Various Pd-complexes with 1,3-bis(2,6-diisopropyl-phenyl)-1H-imidazol-3-ium-2-ide (**L1**), 1,10-phenantroline (**L2**), 3-chloropyridine, aniline (**L3**), benzonitrile (**L4**) and triphenylphosphine (**L5**) ligands (Figure 1) were next tested in the oxidative carbonylation of aniline to diphenylurea. The catalytic experiments were performed with a catalyst loading of 0.01 mol% using the corresponding isolated complexes Pd(**L1**)₂Cl₂, Pd(**L1**)(3-Cl-pyridine)Cl₂, Pd(**L2**)Cl₂, Pd(**L3**)₂Cl₂, Pd(**L4**)₂Cl₂, and Pd(**L5**)₂Cl₂ synthesized according to previous reports.^[16] The results obtained are displayed in Figure 2.

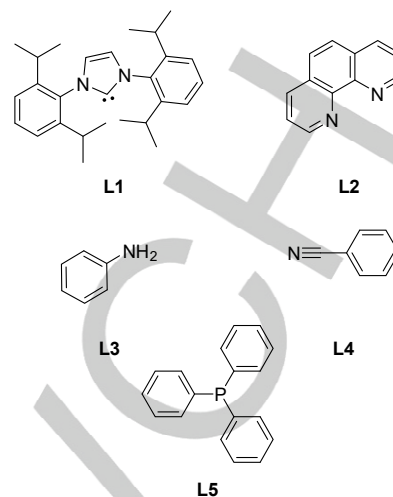


Figure 1. Ligands tested in the oxidative carbonylation of aniline.

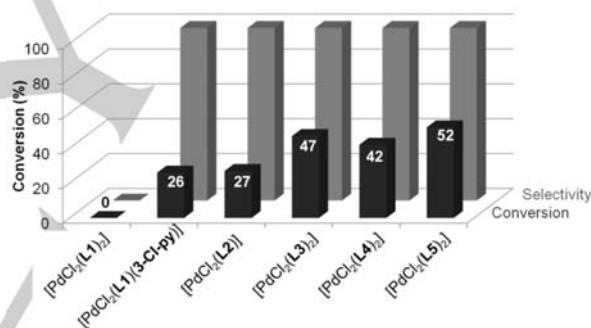


Figure 2. Influence of the ligand in the selective oxidative carbonylation of aniline to diphenylurea. Reaction conditions: Aniline (6 mmol), Pd-complex (0.01 mol%), BQ (6 mmol), CO (0.1 mol), 10 bar total pressure, [BMIM]Cl (7.5 mmol), mesitylene as internal standard (0.6 mmol), toluene (10.5 mL), 140 °C, 1 h.

The highest aniline conversion (52%) was achieved when the Pd(**L5**)₂Cl₂ complex was used, whereas slightly lower conversions (47% and 42%) were obtained with the two complexes Pd(**L3**)₂Cl₂ and Pd(**L4**)₂Cl₂ bearing the monodentate N-donor ligands. The similar results obtained with the latter complexes was probably due to fast replacement of **L4** by **L3** (substrate) resulting in *in-situ* formation of the same catalytically active Pd-**L3** species. When the PEPSI complex Pd(**L1**)(3-Cl-pyridine)Cl₂ and Pd(**L2**)Cl₂ were tested, lower but also similar conversions (26% and 27%, respectively) were obtained. The low conversion obtained with ligand **L2** was somehow unexpected, since very good results were obtained by Shi *et al.* although under more harsh reaction conditions (175 °C and 50 bar CO).^[17] The Pd(**L1**)₂Cl₂ complex bearing two NHC ligands showed no activity at all in agreement with previous reports.^[16g-h] Considering the catalytic behavior which have been reported for bis-Pd(NHC)-

FULL PAPER

complexes an isomerisation from *trans*- to *cis*-configuration is required for the addition of the substrate.^[18] Given the inflexibility of the applied carbene ligands,^[19] this isomerisation is unlikely to take place thus blocking the coordination of the substrate.

In order to elucidate why Pd(PPh₃)₂Cl₂ was the most active pre-catalyst complex, a high pressure (HP) NMR study was performed with this system under *in-situ* conditions applying ¹³C{¹H}- and ³¹P{¹H}-NMR. At the beginning of the experiment, the ³¹P{¹H}-NMR spectrum (Figure 3, trace 1) displayed one signal at δ = 24.30 ppm in agreement with the characterization of the pure compound.^[16b] The addition of aniline caused no change in the spectrum (trace 2), while heating the mixture under Ar lead to a broadening of the signal and an up-field shift to δ = 23.86 ppm (trace 3). No signals belonging to free PPh₃ (or O=PPh₃) were observed, indicating that the complex was stable under these conditions. Upon the addition of CO gas (trace 4) a signal was immediately observed at δ = -4.70 ppm, assigned to uncoordinated PPh₃ in agreement with literature.^[72] Heating the reaction mixture under CO to 80 °C (trace 5) lead to a broadening of the signals to an extent where the ligand signal almost disappeared into the background but, in addition, it also resulted in formation of new signal at δ = 24.82 ppm. Heating to 110 °C (trace 6) caused the signals of both free PPh₃ and Pd(PPh₃)₂Cl₂ to increase in intensity and width indicating rapid ligand exchange on the metal center. Furthermore, new signals were observed at δ = 25.16 and 19.79 ppm. Cooling the sample to 25 °C (trace 7) resulted eventually in three distinct signals at δ = 26.64, 24.30 and 19.54 ppm assignable to PdCO_n(PPh₃)_x,^[20] PdCl₂(PPh₃)₂Cl₂^[16b,20a] and PdCl(CONHPh)(PPh₃)₂,^[6d] respectively.

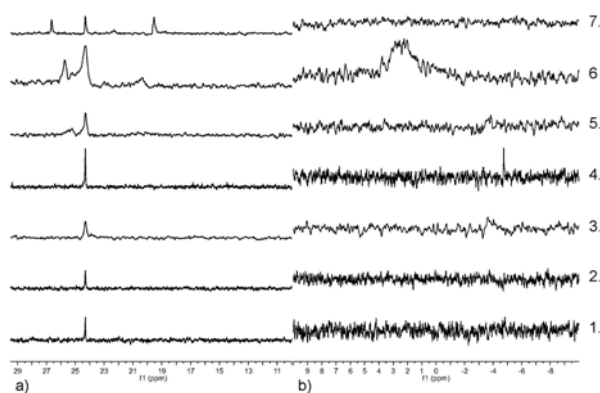


Figure 3. *In-situ* ³¹P{¹H}-NMR (sapphire tube, 162 MHz, toluene) of the Pd(PPh₃)₂Cl₂ catalysed carbonylation of aniline before, under and after formation of diphenylurea. (1) Initial spectra of Pd(PPh₃)₂Cl₂/[BMIM]Cl suspension under Ar at 25 °C, (2) after the addition aniline under Ar at 25 °C, (3) the reaction mixture at 80 °C under Ar, (4) the reaction mixture under 5 bar CO at 25 °C, (5) the reaction mixture under CO at 80 °C, (6) the reaction mixture under CO at 110 °C and (7) the reaction mixture under CO at 25 °C. a, b: b is shown with a five-fold intensity with respect to a.

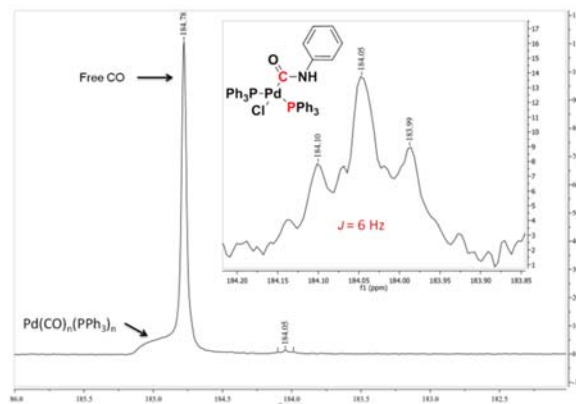


Figure 4. *In-situ* ¹³C{¹H}-NMR (sapphire tube, 100 MHz, toluene, 25 °C, 5 bar ¹²CO:¹³CO = 3:2) of the Pd(PPh₃)₂Cl₂ catalysed carbonylation of aniline after the formation of diphenylurea.

¹³C{¹H}-spectra were also recorded before, under and after the HP-NMR experiment. Figure 4 shows the δ = 186-182 ppm range of the spectrum recorded at the end of the experiment after cooling. It featured free CO at δ = 184.8 ppm with a shoulder at δ ≈ 185 ppm as the most dominant signals and a triplet at δ = 184.0 ppm which was assigned to the Pd-carbamoyl complex.^[6d]

The stability and reactivity of Pd(PPh₃)₂Cl₂ correlated well with the results obtained during catalytic testing. As PPh₃ do not interchange with aniline even at elevated temperatures, the improved conversion obtained with Pd(PPh₃)₂Cl₂ as catalyst is directly related to the coordination of PPh₃. Under an atmosphere of CO and with heating to 110 °C, Pd(PPh₃)₂Cl₂ underwent a rapid exchange of PPh₃ and CO at the metal center, which activated the complex for the formation of the Pd-carbamoyls intermediate proposed by Hiwatari *et al.*^[6d] and Giannoccaro *et al.*^[5a] To the best of our knowledge, it is the first time the Pd-carbamoyl complex have been observed under *in-situ* conditions.

Influence of pressure with O₂ as oxidant

Initial results using O₂ as an oxidant, indicated that low solubility of O₂ in the IL caused incomplete conversion of the aniline in the reaction system (Table 1, entry 3). Optimization of the stirring rate was therefore important to maximize gas solubility. Accordingly, the influence of stirring rate was examined for the Pd(PPh₃)₂Cl₂ catalyst system using O₂ as oxidant and the results are shown in Table 2 (entries 1-3). Increase in conversion from 41% to 79% was observed when the stirring rate was increased from 500 to 1,000 rpm, but further increase in the stirring rate to 1,400 rpm did not provide any improvement in conversion. This fact confirmed that mass transfer of O₂ was rate limiting only with stirring rates below 1000 rpm.

FULL PAPER

Table 2. Influence of the stirring rate and catalyst loading.^[a]

Entry	Catalyst (mol%)	Stirring (rpm)	TOF (h ⁻¹) ^[b]	Conv. (%) ^[c]	Selec. (%) ^[d]
1	0.1	500	103	41	>99
2	0.1	1,000	198	79	>99
3	0.1	1,400	195	78	>99
4	-	1,000	0	0	-
5	0.01	1,000	1,900	76	>99
6	0.2	1,000	98	78	>99
7	0.5	1,000	40	79	>99
8	1	1,000	18	70	>99
9	10	1,000	2	82	>99

[a] Reaction conditions: Aniline (6 mmol), Pd(PPh₃)₂Cl₂, O₂ (6 mmol), CO (0.1 mol), 10 bar total pressure, [BMIM]Cl (7.5 mmol), mesitylene as internal standard (0.6 mmol), toluene (10.5 mL), 140 °C, 4 h. [b] Turn-over-frequency as mmol aniline converted per mmol Pd per hour. [c] Conversion of aniline. [d] Selectivity to diphenylurea.

Next, the catalyst loading was optimized between 0.01 and 10 mol% (Table 2, entries 5-9). The results showed that there was no direct correlation between catalyst loading and conversion with O₂ as oxidant, which was in contrast with the results obtained with BQ (Table 1, entries 6-9). Therefore, it appeared that the oxidative carbonylation under the applied reaction conditions was not first order with respect to the catalyst using O₂ as oxidant.

Table 3. Influence of IL amount and reaction pressure.^[a]

Entry	Pressure (bar)	IL loading (mmol)	TOF (h ⁻¹) ^[b]	Conversion (%) ^[c]	Selectivity (%) ^[d]
1	5	7.5	138	55	>99
2	10	7.5	198	79	>99
3	20	7.5	200	80	>99
4	30	7.5	208	83	>99
5	10	15	215	86	>99
6	10	30	250	100	>99
7	10	0	5	2	n/a

[a] Reaction conditions: Aniline (6 mmol), Pd(PPh₃)₂Cl₂ (0.1 mol%), O₂ (6 mmol), CO, [BMIM]Cl, mesitylene as internal standard (0.6 mmol), toluene (10.5 mL), 140 °C, 4 h, 1000 rpm. [b] Turn-over-frequency as mmol aniline converted per mmol Pd per hour. [c] Conversion of aniline. [d] Selectivity to diphenylurea.

The catalytic performance with varied pressures was also investigated using total pressures of 5-30 bar (Table 3, entries 1-4). An increase in conversion from 55 to 79% was obtained when the total pressure was increased from 5 to 10 bar, whereas further pressure increase to 20 or 30 bar did not improve conversion.

The influence of the amount of IL added in the reaction system was also examined (Table 3, entries 2, 5-7). It was here confirmed, that IL addition improved conversion without affecting the selectivity, and the conversion was quantitative when 30 mmol of the IL was employed. The promoting effect of the IL on the reaction indicated an interaction between the IL and the substrate, the catalyst or the product. The formation of Pd-NHC complexes with Pd-precursors in imidazolium ILs have been reported previously,^[Sj,16g-h,21] however given the negative effect observed on the reaction when NHC-complexes was applied (Figure 2, entries 1 and 2) *in-situ* formation of a Pd-NHC complex was not likely to be related to the promoting effect. With respect to possible interactions with the substrate or the product, the unusually high solubility of diphenylurea in [BMIM]Cl (1:2 molar ratio) lead us to examine the influence of the nature of the IL.

Influence of ionic liquid with O₂ as oxidant

Physical and chemical properties of ILs are tunable by selecting the appropriate ion combination, which in turn may influence the catalytic performance for a studied reaction. Here, various IL ion compositions were also tested for the oxidative carbonylation of aniline to diphenylurea using the standard reaction conditions shown in Figure 5. 1-Butyl-3-methylimidazolium ([BMIM]⁺) was selected as the starting cation in combination with different anions, namely iodide, bistriflimide, bromide and chloride.

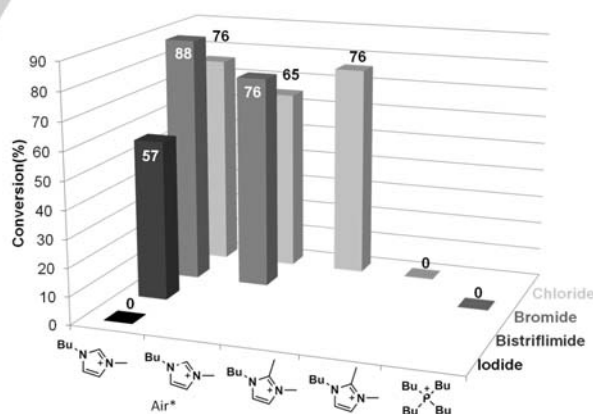


Figure 5. Effect of the IL composition. Reaction conditions: Aniline (12 mmol), Pd(PPh₃)₂Cl₂ (0.1 mol%), O₂ (12 mmol), CO (0.1 mol), 10 bar total pressure, IL (15 mmol), toluene (21 ml), mesitylene as internal standard (1.2 mmol), 140 °C, 500 rpm, 1 h. *10 bar (6 mmol O₂).

The best results in terms of conversion were obtained with [BMIM]Br with up to 88% conversion, while [BMIM]Cl provided 76% conversion and [BMIM][CF₃SO₂]₂N] 57%. Notably, [BMIM]

FULL PAPER

inhibited completely the catalytic reaction, which was unexpected since both Gabriele *et al.*^[50] and Peng *et al.*^[51] have described that iodide to play a key role in the catalytic reaction. Didgikar *et al.*^[52] optimized the iodide/Pd-ratio and obtained the highest conversion with 5 eq. of iodide promoter with respect to Pd, whereas both higher and lower ratios resulted in lower conversion. Here, the application of [BMIM]I gave a iodide/Pd-ratio >1,000 suggesting that the high iodide concentration coordinately saturated the catalyst.

The effect of the alkyl substitution on the IL cation was studied comparing results obtained with [BMIM]Cl and [EMIM]Cl (1-butyl-3-methyl-imidazolium chloride), which both yielded identical conversion (76%) (Figure 5). Use of other cations such as [BMMIM]⁺ (1-butyl-2,3-dimethylimidazolium) or [TBP]⁺ (tetrabutylpyridinium) resulted in no catalytic activity, suggesting that imidazolium cations unsubstituted in the 2-position was required for the reaction. Among the examined anions, bromide gave the best results but [(CF₃SO₂)₂N]⁻ rendered an spontaneous separation of the product and consequently [BMIM][(CF₃SO₂)₂N] was selected for examination of catalyst recyclability. Upon recycling of the catalytic system, a large decrease in conversion was observed from 57% (1st run) to 19% (2nd run) and to 10% (3rd run), clearly showing that the catalyst was not very stable under the applied conditions.

The strong influence of the IL cation could be related to the weak acidity of the C2-hydrogen of imidazolium, which could facilitate increased solubility of the basic aniline substrate.^[22] The acidity of imidazolium ILs are known to be affected by the alkyl-substituents and the ion interactions,^[23] which should make [BMIM][(CF₃SO₂)₂N] the most acidic of the examined ILs and thus better solvent for aniline.^[24] However, the weakly coordinating property of the [(CF₃SO₂)₂N]⁻ anion might have proven insufficient for stabilizing the Pd-species formed during the catalytic cycle. In combination, these opposite effects probably made [BMIM]Br the best compromise between solvation strength and coordination ability. Additional work are ongoing in order to scrutinize the effects of the ILs in more detail.

Conclusions

Selective oxidative carbonylation of aniline to diphenylurea (>99%) was performed with a catalytic system comprised of Pd(PPh₃)₂Cl₂ and [BMIM]Cl with a TOF of 15,600 and 1,900 h⁻¹ using benzoquinone or O₂ as oxidants, respectively. The catalytic activity achieved with the benzoquinone oxidant is, to the best of our knowledge, the highest reported so far under comparatively mild reaction conditions (140 °C and 10 bar). In addition, HP-NMR experiments provided the first *in-situ* observation of a suggested Pd-carbamoyl intermediate confirming the *trans*-conformation of the complex. To investigate the influence of ILs on the reaction, several IL ion compositions were tested and the best results were achieved with [BMIM]Br while the employment of [BMIM][(CF₃SO₂)₂N] facilitated spontaneous product separation. Recycling experiments with the latter IL showed that the resulting catalytic system was reusable in three consecutive reaction runs but with significant loss of activity which was attributed to

instability of the catalytically active Pd-species. Work currently undertaken by our group aims to improve the understanding of the role played by the IL and to optimize the catalytic system to improve its durability.

Experimental Section

General

Solvents for synthesis of ILs and Pd-complexes were supplied by Panrec and dried before use with a MBraun MB-SPS-800 solvent purification system or distilled by standard techniques (acetonitrile and ethyl acetate from CaH₂ and THF from Na/benzophenone). ILs were obtained from Sigma-Aldrich or synthesized by literature method and dried under vacuum (70 °C, >24 h) prior to use. Syntheses of ligands and Pd-complexes were performed in flame-dried glassware under argon using Schlenk technique or in a dry nitrogen glow box when necessary. All other chemicals were supplied by Sigma-Aldrich in analytic grade and used as received. NMR analysis was performed on Bruker, Varian or Oxford 400 MHz instruments with deuterated solvents (Oxford Isotopes). ¹H NMR and ¹³C{¹H} NMR spectra were referenced to residual solvent peaks as published by Fulmer *et al.*^[25] (¹H NMR, 400 MHz DMSO: δ = 2.5 (p, J = 3.7, 1.8), ¹³C{¹H} NMR, 100 MHz DMSO: δ = 39.52), while ³¹P{¹H} NMR spectra was referenced to H₃PO₄. GC-MS analysis was performed using an Agilent 220-MS fitted with a HP-5 column (30 m × 250 mm × 0.25 mm).

Synthesis

1,3-Bis-(2,6-diisopropylphenyl)imidazolium chloride (iPrHCl) was synthesized following a slightly modified literature procedure.^[26] 17.5 g (0.1 mol) 2,6-diisopropylaniline were dissolved in 100 ml ethanol in a round-bottomed flask and 7.00 g (0.05 mol) 40 wt% aqueous glyoxal solution added followed by three drops of formic acid. After stirring the mixture overnight at room temperature, the bright yellow precipitate (bis-imine) was collected on a porous glass filter, washed with cold methanol and dried. Then, 0.938 g (31.2 mmol) paraformaldehyde was transferred to a Schlenk flask under argon and 9.4 ml 4 M HCl in dioxane (37.5 mol) added. The mixture was stirred until the paraformaldehyde was completely dissolved and the solution turned clear. Afterwards, 5.04 g (13.4 mmol) bis-imine was dissolved in 130 ml of THF in another Schlenk flask under argon and cooled to 0 °C. The paraformaldehyde solution was then transferred to the bis-imine solution via cannula, where after the mixture was allowed to heat to room temperature and left stirring overnight. The precipitated white product was finally collected on a porous glass filter, washed with THF and dried. Yield 2.51 g (44 %). ¹H NMR data corresponded to published data: ¹H NMR (400 MHz, CDCl₃) δ 9.88 (s, 1H, N-CH-N), δ 8.14 (d, J = 1.6, 2H, N-CH-CH-N), δ 7.57 (t, J = 7.8, 2H, phen-p), δ 7.35 (d, J = 7.9, 4H, phen-m), δ 2.44 (sep, J = 6.8, 4H, me-CH-me), δ 1.25 (dd, J = 4.9, 6.1, 24H, -CH₃). *1,3-Bis-(2,6-diisopropylphenyl)imidazolyidene (iPr)* was synthesized following a slightly modified published procedure.^[27]

FULL PAPER

212.5 mg (0.5 mol) *i*PrHCl was dispersed in 2 ml THF in a Schlenk flask in the glow box. A solution of 67.3 mg (0.6 mol) ^tBuOK in 5 ml THF was transferred to the *i*PrHCl solution in the glow box, where after the resulting mixture was stirred for 30 min and the solvent removed under vacuum. The solid residue was redissolved in hexane, filtered via cannula to another Schlenk flask and dried under vacuum to obtain an opalescent white product. Yield 127 mg (67%). ¹H NMR data corresponded to published data: ¹H NMR (400 MHz, THF-*d*₈) δ 8.14 (d, *J* = 1.6, 2H, N-CH-CH-N), δ 7.57 (t, *J* = 7.8, 2H, phen-*p*), δ 7.35 (d, *J* = 7.9, 4H, phen-*m*), δ 2.44 (sep, *J* = 6.8, 4H, me-CH-me), δ 1.25 (dd, *J* = 4.9, 6.1, 24H, -CH₃).

Pd(PPh)₂Cl₂ was synthesized according to a slightly modified literature procedure.^[16b] 176.3 mg (0.56 mmol) Pd(CH₃CN)₂Cl₂ was dissolved in 40 ml dichloromethane in a Schlenk flask under argon and 352.5 mg (1.3 mmol) triphenylphosphine added. The solution was then stirred overnight and the solvent removed under reduced pressure to obtain a crude product, which finally was washed several times with ethanol and diethyl ether followed by drying in vacuum overnight. Yield 356.1 mg (89%). ¹H NMR and ³¹P{¹H} NMR data corresponded to published data:^[16f] ¹H NMR (401 MHz, CDCl₃) δ 7.76-7.65 (m, 10H), δ 7.46-7.34 (m, 20H). ³¹P{¹H} NMR (162 MHz, CDCl₃) δ 24.3.

Pd(Phen)Cl₂ was synthesized by a slightly modified literature procedure.^[16c] 64.9 mg (0.25 mmol) Pd(CH₃CN)₂Cl₂ was dissolved in 10 ml of dichloromethane in a Schlenk flask. Addition of 45.1 mg (0.25 mmol) 1,10-phenanthroline (Phen) caused immediate precipitation of the product which was collected by filtration, washed in dichloromethane and dried in vacuum to give quantitative yield. ¹H NMR data of the product corresponded to published data:^[28] ¹H NMR (400 MHz, DMSO-*d*₆) δ 9.35 (d, *J* = 5.4, 2H), δ 8.14 (d, *J* = 8.2, 2H), δ 9.98 (d, *J* = 8.2, 2H), δ 8.29 (s, 2H).

*Pd(*i*Pr)₂Cl₂*. 12.6 mg (0.07 mmol) PdCl₂ was suspended in 5 ml THF in a Schlenk flask in the glove box and a solution of 55 mg (0.14 mmol) *i*Pr in 20 ml THF was added, which resulted in an immediate color change from dark brown to hazy yellow. After stirring overnight, the solvent was removed under vacuum and the remaining solid purified by column chromatography over silica with 1:1 hexane/CH₂Cl₂ as eluent yielding a light yellow product. Yield 27 mg (41%). ¹H NMR data of the product corresponded to published data:^[16a,16g-h] ¹H NMR (400 MHz, CDCl₃) δ 7.35 (t, *J* = 14.0, 4H, Ar-*p*), δ 7.07 (d, *J* = 7.6, 8H, Ar-*m*), δ 6.72 (s, 4H, N-CH-CH-N), δ 2.88 (sept, *J* = 7.6, 8H, me-CH-me), δ 0.90 (t, *J* = 7.6, 24H, -CH₃).

*Pd(*i*Pr)(3-chloropyridine)Cl₂* was synthesized by a published procedure.^[29] 88.5 mg (0.5 mmol) PdCl₂, 234 mg (0.55 mmol) *i*PrHCl, 345.5 mg (2.5 mmol) K₂CO₃ and 2 ml (14.8 mmol) 3-chloropyridine was loaded into a Schlenk flask and stirred at 80 °C overnight. The reaction mixture was cooled to room temperature, diluted with CH₂Cl₂ and filtered over celite and silica. Finally, the solvent was removed under vacuum and the oily solid washed with pentane to obtain a light yellow powder product, Yield 286 mg (89%). ¹H NMR data corresponded to published data:^[29] ¹H NMR (400 MHz, CDCl₃) δ 8.60 (dd, *J* = 2.4, 0.5, 1H, N-CH-CCl), δ 8.52 (dd, *J* = 5.6, 1.4, 1H, N-CH-C), δ 7.55 (ddd, *J* = 8.2, 2.4, 1.4, 1H, CCl-CH-C), δ 7.50 (t, *J* = 2.4, 2H, Ar-*p*), δ 7.35 (d, *J* = 7.8,

4H, Ar-*p*), δ 7.14 (s, 2H, N-CH-CH-N), δ 7.07 (ddd, *J* = 8.2, 5.6, 0.5, 1H, C-CH-C), δ 3.16 (sept, *J* = 6.8, 2H, me-CH-me), δ 1.48 (d, *J* = 6.6, 12H, -CH₃), δ 1.12 (d, *J* = 6.9, 12H, -CH₃).

1-Butyl-3-methylimidazolium bromide ([BMIM]Br) was synthesized according to a published procedure.^[16d] 78.2 ml (0.5 mol) 1-methylimidazol and 97.9 ml (0.9 mol) 1-chlorobutane was dissolved in 100 ml CH₃CN in a Schlenk flask under argon and refluxed for 80 h (completion of the reaction confirmed by TLC). The reaction mixture was then transferred by cannula to another Schlenk flask containing 500 ml well-stirred ethyl acetate and a seed crystal. Subsequently, the flask was cooled to -30 °C for 2 h, the solvent mixture removed by cannula filtration and the solid product dried under vacuum. Yield 161.5 g (>99%). ¹H NMR data corresponded to published data:^[16d] ¹H NMR (400 MHz, CDCl₃) δ 10.8 (s, 1H, N-CH-N), δ 7.22 (d, *J* = 14.0, 2H, N-CH-CH-N), δ 4.32 (t, *J* = 7.6, 2H, N-CH₂-C), δ 4.12 (s, 3H, N-CH₃), δ 1.91 (d, *J* = 7.6, 2H, C-CH₂-C), δ 1.38 (t, *J* = 7.6, 2H, C-CH₂-Me), δ 0.97 (t, *J* = 7.4, 3H, C-CH₃).

Catalytic tests

All catalytic reactions were performed as duplicated experiments in a 100 mL magnetically stirred Berghof reactor or a 300 mL mechanically stirred Parr reactor, both with stirring and internal temperature control. For each reaction, the reactor was loaded with catalyst, IL, internal standard, substrate and solvent and flushed three times with CO gas before charged with a CO/O₂ (9:1) gas mixture unless otherwise stated. CAUTION: Note that the CO/O₂ gas ratio is within the flammability range (15.5-94%^[30]) and should never be applied without taking the due safety precautions.

In an typical experiment with the Berghof reactor, the reactor was loaded with 1.22 g (7.5 mmol) [BMIM]Cl, 4.0 mg (6 μmol) Pd(PPh₃)Cl₂, 10.6 ml toluene, 0.55 ml (6 mmol) aniline, 84 μL (0.6 mmol) mesitylene as internal standard, 9 bar CO, 1 bar O₂ and heated to 140 °C under stirring at 1000 rpm. In all experiments, the liquid volume in the reactor was constant at 12.4 ml and the heating block preheated to 150 °C before the charged reactor was inserted. The reaction time was measured from the onset of set temperature, which was reached in 30 min. Temperature deviations from the set temperature were within ±3°C. After a desired reaction time, the heating block was removed and the reactor cooled to room temperature in an ice bath. Afterwards, the pressure was released and the solvent and IL phases separated.

In an typical experiment with the Parr reactor, the reactor was loaded with 2.34 g (15 mmol) [BMIM]Cl, 8.1 (12 μmol) mg Pd(PPh₃)Cl₂, 22.2 ml toluene, 1.1 ml (12 mmol) aniline, 168 μL (0.12 mmol) mesitylene as internal standard, 9 bar CO, 1 bar O₂ and heated to 140 °C under stirring at 500 rpm. In all experiments, the liquid volume in the reactor was constant at 25.8 ml. The reaction time was measured from the onset of set temperature, which was reached in 1 h. Temperature deviations from the set temperature were within ±3°C. After a desired reaction time, the heating mantle was removed and the reactor cooled to room temperature in an ice bath. Afterwards, the pressure was released and the solvent and IL phases separated.

FULL PAPER

Analysis

Samples of the solvent and IL phases were analyzed by GC-MS and ^1H NMR, respectively. Aniline conversion was quantified using the internal standard method with mesitylene as internal standard. ^1H NMR spectra was measured in DMSO-d_6 and collected with a relaxation time of two times T1. Product yield of diphenylurea and aniline conversion was quantified using the internal standard method with [BMIM]Cl.

Acknowledgements

The authors are grateful to the Ministerio de Economía y Competitividad and the Fondo Europeo de Desarrollo Regional FEDER (CTQ2016-75016-R, AEI/FEDER, UE), the Generalitat de Catalunya (SGR2014), the Universitat Rovira I Virgili (Martí-Franques grant ref. 2013PMF-PIPF-89(0)) for funding and to the staff at Servei de Recursos Científics i Tècnics of the URV for assistance with sample analysis.

Keywords: Aniline • diphenylurea • ionic liquids • oxidative carbonylation • palladium

- [1] D. J. Díaz, A. K. Darko, L. McElwee-White, *European J. Org. Chem.* **2007**, 2007, 4453–4465.
- [2] F. Calderazzo, *Inorg. Chem.* **1965**, 4, 293–296.
- [3] K. L. Dunlap, *Kirk-Othmer Encycl. Chem. Technol.* **2010**, 1–13.
- [4] a) D. J. Díaz, K. G. Hylton, L. McElwee-White, *J. Org. Chem.* **2006**, 71, 734–738. b) P. Shelton, Y. Zhang, T. H. H. Nguyen, L. McElwee-White, *Chem. Commun.* **2009**, 1, 947–9. c) I. Pri-bar, H. Alper, *Can. J. Chem.* **1989**, 68, 1544. d) M. Aresta, P. Giannoccaro, I. Tommasi, A. Dibenedetto, A. Maria, M. Lanfredi, F. Ugozzoli, A. M. Manotti Lanfredi, F. Ugozzoli, M. Lanfredi, F. Ugozzoli, A. M. Manotti Lanfredi, F. Ugozzoli, *Organometallics* **2000**, 1995, 3879–3889. e) J. E. Mccusker, F. Qian, L. Mcelwee-white, *J. Mol. Catal. A Chem.* **2000**, 159, 11–17. f) J. E. Mccusker, C. A. Grasso, A. D. Main, L. Mcelwee-white, V. Uni, V. Gaines, *Org. Lett.* **1999**, 1, 4155–4158.
- [5] a) M. Casiello, F. Iannone, P. Cotugno, A. Monopoli, N. Cioffi, F. Ciminale, A. M. Trzeciak, A. Nacci, *J. Mol. Catal. A Chem.* **2015**, 407, 8–14. b) F. Shi, Y. Deng, *J. Catal.* **2002**, 211, 548–551. c) B. Zhu, R. J. Angelici, *J. Am. Chem. Soc.* **2006**, 128, 14460–14461. d) A. Orejón, A. M. Masdeu-Bultó, P. Salagre, S. Castillón, C. Claver, A. Padilla, B. Almena, F. L. Serrano, *Ind. Eng. Chem. Res.* **2008**, 47, 8032–8036. e) F. Saliu, B. Putomatti, B. Rindone, *Tetrahedron Lett.* **2012**, 53, 3590–3593. f) P. Giannoccaro, C. F. Nobile, P. Mastrorilli, N. Ravasio, *J. Organomet. Chem.* **1991**, 419, 251–258. g) S. A. R. Mulla, S. P. Gupte, R. V. Chaudhari, *J. Mol. Catal.* **1991**, 67, L7–L10. h) S. Kanagasabapathy, S. P. Gupte, R. V. Chaudhari, *Ind. Eng. Chem. Res.* **1994**, 33, 1–6. i) X. Peng, F. Li, X. Hu, C. Xia, C. a. Sandoval, *Chinese J. Catal.* **2008**, 29, 638–642. j) S.-Z. Z. Zheng, X.-G. G. Peng, J.-M. M. Liu, W. Sun, C.-G. G. Xia, *Chinese J. Chem.* **2007**, 25, 1065–1068. k) R. Mancuso, D. S. Raut, N. Della Ca', F. Fini, C. Carfagna, B. Gabriele, *ChemSusChem* **2015**, 8, 2204–2211. l) N. Della Ca', P. Bottarelli, A. Dibenedetto, M. Aresta, B. Gabriele, G. Salerno, M. Costa, *J. Catal.* **2011**, 282, 120–127. m) M. R. Didgikar, S. S. Joshi, S. P. Gupte, M. M. Diwakar, R. M. Deshpande, R. V. Chaudhari, *J. Mol. Catal. A Chem.* **2011**, 334, 20–28. n) B. Gabriele, R. Mancuso, G. Salerno, M. Costa, *Chem. Commun.* **2003**, 486–487. o) B. Gabriele, G. Salerno, R. Mancuso, M. Costa, *J. Org. Chem.* **2004**, 69, 4741–4750. p) P. Giannoccaro, *J. Organomet. Chem.* **1987**, 336, 271–278. q) P. Giannoccaro, C. Ferragina, M. Gargano, E. Quaranta, *Appl. Catal. A Gen.* **2010**, 375, 78–84.
- [6] a) J. Tsuji, N. Iwamoto, *Chem. Commun.* **1966**, 380. b) H. Alper, G. Vasapollo, F. W. Hartstock, M. Mlekuz, *Organometallics* **1987**, 6, 2391–2393. c) V. L. K. Valli, H. Alper, *Organometallics* **1996**, 14, 80–82. d) K. Hiwatari, Y. Kayaki, K. Okita, T. Ukai, I. Shimizu, A. Yamamoto, *Bull. Chem. Soc. Jpn.* **2004**, 77, 2237–2250. e) K. D. Kim, S. M. Lee, N. S. Cho, J. S. Oh, *J. Mol. Catal.* **1992**, 75.
- [7] W. Brackman, *Discuss. Faraday Soc* **1968**, 122–126.
- [8] X. Wang, P. Li, X. Yuan, S. Lu, *J. Mol. Catal. A Chem.* **2006**, 255, 25–27.
- [9] a) J. Chen, S. Lu, *Appl. Catal. A Gen.* **2004**, 261, 199–203. b) H. S. Kim, Y. J. Kim, H. Lee, S. D. Lee, C. S. Chin, *J. Catal.* **1999**, 534, 526–534. c) S. Hwang, H. S. Kim, M. Cheong, *Bull. Korean Chem. Soc.* **2012**, 33, 3864–3866. d) X. Zhang, H. Jing, G. Zhang, *Synth. Commun.* **2010**, 40, 1614–1624.
- [10] a) A. Krogul, J. Skupińska, G. Litwinienko, *J. Mol. Catal. A Chem.* **2011**, 337, 9–16. b) A. Krogul, G. Litwinienko, *J. Mol. Catal. A Chem.* **2015**, 407, 204–211.
- [11] P. A. Jäger, C. N. Rentzea, H. Kieczka, in *Ullmann's Encycl. Industrial Chemistry*, Wiley-VCH, Weinheim, **2012**, pp. 553–560.
- [12] a) N. V. Plechkova, K. R. Seddon, Eds., *Ionic Liquids UnCoiled: Critical Expert Overviews*. Wiley & Sons, Inc., Hoboken, **2012**. b) N. V. Plechkova, K. R. Seddon, Eds., *Ionic Liquids Completely Uncoiled: Critical Expert Overviews*. Wiley & Sons, Inc., Hoboken, **2015**. c) R. Fehrmann, A. Riisager, M. Haumann, Eds., *Supported Ionic Liquids: Fundamentals and Applications*, Wiley-VCH Verlag GmbH & Co. KGaA, **2014**. d) V. I. Părvulescu, C. Hardacre, *Chem. Rev.* **2014**, 107, 2615. e) Z. Gui, N. Zahrtmann, S. Saravanamurugan, I. Reyero, Z. Qi, M. A. Bañares, A. Riisager, E. J. Garcia-Suarez, *Chem. Sel.* **2016**, 1, 5869–5873.
- [13] F. Amoroso, E. Zangrando, C. Carfagna, C. Muller, D. Vogt, M. Hagar, F. Ragaini, B. Milani, *Dalt. Trans.* **2013**, 42, 14583–14602.
- [14] a) Z. Lei, C. Dai, B. Chen, *Chem. Rev.* **2014**, 114, 1289–1326. b) K. Fischer, M. Wilken, *J. Chem. Thermodyn.* **2001**, 33, 1285–1308.
- [15] T. Hoshino, T. Mukaiyama, H. Hoshin, *J. Am. Chem. Soc.* **1952**, 115, 18–21.
- [16] a) M. S. Viciu, R. M. Kissling, E. D. Stevens, S. P. Nolan, *Org. Lett.* **2002**, 4, 2229–2231. b) B. J. V. Verkuil, W. Szyman, B. Wu, A. J. Minnaard, D. B. Janssen, J. G. de Vries, B. L. Feringa, *Chem. Commun.* **2010**, 46, 901–903. c) A. Bontempi, E. Alessio, G. Chanos, G. Mestroni, *J. Mol. Catal.* **1987**, 42, 67–80. d) J. Dupont, C. S. Consorti, P. A. Z. Suarez, R. F. de Souza, *Org. Synth.* **2002**, 79, 236. e) A. R. Mulla, S. P. Gupte, V. Chaudhari, **1991**, 67, 7–10. f) J. Tsuji, H. Guo, *Encycl. Reagents Org. Synth.* **2015**, 1–27. g) H. Lebel, M. K. Janes, A. B. Charette, S. P. Nolan, *J. Am. Chem. Soc.* **2004**, 126, 5046–5047. h) L.-C. Campeau, P. Transandote, K. Fagnou, *Org. Lett.* **2005**, 7, 1857–1860. i) V. L. K. Valli, H. Alper, *Organometallics* **1996**,

FULL PAPER


- 14, 80–82.
- [17] F. Shi, J. Peng, Y. Deng, *J. Catal.* **2003**, 219, 372–375.
- [18] a) J. C. C. Chen, I. J. B. Lin, *Organometallics* **2000**, 19, 5113–5121. b) M. G. Gardiner, W. A. Herrmann, C. Reisinger, J. Schwarz, M. Spiegler, *J. Organomet. Chem.* **1999**, 572, 239–247. c) M. M. Konnick, I. A. Guzei, S. S. Stahl, *J. Am. Chem. Soc.* **2004**, 126, 10212–10213. d) S. S. Stahl, *Science (80-.)* **2005**, 309, 1824–1826. e) M. M. Konnick, N. Decharin, B. V. Popp, S. S. Stahl, *Chem. Sci.* **2011**, 2, 326–330. f) M. M. Konnick, S. S. Stahl, *J. Am. Chem. Soc.* **2008**, 130, 5753–5762. g) M. M. Konnick, B. A. Gandhi, I. A. Guzei, S. S. Stahl, *Angew. Chemie - Int. Ed.* **2006**, 45, 2904–2907.
- [19] A. N. Gómez-Suárez, S. P. Nolan, D. J. Nelson, *Chem. Commun.* **2017**, 53, 2650–2660.
- [20] a) I. del Río, C. Claver, P. W. N. M. van Leeuwen, *Eur. J. Inorg. Chem.* **2001**, 2719–2738. b) D. M. Norton, E. A. Mitchell, N. R. Botros, P. G. Jessop, M. C. Baird, *J. Org. Chem.* **2009**, 74, 6674–6680.
- [21] L. Luza, A. Gual, C. P. Rambor, D. Eberhardt, S. R. Teixeira, F. Bernardi, D. L. Baptista, J. Dupont, *Phys. Chem. Chem. Phys.* **2014**, 16, 18088–18091.
- [22] A. R. C. Morais, A. M. da Costa Lopes, E. Bogel-Lukasik, R. Bogel-Lukasik, *Ind. Eng. Chem. Res.* **2013**, 52, 14722–14726.
- [23] a) S. Tsuzuki, M. Mikami, *Phys. Chem. Chem. Phys.* **2007**, 9, 4780–4784. b) E. I. Izgorodina, D. Golze, R. Maganti, V. Armel, M. Taige, T. J. S. Schubert, D. R. MacFarlane, *Phys. Chem. Chem. Phys.* **2014**, 16, 7209–7221.
- [24] T. Yamada, Y. Tominari, S. Tanaka, M. Mizuno, *J. Phys. Chem. B* **2015**, 119, 15696–15705.
- [25] G. R. Fulmer, A. J. M. Miller, N. H. Sherden, H. E. Gottlieb, A. Nudelman, B. M. Stoltz, J. E. Bercaw, K. I. Goldberg, *Organometallics* **2010**, 29, 2176–2179.
- [26] X. Bantreil, S. P. Nolan, *Nat. Protoc.* **2011**, 6, 69–77.
- [27] A. J. Arduengo, R. Krafczyk, R. Schmutzler, H. A. Craig, J. R. Goerlich, W. J. Marshall, M. Unverzagt, *Tetrahedron* **1999**, 55, 14523–14534.
- [28] L. Pazderski, E. Szlyk, J. Sitkowski, B. Kamienski, L. Kozerski, J. Tousek, R. Marek, *Magn. Reson. Chem.* **2006**, 44, 163–170.
- [29] C. J. O. Brien, A. B. Kantchev, C. Valente, N. Hadei, G. A. Chass, A. Lough, A. C. Hopkinson, M. G. Organ, *Chem. a Eur. J.* **2006**, 12, 4743–4748.
- [30] B. Lewis, G. von Elbe, in *Combustion, Flames Explosions of Gases*, 3rd Ed. (Eds.: B. Lewis, G. von Elbe), Academic Press, Orlando, **1987**, pp. 705–716.

FULL PAPER

Entry for the Table of Contents (Please choose one layout)

FULL PAPER

Ionic Liquid as promotor – Pd-complex systems in combination with imidazolium ionic liquids catalyze the selective oxidative carbonylation of aniline with unprecedented activity under relatively mild conditions. *In-situ* NMR study of the reaction system led to observation of an only previously suggested Pd-intermediate.

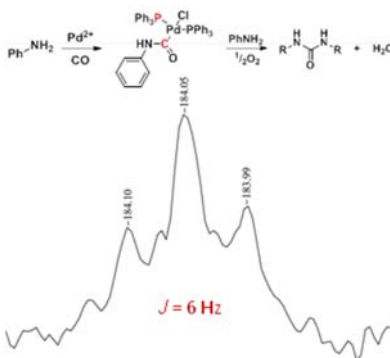

N. Zahrtmann, C. Claver, C. Godard,* A. Riisager,* and E.J. Garcia-Suarez

Page No. – Page No.

Selective Oxidative Carbonylation of Aniline to Diphenylurea with Ionic Liquids