

Jointly published by
Akadémiai Kiadó, Budapest
and Springer, Dordrecht

React.Kinet.Catal.Lett.
Vol. 86, No. 2, 347-354
(2005)

RKCL4754

CATALYTIC INVESTIGATION OF Fe-ZSM5 IN THE SELECTIVE CATALYTIC REDUCTION OF NO_x WITH NH₃

Mukundan Devadas, Oliver Kröcher* and Alexander Wokaun

Paul Scherrer Institute, CH-5232 Villigen PSI, Switzerland

Received February 28, 2005

Accepted June 28, 2005



Abstract

Fe-ZSM5 coated on a cordierite monolith was characterized and tested in the selective reduction of nitrogen oxides (NO_x) with ammonia. More than 70% of the NO_x were converted at T ≥ 350 °C if only NO was present in the feed. For equimolar amounts of NO and NO₂ in the feed, NO_x conversions of over 90% were reached for T = 200-450°C. Hydrothermal ageing of Fe-ZSM5 resulted in a small loss in NO_x conversion and enhanced N₂O formation.

Keywords: Fe-ZSM5, DeNO_x, monolith, SCR, selective catalytic reduction, ammonia

INTRODUCTION

The selective catalytic reduction of NO_x with urea (urea SCR) is the currently favored NO_x abatement technique for mobile heavy-duty diesel engines [1]. Urea is used, because it is a safe and non-toxic storage compound for ammonia (reaction 1), which is the actual reducing agent in the SCR reactions:



*Corresponding author. E-mail: <oliver.kroecher@psi.ch>

Reaction 2 is the so-called standard SCR reaction, implying a 1:1 stoichiometry for ammonia and NO and the consumption of oxygen. The SCR reaction can be accelerated by using equimolar amounts of NO and NO₂ in the reaction mixture (reaction 3), called fast SCR reaction. V₂O₅/WO₃-TiO₂ catalysts are commonly used for this process, due to their high activity at low ammonia slip [2, 3]. Fe-ZSM5 is regarded as a potential alternative to the established vanadia based catalysts, because it functions at temperatures up to 600°C, the risk to emit volatile vanadyl species is avoided and no disposal problems occur. Although some literature is available about ammonia SCR on Fe-ZSM5 powders [4-7], not much is known about the SCR activity of Fe-ZSM5 coated on a monolith.

In the present paper, we report on Fe-ZSM5 prepared by solid-state ion exchange and coated on cordierite monolith. The active material was characterized and the catalytic properties of the freshly prepared as well as the hydrothermally treated catalyst were investigated, focusing on realistic test conditions.

EXPERIMENTAL

Fe-ZSM5 was prepared by the solid-state ion exchange method from H-ZSM5 of module (Si/Al ratio) 28 (supplied by Umicore AG, Germany) and FeCl₂·4H₂O [8]. The Fe-ZSM5 powder was coated on a cordierite monolith by the following method: the slurry was prepared by suspending 0.5 g of the zeolite in 2 cm³ of 0.5 M Al(NO₃)₃·9H₂O solution. Successive immersions of the cordierite monolith in the suspension were performed to achieve the desired zeolite loading. After each immersion, air was softly blown through the channels in order to eliminate excess suspension and to achieve a uniform layer on the surface. The coated monolith was finally dried at RT for 2 h and then calcined at 500°C for 5 h. The weight of the cordierite was determined before and after immersion, in order to control the amount of zeolite loaded on the monolith.

Specification of the coated monolith: cordierite volume = 7.5 cm³, cell density = 400 cpsi, catalyst loading (active mass) = 0.82 g (0.170 mol). ICP-AES: Si/Al = 28, Fe = 11.4 wt.%, Fe/Al = 2.3. X-ray diffraction patterns were recorded with a Philips X`Pert powder diffractometer with FeK α radiation. Measurements were carried out in the 2 θ range 0-70° using a step size of 0.05°. Peak identification was performed with the "Powder Diffraction File™" from ICDD.

The coated Fe-ZSM5 monolith was hydrothermally aged for 50 h at 650°C in 5% water and 10% oxygen in nitrogen.

The setup of the test apparatus has been described in [9]. The composition of diesel exhaust gas was approximated by a model feed gas containing 10% O₂, 5% H₂O, 1000 ppm of NO and N₂. NH₃ was added in the range 100-1000 ppm. In the case of fast SCR, the NO as well as the NO₂ concentration was 500 ppm. The gas hourly space velocity (GHSV = volumetric gas flow/catalyst volume) was 52,000 h⁻¹, representative of typical operative conditions with automotive diesel exhaust.

The concentrations of NO, NO₂, N₂O, NH₃ and H₂O in the gas phase were analyzed by HR-FTIR spectroscopy (Nicolet Magna IR 560, OMNIC QuantPad software) through a heated multiple pass gas cell.

RESULTS AND DISCUSSION

The XRD patterns in Fig. 1 show an unchanged MFI structure for the Fe-ZSM5 powder after solid-state ion exchange and calcination, compared to the parent H-ZSM5. However, the ion exchange process resulted in the additional formation of Fe₂O₃ in the hematite phase ($2\theta = 42.22$ and 45.36).

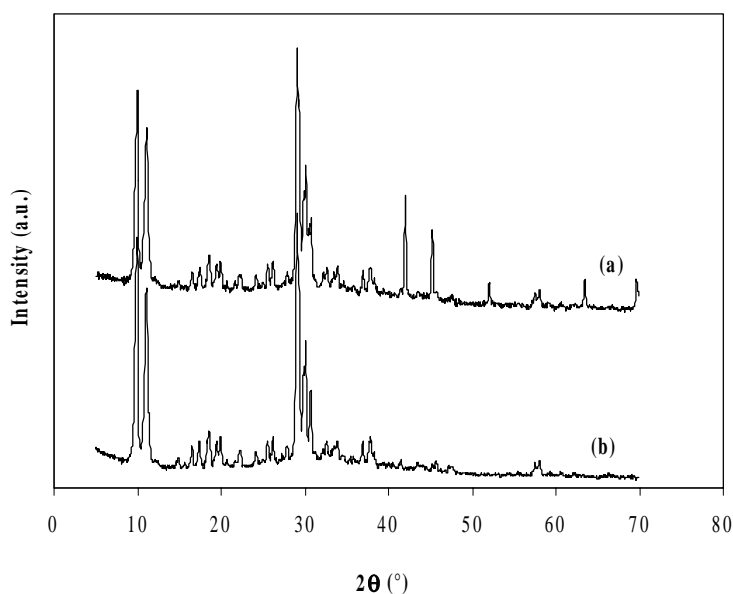


Fig. 1. XRD patterns of (a) Fe-ZSM5 and (b) H-ZSM5 (base material)

The practical application of the SCR process for the exhaust gas treatment of mobile Diesel engines calls for a high NO_x conversion (DeNO_x) and simultaneously for a low slip of ammonia through the catalyst. An ammonia emission of 10 ppm in average is generally accepted for exhaust gas treatment techniques, which necessitates a dosage control for adding the right amount of ammonia relating to the NO_x concentration and the activity of the catalyst at a given temperature. The stoichiometric ratio α represents the ratio between moles of nitrogen added as reducing agent and the moles of NO_x contained in the feed, *e.g.* ammonia as reducing agent: $\alpha = \text{NH}_{3,\text{in}}/\text{NO}_{x,\text{in}}$.

The conventional measurement of DeNO_x vs temperature at constant α in the laboratory is thus not sufficient, since the varying α in real systems is not considered. Only the stepwise increase of the dosing ratio from $\alpha = 0$ -1.2 for each given temperature and the measurement of the resulting emissions gives a full picture of the catalyst performance. From these data obtained for the fresh and aged Fe-ZSM5 monolith under standard SCR conditions, the DeNO_x values were calculated, according to $\text{DeNO}_x = (\text{NO}_{x,\text{in}} - \text{NO}_{x,\text{out}})/\text{NO}_{x,\text{in}}$ [%]. For the fresh Fe-ZSM5 monolith the plot of the ammonia slip vs DeNO_x shows curve

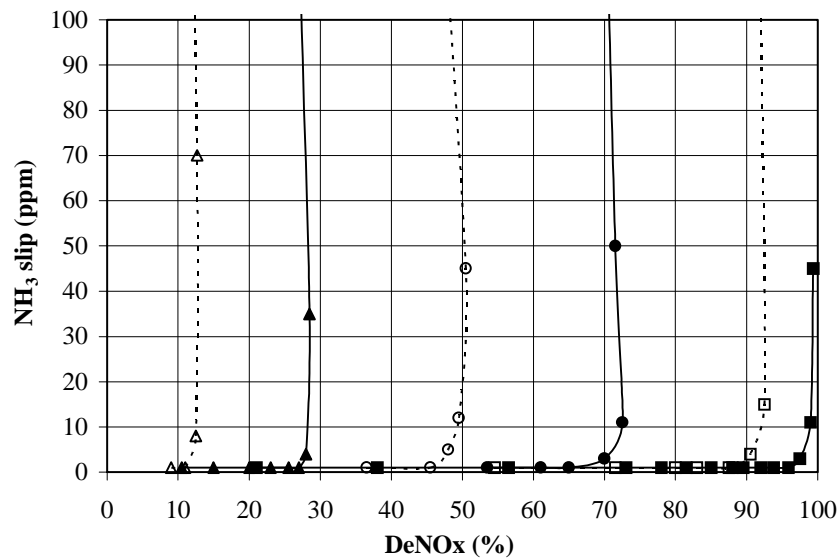


Fig. 2. NH_3 slip through the catalyst vs DeNO_x of fresh Fe-ZSM5 coated on cordierite under standard SCR conditions ($\text{NO}_m = 1000$ ppm). (Δ) 200°C, (\blacktriangle) 250°C, (\circ) 300°C, (\bullet) 350°C, (\square) 400°C, (\blacksquare) 450°C

curve shapes typical for a well suited SCR catalyst (Fig. 2). High NO_x conversions are reached with negligible ammonia slip up to the maximum activity of the catalyst at each given temperature. Only if ammonia is overdosed the excess is slipping through the catalyst. It is discernible from Fig. 2 that the steep part of the curves are slightly bent backward, indicating an inhibition of the SCR reaction by ammonia.

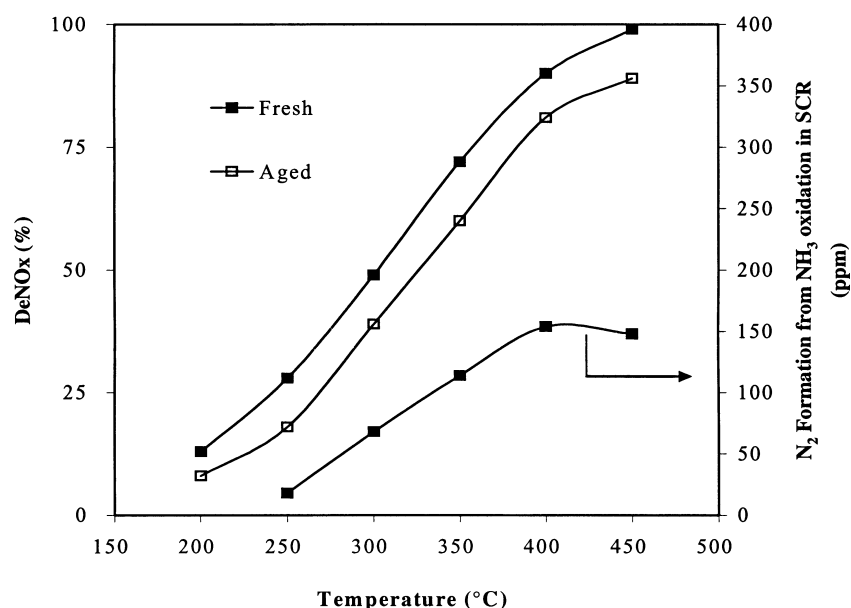


Fig. 3. DeNO_x activity of fresh (■) and aged (□) Fe-ZSM5 and N₂ formed from NH₃ oxidation at 10 ppm ammonia slip

The direct oxidation of NH₃ by O₂ in the exhaust gas to N₂ (NH_{3,ox}) was calculated as difference between the totally consumed NH₃ (NH_{3,cons} = NH_{3,out} - NH_{3,in}) and the NH₃ needed for the SCR reaction (NH_{3,SCR} = NH_{3,in} - DeNO_x/100·NO_{x,in}). From the DeNO_x values and the NH₃ oxidation of fresh and aged catalyst the results at 10 ppm NH₃ slip were selected and plotted vs temperature in Fig. 3. The DeNO_x activity is steadily increasing from 200–450°C, reaching ≥ 90% for T ≥ 400°C. Aging of the catalyst resulted in an absolute decrease of the NO_x conversion of ~ 10% over the entire temperature range, proving the good hydrothermal stability of the catalyst. No N₂O could be detected at all temperatures for both the fresh and the aged catalyst. N₂ formed by NH₃ oxidation was increasing with temperature till T ≤ 400°C. Calculating

the ratio of reaction rates $\text{NH}_{3,\text{ox}}/\text{NH}_{3,\text{SCR}}$ for each temperature revealed that a nearly constant fraction of about 12% of the consumed ammonia is oxidized to nitrogen and about 88% is going into the SCR reaction.

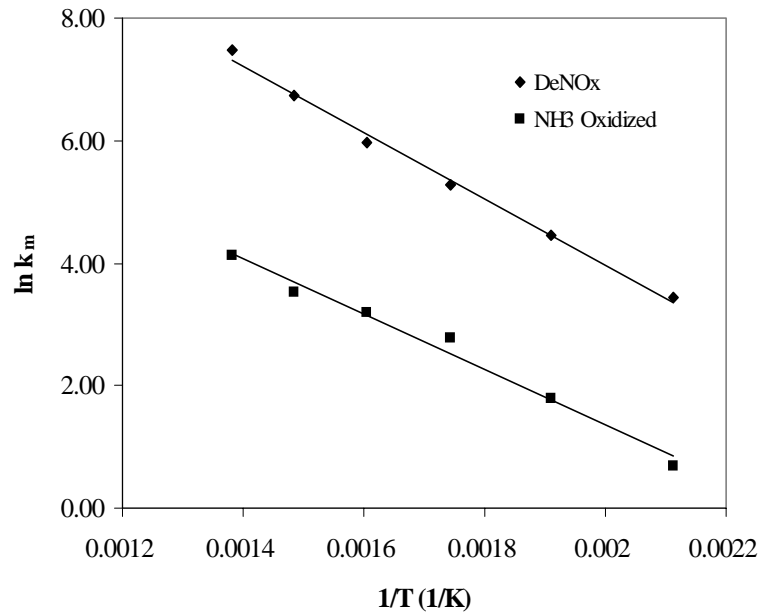


Fig. 4. Arrhenius plot of DeNOx activity (◆) under standard SCR conditions and NH₃ oxidation (■)

For a kinetic analysis of SCR reaction and ammonia oxidation, the DeNOx results from Fig. 3 were evaluated in form of an Arrhenius plot (Fig. 4), complemented with data from a separate experiment, in which only direct NH₃ oxidation was investigated ($\text{NH}_{3,\text{in}} = 1000$ ppm, $\text{NO}_{x,\text{in}} = 0$). For this aim, the measured NO_x conversions and NH₃ oxidation values were converted into rate constants k_m assuming a first order rate law and applying the equation for a plug flow reactor:

$$k_m = -\frac{V^*}{W} \cdot \ln\left(1 - \frac{X}{100}\right)$$

where k_m is the first order rate constant (referred to the catalyst mass) ($\text{cm}^3/\text{g s}$), V^* is the gas flow at the actual conditions (cm^3/s), W is the active mass (g) and

X is the conversion (%). From the slope of the regression line in the Arrhenius plot, the activation energy of the SCR reaction was found to be 45 kJ/mol and the pre-exponential factor is $1.7 \times 10^6 \text{ cm}^3/\text{g s}$. This activation energy is smaller than the value found by Huang *et al.* for Fe-ZSM5 (54 kJ/mol) [10], but it is close to the value found for Cu-ZSM5 (44 kJ/mol) [11]. The activation energy needed for the direct ammonia oxidation is 38 kJ/mol and the pre-exponential factor is $3.3 \times 10^4 \text{ cm}^3/\text{g s}$. The constant ratio of SCR reaction and ammonia oxidation for all temperatures over Fe-ZSM5 was confirmed by the kinetic analysis, revealing similar activation energies and temperature dependencies of the two parallel reactions.

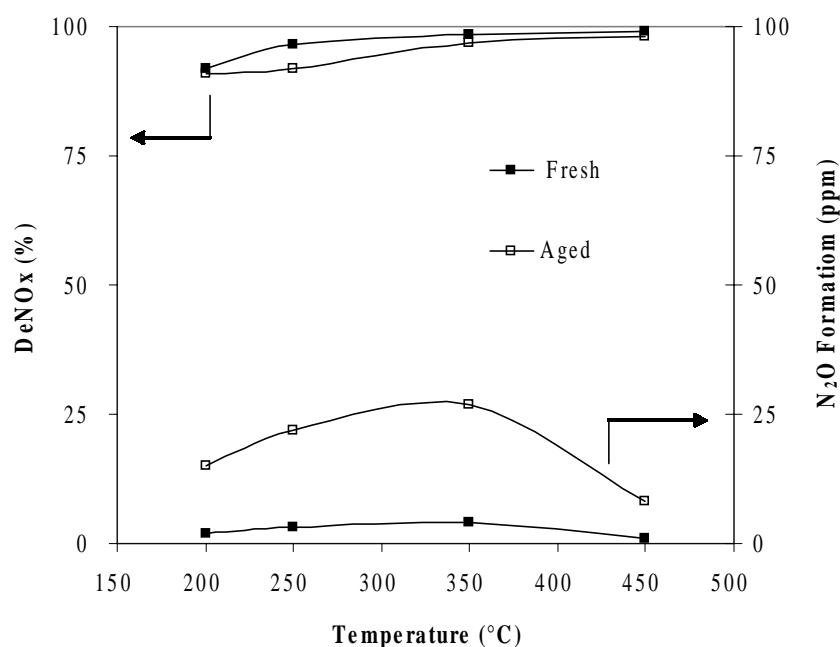


Fig. 5. DeNOx activity and N₂O formation of fresh (■) and aged (□) Fe-ZSM5 coated on cordierite at 10 ppm ammonia slip ($\text{NO}_{\text{in}} = 500 \text{ ppm}$, $\text{NO}_{2,\text{in}} = 500 \text{ ppm}$)

Figure 5 shows the DeNOx activity vs temperature at 10 ppm NH₃ slip for the fresh and aged Fe-ZSM5 monolith under fast SCR conditions where equimolar amounts of NO and NO₂ are present in the feed mixture. The DeNOx activity of the fresh catalyst was tremendously enhanced to $\geq 90\%$ at $T \geq 200^\circ\text{C}$. Negligible amounts ($\sim 5 \text{ ppm}$) of N₂O were produced. The NOx conversion was nearly the same for the aged catalyst. The loss in DeNOx

activity was only ~ 3%, but at the same time the production of N₂O was enhanced at all temperatures, the maximum being at T = 350°C (~ 25 ppm). Long *et al.* [12] explained the SCR reaction and the formation of N₂O over Fe-ZSM5 by the postulation of [NH₄⁺]₂NO₂ as intermediate species, which might react with NO to nitrogen and with NO₂ to nitrogen and N₂O.

CONCLUSIONS

Fe-ZSM5 prepared by solid-state ion exchange is a very active catalyst for the NO reduction with NH₃ under simulated exhausted gas conditions, especially if equimolar amounts of NO and NO₂ are used. However, 12% of the dosed ammonia is always consumed by the oxidation to nitrogen. That implies the necessity of a permanent overdosage of reducing agent if Fe-ZSM5 is chosen as catalyst in a real SCR system. The catalysts remained active even after aging, but the aged catalyst formed N₂O in modest amounts. This has to be regarded critical due to the large greenhouse potential of N₂O. Further investigations are being carried out to identify the Fe sites involved in the SCR reaction and to reveal the influence of Brønsted sites on NO_x conversion.

Acknowledgement. Financial support by the Umicore AG, Germany is gratefully acknowledged.

REFERENCES

1. M. Koebel, M. Elsener, M. Kleemann: *Catal. Today*, **59**, 335 (2000).
2. H. Bosch, F. Janssen: *Catal. Today*, **2**, 369 (1988).
3. P. Forzatti, L. Lietti: *Heterogen. Chem. Rev.*, **3**, 33 (1996).
4. R.Q. Long, R.T. Yang: *J. Catal.*, **188**, 332 (1999).
5. R.Q. Long, R.T. Yang: *Catal Lett.*, **74**, 201 (2001).
6. H.Y. Chen, W.M.H. Sachtler: *Catal. Today*, **42**, 73 (1998).
7. Ai-Zeng Ma, W. Grünert: *Chem. Commun.*, 71 (1991).
8. I.O.Y. Liu, N.W. Cant, M. Kögel, T. Turek: *Catal. Lett.*, **63**, 241 (1999).
9. G. Madia, M. Koebel, M. Elsener, A. Wokaun: *Ind. Eng. Chem. Res.*, **41**, 4008 (2002).
10. H.Y. Huang, R.Q. Long, R.T. Yang: *Appl. Catal. A.*, **235**, 241 (2002).
11. T. Komatsu, M. Nunokawa, I. S. Moon, T. Takahara, S. Namba, T. Yashima: *J. Catal.*, **148**, 427 (1994).
12. R.Q. Long, R.T. Yang: *J. Catal.*, **198**, 20 (2001).