

Contents lists available at ScienceDirect

Materials and Design

journal homepage: www.elsevier.com/locate/matdes

A comprehensive microstructural analysis of Al–WC micro- and nano-composites prepared by spark plasma sintering



Amir Pakdel^{a,*}, Agnieszka Witecka^b, Gauthier Rydzek^a, Dayangku Noorfazidah Awang Shri^c

^a World Premier International Center for Materials Nanoarchitectonics (MANA), National Institute for Materials Science (NIMS), Tsukuba, Japan


^b Institute of Fundamental Technological Research, Polish Academy of Sciences, Warsaw, Poland

^c Faculty of Mechanical Engineering, Universiti Malaysia Pahang, Pekan, Pahang, Malaysia

HIGHLIGHTS

- Aluminum matrix composites containing 1–10 wt.% WC micro-, nano- and bimodal-particles are consolidated by spark plasma sintering (SPS).
- The highest and lowest densification levels are obtained in 1 wt.% microcomposites (99.8%) and 10 wt.% nanocomposites (94.4%), respectively.
- Hardness increases by SPS temperature (400 → 500 °C) in 5 and 10 wt.% microcomposites, but slightly decreases in 1 wt.% microcomposites.
- Nanocomposites achieve largest hardness at 5 wt.% WC concentration, but micro- and bimodal-composites are hardest at 10 wt.% WC concentration.
- Interplay between WC particles distribution homogeneity and composite compressibility during SPS dictate the hardening level achievable in the composites.

GRAPHICAL ABSTRACT

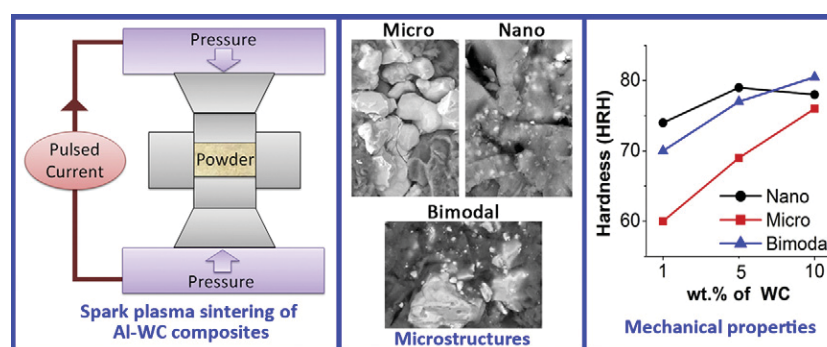

ARTICLE INFO

Article history:

Received 4 November 2016

Received in revised form 18 January 2017

Accepted 21 January 2017

Available online 25 January 2017

Keywords:

Composite
Nanoparticle
Microparticle
Powder metallurgy
SPS
Microstructure

ABSTRACT

There have been many investigations on metal matrix microcomposites produced by conventional casting routes; however, in the past decade, the focus has shifted more toward nanocomposites produced via solid state routes. To have a realistic view of performance prediction and optimum design of such composites, in this work Al matrix composites (AMCs) reinforced with WC microparticles, nanoparticles, and bimodal micro-/nano-particles were prepared by spark plasma sintering. The effects of particle size and concentration, and process variables (i.e. sintering temperature, duration, and pressure) on the evolution of microstructure, density and hardness of the composites were studied comprehensively. Full densification of AMCs with high particle concentration was problematic because of ceramic cluster formations in the microstructure. This effect was more emphasized in AMCs containing nanoparticles. AMCs with microparticles were more easily densified, but their hardness benefits were inferior. On the other hand, the mixture of micro- and nano-particles in Al-WC bimodal composites led to better matrix reinforcement integrity and an overall improvement in the microstructural properties. Finally, increasing the sintering temperature improved the microstructural features

* Corresponding author.

E-mail address: PAKDEL.Amir@nims.go.jp (A. Pakdel).