

Influence of CO₂ Partial Pressure on Ethanol Dry Reforming Using 5%Ce-10%Co/Al₂O₃ Catalyst for Hydrogen Production

Fahim Fayaz*, Ahmad Ziad Sulaiman, Sharanjit Singh, Sweeta Akbari
Faculty of Chemical & Natural Resources Engineering
Universiti Malaysia Pahang (UMP)
Lebuhraya Tun Razak, 26300 Gambang, Kuantan, Pahang, Malaysia
*fahimfayaz10@yahoo.com

Abstract— The influence of CO₂ partial pressure on ethanol dry reforming has been studied over Ce-promoted Co catalyst supported on Al₂O₃ from 20 to 50 kPa, C₂H₅OH was kept at 20 kPa and under atmospheric pressure. The catalyst was synthesized using wet impregnation method and tested in a quartz fixed-bed reactor. X-ray diffraction analysis indicated the formation of CeO₂, Co₃O₄ and spinel CoAl₂O₄ phases on catalyst surface. CoO and Co₃O₄ and CeO₂ phases were formed during temperature-programmed calcination and 5%Ce-10%Co/Al₂O₃ catalyst has a total high surface area of 137.35 m² g⁻¹. Both C₂H₅OH and CO₂ conversions was improved with increasing CO₂ partial pressure from 20 at 50 kPa and an optimal selectivity of H₂ and CO was obtained at 50 kPa.

Keywords—Ethanol dry reforming; Hydrogen; Ce promoter; Co-based catalyst

1. INTRODUCTION

With rise in world's population and energy demand have stimulated an initiative to find the alternative energy source with clean and eco-friendly source. The fossil fuels are accounted more than 80% to meet energy demand of the world. It has created serious environmental problems, such as greenhouse gases and climate changes [1], [2]. In addition, the problems generated by the environmental pollution are considered as a critical challenge for the next generations. Developed countries are investing in the development of fuel processing technology and gaseous fuel for power generation by fuel cells [3]. The production of syngas (a mixture of H₂ and CO) by steam reforming and dry reforming has been emerged as a promising method to produce synthetic fuel or a clean energy carrier. In past few decades, numerous research articles have been published on dry reforming of methane. In this process, greenhouse gases (CO₂ and CH₄) were used as feed-stock to produce eco- friendly syngas [4], [5]. A non-renewable methane, an important component of natural gas is utilized [6]. From the environmental perspective, ethanol is preferred to methane because of easy availability, abundance and cost effectiveness. It is also known as less toxic and renewable fuel [7]. Moreover, ethanol can be produced from biomass, which is one of the most abundantly available renewable resource, can be obtained from forestry waste and residues [8]. The steam reforming of ethanol is also widely acknowledged for syngas production. However, this technique can effectively utilize greenhouse gases (CO₂) and also curtail the rise in level of CO₂ emission [7]. Therefore, ethanol dry reforming using 5%Ce-10%Co/Al₂O₃ catalyst for production of syngas has been thoroughly investigated for syngas production because it can minimize the impact of CO₂ on the environment, by effectively utilizing the ethanol and CO₂ in the reaction [9]. The aim of this research to investigate the physical properties of catalyst and influence of CO₂ partial pressure on ethanol dry reforming for H₂ production over 5% Ce-promoted 10%Co/Al₂O₃ catalyst.

2. EXPERIMENTAL

A. Catalyst preparation

The Gamma- Al_2O_3 support was purchased from Sasol (PURALOX SCCa150/200) and calcined in air at 1023 K for 5 h with heating rate of 5 K min^{-1} to ensure thermal stability. The 5%Ce-10%Co/ Al_2O_3 catalyst was prepared by using the wet impregnation method. Then, accurately weighted amount of $\text{Ce}(\text{NO}_3)_3 \cdot 6\text{H}_2\text{O}$ and $\text{Co}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ aqueous solutions (supplied by Sigma-Aldrich) were mixed with calcined alumina support and magnetically stirred for 3 h at room temperature and followed by drying at 383 K overnight and dried sample was calcined at 773 K for 3 h in air.

B. Catalyst characterization

The catalyst surface area, pore volume and pore diameter were determined in a Thermo Scientific Surfer unit using N_2 physisorption at 77 K. The crystal structures of $\gamma\text{-Al}_2\text{O}_3$ support and 5%Ce-10%Co/ Al_2O_3 catalyst were investigated using the X-ray diffraction (XRD), in a Rigaku Miniflex II system with wavelength, $\lambda = 1.5418 \text{ \AA}$ at 30 kV and 15 mA. The diffraction patterns were recorded from $2\theta = 3^\circ$ to 80° with 1° min^{-1} scan speed and a step size of 0.02° .

Temperature-programmed calcination (TPC) runs was performed for uncalcined 5%Ce-10%Co/ Al_2O_3 catalyst using TGA Q500 unit (TA Instrument). For complete removing of moisture and volatile compounds, sample was initially preheated at 373 K with 10 K min^{-1} heating rate for the 30 min in the flow of N_2 as flow of 100 ml min^{-1} . The sample was heated at 1023 K with different heating rates of $10\text{-}20 \text{ K min}^{-1}$ in the gas mixture of $4\text{N}_2:1\text{O}_2$ (100 ml min^{-1}) for 30 min kept isothermally and subsequently sample was cooled down at room temperature in the same gas mixture.

C. Catalytic tests

The catalytic activity test have been performed in a quartz fixed-bed reactor (L = 17 inches and O.D. = 3/8 inches) placed vertically in a split tubular furnace with varying CO_2 partial pressure from 20-50 kPa and $\text{C}_2\text{H}_5\text{OH}$ was kept at 20 kPa during reaction and reaction temperature of 973 K under atmospheric pressure. Approximately, $0.1 \text{ g}_{\text{cat}}$ of catalyst with average particle size of $125\text{-}160 \text{ }\mu\text{m}$ was mounted by quartz wool in the center of quartz reactor. The inlet flow of gas hourly space velocity, $\text{GHSV} = 42 \text{ L g}_{\text{cat}}^{-1} \text{ h}^{-1}$ was used for all runs to minimize both internal and external transport resistances. The $\text{C}_2\text{H}_5\text{OH}$ was fed into the reactor by using the syringe pump (KellyMed KL-602). Both CO_2 and N_2 flow rates were controlled through the Alicat mass flow controllers. The total flow rate of CO_2 , $\text{C}_2\text{H}_5\text{OH}$, and N_2 gas employed to the reactor was 70 ml min^{-1} . The collected gas from the reactor was analysed using an Agilent GC 6890 series gas chromatograph provided with thermal conductivity detector (TCD) and flame ionization (FID) detectors.

3. RESULTS AND DISCUSSION

A. BET Surface area

The physical properties of $\gamma\text{-Al}_2\text{O}_3$ support and 5%Ce-10%Co/ Al_2O_3 catalyst were obtained from N_2 physisorption measurements summarized in Table 1. The BET surface area of 5%Ce-10%Co/ Al_2O_3 catalyst was $137.35 \text{ m}^2 \text{ g}^{-1}$ and lower than the BET surface area of $\gamma\text{-Al}_2\text{O}_3$ support $175.29 \text{ m}^2 \text{ g}^{-1}$. After impregnation and calcination, the reduction in surface area and average pore volume from $0.46 \text{ cm}^3 \text{ g}^{-1}$ to $0.37 \text{ cm}^3 \text{ g}^{-1}$ was observed with presence of active metal on the surface of catalyst. This result was due to pore blockage with the presence of Ce and Co metal oxide phases.

Table 1: Textual properties of $\gamma\text{-Al}_2\text{O}_3$ support and 5%Ce-10%Co/ Al_2O_3 catalyst.

Catalysts	BET surface area ($\text{m}^2 \text{ g}^{-1}$)	Average pore volume ($\text{cm}^3 \text{ g}^{-1}$)	Average pore diameter (\AA)
$\gamma\text{-Al}_2\text{O}_3$	175.29	0.46	92.96
5%Ce-10%Co/ Al_2O_3	137.35	0.37	82.8

B. X-ray diffraction measurements

The XRD patterns of calcined gamma-Al₂O₃ and 5%Ce-promoted 10%Co/Al₂O₃ catalyst are shown in Fig. 1. The formation of gamma-Al₂O₃ phase was detected at $2\theta = 32.73^\circ, 36.79^\circ, 44.20^\circ, 45.62^\circ, 55.40^\circ$ and 67.06° whilst almost same peaks were observed on the surface of 5%Ce-promoted 10%Co/Al₂O₃ catalyst. Additionally, the peaks were identified on the surface of 5%Ce-promoted catalyst at $2\theta = 31.15^\circ$ and 36.97° belonged to Co₃O₄ phase whilst 2θ of 59.38° and 65.33° formation of spinel CoAl₂O₄. The peak was detected $2\theta = 28.50^\circ$ corresponded to the formation of CeO₂ phase for 5%Ce-promoted catalyst. These results were in agreement with other finding [10].

C. Thermogravimetric studies

The derivative weight profiles of 5%Ce-10%Co/Al₂O₃ catalyst during the temperature-programmed calcination are shown in Fig. 2. The peak P1 positioned at low temperature of 420-495 K with high intensity was due to the metal nitrates decomposition to the metal oxides equations (1) and (2), respectively.



During the air calcination, the second peak (P2) at high temperature of 500-550 K was ascribed to the oxidation of CoO to Co₃O₄ and Ce³⁺ to Ce⁴⁺ equations (3) and (4), respectively. Furthermore, beyond 550 K, there were no peak observed for all three heating ramps due to the completed decomposition of metal precursors to metal oxides (CoO and Co₃O₄) on catalyst surface during the temperature-programmed calcination analysis. This result in good agreement with Mahadi *et al.* [11].



D. Influence of CO₂ partial pressure

The influence of CO₂ partial pressure on ethanol dry reforming was performed at temperature of 973 K with varied CO₂ partial pressure from 20 to 50 kPa and kept C₂H₅OH at 20 kPa. The C₂H₅OH and CO₂ conversions of 5%Ce-10%Co/Al₂O₃ catalyst was shown in Fig. 3. Both C₂H₅OH and CO₂ conversions with increasing of P_{CO2} increased to about 43.96%, and 35.13%, respectively. This result was due to the existence of extra CO₂ Partial pressure in feed which improved the secondary reaction i.e. CH₄ dry reforming for converting CH₄ intermediate product to syngas [12]. Jankhah *et al.* have studied that the ethanol dry reforming conversions obtained at high ratio of CO₂ and C₂H₅OH [13]. Furthermore, the properties of high oxygen storage capacity of Ce loading in the catalyst to enhanced the catalytic activity and stability in the reaction [14]. The influence of CO₂ partial pressure on selectivity of H₂, CO and CH₄ exhibited in Fig. 4. The selectivity of H₂ and CO increased linearly with growing CO₂ partial pressure from 18.03-26.64% and 13.93-20.24%, respectively whilst the selectivity of CH₄ was decreased from 25 to 18% with growing CO₂ partial pressure. This result indicated that the CH₄ and CO₂ reacted through the secondary reaction, i.e. dry reforming of CH₄. Additionally, CH₄ and CO can produced a synthetic gas and improve the H₂ and CO selectivity [15].

4. CONCLUSIONS

5%Ce-10%Co/Al₂O₃ catalyst was prepared using a wet impregnation method and examined for ethanol dry reforming reaction in a quartz fixed-bed reactor at P_{CO2} (20-50 kPa), P_{C₂H₅OH} = 20 kPa and 973 K. Both γ -Al₂O₃ support and 5%Ce-10%Co/Al₂O₃ catalyst possessed that high surface area of 175.29 and 137.35 m² g⁻¹, respectively. The formation of Co₃O₄, CeO₂ and CoAl₂O₄ phases on surface of catalyst indicted by XRD measurements. The complete decomposition of metal precursors to metal oxides (CoO and Co₃O₄) observed at temperature beyond 550 K during the TGA analysis. The optimal C₂H₅OH and CO₂ conversions were obtained at P_{CO2} = 50 kPa. Significantly, with rising CO₂ partial pressure from 20-50 kPa, H₂ and CO selectivity was increased whilst CH₄ selectivity decreased at the same condition.

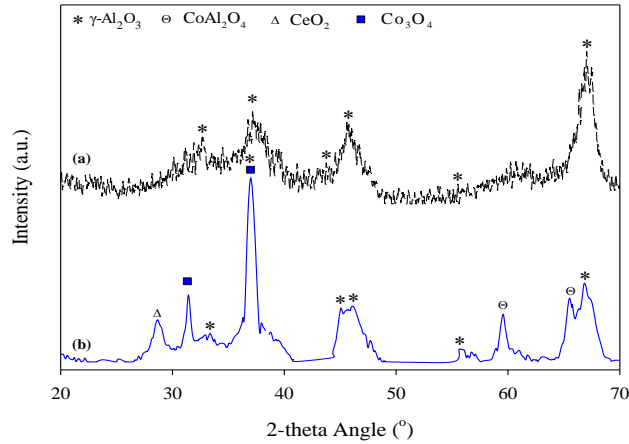


Figure 1: X-ray diffractograms of (a) $\gamma\text{-Al}_2\text{O}_3$ support and (b) 5%Ce-10%Co/ Al_2O_3 catalyst.

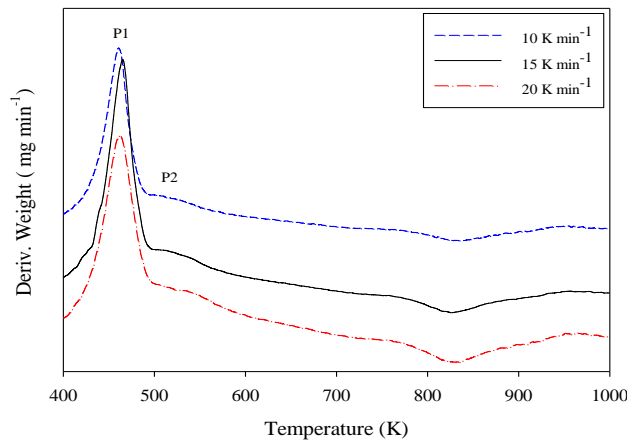


Figure 2: Derivative weight profiles for temperature-programmed calcination runs of 5%Ce-10%Co/ Al_2O_3 catalyst.

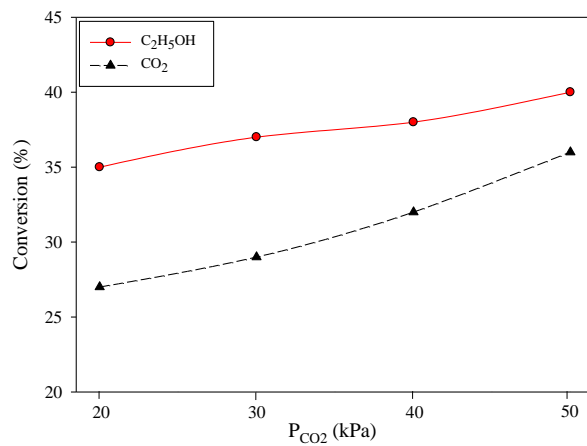


Figure 3: Influence of P_{CO_2} on $\text{C}_2\text{H}_5\text{OH}$ and CO_2 conversions of 5%Ce-10%Co/ Al_2O_3 catalyst at $P_{\text{C}_2\text{H}_5\text{OH}} = 20$ kPa and 973 K.

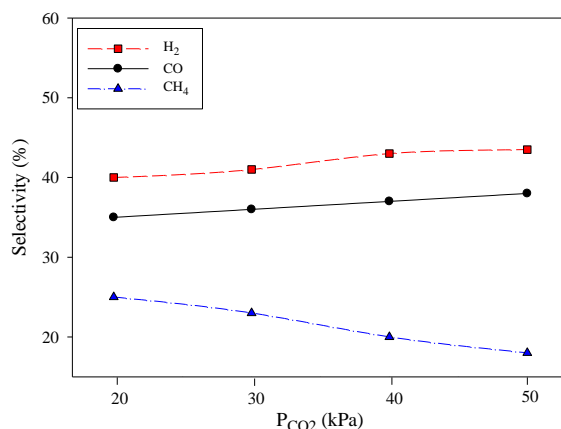


Figure 4: Influence of P_{CO_2} on selectivity of H₂, CO and CH₄ at $P_{C_2H_5OH} = 20$ kPa and 973 K.

ACKNOWLEDGMENT

The authors would like to appreciate for the financial support from UMP Research Grant Scheme (RDU130376) to conduct this study. Fahim Fayaz is also thankful for the Graduate Research Scheme Award (GRS) from Universiti Malaysia Pahang (UMP).

REFERENCES

- [1] D. Das, and T. N. Veziroglu, "Hydrogen production by biological processes: a survey of literature," *Int. J. Hydrogen Energy*, vol. 26, pp. 13–28, 2001.
- [2] M. Ball and M. Wietschel, "The future of hydrogen - opportunities and challenges," *Int. J. Hydrogen Energy*, vol. 34, pp. 615–627, December 2009.
- [3] F. Joensen and J. R. Rostrup-Nielsen, "Conversion of hydrocarbons and alcohols for fuel cells," *J. Power Sources*, vol. 105, pp. 195–201, 2002.
- [4] K. Selvarajah, N. H. H. Phuc, B. Abdullah, F. Alenazey, and D.-V. N. Vo, "Syngas production from methane dry reforming," *Res. Chem. Intermed.*, vol. 42, pp. 269–288, January 2016.
- [5] M. C. J. Bradford and M. a. Vannice, "CO₂ Reforming of CH₄," *Catal. Rev.*, vol. 41, pp. 1–42, February 2007.
- [6] F. Barbir, "Transition to renewable energy systems with hydrogen as an energy carrier," vol. 34, pp. 308–312, August 2009.
- [7] A. N. Fatsikostas, D. I. Kondarides, and X. E. Verykios, "Production of hydrogen for fuel cells by reformation of biomass-derived ethanol," *Catal. Today*, vol. 75, pp. 145–155, 2002.
- [8] M. Ni, D. Y. C. Leung, M. K. H. Leung, and K. Sumathy, "An overview of hydrogen production from biomass," *Fuel Process. Technol.*, vol. 87, pp. 461–472, November 2006.
- [9] W. Wang and Y. Wang, "Dry reforming of ethanol for hydrogen production: Thermodynamic investigation," *Int. J. Hydrogen Energy*, vol. 34, 13, pp. 5382–5389, May 2009.
- [10] M. S. Batista, R. K. S. Santos, E. M. Assaf, J. M. Assaf, and E. a. Ticianelli, "High efficiency steam reforming of ethanol by cobalt-based catalysts," *J. Power Sources*, vol. 134, pp. 27–32, June 2004.
- [11] M. B. Bahari, N. H. H. Phuc, B. Abdullah and D.-V. N. V. Vo, "Ethanol dry reforming for syngas production over Ce-promoted Ni/Al₂O₃ catalyst," *J. Environ. Chem. Eng.* In press
- [12] X. Hu and G. Lu, "Syngas production by CO₂ reforming of ethanol over Ni/Al₂O₃ catalyst," *Catal. Commun.* vol. 10, pp. 1633–1637, May 2009.
- [13] S. Jankhah, N. Abatzoglou, and F. Gitzhofer, "Thermal and catalytic dry reforming and cracking of ethanol for hydrogen and carbon nanofilaments' production," *Int. J. Hydrogen Energy*, vol. 33, pp. 4769–4779, August 2008.
- [14] W. Hong, Z. Lijuan, LI. Miao, L. Yuan, and B. Xue, "Co/CeO₂ for ethanol steam reforming: Effect of ceria morphology," *J. Rare Earths*, vol. 31, pp. 565–571, June 2013.
- [15] M. B. Bahari, F.-L. W. Ming, F. Fayaz, N. Ainirazali, N. H. H. Phuc, and D.-V. N. Vo, "Evaluation of Co-promoted Ni/Al₂O₃ Catalyst for CO₂ Reforming of Ethanol," *J. Eng. Appl. Sci.*, vol. 11, pp. 7249-7253, June 2016.