



Interfacial materials with special wettability

The Harvard community has made this
article openly available. [Please share](#) how
this access benefits you. Your story matters

Citation	Wong, Tak-Sing, Taolei Sun, Lin Feng, and Joanna Aizenberg. 2013. "Interfacial Materials with Special Wettability." MRS Bulletin 38 (05) (May): 366–371. doi:10.1557/mrs.2013.99.
Published Version	doi:10.1557/mrs.2013.99
Citable link	http://nrs.harvard.edu/urn-3:HUL.InstRepos:37255457
Terms of Use	This article was downloaded from Harvard University's DASH repository, and is made available under the terms and conditions applicable to Open Access Policy Articles, as set forth at http://nrs.harvard.edu/urn-3:HUL.InstRepos:dash.current.terms-of-use#OAP

Interfacial Materials with Special Wettability

Tak-Sing Wong, Taolei Sun, Lin Feng, and Joanna Aizenberg

Abstract

Various life forms in nature display a high level of adaptability to their environments through the use of sophisticated material interfaces. This is exemplified by numerous natural examples, such as the self-cleaning of lotus leaves, the water-walking abilities of water striders and spiders, the ultra-slipperiness of pitcher plants, the directional liquid adhesion of butterfly wings, and the water collection capabilities of beetles, spider webs and cacti. The versatile interactions of these natural surfaces with fluids, or special wettability, are enabled by their unique micro/nanoscale surface structures and intrinsic material properties. Many of these biological designs and principles have inspired new classes of functional interfacial materials, which have remarkable potential to solve some of the engineering challenges for industrial and biomedical applications. In this article, we provide a snapshot of the recent state-of-the-art development of biologically inspired materials with extreme fluid repellency and their potential applications in high/low temperature environments, as well as discuss some promising future directions in the field.

Keywords: Biomimetics, Bioinspiration, Special Wettability, Superhydrophobicity, Superoleophobicity, Superomniphobicity

Introduction

Wetting – the interaction of fluids with solid surfaces – impacts many areas of science and technology in the modern era.(1-3) In particular, creating a robust synthetic surface that I) repels various liquids, II) allows for directional/switchable fluid manipulation, and/or III) operates under various environmental conditions would have broad technological implications for areas related to water, energy, and health but has proved extremely challenging.(4) In nature, many biological surfaces are

engineered to have special interfacial interactions with fluids – or special wettability – in order to survive in their innate environments.(5-23) For example, lotus leaves rely on hierarchical micro/nanoscale textures to trap a thin layer of air (Figure 1a), which then acts as a cushion against liquids and helps to keep the surface clean by carrying away dirt – the lotus effect (6); springtails, arthropods that live in the soil, have evolved overhanging nanostructured skin patterns (Figure 1b) that help prevent them from soiling (20); *Nepenthes* pitcher plants capture insects with their highly slippery, liquid infused micro-textured peristome (Figure 1c) without the use of any active prey-capturing mechanisms.(10, 24) Central to many of these functional biological surfaces is the presence of unique micro- and nanostructured architectures that allow them to exhibit special wettability. To this end, mimicking these biological surfaces - biomimetics - and learning from these biological concepts - bioinspiration - have led to important advances in the manufacturing and design of synthetic interfacial materials in recent years.

Biomimetic and Bioinspired Materials

Maturation of high resolution microscopy techniques, together with rapid advancement in micro- and nanomanufacturing, have enabled scientists and engineers to not only uncover the secrets of functional natural interfacial materials, but also to manufacture these functional surfaces using a broad spectrum of synthetic materials. With these collective advances, the field of biomimetics and bioinspiration, particularly the development of interfacial materials, has progressed tremendously during the last decade.(25-27) *In the first article of this issue, Jiang and Wang et al. provide a comprehensive overview of the recent development of bioinspired materials with special wettability, ranging from the superior water-walking ability of water striders, the directional adhesion of butterfly wings, the antifogging functionality of mosquito eyes, the water collection of the cactus and spider silk, to the underwater self-cleaning ability of fish scales.*

Among these many biomimetic studies, the lotus effect has been the most widely studied and investigated, and has accounted for >1000 journal papers published in the last decade alone (Figure 2). This reflects the remarkable interest and need to create highly liquid-repellent materials. Since these bioinspired materials utilize structured surfaces to achieve their fluid repellency, it is instructive to look at some of the fundamental theories and terminologies for wetting on structured surfaces.

Wetting on Structured Surfaces

When a liquid droplet is deposited on a smooth solid surface in air, three distinctive interfacial boundaries arise that intersect at a well-defined contact angle, θ (Figure 3a). Competition between the adhesion forces of the liquid, vapor and solid molecules (or atoms) results in a force equilibrium at the triple line (the line where all three phases meet),(28) which can be described by the Young's equation

$$\gamma_{LV} \cos \theta = \gamma_{SV} - \gamma_{SL}, \quad (1)$$

where γ_{LV} , γ_{SV} , and γ_{SL} are the surface tensions for liquid-vapor, solid-vapor, and solid-liquid interfaces, respectively, and θ is the intrinsic contact angle at the triple line with the solid surface. By convention, if $\theta \geq 90^\circ$, then the solid is said to “hate” the fluid droplet (hydrophobic for the case of water). Likewise, if $\theta < 90^\circ$, then the solid is said to “like” the fluid droplet (hydrophilic for the case of water).

However, real surfaces are rarely smooth. The contact angles of liquid droplets observed (or apparent contact angles, θ^*) on these real surfaces typically deviate significantly from those described by the Young's equation. Wetting of liquid droplets on structured surfaces can be roughly described by two distinct modes. In the first wetting mode, the liquid closely follows the topography of the surface forming a continuous liquid-solid interface (Figure 3b). The apparent contact angle can be described by the Wenzel equation developed in 1936

$$\cos \theta^* = R \cos \theta, \quad (2)$$

where R is the roughness factor, defined as the ratio between the actual surface area and the projected surface area of the solid.(29) The Wenzel equation indicates that roughness can amplify the wettability of a solid. For example, if the solid is intrinsically hydrophobic, roughness will further enhance the surface hydrophobicity (i.e., $\theta^* > \theta$ for $R > 1$).

In the second mode of wetting, the liquid does not follow the topography of the solid surface; instead the liquid is suspended on a mixed interface composed of surface protrusions with air pockets trapped between them (Figure 3c). The apparent contact angle in this mode was first described by the Cassie-Baxter equation in 1944,(30) and was further extended by Cassie to heterogeneous surfaces in 1948,(31)

$$\cos \theta^* = A_1 \cos \theta_1 + A_2 \cos \theta_2, \quad (3)$$

where A_1 and A_2 are area fractions (i.e., $A_1 + A_2 = 1$), and θ_1 and θ_2 are the intrinsic contact angles of materials 1 and 2, respectively. The Cassie equation indicates that to achieve a perfect non-wetting situation (i.e., $\theta^* \sim 180^\circ$), one can maximize the area fraction of the air pockets trapped beneath the liquid droplet. The concept put forth by Cassie and Baxter explained the large contact angles observed in many of the plant and animal surfaces, such as lotus leaves.(32) In addition to the surface energy model proposed by Cassie and Baxter, recent experimental and theoretical studies have highlighted the importance of the topography length scale of the surface roughness (i.e., line energy) to the role of surface wettability.(33-37)

Achieving a high apparent contact angle can reduce the normal adhesion of a liquid droplet with the solid surface due to reduction of the liquid-solid contact area. However, contact angle alone does not quantify the resistance to liquid motion in the direction tangential to the surface.(33, 38-40) In particular, liquids sitting on rough surfaces exhibit a variety of contact angles bounded by two extreme values. The upper limit is known as the advancing contact angle, θ_A , whereas the lower limit is referred to as the receding contact angle, θ_R . The difference between these values is known as contact angle hysteresis, $\Delta\theta$, whose physical origin is attributed to pinning of the liquid contact line (CL) on the nanoscopic surface roughness.(41-44) The presence of

the contact angle hysteresis gives rise to a surface retention force, F_R , that resists the motion of a liquid droplet of a characteristic length, L , i.e., (39)

$$F_R = \gamma_{LV}L(\cos \theta_R - \cos \theta_A). \quad (4)$$

Therefore, minimizing the hysteresis is the key to minimizing resistance to motion, resulting in high mobility of the droplets and therefore in significantly improved liquid-repellency of the surface.

By convention, we describe a material as superhydrophobic if it displays an apparent contact angle for water of $\geq 150^\circ$ with contact angle hysteresis $< \sim 5^\circ - 10^\circ$. If the material displays similar values with oils, we describe the surface as superoleophobic. If the material meets these criteria for both water and oils, we term the material as superomniphobic or superamphiphobic (Table 1).

Extreme Fluid Repellency

Lotus leaves have exceptional ability to repel water but not oils; therefore these natural materials are only superhydrophobic. After more than a decade of research and development, we now have many different ways to create synthetic superhydrophobic surfaces,(45-48) but creating materials that are both superhydrophobic and superoleophobic (i.e. superomniphobic) based on the lotus-leaf model has proved more difficult. A fundamental reason is that oils have intrinsically low surface tension, which makes them prone to wet the micro/nanoscale surface textures more readily than liquids of higher surface tension, thereby displacing the air pockets trapped in between the surface textures and leading to significant liquid pinning.

Despite the challenges, recent efforts have shown that by carefully engineering the surface textures with overhanging features, it is possible to create superomniphobic materials that can repel both water and oils.(49-52) The novelty behind these surfaces is the creation of a local re-entrant curvature such that droplet pinning at the edges of the micro/nanoscale overhanging structures prevents further penetration. This development has further advanced the capabilities of lotus-leaf inspired surfaces to repel not only water, but also a much broader range of fluids.(53)

In the second article of this issue, Tuteja and Choi et al. discuss the recent advances of superomniphobic surfaces and their durability issues. It is interesting to note that springtails also possess similar overhanging nanoscale textured patterns to protect themselves from soiling (Figure 1b).(20) These natural surfaces were shown to resist wetting of many organic liquids and at elevated pressures, and demonstrate a number of similarities to their artificial counterparts.(49-51, 53)

Anisotropic Fluid Repellency

In addition to lotus leaves, which display a high level of omni-directional water repellency, a number of biological surfaces are able to shed water only in a specific direction – known as anisotropic wetting. For example, the wings of butterflies can shed water droplets easily along the radial outward direction away from their wings, but not in the opposite direction.(16) The legs of water striders are covered with tiny oriented hairs with fine nanogrooves that allow them to propel the strider efficiently on water surface.(11, 54) Another example can be found on rice leaves that consist of one-dimensional arrays of oriented micro/nanotextures that enable the transport of water droplets in a particular direction.(9) Central to these biological surfaces are the orientations and arrangements of the surface textures that provide precise control over the direction of droplet motion. Inspirations from these natural anisotropic surfaces have led to artificial surfaces that display similar anisotropic wetting behaviors.(55-57) *In the third article of this issue, Hancock and Demirel summarize recent experimental and theoretical progress in the design, synthesis, and characterization of engineered surfaces that demonstrate anisotropic wetting properties, as well as some of their potential applications.*

Towards Industrial Applications in Extreme Environments

In addition to the fundamental research on these synthetic bioinspired materials, important advances have been made in understanding how these materials could be utilized in various industrial applications under different environmental conditions, particularly in industrial processes that involve phase changes such as

condensation (58-62) and icing (63-70). On one hand, vapor condensation is commonly encountered in power generation, thermal management, and desalination plants; on the other hand, ice formation and accretion present serious economic and safety issues for essential infrastructures such as aircraft, power lines, wind turbines, and commercial and residential refrigerators and freezers. Passive coatings that can effectively remove condensed vapor and/or reduce ice adhesion are thus critically needed. *In the fourth article of the issue, recent developments in the use of superhydrophobic surfaces for condensation control are discussed by Miljkovic and Wang from an academic research perspective. In the last article of the issue, Alizadeh et al. discuss how some of these bioinspired materials can contribute to the effective removal of condensed vapor and ice from an industrial viewpoint.*

Outlook

One of the ultimate goals in the field of bioinspired interfacial materials is to create a robust, scalable, and low-cost surface that can repel any fluids, self-heal upon damage, allow for smart/switchable control of wettability, and operate under a wide range of environmental conditions, such as extreme temperatures, high pressures, and harsh chemicals. As discussed here, cutting-edge development of synthetic liquid-repellent surfaces has primarily been modeled after the lotus-effect, with many important advances made over the last decade (Figure 4). Some of these lotus leaf-inspired surfaces have been designed to repel both aqueous and organic liquids,(49-53), others can be manufactured from low-cost (such as plastics)(71) or mechanically robust (such as ceramic) materials,(72), yet another set of studies demonstrated switchable wettability,(12, 73-76) partially self-healing capability,(77-79) or the ability to operate under moderate pressure (up to ~ 7 atm).(80) However, these impressive properties, where present, have been demonstrated separately on different materials, rather than integrated into a single material. Thus many of these surfaces face severe limitations to their practical applications: they show limited oleophobicity

with high contact angle hysteresis; fail under high pressure (81) and upon any physical damage; and/or cannot completely self-heal.

Very recently, a conceptually different approach to creating liquid-repellent materials – inspired by the slippery *Nepenthes* pitcher plants – was developed that may potentially address many of the challenges found in the lotus leaf-inspired surfaces (Table 2). The new bioinspired material consists of a continuous film of lubricating liquid locked in place by a micro/nanostructured substrate (Figure 3d), and is termed as Slippery Liquid-Infused Porous Surfaces (**SLIPS**),(82) or slippery pre-suffused surfaces (83) or lubricant-impregnated surfaces (84, 85). The liquid-infused structured surface outperforms its natural counterparts and state-of-the-art synthetic surfaces in its ability to repel various simple and complex liquids (water, crude oil, and blood); maintain low contact angle hysteresis ($<2.5^\circ$); restore liquid-repellency after physical damage rapidly (within 0.1-1 s); function at high pressures (up to ~ 676 atm); resist bacterial bio-fouling (86) and ice adhesion (87, 88); enhance condensation (84); and switch wettability in response to mechanical stimuli (89) (see Table 2). Since these properties can all be incorporated into a single material, the slippery surfaces can potentially be used in a wide variety of applications and environments (90), and may provide alternative solutions for designing materials with special wettability that could not be addressed by conventional lotus leaf-inspired surfaces.

Ultimately, the widespread application of any of the aforementioned bioinspired interfacial materials is dictated by their cost, scalability, and robustness, which are important for their practical use on a large scale and accessibility to people with low budgets and around the world. While promising results have been demonstrated for many of these bioinspired materials, continuing research is necessary to bring down the material and fabrication costs, as well as to enhance their longevity and robustness without compromising their functional performances.

Acknowledgments

The authors would like to thank Walter Federle and Holger Bohn for providing the image of the pitcher plant. We thank Alison Grinthal for the help with manuscript preparation. JA and TSW would also like to acknowledge the funding support by the Office of Naval Research MURI grant under award No. N00014-12-1-0875.

Figures & Figure Captions

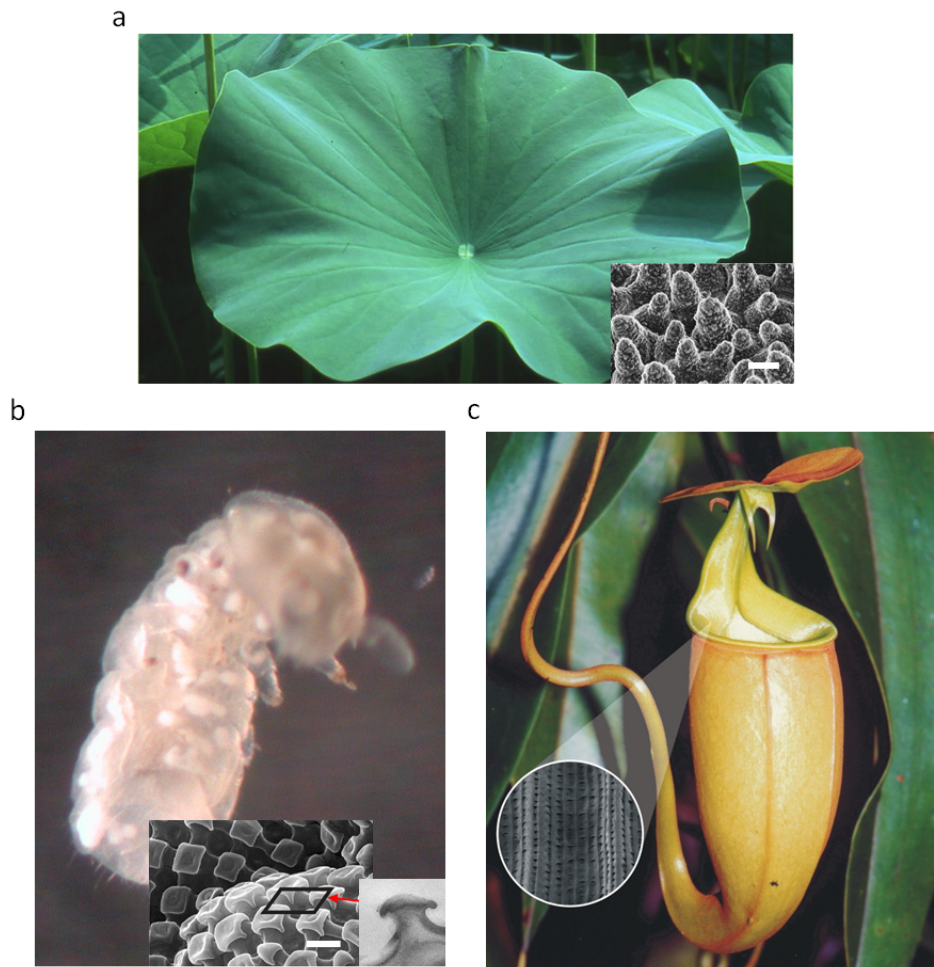


Figure 1. The most repellent biological surfaces in nature. (a) A lotus leaf, known for its exceptional water repellency enabled by hierarchical micro/nano-structures (see inset). Scale bar = 10 μm ; (b) A springtail, which can resist wetting by organic liquids and at elevated pressures as enabled by overhanging nanostructures (see inset). Scale bar = 500 nm; (c) A pitcher plant, which utilizes a highly slippery, liquid-infused micro-structured peristome to capture prey. Inset shows the microstructures on the peristome. All images are reproduced with permission from the Creative Commons Licenses of (20), (91) Pitcher plant image provided courtesy of W. Federle and H. Bohn.

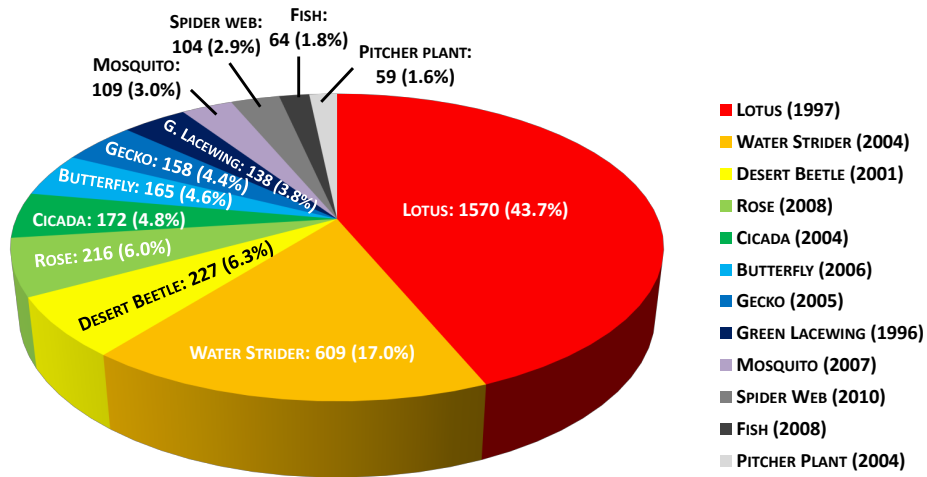


Figure 2. Citations of key papers in biomimicry studies related to interfacial materials with special wettability from the years 2002 to 2012. Citation data obtained from ISI Web of Knowledge provided by Thomson Reuters.

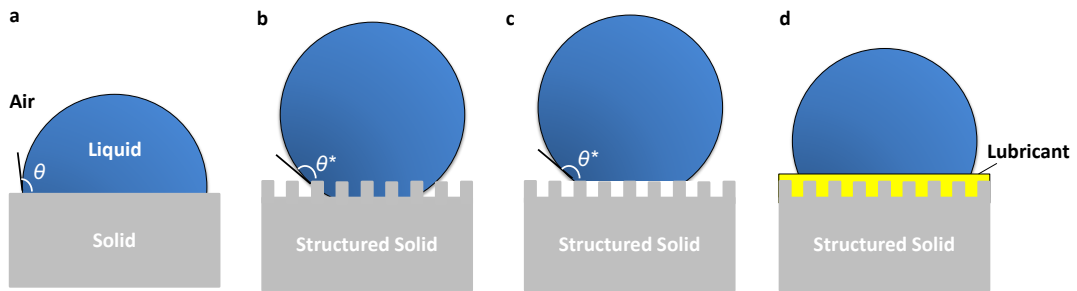


Figure 3. Wetting on smooth and structured surfaces. A liquid droplet sitting on (a) a smooth surface with an intrinsic contact angle, θ ; (b) a textured surface that is completely wetted by the liquid, known as a Wenzel state droplet; (c) a textured surface with trapped air pockets, known as a Cassie state droplet; (d) a textured surface that is infused with an immiscible lubricating fluid (or slippery liquid-infused surfaces).

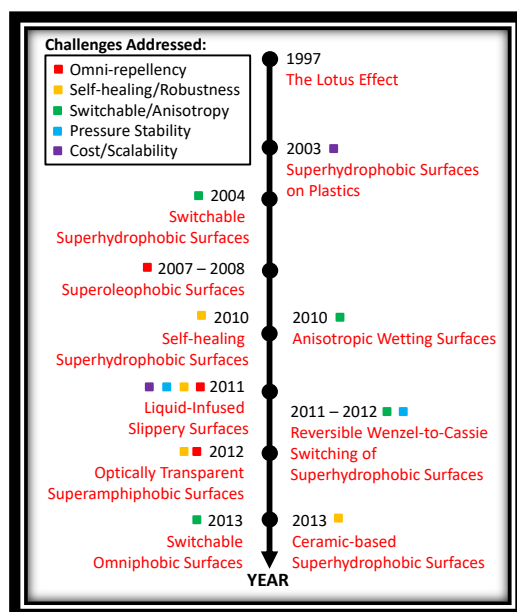


Figure 4. Timeline of key materials innovations and developments in bioinspired liquid repellent surfaces in the past decade (2003 – 2013). (6, 49-52, 55, 56, 71-73, 80, 82, 83, 89, 92) Note that this timeline only covers the materials development, and does not include the key fundamental theoretical/computational/experimental discoveries during the period. Readers are referred to the recent reviews on these topics by Quéré (4), Marmur (93), Nosonovsky and Bhushan (94), and Bormashenko (95).

Table 1. Classification of liquid repellent states

State	Superhydrophobic	Superoleophobic	Omniphobic	Superomniphobic/ Superamphiphobic
Liquids	Water	Oils	Water & Oils	Water & Oils
θ^* (°)	$\geq 150^\circ$	$\geq 150^\circ$	$< 150^\circ$	$\geq 150^\circ$
$\Delta\theta^*$ (°)	$\leq 5 - 10^\circ$	$\leq 5 - 10^\circ$	$\leq 5 - 10^\circ$	$\leq 5 - 10^\circ$

Table 2. A comparison matrix between the performance of SLIPS and the best available parameters of the lotus leaf-inspired superhydrophobic surfaces published in the literature

Technology	Contact Angle Hysteresis (°)	Dynamic Pressure (atm)	Static Pressure (atm)	Self-Healing (sec)	Ice adhesion (kPa)
SLIPS	$< 2.5^{(82)}$ (water & oils)	$> 0.05^{(82)}$ (water & oils)	$676^{(82)}$ (water & oils)	$\sim 0.15^{(82)}$	$\sim 15^{(87)}$
Lotus-leaf-Inspired Surfaces	$\sim 10^\circ - 30^\circ$ (oils) ⁽⁵¹⁾ $< 5^\circ$ (water) ⁽⁵¹⁾	~ 0.01 (oils) ⁽⁵²⁾ > 0.05 (water) ⁽⁹⁶⁾	7 (water) ⁽⁸⁰⁾	$\sim 180^{(78)}$	\sim Order of 100 or above ⁽⁶⁵⁾

References

1. P. G. de Gennes, Wetting - Statics and Dynamics. *Reviews of Modern Physics* **57**, 827 (1985).
2. P.-G. de Gennes, F. Brochard-Wyart, D. Quere, *Capillarity and Wetting Phenomena : Drops, Bubbles, Pearls, Waves* (Springer, New York, 2004).
3. Y. Pomeau, E. Villermaux, Two hundred years of capillarity research. *Physics Today* **59**, 39 (Mar, 2006).
4. D. Quere, Wetting and roughness. *Annual Review of Materials Research* **38**, 71 (2008).
5. T. Wagner, C. Neinhuis, W. Barthlott, Wettability and contaminability of insect wings as a function of their surface sculptures. *Acta Zoologica* **77**, 213 (Jul, 1996).
6. W. Barthlott, C. Neinhuis, Purity of the sacred lotus, or escape from contamination in biological surfaces. *Planta* **202**, 1 (May, 1997).
7. C. Neinhuis, W. Barthlott, Characterization and distribution of water-repellent, self-cleaning plant surfaces. *Annals of Botany* **79**, 667 (1997).
8. A. R. Parker, C. R. Lawrence, Water capture by a desert beetle. *Nature* **414**, 33 (Nov 01, 2001).
9. L. Feng *et al.*, Super-hydrophobic surfaces: From natural to artificial. *Adv Mater* **14**, 1857 (Dec 17, 2002).
10. H. F. Bohn, W. Federle, Insect aquaplaning: Nepenthes pitcher plants capture prey with the peristome, a fully wettable water-lubricated anisotropic surface. *P Natl Acad Sci USA* **101**, 14138 (Sep 28, 2004).
11. X. F. Gao, L. Jiang, Water-repellent legs of water striders. *Nature* **432**, 36 (Nov 4, 2004).
12. T. L. Sun, L. Feng, X. F. Gao, L. Jiang, Bioinspired surfaces with special wettability. *Accounts of Chemical Research* **38**, 644 (Aug, 2005).
13. W. R. Hansen, K. Autumn, Evidence for self-cleaning in gecko setae. *P Natl Acad Sci USA* **102**, 385 (Jan 11, 2005).
14. D. L. Hu, J. W. M. Bush, Meniscus-climbing insects. *Nature* **437**, 733 (Sep 29, 2005).
15. X. F. Gao *et al.*, The dry-style antifogging properties of mosquito compound eyes and artificial analogues prepared by soft lithography. *Adv Mater* **19**, 2213 (Sep 3, 2007).
16. Y. Zheng, X. Gao, L. Jiang, Directional adhesion of superhydrophobic butterfly wings. *Soft Matter* **3**, 178 (2007).
17. L. Feng *et al.*, Petal effect: A superhydrophobic state with high adhesive force. *Langmuir* **24**, 4114 (Apr 15, 2008).
18. M. J. Liu, S. T. Wang, Z. X. Wei, Y. L. Song, L. Jiang, Bioinspired Design of a Superoleophobic and Low Adhesive Water/Solid Interface. *Adv Mater* **21**, 665 (Feb 9, 2009).
19. Y. M. Zheng *et al.*, Directional water collection on wetted spider silk. *Nature* **463**, 640 (Feb 4, 2010).

20. R. Helbig, J. Nickerl, C. Neinhuis, C. Werner, Smart Skin Patterns Protect Springtails. *Plos One* **6**, (Sep 30, 2011).
21. N. J. Mlot, C. A. Tovey, D. L. Hu, Fire ants self-assemble into waterproof rafts to survive floods. *P Natl Acad Sci USA* **108**, 7669 (May 10, 2011).
22. C. Duprat, S. Protiere, A. Y. Beebe, H. A. Stone, Wetting of flexible fibre arrays. *Nature* **482**, 510 (Feb 23, 2012).
23. J. Ju, Y. Zheng, T. Zhao, R. Fang, L. Jiang, A multi-structural and multi-functional integrated fog collection system in cactus. *Nat Commun* **3**, 1247 (04 December 2012, 2012).
24. Y. Forterre, J. M. Skotheim, J. Dumais, L. Mahadevan, How the Venus flytrap snaps. *Nature* **433**, 421 (Jan 27, 2005).
25. N. F. Lepora, P. Verschure, T. J. Prescott, The state of the art in biomimetics. *Bioinspiration and Biomimetics* **8**, (2013).
26. J. Genzer, A. Marmur, Biological and synthetic self-cleaning surfaces. *MRS Bull* **33**, 742 (Aug, 2008).
27. B. Bhushan, Biomimetics: lessons from nature - an overview. *Philos T R Soc A* **367**, 1445 (Apr 28, 2009).
28. T. Young, An essay on the cohesion of fluids. *Philosophical Transactions of the Royal Society of London* **95**, 65 (1805).
29. R. N. Wenzel, Resistance of solid surfaces to wetting by water. *Industrial and Engineering Chemistry* **28**, 988 (1936).
30. A. B. D. Cassie, S. Baxter, Wettability of porous surfaces. *Transactions of the Faraday Society* **40**, 0546 (1944).
31. A. B. D. Cassie, Contact Angles. *Discussions of the Faraday Society* **3**, 11 (1948).
32. A. B. D. Cassie, S. Baxter, Large contact angles of plant and animal surfaces. *Nature* **155**, 21 (1945).
33. D. Oner, T. J. McCarthy, Ultrahydrophobic surfaces. Effects of topography length scales on wettability. *Langmuir* **16**, 7777 (Oct 3, 2000).
34. C. W. Extrand, Criteria for ultralyophobic surfaces. *Langmuir* **20**, 5013 (Jun 8, 2004).
35. C. Dorrer, J. Ruhe, Advancing and receding motion of droplets on ultrahydrophobic post surfaces. *Langmuir* **22**, 7652 (Aug 29, 2006).
36. T. S. Wong, C. M. Ho, Dependence of Macroscopic Wetting on Nanoscopic Surface Textures. *Langmuir* **25**, 12851 (Nov 17, 2009).
37. E. Bormashenko, General equation describing wetting of rough surfaces. *J Colloid Interf Sci* **360**, 317 (Aug 1, 2011).
38. R. H. Dettre, R. E. Johnson, Contact angle hysteresis .4. Contact angle measurements on heterogeneous surfaces. *Journal of Physical Chemistry* **69**, 1507 (1965).
39. C. G. Fumidge, Studies at phase Interfaces .1. Sliding of liquid drops on solid surfaces and a theory for spray retention. *Journal of Colloid Science* **17**, 309 (1962).

40. W. Chen *et al.*, Ultrahydrophobic and ultralyophobic surfaces: Some comments and examples. *Langmuir* **15**, 3395 (May 11, 1999).
41. J. W. Gibbs, *The scientific papers of J. Willard Gibbs*. (Dover Publications, New York, ed. New Dover ed., 1961).
42. J. F. Oliver, C. Huh, S. G. Mason, Resistance to spreading of liquids by sharp edges. *J Colloid Interf Sci* **59**, 568 (1977).
43. T. Ondarcuhu, A. Piednoir, Pinning of a contact line on nanometric steps during the dewetting of a terraced substrate. *Nano Lett* **5**, 1744 (Sep, 2005).
44. T. S. Wong, A. P. H. Huang, C. M. Ho, Wetting Behaviors of Individual Nanostructures. *Langmuir* **25**, 6599 (Jun 16, 2009).
45. D. Quere, Non-sticking drops. *Reports on Progress in Physics* **68**, 2495 (Nov, 2005).
46. X. M. Li, D. Reinhoudt, M. Crego-Calama, What do we need for a superhydrophobic surface? A review on the recent progress in the preparation of superhydrophobic surfaces. *Chem Soc Rev* **36**, 1529 (2007).
47. P. Roach, N. J. Shirtcliffe, M. I. Newton, Progress in superhydrophobic surface development. *Soft Matter* **4**, 224 (2008).
48. C. Dorrer, J. Ruhe, Some thoughts on superhydrophobic wetting. *Soft Matter* **5**, 51 (2009).
49. A. Tuteja *et al.*, Designing superoleophobic surfaces. *Science* **318**, 1618 (Dec 7, 2007).
50. A. Ahuja *et al.*, Nanonails: A simple geometrical approach to electrically tunable superlyophobic surfaces. *Langmuir* **24**, 9 (Jan 1, 2008).
51. A. Tuteja, W. Choi, J. M. Mabry, G. H. McKinley, R. E. Cohen, Robust omniphobic surfaces. *P Natl Acad Sci USA* **105**, 18200 (Nov 25, 2008).
52. X. Deng, L. Mammen, H. J. Butt, D. Vollmer, Candle Soot as a Template for a Transparent Robust Superamphiphobic Coating. *Science* **335**, 67 (Jan 6, 2012).
53. S. Pan, A. K. Kota, J. M. Mabry, A. Tuteja, Superomniphobic Surfaces for Effective Chemical Shielding. *J Am Chem Soc* **135**, 578 (2013).
54. D. L. Hu, B. Chan, J. W. M. Bush, The hydrodynamics of water strider locomotion. *Nature* **424**, 663 (Aug 7, 2003).
55. K. H. Chu, R. Xiao, E. N. Wang, Uni-directional liquid spreading on asymmetric nanostructured surfaces. *Nature Materials* **9**, 413 (May, 2010).
56. N. A. Malvadkar, M. J. Hancock, K. Sekeroglu, W. J. Dressick, M. C. Demirel, An engineered anisotropic nanofilm with unidirectional wetting properties. *Nature Materials* **9**, 1023 (Dec, 2010).
57. M. J. Hancock, K. Sekeroglu, M. C. Demirel, Bioinspired Directional Surfaces for Adhesion, Wetting, and Transport. *Adv Funct Mater* **22**, 2223 (Jun 6, 2012).
58. C. H. Chen *et al.*, Dropwise condensation on superhydrophobic surfaces with two-tier roughness. *Appl Phys Lett* **90**, (Apr 23, 2007).
59. J. B. Boreyko, C. H. Chen, Self-Propelled Dropwise Condensate on Superhydrophobic Surfaces. *Phys Rev Lett* **103**, (Oct 30, 2009).

60. R. Enright, N. Miljkovic, A. Al-Obeidi, C. V. Thompson, E. N. Wang, Condensation on Superhydrophobic Surfaces: The Role of Local Energy Barriers and Structure Length Scale. *Langmuir* **28**, 14424 (Oct 9, 2012).
61. N. Miljkovic, R. Enright, E. N. Wang, Effect of Droplet Morphology on Growth Dynamics and Heat Transfer during Condensation on Superhydrophobic Nanostructured Surfaces. *Acs Nano* **6**, 1776 (Feb, 2012).
62. N. Miljkovic *et al.*, Jumping-Droplet-Enhanced Condensation on Scalable Superhydrophobic Nanostructured Surfaces. *Nano Lett* **13**, 179 (Jan, 2013).
63. L. L. Cao, A. K. Jones, V. K. Sikka, J. Z. Wu, D. Gao, Anti-Icing Superhydrophobic Coatings. *Langmuir* **25**, 12444 (Nov 3, 2009).
64. S. A. Kulinich, M. Farzaneh, Ice adhesion on super-hydrophobic surfaces. *Appl Surf Sci* **255**, 8153 (Jun 30, 2009).
65. A. J. Meuler *et al.*, Relationships between Water Wettability and Ice Adhesion. *Acs Appl Mater Inter* **2**, 3100 (Nov, 2010).
66. L. Mishchenko *et al.*, Design of Ice-free Nanostructured Surfaces Based on Repulsion of Impacting Water Droplets. *Acs Nano* **4**, 7699 (Dec, 2010).
67. K. K. Varanasi, T. Deng, J. D. Smith, M. Hsu, N. Bhate, Frost formation and ice adhesion on superhydrophobic surfaces. *Appl Phys Lett* **97**, (Dec 6, 2010).
68. M. He *et al.*, Super-hydrophobic film retards frost formation. *Soft Matter* **6**, 2396 (2010).
69. S. A. Kulinich, S. Farhadi, K. Nose, X. W. Du, Superhydrophobic Surfaces: Are They Really Ice-Repellent? *Langmuir* **27**, 25 (Jan 4, 2011).
70. V. Bahadur *et al.*, Predictive Model for Ice Formation on Superhydrophobic Surfaces. *Langmuir* **27**, 14143 (Dec 6, 2011).
71. H. Y. Erbil, A. L. Demirel, Y. Avci, O. Mert, Transformation of a simple plastic into a superhydrophobic surface. *Science* **299**, 1377 (Feb 28, 2003).
72. G. Azimi, R. Dhiman, H.-M. Kwon, A. T. Paxson, K. K. Varanasi, Hydrophobicity of rare-earth oxide ceramics. *Nature Materials*, (2013).
73. T. L. Sun *et al.*, Reversible switching between superhydrophilicity and superhydrophobicity. *Angew Chem Int Edit* **43**, 357 (2004).
74. A. Sidorenko, T. Krupenkin, A. Taylor, P. Fratzl, J. Aizenberg, Reversible switching of hydrogel-actuated nanostructures into complex micropatterns. *Science* **315**, 487 (Jan 26, 2007).
75. A. Sidorenko, T. Krupenkin, J. Aizenberg, Controlled switching of the wetting behavior of biomimetic surfaces with hydrogel-supported nanostructures. *J Mater Chem* **18**, 3841 (2008).
76. A. Grigoryev, T. Tokarey, K. G. Kornev, I. Luzinov, S. Minko, Superomniphobic Magnetic Microtextures with Remote Wetting Control. *J Am Chem Soc* **134**, 12916 (Aug 8, 2012).
77. Y. Li, L. Li, J. Q. Sun, Bioinspired Self-Healing Superhydrophobic Coatings. *Angew Chem Int Edit* **49**, 6129 (2010).
78. H. Wang *et al.*, Durable, Self-Healing Superhydrophobic and Superoleophobic Surfaces from Fluorinated-Decyl Polyhedral Oligomeric Silsesquioxane and Hydrolyzed Fluorinated Alkyl Silane. *Angewandte Chemie* **50**, 11433 (2011).

79. X. L. Wang, X. J. Liu, F. Zhou, W. M. Liu, Self-healing superamphiphobicity. *Chem Commun* **47**, 2324 (2011).
80. C. Lee, C. J. Kim, Underwater Restoration and Retention of Gases on Superhydrophobic Surfaces for Drag Reduction. *Phys Rev Lett* **106**, (Jan 7, 2011).
81. R. Poetes, K. Holtzmann, K. Franze, U. Steiner, Metastable Underwater Superhydrophobicity. *Phys Rev Lett* **105**, (Oct 14, 2010).
82. T. S. Wong *et al.*, Bioinspired self-repairing slippery surfaces with pressure-stable omniphobicity. *Nature* **477**, 443 (Sep 22, 2011).
83. A. Lafuma, D. Quere, Slippery pre-suffused surfaces. *Epl-Europhys Lett* **96**, (Dec, 2011).
84. S. Anand, A. T. Paxson, R. Dhiman, J. D. Smith, K. K. Varanasi, Enhanced Condensation on Lubricant-Impregnated Nanotextured Surfaces. *Acs Nano* **6**, 10122 (Nov, 2012).
85. J. D. Smith *et al.*, Droplet mobility on lubricant-impregnated surfaces. *Soft Matter* **9**, 1772 (2013).
86. A. K. Epstein, T. S. Wong, R. A. Belisle, E. M. Boggs, J. Aizenberg, Liquid-infused structured surfaces with exceptional anti-biofouling performance. *P Natl Acad Sci USA* **109**, 13182 (Aug 14, 2012).
87. P. Kim *et al.*, Liquid-Infused Nanostructured Surfaces with Extreme Anti-Ice and Anti-Frost Performance. *Acs Nano* **6**, 6569 (Aug, 2012).
88. H. A. Stone, Ice-Phobic Surfaces That Are Wet. *Acs Nano* **6**, 6536 (Aug, 2012).
89. X. Yao *et al.*, Adaptive fluid-infused porous films with tunable transparency and wettability. *Nature Materials*, in press (2013).
90. M. Nosonovsky, Materials Science Slippery When Wetted. *Nature* **477**, 412 (Sep 22, 2011).
91. H. J. Ensikat, P. Ditsche-Kuru, C. Neinhuis, W. Barthlott, Superhydrophobicity in perfection: the outstanding properties of the lotus leaf. *Beilstein J Nanotech* **2**, 152 (Mar 10, 2011).
92. T. Verho *et al.*, Reversible switching between superhydrophobic states on a hierarchically structured surface. *P Natl Acad Sci USA* **109**, 10210 (Jun 26, 2012).
93. A. Marmur, Solid-Surface Characterization by Wetting. *Annual Review of Materials Research* **39**, 473 (2009).
94. M. Nosonovsky, B. Bhushan, Superhydrophobic surfaces and emerging applications: Non-adhesion, energy, green engineering. *Curr Opin Colloid In* **14**, 270 (Aug, 2009).
95. E. Bormashenko, Wetting transitions on biomimetic surfaces. *Philos T R Soc A* **368**, 4695 (Oct 28, 2010).
96. T. P. N. Nguyen, P. Brunet, Y. Coffinier, R. Boukherroub, Quantitative testing of robustness on superomniphobic surfaces by drop impact. *Langmuir* **26**, 18369 (2010).

Author biographies

Joanna Aizenberg

School of Engineering and Applied Sciences, Harvard University, Cambridge, MA, USA; tel. 617-495-3558; and email jaiz@seas.harvard.edu



Aizenberg is the Amy Smith Beryson Professor of Materials Science and the Director of the Kavli Institute for Bionano Science and Technology at Harvard University. She pursues a broad range of research interests that include biomimetics, self-assembly, smart materials, crystal engineering, surface science, and biooptics. She received the B.S. degree in Chemistry from Moscow State University, and the Ph.D. degree in Structural Biology from the Weizmann Institute of Science. Prior to her appointment at Harvard, Aizenberg spent a decade at Bell Laboratories. Her selected awards include: R&D 100 Award for best innovation in 2012; Fred Kavli Distinguished Lectureship in Nanoscience, MRS 2009; Ronald Breslow Award for the Achievement in Biomimetic Chemistry, ACS 2008; Industrial Innovation Award, ACS 2007; Arthur K. Doolittle Award, ACS 1999. Aizenberg is an AAAS and APS Fellow; she has served on the Board of Directors of the Materials Research Society and on the Board on Physics and Astronomy of the National Academies.

Lin Feng

Department of Chemistry, Tsinghua University, Beijing, P.R. China; email fl@mail.tsinghua.edu.cn



Feng is an Assistant Professor of Chemistry, Tsinghua University. She received her Ph. D. degree in Institute of Chemistry, Chinese Academy of Sciences in 2003. She was engaged her post-doc research work at Institute of Physics, Chinese Academy of Sciences (2005) and worked as a visiting scholar in University of California, Berkeley (2009). Her research interests are focused on Biomimic functional nano-scale interfacial materials, nano-scale interfacial materials for oil/water separation and the research of nanocatalyst.

Taolei Sun

State Key Laboratory of Advanced Technology for Materials Synthesis and Processing, Wuhan University of Technology, Wuhan 430070, P.R. China; email suntl@whut.edu.cn



Sun joined Wuhan University of Technology in 2009. He is currently “Changjiang Scholar” Distinguished Professor and Chair Professor at the State Key Laboratory. After earning his PhD degree at the Chinese Academy of Science in 2002 and two years of postdoctoral research, he worked in Muenster University as the Humboldt Fellow. One year later (2006), he was awarded the Sofja Kovalevskaja Award by Alexander von Humboldt Foundation in recognition of his scientific contribution on functional biointerface materials, supporting him to build the “Bio- & Nano-interface” research group working as the group leader until 2011.

Tak-Sing Wong

Department of Mechanical and Nuclear Engineering, The Pennsylvania State University, University Park, PA, USA; tel. 814-865-6122; and email ts Wong@psu.edu



Wong is an Assistant Professor of Mechanical Engineering at The Pennsylvania State University. He received his PhD degree from the University of California, Los Angeles (2009) and his B.Eng. degree from The Chinese University of Hong Kong (2003), both in mechanical engineering. He was a Croucher Postdoctoral Fellow at the Wyss Institute for Biologically Inspired Engineering at Harvard University (2010 – 2012). His research group is interested in utilizing biologically inspired strategies to design functional interfacial materials for various energy, biomedical, and industrial-related applications. Wong is a recipient of the 2012 R&D 100 award for the invention of Slippery Liquid-Infused Porous Surfaces (SLIPS).