

1 Merging flexibility with superinsulation: machinable, 2 nanofibrous pullulan-silica aerogel composites

3
4 Shanyu Zhao ^{1*}, Olivier Emery ¹, Anja Wohlhauser ², Matthias M. Koebel ¹, Christian Adlhart
5 ², Wim J. Malfait ^{1*}

6 ¹ *Laboratory for Building Energy Materials and Components, Empa, Überlandstrasse 129,*
7 *8600 Dübendorf, Switzerland*

8 ² *Institute of Chemistry and Biotechnology, Zurich University of Applied Sciences ZHAW,*
9 *Einsiedlerstrasse 31, CH-8820 Wädenswil, Switzerland*

10

11 * Corresponding authors: shanyu.zhao@empa.ch, wim.malfait@empa.ch

12

13 **Abstract:** Freeze-dried nanofibrous scaffolds are flexible, but typically have high thermal
14 conductivities. Conversely, silica aerogel has an ultra-low thermal conductivity, but is brittle.
15 Here, the impregnation of pullulan/PVA nanofiber scaffolds with hydrophobic silica aerogel
16 decreased the thermal conductivity from 31.4 to 17.7 mW/(m·K). The compatibility between
17 the silylated nanofibers and the silica aerogel promotes the overgrowth of silica particles onto
18 the fiber surfaces and the fiber incorporation. The composites display improved compressive
19 and tensile properties compared to the neat pullulan scaffold and silica aerogel. The
20 composite's E-modulus is 234 kPa compared to 4 kPa for the pullulan scaffold and 102 kPa
21 for the silica aerogel. The composite's tensile strength is five times higher than that of the
22 silica aerogel. Because of its reduced brittleness, the pullulan-silica aerogel composites can be
23 shaped using a sharp blade. The composites can sustain uniaxial compression up to 80%

24 strain, but the decompressed composites display two times higher densities because the strain
25 is partially irreversible. This densification reduces thermal conductivity to 16.3 mW/(m·K)
26 and increases final compressive strength by a factor of seven. Both the as prepared and
27 densified composites demonstrate unique material properties in terms of thermal conductivity,
28 mechanical strength and machinability.

29

30 **Keywords:** nanocomposite; polysaccharide; nanofibers; hybrid aerogels; densification

31

1. Introduction

Biopolymer aerogels were among the first aerogels ever synthesized [1] and have seen a strong revival in the last decade, motivated by the potential for new technical applications of aerogels, the search for more sustainable aerogel precursors, and a strong motivation from the academic community to add value to biopolymer materials [2]. Among biopolymers, polysaccharides have received particular attention, because they are available in large quantities from agricultural production, often as a by-product (pectin) or waste material (cellulose, chitin), and their use as a feedstock for advanced materials could be a great value proposition. Many biopolymer aerogel studies target applications in thermal insulation [3-7], the most prominent industrial application of silica aerogel, but the vast majority of materials produced do not reach the ultra-low thermal conductivities associated with silica aerogels [2, 8], despite some notable exceptions with thermal conductivities below 20 mW/(m·K), for example from pectin [3, 9], chitosan [10, 11] and cellulose [8, 12-14]. In addition, concerns about long-term stability have not yet been fully addressed.

Cellulose, alginate, pectin, starch carrageenan and chitin/chitosan account for the vast majority of polysaccharide aerogel studies [2, 15-17], but alternative polysaccharides have received far less attention in aerogel research. Pullulan is a starch-derived polysaccharide based on maltotriose units connected by α -1,6 glycosidic bonds. Recently, low-density, freeze-dried scaffolds have been prepared from electrospun pullulan-polyvinyl alcohol nanofibers [18-21]. These novel materials have a strong application potential in wound healing, gas filtration and oil-water separation, but do not possess a sufficiently high fraction of mesopores to qualify as thermal superinsulators, which is confirmed by the thermal conductivity measurements presented in this work (see below).

58 Here, we impregnated nanofibrous, silylated pullulan scaffolds [18] with silica aerogel
59 through a sol impregnation based process. The rationale is that the small pore sizes in silica
60 aerogels, which are below the mean free path length of air (~70 nm at 1 bar and 25°C), will
61 reduce the gas phase thermal conduction. At the same time, the tortuosity of the silica and
62 pullulan nanofiber networks should limit the solid phase conduction. Recent publications on
63 aerogel materials and composites have combined silica aerogel with (bio)polymers and fibers
64 over a wide range of length scales. The industrially most relevant approach is the
65 impregnation of silica aerogel into macroscopic fiber blankets [22-25]. The use of nanofibers
66 represents an intermediate length scale, where either the nanofibers are added to the silica sol
67 in a cogelation approach [26-34] or a preformed nanofibrous scaffold is impregnated with a
68 silica sol [35-37]. The latter approach is the one pursued in this study. At the smallest length
69 scale, the (bio)polymers or their monomeric precursors have been incorporated as individual
70 molecules, first through post-modification [38-40] and more recently through co-gelation
71 approaches [41-46]. Finally, biopolymer-free, silicone-like rather than silica-like aerogels
72 with excellent thermal and mechanical properties have been prepared from functionalized
73 silanes [47, 48].

74

75 Here, we aim to synthesize a material that combines the excellent thermal conductivity of
76 silica aerogel with the flexibility of nanofibrous pullulan scaffolds. Therefore, previously
77 fabricated, silylated nanofibrous pullulan scaffolds were impregnated with a silica sol,
78 followed by gelation, aging, hydrophobization and supercritical drying. The resulting
79 nanocomposites were then analysed in terms of their thermal and mechanical properties.

80

81 **2. Experimental**

82

83 ***2.1 Synthesis***


84

85 The preparation and characterization of the pullulan/PVA nanofibrous scaffolds is detailed in
86 a previous publication [18] and will only be summarized here. Pullulan/PVA nanofibers were
87 prepared by free liquid surface electrospinning an aqueous solution of 4 wt% pullulan and 6
88 wt% polyvinylalcohol (PVA) at 80 kV. The recovered nanofibrous membrane was cut into ca.
89 1 cm² pieces and dispersed in 1,4-dioxane for 20 minutes at 13000 rpm. The homogenous
90 dispersion was cast into a mold, frozen, freeze-dried for 48 h and thermally cross-linked at
91 180°C for 40 minutes. Finally, the cross-linked pullulan/PVA scaffolds were hydrophobized
92 for 24 h by chemical vapour deposition in a desiccator saturated in trichloro(octyl)silane,
93 followed by the elimination of excess silane and HCl under vacuum (10 mbar, 2h).

94 The pullulan-silica aerogel composites were prepared according to Figure 1. A
95 polyethoxydisiloxane (PEDS) sol stock solution, i.e. pre-polymerized tetraethoxysilane
96 (TEOS) with a water-to-TEOS molar ratio of 1.5 and a SiO₂ equivalent concentration of 20
97 wt% in ethanol, was used as silica precursor. 30 ml of PEDS solution was diluted with 120 ml
98 ethanol (F25-A-MEK, 94 wt% ethanol denatured with 2% methyl ethyl ketone, Alcosuisse,
99 Switzerland) to a silica concentration of 4 wt%. Then, 5 ml of water and 1.2 ml of 5.5 M
100 NH₄OH aqueous solution were added to trigger gelation. The activated sol was portioned into
101 6 aliquots of 20 ml and cast into a prefabricated pullulan/PVA nanofibrous scaffolds,
102 followed by 5 minutes degassing in a vacuum chamber (~10 mbar) to remove air bubbles
103 trapped in the fiber scaffold. Gelation typically occurred 10 to 15 minutes after the base
104 addition at room temperature. The gelled composites were covered with ethanol and aged
105 overnight at 55°C. The aged gels (120 ml in total) were hydrophobized by immersing them in
106 a mixture of hexamethyldisiloxane (240 ml), ethanol (8.82 ml) and 37% HCl (0.96 ml). After
107 washing with ethanol once, the gels were dried supercritically in a SCF extractor (Autoclave
108 4334/A21-1, Separex, France). A set of reference silica aerogels was also prepared according
109 to the same procedure, but without the nanofibrous pullulan scaffold. The surfaces of the

110 dried samples were polished prior to performing the mechanical tests and thermal
111 conductivity measurements, with 400 grit sandpaper to remove the edges (menisci), and 2000
112 grit paper for finishing.

113

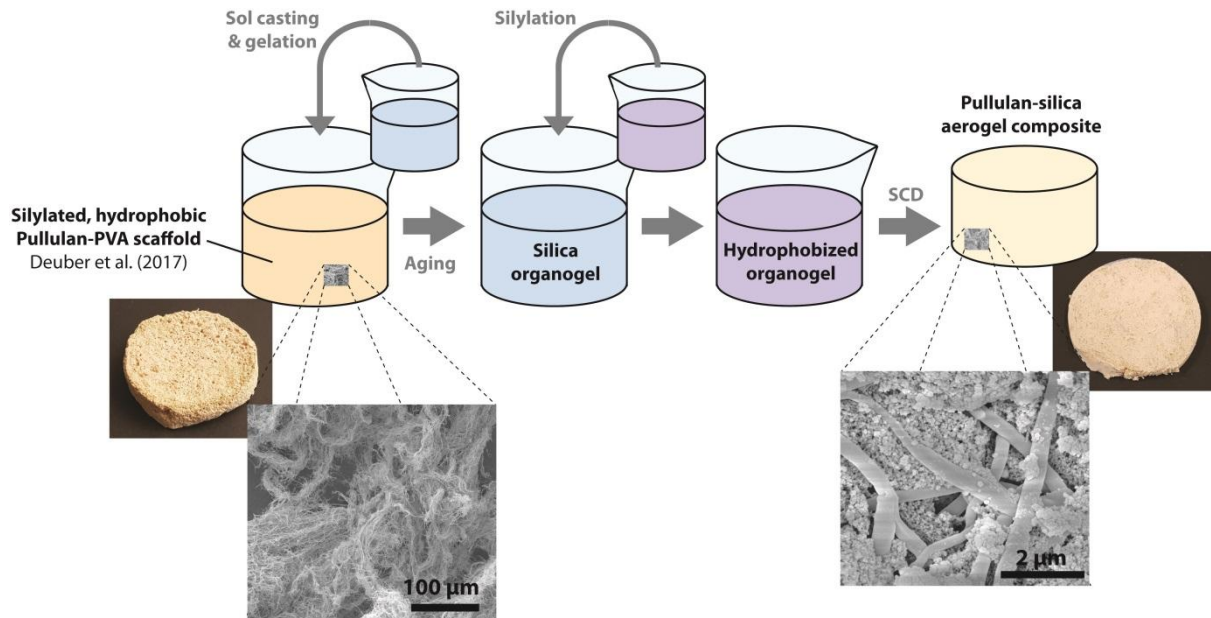

114

115 Figure 1. Synthesis scheme for the pullulan/PVA-silica aerogel nanocomposites.

116

117 2.2 Characterization

118

119 **Density and Brunauer-Emmett-Teller (BET).** The bulk density was calculated from the
120 mass and volume of the regularly shaped, cylindrical samples and the skeletal density was
121 approximated by the linear combination of the known skeletal densities of the constituents:
122 silica aerogel 2.0 g cm^{-3} , pullulan 1.5 g cm^{-3} , and PVA 1.2 g cm^{-3} . The BET specific surface
123 of the composites was determined by nitrogen sorption after degassing at 100°C and 133 mbar
124 for 20 h. Nitrogen adsorption and desorption isotherms were obtained at liquid nitrogen
125 temperature on a Micromeritics TriFlex instrument with 15 seconds equilibration time. The
126 specific surface area of the samples was determined by the Brunauer-Emmett-Teller (BET)
127 method. The pore size distributions and pore diameter D'_{pore} were obtained from the

128 desorption branch of the isotherm using the Barrett–Joyner–Halender (BJH) model, despite
129 the known limitations of nitrogen sorption analysis in determining pore volume and pore size
130 [49].

131 **SEM characterization and Energy Dispersive X-ray (EDX).** Composite aerogels were
132 analyzed after coating with a platinum layer of nominally 10 nm, which refers to the thickness
133 of the Pt coating on the quartz sensor, whereas the actual thickness on the sample may be
134 quite a bit thinner because of the high surface area of the samples. SEM analysis of all
135 materials was performed on a FEI Nova NanoSEM 230 instrument (FEI, Hillsboro, Oregon,
136 USA) at an accelerating voltage of 10 kV and a working distance of 5 mm. The elemental
137 composition was obtained by using energy dispersive X-ray spectrometry (EDX, INCA X-
138 Act, Oxford Instruments, UK) using 20 kV acceleration voltage and a 6mm working distance.

139 **Solid-state NMR spectra** were collected on a Bruker Avance III spectrometer equipped with
140 a wide-bore 9.4 T magnet with ^1H , ^{13}C and ^{29}Si Larmor frequencies of 400.2, 100.6 and 79.5
141 MHz, respectively. ^1H - ^{13}C cross polarization (CP) and ^1H - ^{13}C CP spectra were collected with
142 respective contact times of 2 and 5 ms, 7 mm zirconia rotors, a magic angle spinning (MAS)
143 rate of 4 kHz, a recycle delay of 2 s and between 180 and 27000 scans, depending on the
144 sample.

145 **Mechanical properties**

146 Uniaxial compression tests of the composites were performed on monolithic cylindrical
147 samples (~22 mm diameter, ~ 30 mm high) using a universal materials testing machine
148 (Zwick/Z010, Zwick/Roell, Germany), equipped with a 10 kN force transducer (KAP-S, AST
149 Gruppe GmbH, Germany) in a controlled environment (23°C, 50% relative humidity). Elastic
150 moduli were measured in compression mode and were calculated from the linear region of the
151 stress-strain curves which typically occurred at 3 ± 2 % strain. A constant deformation rate of
152 1 mm/min was used and compressive strength values were taken at the first noticeable sign of
153 cracking. Tensile strength was estimated by the Brazilian split test, which is typically used in

154 cements and ceramic materials and entails the compression of a cylindrical sample lying on its
155 side [50]. The tensile strength σ_T can be calculated from the geometry and the compressive
156 force F as shown in Eq. 1, where D and L are the diameter and length of the samples. The test
157 setup was the same apparatus as used for the uniaxial compression test, but the loading cell
158 was adapted with a customized holder to fit to the cylindrical samples.

$$159 \quad \sigma = \frac{F}{\pi\left(\frac{D}{2}\right)L} \quad (1)$$

160 **Thermal conductivity**

161 Thermal conductivity measurements of flat cylindrical tiles of approximately 45 mm in
162 diameter and 7 mm thickness were carried out on a custom-built guarded hot plate device
163 designed for small samples / low thermal conductivity materials (guarded zone: 50×50 mm²,
164 measuring zone: 25×25 mm²) at a temperature of 25°C on the hot side and 10°C on the cold
165 side (the apparatus is shown in Figure S1, SI).[51] In order to be consistent with
166 measurements according to the European standards [52], calibration measurements were
167 carried out using conventional expanded polystyrene samples measured first in the standard
168 test equipment (conventional guarded hot-plate device) and then cut into smaller pieces to be
169 measured in a second run in the smaller apparatus. The accuracy of the custom-built device
170 was determined to be ±1.0 mW/(m·K) by measuring over 20 samples with known thermal
171 conductivities in the range of 15 to 25 mW/(m·K).

172 **Water contact angle**

173 The surface wettability of samples was evaluated by water contact angle measurement using a
174 Contact Angle System OCA (Dataphysics TBU 90E, Germany), combined with a high-speed
175 camera. Water droplets were deposited directly on the top or bottom surfaces of the samples.
176 Two measurements were performed per sample and averaged. The volume of the water
177 droplet was 5 µL, and the tip used was a precision stainless steel tip (Gauge 32, EFD).

178

3. Results and Discussion

3.1 Chemistry, microstructure and the pullulan-silica aerogel interface


The ^1H - ^{29}Si CP MAS NMR spectrum of the pullulan/PVA scaffolds (Figure 2a) displays no observable signals, indicating that the concentration of grafted octylsilyl groups is too low to be detected by our current solid-state NMR experiment. This is not surprising, given the relatively low surface area ($\sim 10\text{ m}^2/\text{g}$ predicted from a nanofiber diameter of $240\pm 55\text{ nm}$) and resulting low concentration of octylsilyl groups from the chemical vapour deposition of trichloro(octyl)silane, with $<5\text{ wt}\%$ weight gain or $<1\text{ wt}\%$ of Si [18]. The grafted silanes however can be detected as a (weak) Si signal in the EDX spectra of the silylated pullulan/PVA sponges (Figure S1). The ^1H - ^{29}Si CP MAS NMR spectrum of both the reference silica aerogel and the pullulan-silica aerogel nanocomposites displays the typical peaks from the trimethylsilyl (TMS) groups and the Q^n species of the silica aerogel, where Q^n is a Si atom coordinated by n bridging oxygens ($\equiv\text{Si-O-Si}\equiv$) and $4-n$ non-bridging oxygens ($\equiv\text{Si-OH}$ or $\equiv\text{Si-OCH}_2\text{CH}_3$).

The ^1H - ^{13}C CP MAS NMR spectrum of the pullulan/PVA scaffold displays the bands expected for a mixture of pullulan [53] and PVA [54]. In addition, bands related to the caramelization products that originate from the thermal cross-linking step are present [55]. Note that, as for the ^1H - ^{29}Si CP spectrum, the signal from the grafted octylsilyl groups is not intense enough to be detected in the ^1H - ^{13}C CP spectrum. The ^1H - ^{13}C CP MAS NMR spectrum of the reference silica aerogel displays three main bands, related to trimethylsilyl groups and the methyl and methylene groups of the ethoxy groups ($\equiv\text{Si-OCH}_2\text{CH}_3$), as expected for a PEDS derived silica aerogel prepared in an ethanol-based solvent [56, 57]. The ^1H - ^{13}C CP MAS NMR spectrum of the pullulan-silica aerogel nanocomposite closely

205 resembles a linear combination of the spectra of the neat pullulan/PVA sponge (~25% of
206 signal) and that of the reference silica aerogel (~75% of signal), in proportions that are
207 consistent with the densities of the pullulan/PVA scaffold (0.030 g/cm³), reference silica
208 aerogel (0.071 g/cm³) and pullulan-silica aerogel nanocomposite (0.099 g/cm³).


209
210 Although CP NMR spectra are not quantitative in nature, a comparison of the relative peak
211 intensities for different samples does provide a qualitative measure of species concentrations
212 because the CP conditions were kept constant between the different measurements. The
213 TMS/Qⁿ peak intensity ratio is higher in the ¹H-²⁹Si spectrum of the reference silica aerogel
214 than for the pullulan-silica aerogel composite (Figure 2a), indicating that the former is more
215 completely hydrophobized. A higher degree of hydrophobization should be associated with a
216 higher degree of polymerization because oxygen bridges ($\equiv\text{Si-O-Si}(\text{CH}_3)_3$) are formed during
217 the grafting reaction of TMS, and this is confirmed by the higher Q⁴/Q³ peak ratio for the
218 reference silica aerogel. Finally, the higher hydrophobization degree for the reference silica
219 aerogel is also confirmed by the higher TMS/ethoxy peak ratios in the ¹H-¹³C spectrum
220 (Figure 2b). In previous studies on silica-pectin and silica-chitosan hybrid aerogels, prepared
221 from molecular rather than nanofibrous polysaccharides, we have observed a similar effect,
222 i.e. a less complete hydrophobization for the hybrid aerogels compared to neat silica aerogel
223 [42, 43]. Note that this difference in TMS concentration does not affect the water contact
224 angle, which is the same for both the reference silica aerogel and the composite (~140°, Table
225 1).

226

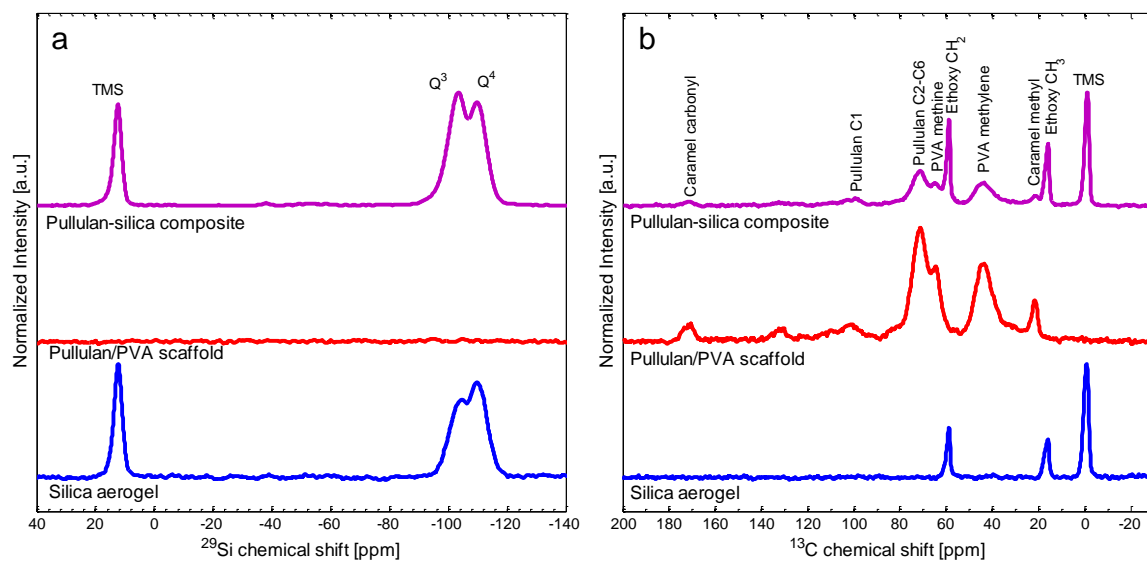

227
 228 Figure 2. Solid-state MAS NMR spectra of the reference silica aerogel, silylated
 229 pullulan/PVA scaffold, and pullulan-silica aerogel composite; a) ^1H - ^{13}C CP spectra; b) ^1H -
 230 ^{29}Si CP spectra.

231
 232 The pullulan/PVA scaffolds display a hierarchical pore structure with major cellular pores
 233 from the freeze-drying process, separated by pore walls with high local concentrations of
 234 entangled nanofibers with minor pores in between. The pullulan/PVA nanofibers themselves
 235 have fiber diameters on the order of 250 nm, consistent with those prepared in an earlier study
 236 [18], and have smooth surfaces. Locally, nanoparticle aggregates formed on the pullulan/PVA
 237 nanofibers (Figure 3b) and EDX analysis (Figure S1) confirms these to be rich in Si. These
 238 aggregates are clearly originating from the trichloro(octyl)silane chemical vapour deposition
 239 process. The Si content of the smooth fiber surfaces, further away from the nanoparticle
 240 aggregates, is close to the EDX detection limit, i.e. either just below or just above the
 241 detection limit, depending on the location of the analysis (Figure S1).

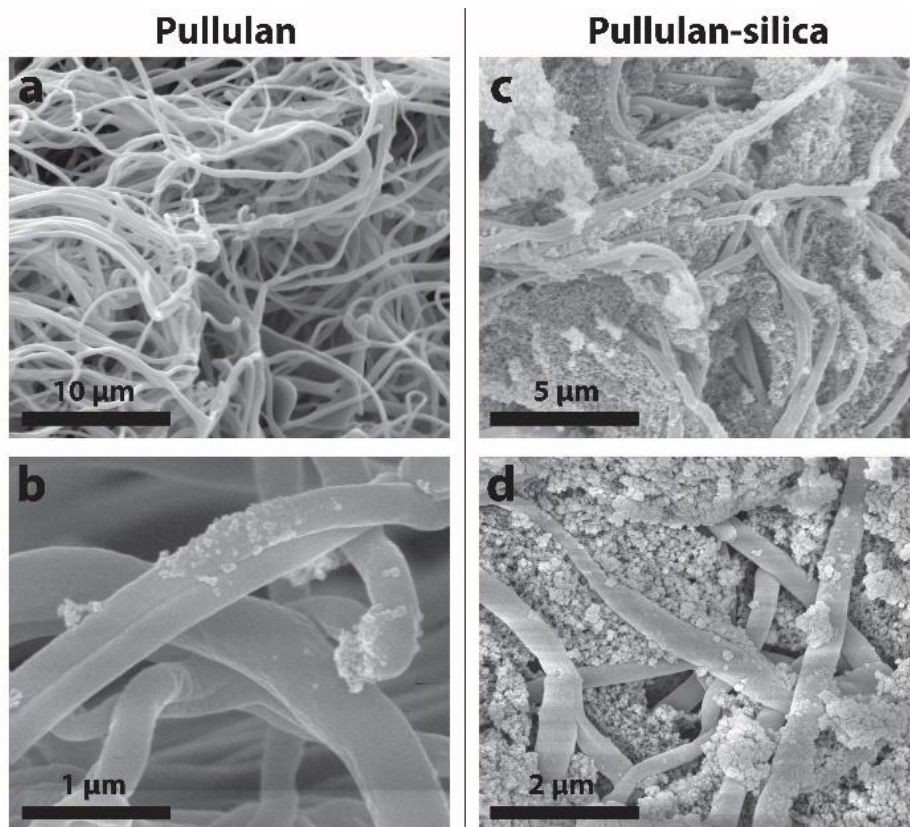

243

244 Figure 3. SEM images of a silylated pullulan/PVA scaffold (a,b) and the pullulan-silica
 245 aerogel composites (c,d).

246

247 The SEM images of the pullulan-silica aerogel nanocomposites confirm that the silica aerogel
 248 phase completely fills the interstitial pores between the pullulan/PVA nanofibers and no
 249 macroscopic voids are present in the composites (Figure 3c,d). The silica aerogel phase itself
 250 displays the particle-network mesostructure typical for silica aerogels, with secondary
 251 particles of around 20 to 50 nm in diameter (Figures 4, 3d). The mesoporosity of the silica
 252 aerogel inside the pullulan-silica aerogel nanocomposites is confirmed by nitrogen sorption
 253 analysis (Figure S2), with a strong signal in the capillary condensation regime, a specific
 254 surface area (S_{BET}) of 617 m²/g and a BJH mesopore volume of 2.4 cm³/g. Note that the
 255 specific surface area and specific BJH mesopore volume of the silica aerogel phase within the
 256 composite is most likely higher than the values reported above, because approximately 30%


257 of the mass of the composite consists of low surface area pullulan/PVA fibers. The average
258 pore diameter, as approximated from the density and surface area, assuming cylindrical pores,
259 shown in Equation 1.

$$260 \quad D'_{pore} = 4 V_{pore} / S_{BE} \quad (1)$$

261 where $V_{pore} = 1/\rho_{envelope} - 1/\rho_{skeletal}$, is around 60 nm.

262

263 In a recent study, we observed a strong beneficial effect of silylation on the mechanical
264 properties of cellulose foam-silica aerogel nanocomposites [35] and the same mechanism is
265 probably acting in the pullulan-silica aerogel system. The pullulan/PVA nanofiber surfaces in
266 the composites are overgrown with colloidal silica secondary aerogel particles (Figure 4),
267 suggesting a good interfacial compatibility between the silylated pullulan/PVA surface and
268 the silicon alkoxide based silica sol. The high compatibility is mediated by the nanofiber
269 surface modification with a trichloro(octyl)silane derived polysiloxane CVD layer that
270 benefits from the high reactivity of the chlorosilanes to form $\equiv\text{C-O-Si}\equiv$ bonds on the
271 biopolymer surface. The silica growth on the silylated nanofibers progresses through $\equiv\text{Si-O-}$
272 $\text{Si}\equiv$ bond formation, which offsets the somewhat lower reactivity of the alkoxy silanes during
273 the silica sol-gel impregnation step compared to the higher reactivity of the chlorosilanes
274 during the chemical vapour deposition. CVD silane mediated silica overgrowth on the
275 pullulan/PVA nanofibers (see schematic sketch in Figure 4) ensures that the nanofibers are
276 fully incorporated into the silica aerogel structure, also mechanically, and improves the
277 reinforcement effect that the nanofibrous scaffold has on the composite.

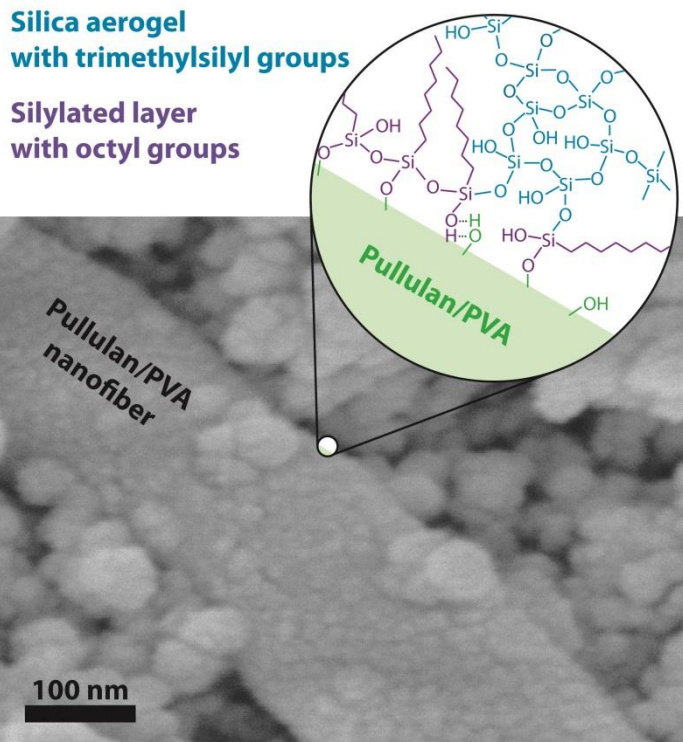

278

279 Figure 4. SEM image of a pullulan/PVA-silica aerogel composite and a schematic overview
 280 of the chemical interactions at the interface between the silylated nanofiber and the silica
 281 aerogel.

282

283 **3.2 Thermal and mechanical properties**

284

285 With a thermal conductivity of 31.4 mW/(m·K) (Table 1, Figure 5b), the hydrophobic, freeze-
 286 dried pullulan/PVA scaffolds are good thermal insulators in their own right, with a
 287 performance that is similar to high performance mineral wool or polystyrene insulation.
 288 However, they are not superinsulators because the pores between the pullulan/PVA
 289 nanofibers are large (between 1 to 1000 μm) compared to the mean free path length of the air
 290 molecules (~ 70 nm STP) and hence, gas phase conduction is not reduced by the Knudsen
 291 effect. The reference silica aerogel in this study has a thermal conductivity of 17.5
 292 mW/(m·K), i.e. well below the ~ 26 mW/(m·K) typical for standing air, because the gas phase
 293 conduction within the aerogel mesopores is limited by the Knudsen effect. However, the



294 thermal conductivity of the reference silica aerogel is somewhat higher than that of an
295 optimized silica aerogel because of its specifically designed density (0.071 g/cm^3) below the
296 optimum for minimal thermal conductivity (typically near 0.120 g/cm^3 [50, 58]). With a value
297 of $17.7 \text{ mW/(m}\cdot\text{K)}$, the pullulan-silica aerogel composite has a near-identical thermal
298 conductivity to the reference silica aerogel, which indicates that the solid conduction through
299 the pullulan-fiber network is not significant. This is not unexpected as solid conduction
300 through low-density fiber networks is generally low [59, 60]. The ultra-low thermal
301 conductivity of the pullulan-silica aerogel composite is comparable to that of high quality
302 silica aerogel and places this hybrid material among the very best silica-(bio)polymer hybrid
303 aerogels in terms of thermal conductivity [41-43, 61-63], in contrast to classical polymer-
304 reinforced aerogels (X-aerogels) for which the, admittedly much stronger, increase in
305 mechanical strength is accompanied by a large penalty in density and thermal conductivity
306 [38, 64, 65].

307

308 The compression properties of the freeze-dried pullulan/PVA scaffolds have been described in
309 detail before [18]: the materials can sustain compression stress without rupture up to at least
310 80%, but display a low E modulus and final compressive strength commensurate with their
311 low density (Table 1, Figure 5a,b). The reference silica aerogel displays compressive
312 properties expected for low density silica aerogels (0.071 g/cm^3): unlike the more elastic and
313 brittle intermediate and high density silica aerogels [50], the reference aerogels studied
314 plastically deform and can sustain uniaxial compression up to at least 80% strain. However,
315 several minor stress release events - linked to multiple crack initiations - are evident from the
316 stress-strain curves between 50 and 80% strain for some samples, leading to a relatively wide
317 scatter in final compressive strength, i.e. σ_{80} (Figure 5a). The pullulan-silica aerogel
318 composites also sustain uniaxial compression up to at least 80%, but have smoother, more
319 reproducible stress-strain curves. The composites display an increase in E modulus by a factor

320 of 56 and 2.3 compared to the neat pullulan/PVA scaffolds and the reference silica aerogel,
321 respectively, with similar increases in σ_{80} . The tensile strength of the silica aerogel and
322 pullulan-silica aerogel composite was estimated from the Brazilian split test [50] and is nearly
323 five times higher for the composite than for the reference silica aerogel (Table 1). As for the
324 compression tests, the stress-strain curves of the pullulan-silica aerogel composite are smooth,
325 whereas those of the reference silica aerogel display minor episodes of step-wise stress
326 releases that decrease the tensile strength and lead to a large sample-to-sample variation
327 (Figure S3). Thanks to their improved compression and tensile properties, the pullulan-silica
328 aerogel composites can be shaped simply by cutting with a sharp blade (Figure 5c), a
329 remarkable feature for silica aerogel composites.

330

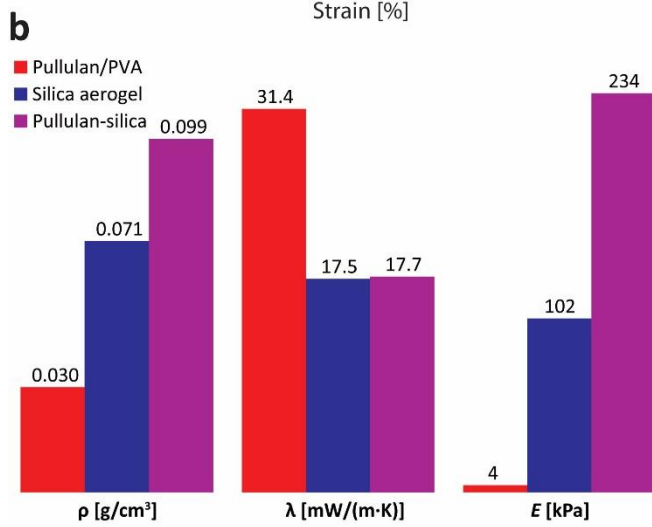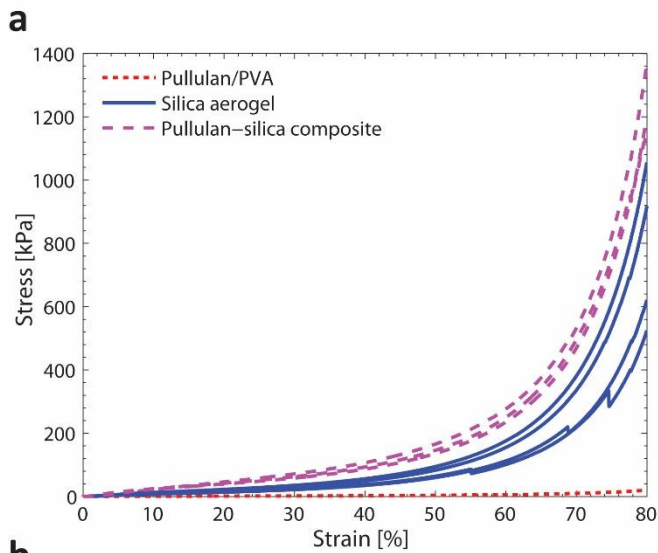

331

332 Figure 5. a) Stress-strain curves during uniaxial compression upon first compression; each
 333 curve corresponds to a different sample. b) Thermal and mechanical properties. c)
 334 Demonstration of the ability to shape the pullulan-silica aerogel composites by cutting.

335

Table 1. Density, thermal conductivity and mechanical properties.

	ρ		λ		WCA	Compression (cylinders)			Compression (plates)			Brazilian test		
						E		ϵ_{\max}	σ_{50}		σ_{80}		σ_T	
	[g/cm ³]	±	[mW/(m·K)]	±	[°]	[kPa]	±	[%]	[kPa]	±	[kPa]	±	[kPa]	±
Pullulan/PVA scaffolds	0.030	0.004	31.4	1.7	132	4	-	>80	8	-	48	-	n.a.	
Silica aerogel	0.071	0.002	17.5	0.6	140	102	27	>80	57	15	470	84	7	8
Pullulan-silica composite	0.099	0.005	17.7	0.9	141	234	23	>80	164	30	818	105	34	7
Compressed composite	0.182	0.015	16.3	1.1	n.a.	n.a.	n.a.	n.a.	1057	-	6121	-	n.a.	

n.a.: not analyzed

WCA: water contact angle

±: calculated as $1.96 \cdot \text{STD}/n^{1/2}$, where n is the number of measurements

336

337


338 ***3.3 Improving thermal and mechanical properties through uniaxial irreversible*** 339 ***compression***

340

341 A relatively low SiO₂ equivalent concentration in the silica sol was selected for the synthesis
342 of the reference and composite aerogels and this leads to a low density of the resulting
343 aerogels (Table 1). This low density in turn leads to thermal conductivities that are somewhat
344 higher than usual for silica aerogel, presumably because the low densities leads to larger pore
345 sizes and a sub-optimal suppression of the gas phase thermal conductivity [50, 58]. Recently,
346 Plappert et al. [12] irreversibly compressed pre-formed low-density cellulose aerogels to
347 decrease the thermal conductivity and increase the mechanical strength. The same approach
348 was applied here. The pullulan-silica aerogel nanocomposites can sustain uniaxial
349 compression up to 80% strain, but display double the density after decompression, compared
350 to the original composite (0.183 versus 0.101 g/cm³). In other words, part of the strain is
351 irreversible. The compressed pullulan-silica aerogel composite displays a 1.4 mW/(m·K)
352 lower thermal conductivity of 16.3 mW/(m·K). The reduction in thermal conductivity is
353 consistent with a decrease in gas phase conduction due to a decrease in average pore size: the
354 compression treatment reduces the average pore size from ~60 to 35 nm, as calculated from
355 the density, pore volume and BET surface area (560 m²/g), to well below the mean free path
356 of air (70 nm at STP). More strikingly, the mechanical properties are improved by nearly an

357 order of magnitude, for example the maximum compressive strength (σ_{80}) increased from
358 0.82 to 6.12 MPa (Table 1, Figure 6). The mechanical properties of the pullulan foam, silica
359 aerogel, composite aerogel, and compressed composite aerogel follow a single power-law
360 behaviour as a function of density, for example both σ_{80} and σ_{50} correlate with $\rho^{2.7}$ (Figure S4).
361 Power law behaviour is common for (biopolymer) aerogels [2, 26], but it is somewhat
362 surprising that the very different materials studied here define a single trend. This indicates
363 that, at least for the investigated systems, density is the primary factor that determines the
364 compressive properties, with less prominent effects from the composition of the solid phase
365 (pullulan/PVA versus silica) or the morphology of the microstructure (nanofibrous foam
366 versus particle based network). In summary, permanent densification through uniaxial
367 compression provides a substantial improvement of the thermal and the mechanical properties
368 of the composites, without compromising machinability (Figure S5).

369

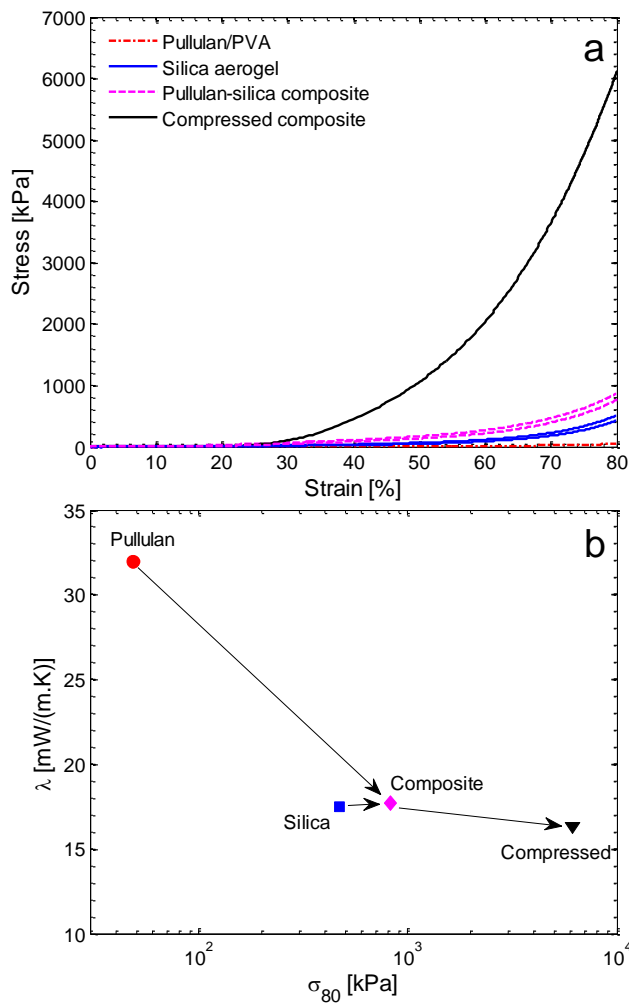

370

371 Figure 6. a) Stress-strain curves under uniaxial compression of sample plates. b) Ashby plot
 372 of thermal conductivity versus σ_{80} .

373

374 3.4 Comparison with constituent reference compounds and other hybrid aerogels

375

376 The thermal and mechanical properties illustrate that the pullulan-silica aerogel composite is
 377 more than just the sum of its parts and has superior properties compared to both the neat
 378 pullulan/PVA scaffold and the neat silica aerogel. This is true for the mechanical properties
 379 collected under lab scale conditions, e.g. compression testing on polished cylinders, but even
 380 more so for the real world behaviour, e.g. in terms of machinability, fragility and dust release.

381 The spider plot in Figure 7a compares the four materials studied here in terms of their thermal


382 insulation performance, machinability, non-brittleness, dust release, hydrophobicity and E
383 modulus. The silica aerogel phase imparts the as-prepared and densified composites with an
384 ultra-low thermal conductivity. The pullulan/PVA scaffolds impart the composites with a low
385 dust release and machinability. As discussed above, the E modulus of the composites benefits
386 from the higher density, particularly for the densified composite, but also for the as-prepared
387 samples (Table 1, Figures 5, 6, S4) and because of the power law dependence of the
388 compression properties on density, these effects exceed the benefits expected for a simple
389 additive behaviour. Importantly, no application relevant properties are worse in the composite
390 than in the neat counterparts.

391

392 Some application relevant properties of silica aerogel hybrids from the literature are plotted in
393 Figure 7b for comparison. Standard silica aerogel, with a density of 0.100 to 0.120 g/cm³,
394 displays elastic compression behaviour, but is very brittle and not machinable [50]. The
395 closest materials in terms of microstructure and synthesis procedure are the silica aerogel –
396 nanofibrillated cellulose foam composites we prepared in a previous study, which were also a
397 major inspiration for the current work. In that study, silylation of the biopolymer foam was
398 found to improve the interfacial compatibility with silica aerogels [18, 66], but because the
399 scaffold was impregnated with a standard density silica aerogel, the mechanical reinforcement
400 effects were rather limited: because of its relatively low density, the silica aerogel employed
401 in the current study is non-brittle [50], and combined with the flexible, highly machinable
402 pullulan-PVA scaffolds, the composites inherit the merits from each component and
403 synergistically enhance the overall properties, particularly in terms of dust release and
404 machinability. Macroscopic fiber blankets filled with silica aerogel [22, 23] are also easy to
405 cut into shape, but typically suffer from a high dust release, in contrast to the composites
406 presented in this study, which display a very low dust release, presumably because of the high
407 interfacial compatibility (Figure 4) and because the nanofibrous scaffolds are more effective

408 at locking fractured aerogel particles in place (Figure 3). Classical polymer reinforced
 409 aerogels (X-aerogels) have excellent mechanical properties, with particularly high E-moduli
 410 [65], but strongly increased thermal conductivities. In contrast, recent (bio)polymer aerogel
 411 reinforced silica aerogels prepared by co-gelation approaches have good thermal properties, a
 412 low dust release, but poor machinability [41-43]. Finally, single phase organic-silica aerogels
 413 based on functional organosilanes have been developed with excellent thermal and
 414 mechanical properties [47, 48]. Most of the cited materials above, and also the pullulan-silica
 415 aerogel composites developed here, have not yet been evaluated for a range of other
 416 application relevant properties, including fire behaviour and long term stability, but these are
 417 beyond the scope of a scientific study.

418

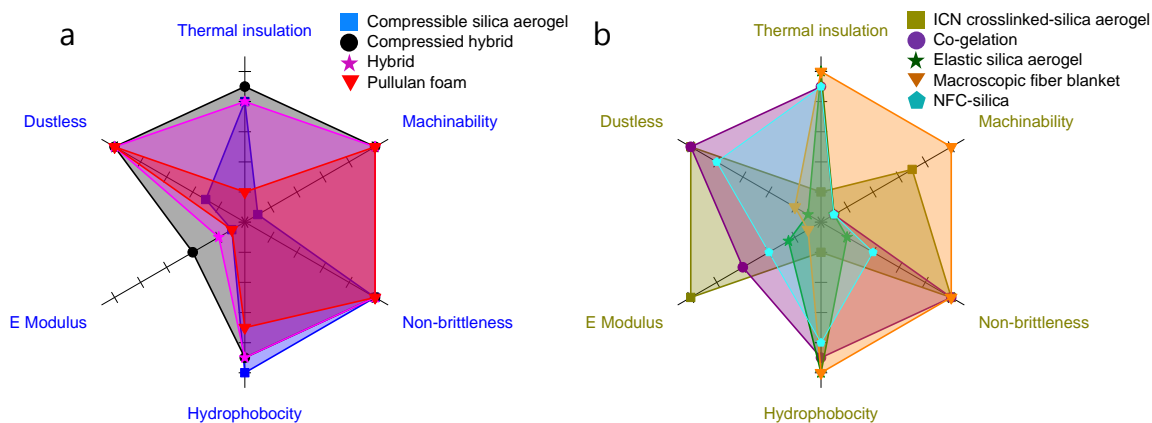

419

420 Figure 7. Comparison of thermal, mechanical and hydrophobic properties of a) the
 421 compressible silica aerogel (0.070 g/cm^3), freeze dried pullulan scaffolds, and their as-
 422 prepared and compressed hybrids developed in this study; b) PU-silica X-aerogels [65], co-
 423 gelation polymer-silica aerogel hybrids [41-43], macroscopic fiber aerogel blankets [22, 23],
 424 NFC-silica aerogel nanocomposites [35], elastic silica aerogel (0.120 g/cm^3) [50].

425

426 Conclusions

427

428 Recently, a wide variety of sol-gel derived, freeze-dried scaffolds have been prepared from
429 (bio)polymer nanofibers. Although these materials often have a low thermal conductivity, in
430 our case equivalent to that of high quality conventional thermal insulation, this is not low
431 enough to offset the more complex synthesis procedure. In addition, the materials are not
432 competitive with classical aerogels in terms of thermal conductivity. In this study, we have
433 demonstrated that the impregnation of silica aerogel decreases the thermal conductivity of the
434 pullulan/PVA scaffold from 31.4 to 17.7 mW/(m·K). At the same time, the pullulan-silica
435 aerogel nanocomposites display strongly improved compression and tensile properties by a
436 factor of 2 and 5 as compared with pure silica aerogel, which makes them easy to shape and
437 machine. Densification of the as-prepared, low-density nanocomposites further reduces
438 thermal conductivity to 16.3 mW/(m·K) and strongly increases the mechanical strength about
439 an order of magnitude and densification through uniaxial compression provides a simple way
440 to tune the thermal and mechanical properties towards specific applications.

441

442 **Acknowledgements**

443

444 We thank Beatrice Fischer and Daniel Rentsch for providing access to the mechanical testing
445 and NMR instruments, respectively. The NMR spectrometer was funded in part by SNF grant
446 150638.

447

448 **Data availability**

449 The raw/processed data required to reproduce these findings cannot be shared at this time due
450 to technical or time limitations.

451

452

453

454 **References**

- 455 [1] S.S. Kistler, Coherent Expanded Aerogels and Jellies, *Nature* 127 (1931) 741-741
 456 <https://doi.org/10.1038/127741a0>.
- 457 [2] Z. Shanyu, M.W. J., G.A. Natalia, K.M. M., N. Gustav, Biopolymer Aerogels and Foams: Chemistry,
 458 Properties, and Applications, *Angew. Chem. Int. Ed.* 57(26) (2018) 7580-7608
 459 <https://doi:10.1002/anie.201709014>.
- 460 [3] S. Groult, T. Budtova, Thermal conductivity/structure correlations in thermal super-insulating pectin
 461 aerogels, *Carbohydr. Polym.* 196 (2018) 73-81 <https://doi.org/10.1016/j.carbpol.2018.05.026>.
- 462 [4] H.-B. Zhao, M. Chen, H.-B. Chen, Thermally insulating and flame retardant polyaniline/pectin
 463 aerogels, *ACS Sustainable Chem. Eng.* 5(8) (2017) 7012-7019 DOI:
 464 10.1021/acssuschemeng.7b01247.
- 465 [5] C. Jiménez-Saelices, B. Seantier, B. Cathala, Y. Grohens, Spray freeze-dried nanofibrillated cellulose
 466 aerogels with thermal superinsulating properties, *Carbohydr. Polym.* 157 (2017) 105-113
 467 <https://doi.org/10.1016/j.carbpol.2016.09.068>.
- 468 [6] G. Horvat, T. Fajfar, A. Perva Uzunalić, Ž. Knez, Z. Novak, Thermal properties of polysaccharide
 469 aerogels, *J. Therm. Anal. Calorim.* 127(1) (2016) 363-370 [https://doi.org/10.1007/s10973-016-](https://doi.org/10.1007/s10973-016-5814-y)
 470 [5814-y](https://doi.org/10.1007/s10973-016-5814-y).
- 471 [7] H. Maleki, S. Montes, N. Hayati-Roodbari, F. Putz, N. Huesing, Compressible, Thermally Insulating,
 472 and Fire Retardant Aerogels through Self-Assembling Silk Fibroin Biopolymers Inside a Silica
 473 Structure- An Approach towards 3D Printing of Aerogels, *ACS Appl. Mater. Interfaces* 10(26)
 474 (2018) 22718–22730 DOI: 10.1021/acsam.8b05856.
- 475 [8] Y. Kobayashi, T. Saito, A. Isogai, Aerogels with 3D Ordered Nanofiber Skeletons of Liquid-Crystalline
 476 Nanocellulose Derivatives as Tough and Transparent Insulators, *Angew. Chem. Int. Ed.* 53(39)
 477 (2014) 10394-10397 DOI: 10.1002/anie.201405123.
- 478 [9] C. Rudaz, R. Courson, L. Bonnet, S. Calas-Etienne, H. Sallée, T. Budtova, Aeropectin: Fully Biomass-
 479 Based Mechanically Strong and Thermal Superinsulating Aerogel, *Biomacromolecules* 15(6) (2014)
 480 2188-2195 DOI: 10.1021/bm500345u.
- 481 [10] S. Takeshita, S. Yoda, Chitosan Aerogels: Transparent, Flexible Thermal Insulators, *Chem. Mater.*
 482 27(22) (2015) 7569-7572 DOI: 10.1021/acs.chemmater.5b03610.
- 483 [11] S. Takeshita, S. Yoda, Translucent, hydrophobic, and mechanically tough aerogels constructed
 484 from trimethylsilylated chitosan nanofibers, *Nanoscale* 9(34) (2017) 12311-12315 DOI:
 485 10.1039/C7NR04051B.
- 486 [12] S.F. Plappert, J.-M. Nedelec, H. Rennhofer, H.C. Lichtenegger, F.W. Liebner, Strain Hardening and
 487 Pore Size Harmonization by Uniaxial Densification: A Facile Approach toward Superinsulating
 488 Aerogels from Nematic Nanofibrillated 2,3-Dicarboxyl Cellulose, *Chem. Mater.* 29(16) (2017) 6630-
 489 6641 DOI: 10.1021/acs.chemmater.7b00787.
- 490 [13] F. Fischer, A. Rigacci, R. Pirard, S. Berthon-Fabry, P. Achard, Cellulose-based aerogels, *Polymer*
 491 47(22) (2006) 7636-7645 <http://dx.doi.org/10.1016/j.polymer.2006.09.004>.
- 492 [14] M. Schestakow, I. Karadagli, L. Ratke, Cellulose aerogels prepared from an aqueous zinc chloride
 493 salt hydrate melt, *Carbohydr. Polym.* 137 (2016) 642-649
 494 <https://doi.org/10.1016/j.carbpol.2015.10.097>.
- 495 [15] C.A. García-González, M. Alnaief, I. Smirnova, Polysaccharide-based aerogels—Promising
 496 biodegradable carriers for drug delivery systems, *Carbohydr. Polym.* 86(4) (2011) 1425-1438
 497 <http://dx.doi.org/10.1016/j.carbpol.2011.06.066>.
- 498 [16] M. Alnaief, R. Obaidat, H. Mashaqbeh, Effect of processing parameters on preparation of
 499 carrageenan aerogel microparticles, *Carbohydr. Polym.* 180 (2018) 264-275
 500 <https://doi.org/10.1016/j.carbpol.2017.10.038>.

- 501 [17] I. Smirnova, P. Gurikov, Aerogel production: Current status, research directions, and future
502 opportunities, *J. Supercrit. Fluids* 134 (2018) 228-233 <https://doi.org/10.1016/j.supflu.2017.12.037>.
- 503 [18] F. Deuber, S. Mousavi, L. Federer, C. Adlhart, Amphiphilic Nanofiber-Based Aerogels for Selective
504 Liquid Absorption from Electrospun Biopolymers, *Adv. Mater. Interfaces* 4(12) (2017) 1700065
505 DOI: 10.1002/admi.201700065.
- 506 [19] F. Deuber, S. Mousavi, M. Hofer, C. Adlhart, Tailoring pore structure of ultralight electrospun
507 sponges by solid templating, *ChemistrySelect* 1(18) (2016) 5595-5598
508 <https://doi.org/10.1002/slct.201601084>.
- 509 [20] F. Deuber, S. Mousavi, L. Federer, M. Hofer, C. Adlhart, Exploration of Ultralight Nanofiber Aerogels
510 as Particle Filters: Capacity and Efficiency, *ACS Appl. Mater. Interfaces* 10(10) (2018) 9069-9076
511 DOI: 10.1021/acsami.8b00455.
- 512 [21] S. Mousavi, F. Deuber, S. Petrozzi, L. Federer, M. Aliabadi, F. Shahraki, C. Adlhart, Efficient dye
513 adsorption by highly porous nanofiber aerogels, *Colloids Surf., A* 547 (2018) 117-125
514 <https://doi.org/10.1016/j.colsurfa.2018.03.052>.
- 515 [22] R.G. Martinez, E. Goiti, G. Reichenauer, S. Zhao, M. Koebel, A. Barrio, Thermal assessment of
516 ambient pressure dried silica aerogel composite boards at laboratory and field scale, *Energy and*
517 *Buildings* 128 (2016) 111-118 <https://doi.org/10.1016/j.enbuild.2016.06.071>.
- 518 [23] C. Stepanian, Highly flexible aerogel insulated textile-like blankets, *US Patents*, US20070154698A1,
519 2007.
- 520 [24] T. Zhou, X. Cheng, Y. Pan, C. Li, L. Gong, H. Zhang, Mechanical performance and thermal stability
521 of glass fiber reinforced silica aerogel composites based on co-precursor method by freeze
522 drying, *Appl. Surf. Sci.* 437 (2018) 321-328 <https://doi.org/10.1016/j.apsusc.2017.12.146>.
- 523 [25] S. Salomo, T.X. Nguyen, D.K. Le, X. Zhang, N. Phan-Thien, H.M. Duong, Advanced Fabrication and
524 Properties of Hybrid Polyethylene Terephthalate Fiber-Silica Aerogels from Plastic Bottle Waste,
525 *Colloids Surf., A* (2018) <https://doi.org/10.1016/j.colsurfa.2018.08.015>.
- 526 [26] J.C.H. Wong, H. Kaymak, P. Tingaut, S. Brunner, M.M. Koebel, Mechanical and thermal properties of
527 nanofibrillated cellulose reinforced silica aerogel composites, *Microporous Mesoporous Mater.*
528 217 (2015) 150-158 <https://doi.org/10.1016/j.micromeso.2015.06.025>.
- 529 [27] J. Fu, S. Wang, C. He, Z. Lu, J. Huang, Z. Chen, Facilitated fabrication of high strength silica aerogels
530 using cellulose nanofibrils as scaffold, *Carbohydr. Polym.* 147 (2016) 89-96
531 <http://dx.doi.org/10.1016/j.carbpol.2016.03.048>.
- 532 [28] H.-Y. Mi, X. Jing, H.-X. Huang, X.-F. Peng, L.-S. Turng, Superhydrophobic Graphene/Cellulose/Silica
533 Aerogel with Hierarchical Structure as Superabsorbers for High Efficiency Selective Oil Absorption
534 and Recovery, *Ind. Eng. Chem. Res.* 57(5) (2018) 1745-1755 DOI: 10.1021/acs.iecr.7b04388.
- 535 [29] E. Kelechi, O.A. Elvis, A.K. Kanayo, Synthesis and Characterization of Chitosan-Silica Hybrid Aerogel
536 using Sol-Gel Method, *Journal of King Saud University-Science* (2018)
537 <https://doi.org/10.1016/j.jksus.2018.08.005>.
- 538 [30] M.C. Rodríguez-Robledo, M.A. González-Lozano, P. Ponce-Peña, P. Quintana Owen, M.A. Aguilar-
539 González, G. Nieto-Castañeda, E. Bazán-Mora, R. López-Martínez, G. Ramírez-Galicia, M. Poisot,
540 Cellulose-Silica Nanocomposites of High Reinforcing Content with Fungi Decay Resistance by
541 One-Pot Synthesis, *Materials* 11(4) (2018) 575 DOI:10.3390/ma11040575.
- 542 [31] L. Vasquez-Zacarias, P. Ponce-Peña, T. Pérez-López, E.A. Franco-Urquiza, G. Ramírez-Galicia, M.
543 Poisot, Hybrid Cellulose-Silica Materials from Renewable Secondary Raw Resources: An
544 Eco-friendly Method, *Global Challenges* (2018) 1700119 <https://doi.org/10.1002/gch2.201700119>.
- 545 [32] N. Rangelova, L. Aleksandrov, S. Nenkova, Synthesis and characterization of pectin/SiO₂ hybrid
546 materials, *J. Sol-Gel Sci. Technol.* 85(2) (2018) 330-339 [https://doi.org/10.1007/s10971-017-4556-](https://doi.org/10.1007/s10971-017-4556-z)
547 [z](https://doi.org/10.1007/s10971-017-4556-z).
- 548 [33] C. Wang, H. Cheng, C. Hong, X. Zhang, T. Zeng, Lightweight chopped carbon fibre reinforced
549 silica-phenolic resin aerogel nanocomposite: facile preparation, properties and application to

- 550 thermal protection, *Composites Part A: Applied Science and Manufacturing* (2018)
551 <https://doi.org/10.1016/j.compositesa.2018.05.026>.
- 552 [34] Y.-G. Kim, H.S. Kim, S.M. Jo, S.Y. Kim, B. Yang, J. Cho, S. Lee, J.E. Cha, Thermally insulating, fire-
553 retardant, smokeless and flexible polyvinylidene fluoride nanofibers filled with silica aerogels,
554 *Chem. Eng. J.* (2018) <https://doi.org/10.1016/j.cej.2018.06.102>.
- 555 [35] S. Zhao, Z. Zhang, G. Sèbe, R. Wu, R.V. Rivera Virtudazo, P. Tingaut, M.M. Koebel, Multiscale
556 Assembly of Superinsulating Silica Aerogels Within Silylated Nanocellulosic Scaffolds: Improved
557 Mechanical Properties Promoted by Nanoscale Chemical Compatibilization, *Adv. Funct. Mater.*
558 25(15) (2015) 2326-2334 DOI: 10.1002/adfm.201404368.
- 559 [36] G. Hayase, K. Kanamori, K. Abe, H. Yano, A. Maeno, H. Kaji, K. Nakanishi, Polymethylsilsesquioxane-
560 Cellulose Nanofiber Biocomposite Aerogels with High Thermal Insulation, Bendability, and
561 Superhydrophobicity, *ACS Appl. Mater. Interfaces* 6(12) (2014) 9466-9471 DOI:
562 10.1021/am501822y.
- 563 [37] H. Sai, R. Fu, J. Xiang, Y. Guan, F. Zhang, Fabrication of elastic silica-bacterial cellulose composite
564 aerogels with nanoscale interpenetrating network by ultrafast evaporative drying, *Compos. Sci.*
565 *Technol.* 155 (2018) 72-80 <https://doi.org/10.1016/j.compscitech.2017.11.004>.
- 566 [38] J.P. Randall, M.A.B. Meador, S.C. Jana, Polymer reinforced silica aerogels: effects of
567 dimethyldiethoxysilane and bis(trimethoxysilylpropyl)amine as silane precursors, *J. Mater. Chem. A*
568 1(22) (2013) 6642-6652 DOI: 10.1039/C3TA11019B.
- 569 [39] M.A.B. Meador, E.F. Fabrizio, F. Ilhan, A. Dass, G. Zhang, P. Vassilaras, J.C. Johnston, N. Leventis,
570 Cross-linking amine-modified silica aerogels with epoxies: mechanically strong lightweight porous
571 materials, *Chem. Mater.* 17(5) (2005) 1085-1098 DOI: 10.1021/cm048063u.
- 572 [40] N. Leventis, A. Palczer, L. McCorkle, G. Zhang, C. Sotiriou-Leventis, Nanoengineered silica-polymer
573 composite aerogels with no need for supercritical fluid drying, *J. Sol-Gel Sci. Technol.* 35(2) (2005)
574 99-105 <https://doi.org/10.1007/s10971-005-1372-7>.
- 575 [41] S. Iswar, G.M. Snellings, S. Zhao, R. Erni, Y.K. Bahk, J. Wang, M. Lattuada, M.M. Koebel, W.J. Malfait,
576 Reinforced and superinsulating silica aerogel through in situ cross-linking with silane terminated
577 prepolymers, *Acta Mater.* 147 (2018) 322-328 <https://doi.org/10.1016/j.actamat.2018.01.031>.
- 578 [42] S. Zhao, W.J. Malfait, A. Demilecamps, Y. Zhang, S. Brunner, L. Huber, P. Tingaut, A. Rigacci, T.
579 Budtova, M.M. Koebel, Strong, Thermally Superinsulating Biopolymer-Silica Aerogel Hybrids by
580 Cogelation of Silicic Acid with Pectin, *Angew. Chem. Int. Ed.* 54(48) (2015) 14282-14286 DOI:
581 10.1002/anie.201507328.
- 582 [43] S. Zhao, W.J. Malfait, E. Jeong, B. Fischer, Y. Zhang, H. Xu, E. Angelica, W.M. Risen, J.W. Suggs, M.M.
583 Koebel, Facile One-Pot Synthesis of Mechanically Robust Biopolymer-Silica Nanocomposite
584 Aerogel by Cogelation of Silicic Acid with Chitosan in Aqueous Media, *ACS Sustainable Chem.*
585 *Eng.* 4(10) (2016) 5674-5683 DOI: 10.1021/acssuschemeng.6b01574.
- 586 [44] Z. Fei, Z. Yang, G. Chen, K. Li, Preparation of tetraethoxysilane-based silica aerogels with polyimide
587 cross-linking from 3, 3', 4, 4'-biphenyltetracarboxylic dianhydride and 4, 4'-oxydianiline, *J. Sol-Gel*
588 *Sci. Technol.* 85(3) (2018) 506-513 <https://doi.org/10.1007/s10971-017-4566-x>.
- 589 [45] H. Li, C. Sun, R. Li, Y. Fu, L. Song, A. Yang, H. Liu, Preparation and characterization of silica
590 aerogel/polymethyl methacrylate composites with electrostatic interaction phase interface, *J.*
591 *Polym. Eng.* 38(8) (2018) 811-818 <https://doi.org/10.1515/polyeng-2017-0402>.
- 592 [46] V.G. Parale, K.-Y. Lee, H.-Y. Nah, H. Choi, T.-H. Kim, V.D. Phadtare, H.-H. Park, Facile synthesis of
593 hydrophobic, thermally stable, and insulative organically modified silica aerogels using co-
594 precursor method, *Ceram. Int.* 44(4) (2018) 3966-3972
595 <https://doi.org/10.1016/j.ceramint.2017.11.189>.
- 596 [47] G. Zu, T. Shimizu, K. Kanamori, Y. Zhu, A. Maeno, H. Kaji, J. Shen, K. Nakanishi, Transparent,
597 Superflexible Doubly Cross-linked Polyvinylpolymethylsiloxane Aerogel Superinsulators via
598 Ambient Pressure Drying, *ACS NANO* 12(1) (2018) 521-532 DOI: 10.1021/acsnano.7b07117.

- 599 [48] T. Shimizu, K. Kanamori, A. Maeno, H. Kaji, C.M. Doherty, K. Nakanishi, Transparent Ethenylene-
600 Bridged Polymethylsiloxane Aerogels: Mechanical Flexibility and Strength and Availability for
601 Addition Reaction, *Langmuir* 33(18) (2017) 4543-4550 DOI: 10.1021/acs.langmuir.7b00434.
- 602 [49] G. Reichenauer, Structural Characterization of Aerogels, in: M.A. Aegerter, N. Leventis, M.M. Koebel
603 (Eds.), *Aerogels Handbook*, Springer New York 2011, pp. 449-498.
- 604 [50] J.C.H. Wong, H. Kaymak, S. Brunner, M.M. Koebel, Mechanical properties of monolithic silica
605 aerogels made from polyethoxydisiloxanes, *Microporous Mesoporous Mater.* 183 (2014) 23-29
606 <http://dx.doi.org/10.1016/j.micromeso.2013.08.029>.
- 607 [51] T. Stahl, S. Brunner, M. Zimmermann, K. Ghazi Wakili, Thermo-hygric properties of a newly
608 developed aerogel based insulation rendering for both exterior and interior applications, *Energy*
609 and Buildings 44(0) (2012) 114-117 <http://dx.doi.org/10.1016/j.enbuild.2011.09.041>.
- 610 [52] European Standard EN 12667, Thermal performance of building materials and products –
611 determination of thermal resistance by means of guarded hot plate and heat flow meter methods
612 – products of high and medium thermal resistance, Brussels, 2001.
- 613 [53] R.S. Singh, G.K. Saini, J.F. Kennedy, Downstream processing and characterization of pullulan from a
614 novel colour variant strain of *Aureobasidium pullulans* FB-1, *Carbohydr. Polym.* 78(1) (2009) 89-94
615 <https://doi.org/10.1016/j.carbpol.2009.03.040>.
- 616 [54] K. Katsuraya, K. Hatanaka, K. Matsuzaki, S. Amiya, Assignment of finely resolved ¹³C NMR spectra
617 of poly (vinyl alcohol), *Polymer* 42(24) (2001) 9855-9858 [https://doi.org/10.1016/S0032-](https://doi.org/10.1016/S0032-3861(01)00536-5)
618 [3861\(01\)00536-5](https://doi.org/10.1016/S0032-3861(01)00536-5).
- 619 [55] R.D. Huang, M.S. Feather, Carbon-13 NMR study of some Maillard reaction products arising from
620 D-glucose-DL-alanine interactions, *J. Agric. Food. Chem.* 36(4) (1988) 673-676 DOI:
621 10.1021/jf00082a001.
- 622 [56] W.J. Malfait, R. Verel, M.M. Koebel, Hydrophobization of Silica Aerogels: Insights from Quantitative
623 Solid-State NMR Spectroscopy, *J. Phys. Chem. C* 118(44) (2014) 25545-25554 DOI:
624 10.1021/jp5082643.
- 625 [57] W.J. Malfait, S. Zhao, R. Verel, S. Iswar, D. Rentsch, R. Fener, Y. Zhang, B. Milow, M.M. Koebel,
626 Surface Chemistry of Hydrophobic Silica Aerogels, *Chem. Mater.* 27(19) (2015) 6737-6745 DOI:
627 10.1021/acs.chemmater.5b02801.
- 628 [58] N. Hüsing, U. Schubert, Aerogels—Airy Materials: Chemistry, Structure, and Properties, *Angew.*
629 *Chem. Int. Ed.* 37 (1998) 22-45 DOI: 10.1002/(sici)1521-3773(19980202)37:1/2<22::aid-
630 anie22>3.0.co;2-i.
- 631 [59] J. Kim, T.-H. Song, Vacuum insulation properties of glass wool and opacified fumed silica under
632 variable pressing load and vacuum level, *Int. J. Heat Mass Transfer* 64 (2013) 783-791
633 <https://doi.org/10.1016/j.ijheatmasstransfer.2013.05.012>.
- 634 [60] Z. Chen, Z. Chen, Z. Yang, J. Hu, Y. Yang, L. Chang, L.J. Lee, T. Xu, Preparation and characterization
635 of vacuum insulation panels with super-stratified glass fiber core material, *Energy* 93 (2015) 945-
636 954 <https://doi.org/10.1016/j.energy.2015.08.105>.
- 637 [61] J. Cai, S. Liu, J. Feng, S. Kimura, M. Wada, S. Kuga, L. Zhang, Cellulose–Silica Nanocomposite
638 Aerogels by In Situ Formation of Silica in Cellulose Gel, *Angew. Chem. Int. Ed.* 51(9) (2012) 2076-
639 2079 DOI: 10.1002/anie.201105730.
- 640 [62] G. Markevicius, R. Ladj, P. Niemeyer, T. Budtova, A. Rigacci, Ambient-dried thermal superinsulating
641 monolithic silica-based aerogels with short cellulosic fibers, *J. Mater. Sci.* 52(4) (2017) 2210-2221
642 <https://doi.org/10.1007/s10853-016-0514-3>.
- 643 [63] A. Demilecamps, C. Beauger, C. Hildenbrand, A. Rigacci, T. Budtova, Cellulose–silica aerogels,
644 *Carbohydr. Polym.* 122(0) (2015) 293-300 <http://dx.doi.org/10.1016/j.carbpol.2015.01.022>.
- 645 [64] M.A.B. Meador, L.A. Capadona, Process for preparing polymer reinforced silica aerogels, US
646 Patents, 2011.

- 647 [65] M.A.B. Meador, L.A. Capadona, L. McCorkle, D.S. Papadopoulos, N. Leventis, Structure–Property
648 Relationships in Porous 3D Nanostructures as a Function of Preparation Conditions: Isocyanate
649 Cross-Linked Silica Aerogels, *Chem. Mater.* 19(9) (2007) 2247-2260 DOI: 10.1021/cm070102p.
- 650 [66] Z. Zhang, G. Sèbe, D. Rentsch, T. Zimmermann, P. Tingaut, Ultralightweight and Flexible Silylated
651 Nanocellulose Sponges for the Selective Removal of Oil from Water, *Chem. Mater.* 26(8) (2014)
652 2659-2668 DOI: 10.1021/cm5004164.
- 653

S. Zhao, W. Malfait, C. Adlhart and M. Koebel conceived of the presented idea. A. Wohlhauser synthesized the pullulan/PVA nanofibers. O. Emery and S. Zhao fabricated the composites. W. Malfait assisted with NMR measurements, and S. Zhao did all the rest characterization. W. Malfait wrote the manuscript with support from S. Zhao. M. Koebel helped to supervise the project. All authors provided critical feedback and helped shape the research, analysis and manuscript.