

Chapter 11 Evaluating the performance of fabrics for sportswear

Praburaj Venkatraman

Table of contents

Introduction	1
Physical measurements for woven and knitted fabrics	4
Fabric area density:	5
Fabric Thickness:	6
Fabric bulk density	8
Fabric construction	8
Fabric cover factor	10
Fabric count	10
Evaluating durability	11
Abrasion resistance	12
Fabric handle in sportswear	17
Fabric stiffness	18
Fabric drape	19
Fabric stretch and recovery	20
Measurement of fabric comfort	22
Wicking and its effect on fabric comfort	23
Moisture Management Tester (MMT)	23
Influence of moisture transfer in functional clothing (Permetest)	27
Fabric specifications and interpreting results	30
References	35

Introduction

Evaluation of fabrics for its performance is mandatory particularly during design and development of sportswear and performance apparel. By investigating the properties of fabrics through textile testing it is possible to determine its suitability for its intended application. Specific fibre types can be blended to meet consumer requirements, for

Table 1 Various sports and their requirements			
Popular sports	Fabrics used	Frequently used product name	Specific properties
Cycling	Brushed knitted fabrics with stretch	Cycling tights	Three-way stretch Insulation during winter Soft next to the skin
Skiing	Warp knitted fabric	Base layer thermal	Thermal resistance Stretch and recovery Moisture permeable
	Single weft knit, napped technical back	Mid layer fleece	Thermal insulation
	Breathable coated woven fabrics (high density)	Outer shell jackets	Water proof Breathable Durable
Running	Warp/weft knitted fabric with bi-directional stretch	Compression tights –	Stretch and recovery Comfort
	Knitted fabric	Tops and leggings	
	Woven fabric	Jogging shorts	Light weight Quick drying
Football	Warp and weft knit	Tights	Stretch and recovery Moisture permeable
	Knitted fabric	Tops	Comfortable/moisture management
	Woven fabric	Trousers	Durable
Swimming	Woven and knit fabrics with elastomeric filaments	Female/male swim suits	Stretch and recovery Quick drying Durable
		Training jackets and trousers	

In this chapter, specific test methods relating to fabric durability, fabric handle, stretch and recovery, moisture transport, water vapour permeability and thermal resistance are discussed. The test methods are referred to British standards which provide definition of various parameters, examples are included to enable the reader to interpret the test results and explanation is provided on how those parameters affect garment performance and research relating to these parameters (Figure 1).



Different Type of sports

Figure 1 Different type of individual sport

Physical measurements for woven and knitted fabrics

Fabric's physical parameters play an important role in determining their characteristics which is widely used by professionals as 'specifications' whilst making decisions such as suitability for a particular end use or to communicate across the fashion supply chain. In this section, the following parameters will be discussed:

- Fabric area density or fabric weight
- Fabric thickness
- Fabric bulk density



Figure 2 Fabric gsm cutter
 (Image courtesy of MMU Textile Lab)

Table 2 Fabric weight for fabrics used in sportswear		
Fabric type	grams/square metre (g/m²)	Function /end uses
Very light weight fabric	18	Base layer, light weight, moisture management smooth fabric worn next to skin
Light weight fabric	< 100	Mid layer fabric used for tops, trousers, trainers, etc.
Medium weight fabric	130 - 180	Soft shell fabrics used outer layer jackets, these are either laminated or coated with finishes
Heavy weight fabrics	250+	Hard shell heavy weight fabrics used for jackets, trousers, and high performance technical materials used for outdoor applications

Fabric Thickness:

It is the distance between the upper and lower surface of the fabric and is measured using a thickness gauge or tester (Figure 3). The test sample is placed between two reference plates which exerts a known pressure on the sample. The distance between plates is recorded in mm (BS EN ISO 5084). The fabric thickness affects garment production

especially in adjusting the sewing machine settings. This could be selection of a needle or fabric feed system. Selection of needle depends on the stitch density (seams per inch) required. In sportswear stitch density is finer than for a jacket. For knitwear, a ball pointed tip is preferred which prevents from fabric damage (laddering effect). For instance, in the case of knitted stretch fabrics with fine thickness that slips during sewing due to slippage results in fabric being gathered or staggered, in this case, a differential feed system at the top and bottom will be used in sewing machine, one end will feed the fabric quicker and the other feeds slowly resulting in a good quality seam. Fabric thickness also affects the overall performance of a garment, especially, the abrasion resistance of fabrics, the higher the fabric thickness, the higher resistance to abrasive action (Özdil et al, 2012). Table 3 generally classifies the thickness of fabrics.



Figure 3 Fabric thickness tester

(Image courtesy of MMU Textile Lab)

Table 3 Fabric Thickness	
Type	Thickness (mm)
Thin	< 0.20
Medium	0.23 – 0.46
Thick	> 0.47
Source: Collier and Epps (1999)	

Fabric bulk density

Fabric bulk density takes into account the fabric weight and thickness. It represent the bulkiness of the fabric relative to its thickness. It is an important factor in determining the garment comfort. A thick fabric with an average weight is more comfortable in cold conditions or outdoor sports on the other hand a thin fabric of same weight will be ideal in warm conditions. It is generally expressed in g/cm³. Bulk density is calculated using the equation given below.

$$Bulk\ density = \frac{fabric\ thickness\ in\ cm \times fabric\ weight\ in\ g/cm^2}{10,000}$$

Fabric construction

The repeat of the design is presented by shading the box that represents the warp interlacing over the weft yarn (Figure 4 and 5). This is called ‘fabric design’ construction.

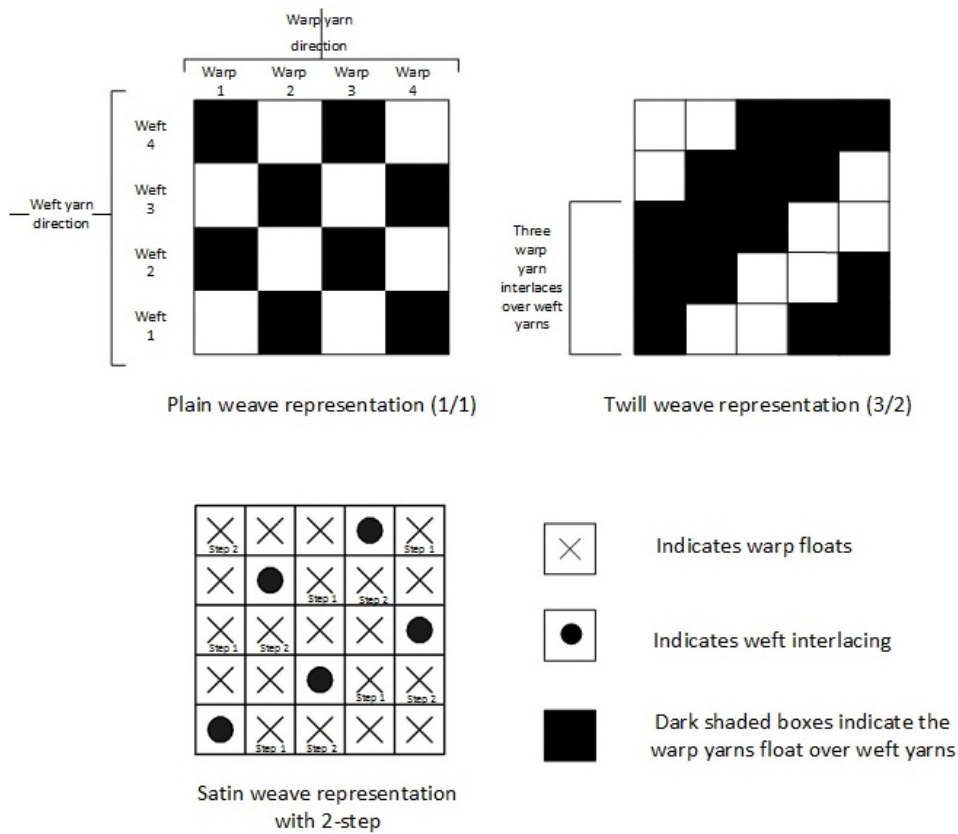


Figure 4 Woven fabric construction

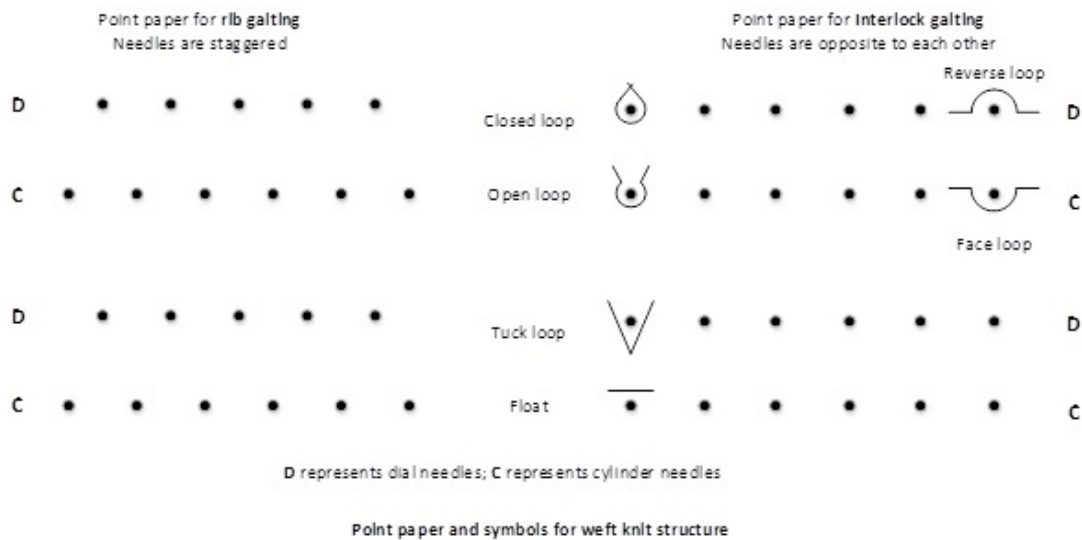


Figure 5 Point paper for weft knitted fabric representation

(Source: Taylor, 1999)

Fabric cover factor

Cover factor for woven fabrics indicates the extent to which a fabric area is covered by one set of yarns. In woven fabrics, cover factor is determined in warp and weft direction. In knitted fabrics cover factor is also termed as tightness factor. It is generally denoted by K.

It is calculated using the formula, $K = \frac{\text{threads per cm} \sqrt{\text{tex}}}{10}$ for woven fabrics

Tightness factor $K = \frac{\sqrt{\text{tex}}}{\text{stitch length in mm}}$ for knitted fabrics

Fabric count

A fabric counter or magnifying glass is used to determine fabric count. Fabric count is assessed by counting the number of warp or weft yarns in woven fabric (Figure 6b) and counting the number of courses and wales in knitted fabrics (Figure 6a). The fabric count plays an important role in determining the closeness of the weave or knit that affects various properties such as porosity, permeability, durability of the fabric.

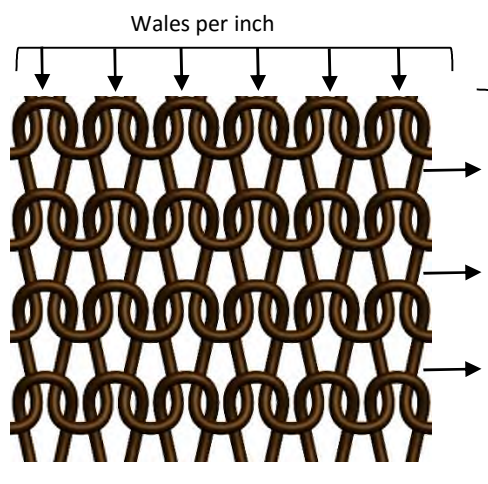


Figure 6 a Knitted fabric structure

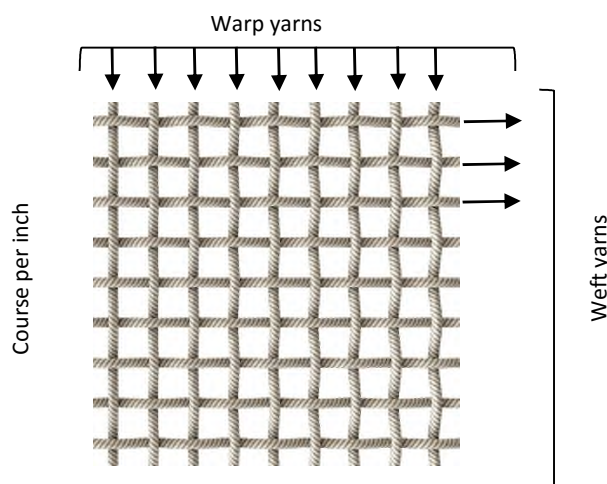


Figure 6b Woven fabric structure

(Source: Dreamstime)

Evaluating durability

Durability is one of the important parameter when selecting a fabric for a particular end use. Sports activity involves repeated body movements and sportswear can abrade in several ways, for instance fabric rubbing with another layer of fabric, fabric abrading in particular areas including, crotch, knee, and under arms; rubbing against another object due to trip or fall; garment abrasion while laundering; and abrasion can also occur between yarns and fibres when fabric is stretched repeatedly. The effect of fabric abrasion depends on various elements, fibre type and its properties; yarn quality and its structure; and fabric construction.

Factors that affect abrasion resistance of fabrics

- Presence of longer fibres in the yarn offer better resistance to abrasion than short fibres
- Increased in fibre diameter enhances resistance to a certain extent
- Optimum yarn twist offers good resistance to abrasion
- Increasing yarn linear density increases resistance with a constant fabric density
- Uniform yarn crimp in the fabric (warp and weft) enables even wear across the fabric
- Warp or weft floats are highly susceptible to abrasion
- Fabric weight and its relative thickness affects the abrasion resistance
- Abrasion also depends on fabric count (ends and picks per inch) the more threads per inch the lesser the wear
- Type of yarns also affects abrasion resistance, for instance, air jet spun yarn – high resistance to abrasion; ring spun yarn possess moderate resistance and open –end spun yarn possess low resistance to abrasion

Abrasion resistance

The usual method to evaluate fabric abrasion is Martindale abrasion tester, where the instrument (BS EN ISO 12947-2/2014) subjects specimen to a uniform rubbing motion (Lissajou's figure) and is repeated until two threads are broken (woven fabric). Various methods are used to determine the end of the test are the evaluation of change in before and after sample weight, change in colour using a colour change chart (ISO 105 A02) or examining whether the sample distortion or being rubbed away and completion of specified number of cycles (Johnson and Cohen, 2010). However, in this section Taber Abrasion tester is discussed (BS EN ISO 5470-1/1999) that works on the principle of rotary platform which tests flat abrasion and is intended for heavier woven and knitted fabrics as the abrading action is severe (Figure 7). In this method, the instrument uses a flat abrasive action in which the fabric is placed on a rotatory platform and is abraded by two abrasive wheels. Six samples of dimension 114 ± 1 mm diameter with a central hole of diameter 6.35 mm is chosen and is conditioned. The load applied can be varied depending upon the type of abrasion required for instance from very gentle (2.5 N) to harsh action (9.8 N). Similarly, the rotary wheels can be either rubber and abrasive grain or vitrified version depending on the required abrasive action. The sample weight is measured prior to test in milligrams. To determine the average rate of loss in mass, the loss in mass for every 100 cycles should be recorded. The end of test is determined by change in colour of abraded portion, change in mass, or change in surface distortion.



Figure 7 Taber Abrasion Tester

(Image courtesy of MMU Textile Lab)

Laminated or coated or heavy multi-layered fabrics that are intended for jackets, trousers, back pack, footwear (Cordura[®] Naturalle) are often subjected to this test to evaluate their resistance to abrasion. Three heavy weight woven fabrics that are intended for outer wear for jackets were randomly selected. Fabric 1 (282 g/m²), fabric 2 (375 g/m²) and fabric 3(245 g/m²). Fabric 1 is laminated at its back side; fabric 2 and 3 are coated fabrics. The standard load of 7.35 N was applied and an abrasant H18 (Non-resilient) vitrified surface that applied medium abrasive action.

Table 4 Percentage change in mass				
Abrasion resistance		Fabric 1 (yellow)	Fabric 2 (green)	Fabric 3 (camo)
Initial weight (mg)		2530 mg	3260 mg	2080 mg
Average rate of loss in mass	100 cycles	4.74% (2410 mg)	1.84 % (3200 mg)	2.40 % (2030 mg)
	200 cycles	5.13% (2400 mg)	3.37% (3150 mg)	2.88 % (2020 mg)
	300 cycles	6.32 % (2370 mg)	5.52 % (3080 mg)	5.05 % (1980 mg)

	400 cycles	7.50% (2340 mg)	6.44 % (3050 mg)	5.76 % (1960 mg)
	500 cycles	7.90% (2330 mg)	8.58 % (2980 mg)	6.25% (1950 mg)
	Average	6.32 %	5.15%	4.46%



Figure 8 Taber abrasion test samples

It could be observed from Table 4 that in the case of fabric1, the specimen endured surface distortion between 300-500 cycles and rate of loss of mass is higher especially at 500 cycles. At 500 cycles, the top surface of the fabric had been lost leaving the coating exposed. In the case of fabric 2, the rate of loss of mass varied and the fabric surface was distorted and loss of colour was also noted. However, the fabric structure remained unaltered. The thickness of fabric 3 was less compared to remaining samples and fabric surface was distorted with change in colour and thread bare was also noted at 500 cycles. The samples are illustrated in Figure 8 which shows the material at the start and at the end of 500 cycles.

Fabric pilling

Pilling is a fault commonly observed in knitted woollen goods or fabrics made from soft twist yarns. Pilling occurs when rubbing action in wear causes loose fibres from surface



Figure 10 Preparation of sample for pilling test

(Author's image)

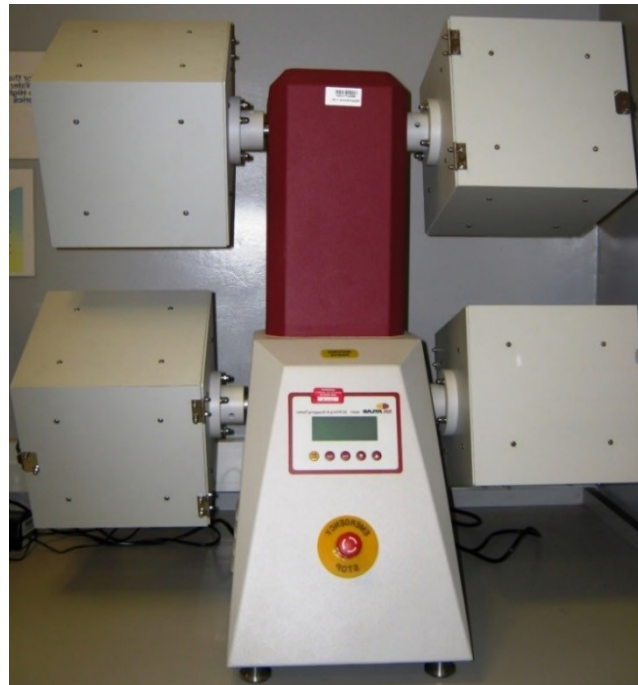


Figure 11 Pilling box used to measure pilling resistance of fabrics

(Image courtesy of MMU Textile Lab)



Figure 12 Pilling assessment photographs

(Image courtesy of MMU Textile Lab)

Table 5 Visual Assessment: Fabric pilling		
Rating	Description	Notes
5	No change	No visible change
4	Slight change	Slight surface fuzzing
3	Moderate change	Exhibits fuzzing and/or pills
2	Significant change	Distinct fuzzing and/or pilling
1	Severe change	Dense fuzzing and/or pilling covering specimen.

Fabric handle in sportswear

In fashion industry, a number of personnel handle fabrics for its suitability to an end-use especially during manufacturing. Fabric handle is an individual’s response to touch when a fabric is handled. This could also refer to how a fabric drape. A number of subjective attributes have been used to refer fabric handle, for instance, smooth, rough, stiff, soft, crisp, silky, etc. Subjective grading is often not consistent, as what a person perceives as

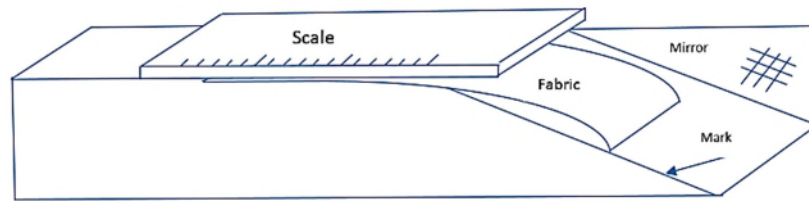


Figure 13b. Close-up view here >

(Image courtesy of MMU Textile Lab)

Flexural rigidity (G) is calculated using the equation given below which determines the resistance of fabrics to bending by external forces. Flexural rigidity, $G = 0.1 MC^3$ where, M is mass per unit area in g/cm^2 and C is bending length in cm. Flexural rigidity is reported in mg.cm.

Fabric drape

Drape is a characteristic of a material to freely fall or hang over a three dimensional form. This parameter is important to determine fabric handle. In this method, (BS 5058: 1973), a fabric specimen of diameter 30 cm for medium fabrics (24 cm diameter for limp fabrics; 36 cm diameter for stiff fabrics) is placed on a circular disc (Figure 14) and the specimen is allowed to drape on its own weight. Using a light source placed beneath the specimen, a shadow of the draped specimen is cast on a paper ring (Figure 14b). The outline of the fabric shadow traced on the paper (of known mass, W_0) and traced paper ring is weighed (W_1). Drape coefficient is calculated as the percentage of the total area of the paper ring obtained by vertically projecting the shadow of the draped specimen.

A fabric with a drape coefficient closer to 100% is stiffer, whilst a fabric with drape coefficient closer to zero is pliable and more drapable. In woven fabric grain affects

drape in garments. Figure 1 illustrates a plain single jersey fabric whose drape coefficient was 20% indicating a limp fabric.



Figure 14a Drape meter

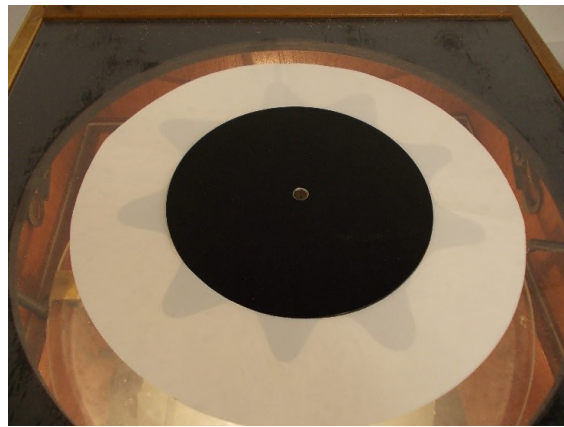


Figure 14b Shadow of the draped specimen

(Image courtesy of MMU Textile Lab)

$$\text{Drape coefficient (\%)} = \frac{W_1}{W_0} \times 100$$

where, W_1 is weight of paper in the shadow region (g); W_0 is weight of paper ring (g). The experiment is repeated for six specimens and average is reported and is carried out in standard atmospheric conditions (BS 1051), i.e. a relative humidity of 65 ± 2 % and a temperature of 20 ± 2 °C. Limp fabrics are difficult to handle during the garment manufacture mainly during fabric laying-up, spreading and stitching. Stiff fabrics are difficult to form body form shapes particularly shoulder, arm hole, etc.

Fabric stretch and recovery

Importance of stretch and recovery was highlighted in Chapter 7. During wearing and removal of knitwear or certain sportswear stretch is an important parameter. BS 4294:1968 is commonly used to determine the stretch and recovery of woven and knit fabrics using the apparatus Fryma fabric extensometer. It consists of two jaws (75 mm wide), a fixed and a movable jaw capable of holding the specimen without slippage (see

wicking. Performance of fabrics are affected by a combination of fibre properties and composition, yarn formation, and fabric structure (see Chapter 3).

In sportswear, particularly athletic apparel fabrics chosen should have quick drying and good wicking property to handle excess sweat produced by the body. Zhou et al. (2014) highlighted that fibres with greater surface area has better wicking. Zhou et al. reported the comfort properties of six interlock knitted fabrics made from various blends of chemically and physically modified polyester filament (PET) with trefoil cross section and cotton fibres. Modified polyester fibre had enhanced moisture management particularly 35% PET and 65% cotton blend knitted fabric.

Wicking and its effect on fabric comfort

Wicking is the movement of liquid by capillary action, provided that the liquid wets the assembly of fibres so that it can move from its source to some distance against the gravitational forces by occupying the available capillary spaces. The smallest capillary possess greater capillary forces, hence the wickability. Wicking depends upon the surface properties of fibres, surface area, density, thickness and the capillary path through the fabric. Moreover, the rate of wicking is different along warp (wale) than weft (course) direction.

Moisture Management Tester (MMT)

The moisture management tester was developed by Hong Kong Polytechnic University and SDL Atlas Textile Testing Solutions to determine the dynamic liquid transport properties of knitted and woven fabrics. The test method is depends on the change in the contact electrical resistance of fabric during moisture transport (Yao et al., 2008). The apparatus is used to measure the liquid transport in multiple directions. MMT consists of

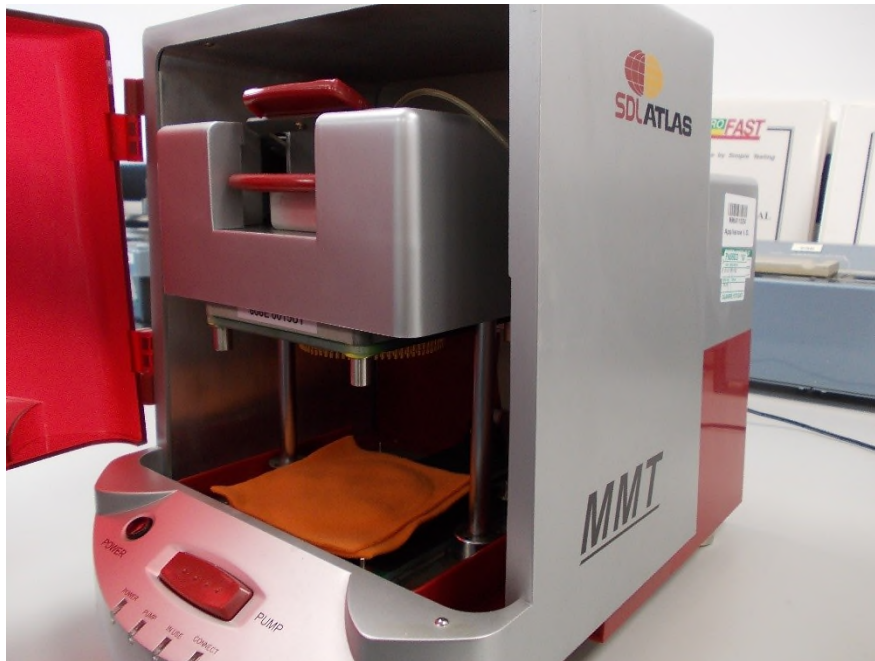


Figure 16 Moisture Management Tester (MMT)

(Image courtesy of MMU Textile Lab)

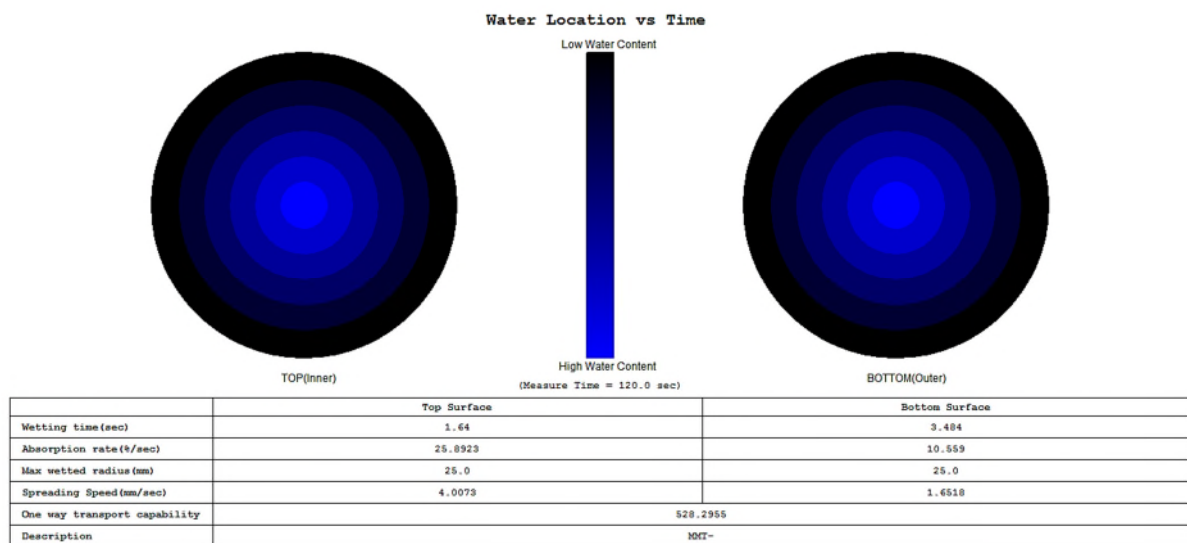


Figure 17 MMT output – water location Vs time

(Image courtesy of MMU Textile Lab)



Figure 19 Permetest

(Image courtesy of MMU Textile Lab)

The results are presented in the equipment as well as via a software connected to a PC. The image below (Figure 20) illustrates a typical output from the Permetest. The instrument also allows to record the test and calculate simple statistical test, mean, median and standard deviation. The relative water vapour permeability (RWVP) is determined using the formula:

$$RWVP = \frac{\text{Heat lost with the fabric placed on measuring head } (u_1)}{\text{Heat lost with bare measuring head } (u_0)} \times 100$$

Table 6 Outcomes from Permetest			
Type of material	Water vapour resistance (m ² Pa W ⁻¹)	Relative water vapour permeability (%)	Dry thermal resistance (Km ² W ⁻¹)
Base layer knit 1 (Skins)	3.7	72.8	2.8
Base layer knit 1 (SUD)	4.0	75.3	2.8
Fleece	7.3	57.1	7.9
Coated fabric (grey woven fabric)	8.5	54.0	Not applicable as the fabric is very thin
Outer layer	4.2	67.1	Not applicable as the fabric is very thin

Table 6 highlights the results of widely used sports fabrics (base layer, fleece, coated fabric and outer layer) including dry thermal resistance, relative water vapour permeability and water vapour resistance.

Thermal resistance of fabrics

Celcar (2010) reported that as the fabric thickness increase, water vapour resistance and thermal resistance of the fabrics also increases.

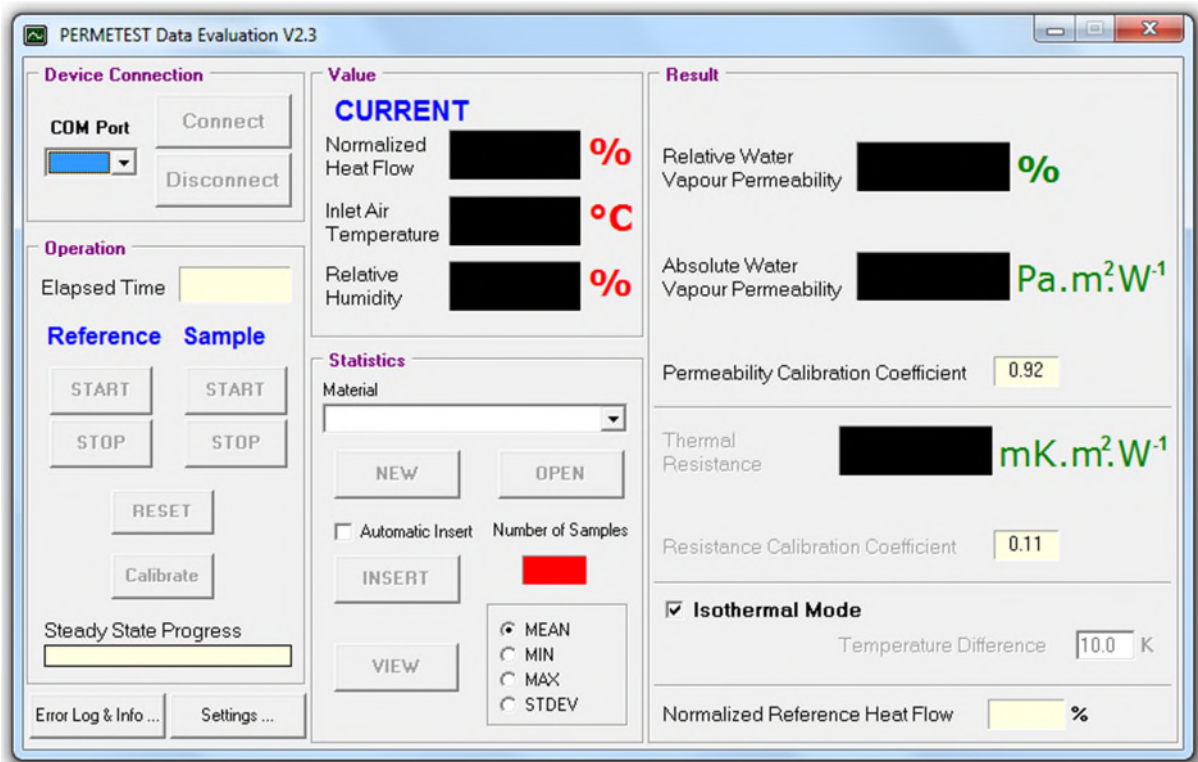


Figure 20 Typical output from Permetest

Fabric specifications and interpreting results

Table 7 presents the experimental values relating to fabric's physical characteristics, durability, aesthetics and fabric comfort which are some of the vital pre-requisites for a fabric to find its usage in sportswear and performance clothing. The woven material made of 100% polyester is a light weight fabric intended for mid-layer soft shell jackets that is water repellent whilst the knitted fabric is medium weight fabric with a water repellent finish intended to be used as a tops for men and women. The woven fabric has a 1/1 plain weave structure in which both sides of the fabric appear similar and the knitted fabric is a single jersey, which possess a distinct technical face and back. It is made of polyester and lycra. Fabric thickness of woven fabric is less than 0.20 mm whilst the knitted fabric is 0.66 mm. Fabric thickness plays an important role during joining of fabrics especially in maintaining the pressure at the presser foot of a sewing machine. Fabric cover factor determines the extent to which a set of yarn covers the area of a fabric. The warp cover factor 13.5 and weft cover factor 6.3 indicates that area covered

TABLE 7 Example fabric specification

Properties		01 Woven fabric		02 Knitted fabric		
Fabric physical characteristics	Area density (g/m ²)	115		255		
	Bulk density (g/cm ³)	0.64		0.39		
	Thickness (mm)	0.18		0.66		
	Fabric cover (K) factor/stitch density	13.5 + 6.3		11.0		
	Fabric structure	1/1 plain weave		Single jersey		
	Fibre composition (%)	100% polyester		Polyester/lycra		
	Yarn count (tex)	Warp 5.0 Weft 12.0		20.0		
Fabric density	Woven fabric (ends per inch x picks per inch)	100 x 72		NA		
	Knitted fabric (courses per cm and wales per cm)	NA		22 x 15		
Durability	Fabric pilling (grade)		5		4	
	Abrasion resistance @ 10,000	Change in colour	Very minor change		Slight increase in shade	
		Rate of loss of mass	Nil		0.01	
		Thread bare	No		No	
Aesthetics	Fabric handle stiffness Flexural rigidity (µNm) Bending modulus (N/m ²)	Warp 12.0 0.4	Weft 4.3 0.1	Wales 2.8 0.1	Courses 0.5 0	
	Fabric drape coefficient (%)	55.3		17.41		
Comfort	Moisture transport (wicking)	Water proof		Water repellent fabric (see fabric finger print)		
	Stretch and recovery Mean extension Mean residual extension	Not applicable		Wale 79% 2.66%	Courses 146% 6.75%	
	Water vapour resistance (Pa m ² /W)	11.7		4.3		

applications which is targeted on low to medium market where the garment usage is less frequent.

Summary

Sportswear and functional clothing sector drives innovation, particularly in the area of fabric and accessories. Textile testing had been instrumental in determining the performance of these innovative high performance materials. In addition, different type of sporting activity requires different performance and the choice of fabrics vary. For example, an outdoor cycling kit requires a fabric that is light weight, possess stretch, and offers thermal balance next to the skin. However, a ski wear requires good thermal insulation to protect the wearer from severe cold condition. The chapter highlighted the importance of fabric evaluation in determining the fit for purpose using various textile parameters including physical characteristics, durability, aesthetics and comfort. Each test parameter was referred to British standards and a brief description of the test method was presented along with the visual illustration of the test equipment. In addition, example results were also presented to enable the reader to understand the outcomes and its relevance in fabric assessment (grade). The chapter also emphasized the importance of physical characteristics of fabric on its performance. In the case of performance assessment various test equipment including Taber abrasion tester, pilling box, stiffness tester, drape meter, moisture management tester, Fryma extensiometer and Permetest was discussed. The final section which outlined the fabric specification with example results between woven and knitted fabrics will enable the reader to interpret test results and comprehend how performance is assessed using the outcomes. The test methods discussed in the chapter were presented in the context of evaluating fabrics used in performance clothing and will serve as an invaluable resource to professionals and novice alike.

11. BS EN ISO 5084, (1997), Determination of thickness of textiles and textile products
12. BS EN ISO 12947-2 (1998), Textiles. Determination of the abrasion resistance of fabrics by Martindale method.
13. BS EN ISO 5470-1, (1999), Determination of abrasion resistance of fabrics: Taber abrader
13. BS EN ISO 12945-1: (2001), Determination of fabric propensity to surface fuzzing and to pilling - Pilling box method
14. BS 3356, (1990), Method for determination of bending length and flexural rigidity of fabrics
15. BS 5058, (1973), Method for the assessment of drape of fabrics
16. BS 4294, (1968), Methods of test for stretch and recovery properties of fabrics
14. McQueen, R.H., Batcheller, J.C., Mah, T., Hooper, P.M., (2013), Development of a protocol to assess fabric suitability for testing liquid moisture transport properties, Journal of the Textile Institute. 2013, Vol. 104 Issue 8, p900-905
15. Das B., Das, A., Kothari, et al., (2009), Moisture flow through blended fabrics – effect of hydrophilicity, Journal of Engineered fibres and fabrics, Vol. 4, Issue 4, pp-20-28
16. Özdil, N., Kayseri, Ö. G., Mengüç, G.S., (2012), Analysis of abrasion characteristics in Textiles, Abrasion resistance of materials, Eds. Adamiak, M., ISBN: 978-953-51-0300-4 www.intechopen.com