



*Citation for published version:*

Brullot, W, Strobbe, R, Bynens, M, Bloemen, M, Demeyer, PJ, Vanderlinden, W, De Feyter, S, Valev, VK & Verbiest, T 2014, 'Layer-by-Layer synthesis and tunable optical properties of hybrid magnetic-plasmonic nanocomposites using short bifunctional molecular linkers', *Materials Letters*, vol. 118, pp. 99-102.  
<https://doi.org/10.1016/j.matlet.2013.12.057>

*DOI:*

[10.1016/j.matlet.2013.12.057](https://doi.org/10.1016/j.matlet.2013.12.057)

*Publication date:*

2014

*Document Version*

Peer reviewed version

[Link to publication](#)

## University of Bath

### General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

### Take down policy

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

## **Layer-by-Layer synthesis and tunable optical properties of hybrid magnetic-plasmonic nanocomposites using short bifunctional molecular linkers.**

Ward Brullot,\* Rik Strobbe, Maud Bynens, Maarten Bloemen, Pieter-Jan Demeyer, Willem Vanderlinden, Steven De Feyter, Ventsislav K. Valev and Thierry Verbiest

W. Brullot, R. Strobbe, M. Bynens, M. Bloemen, P.J. Demeyer, Dr. W. Vanderlinden, Prof. S. De Feyter, Prof. T. Verbiest  
Molecular Imaging and Photonics, Department of Chemistry, KU Leuven, Celestijnenlaan 200D, Box 2425, 3001 Heverlee (Leuven), Belgium  
Phone: +32 16 3 27154  
E-mail: ward.brullot@fys.kuleuven.be

Dr. V.K. Valev  
Cavendish Laboratory, Department of Physics, University of Cambridge, JJ Thomson Avenue, Cambridge, CB30HE, United Kingdom

### **Abstract**

Spurred by research in magnetoplasmonics, plasmon-enhanced magneto-optical effects and active plasmonics, the demand for hybrid magnetic-plasmonic nanoparticle-based materials of optical quality is high. Currently used synthesis methods involve possibly interfering polymer media or polyelectrolyte interlayers, grooved supports or non-transparent substrates. To obtain homogeneous, partially transparent and polymer/polyelectrolyte-free magnetic-plasmonic nanocomposites with angle-independent optical properties, we produced hybrid gold-magnetite and silver-magnetite nanocomposites by a novel Layer-by-Layer synthesis using short bifunctional molecular linkers on glass substrates. Resulting nanocomposites had high nanoparticle filling fractions and showed tunability of the plasmon wavelength over a very broad spectral range by changing composite thickness through the number of added nanoparticle layers. The angle-independence of optical properties and the abilities to switch the plasmonic material and to tune the plasmon resonances of the magnetic-plasmonic composites make these materials a unique platform for magnetoplasmonic research.

**Keywords:** nanocomposite, layer-by-layer, magnetic-plasmonic, nanoparticle, tunable optical property

### **1. Introduction**

Research into nanoparticle-based magnetoplasmonics, active plasmonics and plasmon-enhanced magneto-optics has strongly intensified. [1–5] Such research holds promise for both unraveling fundamental questions about magnetic-plasmonic interactions as well as applications in sensing, optical switching and optical components fabrications. The ability to

reliably synthesize high optical quality magnetic-plasmonic nanocomposites with high nanoparticle filling fractions and without introducing unnecessary background signal facilitates experiments and is a prerequisite to interpret results correctly. Furthermore, for many experiments or applications, such as optical Faraday isolators, (partial) transparency is a must.[3,6] Previously, nanocomposites were synthesized on non-transparent or grooved substrates, [5] using polymers as dispersion medium for spin-coated or drop-casted samples or polyelectrolyte interlayers in Layer-by-Layer synthesis. [7–9] Polymers and polyelectrolytes have the disadvantages that nanoparticle filling fractions are inherently limited and that they possibly introduce undesired background signal, chemical incompatibility and interfere with signal acquisition. Furthermore, such molecules introduce an undefined and often large distance between adjacent nanoparticles, impeding correct interpretation of results. Here we present a versatile Layer-by-Layer synthesis method on glass substrates using short bifunctional, i.e. with two functional groups, molecular linkers that results in homogeneous samples with very high nanoparticle filling fractions and controlled distances between adjacent particles. Tunable plasmon properties, of both silver- and gold-magnetite nanocomposites, over a broad spectral range combined with angle-independent optical properties and a variable composite thickness make these high quality composites an ideal platform for magneto-plasmonic research.

## **2. Materials and methods**

### **2.1. Materials**

All obtained chemicals were used without further purification. Anhydrous iron(III)trichloride (98%), n-octylamine (99+%) and ethanediol (for analysis) were purchased from Acros Organics. (3-Aminopropyl)trimethoxysilane (APTMS) (97%) was obtained from ABCR. Gold(III)chloride trihydrate (99.9+%), Sulfuric acid (95-97%) and Nochromix cleaning agent were purchased from Sigma-Aldrich. Acetic acid (100%) was bought from VWR, silver nitrate from UCB, tri-sodium citrate (99.5+%) from Chem-Lab and sodium borohydride (98+%) from Janssen Chemica.

### **2.2. Methods**

*Iron oxide nanoparticle synthesis* - Iron oxide nanoparticles were synthesized using an in-house modified force hydrolysis method.[10] XRD experiments showed that the dominant iron oxide phase was magnetite (Supp. info).


*Functionalization of iron oxide nanoparticles* – 300mg of n-octylamine coated nanoparticles were dispersed in 300ml methanol using an ultrasonic bath. Then 3ml APTMS was added, together with 3 drops of acetic acid and the mixture was further sonicated for 2h. After washing with acetone through magnetically assisted precipitation and drying in vacuo, a powder of amine-functionalized iron oxide nanoparticles was obtained. These functionalized nanoparticles could then be redispersed in MeOH in a desired concentration using ultrasonication. Functionalized particles had a size of  $7.98 \pm 2.4$ nm and show superparamagnetic behavior with a saturation magnetization of 18.88emu/g (Supp. info).

*Synthesis of metal nanoparticles* - For the gold colloid synthesis, a method based on an aqueous citrate reduction was employed.[11] After synthesis, a deep red colored dispersion was obtained. This dispersion was diluted 5x with MilliQ water before use to obtain a final Au concentration of 0.2mM. Au nanoparticles had a size of  $9.25 \pm 1.31$ nm and exhibited a clear plasmon resonance centered on 530nm (Supp. info). Silver nanoparticles were produced using a method based on an aqueous sodium borohydride reduction in presence of citrate capping molecules. [12] The pale yellow colored dispersion was used without further dilution. Ag nanoparticles showed a plasmon resonance at 400nm and had a size of  $9.59 \pm 0.27$ nm as measured by TEM (Supp. info). Final Ag concentration was 0.15mM.

*Synthesis of nanocomposites* (Figure 1A-D) - Synthesis started by cleaning glass microscope slides (16x16mm) with NoChromix cleaning solution (7g/100ml NoChromix in MilliQ water, add 100ml sulfuric acid 97%) for 1h. These cleaned substrates were then functionalized with APTMS (1vol% in MeOH, 1h) and rinsed with MeOH and water. [11] A first metal nanoparticle layer was added by putting the functionalized substrate in 10ml of a metal NP dispersion while shaking (350rpm) for 1.5h and rinsing with water and MeOH afterwards. By putting the sample in 10ml of a 0.3mg/ml dispersion of functionalized iron oxide nanoparticles in MeOH for 1h, a layer of these nanoparticles could be added on top of the gold nanoparticle layer. After rinsing the sample with methanol and water, adding extra nanoparticle layers was possible by repeating the previous steps. The nature of the Layer-by-

Layer synthesis allows for homogeneous coating of large-area substrates.

*Characterization* – Nanoparticles and composites were characterized using transmission electron microscopy (80kV Zeiss EM-900, 300 mesh Formvar on copper grids as substrate), scanning electron microscopy (XL30 ESEM FEG microscope), room temperature X-ray diffraction experiments (horizontal Geigerflex diffractometer in Bragg-Brentano geometry reflection mode, mounted on a Rigaku RU-200B rotating Cu-anode with an output power of 4kW), vibrating sample magnetometry (300K, Oxford instruments VSM Maglab), scanning force microscopy (multimode 8 from Bruker using an AC240TS tip) and UV-visible absorbance measurements (Perkin Elmer 900).

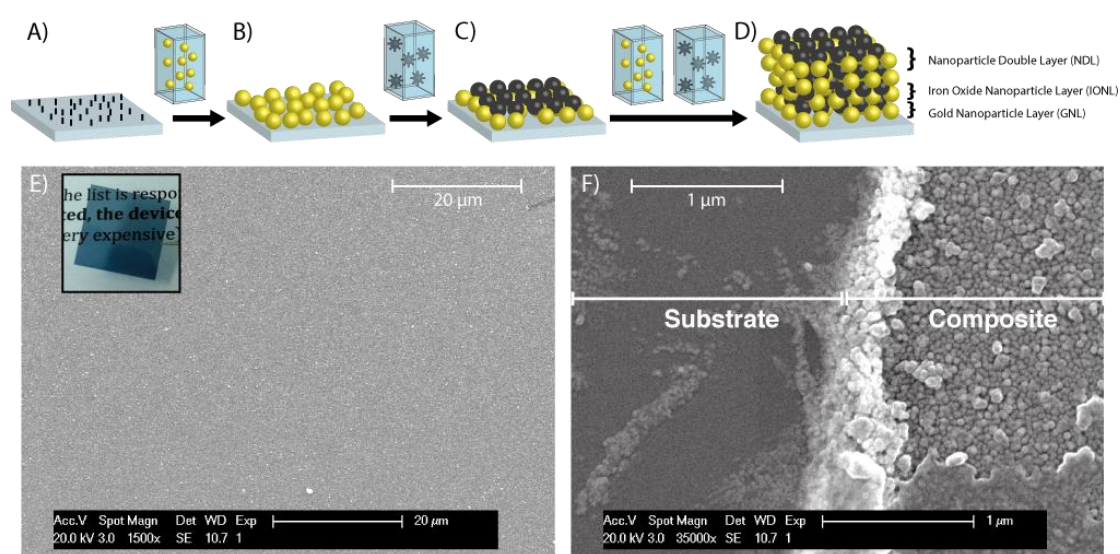

**Figure 1:** Layer-by-Layer synthesis procedure for used in this work (A-D), a photograph of a 5 ND Au-Mag sample above a text (inset E) and large area (E) and zoomed-in (F) scanning electron microscopy images of a Au-Mag 5 ND sample.

### 3. Results and discussion

Au-magnetite nanocomposites with different numbers of nanoparticle double layers (NDLs), which are one gold and one iron oxide nanolayer combined (Figure 1D), were synthesized. A 5 ND Au-magnetite composite on a glass support is blue colored when viewed perpendicular and shows gold reflectivity if tilted. The sample is homogeneous, showing no large aggregates or defects (Figure 1E, inset). Scanning electron microscopy (SEM) images confirm homogeneity over at least 100 micrometer and show a relatively smooth surface (Figure 1E). When zoomed in on the same sample next to a scratch, a clear height difference between substrate and sample can be observed (Figure 1F).


Due to the strong bonding between the silane group and the iron oxide nanoparticles on

the one and the amine group of the linker molecule and the gold nanoparticles on the other hand, the samples are robust and do not release material in the storage solvent.[10,11] Stored in methanol, the composites were stable for at least 1 year as evidenced by UV-visible absorbance spectroscopy. Ultrasonic treatment of 5 NDL Au-magnetite composite does not result in any change in the UV-visible absorbance spectrum, indicating the stability and robustness of the samples. Reproducibility of the method is high (Sup. info).

UV-Visible absorbance spectra of a 1 NDL Au-magnetite nanocomposite shows a plasmon resonance peak at approximately 520nm, corresponding to that of dispersed gold nanoparticles (Figure 2). By adding NDLS, a second redshifted plasmon peak due to plasmonic near-field coupling arises. When gold nanoparticles interact optically, the plasmon modes couple, resulting in redshifts of the plasmon wavelength.[13] The observed significant redshift of the plasmon wavelength in the synthesized samples from 530 nm to 650 nm indicates that gold nanoparticles are interacting strongly and thus are close to each other. Presence of magnetite nanoparticles is evidenced by the absorbance peak due to intervalence charge transfer (IVCT) centered around 385nm.[14] A linear relationship between the absorbance maximum and the number of layers was found (Figure 3), evidencing the Layer-by-Layer synthesis of the composites. The same linear relationship was found for the absorbance at the iron oxide NP IVCT and the Au LSPR and coupled plasmon modes as a function of NDLS (Sup. Info). Changes in the UV-Visible absorbance spectra as a function of added NDLS can be visually observed as a change in color of the Au-magnetite composites from reddish pink over blue to dark blue with increasing number of NDLS. Use of glass substrates allows for partial transparency of the composites in the UV-Visible, enabling magnetoplasmonic and magneto-optical measurements and applications.


The absorbance properties of the composites, including the plasmon properties, are largely independent of the sample angle relative to the incoming light beam (Sup. info), which is in stark contrast to the strong angle dependence of propagating plasmon resonance excitation of continuous bulk gold layers.[3,15] Lyon *et al.* observed that the strict angle requirements for exciting surface plasmon modes in continuous gold layers can be partially lifted by covering the surface with gold colloids.[16] In the synthesized composites, only spherical gold nanoparticles are responsible for the plasmon behavior, which fully alleviates

the incident angle requirements. Angle independent optical properties can be a great advantage for (magneto-)optical experiments and applications.

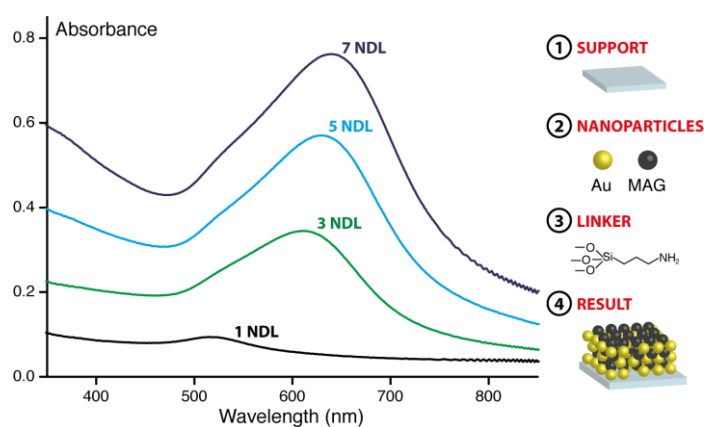


**Figure 2: UV-Visible absorbance spectra of Au-Mag composites show a redshift of the localized surface plasmon band as a function of added NDL. The presence of magnetite nanoparticles is indicated by the resonance at 385nm.**

The average thickness of the Au-magnetite nanocomposites, as measured by scanning force microscopy (Sup. info), increases linearly with the number of added NDLs. This confirms the Layer-by-Layer like construction (Figure 3). A thickness of  $13.2 \pm 7.3$  nm was measured for a 1 NDL sample. When fitted with a linear equation ( $R^2 = 0.99$ ), the average increase of thickness for 1 NDL after the first NDL is  $7.3 \pm 0.4$  nm. These data are consistent with structures in which, resembling a closed-packed material, the nanoparticles of the next nanoparticle layers occupy the cavities in the previous and a high quality stacking of layers is obtained (graphics Figure 3). Structures with such a packed arrangement of nanoparticles allow a high nanoparticle filling fractions or occupied volume fractions up to, in the case of fully close-packed arrangements, a theoretical maximum of 74%. [17] The number of layers that can be added is in principle unlimited, although some quality loss is likely with very high layer numbers. Up until 10 NDLs no loss of optical quality was observed (Sup. Info). Such structures with high nanoparticle filling, and absence of polymer, polyelectrolyte or other possibly interfering interlayers and of high optical quality are well suited for studying plasmon-enhanced effects or investigate fundamentals of active plasmonics.

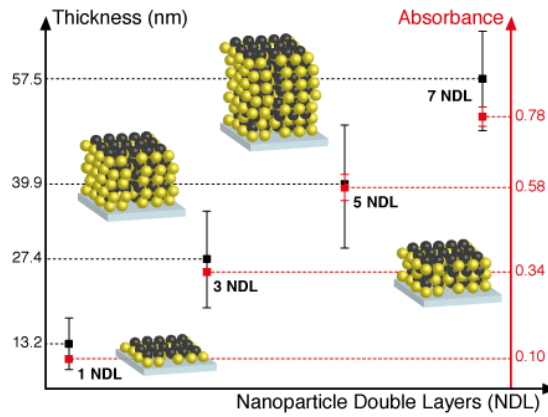

**Figure 3:** Both the thickness, as measured by scanning force microscopy, and the absorbance at maximum intensity increase linearly with increasing number of nanoparticle double layers. These results demonstrate the Layer-by-Layer construction of the Au-Mag composites.

Using silver instead of Au nanoparticles in the Layer-by-Layer synthesis also results in stable and homogeneous nanocomposites. The UV-visible absorbance spectra of such composites show only 2 absorbance bands (Figure 4). One broad band is centered on 400nm due to the overlap of the IVCT and plasmon resonances of magnetite and single Ag nanoparticles. When more than one NDL is added, a strongly redshifted plasmon band at around 550-575nm occurs due to near-field optical coupling of Ag nanoparticles. Same as for the Au-based composites, a linear relationship between the absorbance maximum and the number of layers was found (Sup. Info), evidencing the Layer-by-Layer synthesis of the composites.

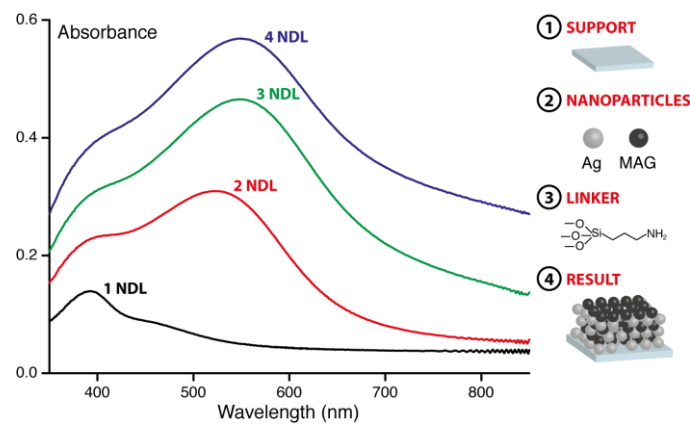

**Figure 4:** A strong redshift of the plasmon wavelength is observed in UV-Visible absorbance spectra of Ag-Mag composites. The resonance of magnetite nanoparticles (385nm) overlaps with the LSPR of Ag NP.

The abilities to switch the plasmonic material and to tune the plasmon resonances of the magnetic-plasmonic composites over a very broad UV-visible spectral range as a function of added NDLs provides a unique platform for magnetoplasmonic research.



#### 4. Conclusion

Magnetic-plasmonic nanocomposites of optical quality and variable thickness based on Au or Ag and magnetite nanoparticles were reproducibly synthesized on glass substrates by a polymer/polyelectrolyte-free Layer-by-Layer method using short bifunctional molecular linkers. High nanoparticle filling fractions in well-stacked multilayers were obtained. Plasmon resonance wavelengths could be tuned over a very broad spectral range by changing the plasmonic material or the number of added nanoparticle layers. Optical properties proved angle-independent. Such high quality composites without possibly interfering interlayers provide excellent materials for research into plasmon influenced (magneto-)optical effects, active plasmonics through magnetism or possibly magnetoresistance effects.

#### 5. Acknowledgements

The authors thank Prof. J. Billen of the KU Leuven for help with the transmission electron microscopy images and the Department of Metallurgy and Materials Engineering of the KU Leuven for access to Scanning Electron Microscopy. The authors are grateful to M. Vanbel and S. Vandendriessche of the Division Molecular Visualization and Photonics of the KU Leuven for inspiring discussions on the topic and critical reading of the manuscript. W. Brullot and M. Bloemen are grateful for a Ph.D. grant by the Agency for Innovation by Science and Technology (IWT) Flanders. P.J. Demeyer thanks the Department of Chemistry of the KU Leuven for a FLOF Grant. V.K. Valev acknowledges financial support from the EPSRC grant EP/G060649/1. T. Verbiest and S. De Feyter acknowledge support from the KU Leuven (GOA Research Grant). T. Verbiest acknowledges the FWO-Vlaanderen for financial support through research project G.0C02.13N.

#### 6. References

- [1] Dani RK, Wang H, Bossmann SH, Wysin G, Chikan V. Faraday rotation enhancement of gold coated Fe<sub>2</sub>O<sub>3</sub> nanoparticles: Comparison of experiment and theory. *J Chem Phys* 2011;135:224502.
- [2] Jain PK, Xiao Y, Walsworth R, Cohen AE. Surface plasmon resonance enhanced magneto-optics (SuPREMO): Faraday rotation enhancement in gold-coated iron oxide nanocrystals. *Nano Lett* 2009;9:1644–50.
- [3] Armelles G, Cebollada A, García-Martín A, González MU. Magnetoplasmonics: Combining Magnetic and Plasmonic Functionalities. *Adv Opt Mater* 2013;1:10–35.
- [4] Armelles G, Cebollada A. Magneto-optical Properties of Core–Shell Magneto-plasmonic Au–Co<sub>x</sub>Fe<sub>3-x</sub>O<sub>4</sub> Nanowires. *Langmuir* 2012:4–7.
- [5] Caminale M, Anghinolfi L, Magnano E, Bondino F, Canepa M, Mattera L, et al. Tuning the magneto-optical response of iron oxide nanocrystals in Au- and Ag-based plasmonic media. *ACS Appl Mater Interfaces* 2013;5:1955–60.
- [6] Chin JY, Steinle T, Wehler T, Dregely D, Weiss T, Belotelov VI, et al. Nonreciprocal plasmonics enables giant enhancement of thin-film Faraday rotation. *Nat Commun* 2013;4:1599.

- [7] Pichon BP, Louet P, Felix O, Drillon M, Begin-colin S, Decher G. Magnetotunable Hybrid Films of Stratified Iron Oxide Nanoparticles Assembled by the Layer-by-Layer Technique. *Chem Mater* 2011;23:3668–75.
- [8] Wouters J, Lebedev OI, Van Tendeloo G, Yamada H, Sato N, Vanacken J, et al. Preparing polymer films doped with magnetic nanoparticles by spin-coating and melt-processing can induce an in-plane magnetic anisotropy. *J Appl Phys* 2011;109:076105.
- [9] Vandendriessche S, Valev VK, Verbiest T. Characterization of magnetization-induced second harmonic generation in iron oxide polymer nanocomposites. *Appl Opt* 2012;51:209–13.
- [10] Brulot W, Reddy NK, Wouters J, Valev VK, Goderis B, Vermant J, et al. Versatile ferrofluids based on polyethylene glycol coated iron oxide nanoparticles. *J Magn Magn Mater* 2012;324:1919–25.
- [11] Keating CD, Musick MD, Keefe MH, Natan MJ. Kinetics and Thermodynamics of Au Colloid Monolayer Self-Assembly: Undergraduate Experiments in Surface and Nanomaterials Chemistry. *J Chem Educ* 1999;76:949.
- [12] Tejamaya M, Römer I, Merrifield RC, Lead JR. Stability of citrate, PVP, and PEG coated silver nanoparticles in ecotoxicology media. *Environ Sci Technol* 2012;46:7011–7.
- [13] Jain PK, El-Sayed M a. Plasmonic coupling in noble metal nanostructures. *Chem Phys Lett* 2010;487:153–64.
- [14] Fontijn WFJ, Zaag PJ Van Der, Devillers MAC, Brabers VAM, Metselaar R. Optical and magneto-optical polar Kerr spectra of Fe<sub>3</sub>O<sub>4</sub> and Mg<sup>2+</sup>-orAl<sup>3+</sup>-substituted Fe<sub>3</sub>O<sub>4</sub>. *Phys Rev B* 1997;56:5432–42.
- [15] Gwon HR, Lee SH. Spectral and Angular Responses of Surface Plasmon Resonance Based on the Kretschmann Prism Configuration. *Mater Trans* 2010;51:1150–5.
- [16] Lyon LA, Pen DJ, Natan MJ. Surface Plasmon Resonance of Au Colloid-Modified Au Films : Particle Size Dependence. *J Phys Chem B* 1999:5826–31.
- [17] Hales TC, Ferguson SP. The Hales-Ferguson Proof. In: Lagarias JC, editor. *The Kepler Conjecture*, Springer; 2011.