



Citation for published version:

Shokrani Chaharsooghi, A, Dhokia, V & Newman, S 2018, 'Energy Conscious Cryogenic Machining of Ti-6Al-4V Titanium Alloy', Proceedings of the Institution of Mechanical Engineers, Part B: Journal of Engineering Manufacture, vol. 232, no. 10, pp. 1690-1706. <https://doi.org/10.1177/0954405416668923>

DOI:

[10.1177/0954405416668923](https://doi.org/10.1177/0954405416668923)

Publication date:

2018

Document Version

Peer reviewed version

[Link to publication](#)

Shokrani, A. Dhokia, V. Newman, ST., Energy conscious cryogenic machining of Ti-6Al-4V titanium alloy, Proceedings of the Institution of Mechanical Engineers, Part B: Journal of Engineering Manufacture, Volume: 232 issue: 10, page(s): 1690-1706. Copyright © 2016 IMechE. Reprinted by permission of SAGE Publications.

University of Bath

General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

Take down policy

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

Original article

Energy Conscious Cryogenic Machining of Ti-6Al-4V Titanium Alloy

Abstract

Manufacturing and in particular machining are responsible for a significant portion of global industrial energy consumption (25%). Previous research has shown that precise selection of cutting parameters can improve the energy consumption of machining processes. Cryogenic machining has attracted significant attention for improving the machinability of difficult-to-machine materials whilst also eliminating the environmental and health issues associated with the use of cutting fluids. Despite the advantages, there is a considerable research gap in cryogenic milling operations. This article investigates the effect of cryogenic cooling using liquid nitrogen in end milling of Ti-6Al-4V. A robust and rigorous methodology was developed and a series of machining experiments were conducted using a combination of cutting parameters repeated at dry, flood and cryogenic cooling environments. The investigations indicated that cryogenic cooling considerably reduces tool wear when compared to dry and flood cooling whilst allowing for using higher cutting speeds. The cutting tool used for cryogenic machining at 200m/min cutting speed, 0.03mm/tooth feed rate and 5mm depth of cut showed minimum flank wear. Furthermore, the investigations demonstrated that using the machine's coolant pump in flood cooling

resulted in higher power and energy consumption than dry and cryogenic cooling. This article clearly shows that higher material removal rates are required in order to minimise specific machining energy. Therefore, since cutting speed is limited in dry machining, cryogenic machining is the more favourable as higher cutting speeds can be used. Using cryogenic machining at 200m/min cutting speed resulted in an 88% reduction in energy consumption of the machine tool as compared to flood cooling at 30m/min whilst minimum tool wear (10µm) was detected. This clearly demonstrates the significant capabilities of cryogenic machining when compared with more conventional machining approaches.

Keywords:

Cryogenic machining; tool wear; CNC milling; power consumption; energy consumption.

1. Introduction

Industrialisation and economic development at the cost of environment has been a matter of concern for centuries¹. The increasing global power consumption and significant reliance on fossil fuels has raised serious concerns on meeting the demand, sustainability of the energy sources and their adverse impact on the environment. It has been reported that fossil fuels contribute to more than 80% of the global energy consumption² whilst the demand for energy is predicted to increase by 45% in 2030 as compared to 2011's levels³. Jacobson and Delucchi⁴ have proposed a large scale conversion towards clean, renewable and reliable energy sources as a way to overcome energy insecurity and increasing environmental issues such as climate change and air and water pollution. However, the prospect of energy for the foreseeable future is still based on fossil fuels and therefore energy efficiency and rationalisation of energy consumption is the most effective method of controlling increased environmental impacts of energy consumption³.

The manufacturing sector is responsible for almost 30% of the global energy consumption^{5, 6} with machining being one the key components of manufacturing. It has been reported that 99% of the environmental impact of machining is due to electrical energy consumption⁷. Knowing that energy consumption is the integral of power consumption over time, many researchers^{8, 9} have identified that machine tools' idle power consumption is the single largest component of machine tools' power consumption profile. Apostolos et al.^{10, 11} reported that in laser machining, a significant portion of machines' energy consumption is required for running the machine whilst only 5.7% of the total energy consumption is used for actual machining operation. The authors identified that in order to increase the efficiency in laser machining, higher laser powers and pulse are more

favourable as less time is required to heat the workpiece material and less energy is lost between each pulse¹⁰. In grinding operations, Salonitis^{12, 13} reported that almost 80% of the total effective power is drawn by the coolant pump and grinding wheel motor. Dahmus and Gutwoski¹⁴ reported that only 14.8% of the total machine tools' energy consumption is used for material cutting. Based on this, Salonitis and Ball⁵ proposed the following model for energy consumption in machining.

$$\text{Equation 1} \quad E_{total} = E_{process} + E_{peripherals}$$

where $E_{process}$ is the energy required for cutting the material and $E_{peripherals}$ is the energy consumed for running various components of the machine tool e.g. coolant pump, controls, etc. Interestingly, the $E_{peripherals}$ is not limited to material cutting processes e.g. machining and can be identified in other processes. For instance, Salonitis et al.¹⁵ found that only 30% of the total energy consumed in casting, is used for melting the material. Based on this, Mahrabi et al.¹⁶, Salonitis et al.¹⁵ and Dai and Jolly¹⁷ proposed a number of techniques which can significantly reduce the energy consumption in foundry and casting operations.

In conventional machining operations, Balogun and Mativenga¹⁸ identified that the cutting tool tip energy is considerably lower than the energy required for running the machine tool at no load. Therefore, they recommended minimising the idle time of the machine tool. Minimising the energy consumption of the machine tools when idle requires the use of more energy efficient equipment, improved design and a dematerialised machine frame/body¹⁸. On the one hand, energy conscious process planning can significantly reduce the energy consumption of a machine tool during material cutting^{9, 19}. Similarly, Avram and Xiouchakis²⁰ has identified excess operating time and unreasonable load on the machine tools' drives as two major ways of wasting energy which can be addressed in process

planning for machining operations. Aramcharoen and Mativenga⁹ have identified that the machine tools' energy demand is generally affected by tool wear and tool path which are generally overlooked. Various researchers^{21, 22} have identified the importance of considering tool wear/life and energy consumption, simultaneously. This is mainly due to the fact that cutting parameters not only affect the material removal rate but also have significant effect on tool wear²².

Whilst 80% of Ti-6Al-4V is used in aerospace and medical industries, it is described as the most used titanium alloy forming 50% of the global titanium metal production²³. Titanium and its variant alloys are one the most commonly used structural materials in aerospace and medical industries due to high specific strength, hardness and wear resistance²⁴. High cutting temperatures, short tool life and poor surface integrity are inherent characteristics that make machining titanium notoriously difficult. Due to the poor thermal conductivity, the heat generated at the cutting zone accumulates resulting in thermal softening of the cutting tool, adhesion and diffusion wear. It is reported that about 80% of the heat generated at the cutting zone is conducted through the cutting tool as compared to 50% for steels²⁵. Titanium is chemically reactive to all known cutting tool materials and welds onto the cutting tool resulting in chipping and premature tool failure²⁵.

In order to control the heat generated at the cutting zone, the generous use of cutting fluids at high pressures is typically recommended²⁶. However, cutting fluids and more specifically, water-miscible (soluble oil or emulsion) is considered as environmentally pollutant which requires constant maintenance and costly disposal²⁴. Moreover, many governmental organisations such as the UK Health and Safety Executive (HSE)²⁷, US Occupational Safety and Health Administration²⁸ and Canadian Centre for Occupational

Health and Safety²⁹ have identified cutting fluids as hazardous substances. Cutting fluids require routine maintenance to reassure their performance as bacterial and fungal growth can deteriorate their cooling/lubrication characteristics^{24, 30}. The presence of harmful chemicals such as formaldehyde and aromatic chains and the existence of dead bacterial masses such as endotoxin are proven sources of health hazards³¹. The exposure to cutting fluids is linked to a group of occupational health diseases ranging from asthma and dermatitis^{32, 33} to various types of cancer^{34, 35}.

Cryogenic cooling has been acknowledged as an alternative method for cooling in machining difficult-to-machine materials³⁶⁻³⁸. In this technique, a controlled amount of liquid nitrogen (LN₂) is sprayed into the cutting zone in order to remove the heat generated at the cutting zone and alter the material properties of the cutting tool and workpiece³⁹. Hong and Zhao⁴⁰ reported that cryogenic cooling in turning Ti-6Al-4V alloy has resulted in 5 times improvement as compared to flood emulsion cooling. Pusavec and Kopac⁴¹ reported that by using LN₂ coolant in turning titanium alloy, the cutting tool can withstand higher cutting speeds as compared to dry and flood cooling. This has resulted in up to 70% reduction in machining cost⁴¹. Nitrogen is a colourless and odourless gas which forms 78% of the air³⁶. It is lighter than air which disperses into air after application eliminating the requirement for cleaning and extra ventilation³⁸.

Pusavec and Kopac⁴² reported that cryogenic cooling allows for extended tool life and higher productivity in machining Inconel 718. Based on this, they found that considering the energy used for cleaning parts and chips from conventional coolants and manufacturing cutting tool inserts, cryogenic machining is more sustainable than conventional water-miscible flood cooling. Pusavec and Kopac⁴² identified 90m/min

cutting speed as a breaking point where the energy requirements for producing cutting tools surpasses the energy requirements for liquefying nitrogen. Fratila ⁴³ highlighted the importance of considering the power consumption for preparing cutting tools, circulating and preparing cutting fluids and cleaning parts/chips in conventional machining. Truesdale and Shin⁴⁴ stated that significant cost reduction can be achieved through using higher cutting speeds in cryogenic machining of nickel based alloys. Furthermore, Lu and Jawahir⁴⁵ used Process Sustainability Index (*ProcSI*) method to comprehensively analyse the sustainability performance of cryogenic machining. Lu and Jawahir ⁴⁵ identified that if applied correctly, cryogenic machining can significantly improve the sustainability performance of machining processes.

Although there is a considerable amount of research in cryogenic machining, Shokrani et al.³⁶ identified that a significant body of this research is concentrated on single-point cryogenic turning operations leaving a major research gap for multi-point intermittent operations such as milling. It is particularly important as unlike multi-point milling, single point cutting does not suffer from cyclic mechanical and thermal load. This research aims to bridge this gap by investigating the effect of cryogenic cooling on tool wear, power and energy consumption and specific machining energy in solid carbide end milling of Ti-6Al-4V titanium alloy as compared to conventional dry and flood cooling.

2. Methodology

In order to minimise the noise and ensure repeatability and reproducibility of the results, a systematic methodology was developed as shown in figure 1.

The investigations were based on comparing the effects of cryogenic cooling with conventional dry and flood cooling. The machining experiments were end milling operation using solid carbide cutting tools and were repeated three times to ensure repeatability of the process. An intact 12mm diameter solid tungsten carbide cutting tool with 3 flute and TiN-TiAlN coating with 12° rake angle and 38° helix angle was used for each machining experiment.

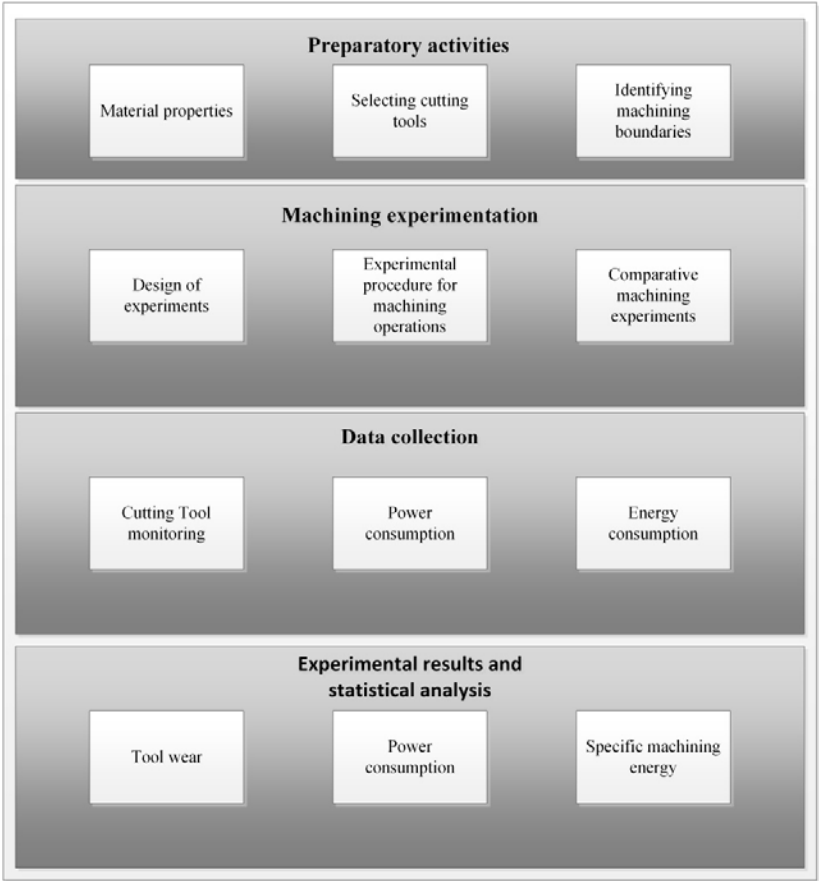


Figure 1, Methodology for empirical investigation

In order to investigate the effect of cryogenic cooling and fully capture the effect of various parameters, a hybrid design of experiment (DoE) was developed for experimentations, as illustrated in figure 2. Cutting speed, feed rate and depth of cut were identified as the major cutting parameters affecting the machining performance in end milling operations⁴⁶. Therefore, in this DoE, an L9 orthogonal array was used to generate a meaningful combination of cutting speed, feed rate and depth of cut. Three levels of maximum, minimum and medium were used for each parameter to generate the L9 DoE.

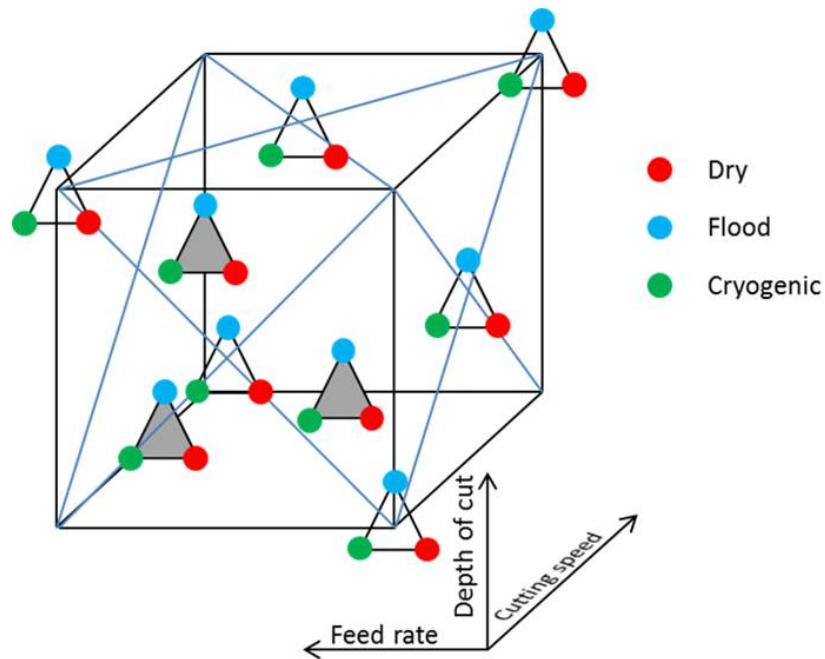


Figure 2, L9 design of experiment with repetition for dry, flood and cryogenic cooling machining environments

As shown in figure 2, to include machining environment for the experiments, the L9 DoE was repeated three times under dry, flood and cryogenic cooling environments. The levels for each machining parameter were based on initial screening experiments⁴⁷⁻⁴⁹ and the machine tool's and cutting tool's capabilities.

Table 1 demonstrates the detailed hybrid L9x3 DoE used for this investigation. Using this DoE, the machining environments are compared using a full factorial method whilst the effects of cutting parameters are also taken into account using L9 orthogonal array. Each machining experiment was repeated 3 times to ensure repeatability. Based on BS ISO 5725-1:1994⁵⁰ and BS ISO 5725-3:1994⁵¹, in the context of precision measurement, many factors (e.g. operator, equipment, environment and time) may affect the accuracy and correctness of the measured results. Therefore, the recommendations of these standards were strictly followed throughout the experimentation and measurement.

The machining experiments were conducted on a Bridgeport VMC 610 vertical CNC milling centre. For flood cooling experiments, water-miscible cutting fluid with extreme pressure additives at 8% concentration were used as recommended by the supplier. A cryogenic cooling nozzle was designed and built in-house for cryogenic machining experiments^{48, 49}. Figure 3 demonstrates a schematic view of the system. The nozzle was designed to spray a minimum amount of liquid nitrogen (LN2) at -196°C and 1bar along the cutting tool into the cutting zone based on screening experiments and as identified by Shokrani et al.⁴⁹. As shown in figure 3, the LN2 is supplied through a self-pressurised Dewar which eliminates the requirements for an external power supply.

Table 1, Design of experiments for machining experiments with

ID	Cryogenic					
	Flood					
	Dry					
				Cutting Speed	Feed Rate	Depth of Cut
				m/min	mm/tooth	mm
1	C1	F1	D1	30	0.03	1
2	C2	F2	D2	30	0.055	3
3	C3	F3	D3	30	0.1	5
k4	C4	F4	D4	115	0.03	3
5	C5	F5	D5	115	0.055	5
6	C6	F6	D6	115	0.1	1
7	C7	F7	D7	200	0.03	5
8	C8	F8	D8	200	0.055	1
9	C9	F9	D9	200	0.1	3

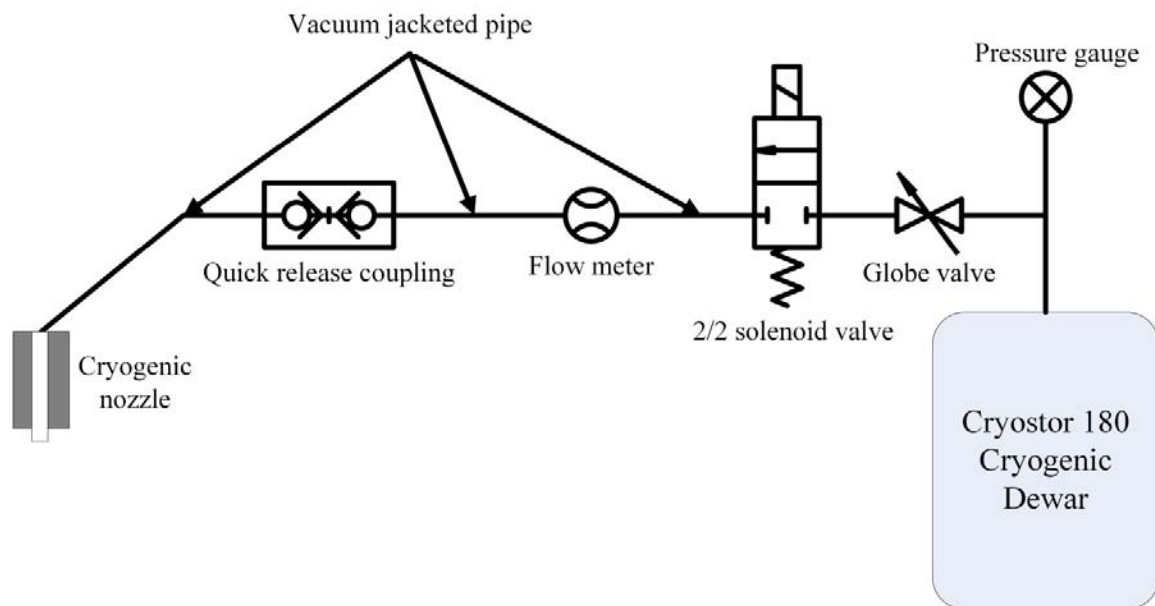


Figure 3, Schematic view of the cryogenic cooling system used for cryogenic machining⁴⁹

A block of annealed Ti-6Al-4V alloy with dimensions of 50mm x 50mm x 150mm was supplied for each machining experiment. The average hardness of the blocks was $285 \pm 5\%$ HV which was measured using a Vicker's hardness tester.

The machining experiments consisted of 4x150mm straight side milling along the test piece blocks. The tool overhang was kept constant for all experiments to minimise the variations due to tool deflection. The power consumption of the machine tool was monitored during the experiments using a Hioki Clamp on Hi-tester 3169-20 power demand analyser which was wired into the machine tool.

The energy consumption of the machine tool and the specific machining energy were calculated from the machine tool's power consumption using equation 2 and 3, respectively⁵².

$$\text{Equation 2} \quad E = \int_{t_0}^t P dt$$

$$\text{Equation 3} \quad SE = \frac{E}{V} = \frac{\int_{t_0}^t P dt}{V}$$

Where E is energy in joules, P is power in watts, V is volume of machined material in mm^3 , t_0 is the time in seconds when cutting tool engages with the material and t is the time in seconds when the cutting tool leaves the material.

After the machining experiments were conducted, the cutting tool was dismantled and cleaned by acetone. The cleaned cutting tool was then examined under a tool maker's microscope equipped with a high resolution digital camera. The tool wear was measured following the instructions provided by ISO 8688-2:1989⁵³ and all tool wear phenomenon e.g. chipping, notching, etc. were treated as flank wear for comparison.

3. Results and analysis

The results from machining experiments are presented and analysed below. Moreover, the effect of the machining environment on tool life, power consumption, energy consumption and specific machining energy are further investigated.

3.1 Tool wear

After conducting the machining experiments, the flank wear of the cutting tools was measured for each experiment. The average tool wear results of the experiments are provided in figure 4. The results indicated that in most cases, cryogenic cooling produced the lowest tool wear as compared to dry and flood cooling. Adversely, on average, the highest tool wear was detected on the tools used in dry environment.

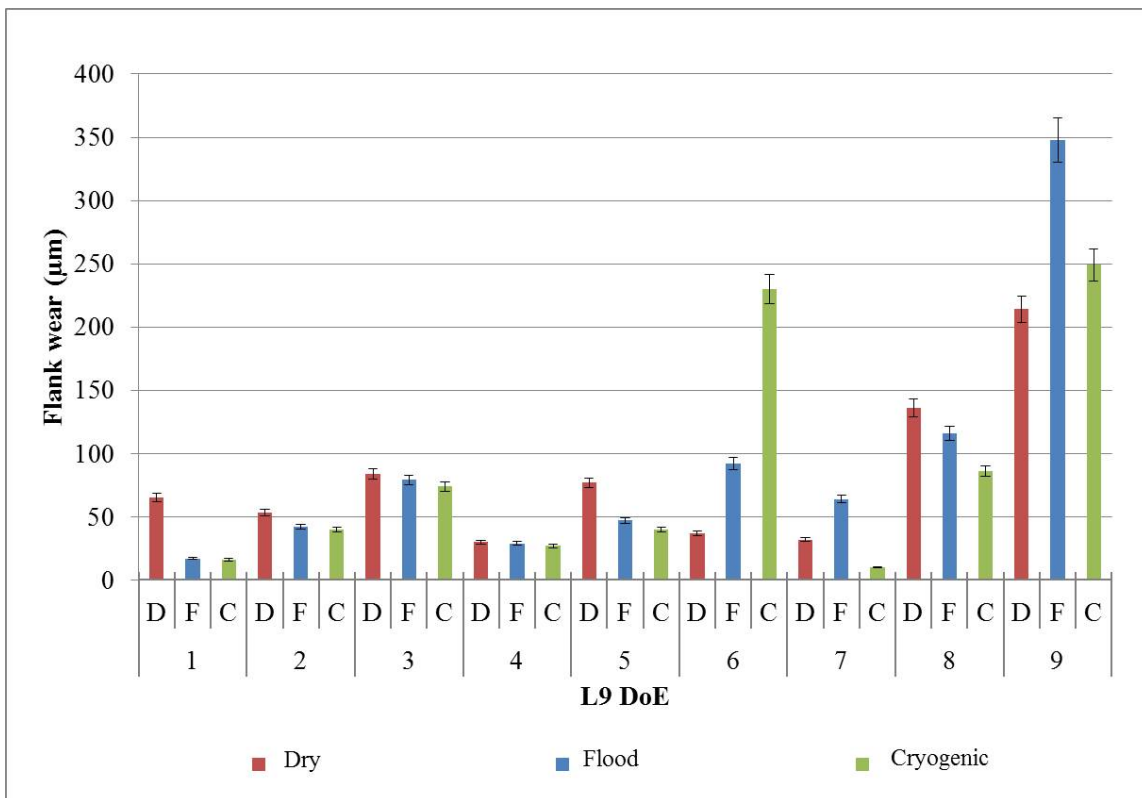


Figure 4, Tool wear for each machining experiment

As illustrated in figure 4, increasing the feed rate has a significant effect on tool wear which is irrespective of machining environment. Furthermore, the data for tool wear indicates that cutting speed significantly intensifies the effect of feed rate on tool wear. As shown in figure 4, comparison of the measurement results for tool wear revealed that the smallest flank wear in cryogenic machining is associated with experiment C7 (10 μ m), whilst they are W1 (17 μ m) and D4 (30 μ m) for wet and dry machining respectively. From this, it can be concluded that lower tool flank wear can be expected in cryogenic machining whilst increased productivity can be achieved as a result of higher cutting speed in comparison with dry and wet machining.

The second lowest tool wear was also attributed to the tool used under cryogenic cooling for experiment C1 at 30m/min cutting speed, 0.03mm/tooth and 1mm depth of cut. Analysis of the micrographs of the cutting tool, illustrated in figure 5, indicates that mechanical tool wear mechanisms e.g. abrasion and chipping are dominant at lower cutting speeds and feed rates. In contrast, thermomechanical and chemical phenomena such as attrition, crater wear and adhesion were observed at higher cutting speeds and feed rates. For instance, whilst abrasion was the dominant tool wear mechanism for D1, W1 and C1 (figure 5), smearing and adhesion can be seen for the tools D9, W9 and C9. Moreover, smearing on the flank face was detected on the cutting tools which more profound at lower cutting speeds.

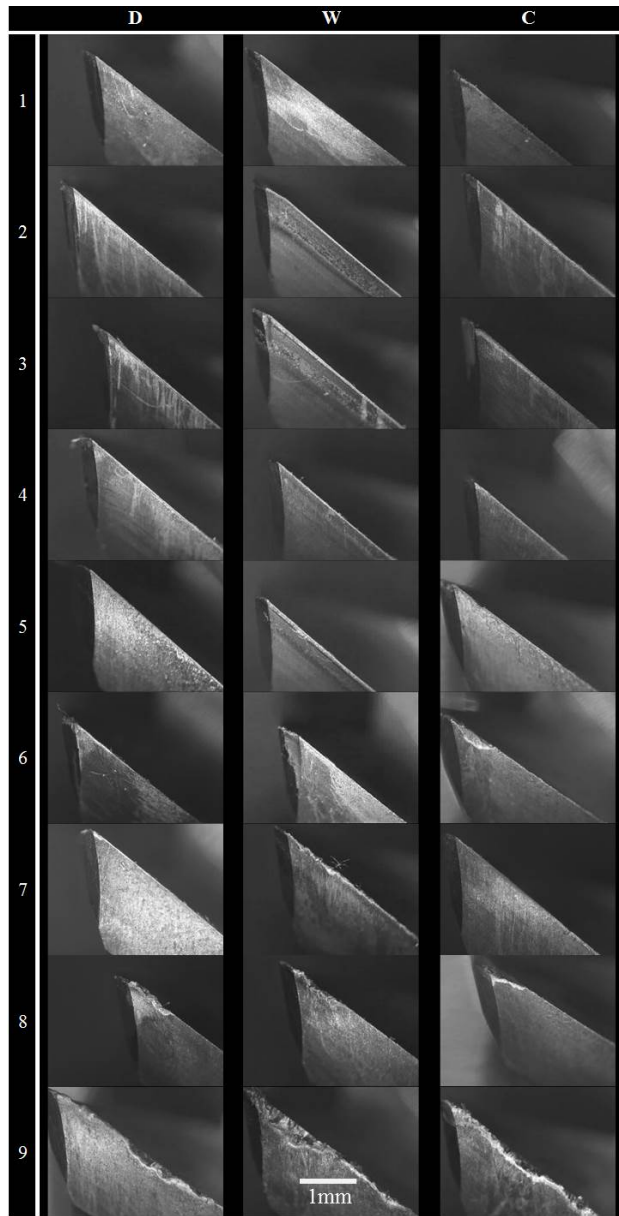


Figure 5, Micrographs of the cutting tools used for machining experiments

The tools used for experiment 9 showed the highest tool wear across all machining environments. As explained in the methodology, the maximum level of cutting speed and feed rate was used for experiment 9. Thermomechanical wear mechanism was dominant for all cutting tools in experiment 9. The tool wear was initiated by crater wear and chipping of the cutting edge and was followed by attrition and abrasion. As shown in figure 5, significant chipping on the rake face and attrition and abrasion wear on the flank face resulted in tool failure in experiment 9. It is noteworthy to mention that catastrophic failure occurred for two of the cutting tools used for experiment D9 and the cutting tools failed prematurely before reaching the 600mm machining length. Therefore, the value shown in figure 4 for tool wear is only representative of one experiment.

Unlike the flank face, the rake face is not in direct contact with machined surface. However, welding and formation of built up edge on the rake face has the potential of weakening the cutting edge by making crater wear. As shown in figure 6, flaking, crater wear and formation of built up edge were dominant for all machining experiments irrespective of machining environment. It has been noticed that the crater wear formed a narrow line adjacent to the cutting edge on all the cutting tools.

Constant flow of the chips over the rake face removes material from the cutting tool adjacent to the cutting edge and forms crater wear. This potentially weakens the cutting edge resulting in chipping and tool failure. As illustrated in figure 6, cryogenic cooling significantly reduced the severity of this phenomenon showing the potential to improve the tool life.

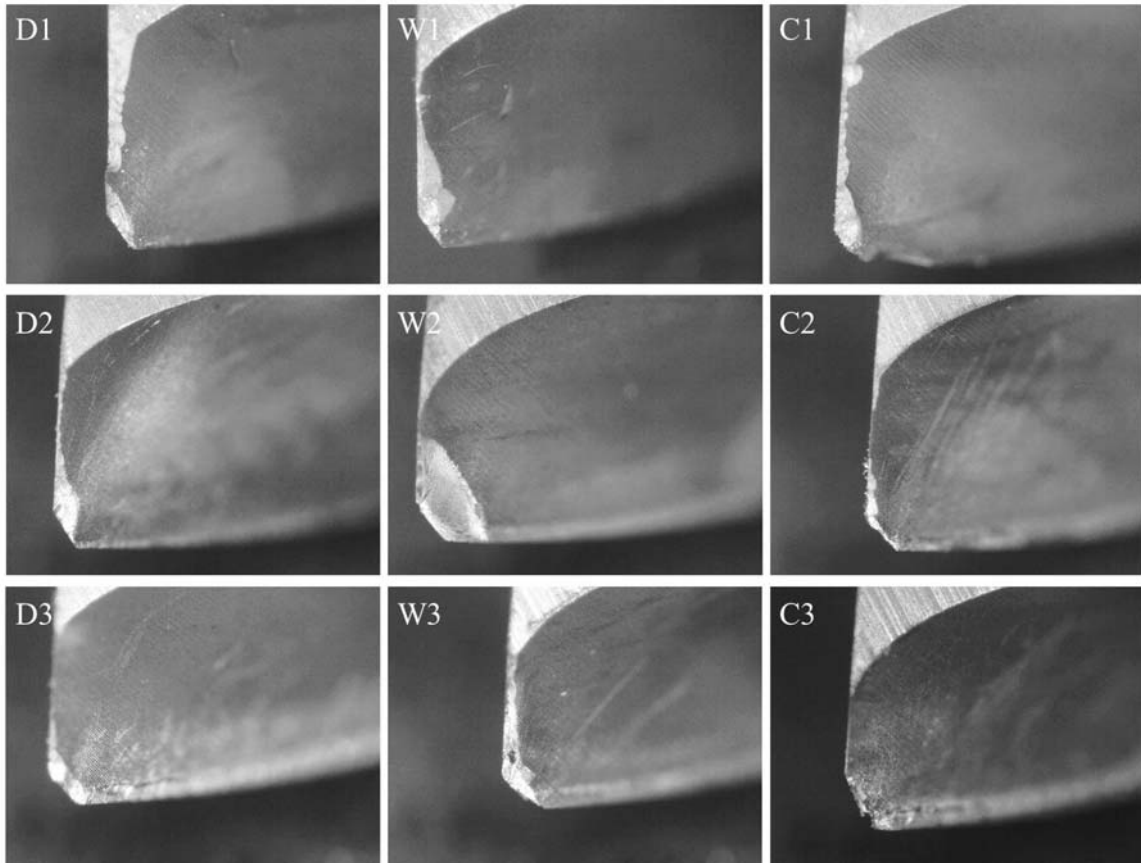


Figure 6, Flaking and crater wear on the tools used in machining experiments

3.2 Power consumption

The power consumption of the machine tool was monitored at a sampling rate of 1Hz during the machining experimentations. Figure 7 illustrates an example of the power consumption of the Bridgeport VMC 610 machine tool with and without using coolant

pump. The power consumption graph shown in figure 7 can be categorised into 8 distinct areas illustrated under the graphs. In the region 1, the machine is turned on and the emergency stop button is pressed. Releasing the emergency stop (region2) will result in activating the machine's drives and therefore increasing the machine tool's power consumption from 470W to 870W in idle mode. In the third region, the coolant pump was turned on for flood machining graph for 50 seconds. As shown in figure 7, there is peak at the start of the graph indicating inrush for the coolant pump motor. On average, the coolant pump adds 800W to the total machine tool's power consumption independent of cutting parameters. At the end of the third region, the coolant pump was turned off for 50 seconds (region 4). Since no coolant pump is used for dry machining, the power consumption of the machine tool was identical in the 3rd, 4th and 5th regions for dry cutting graph. The coolant pump was turned on at the start of region 5 and the machine was set for machining. Following the process plan, at the end of region 5 and start of region 6, the spindle was turned on and the cutting tool moved to the start position for machining with rapid move. This together with the spindle motor's inrush has resulted in a sharp peak in region 6. Afterward, the cutting tool moves with feed towards the workpiece material. In region 7, the cutting tool engages with workpiece material resulting in increased power consumption. When the cutting tool exits the workpiece at the end of region 7, the move with feed continues for 10 second the spindle and coolant pump stop and the power consumption graph plunges back to the idle mode.

In order to identify the effect of various cutting parameters and machining environment on power consumption, the power consumption of the none-material cutting moves e.g. idle mode, rapid movement, plunging and move with feed without material cutting were isolated. Furthermore, in order to remove the noise from the measurements, a

Gaussian filter was applied on the measured results. Salonitis¹³ and Salonitis and Ball⁵ found that the peripherals of the machine tool e.g. coolant pump, lubricant pump, controller, etc. have constant power consumption which is not affected by cutting parameters. Therefore, they suggested that the monitoring procedure has to be designed in a way to be able to detect and consider these elements for power consumption. In the present study, the idle power consumption of the machine was identified to be constant irrespective of the machine tool's state. Furthermore, the power consumption for coolant pump and rapid move was constant.

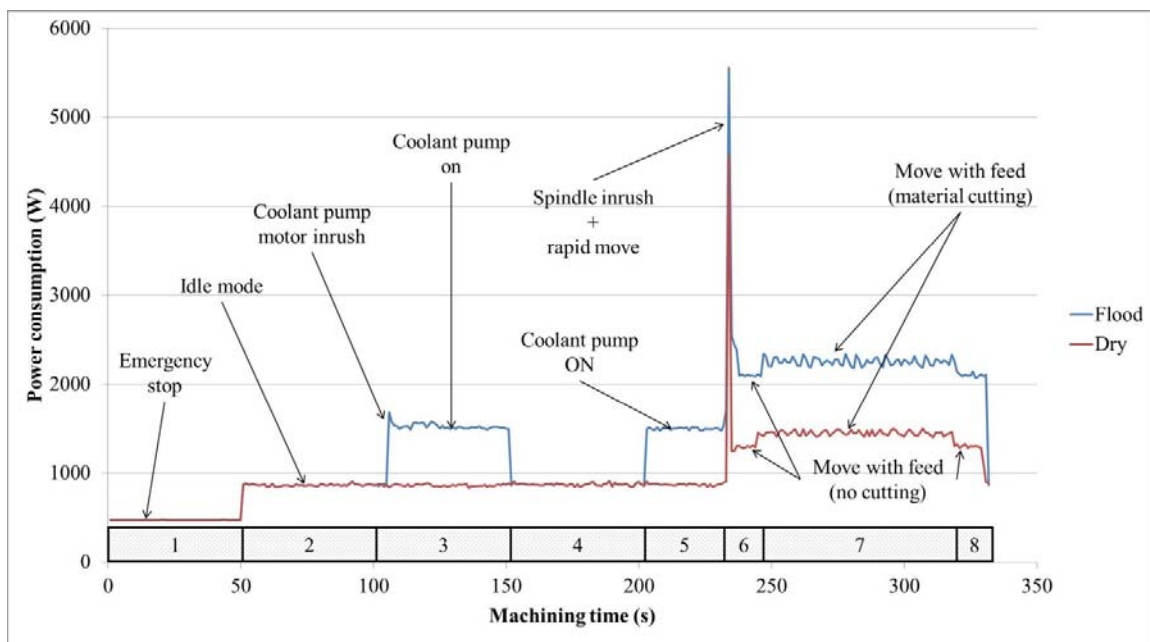


Figure 7, Example power consumption graphs of CNC milling process

The average power consumption of the machine tool was then calculated for each machining experiment. As shown in figure 8, the power consumption of the machine tool is distinctly higher for all experiments conducted under flood cooling. This is due to the average 880w power consumption of the machine tool’s coolant pump. Analysis of the means for the power consumption indicated that the lowest power consumption was attributed to dry machining as illustrated in figure 9.

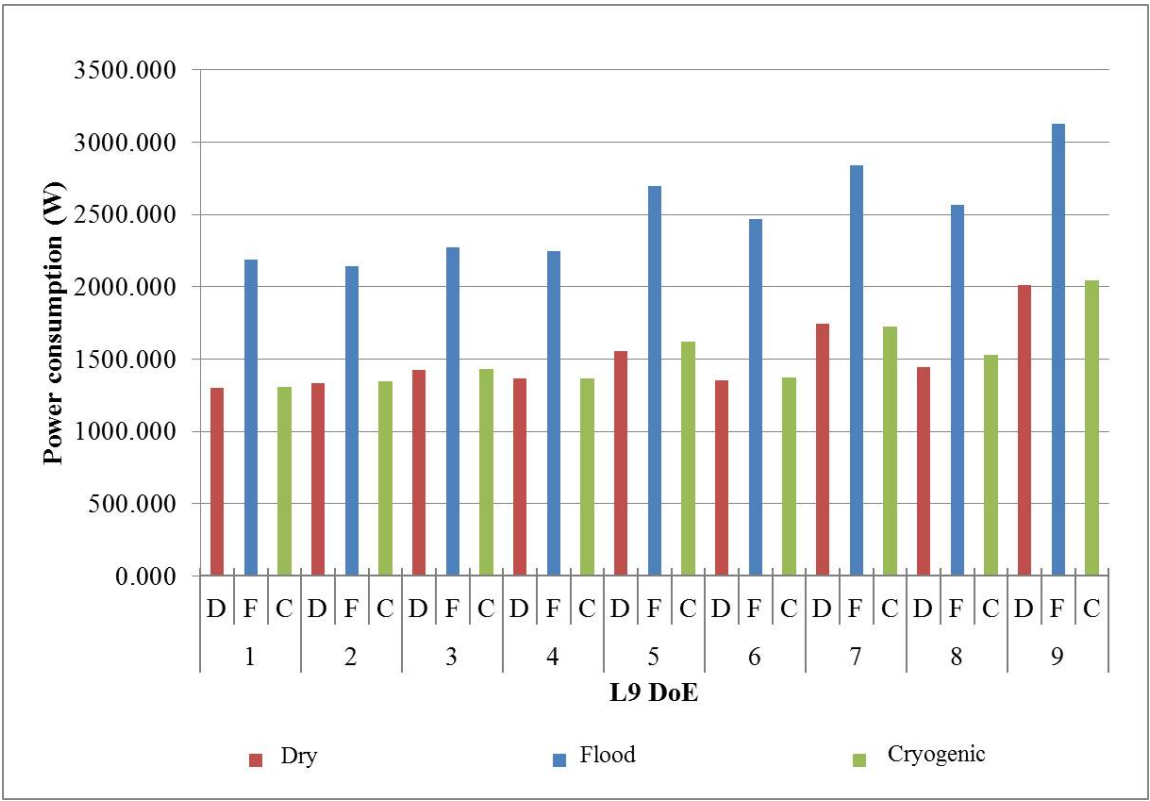


Figure 8, Power consumption of the machine tool for each machining experiment

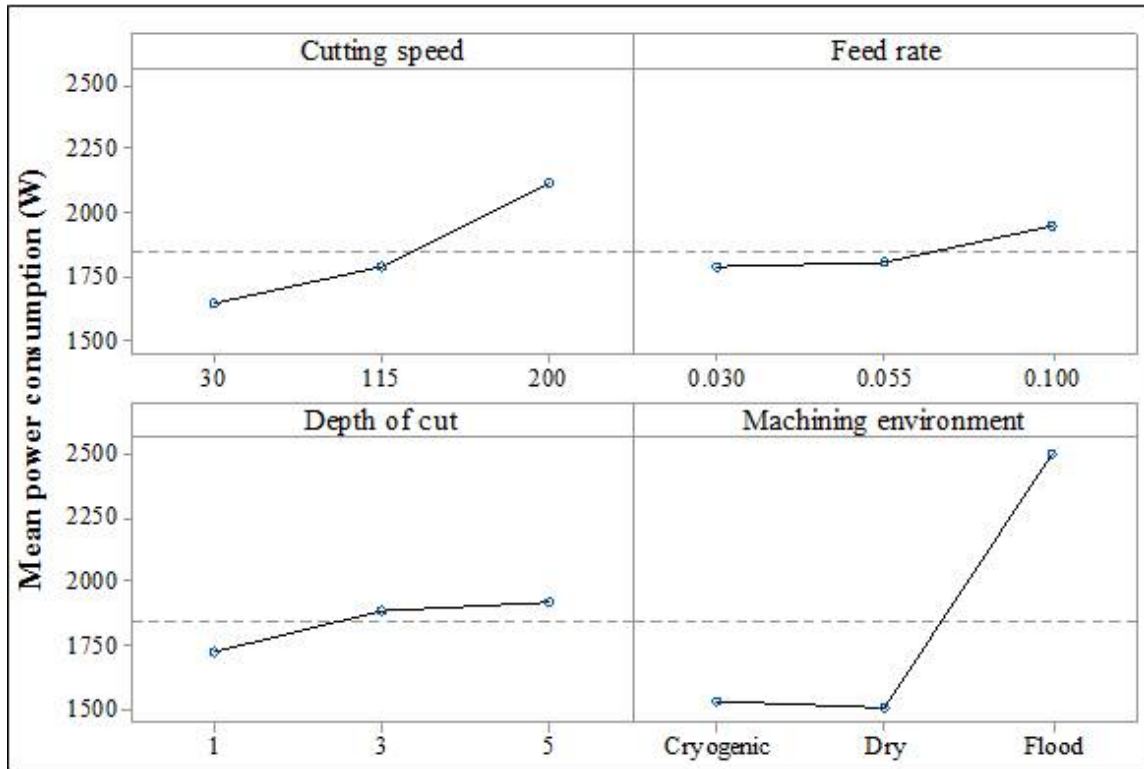


Figure 9, Analysis of means for power consumption

On average, the power consumption in cryogenic machining was 1.5% more than that of dry machining. This can be due to the increased material hardness at extremely low cryogenic temperatures as stated by Hong⁴⁰. As shown in figure 10 (top), the histogram of power consumption for machining environments indicated that the measurement results are skewed towards flood cooling. Therefore, 880W were deduced from the power consumption of the experiments in flood cooling to isolate the effect of coolant pump on the power consumption. Analysis indicated that the effect of machining environment where coolant pump's power consumption is isolated is not statistically significant.

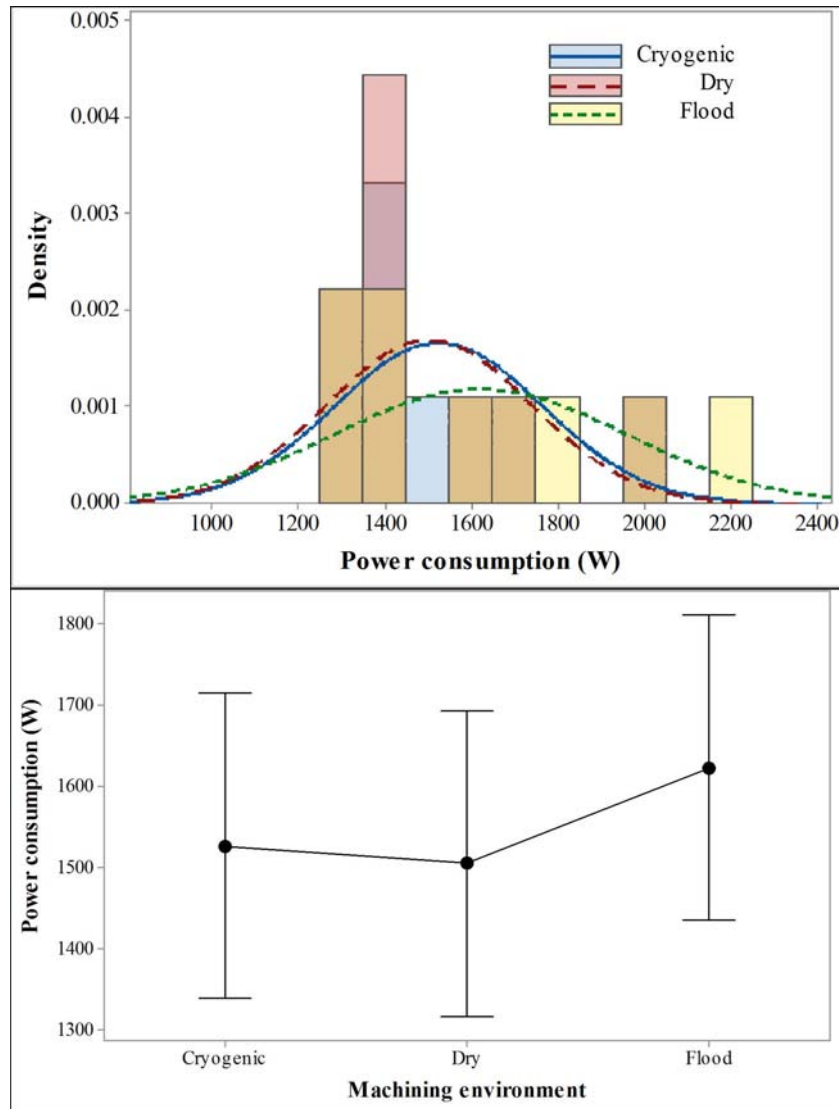


Figure 10, Histogram of power consumption using dry, cryogenic and flood cooling (top) and mean power consumption of various machining environments when coolant pump's power consumption is isolated (bottom)

As shown in figure 10 (bottom), whilst the average power consumption in flood cooling is higher than that of dry and cryogenic machining, the wide range of measurement results (standard deviation) does not confirm a statistically significant difference between the means.

Furthermore, the analysis of means, shown in figure 9, suggests that lower levels of cutting speed, feed rate and depth of cut should be used in order to reduce power consumption in milling operations. Although it seems logical to reduce the rotational speed of the machine tool's spindle and axes and reduce the torque by choosing lighter depth of cut, this would significantly affect the productivity and material removal rate. Moreover, whilst the power consumption is a useful guide for choosing the right equipment (spindle power, axes motors, etc.) for machining, it does not necessarily reflect the amount of energy required for machining a component.

3.3 Energy consumption and specific machining energy

As explained in the methodology, energy is the integration of power consumption over time and evidently, it is significantly affected by the machining time. For this investigation, the energy consumption of the machine tool was calculated for each machining experiment from the power consumption and is illustrated in figure 11. Moreover, the specific machining energy was calculated to indicate the amount of energy used by the machine tool for cutting a unit volume (1mm^3) of Ti-6Al-4V as demonstrated in figure 12.

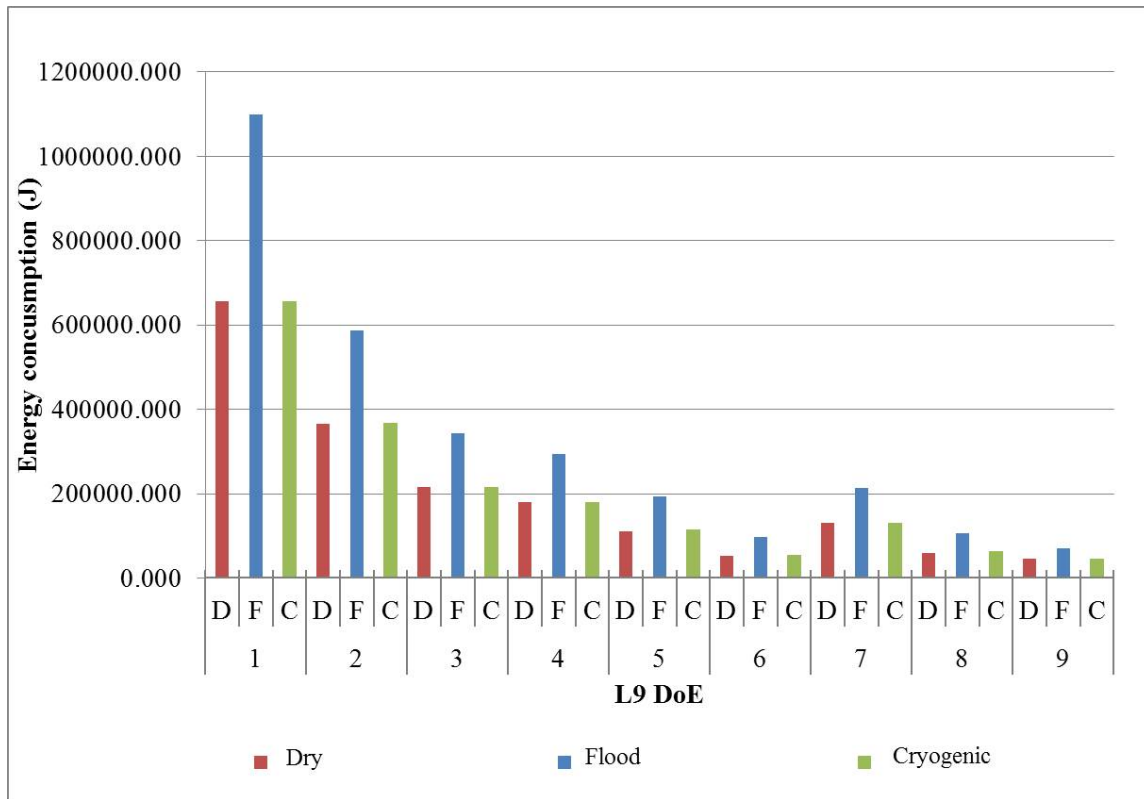


Figure 11, Energy consumption of the machine tool during each machining experiment

As shown in figure 11, increased material removal rate through using higher cutting speeds and feed rates has significantly reduced the energy consumption and specific machining energy. Since the machining time for similar experiments under different machining environment is identical, similar conclusions to the power consumption can be drawn for the effects of machining environment on energy consumption. The analysis shows that flood cooling is the least favourable machining environment mainly due to the significant energy consumption of the coolant pump. As shown in figure 13, the Boxplot

graphs indicated that the average energy consumption is higher for flood cooling whilst there is no significant difference between dry and cryogenic machining. Moreover, the Boxplot graphs indicated the existence of outliers and skewness in the measurement results.

Therefore, the SN ratio of the results using equation 4, smaller-is-better, was used for the analysis as recommended by Xin⁵⁴.

Equation 4 Smaller-is-better $SN = -10 \log_{10}\left(\frac{\sum y^2}{n}\right)$

where for experiment Y, y is the measured values and n is the sample size.

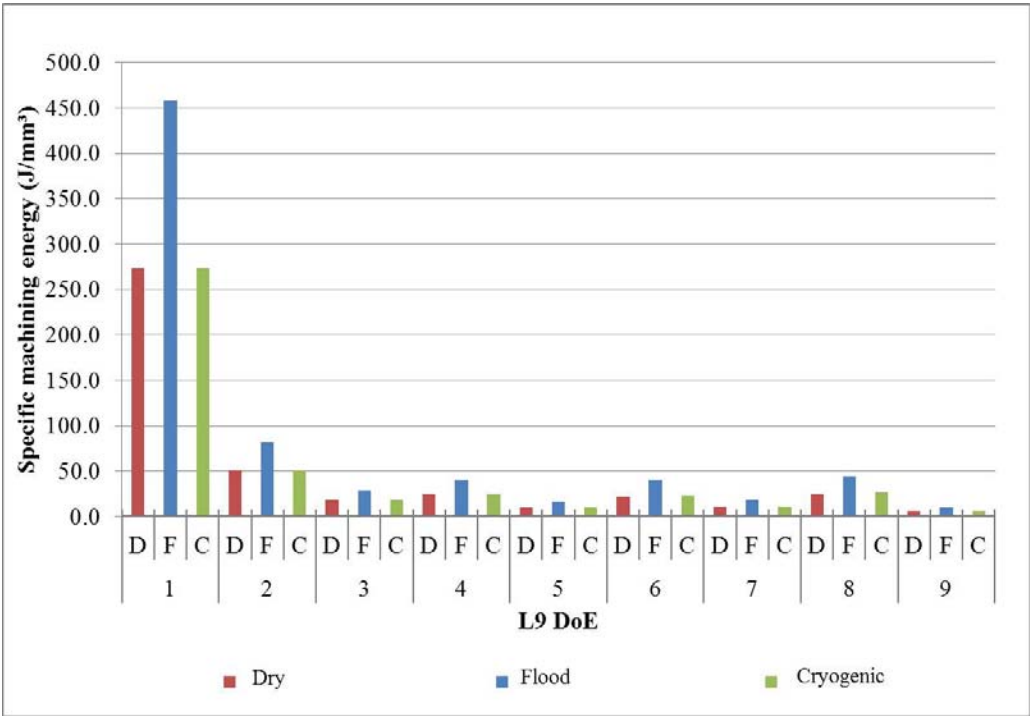


Figure 12, Specific machining energy for each machining experiment

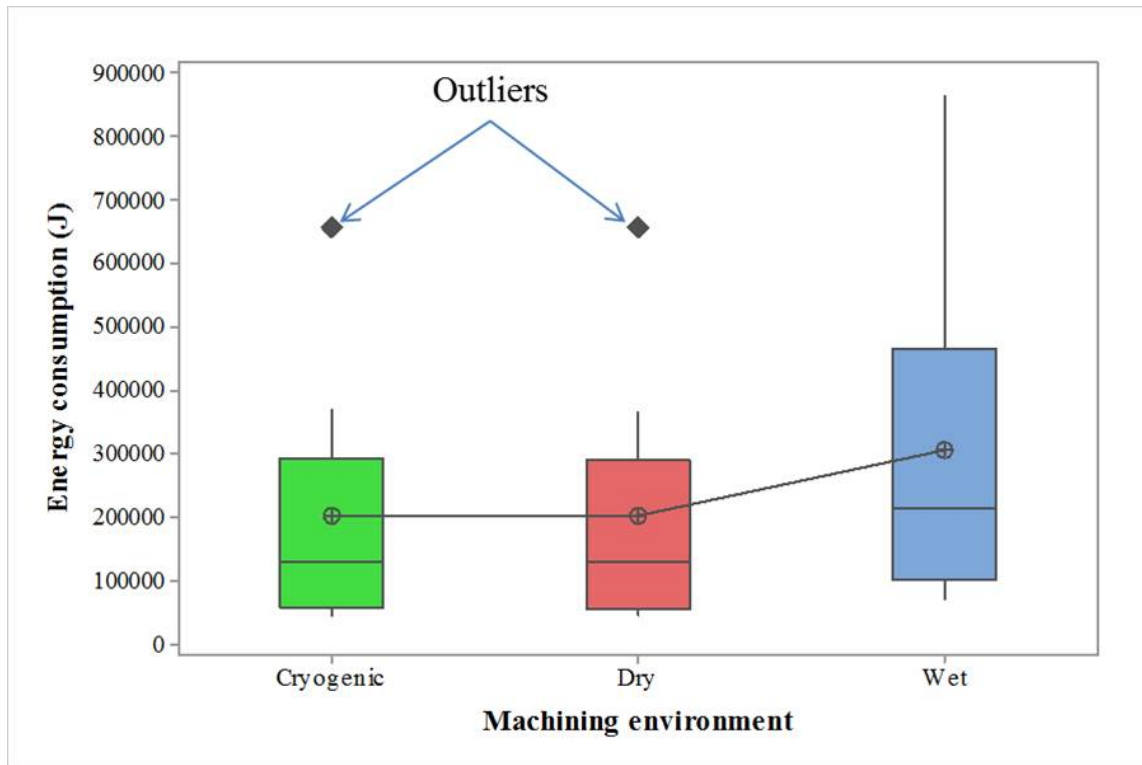


Figure 13, Boxplot graphs of energy consumption for machining environment

Analysis of mean SN ratio graphs, as shown in figure 14, indicated that higher levels of cutting speed and feed rate have the largest mean SN ratio and therefore are more favourable. The analysis indicated that the effect of depth of cut on the energy consumption is not as significant whilst lighter depths of cut are more favourable. By definition, it can be understood that the higher the cutting speed and feed rate, the higher material removal rate and hence shorter machining time. Therefore, lower energy is required for machining the test piece material. In contrast, higher depths of cut induce more torque on the spindle and axes motors resulting in higher energy consumption.

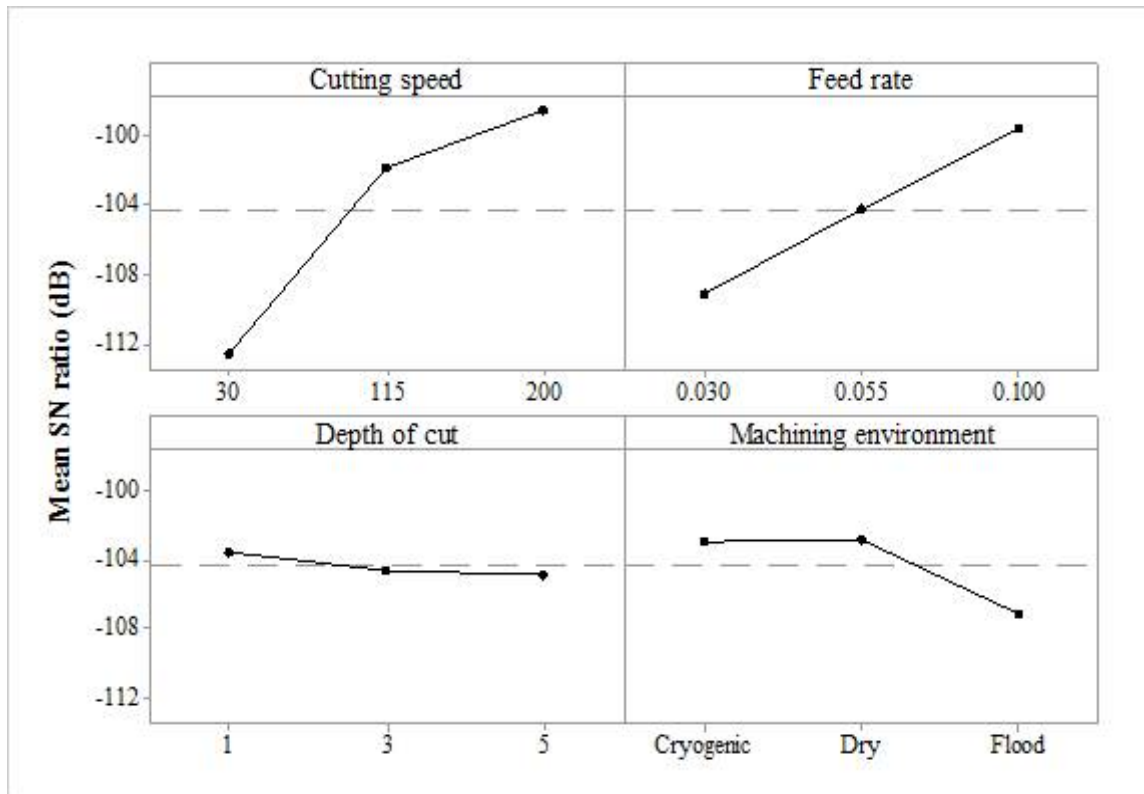


Figure 14, Mean SN ratio graphs of energy consumption

The analysis of specific machining energy (figure 12) demonstrated that experiment 1 has the highest specific machining energy whilst increasing cutting parameters significantly reduces the specific machining energy. As shown in figure 15 (left), the Boxplot graph of the specific machining energy for machining environment indicates that the specific machining energy is not significantly affected by machining environment. As explained previously for power and energy consumption, the use of coolant pump resulted in higher specific machining energy for experiments conducted under flood cooling.

Isolating the coolant pump energy consumption from the analysis, it was revealed that the effect of machining environment on the specific machining energy is very limited as shown in figure 15 (right). Furthermore, it was found that all groups contain outliers which necessitate SN ratio analysis.

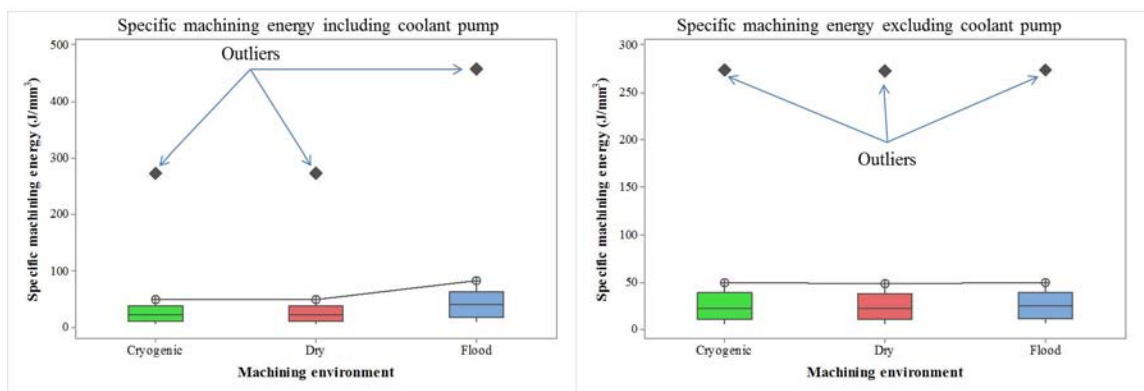


Figure 15, Boxplot graphs of specific machining energy including the coolant pump (left) and excluding the coolant pump (right) power consumption

The SN ratio analysis of the data for specific machining energy, illustrated in figure 16, indicated that the higher levels of cutting speed, feed rate and depth of cut have the highest mean SN ratio and therefore are most favourable for reducing the amount of energy required for machining a unit volume of Ti-6Al-4V material. Dry and cryogenic machining demonstrated almost equal mean SN ratio and are more favourable than flood. The analysis revealed that increasing material removal rate through utilising higher cutting speeds, feed rates and depths of cut is the most convenient way of minimising specific machining energy. This way, the total energy consumption for machining a part will be also minimised.

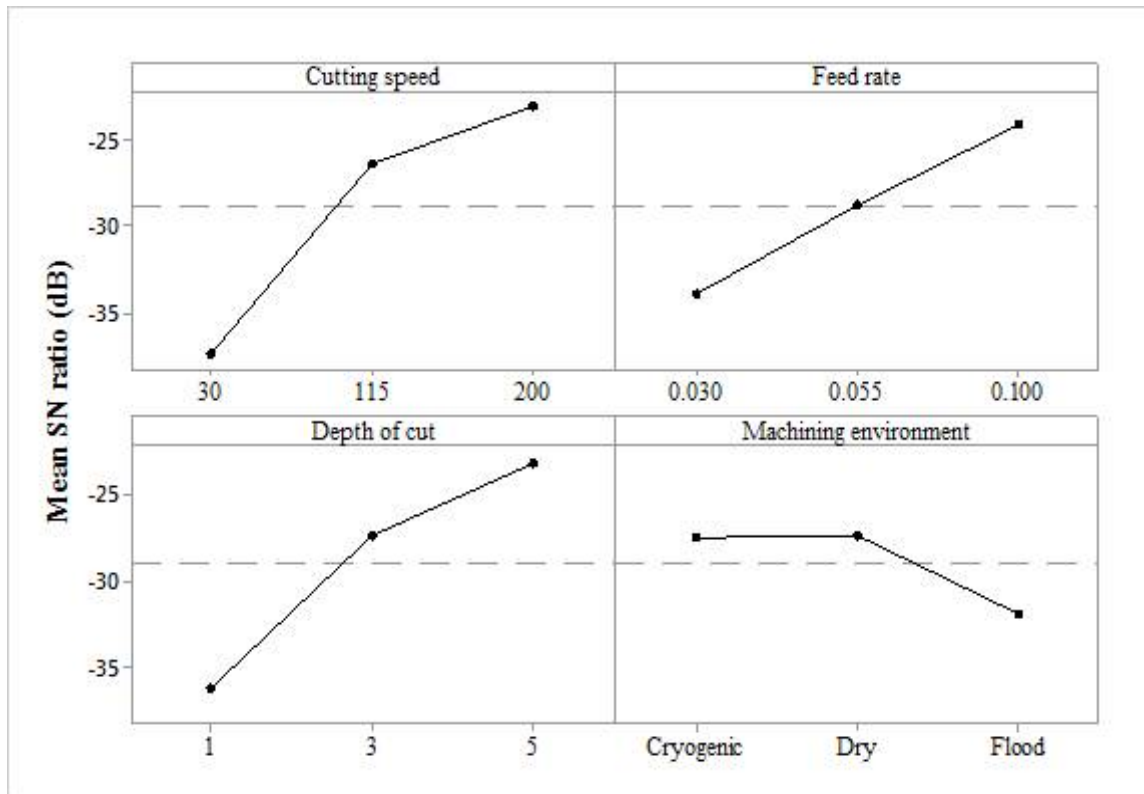


Figure 16, Mean SN ratio graphs of specific machining energy for input parameter

4. Discussion

Analysis of the cutting parameters and machining environment indicated that cryogenic machining is the best way to minimise tool wear and therefore improved tool life in machining Ti-6Al-4V titanium alloy. Bordin et al.⁵⁵ and Venugopal et al.^{56, 57} reported that cryogenic cooling considerably reduced tool wear in turning Ti-6Al-4V workpieces. Specifically, the authors found that cryogenic cooling restricted the adhesion wear on both

rake and flank faces. Similarly, limited crater wear was observed on the rake face as compared to dry machining. This is in agreement with the findings of this research in cryogenic CNC milling where the tools used for cryogenic machining had lower crater wear as compared to their counterparts used for machining in dry and flood cooling.

As shown in figure 17, the Ti-6Al-4V alloy used in this study consists of alpha titanium phase with hexagonal closed pack (hcp) structure and beta phase with body centred cubic structure (bcc). In figure 17, the plates of alpha titanium appear darker and beta titanium boundaries are shown in brighter colour. The deformation of metals takes place by sliding (slip) of closed pack planes in the crystal structure. An ideal hcp structure with c/a ratio of 1.633 have 3 slip systems along its (0002) basal planes in the direction of $\langle 11\bar{2}0 \rangle$ ^{23, 58}. However, in the case of titanium with c/a ratio of 1.587, the basal plane is less widely separated and thus other planes compete for slip activity resulting in material ductility. The bcc structure, on the other hand, does not have close packed slip plane and requires heat for activation. The slip in bcc structures usually takes place at {110} planes in $\langle 111 \rangle$ direction²³. At low temperatures, bcc structures become brittle resulting in material fracture prior to undergoing significant deformation⁵⁸.

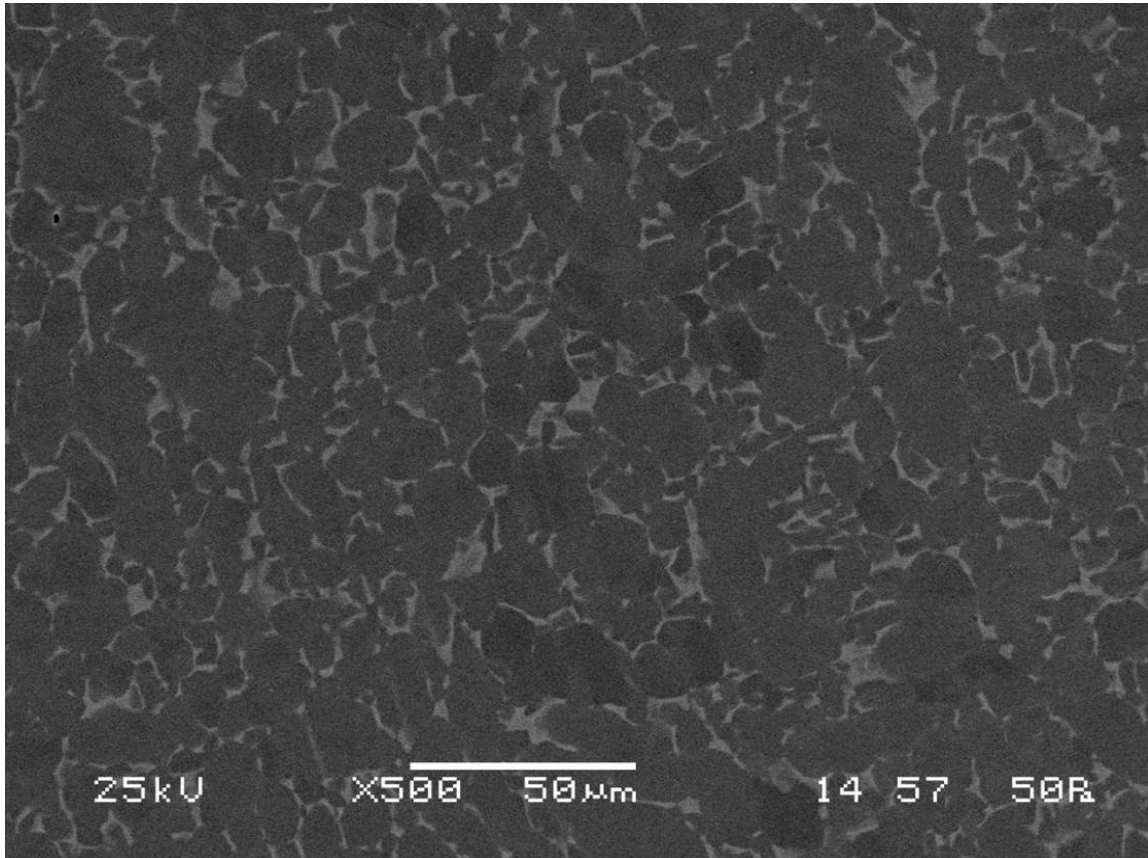


Figure 17, SEM micrograph of the Ti-6Al-4V titanium alloy used in this research

As shown in figure 18⁵⁹ and 19⁶⁰, reducing the material temperature to -196°C significantly reduces the percent elongation and fracture toughness of Ti-6Al-4V alloy, respectively. This, in turn, facilitates material cutting, reduces tool wear and allows for employing higher cutting speeds. Furthermore, the investigations revealed that using a cryogenic environment at -196°C facilitate heat removal from the cutting zone and reduces

chemical affinity between cutting tool and workpiece materials enabling using higher cutting speeds.

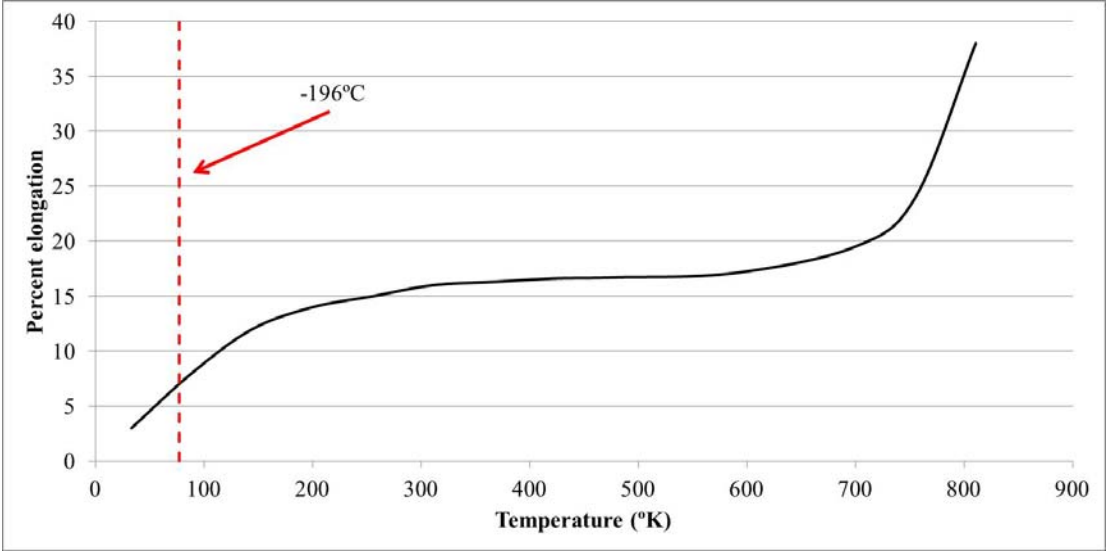


Figure 18, Percent elongation vs. temperature graph of Ti-6Al-4V adapted from⁵⁹

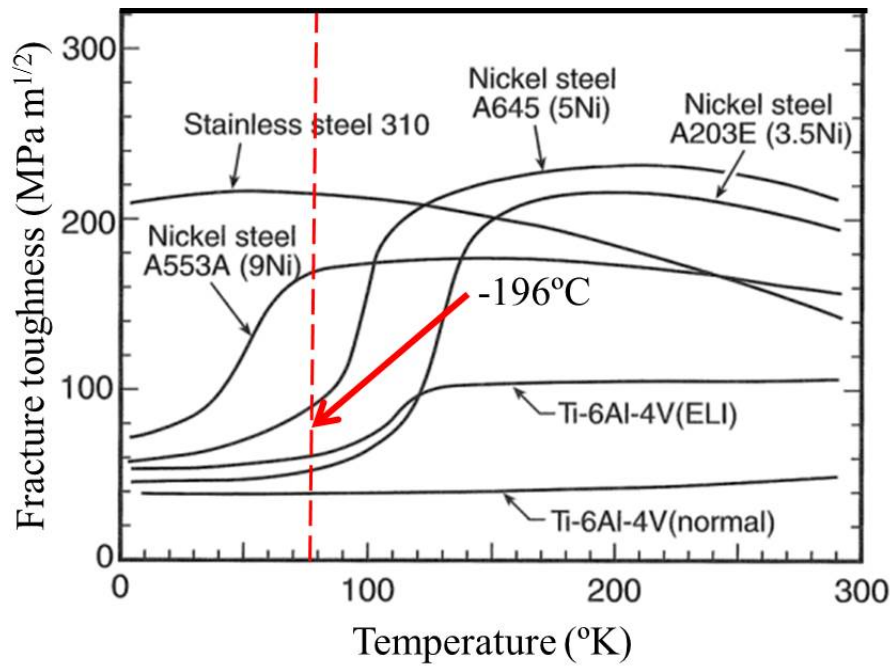


Figure 19, Fracture toughness vs. temperature graph of Ti-6Al-4V⁶⁰

For instance, the lowest tool wear was occurred on the tool used in experiment 7 at 200m/min cutting speed. Similar observations have been reported by Hong and Broome³⁰ and Kalyan Kumar and Choudhury⁶¹ in turning operations. Hong et al.⁶² stated that, in turning operations, at high cutting speeds of 150m/min, the cutting tools failed prematurely under flood cooling whilst 5 times improvement was achieved using cryogenic machining. The authors noted that the improvement in tool life is more significant at higher cutting speeds. Similar observations are reported by Khan and Ahmed⁶³.

The analysis for power consumption indicated that a significant amount of energy is used for coolant pump in the machine tool. This has made flood cooling the least

favourable machining environment from power and energy consumption point of view. Based on the results, the coolant pump accounted for 36%-44% of the total power consumption of the machine tool. Similar observations were reported by Gutowski et al.⁸ that 85.2% of the machining power consumption is constant even if the machine is idle. The researchers⁸ attributed this to the pumping of coolant, lubricant and hydraulic fluids. Aggarwal et al.⁶⁴ conducted a series of comparative machining experiments to identify the effect of cryogenic cooling in turning of AISI P20 steel. In their research, machining environment, cutting speed and depth of cut was found to be the most significant parameters affecting power consumption. They identified the elimination of coolant pump's power consumption as a result of dry and cryogenic machining as an underlying reason for the significance of machining environment for power consumption. Moreover, although cryogenic cooling has increased the hardness of AISI P20 steel by 10%, the researchers found that cryogenic cooling has resulted in lower power consumption than dry machining. They attributed this reduction to the reduced cutting temperature and therefore machining stress and cutting forces⁶⁵. In contrast, the investigations, detailed in section 3.2, indicated that that cryogenic cooling resulted in 1.5% increase in power consumption as compared to dry machining. Hong et al.⁶⁶ stated that cryogenic cooling produced higher cutting forces than dry machining in turning of Ti-6Al-4V. They attributed this rise to the increased material hardness and strength as a result of cryogenic temperatures.

In order to minimise the energy consumption of a machine tool, higher levels of cutting speed and feed rate are desired. This is mainly due to the fact the amount energy required for running the machine tool is significant⁸. Fratila⁶⁷ noted that in machining 16MnCr5 alloyed steel, the amount of energy used for cutting material is 45% less than the actual machine tool's energy consumption. Therefore, reducing the machining time can

significantly reduce the energy consumption. The experiments clearly showed that employing 200m/min cutting speed is possible using cryogenic cooling which results in almost 7 times reduction in machining time. As shown in figure 20, Li et al.⁷ reviewed the energy consumption of various machine tools and noticed that on average, only 17% of the total machine tools' energy consumption is due to the servo drives. In contrast, on average 31% of the machine tools' energy consumption is associated with coolant/lubricant system which is close to the 40% increase in energy consumption in flood cooling found in this research (section 3.3.).

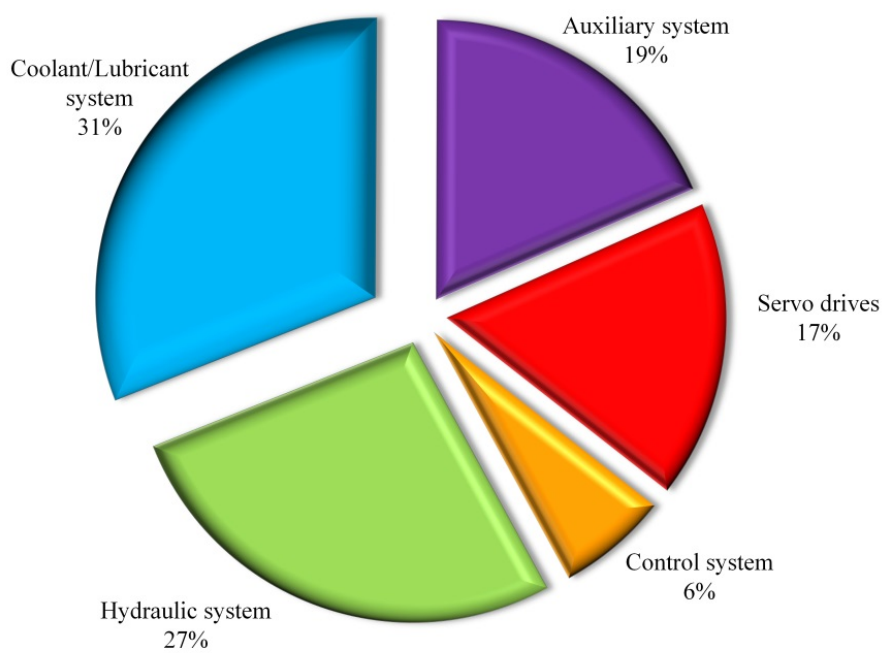


Figure 20, Energy consumption breakdown of a machine tool, adapted from Li et al.⁷

The most important parameter for energy efficient machining, however, is the specific machining energy as it defines the amount of energy required for machining a specific part. Helu et al.⁶⁸ claimed that one way of achieving sustainability and reducing resource cost is to increase cutting speed and depth of cut. However, it is noted that this may deteriorate the cutting tool faster and hence not applicable^{21, 68}. The analysis of the data detailed in section 3, indicated that increasing material removal rate by using higher values for cutting speed, feed rate and depth of cut is the most effective way of minimising specific machining energy. Since titanium is notoriously considered a difficult-to-machine material, employing higher cutting speeds and feed rates is generally not applicable, using conventional machining techniques²⁴. As demonstrated in experiment 7, cryogenic cooling has shown promising potentials for allowing using higher values of cutting speed (200m/min) and therefore increased material removal rate and lower specific machining energy. Comparison between the experiment C7 and F1 indicates that 7 times increase in cutting speed has resulted in about 88% reduction in energy consumption whilst increasing the productivity by 7 times. Despite this, for sustainable manufacturing, the energy consumption for preparing liquid nitrogen and preparation, maintenance and disposal of water-miscible cutting fluid together with the environmental impact of manufacturing cutting tools should be considered.

5. Conclusions

A systematic methodology was developed to investigate the effects of cryogenic cooling in machining Ti-6Al-4V and investigate the power consumption, energy consumption and specific machining energy in end milling operations. Based on the results and analysis, the following conclusions were drawn:

- The investigations indicated that cryogenic cooling is the most favourable machining environment to minimise tool wear in end milling Ti-6Al-4V whilst eliminating the use of hazardous water-based cutting fluids;
- The 12mm diameter coated solid carbide cutting tool used for cryogenic machining at 200m/min cutting speed, 0.03mm/tooth feed rate and 5mm depth of cut possessed the lowest tool wear among all combinations of cutting parameters and machining environments;
- This study indicated that mechanical tool wear phenomena, such as chipping and abrasion, are dominant at lower levels of cutting speed and feed rate. Increasing the cutting speed and feed rate resulted in thermal and mechanical tool wear mechanisms such as adhesion, built up edge and crater wear;
- The coolant pump of the machine tool consumes a significant portion of the machine power making dry and cryogenic cooling the most favourable machining environments for minimising power consumption. The analysis revealed that on average 40% of the power consumption in flood cooling is attributed to the coolant pump. Introducing the workpiece material to cryogenic temperatures results in an increased material hardness and therefore 1.5% increased power consumption in comparison to dry machining;
- Increasing material removal rate is necessary for minimising specific machining energy. However, tool life is a limiting factor for realisation of higher material removal rates through increased cutting speed, feed rate and depth of cut. Using cryogenic cooling, the material removal rate of more than 9500mm³/min with minimum tool wear was achieved. Through increased material removal rate,

cryogenic cooling has shown significant potential to minimise specific machining energy;

- Cryogenic cooling allowed for a 7 fold increase in cutting speed and productivity whilst 88% energy saving was achieved. This indicates the significant potential of cryogenic cooling for revolutionising machining of titanium alloys.

Acknowledgement

The authors would like to acknowledge the industrial partners for supporting this research.

References

1. Gimpel J. *The medieval machine: The industrial revolution of the Middle Ages*. Penguin Books, 1977.
2. The-World-Bank. Fossil fuel energy consumption. The World Bank, 2015.
3. Seow Y and Rahimifard S. A framework for modelling energy consumption within manufacturing systems. *CIRP Journal of Manufacturing Science and Technology*. 2011; 4: 258-64.
4. Jacobson MZ and Delucchi MA. Providing all global energy with wind, water, and solar power, Part I: Technologies, energy resources, quantities and areas of infrastructure, and materials. *Energy Policy*. 2011; 39: 1154-69.
5. Salonitis K and Ball P. Energy Efficient Manufacturing from Machine Tools to Manufacturing Systems. *Procedia CIRP*. 2013; 7: 634-9.
6. Schmid SR. Energy consumption in manufacturing. *AIP Conference Proceedings*. 2012; 1431: 417-24.

7. Li W, Zein A, Kara S and Herrmann C. An Investigation into Fixed Energy Consumption of Machine Tools. In: Hesselbach J and Herrmann C, (eds.). *Glocalized Solutions for Sustainability in Manufacturing*. Springer Berlin Heidelberg, 2011, p. 268-73.
8. Gutowski T, Murphy C, Allen D, et al. Environmentally benign manufacturing: Observations from Japan, Europe and the United States. *Journal of Cleaner Production*. 2005; 13: 1-17.
9. Aramcharoen A and Mativenga PT. Critical factors in energy demand modelling for CNC milling and impact of toolpath strategy. *Journal of Cleaner Production*. 2014; 78: 63-74.
10. Apostolos F, Alexios P, Georgios P, Panagiotis S and George C. Energy Efficiency of Manufacturing Processes: A Critical Review. *Procedia CIRP*. 2013; 7: 628-33.
11. Apostolos F, Panagiotis S, Konstantinos S and George C. Energy Efficiency Assessment of Laser Drilling Process. *Physics Procedia*. 2012; 39: 776-83.
12. Salonitis K. Energy Efficiency and Environmental Impact Implications of Grind-Hardening Process. *Grind Hardening Process*. Springer, 2015, p. 81-91.
13. Salonitis K. Energy efficiency assessment of grinding strategy. *International Journal of Energy Sector Management*. 2015; 9: 20-37.
14. Dahmus JB and Gutowski TG. An environmental analysis of machining. *ASME 2004 international mechanical engineering congress and exposition*. American Society of Mechanical Engineers, 2004, p. 643-52.
15. Salonitis K, Zeng B, Mehrabi HA and Jolly M. The Challenges for Energy Efficient Casting Processes. *Procedia CIRP*. 2016; 40: 24-9.

16. Mahrabi H, Jolly M and Salonitis K. Methods of Reducing Material Waste and Saving Energy in Investment Casting. In: M. Tiryakioğlu MJaGB, (ed.). *Shape Casting: 6th International Symposium*. Wiley Online Library, 2016, p. 67-76.
17. Dai X and Jolly M. Potential energy savings by application of the novel CRIMSON aluminium casting process. *Applied Energy*. 2012; 89: 111-6.
18. Balogun VA and Mativenga PT. Modelling of direct energy requirements in mechanical machining processes. *Journal of Cleaner Production*. 2013; 41: 179-86.
19. Newman ST, Nassehi A, Imani-Asrai R and Dhokia V. Energy efficient process planning for CNC machining. *CIRP Journal of Manufacturing Science and Technology*. 2012; 5: 127-36.
20. Avram OI and Xirouchakis P. Evaluating the use phase energy requirements of a machine tool system. *Journal of Cleaner Production*. 2011; 19: 699-711.
21. Rajemi MF, Mativenga PT and Aramcharoen A. Sustainable machining: selection of optimum turning conditions based on minimum energy considerations. *Journal of Cleaner Production*. 2010; 18: 1059-65.
22. Bhushan RK. Optimization of cutting parameters for minimizing power consumption and maximizing tool life during machining of Al alloy SiC particle composites. *Journal of Cleaner Production*. 2013; 39: 242-54.
23. Lütjering G and Williams JC. *Titanium*. 2 ed. New York: Springer, 2007.
24. Shokrani A, Dhokia V and Newman ST. Environmentally conscious machining of difficult-to-machine materials with regard to cutting fluids. *International Journal of Machine Tools and Manufacture*. 2012; 57: 83-101.
25. Ezugwu EO and Wang ZM. Titanium alloys and their machinability—a review. *Journal of Materials Processing Technology*. 1997; 68: 262-74.

26. Bermingham M, Palanisamy S, Kent D and Dargusch M. A comparison of cryogenic and high pressure emulsion cooling technologies on tool life and chip morphology in Ti-6Al-4V cutting. *Journal of Materials Processing Technology*. 2011; 212: 752–65.
27. COSHH. COSHH essentials for machining with metalworking fluids. *Control of Substances Hazardous to Health (COSHH)*. Health and Safety Executive, 2015.
28. OSHA. Metalworking Fluids. Occupational Safety and Health Administration, 2015.
29. CCOHS. Metalworking Fluids. *Chemicals and Materials*. Canadian Centre for Occupational Health and Safety, 2015.
30. Hong SY and Broome M. Economical and ecological cryogenic machining of AISI 304 austenitic stainless steel. *Clean Technologies and Environmental Policy*. 2000; 2: 157-66.
31. Shokrani A, Dhokia V and Newman S. A Techno-Health Study of the Use of Cutting Fluids and Future Alternatives. *24th International Conference on Flexible Automation and Intelligent Manufacturing (FAIM 2014)*. San Antonio, Texas 2014.
32. Suuronen K, Aalto-Korte K, Piipari R, Tuomi T and Jolanki R. Occupational dermatitis and allergic respiratory diseases in Finnish metalworking machinists. *Occupational Medicine*. 2007; 57: 277-83.
33. Hannu T, Suuronen K, Aalto-Korte K, et al. Occupational respiratory and skin diseases among Finnish machinists: findings of a large clinical study. *International archives of occupational and environmental health*. 2013; 86: 189-97.
34. Clapp RW, Jacobs MM and Loechler EL. Environmental and occupational causes of cancer: new evidence 2005-2007. *Reviews on environmental health*. 2008; 23: 1-38.

35. Malloy EJ, Miller KL and Eisen EA. Rectal cancer and exposure to metalworking fluids in the automobile manufacturing industry. *Occupational and environmental medicine*. 2007; 64: 244-9.
36. Shokrani A, Dhokia V, Munoz-Escalona P and Newman S. State-of-the-art cryogenic machining and processing. *International Journal of Computer Integrated Manufacturing*. 2013; 26: 616-48.
37. Kaynak Y, Lu T and Jawahir I. Cryogenic Machining-Induced Surface Integrity: A Review and Comparison with Dry, MQL, and Flood-Cooled Machining. *Machining Science and Technology*. 2014; 18: 149-98.
38. Pusavec F, Krajnik P and Kopac J. Transitioning to sustainable production – Part I: application on machining technologies. *Journal of Cleaner Production*. 2010; 18: 174-84.
39. Hong SY and Ding Y. Cooling approaches and cutting temperatures in cryogenic machining of Ti-6Al-4V. *International Journal of Machine Tools and Manufacture*. 2001; 41: 1417-37.
40. Hong SY and Zhao Z. Thermal aspects, material considerations and cooling strategies in cryogenic machining. *Clean Technologies and Environmental Policy*. 1999; 1: 107-16.
41. Pusavec F and Kopac J. Achieving and Implementation of Sustainability Principles in Machining Processes. *Journal of Advances in Production Engineering and Management*. 2009; 3-4: 58-69.
42. Pušavec F and Kopač J. Sustainability assessment: cryogenic machining of Inconel 718. *Strojniški vestnik-Journal of Mechanical Engineering*. 2011; 57: 637-47.

43. Fratila D. Sustainable Manufacturing Through Environmentally-Friendly Machining. In: Davim PJ, (ed.). *Green Manufacturing Processes and Systems*. Berlin, Heidelberg: Springer Berlin Heidelberg, 2013, p. 1-21.
44. Truesdale S and Shin Y. Microstructural Analysis and Machinability Improvement of Udimet 720 Via Cryogenic Milling. *Machining Science and Technology*. 2009; 13: 1-19.
45. Lu T and Jawahir IS. Metrics-based Sustainability Evaluation of Cryogenic Machining. *Procedia CIRP*. 2015; 29: 520-5.
46. Kalpakjian S and Schmid S. *Manufacturing engineering and technology*. 6th ed. Upper Saddle River, New Jersey: Prentice Hall, 2009.
47. Shokrani A, Dhokia V and Newman ST. Study of the Effects of Cryogenic Machining on the Machinability of Ti-6Al-4V Titanium Alloy. *12th Euspen International Conference*. Stockholm2012.
48. Shokrani A, Dhokia V and Newman ST. Evaluation of Cryogenic CNC Milling of Ti-6Al-4V Titanium Alloy. *22nd International Conference on Flexible Automation and Intelligent Manufacturing*. Helsinki-Stockholm2012.
49. Shokrani A, Dhokia V and Newman ST. Investigation of the effects of cryogenic machining on surface integrity in CNC end milling of Ti-6Al-4V titanium alloy. *Journal of Manufacturing Processes*. 2016; 21: 172-9.
50. British-Standard-Institution. Accuracy (trueness and precision) of measurement methods and results-Part 1: General principles and definitions. London: BSI, 1994.
51. British-Standard-Institute. Accuracy (Trueness and Precision) of measurement methods and results – Part 3: Intermediate measures of the precision of a standard measurement method. *International Organization for Standardization, Geneva*. London: BSI, 1994.

52. Grzesik W. *Advanced machining processes of metallic materials: theory, modelling and applications*. Oxford: Elsevier Science, 2008.
53. ISO-8688-2. Tool life testing in milling -- Part 2: End milling. Geneva: International-Organization-for-Standardization, 1989.
54. Xin Q. *Diesel Engine System Design*. Cambridge: Woodhead Publishing, 2011, p.212-7.
55. Bordin A, Bruschi S, Ghiotti A and Bariani PF. Analysis of tool wear in cryogenic machining of additive manufactured Ti6Al4V alloy. *Wear*. 2015; 328–329: 89-99.
56. Venugopal K, Paul S and Chattopadhyay A. Tool wear in cryogenic turning of Ti-6Al-4V alloy. *Cryogenics*. 2007; 47: 12-8.
57. Venugopal K, Paul S and Chattopadhyay A. Growth of tool wear in turning of Ti-6Al-4V alloy under cryogenic cooling. *Wear*. 2007; 262: 1071-8.
58. Campbell FC. *Phase Diagrams - Understanding the Basics*. Materials Park, Ohio: ASM International, 2012.
59. Military Handbook, MIL-HDBK-5H: *Metallic Materials and Elements for Aerospace Vehicle Structures* (Knovel Interactive Edition). U.S. Department of Defense, 2003, p. 6-55.
60. Moosbrugger C. *Atlas of Stress Strain Curves, 2nd ed.*; . Materials Park, OH, USA: ASM International, 2002.
61. Kalyankumar K and Choudhury S. Investigation of tool wear and cutting force in cryogenic machining using design of experiments. *Journal of Materials Processing Technology*. 2008; 203: 95-101.

62. Hong SY, Markus I and Jeong W. New cooling approach and tool life improvement in cryogenic machining of titanium alloy Ti-6Al-4V. *International Journal of Machine Tools and Manufacture*. 2001; 41: 2245-60.
63. Khan A and Ahmed M. Improving tool life using cryogenic cooling. *Journal of Materials Processing Technology*. 2008; 196: 149-54.
64. Aggarwal A, Singh H, Kumar P and Singh M. Optimizing power consumption for CNC turned parts using response surface methodology and Taguchi's technique—A comparative analysis. *Journal of Materials Processing Technology*. 2008; 200: 373-84.
65. Aggarwal A, Singh H, Kumar P and Singh M. Optimization of multiple quality characteristics for CNC turning under cryogenic cutting environment using desirability function. *Journal of Materials Processing Technology*. 2008; 205: 42-50.
66. Hong SY, Ding Y and Jeong W. Friction and cutting forces in cryogenic machining of Ti-6Al-4V. *International Journal of Machine Tools and Manufacture*. 2001; 41: 2271-85.
67. Fratila D. Macro-level environmental comparison of near-dry machining and flood machining. *Journal of Cleaner Production*. 2010; 18: 1031-9.
68. Helu M, Behmann B, Meier H, Dornfeld D, Lanza G and Schulze V. Impact of green machining strategies on achieved surface quality. *CIRP Annals-Manufacturing Technology*. 2012; 61: 55-8.