

# PCCP

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: J. Patzsch, A. Folli, D. Macphee and J. Z. Bloh, *Phys. Chem. Chem. Phys.*, 2017, DOI: 10.1039/C7CP05960D.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [author guidelines](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the ethical guidelines, outlined in our [author and reviewer resource centre](#), still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

Cite this: DOI: 10.1039/xxxxxxxxxxx

# On the Underlying Mechanisms of the Low Observed Nitrate Selectivity in Photocatalytic NO<sub>x</sub> Abatement and the Importance of the Oxygen Reduction Reaction

Julia Patzsch,<sup>a</sup> Andrea Folli,<sup>b</sup> Donald E. Macphree<sup>c</sup> and Jonathan Z. Bloh<sup>\*a</sup>

Received Date

Accepted Date

DOI: 10.1039/xxxxxxxxxxx

www.rsc.org/journalname

Semiconductor photocatalysis could be an effective means to combat air pollution, especially nitrogen oxides, which can be mineralized to nitrate. However, the reaction typically shows poor selectivity, releasing a number of unwanted and possibly toxic intermediates such as nitrogen dioxide. Up to now, the underlying principles that lead to this poor selectivity were not understood so a knowledge-based catalyst design for more selective materials was impossible. Herein, we present strong evidence for the slow oxygen reduction being one the causes, as the competing back-reduction of nitrate leads to the release of nitrogen dioxide. Consequently, engineering the photocatalyst for a better oxygen reduction efficiency should also increase the nitrate selectivity.




## 1 Introduction

Nitrogen oxides (NO<sub>x</sub>), especially nitric oxide (NO) and nitrogen dioxide (NO<sub>2</sub>), play a major role in atmospheric chemistry and air pollution. Despite the presence of some natural emission processes, the majority of NO<sub>x</sub> emissions are formed anthropogenically in high-temperature processes such as internal combustion engines, gas- or oil-fired heating and industrial furnaces.<sup>1</sup> They constitute a major environmental and health concern as they are toxic compounds and also facilitate the formation of ozone and acid rain.<sup>2,3</sup> As a consequence, increasingly stronger regulations and policies are in place enforcing actions to reduce emissions and to lower the overall pollutant levels.<sup>4</sup> However, recent studies and events have shown that in many European cities emission standards are frequently exceeded as well as emission treatment systems not being as efficient as they are claimed to be.<sup>5–7</sup>

Apart from reducing the emissions directly at the emission source, which appears to be more difficult than anticipated, semiconductor photocatalysis presents an appealing alternative capable of removing NO<sub>x</sub> and other air pollutants from the air once they have already been released and dispersed.<sup>8</sup> Additionally, photocatalysis needs neither maintenance nor external reagents, since the only requirements are sunlight, water and molecular oxygen, which are already present in outdoor conditions.

Nitrogen monoxide can be oxidized over illuminated titanium

dioxide by hydroxyl radicals which are formed by water oxidation or by hydroperoxyl radicals, eqns. 2,3 and 10. The products of this oxidation, nitrous acid (HONO) or nitrogen dioxide (NO<sub>2</sub>), can be further oxidized to eventually form nitric acid or nitrate (HONO<sub>2</sub>/NO<sub>3</sub><sup>−</sup>), eqns. 4–5. The nitrate will remain on the photocatalyst until it is washed off during the next rainfall.








On the other hand, the photo-generated conduction band electrons typically react with the ubiquitous molecular oxygen, forming superoxide radicals and hydroperoxyl radicals after subsequent protonation, eqn. 6. The so formed hydroperoxyl radical may either take up an additional conduction band electron, eqn. 7, or react with NO, eqn. 10, forming hydrogen peroxide or hydroxyl radicals, respectively. In the latter case, the oxidation of NO to NO<sub>2</sub> constitutes two oxidation equivalents. The peroxide can subsequently be reduced in two steps to a hydroxyl radical, eqn. 8, and then water, eqn. 9. Hydrogen peroxide can also directly oxidize nitrogen oxides, eqn. 11, serving as an oxidation equivalent and also releasing an additional hydroxyl radical in the process. Overall, in the optimal case the reductive pathway of photocatalysis can yield up to 3 oxidation equivalents per re-

<sup>a</sup> DECHEMA-Forschungsinstitut, Theodor-Heuss-Allee 25, 60486 Frankfurt am Main, Germany; E-mail: bloh@dechema.de

<sup>b</sup> School of Chemistry, Cardiff University, Main Building, Park Place, Cardiff CF10 3AT, Wales, United Kingdom.

<sup>c</sup> University of Aberdeen, Department of Chemistry, Meston Walk, Aberdeen AB24 3UE, United Kingdom.


active photon, effectively quadrupling the oxidation rate. This is expected to mainly take place when the overall generation rate of charge carriers is low and the concentration of nitrogen oxides is high, so that unproductive consecutive reduction events are less likely. In the worst case, molecular oxygen takes up 4 conduction band electrons to convert to water, yielding no oxidation equivalents. This highlights the immense importance of the reductive pathway in the photocatalytic  $\text{NO}_x$  abatement.



All of the intermediate species mentioned above, namely nitrous acid and nitrogen dioxide, may also be released during the reaction if they are not converted fast enough. This can be expressed as the nitrate selectivity of the reaction, *i.e.*, how much of the nitrogen oxide is directly converted to nitrate and not released as intermediates. Unfortunately, this selectivity is rather low for unmodified titanium dioxide photocatalysts, which display values from only 7 to 39 %, meaning that the majority is released as nitrogen dioxide instead of the desired product, nitrate.<sup>9</sup> This is a major problem for the targeted application as air pollution control as nitrogen dioxide is much more toxic than nitrogen monoxide, so the photocatalyst bears the potential to make the situation worse rather than better.<sup>9</sup> For instance, the commonly used P25 photocatalyst shows an net increase in  $\text{NO}_2$  concentration upon being illuminated in a 1:1 mixture of NO and  $\text{NO}_2$ , which not untypical for environmental conditions, *cf.* Figures S2-S3.

The typical behaviour of a photocatalyst during the  $\text{NO}_x$  abatement is illustrated in Figure 1 on the basis of Evonik Degussa Aeroxide P25 powder; it has been shown that virtually all unmodified commercial  $\text{TiO}_2$  photocatalysts behave similarly.<sup>9</sup> It can be seen that the activity of the sample is quite good, almost half of the supplied NO is converted ( $\gamma \approx 4.4 \times 10^{-5}$ ), however, the main product of the reaction is not the desired nitrate but  $\text{NO}_2$  (or HONO as the employed analyzer cannot distinguish between the two).<sup>10-12</sup> At the beginning of the experiment, the selectivity is already poor at approximately 32 %, followed by a sharp drop to about 23 % in the first hour of illumination with a continued less steep but steady decline afterwards. The absolute activity of NO conversion also decreases with time, while the  $\text{NO}_2$  formation seems to be less affected by this with a barely noticeable smaller decline, resulting in the lower selectivity.

The adsorption capacity for  $\text{NO}_2$  on  $\text{TiO}_2$  is much higher than that for NO and should therefore buffer the  $\text{NO}_2$  formation to some extent.<sup>13</sup> However, significant  $\text{NO}_2$  evolution is usually observed immediately upon illumination. This illustrates, that there

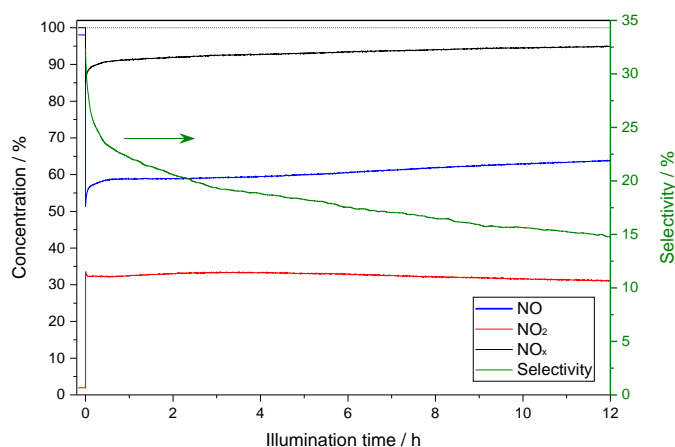

**Fig. 1** A representative experiment for the photocatalytic oxidation of nitric oxide (NO) according to ISO 22197-1 using Aeroxide P25 powder. Plotted are the relative concentrations of NO (blue),  $\text{NO}_2$  (red) and  $\text{NO}_x$  (black) on the left axis as well as the selectivity towards the desired product nitrate (green) on the right axis.

are two different mechanisms to consider. First there is the intrinsic activity of a material which is observed at the very beginning of an experiment with a clean surface. This intrinsic activity is likely governed by the individual NO and  $\text{NO}_2$  reaction rates as well as their adsorption behaviour on the catalyst. However, if this was the only mechanism at work, the selectivity should be constant in prolonged experiments. The only thing changing over time is the amount of nitrate adsorbed on the surface, which will inevitably reduce the catalyst's activity by blocking adsorption sites.

If the activity decrease was solely due to blocked surface adsorption sites by accumulated nitrate, it should affect the respective reaction rates of NO and  $\text{NO}_2$  by the same factor, leading to an overall decrease in activity but still the same selectivity. However, in the experiments, while the rate of NO oxidation drops during prolonged experiments, the rate of  $\text{NO}_2$  evolution stays nearly constant and is seemingly unaffected by the reduced oxidation rate of NO, which should lead to lower  $\text{NO}_2$  formation. Also, experiments at different inlet concentrations of NO allow to create different ratios of NO and  $\text{NO}_2$  reaction rates as the former shows mixed zero and first order kinetics while the latter is ideal first order. For a simple follow-up reaction one would expect the selectivity to have a strong dependence on the ratio between the first and second step reaction rates. However, as seen in Table S1, while this ratio changes from 5 to 15 with lowered inlet concentration, the observed selectivity stays virtually identical. This disconnection between  $\text{NO}_2$  evolution rate and both the NO oxidation rate and the degree of free surface adsorption sites leads us to believe that the release of  $\text{NO}_2$  as an intermediate species in the oxidation pathway cannot be the sole cause of the observed  $\text{NO}_2$  evolution.

There rather seems to be an additional mechanism in place that leads to a significant decrease in selectivity in the prolonged experiments. As essentially, the only thing changing is the concentration of accumulated nitrate on the surface, this is likely the cause for the observed phenomenon. This nitrate accumulation

seems to poison the catalyst in a way that not only reduces its activity due to blocked surface sites but also reduces its selectivity. The latter effect is also much more pronounced and is noticeable at far lower nitrate coverages. In the present example with P25, the activity for NO oxidation, expressed as the apparent first order rate constant, decreases by only 0.4 % from  $0.894 \text{ s}^{-1}$  to  $0.890 \text{ s}^{-1}$  from 1 hour to 2 hour illumination time. In the same time-frame, however, the selectivity decreases by 7.9 % from 22.3 % to 20.5 %.

## 2 Proposed mechanism of the observed selectivity decline


When considering the mechanism of photocatalytic  $\text{NO}_x$  oxidation, nitrate or nitric acid is often considered to be the inert end product of the reaction which stays on the photocatalyst surface until it is eventually washed off by rain. However, there are some experiments which show that a nitrate-rich or nitrate-saturated photocatalyst surface can release significant amounts of  $\text{NO}_2$  upon illumination, even in an  $\text{NO}_x$  free atmosphere.<sup>14</sup> Presumably, this is caused by a photocatalytic reaction with adsorbed nitrate to nitrogen dioxide, which is subsequently desorbed and released. Previously, this has been attributed to photocatalytic oxidation of nitrate to  $\text{NO}_3$  with subsequent photolysis, leading to NO,  $\text{NO}_2$  and  $\text{O}_3$ .<sup>12,14</sup> However, in these studies  $\text{NO}_3$  was never actually detected and it was observed that the evolution of  $\text{NO}_x$  during irradiation of a nitrate-saturated  $\text{TiO}_2$ -surface is much higher in nitrogen than in air atmosphere, which suggests that oxygen suppresses the mechanism. Also in the former case, no suitable reduction mechanism was reported in the absence of oxygen as an electron acceptor. Therefore, we propose here that nitrate adsorbed on  $\text{TiO}_2$  can also be photocatalytically reduced, this will directly yield  $\text{NO}_2$  via reaction 12. We cannot say whether the previously proposed oxidation pathway via  $\text{NO}_3$  also takes place simultaneously, but from the strong dependence on the oxygen concentration we suspect the reduction pathway to be predominant. Nitrogen dioxide formed through these "renoxification" processes, rather than as an intermediate in the oxidation pathway, can be a major contributor of the observed nitrogen dioxide evolution during photocatalytic NO oxidation and is the likely cause for the drop in selectivity in prolonged experiments. Studies by Monge et al. have also shown HONO as a minor by-product of the renoxification, presumably formed by further reduction of  $\text{NO}_2$ .<sup>12,14</sup>



The adsorbed nitrate on the titanium dioxide will be in constant competition with molecular oxygen for the electrons. Unfortunately, as already outlined by Gerischer and Heller in 1991, oxygen reduction on titanium dioxide proceeds slowly and will often present the rate-determining step of the overall reaction unless oxygen reduction promoting co-catalysts are employed.<sup>15</sup> However, if an alternative electron acceptor is present, titanium dioxide will readily reduce it. At a reduction potential of  $+0.80 \text{ V}_{\text{RHE}}$ ,<sup>16</sup> nitrate is a much better electron acceptor than molecular oxygen at  $-0.05 \text{ V}_{\text{RHE}}$  (one-electron-reduction)<sup>17</sup>. Therefore, the reduction of nitrate is actually ther-

modynamically favoured in comparison with molecular oxygen.

Taking reaction constants obtained in stopped-flow experiments in liquid media as an indication, the reduction of oxygen and nitrate should proceed with similar reaction rates.<sup>18,19</sup> The situation in the gas phase might be different and might more closely resemble the respective redox potentials, resulting in a higher rate for nitrate than for oxygen; the following considerations should therefore be taken as a conservative estimate where the real behaviour might favour nitrate reduction even more. While oxygen is usually much more concentrated in ambient air than the  $\text{NO}_x$  species by 6-8 orders of magnitude, it is already enriched and immobilized on the photocatalyst surface and does not have to adsorb first. When considering the surface coverage as the rate determining element rather than the concentration in air, the situation looks much more in favour for nitrate. Ignoring the contribution of other adsorbed species such as NO,  $\text{NO}_2^-$  or  $\text{NO}_2$ , since they are expected at relatively low concentrations, the surface coverage of oxygen and nitrate can be calculated using known adsorption constants for water ( $K_{\text{H}_2\text{O}} = 50.7 \text{ m}^3 \text{ mol}^{-1}$ )<sup>20</sup> and oxygen ( $K_{\text{O}_2} = 0.62 \text{ m}^3 \text{ mol}^{-1}$ )<sup>21</sup> and Langmuirian adsorption behaviour for competitive adsorption. The resulting surface coverage and relative reduction rate of nitrate (assuming identical reaction constants) for a model case of 50 % relative humidity can be seen in Figure 2.

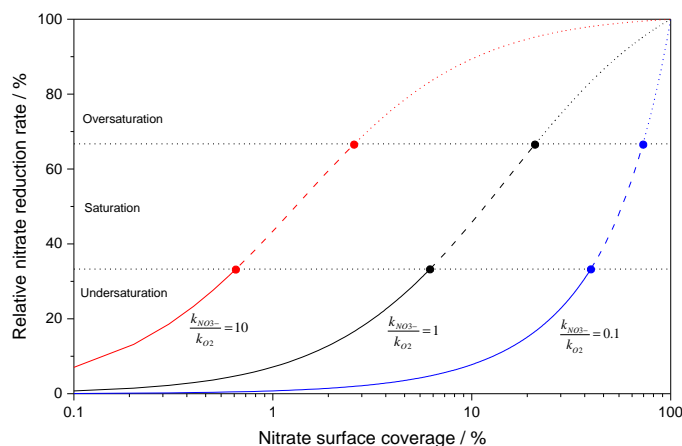

**Fig. 2** The calculated relative nitrate reduction rate calculated according to eqn. 23 assuming 50 % relative humidity. The reaction constant for nitrate reduction is assumed to be identical (black) as well as ten times higher (red) or lower (blue) than the oxygen reduction constant, respectively. Also displayed is the expected regime for saturation if pure NO gas is used.




Surprisingly, even at a nitrate surface coverage of only a few percent, a significant amount of electrons ends up reducing nitrate instead of oxygen. At 6.1 % coverage, already a third of the electrons reduce nitrate. The diagram also shows the situation when the nitrate reduction is ten times faster than oxygen reduction, which given the redox potentials is not unrealistic, and when it is ten times smaller. In the former case, a third of the electrons reduce nitrate already at a nitrate surface coverage of 0.7 % while in the latter case, it takes a coverage of 40 % to achieve the same effect. A higher humidity will also further favour nitrate re-



duction, as adsorption sites for oxygen will be further diminished by additional adsorbed water, closely resembling the experimentally observed behaviour that the selectivity drops notably with increasing humidity.<sup>22</sup> Note that this calculation is neither accurate nor quantitative, as this would require presently not available precise data of the reduction constants for both nitrate and oxygen in the gas phase as well as on the competitive adsorption behaviour of nitrate, water and oxygen. This calculation can, however, give a rough estimate of the qualitative behaviour of the system and illustrate the immense importance of the oxygen reduction rate.

### 3 Consequences of nitrate reduction

Each electron reducing a nitrate molecule effectively neutralises one direct oxidation equivalent and up to three indirect oxidation equivalent by preventing the formation of a superoxide radical. Consequently, this reaction pathway is very detrimental to the overall reaction balance and should be prevented as much as possible. At some point, the chemical potential for nitrate reduction will be so high that it will completely counteract the oxidative pathway and the net nitrate concentration will be constant through the reactions 13, 6, 10, 5 and 12, resulting in the net reaction 14:



This situation will be reached when one third to two thirds of the electrons end up reducing nitrate instead of oxygen, depending on the reaction pathway, *i.e.*, how many oxidation equivalents are generated by the reduced oxygen (0 to 3). Keep in mind that, according to our previous calculation, this can already happen at a nitrate surface coverage as low as 6 % (or 0.7 % if the nitrate reduction rate is ten times higher than estimated). At this point, the photocatalyst will stop reducing the overall  $\text{NO}_x$  level entirely and just turn into a very effective converter of NO to  $\text{NO}_2$ . This is exactly what is being observed when  $\text{TiO}_2$  films are exposed NO and irradiated long enough for this equilibrium to occur. Mills and co-workers reported that  $\text{TiO}_2$ -coated glass slides show this behaviour already after a couple of hours of illumination under ISO 22197-1 conditions.<sup>23</sup> Similar findings were also reported by Okho *et al.* who observed nitrate saturation of a  $\text{TiO}_2$  thin film after just an hour of illumination.<sup>24</sup>

These very thin films are naturally prone to be saturated fast as they do not have a large surface area and porosity to absorb a large amount of nitrate. Note that this situation does not represent full surface coverage with nitrate but merely a situation

where the formation and reduction rates of nitrate are equal. Complete nitrate coverage can be achieved by using pure  $\text{NO}_2$  gas in the experiment, as only one oxidation equivalent (as compared to three for NO) is necessary for nitrate formation, thus keeping the balance with the corresponding electron reducing a nitrate ion. Under these conditions, roughly four times as much nitrate can be deposited onto  $\text{TiO}_2$  when compared to using pure NO gas.<sup>24,25</sup> Saturation does not occur very fast with powders or thicker layers as the nitrate formed on the exposed surface can easily diffuse to deeper layers which are photocatalytically inactive but serve as reservoir to dilute the nitrate coverage on the photocatalytically active exposed surface.<sup>25</sup> Similar effects can be achieved by mixing the photocatalyst with high surface area adsorber materials such as activated carbon or cementitious matrices.<sup>26–28</sup> This effect will keep the effective nitrate coverage relatively constant for a long time while the reservoir is being filled, leading to the quasi-equilibrium selectivity often observed on powder samples after some irradiation time.<sup>9</sup> This means that for thicker samples, the nitrate surface coverage on the photocatalytically active part will be quasi-stationary for a very broad operational window where the rate of newly formed nitrate on the exposed surface is very similar to the transport to deeper layers. This will likely represent the situation in real world scenarios for most of the time and should therefore be considered for photocatalyst evaluation procedures.

If the system is artificially oversaturated, *e.g.* by adsorbing high amounts of nitrate on the photocatalyst prior to the experiment, it will reduce the excess nitrate under illumination and release it as  $\text{NO}_2$  until the equilibrium is restored.<sup>24</sup>

The saturation situation where  $\text{TiO}_2$  just converts NO to  $\text{NO}_2$  (eqn. 14) is to be avoided at all costs as if it happens in real world scenarios as it will lead to an overall increase in ambient  $\text{NO}_2$  levels. It is therefore paramount that the photocatalyst never reaches critical nitrate surface coverage in between regenerating rainfalls. This allowable period can be extended by just using a larger amount of photocatalyst or an alternative adsorber so the adsorption capacity is increased.<sup>29,30</sup> However, if this adsorbed nitrate in deeper layers of the adsorber can be readily washed off by rainfall and thus regenerated is not certain yet so this might only lead to a one-time effect that will not matter in the long term. An alternative or complementary approach is to modify the photocatalyst in a way that effectively suppresses the nitrate reduction pathway.

### 4 Suppressing the nitrate reduction

Suppressing this unwanted side-reaction could be achieved by lowering the amount of nitrate on the catalyst surface or by making the alternative reduction reactions such as oxygen reduction more favourable. The former seems impossible to achieve as nitrate is the ultimate product of the  $\text{NO}_x$  oxidation reaction and will always be formed on an active catalyst. This leaves making the oxygen reduction more favourable in comparison to nitrate reduction as the only viable option. This can be achieved by producing specific surface sites or employing co-catalysts which either directly improve electron transfer to oxygen or unlock the multi-electron reductions which are normally kinetically hindered on

titanium dioxide. These multi-electron reductions, *cf.* eqns. 15–16, feature more positive redox potentials and are thus thermodynamically favoured. The former would be more beneficial in this context as it would still generate oxidative species ( $\text{H}_2\text{O}_2$ ) that could participate in the  $\text{NO}_x$  oxidation reactions.



If the relative rate of oxygen reduction can be increased by an order of magnitude, it will have a dramatic effect on the nitrate reduction reaction, effectively suppressing it until very high nitrate surface coverages are reached, *cf.* Figure 2. Also, at the same surface coverage, nitrogen dioxide release through nitrate reduction will be suppressed considerably, resulting in a significantly increased apparent selectivity. This might also explain the different selectivity of the three common titanium dioxide modifications, anatase, rutile and brookite. We recently reported that brookite (39 %) is the most selective of the three, closely followed by anatase (25 to 29 %), while pure rutile is very unselective (6 to 7 %).<sup>9</sup> This can be readily explained by their different conduction band potentials, which at  $-0.4 \text{ V}_{\text{RHE}}$ ,  $-0.2 \text{ V}_{\text{RHE}}$  and  $0.0 \text{ V}_{\text{RHE}}$ , respectively, are increasingly unsuitable for oxygen reduction at  $-0.05 \text{ V}_{\text{RHE}}$ .<sup>31–33</sup>

To prove that oxygen plays a major role in the selectivity mechanism, experiments were performed under both synthetic air (20 %  $\text{O}_2$  / 80 %  $\text{N}_2$ ) and pure oxygen atmospheres using Aeroxide P25 powders. The results for both pure NO and pure  $\text{NO}_2$  as reactants, both in 1 ppm concentration, yielded the respective apparent first order reaction constants and the selectivity towards nitrate, *cf.* Table 1.

Under oxygen atmosphere the apparent rate constant for NO oxidation is increased by 55 % compared to synthetic air atmosphere while keeping essentially the same initial selectivity. The  $\text{NO}_2$  oxidation rate, on the other hand, is not significantly altered so that the ratio of NO to  $\text{NO}_2$  reaction rates is increased by about 50 %. This should promote accumulation of the intermediate,  $\text{NO}_2$ , and should lead to a lower observed selectivity under oxygen atmosphere, which is not observed - showing yet again that the slow follow-up reaction of  $\text{NO}_2$  cannot explain the observed low selectivity.

The nitrate surface coverage at a specific time can be calculated from the amount of formed nitrate, eqn. 17:

$$\theta(t) = \frac{\dot{V} \cdot p \cdot N_A}{R \cdot T \cdot m \cdot S_A \cdot \theta_{\max}} \cdot \int_0^t (c(\text{NO}_x)_{\text{in}}(t) - c(\text{NO}_x)_{\text{out}}(t)) dt \quad (17)$$


with the volume flux ( $\dot{V}$ ), pressure ( $p$ ), Avogadro's constant ( $N_A$ ), gas constant ( $R$ ), absolute temperature ( $T$ ), mass of catalyst ( $m$ ), its specific surface area ( $S_A$ ) and the maximum nitrate surface coverage ( $\theta_{\max} = 2 \text{ nm}^{-2}$ ).<sup>25</sup>

Based on the idea that the nitrate reduction is the sole reason for decreasing selectivity with longer reaction times, we developed a model to describe the relationship between observed se-

lectivity and nitrate surface coverage, eqn. 18. In this equation,  $S_0$  represents the initial or intrinsic selectivity of the sample when no nitrate is yet present,  $k_o$  is a dimensionless figure for the relative oxygen reduction rate (*cf.* eqn. 24) and  $\alpha$  is a factor that describes how soon oxygen reduction switches between four-, two- and one-electron reduction pathway. A detailed derivation of the formula is presented in section 8.

$$S(\theta) = S_0 - \theta \cdot \frac{(2 + S_0)(4 - 3(1 - e^{-\alpha\theta}))}{4(\theta + k_o(1 - \theta)) - 3\theta(1 - e^{-\alpha\theta})} \quad (18)$$

Using this equation, selectivity-nitrate coverage profiles of different catalysts can be analysed to extract intrinsic selectivity and relative oxygen reduction rates. In order to prove the involvement of oxygen in the mechanism, experiments in both air and pure oxygen were conducted. As can be seen in Figure 3, while the initial selectivity under both conditions is effectively identical, the selectivity drops about twice as fast with increasing surface coverage under synthetic air compared to under oxygen atmosphere.

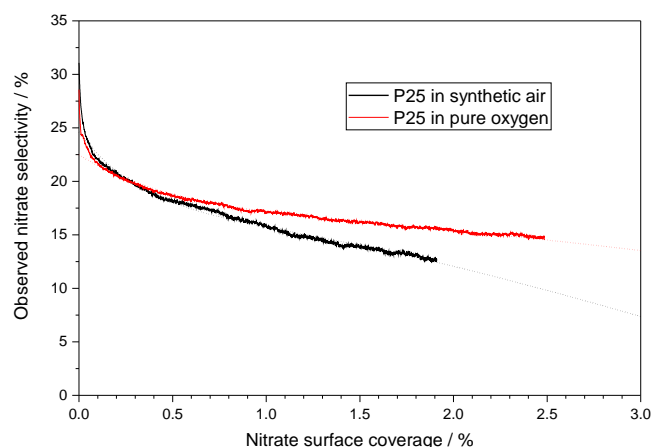

**Fig. 3** The observed nitrate selectivity ( $X_{\text{NO}_x}/X_{\text{NO}}$ ) of a P25 sample with 1 ppm NO under synthetic air (black) and pure oxygen conditions (red), plotted against the nitrate surface coverage calculated using eqn. 17. Dotted lines depict the modelling according to eqn. 18.

This illustrates that the higher oxygen reduction rate resulting from the higher oxygen partial pressure and consequently higher oxygen surface coverage mitigates the detrimental effect of increasing nitrate surface coverage on the selectivity. After an initial very fast decay, presumably caused by transient effects such as adsorption and light induced surface remodelling, the plot shows the predicted behaviour according to eqn. 18 and can be fit with good precision. The resulting  $k_o$  values are 0.095 and 0.203 for for synthetic air and oxygen atmosphere, respectively, while the intrinsic selectivity  $S_0$  is very similar, 24.6 % and 22.5 %. This is a very strong indication for the involvement of the oxygen reduction reaction in the mechanism responsible for the decrease in selectivity at longer irradiation times. However, the low initial or intrinsic selectivity of the material could not be altered simply by increasing the oxygen concentration.

**Table 1** Comparison of apparent first-order rate constants ( $k$ ), reactive uptake coefficients ( $\gamma$ ) and selectivity ( $S$ ) of NO and NO<sub>2</sub> after 2 h of reaction in both synthetic air and oxygen atmosphere. At this point, most transient effects such as adsorption have worn off while the effect of the nitrate surface coverage is still negligible ( $\theta < 0.5\%$ ).

Atmosphere	$k_{\text{NO}} / \text{s}^{-1}$	$\gamma_{\text{NO}} / -$	$k_{\text{NO}_2} / \text{s}^{-1}$	$\gamma_{\text{NO}_2} / -$	Ratio NO/NO <sub>2</sub>	$S / \%$
20 % O <sub>2</sub> / 80 % N <sub>2</sub>	1.018	$4.48 \times 10^{-5}$	0.156	$8.49 \times 10^{-6}$	6.53	19.6
100 % O <sub>2</sub>	1.586	$6.97 \times 10^{-5}$	0.164	$8.93 \times 10^{-6}$	9.67	19.4

## 5 Examples of more selective catalysts

There are several reported examples of modified photocatalysts where the observed nitrate selectivity was significantly increased. These can be taken as case studies to see if the abovementioned hypothesis holds true. Keep in mind that this can either be increased selectivity from a higher intrinsic selectivity or from a higher nitrate tolerance, *i.e.*, slower drop in selectivity with increasing illumination time. Which of the two is present is difficult to say due to the difference in employed reaction conditions.

One way to achieve a higher selectivity is by using platinum as a co-catalyst. As shown recently, the observed nitrate selectivity could be improved from 25 % for pristine titanium dioxide to 65 % by adding 0.4 % of platinum to the material.<sup>34</sup> The oxygen reduction capabilities of the photocatalysts were not directly measured in this study, however, it is well known that platinum nanoparticles greatly enhance the oxygen reduction rate on TiO<sub>2</sub>.<sup>35–37</sup> In a similar fashion, a recent study by Fujiwara *et al.* used palladium as a co-catalyst, another well known oxygen reduction catalyst.<sup>36,38,39</sup> Here, by adding 1 wt % of palladium, the nitrate selectivity was increased from 13 % to up to 48 % while at the same time, the absolute activity also increased significantly. However, due to their limited production and unfavorable economics, using platinum-group metals (PGM) even in sub-percent concentrations would be challenging for large volume applications in building materials such as concrete.

Recently, we also reported on the properties of W-doped and W/N-codoped titanium dioxide.<sup>9,33,40,41</sup> These materials also show dramatically enhanced selectivity towards nitrate of more than 80 % when doped with a least 4.8 at.% of tungsten. Unfortunately, this beneficial property comes at the expense of absolute NO<sub>x</sub> abatement activity, which in turn decreases by a factor of 4. The increased selectivity is also accompanied by improved oxygen reduction capabilities as determined by oxygen reduction current measurements.<sup>42</sup> Interestingly, these materials do not seem to evolve any nitrous gases when a nitrate-saturated sample is exposed to UV radiation. This is further evidence for the theory that enhanced oxygen reduction suppresses competitive nitrate reduction which in turn leads to higher observed selectivity.

The same procedure can also be applied to other semiconductors. We recently reported several studies on zinc oxide for NO<sub>x</sub> abatement.<sup>43,44</sup> While zinc oxide seems to be more selective intrinsically, showing 55 % nitrate selectivity as a pristine material, it can be further improved by decorating the particles with transition metals that facilitate the oxygen reduction reaction.<sup>44</sup> The selectivity is increased from 55 % to 87 % by just adding 0.1 at.% of ruthenium.<sup>44</sup> Higher concentrations of the metal do not further increase activity or selectivity. Interestingly, while the conversion of NO is decreased for the ruthenium-modified samples,

owing to the higher selectivity, the overall conversion of NO<sub>x</sub> is slightly increased.<sup>44</sup> These changes are accompanied by an increased oxygen-reduction capability, which is increased by the factor of 14 in comparison to pristine ZnO.<sup>44</sup> Another example is manganese-modified zinc oxide.<sup>43,44</sup> These materials exhibit very high selectivity towards nitrate of 85 % or higher when modified with at least 1 at.% of manganese.<sup>45</sup> The selectivity increase is accompanied by a dramatic increase in oxygen reduction capability, as seen in oxygen reduction current measurements.<sup>44,45</sup> Both, the onset of oxygen reduction is shifted anodically, indicating multi-electron-reduction, as well as the current is higher than in pristine zinc oxide by a factor of up to ten. However, as in the case of W-doped TiO<sub>2</sub>, the absolute NO<sub>x</sub>-abatement activity of the samples is lowered when compared to pristine ZnO by a factor of 4.<sup>45</sup>

Up to now, more selective DeNO<sub>x</sub> photocatalysts have either utilized very expensive metal co-catalysts (Pt, Pd, Ru) or the selectivity increase was accompanied by a reduction in absolute activity (Mn-modified ZnO, W-doped TiO<sub>2</sub>). The former are unsuitable for the large-scale application in building materials as even using very low amounts of noble metals will increase the catalysts price by several orders of magnitude. The latter might be suitable for large-scale application but their lowered activity will reduce the overall efficacy of the material.

While we do not yet have definite proof of the proposed mechanism of increased selectivity, all experimental evidence gathered, both by ourselves and independently by other groups, points towards enhanced oxygen reduction being the cause of the increased selectivity. If this is the case, it can be achieved with far easier means than the previously mentioned examples.

It is well known that grafting a photocatalyst with transition metal ions such as Cu<sup>2+</sup> or Fe<sup>3+</sup> significantly increases their oxygen reduction capabilities.<sup>46–48</sup> The grafting can easily be achieved with wet impregnation techniques and only uses very small amounts of abundant and affordable elements. As an additional benefit, the modification is usually accompanied by an increase in observed activity due to the enhanced charge separation and as a direct result of improved oxygen reduction as well as a slight visible light activity. If our theory holds true, these materials should also exhibit higher nitrate selectivity in NO<sub>x</sub> abatement experiments, while avoiding all the negative side-effects of the previously mentioned approaches.

## 6 Conclusion

The nitrate that is formed during the photocatalytic NO<sub>x</sub> abatement is not just a non-reactive end-product but leads to nitrate poisoning of the catalyst, resulting in lower activity but more significantly, in greatly reduced selectivity. The latter is likely a result

from the back-reduction of nitrate, a competitive reaction to the reduction of molecular oxygen.

This unwanted and extremely detrimental reaction can be effectively suppressed by making the oxygen reduction more favorable in comparison, e.g., by increasing the oxygen partial pressure or by modifying the photocatalyst with oxygen-reduction co-catalysts. An analysis of reports of more selective photocatalysts revealed that all of them have improved oxygen-reduction capabilities, as well.

If this is done in a controlled way that does not compromise the intrinsic photocatalytic activity of the material, such as selectively doping or grafting the surface with a very small concentration of co-catalysts, the increased selectivity could probably be achieved without any negative side-effects. Consequently, these materials would be much better suited for the application in building materials for environmental air pollution reduction and should replace the currently employed first-generation photocatalysts.

Also, research should be devoted to determining the expected duration the photocatalyst will experience in the field between regenerating rainfalls and the amount of nitrate surface coverage that is achieved in that interval. This state will ultimately represent the real world working conditions and this presently lacking information will help to further optimize the catalyst with respect to minimizing its nitrogen dioxide forming potential. Evaluation of photocatalyst materials in the laboratory, which are at present usually performed on freshly prepared nitrate-free materials, should also be done at nitrate surface saturation conditions that better resemble expected real world scenarios.

## 7 Experimental details

The  $\text{NO}_x$  abatement experiments were performed in a setup according to the international standard ISO 22197-1.<sup>49</sup> The nitrogen oxide gas, either nitrogen monoxide or dioxide, was supplied as a concentrated test gas mixture and was diluted to 1 ppm and  $3 \text{ L min}^{-1}$  flow rate by both a dry and wet synthetic air stream and made up to 50 % relative humidity. This test gas mixture was then passed through the photocatalytic reactor made out of PEEK which comprises a sample holder with the dimensions of  $5 \times 10 \text{ cm}^2$ , in which the photocatalyst powder was placed. Approximately 2.8 g of the photocatalyst powders were uniformly dispersed on the sample holder and slightly pressed on with a flat plunger to form a uniform flat surface. The sample holder is illuminated from above through a UVA transparent cover glass by a 365 nm UVA-LED-array (Omicron Laserage Laserprodukte GmbH, Germany) which is calibrated to deliver an irradiance of  $10 \text{ W m}^{-2}$  at the sample surface. The gas stream is passed above the sample through a 5 mm high slit that is regularly reduced to 1 mm by turbulence barriers, which was reported to improve mass transfer (see Ifang *et al.* for details)<sup>50</sup>. All tubing and connections were made of polymers to avoid metal surfaces which could catalytically convert the  $\text{NO}_x$ . The resulting gas stream was analyzed using an environmental  $\text{NO}_x$  analyzer (Horiba APNA-370). It should be noted that the used analyzer does not discriminate between HONO and  $\text{NO}_2$  but measures both as  $\text{NO}_2$ . Consequently, all values reported herein for  $\text{NO}_x$  are strictly speaking  $\text{NO}_y$ .

The changes in the concentrations of the pollutants were used

to calculate the conversions ( $X = 1 - c/c_0$ ) and the nitrate selectivity ( $S = \frac{X_{\text{NO}_3}}{X_{\text{NO}}}$ ). From these, apparent first order rate constants were calculated according to eqn. 19.<sup>50</sup>

$$k = -\frac{\ln(c/c_0)}{\tau} \quad (19)$$

Since the residence time ( $\tau$ ) in the reactor is 0.5 s, the formula can be rewritten as eqn. 20.

$$k = -2 \cdot \ln(1 - X) \cdot \text{s}^{-1} \quad (20)$$

In order to make the data more comparable and setup-independent, reactive uptake coefficients ( $\gamma$ ) have been calculated according to eqn. 21, with a surface-to-volume ratio ( $S/V$ ) of  $200 \text{ m}^{-1}$  for the ISO setup.<sup>50</sup> Factors for converting rate constants into reactive uptake coefficients for the given system are  $4.397 \times 10^{-5} \text{ s}$  for NO and  $5.445 \times 10^{-5} \text{ s}$  for  $\text{NO}_2$ , respectively.

$$\gamma = \frac{4 \cdot k}{\bar{v} \cdot S/V} \quad (21)$$

It should be noted that the kinetic constants for NO oxidation determined this way are imprecise and likely significantly underestimated. The reason for this is twofold. First, for the given system the kinetics are not ideal first order but mixed first and zero order, cf. Figure S1. Also, for the high conversion values observed, the reaction is significantly influenced by mass transfer.<sup>23</sup> Therefore, the data are reported as apparent first order kinetic constants and should only be taken as a lower limit, the real values are likely significantly higher. Unfortunately, an accurate determination of the kinetic constants would require both very low pollutant gas concentration and significantly lowered light intensity to achieve both ideal first order kinetics and a low conversion. This negatively impacts the precision of the measurement but more importantly, makes the results not readily transferable to ISO conditions, under which most reported experiments are performed. We therefore chose this imprecise approach in order to retain comparability with the majority of the literature.

The above limitation does not hold true for the case of  $\text{NO}_2$ , which shows ideal first order behavior in the concentration range studied and also shows low conversion which should not be significantly influenced by mass transfer limitations.

## 8 Model derivation

The surface coverage of oxygen ( $\theta_{\text{O}_2}$ ) as a function of nitrate surface coverage ( $\theta_{\text{NO}_3}$ ) and relative humidity ( $k_{\text{H}_2\text{O}}$ ) can be calculated according to eqn. 22 using Langmuir isotherms for competitive adsorption and the respective adsorption constants  $K_{\text{O}_2}$ ,  $K_{\text{H}_2\text{O}}$ . Here, it is assumed that only water and molecular oxygen competitively adsorb on the surface and all other gas phase constituents have negligible influence on the adsorption behavior.

$$\theta_{\text{O}_2} = \frac{K_{\text{O}_2} \cdot c_{\text{O}_2}}{K_{\text{O}_2} \cdot c_{\text{O}_2} + K_{\text{H}_2\text{O}} \cdot c_{\text{H}_2\text{O}} + 1} \quad (22)$$

Assuming that the respective reaction rates are linearly dependent on the surface coverage, the relative nitrate reduction rate  $f$  can then be calculated according to eqn. 23. This equation also considers that the oxygen surface coverage decreases from



its original value  $\theta_{O_2}^0$  with increasing nitrate surface coverage due to the blocking of adsorption sites.

$$f = \frac{k_{NO_3-} \cdot \theta_{NO_3-}}{k_{NO_3-} \cdot \theta_{NO_3-} + k_{O_2} \cdot \theta_{O_2}^0 \cdot (1 - \theta_{NO_3-})} \quad (23)$$

For simplicity reasons,  $\theta_{NO_3-}$  will be abbreviated as  $\theta$  and the oxygen contribution is simplified according to eqn. 24, transforming eqn. 23 into eqn. 25:

$$k_o = \frac{k_{O_2} \cdot \theta_{O_2}^0}{k_{NO_3-}} \quad (24)$$

$$f = \frac{\theta}{\theta + k_o - \theta \cdot k_o} \quad (25)$$

Now we will analyze the different reaction pathways of the photogenerated holes and electrons. The following reaction rates are normalized for one reactive electron/hole-pair (molecules converted per reactive photon), assuming that for each oxidation also a reduction must occur simultaneously and are dimensionless. In these equations,  $\beta$  is a figure for the amount of oxidation equivalents that are generated from each reduction of oxygen (0 to 3), as explained in the introduction. For each reactive photon, the amount of oxidation equivalents generated equals one (from the holes) plus up to three (from the electrons) which is further reduced if the electron reduces nitrate instead. In total this equates to  $(1 + \frac{\beta \cdot (1-f)}{4-\beta})$ . To simplify things and also because it is not measured directly, HONO will not be considered as a viable reaction intermediate in the following. Instead, NO can either be oxidized to  $NO_2$  before it is released, which takes 2 oxidation equivalents (eqn. 26), or to nitrate, which takes 3 oxidation equivalents (eqn. 27). The ratio between these two reaction pathways constitutes the initial or intrinsic selectivity of the material,  $S_0$ .

$$rate(NO- > NO_2) = (1 + \frac{\beta - f \cdot \beta}{4 - \beta}) \cdot \frac{1 - S_0}{2 + S_0} \quad (26)$$

$$rate(NO- > NO_3^-) = (1 + \frac{\beta - f \cdot \beta}{4 - \beta}) \cdot \frac{S_0}{2 + S_0} \quad (27)$$

$$rate(NO_3^- - > NO_2) = f \quad (28)$$

The experimentally observed selectivity is the ratio between net nitrate formation and nitrogen monoxide oxidation, eqn. 29, which can be rewritten using eqns. 26-28, resulting in eqn. 30.

$$S = \frac{rate(NO- > NO_3^-) - rate(NO_3^- - > NO_2)}{rate(NO- > NO_2) + rate(NO- > NO_3^-)} \quad (29)$$

$$S = S_0 - \frac{f \cdot (2 + S_0) \cdot (4 - \beta)}{4 - f \cdot \beta} \quad (30)$$

With eqn. 25 this finally becomes eqn. 31.

$$S(\theta) = S_0 - \theta \cdot \frac{(2 + S_0)(4 - \beta)}{4(\theta + k_o(1 - \theta)) - \theta \cdot \beta} \quad (31)$$

As mentioned in the introduction part, the amount of oxidation equivalents generated through the reduction of oxygen ( $\beta$ ) is likely not constant but will increase with lower reaction rate,

e.g., when the nitrate coverage is higher and less electrons reach oxygen. Modeling this exactly is beyond this study, instead it will be approximated by using a simple exponential decay function with the parameter  $\alpha$ , eqn. 32, which transforms eqn. 31 into eqn. 18.

$$\beta = 3(1 - e^{-\alpha\theta}) \quad (32)$$

$$S(\theta) = S_0 - \theta \cdot \frac{(2 + S_0)(4 - 3(1 - e^{-\alpha\theta}))}{4(\theta + k_o(1 - \theta)) - 3\theta(1 - e^{-\alpha\theta})} \quad (18)$$

## 9 Acknowledgement

The authors are grateful to the German Ministry of Economics for funding the AiF/IGF project 18152N and to the European Commission for funding the European Project Light2CAT (grant agreement no. 283062) in which some of the results presented here were obtained.

## References

- 1 K. Skalska, J. S. Miller and S. Ledakowicz, *Sci. Total Environ.*, 2010, **408**, 3976–89.
- 2 U. Gehring, O. Gruziova, R. M. Agius, R. Beelen, A. Custovic, J. Cyrzs, M. Eeftens, C. Flexeder, E. Fuertes, J. Heinrich, B. Hoffmann, J. C. de Jongste, M. Kerkhof, C. Klümper, M. Korek, A. Mölter, E. S. Schultz, A. Simpson, D. Sugiri, M. Svartengren, A. von Berg, A. H. Wijga, G. Pershagen and B. Brunekreef, *Environ. Health Perspect.*, 2013, **121**, 1357–1364.
- 3 B. Chen, C. Hong and H. Kan, *Toxicology*, 2004, **198**, 291–300.
- 4 The European Parliament and the Council of the European Union, *Off. J. Eur. Union*, 2008, **L152**, 1–44.
- 5 M. L. Williams and D. C. Carslaw, *Atmos. Environ.*, 2011, **45**, 3911–3912.
- 6 R. Kurtenbach, J. Kleffmann, A. Niedojadlo and P. Wiesen, *Environ. Sci. Eur.*, 2012, **24**, 21.
- 7 V. Franco, F. P. Sánchez, J. German and P. Mock, *Real-World Exhaust Emissions From Modern Diesel Cars*, October, 2014.
- 8 R. De\_Richter and S. Caillol, *J. Photochem. Photobiol. C Photochem. Rev.*, 2011, **12**, 1–19.
- 9 J. Z. Bloh, A. Folli and D. E. Macphée, *RSC Adv.*, 2014, **4**, 45726–45734.
- 10 A. Gandolfo, V. Bartolomei, E. Gomez Alvarez, S. Tlili, S. Gligorovski, J. Kleffmann and H. Wortham, *Appl. Catal. B Environ.*, 2015, **166-167**, 84–90.
- 11 S. Laufs, G. Burgeth, W. Duttlinger, R. Kurtenbach, M. Maban, C. Thomas, P. Wiesen and J. Kleffmann, *Atmos. Environ.*, 2010, **44**, 2341–2349.
- 12 M. E. Monge, C. George, B. D'Anna, J.-F. Doussin, A. Jam-moul, J. Wang, G. Eyglunent, G. Solignac, V. Daële and A. Mellouki, *J. Am. Chem. Soc.*, 2010, **132**, 8234–5.
- 13 L. Sivachandiran, F. Thevenet, P. Gravejat and A. Rousseau, *Appl. Catal. B Environ.*, 2013, **142-143**, 196–204.
- 14 M. E. Monge, B. D'Anna and C. George, *Phys. Chem. Chem.*

- Phys.*, 2010, **12**, 8991–8.
- 15 H. Gerischer and A. Heller, *J. Phys. Chem.*, 1991, **95**, 5261–5267.
  - 16 P. Vanýsek, *Handb. Chem. & Physics*, 91th Ed., CRC Press, 2010.
  - 17 P. Wardman, *J. Phys. Chem. Ref. Data*, 1989, **18**, 1637–1755.
  - 18 R. Gao, A. Safrany and J. Rabani, *Radiat. Phys. Chem.*, 2003, **67**, 25–39.
  - 19 H. H. Mohamed, C. B. Mendive, R. Dillert and D. W. Bahnemann, *J. Phys. Chem. A*, 2011, **115**, 2139–47.
  - 20 M. Ballari, M. Hunger, G. Hüskén and H. Brouwers, *Catal. Today*, 2010, **151**, 71–76.
  - 21 R. Dillert and A. Engel, *Phys. Chem. Chem. Phys.*, 2013, **15**, 20876–20886.
  - 22 M. Ballari, Q. Yu and H. Brouwers, *Catal. Today*, 2011, **161**, 175–180.
  - 23 A. Mills, L. Burns, C. O'Rourke and S. Elouali, *J. Photochem. Photobiol. A Chem.*, 2016, **321**, 137–142.
  - 24 Y. Ohko, Y. Nakamura, N. Negishi, S. Matsuzawa and K. Takeuchi, *J. Photochem. Photobiol. A Chem.*, 2009, **205**, 28–33.
  - 25 Y. Ohko, Y. Nakamura, A. Fukuda, S. Matsuzawa and K. Takeuchi, *J. Phys. Chem. C*, 2008, **112**, 10502–10508.
  - 26 A. Folli, I. Pochard, A. Nonat, U. H. Jakobsen, A. M. Shepherd and D. E. Macphée, *J. Am. Ceram. Soc.*, 2010, **93**, 3360–3369.
  - 27 A. Folli, C. Pade, T. B. Hansen, T. De Marco and D. E. Macphée, *Cem. Concr. Res.*, 2012, **42**, 539–548.
  - 28 D. E. Macphée and A. Folli, *Cem. Concr. Res.*, 2016, **85**, 48–54.
  - 29 A. Yamamoto, Y. Mizuno, K. Teramura, S. Hosokawa and T. Tanaka, *ACS Catal.*, 2015, **5**, 2939–2943.
  - 30 H. Ichiura, T. Kitaoka and H. Tanaka, *Chemosphere*, 2003, **51**, 855–860.
  - 31 T. A. Kandiel, A. Feldhoff, L. Robben, R. Dillert and D. W. Bahnemann, *Chem. Mater.*, 2010, **22**, 2050–2060.
  - 32 A. Mills and S. Le Hunte, *J. Photochem. Photobiol. A Chem.*, 1997, **108**, 1–35.
  - 33 J. Z. Bloh, A. Folli and D. E. Macphée, *J. Phys. Chem. C*, 2014, **118**, 21281–21292.
  - 34 Y. Hu, X. Song, S. Jiang and C. Wei, *Chem. Eng. J.*, 2015, **274**, 102–112.
  - 35 F. B. Li and X. Z. Li, *Chemosphere*, 2002, **48**, 1103–1111.
  - 36 S. K. Lee and A. Mills, *Platin. Met. Rev.*, 2003, **47**, 61–72.
  - 37 D. W. Bahnemann, J. Mönig and R. Chapman, *J. Phys. Chem.*, 1987, **91**, 3782–3788.
  - 38 K. Fujiwara, U. Müller and S. E. Pratsinis, *ACS Catal.*, 2016, 1887–1893.
  - 39 M. Shao, *J. Power Sources*, 2011, **196**, 2433–2444.
  - 40 A. Folli, J. Z. Bloh, E.-P. Beukes, R. F. Howe and D. E. Macphée, *J. Phys. Chem. C*, 2013, **117**, 22149–22155.
  - 41 A. Folli, J. Z. J. Bloh and D. Macphée, *J. Electroanal. Chem.*, 2015, **780**, 367–372.
  - 42 A. Folli, J. Z. Bloh, K. L. Armstrong, E. Richards, D. M. Murphy, L. Li, C. Kiely, I. Smith, A. McLaughlin and D. E. Macphée, *ACS Catal.*, 2017, Submitted.
  - 43 J. Z. Bloh, R. Dillert and D. W. Bahnemann, *Environ. Sci. Pollut. Res.*, 2012, **19**, 3688–3695.
  - 44 J. Z. Bloh, R. Dillert and D. W. Bahnemann, *Phys. Chem. Chem. Phys.*, 2014, **16**, 5833–5845.
  - 45 J. Z. Bloh, *Dissertation*, Gottfried Wilhelm Leibniz Universität Hannover, 2012.
  - 46 S. Neubert, D. Mitoraj, S. A. Shevlin, P. Pulisova, M. Heimann, Y. Du, G. K. L. Goh, M. Pacia, K. Kruczała, S. Turner, W. Macyk, Z. X. Guo, R. K. Hocking and R. Beranek, *J. Mater. Chem. A*, 2016, **4**, 3127–3138.
  - 47 M. Nishikawa, R. Takanami, F. Nakagoshi, H. Suizu, H. Nagai and Y. Nosaka, *Appl. Catal. B Environ.*, 2014, **160–161**, 722–729.
  - 48 M. Nishikawa, Y. Mitani and Y. Nosaka, *J. Phys. Chem. C*, 2012, **116**, 14900–14907.
  - 49 International Organization for Standardization, *ISO 22197-1: Fine ceramics (advanced ceramics, advanced technical ceramics) - Test method for air-purification performance of semiconducting photocatalytic materials - Part 1 : Removal of nitric oxide*, International organization for standardization technical report, 2007.
  - 50 S. Ifang, M. Gallus, S. Liedtke, R. Kurtenbach, P. Wiesen and J. Kleffmann, *Atmos. Environ.*, 2014, **91**, 154–161.