



Polyolefin Fibres

Structure, Properties and
Industrial Applications

Second Edition



THE TEXTILE INSTITUTE BOOK SERIES

Edited by Samuel C. O. Ugbolue



Polyolefin Fibres

The Textile Institute Book Series

Incorporated by Royal Charter granted in 1925, The Textile Institute was established as the professional body for the textile industry to provide support to businesses, practitioners and academics involved with textiles and to provide routes to professional qualifications through which Institute Members can demonstrate their professional competence. The Institute's aim is to encourage learning, recognise achievement, reward excellence and disseminate information about the textiles, clothing and footwear industries and the associated science, design and technology; it has a global reach with individual and corporate members in over 80 countries.

The Textile Institute Book Series supersedes the former 'Woodhead Publishing Series in Textiles', and represents a collaboration between The Textile Institute and Elsevier aimed at ensuring that Institute Members and the textile industry continue to have access to high calibre titles on textile science and technology.

Books published in The Textile Institute Book Series are offered on the Elsevier web site at: store.elsevier.com and are available to Textile Institute Members at a substantial discount. Textile Institute books still in print are also available directly from the Institute's web site at: www.textileinstitute.org.

To place an order, or if you are interested in writing a book for this series, please contact Matthew Deans, Senior Publisher: m.deans@elsevier.com.

Recently Published and Upcoming Titles in The Textile Institute Book Series:

Handbook of Technical Textiles, Volume 1, 2nd Edition, A. Richard Horrocks and Subhash C. Anand, 9781782424581

Handbook of Technical Textiles, Volume 2, 2nd Edition, A. Richard Horrocks and Subhash C. Anand, 9781782424659

Geotextiles, Robert Koerner, 9780081002216

Advances in Braiding Technology, Yordan Kyosev, 9780081009260

Antimicrobial Textiles, Gang Sun, 9780081005767

Active Coatings for Smart Textiles, Jinlian Hu, 9780081002636

Advances in Women's Intimate Apparel Technology, Winnie Yu, 9781782423690

Smart Textiles and Their Applications, Vladan Koncar, 9780081005743

Advances in Technical Nonwovens, George Kellie, 9780081005750

Activated Carbon Fiber and Textiles, Jonathan Chen, 9780081006603

Performance Testing of Textiles, Lijing Wang, 9780081005705

Colour Design, Janet Best, 9780081012703

Forensic Textile Science, Debra Carr, 9780081018729

Principles of Textile Finishing, Asim Kumar Roy Choudhury, 9780081006467

High-Performance Apparel, John McLoughlin and Tasneem Sabir, 9780081009048.

Polyolefin Fibres

Structure, Properties and Industrial Applications

Second Edition

Edited by

Samuel C. O. Ugbolue

Edwin Clark University, Kiagbodo, Delta State, Nigeria


University of Massachusetts, Dartmouth, MA,
United States

Federal University of Technology, Owerri, Nigeria

Scudin LP, Taunton, MA, United States



The Textile Institute



WP

WOODHEAD
PUBLISHING

An imprint of Elsevier

Woodhead Publishing is an imprint of Elsevier
The Officers' Mess Business Centre, Royston Road, Duxford CB22 4QH, United Kingdom
50 Hampshire Street, 5th Floor, Cambridge, MA 02139, United States
The Boulevard, Langford Lane, Kidlington OX5 1GB, United Kingdom

Copyright © 2017 Elsevier Ltd. All rights reserved.

No part of this publication may be reproduced or transmitted in any form or by any means, electronic or mechanical, including photocopying, recording, or any information storage and retrieval system, without permission in writing from the publisher. Details on how to seek permission, further information about the Publisher's permissions policies and our arrangements with organizations such as the Copyright Clearance Center and the Copyright Licensing Agency, can be found at our website: www.elsevier.com/permissions.

This book and the individual contributions contained in it are protected under copyright by the Publisher (other than as may be noted herein).

Notices

Knowledge and best practice in this field are constantly changing. As new research and experience broaden our understanding, changes in research methods, professional practices, or medical treatment may become necessary.

Practitioners and researchers must always rely on their own experience and knowledge in evaluating and using any information, methods, compounds, or experiments described herein. In using such information or methods they should be mindful of their own safety and the safety of others, including parties for whom they have a professional responsibility.

To the fullest extent of the law, neither the Publisher nor the authors, contributors, or editors, assume any liability for any injury and/or damage to persons or property as a matter of products liability, negligence or otherwise, or from any use or operation of any methods, products, instructions, or ideas contained in the material herein.

British Library Cataloguing-in-Publication Data

A catalogue record for this book is available from the British Library

Library of Congress Cataloging-in-Publication Data

A catalog record for this book is available from the Library of Congress

ISBN: 978-0-08-101132-4 (print)

ISBN: 978-0-08-101251-2 (online)

For information on all Woodhead Publishing publications
visit our website at <https://www.elsevier.com/books-and-journals>



Working together
to grow libraries in
developing countries

www.elsevier.com • www.bookaid.org

Publisher: Matthew Deans

Acquisition Editor: David Jackson

Editorial Project Manager: Edward Payne

Production Project Manager: Priya Kumaraguruparan

Cover Designer: Vicky Pearson Esser

Typeset by MPS Limited, Chennai, India

Contents

List of Contributors	xi
Preface	xv
Part I Structure and properties of polyolefin fibres	1
1 Types of polyolefin fibres	3
<i>A. Crangle</i>	
1.1 Introduction	3
1.2 Definitions of polymers, fibres and polyolefins	4
1.3 Chemistry of alkene (olefin) monomers	4
1.4 Polymers and polymerization reactions	6
1.5 Stereochemistry and the structure of polyolefins	8
1.6 Polyethylene fibres	14
1.7 Polypropylene fibres	15
1.8 Polyolefin fibres from copolymers	17
1.9 Polyolefin fibres from polymer blends or alloys	19
1.10 Polyolefin bi-component fibres	21
1.11 Polyolefin nanocomposite fibres	22
1.12 Classification of polyolefin fibres and textiles	23
1.13 Future trends	23
1.14 Conclusions	26
1.15 Sources of further information and advice	27
References	28
2 The structural and chemical properties of polyolefin fibres	33
<i>Robert R. Mather</i>	
2.1 Introduction	33
2.2 Arrangements of polyolefin chains	34
2.3 Crystalline structures	36
2.4 Crystal morphology	38
2.5 Chemical properties	39
2.6 Oxidation of polyolefin fibres	39
2.7 Stabilizers	44
2.8 Surface chemistry of polyolefin fibres	50
2.9 Sources of further information	55
References	55

3	The structural mechanics of polyolefin fibrous materials and nanocomposites	59
	<i>Samuel C.O. Ugbolue</i>	
3.1	Introduction	59
3.2	The structure and mechanics of polyolefin fibrous materials	60
3.3	The mechanical properties of polyolefin fibres and films	61
3.4	Characterization of polyolefin fibrous materials and nanocomposites	68
3.5	Structure–property improvements of polyolefin nanocomposites	72
3.6	Fibre-reinforced polyolefins	80
3.7	Design and fabrication of polyolefin auxetic textile structures	80
3.8	Concluding remarks	82
	Acknowledgment	82
	References	82
	Further reading	88
4	Polyolefins and the environment	89
	<i>Oluranti Agboola, Rotimi Sadiku, Touhami Mokrani, Ismael Amer and Odunayo Imoru</i>	
4.1	Introduction	89
	References	123
5	The use of polyolefins in industrial and medical applications	135
	<i>Yong K. Kim</i>	
5.1	Introduction	135
5.2	Technical textile applications of polyolefins	138
5.3	Polyolefin fibre types and properties	139
5.4	Technical textile structures from polyolefin fibres	141
5.5	Industrial applications of polyolefin fibres	146
5.6	Conclusion and future trends	153
	References	154
6	Advances in polyolefin-based spunbond and binder fibres	157
	<i>Rajen M. Patel, Jill Martin, Gert Claasen and Thomas Allgeuer</i>	
6.1	Introduction	157
6.2	Monocomponent polyethylene-based soft spunbond fabrics	159
6.3	Monocomponent polypropylene-based soft spunbond fabrics	170
6.4	Bi-component spunbond fabric and bi-component binder fibres	174
	Summary	182
	Acknowledgments	183
	References	183

Part II	Improving the functionality of polyolefins	187
7	Production of polyolefins	189
	<i>Richard Kotek, Mehdi Afshari, Huseyin Avci and Mesbah Najafi</i>	
7.1	Introduction	189
7.2	Manufacturing of polyolefins	190
7.3	Melt spinning of PP	209
7.4	Melt spinning of PE	246
7.5	High performance-technical polypropylene fibres and yarns	250
7.6	Other production methods for polyolefins	253
	References	261
8	Enhancing hygiene/antimicrobial properties of polyolefins	265
	<i>Mohammad Badrossamay and Gang Sun</i>	
8.1	Introduction	265
8.2	Antimicrobial functions	266
8.3	Antimicrobial polyolefins	267
8.4	Future trends	280
	References	281
	Further reading	284
9	Improving the use of polyolefins in nonwovens	285
	<i>Sanjiv R. Malkan</i>	
9.1	Introduction	285
9.2	Nonwoven definition	287
9.3	Nonwoven market	288
9.4	Classification of nonwoven fabrics	289
9.5	Finishing of nonwovens	299
9.6	Characteristics and properties of nonwoven fabrics	300
9.7	Consumption profile of polyolefin in nonwovens	301
9.8	Applications of polyolefin nonwovens	308
9.9	Future trends	309
	References	310
10	Testing, product evaluation and quality control of polyolefins	313
	<i>Samuel C.O. Ugbohue</i>	
10.1	Introduction	313
10.2	Testing and characterization of polyolefins	314
10.3	Selected product analysis and performance evaluation: Case study on polyolefin nanocomposites	325
10.4	Evaluation of auxetic textile structures	333
10.5	Quality control considerations	335
	Acknowledgment	336
	References	336
	Further reading	338

11	Polyolefin nanocomposite fibres and films	339
	<i>Qinguo Fan</i>	
11.1	Introduction	339
11.2	Polyolefin nanocomposite fibres and films	339
11.3	Preparation of polyolefin nanocomposite fibres and films	342
11.4	Characterization and analysis	343
11.5	Applications of polyolefin nanocomposites	348
11.6	Chemical applications	350
11.7	Conclusions	353
	Acknowledgments	354
	References	354
12	Improving the coloration/dyeability of polyolefin fibres	359
	<i>Renzo Shamey</i>	
12.1	Introduction	359
12.2	Overview of structural features of polyolefins	359
12.3	An overview of dye–fibre interactions	362
12.4	Colorants	364
12.5	Coloration of unmodified polyolefins	364
12.6	Improving coloration of PP through fibre modification	377
12.7	Conclusions	382
	Acknowledgments	383
	References	383
	Further reading	388
Part III	Enhanced applications and uses of polyolefin fibres	389
13	Improving wear resistance of polyolefins	391
	<i>Vincent Ojijo and Emmanuel R. Sadiku</i>	
13.1	Introduction	391
13.2	Types of polyolefin	392
13.3	Polyethylene	392
13.4	Polypropylene	395
13.5	Wear in polymers	397
	Conclusions	415
	References	415
14	Improving the thermal and flame resistance properties of polyolefins	421
	<i>Stephen C. Agwuncha, Idowu D. Ibrahim and Emmanuel R. Sadiku</i>	
14.1	Introduction	421
14.2	Thermal properties of polyolefins	422
14.3	Factors affecting the thermal properties of polyolefins	423
14.4	Improving the thermal properties of polyolefins	425

14.5	Effect of nanoparticles loading on the thermal properties of polyolefins	430
14.6	Flame resistance properties of polyolefins	434
14.7	Factors affecting the flame resistance properties of polyolefins	434
14.8	Improving the flame resistance properties of polyolefins	435
14.9	Future trends	438
14.10	Conclusion	438
	References	439
	Further reading	447
15	Automotive components composed of polyolefins	449
	<i>Rotimi Sadiku, David Ibrahim, Oluranti Agboola, Shesan J. Owonubi, Victoria O. Fasiku, Williams K. Kupolati, Tamba Jamiru, Azunna A. Eze, Oludaisi S. Adekomaya, Kokkarachedu Varaprasad, Stephen C. Agwuncha, Abbavaram B. Reddy, Bandla Manjula, Bilainu Oboirien, Clara Nkuna, Mbuso Dlundu, Adetona Adeyeye, Tobi S. Osholana, Goitse Phiri, Olayinka Durowoju, Peter A. Olubambi, Frank Biotidara, Mercy Ramakokovhu, Brendon Shongwe and Vincent Ojijo</i>	
15.1	Introduction: brief survey of polyolefin resins and their general properties	449
15.2	Types of polyolefins	452
15.3	Ethylene copolymers	457
15.4	PP and its composites	459
15.5	Polyolefin-based nanocomposites	465
15.6	Foamable and expandable polyolefins	467
15.7	Sun visors	472
15.8	EPRs—ethylene propylene diene and ethylene propylene copolymers	472
15.9	Other poly(α -olefins)	473
15.10	Cyclo-olefin copolymers: properties and applications	474
15.11	Chlorinated PE and chlorosulfonated PE	475
15.12	Thermoplastic elastomers	475
15.13	Specific automotive components made of polyolefin-based materials	482
15.14	Future trend	489
15.15	Conclusions	490
	References	492
16	The use of polyolefins in geotextiles and engineering applications	497
	<i>Williams K. Kupolati, Emmanuel R. Sadiku, Idowu D. Ibrahim, Adeyemi O. Adeboje, Chewa Kambole, Olukayode O.S. Ojo, Azunna A. Eze, Philip Paige-Green and Julius M. Ndambuki</i>	
16.1	Introduction	497
16.2	Definitions of polyolefins and geotextiles	497
16.3	Types and properties of polyolefins and geotextiles	498

16.4	Polyolefins in geotextiles	502
16.5	Applications of polyolefins in engineering	511
16.6	Future trends	512
16.7	Conclusion	513
	Acknowledgements	514
	References	514
	Further reading	516
17	Biomedical applications of polyolefins	517
	<i>Shesan J. Owonubi, Stephen C. Agwuncha, Victoria O. Fasiku, Emmanuel Mukwevho, Blessing A. Aderibigbe, Emmanuel R. Sadiku and Deon Bezuidenhout</i>	
17.1	Introduction	517
17.2	Biomedical applications of polyolefins	520
17.3	Conclusion	527
17.4	Further reading	528
	Acknowledgements	528
	References	529
18	Use of polyolefins in hygienic applications	539
	<i>Bandla Manjula, Abbavaram B. Reddy, Emmanuel R. Sadiku, Veluri Sivanjineyulu, Gomotsegang F. Molelekwa, Jarugala Jayaramudu and Kasilingam Raj Kumar</i>	
18.1	Introduction	539
18.2	Common types of polyolefins polymers	540
18.3	Structure, properties, and applications of polyolefins	540
18.4	Hygienic	544
18.5	Hygienic applications	547
18.6	Filters	555
18.7	Hygienic bands	555
18.8	Surgical masks	556
18.9	Conclusions	558
	Acknowledgment	558
	References	558
	Index	561

List of Contributors

Adeyemi O. Adeboje Tshwane University of Technology, Pretoria, South Africa

Oludaisi S. Adekomaya Tshwane University of Technology, Pretoria, South Africa

Blessing A. Aderibigbe University of Fort Hare, Eastern Cape, South Africa

Adetona Adeyeye Tshwane University of Technology, Pretoria, South Africa

Mehdi Afshari E. I. DuPont de Nemours Richmond, Richmond, VA, United States

Oluranti Agboola Tshwane University of Technology, Pretoria, South Africa; University of South Africa, Johannesburg, South Africa

Stephen C. Agwuncha Ibrahim Badamasi Babangida University, Lapai, Nigeria; Tshwane University of Technology, Pretoria, South Africa

Thomas Allgeuer Dow Plastics, Horgen, Switzerland

Ismael Amer University of South Africa, Johannesburg, South Africa

Huseyin Avci Istanbul Technical University, Istanbul, Turkey

Mohammad Badrossamay University of California, Davis, CA, United States

Deon Bezuidenhout University of Cape Town, Cape Town, South Africa

Frank Biotidara Yaba College of Technology, Lagos, Nigeria

Gert Claasen Dow Plastics, Horgen, Switzerland

A. Crangle Formerly of University of Ulster at Belfast, United Kingdom

Mbuso Dlodlu Tshwane University of Technology, Pretoria, South Africa

Olayinka Durowaju Tshwane University of Technology, Pretoria, South Africa

- Azunna A. Eze** Tshwane University of Technology, Pretoria, South Africa
- Qinguo Fan** University of Massachusetts, Dartmouth, MA, United States
- Victoria O. Fasiku** North-West University, Mmabatho, South Africa
- David Ibrahim** Tshwane University of Technology, Pretoria, South Africa
- Idowu D. Ibrahim** Tshwane University of Technology, Pretoria, South Africa
- Odunayo Imoru** Federal University of Technology, Minna, Nigeria
- Tamba Jamiru** Tshwane University of Technology, Pretoria, South Africa
- Jarugala Jayaramudu** Indian Rubber Manufacturers Research Association, Thane, India
- Chewe Kambole** Tshwane University of Technology, Pretoria, South Africa
- Yong K. Kim** University of Massachusetts, Dartmouth, MA, United States
- Richard Kotek** North Carolina State University, Raleigh, NC, United States
- Williams K. Kupolati** Tshwane University of Technology, Pretoria, South Africa
- Sanjiv R. Malkan** Hunter Douglas, Broomfield, CO, United States
- Bandla Manjula** Tshwane University of Technology, Pretoria, South Africa
- Jill Martin** The Dow Chemical Company, Freeport, TX, United States
- Robert R. Mather** Heriot-Watt University, Edinburgh, United Kingdom
- Touhami Mokrani** University of South Africa, Johannesburg, South Africa
- Gomotsegang F. Molelekwa** KU Leuven, Leuven, Belgium; Tshwane University of Technology, Pretoria, South Africa
- Emmanuel Mukwevho** North-West University, Mmabatho, South Africa
- Mesbah Najafi** North Carolina State University, Raleigh, NC, United States
- Julius M. Ndambuki** Tshwane University of Technology, Pretoria, South Africa
- Clara Nkuna** Tshwane University of Technology, Pretoria, South Africa

Bilainu Oboirien CSIR Materials Science & Manufacturing, Pretoria, South Africa

Vincent Ojjo Council for Scientific and Industrial Research, Pretoria, South Africa

Olukayode O.S. Ojo Tshwane University of Technology, Pretoria, South Africa

Peter A. Olubambi University of Johannesburg, Johannesburg, South Africa

Tobi S. Osholana Tshwane University of Technology, Pretoria, South Africa

Shesan J. Owonubi Tshwane University of Technology, Pretoria, South Africa; North-West University, Mmabatho, South Africa

Philip Paige-Green Tshwane University of Technology, Pretoria, South Africa

Rajen M. Patel The Dow Chemical Company, Freeport, TX, United States

Goitse Phiri Tshwane University of Technology, Pretoria, South Africa

Kasilingam Raj Kumar Indian Rubber Manufacturers Research Association, Thane, India

Mercy Ramakokovhu Tshwane University of Technology, Pretoria, South Africa

Abbavaram B. Reddy Tshwane University of Technology, Pretoria, South Africa

Emmanuel R. Sadiku Tshwane University of Technology, Pretoria, South Africa

Rotimi Sadiku Tshwane University of Technology, Pretoria, South Africa

Renzo Shamey North Carolina State University, Raleigh, NC, United States

Brendon Shongwe Tshwane University of Technology, Pretoria, South Africa

Veluri Sivanjineyulu Chang Gung University, Taoyuan, Taiwan

Gang Sun University of California, Davis, CA, United States

Samuel C.O. Ugbolue Edwin Clark University, Kiagbodo, Nigeria; University of Massachusetts, Dartmouth, MA, United States; Federal University of Technology, Owerri, Nigeria; Scudin LP, Taunton, MA, United States

Kokkarachedu Varaprasad Tshwane University of Technology, Pretoria, South Africa; Centro de Investigación de Polímeros Avanzados, Concepción, Chile

This page intentionally left blank

Preface

Since publishing the First Edition of polyolefin fibres: industrial and medical applications tremendous advances have been made in polymer science and engineering particularly in the important fields of nanocomposites and biomaterials. The import of polyolefins remains very strong and concerted demands have led to the publishing of the second edition of the book titled, Polyolefin fibres: Structure, Properties and Industrial Applications. Polyethylene and polypropylene (PP) are very important polyolefin polymers and the fastest growing polymer family. Polyolefins cost less to produce and process than many other plastics and materials they replace. Indeed, PP is a versatile and widely used synthetic polymer for hygienic applications like food packaging, surgical masks, diapers, hygiene bands, filters, automotive parts, and medical devices. Polyolefins are also important for fibres and films; PP fibres are used widely in upholstery fabrics, geotextiles, and carpet backing. Evidently, because of the low cost, high strength, high toughness, and resistance to chemicals, PP fibres find a broad spectrum of use in the industrial, home furnishing sectors, and medical applications. Thus our knowledge in engineering nanocomposite polyolefin materials has proved invaluable in improving the range of commercially available products. However, PP fibres do not enjoy comparable popularity in the apparel sector of the textile industry; one of the main reasons being lack of dyeability.

Specifically, this Second Edition is made up of three parts, namely: Part I: Structure and properties of polyolefin fibres with special emphasis on the types of polyolefin fibres, their structure and chemical properties, detailed discussion on the structural mechanics of polyolefin fibrous materials and nanocomposites, polyolefins and the environment, the use of polyolefins in industrial and medical applications, and advances in polyolefin-based fibres for hygienic and medical applications.

Part II: Improving the functionality of polyolefins places emphasis primarily on the production methods for polyolefin fibres, enhancing the hygiene/antimicrobial properties of polyolefins, improving their use in nonwovens, testing and quality control of polyolefins, the current status of polyolefin nanocomposite fibres and films and efforts geared towards improving the coloration/dyeability of polyolefin fibres.

Part III: Enhanced applications and uses of polyolefin fibres focus on various topics dealing with improving the wear resistance of polyolefins; improving thermal and flame resistance properties of polyolefins; discussions about the various polyolefin automotive components, the use of polyolefins in geotextiles and engineering

applications; the increasing use of polyolefins in biomedical applications and also the use of polyolefins in hygienic applications.

I am most grateful to all the contributors for their time, determination, and enthusiasm in insuring that the deadline of the editorial team was met. I am indebted to all the members of my family for their support, interest, and encouragement in the realization of this book project. Many of my graduate students and visiting scientists from various universities across the globe have made contributions through our shared research projects over the years and their efforts are duly acknowledged.

I believe this book provides excellent information not only for researchers, academics, and professionals in the biomaterials, nonwoven, and medical areas but also for technologists, engineers, product designers, marketers, and managers in the polymer, textile, and allied industries.

Samuel C.O. Ugbolue^{1,2}

¹Scudin LP, Taunton, MA, United States

²Edwin Clark University, Kiagbodo, Nigeria

Part I

Structure and properties of polyolefin fibres

Polyolefins and the environment

4

*Oluranti Agboola¹, Rotimi Sadiku², Touhami Mokrani¹,
Ismael Amer¹ and Odunayo Imoru³*

¹University of South Africa, Johannesburg, South Africa,

²Tshwane University of Technology, Pretoria, South Africa,

³Federal University of Technology, Minna, Nigeria

4.1 Introduction

4.1.1 Polyolefins

Polyolefins (PO) are the leading and largest volume industrial polymer in the world and they are used for the production of a wide range of commercial products that are used in nearly every aspect of our daily lives, such as household bottles, pipes, automobile parts, packaging films, etc. [1]. PO derive their physical properties from the arrangement or the entanglement of the atoms in the chain molecules. Branching caused by radical transfer influences the physical properties as well as the molecular distribution [2]. They are based on low-cost petrochemicals or natural gas and the required monomers are produced by cracking or refining of crude oil and therefore, resource depletion may become a determining factor in the future production of PO [3]. It is, therefore, highly desirable that PO material does not have any negative effect on the environment during its transformation into articles or components or during service [4]. It is important to avoid any negative effects at the end of the life cycle of PO (see Fig. 4.1).

PO are saturated hydrocarbon polymers, based on ethylene; high-density polyethylene (HDPE), low-density polyethylene (LDPE) and linear low-density polyethylene (LLDPE), propylene and higher α -olefins or combinations of these monomers. PO also take great advantage of their chemical nature, being composed by carbon and hydrogen only, with respect to other plastics, such as poly(vinyl chloride) (PVC), polyamides, and polyurethanes [5]. PO, intended as polymers and copolymers of ethylene and propylene, represent more than 40% of plastics produced every year, with a clear tendency to increase such percentage. As the use of the material widens, so does the amount of waste disposed off into the environment [5]. Therefore PO play a major role in environmental issue and every progress achieved for them is a substantial progress for the whole issue [6]. Chemical and biological inertness of polyolefins were seen, originally as advantages. The high stability of these compounds and resistance to degradation has led to their accumulation in the environment, considerably increasing visible pollution and contributing to the clogging of drains during heavy rains, among other problems [7–10]. Environmental appearance is becoming an important factor that impacts on the market position of polyolefins, thus the appearance depends on the raw materials and

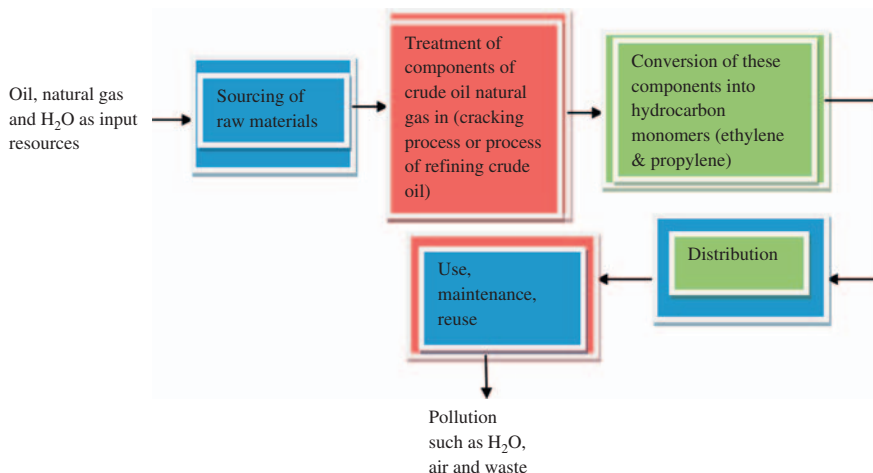


Figure 4.1 Polyolefins product life cycle.

the processes employed for the manufacture of these materials. Furthermore, product recyclability or biodegradability and the use of renewable resources need to be considered.

4.1.1.1 Polyethylene

Polyethylene (PE), a member of the important family of polyolefin resin, is the most widely used plastic in the world. They are prepared by the catalytic polymerization of ethylene [11]. It is a thermoplastic polymer consisting of long chains, produced by combination of the monomer molecules, i.e., ethylene. Depending on the mode of polymerization, three basic types of PE are frequently used: linear HDPE, branched LDPE, and LLDPE [12]. PEs are crystalline thermoplastics that possess toughness, excellent chemical resistance and excellent electrical insulating properties, near-zero moisture absorption, low coefficient of friction and ease of processing. Their heat deflection temperatures are reasonable but not high.

HDPE possesses greater stiffness, rigidity, improved heat resistance, and increased resistance to permeability than LDPE and LLDPE. HDPE has a low degree of branching and thus greater intermolecular forces and tensile strength. It can be produced by chromium/silica catalysts, Ziegler-Natta catalysts or metallocene catalysts [13]. HDPE is produced in molecular weights (MWs), ranging from 10,000 to several million. It has a linear polymeric chain (see Fig. 4.2), combined with a high density and melting point [14]. HDPE is used in the production of milk jugs, detergent bottles, margarine tubs, garbage containers, toys, and water pipes and in packaging.

Low-density PE is manufactured under high temperature and pressure using peroxide initiators. On the other hand, LLDPE is manufactured under low pressure. LLDPE is prepared by introducing short branching via copolymerization with

4.1.1.2 Polypropylene

Polypropylene (PP) is a synthetic resin produced via the polymerization of propylene. PP films are widely used in packaging, textile, stationaries, and in a variety of other applications due to their great potentials in such areas as barrier properties, brilliance, dimensional stability, and processability. In many aspects, PP is similar to PE, especially in respect to their electrical properties and dissolution behavior. The properties of PP depend on the MW and molecular weight distribution (MWD), crystallinity, type and proportion of comonomer (if used). The mechanical properties of PP are strongly dependent on its crystallinity. Increasing crystallinity enhances stiffness, yield stress, and flexural strength; however, toughness and impact strength decrease [13]. The PP manufacturing process consists of a raw material, refining process, polymerization process, after treatment process, and granulation process. Propylene can also be polymerized with ethylene to produce an elastic ethylene–propylene copolymer. A large proportion of PP production is melt-spun into fibres. PP fibre is a major factor in home furnishings, such as upholstery and indoor–outdoor carpets [16]. The propene molecule is asymmetrical (see Fig. 4.4).

When polymerized, three basic chain structures can be formed and they are dependent on the position of the methyl groups: two are stereo-regular (isotactic and syndiotactic) and the third does not have a regular structure and it is termed atactic, as shown in Fig. 4.5 [17].

4.1.2 Polyolefin degradation

The negative change of properties (tensile strength, color, etc.) of a polymer or a polymer-based product under the influence of one or more environmental factors is known as polymer degradation. Naturally the degradation of plastics is a very slow process and it is a function of environmental factors such as temperature, humidity of air and moisture in the polymer, pH, and solar energy; polymer properties and biochemical factors. Degradation gives rise to changes in material properties such as optical, mechanical, or electrical characteristics which are evidenced as crazing, cracking, erosion, discoloration, and phase separation. The most problematic plastics are polyolefins as they are resistant to microbial attack (fungi and bacteria, etc.), due to the absence of any active functional groups [18]. This means that the surface of polyolefin material or articles made from polyolefins are hydrophobic, thus inhibit the growth of microflora on them [19]. Depending on the environmental factor, types of polyolefin degradation have been classified as photo-oxidative degradation, thermal degradation, ozone-induced degradation, mechanochemical degradation, catalytic degradation, and biodegradation [20].




Figure 4.4 Propene molecule.

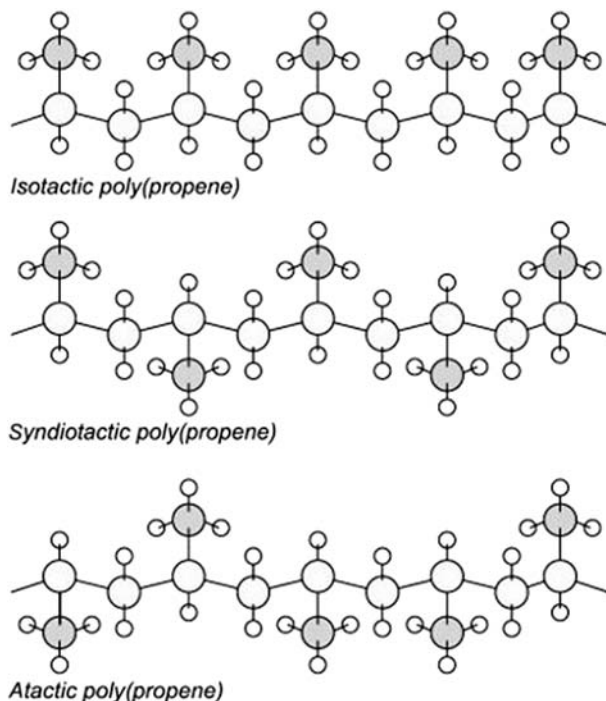


Figure 4.5 Molecular structures of polypropylene [17].

4.1.2.1 Thermal degradation

During the process of polymeric materials degradation and oxygen diffusion prevalently occur in the amorphous regions, linking degradability to the thermal history of the material [21]. A process whereby the action of heat or elevated temperature on a material, product, or assembly causes a loss of physical, mechanical, or electrical properties is known as thermal degradation. The rate of thermal degradation directly depends on the temperature, with high degradation values achievable at high temperatures [22]. At high temperature the components of the long-chain backbone of the polymer can begin to separate (molecular scission) and then react with one another to change the properties of the polymer. The chemical reactions involved in thermal degradation lead to physical and optical property changes that are relative to the initially specified properties. Generally, thermal degradation involves changes in the MW and the MWD of the polymer. Other property changes include: chalking, color changes, cracking, reduced ductility, and embrittlement [23].

The thermal degradation of polymers has become a progressively important method for the conversion of waste plastics into valuable chemicals and fuel. It is thus, important to have a good knowledge of the thermal degradation kinetics of polymers in order to improve their thermal behavior. Studies on pyrolysis kinetics

of polyolefin wastes have been carried out and most of these studies have been developed on the assumption that the reaction can be described by an n th order reaction model [24–30]. The assumption of an n th order reaction model would result in the Arrhenius parameters deviating from the real models [31]. A method of estimating the Arrhenius parameters as well as the reaction model of the pyrolysis of PP from isothermal kinetic results was described by some researchers [32,33]. They introduced a custom-made thermobalance that is able to record weight decrease with time under pure static condition. A best fit of experimental reduced-time-plot to theoretical models led to a conclusion that the pyrolysis reaction model and the Arrhenius parameters of PP vary with reaction temperature.

Mechanism of thermal degradation

In the last six decades, many investigations have been undertaken in order to clarify the degradation mechanism of polyolefins. The mechanism of polymer degradation is immensely complex, involving the simultaneous formation and decomposition of hydroperoxides. Degradation is promoted by oxygen, humidity and strain and results in such flaws as brittleness, cracking, and fading [34]. The thermal degradation of polymers consists of two distinct reactions, which occur simultaneously in the reactor. One is a random scission of links, causing a MW reduction of the raw polymer and the other is a chain-end scission of C–C bonds, generating volatile products [35].

The chain-end scission occurs at the gas–liquid interface in the working reactor. A continuous flow reactor for the thermal degradation of PE, PP, and polystyrene (PS) has been investigated and discussed as a typical example for the chain-end scission mechanism [36]. The nature and composition of the pyrolysis products provide important and profitable information about mechanism of thermal degradation [37]. The chain-end degradation begins from the end of the chain and successively releases the monomer units. The route of this type of degradation is also known as depolymerization reaction. The reaction involves successive release of monomer units from the chain ends. Such reactions are the opposite of the propagation step in addition polymerization and they occur through free radical mechanism [35]. The MW of the polymer in this type of degradation decreases slowly and large quantity of the monomer is liberated simultaneously. Generally, chain-end degradation takes place when the backbone bonds are weaker than the bonds of the side groups and only with polymer molecules, carrying active chain ends with a free radical, cation, anion, etc.

The degradation mechanism that is often attributed to the pyrolysis of a wide number of polymers is random scission. In the random scission mechanism the backbone of the polymer will break randomly; this can occur at any position of the backbone, as a result of the rapid decrease in the MW. As new free radicals with high reactivity are formed, monomers cannot be a product of this reaction; furthermore, intermolecular chain transfer and disproportion termination reactions can occur. For random degradation to occur the polymer chain does not necessarily require to carry any active site [38]. The mechanism of thermal degradation of PE has also been discussed as an example for random scission type reactions [39]. PE

also undergoes random degradation through migration of a hydrogen atom from one carbon to another thus generating two fragments [40]. The kinetics of decomposition of PP and PE are very significant, they serve as an example of a complicated radical chain mechanism and design of waste incineration and other recycling procedures. This is because PP and PE are respectively used in high amounts for packaging and they constitute the main components of plastic waste from domestic refuse.

Direct pyrolysis–mass spectrometry (Py–MS) is also applied in order to determine the primary structure of macromolecules and to further investigate selective thermal degradation mechanisms. This technique allows the thermal decomposition products of the polymer sample to be observed directly in the ion source of the mass spectrometer, so that the evolving products are ionized and continuously detected by repetitive mass scans almost simultaneously with their formation [41].

Methods of thermal degradation

Thermogravimetric analysis (TGA) method is one of the methods of thermal analysis techniques used in characterizing a wide variety of materials. TGA is used to measure the amount and rate of change in the mass of a sample as a function of temperature or time in a controlled atmosphere. The measurements are used mainly to determine the thermal and oxidative stabilities of polymeric materials and their compositional properties [42]. The rate of degradation in TGA ($d\alpha/dt$) is defined as the rate of change of the degree of conversion. The degree of degradation or conversion can be calculated in terms of mass as shown below [43]:

$$\alpha = \frac{w_o - w}{w_o - w_\infty} \quad (4.1)$$

where w_o , w , and w_∞ are the initial weight, the actual weight at each point of the curve, and the final weight measured at the end of the degradation process, respectively. In a TGA instrument, sample is submitted to constant heating rate from room temperature to 600°C or more, under the nitrogen flow. The reaction products can be analyzed by gas chromatography [35]. TGA was used to investigate the kinetic analysis of thermal degradation of polyolefin mixture between PP and LDPE under pyrolysis atmosphere at different compositions [30]. It was found that thermal degradation process of polyolefin mixture was a triple step process and an addition of PP reduced the degradation temperature.

Pyrolysis–gas chromatography–mass spectrometry (Py–GS/MS) method is an instrumental method of chemical analysis in which the sample is heated to decomposition in order to produce smaller molecules and more analytical useful fragments that are separated by gas chromatography and detected using mass spectrometry [44]. As Py–GC/MS decomposes instantly, aggregates of pyrolysates and other side products rarely occur. Thus chemically unchanged pyrolysates can be examined. Py–GC/MS can be used to examine the composition of polymer materials that are difficult to dissolve in a solvent, investigate resin deterioration, and analyze volatile additives [45]. This method of analysis involves putting the sample in the

inactivated sample holder of the microfurnace, dropping the sample holder into the reactor core, which is wrapped with high frequency coils, and filled with helium as the carrier gas using a switch, and then pyrolyzing it. The pyrolysis results are rather stable due to the comparatively low dispersion temperature changes resulting from the sample holder's small capacity [46].

Batch reactor method: Chemical reactions take place almost everywhere in the environment; nonetheless chemical reactors are defined as devices well designed to contain chemical reactions under controlled conditions toward specified products. These devices are designed to maximize the net present value of a given reaction. Reactor design also plays a fundamental role, as it has to overcome problems related to the low thermal conductivity and high viscosity of molten polymers [41]. The thermal degradation of waste plastic can take place in a glass reactor under atmospheric pressure with definite weight of sample that is loaded into bottom of the reactor for thermal degradation. The purging of the reactor with nitrogen gas at a flow rate of 10 mL/min at 120°C for 60 min is required to remove the physically adsorbed water from the plastic sample. After the nitrogen flow is stopped the reactor temperature is increased to the degradation temperature (430°C) at a heating rate of 3°C min⁻¹ and the waste plastic bed temperature is taken as the temperature of the degradation. The gaseous products can be condensed (using a cold-water condenser) to liquid products and trapped in a measuring jar [35]. The compositions of the pyrolysis products of pure LDPE and PS and their mixtures were investigated over a temperature range from 300 to 500°C. The pyrolysis experiments were carried out in a closed batch reactor pressurized autoclave under inert nitrogen atmosphere in order to study the effects of reaction temperature and residence time. The main objective was to convert the waste plastics to oil products for use as a hydrocarbon fuel oil or raw chemical feedstock. The effects of temperature and residence time were studied in order to ascertain the optimum conditions necessary for the production of oil and to investigate the effects of these parameters on the compositions of reaction products, with a special emphasis on the oil. LDPE was thermally degraded to oil at 425°C and the thermal cracking of LDPE in a batch reactor resulted in production of a broad range of hydrocarbon compounds where the yield of aromatics and aliphatics (olefins and paraffins) deeply depended on the pyrolysis temperature and residence time [47]. As waste, HDPE was pyrolyzed in a batch reactor at a temperature of between 400°C and 550°C at a heating rate of 20°C/min with the aim of optimizing the liquid product yield at a temperature range of between 400°C and 550°C. The results of the pyrolysis experiments showed that, at a temperature of 450°C and below, the major product of the pyrolysis was oily liquid which became a viscous liquid or waxy solid at temperatures above 475°C. The yield of the liquid fraction obtained increased with the residence time for waste HDPE. The liquid fractions obtained were analyzed for composition using FTIR and GC-MS [48]. The kinetics of virgin and waste PP and LDPE were recently studied by a modified Coats-Redfern method. Afterward the thermal cracking of these materials in a semibatch reactor under atmospheric pressure in nitrogen was investigated. Both virgin and waste plastics are decomposed at 420–460°C. In order to help in the understanding of the processes for polyolefin degradation the

main reaction paths and the mechanisms for the thermal cracking of polyolefins in a semibatch reactor under atmospheric pressure, though thermal reactions occurring in a reactor are complex and this investigated by Ya et al. [49]. Owing to the short residence time and atmospheric pressure in the pyrolysis process, the high yield of the gaseous product and high yield of unsaturated hydrocarbons in both gaseous and liquid products can be obtained in a semibatch reactor. The results confirmed that chain scission reactions are predominant degradation mechanisms in the thermal cracking process. They concluded that the reaction of the intramolecular hydrogen and the β -scission of the end or middle chain radicals are responsible for the reduction in gaseous and liquid products. In the case of LDPE the reaction of intermolecular hydrogen and β -scission, followed by intramolecular hydrogen reaction may be contributed to form the 1-alkane and 1-alkene with same carbon number.

4.1.2.2 Photo-oxidation degradation

A natural weathering that has great effect produced by oxygen and light radiation is technically referred to as photo-oxidation [50]. Photo-oxidation is therefore the degradation of the surface of a polymer/material in the presence of oxygen or ozone radiation. It is one of the leading chemical degradation mechanisms in photoactive materials and occurs when organic materials are exposed to air and light. Materials that are subjected to oxygen are degraded faster in the presence of radiation than in the absence. The chemical changes that occur during degradation cause disruption of the π conjugation of the polymers and reduce photo absorbance in a process called photo bleaching [51]. The effect is facilitated by radiant energy such as artificial or UV light. The chemical changes reduce polymer's MW and as a consequence of this change, the materials become more brittle with a reduction in its tensile, impact, and elongation strength.

The most common photoreaction for all materials is photo-oxidation. Usually free radicals are generated as transient species in photolytic processes. Since oxygen reacts readily with most free radicals, peroxy radicals will be formed. Photolysis, therefore, can give rise to autoxidative free radical chain reaction. For example, the primary reaction steps for photo-oxidation of polyolefins are as shown in Eqs. (4.2)–(4.15). The steps involve initiation, propagation, chain branching, and termination.

During the mechanism of initiation, the absorption of UV light that has sufficient energy to break the chemical bonds in the main polymer is responsible for polymer degradation. It involves a radical chain mechanism for the formation of initial radical. For the photo initiated oxidation of many commercial polymers this reaction is considered to be very important due to the presence of peroxide groups as chemically bound impurities, originating from processing at a very high temperature in the presence of oxygen. In general, initiation reaction occurs by random chain scission or chain-end initiation. This step is followed by depropagation step forming monomer [35], as depicted below.



The propagating reactions of auto-oxidation cycle are common to all carbon backbone polymers. Propagation is a process in which a reactive intermediate is continuously regenerated during the course of chemical reactions. These reactions lead to generation of hydroperoxide species and are not directly led to backbone cleavage but they are the key intermediates to stimulate reactions. The key reaction in the propagation sequence is the formation of polymer peroxy radicals ($\text{ROO}\cdot$). The next propagation step is the abstraction of hydrogen atom by the polymer peroxy radicals ($\text{ROO}\cdot$) in order to generate new polymer alkyl radical ($\text{R}\cdot$) and polymer hydroperoxide (ROOH) [52]. Hydroperoxide species generated in the propagating step lead to backbone degradation through the cleavage of hydroperoxide O—O bond followed by β -scission [35].




Branching in polymer occurs by the replacement of a substituent, e.g., a hydrogen atom, on a monomer subunit, by another covalently bonded chain of that polymer. In chain branching, polymer oxy radicals ($\text{RO}\cdot$) and hydroxyl radicals ($\text{HO}\cdot$) are formed by photolysis. The oxidation of polyolefin is a radical chain type mechanism. At processing temperature, above ambient temperature polymer radicals $\text{R}\cdot$ are formed. The radicals react with oxygen to form peroxide radicals $\text{ROO}\cdot$ which abstract hydrogen from the polymer backbone in order to form a hydroperoxide (ROOH) and other radicals [53].




Termination of polymer radicals occurs by a bimolecular recombination. The termination of photodegradation process is achieved by “mopping up” the free radicals in order to create inert products. This occurs naturally by combining free radicals or assisted by using stabilizers in the plastic [35].

In here, crosslinking is a result of the reaction of different free radicals with each other. When the oxygen pressure is high, the termination reaction almost occurs by the reaction in Eq. (4.13). At low oxygen pressure, other termination reactions occur to some extent [52].



Hydroperoxide groups are formed in the propagation reaction as shown in Eq. (4.16). At wavelengths below 300 nm hydroperoxides are photolytically decomposed [54]. The most damaging UV wavelength for a specific plastic depends on the bonds present and maximum degradation therefore occurs at different wavelengths for different types of plastics, e.g., it is around 300 nm for PE and ~ 370 nm for PP [35].



PO are often used for outdoor applications. By virtue of the weather conditions the material age and therefore change their properties (cracking of the surface, color changes, embrittlement, decrease of the mechanical features, etc.). Weathering of polymers may be caused by various factors, for example mechanical stress, oxidation, heat-, or biodegradation. One of the most severe factors contributing to photo-oxidation degradation is ultraviolet (UV) radiation [54]. Most of the synthetic polymers are susceptible to degradation initiated by UV and visible light. Normally the near-UV radiations (wavelength 290–400 nm) in the sun determine the lifetime of polymeric materials in outdoor applications [55]. When PE and PP films are exposed to solar UV radiation, they readily lose their extensibility, mechanical strength, and mechanical integrity along with decrease in their average MW [56,57]. The deleterious effects of solar UV radiation in particular on biopolymers, and polymers are well known. The phenomenon is of special interest to the building industry, which relies on polymer building products that are routinely exposed to sunlight during use. Most of the common polymers used in such applications contain photo-stabilizers in order to control photo-damage and to ensure acceptable lifetimes under outdoor exposure conditions [58].

Photochemical oxidation degradation

Photochemical oxidation which is initiated by light is considered the reaction of a chemical change in a substance which causes it to lose electrons. Photochemical

oxidation processes generally involve the generation and use of relatively powerful nonselective transient oxidizing species, primarily the hydroxyl radical ($\cdot\text{OH}$) and in some cases the singlet oxygen which can be generated by photochemical means. The following processes can be considered photochemical oxidation process.

- UV/oxidation processes
- Vacuum ultraviolet (VUV) photolysis
- The photo-fenton process
- Sensitized photochemical oxidation processes

Research on polymer degradation has proof that practically all polymers and polymer-based materials are oxidized by atmospheric oxygen. The reactions induced in polymers by UV irradiation depend on different factors such as internal and external impurities, physical state of the sample, chain structure and characteristics of the radiation source, etc. Hydrogen atom abstraction could occur to a certain extent when impurities in the polymer create macroradical sites. These will react with oxygen, thus producing peroxy radicals and subsequently hydroperoxides, which are thermally and photochemically unstable and will induce further breakdown. Again, polymer degradation results in chemically irreversible reactions or physical changes, the knowledge of the processes involved is important to prevent the premature failure of these materials [59].

Oxidation processes based on the use of ozone (O_3), hydrogen peroxide (H_2O_2), and UV irradiation are currently employed for wastewater treatment as chemical oxidation processes ($\text{O}_3/\text{H}_2\text{O}_2$, O_3 , $\text{H}_2\text{O}_2/\text{Fe}^{2+}$) or photochemical oxidation processes ($\text{H}_2\text{O}_2/\text{UV}$, O_3/UV) [60]. Some researchers have studied photochemical oxidation processes of some polymers. Sørensen et al. [61] investigated the degradation pathway for the oxidation of ethylenediaminetetraacetate (EDTA) in the UV/ H_2O_2 -process. In absence of iron ions the mineralization of EDTA was dominated by the reaction of the HO—radicals generated by the photolysis of H_2O_2 . In the presence of iron ions, photolytic decarboxylation processes inside the complex get an important role during degradation, and the organic degradation products ethylenediaminetriacetate, ethylenediaminediacetate, ethylenediaminemonoacetate were found. By combining product studies with balances of carbon and nitrogen the degradation pathway in the UV/ H_2O_2 -process could be elucidated. No toxic degradation products were identified. Therefore the process was well suited for the elimination of EDTA in water treatment.

Kinetics of photochemical oxidation of polyolefins

The kinetics of decomposition of PE and PP are very important because they provide insight into a complex radical chain mechanism, relevant for the design of waste incineration and other recycling procedures. The kinetics of photochemical oxidation of polyolefin has been investigated by some researchers [62–64]. Photochemical oxidation can be described by a very close mechanistic scheme differing only by their initiation step. In any quantitative approach to the kinetics of photochemical oxidation of a polymer the control of the initiation rate is of major

importance. Polymers, in which the absorbing species are not identified, the absorption of light, are essentially dependent on the sample studied [65].

A mathematical expression for the oxidation rate was obtained through the conventional concepts of chemical kinetics by making four simplifying assumptions: (1) unicity of reactive site, i.e., oxidation occurs exclusively on the most labile CH bond; (2) low conversion ratios of oxidation process, i.e., concentration of reactive sites remains virtually constant; (3) constancy of initiation rate in the case of oxidation induced by an extrinsic factor; (4) steady-state for radicals concentrations in all oxidation cases, but also for hydroperoxides concentration in the case of pure thermal oxidation [66]. Cunliffe and Davis [67], Furneaux et al. [68], and Audouin et al. [69] developed kinetics model with the aim of describing other oxidation regimes of lower oxygen concentration than oxygen excess. These authors included other possible termination reactions such as bimolecular combinations of alkyl-alkyl and alkyl-peroxy radicals, to the previous mechanistic scheme. Long kinetic chain and the existence of an interrelationship between termination rate constants were assumed. They obtained a hyperbolic expression for the oxidation rate by making two additional simplifying assumptions; this was added to the previous four assumptions. With this model the oxygen concentration dependence of the oxidation rate of thin polymer films was described and the critical value of the oxygen partial pressure above which oxygen is in excess was determined. There are other new developed kinetic models. The introduction of a term of photo-induced initiation in a numerical model has been performed by Kiil [70] in the case of the photo-oxidation of epoxy coatings, but the corresponding initiation rate has been described through an empirical law.

Mechanism of photodegradation of polyolefins

Photo-oxidation is the result of the absorption of light, which leads to the formation of radicals that induce oxidation of the material. For polyolefins (PE and PP, especially), photo-oxidation is the dominating mechanism because these polymers do not have an inherent absorption at wavelengths present in terrestrial sunlight (>290–400 nm), therefore, photolysis cannot play an important role. Although, irradiation of these polymers with terrestrial wavelengths results in accelerated degradation; especially for PP, this can be attributed to the impurities that are formed during storage and processing. The steps of photo-oxidation have been described in Section 4.2.2.

The photodegradation mechanism [71,72] of PP occurs when primary events following irradiation of PP with UV light in vacuum are bond-scission and crosslinking as shown in Fig. 4.6.




Figure 4.6 Chain scission of polypropylene.




Figure 4.7 Dissociation of carbon–hydrogen bond.




Figure 4.8 Chain scission of PP as a result of disproportionation reaction.

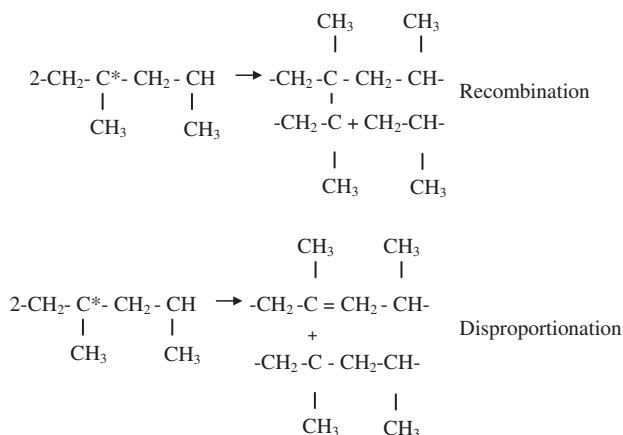


Figure 4.9 Crosslinking of polypropylene radicals [73].

The dissociation of carbon–hydrogen bonds at the tertiary carbon is another possible reaction (see Fig. 4.7).

This could lead to chain scission by a disproportionation reaction (see Fig. 4.8).

Crosslink is formed by the reaction of two propylene radicals (Fig. 4.9).

Pure PE is a relatively stable material in the absence of oxygen, under UV radiation. Chain scission and hydrogen abstraction occur after a long exposure to UV light of short wavelength (254 nm) in a nitrogen atmosphere or in vacuum. Crosslinking and evolution [72] of hydrogen can also be observed (see Fig. 4.10).

Methods of photodegradation

The most important factors of photodegradation are sunlight, atmospheric oxygen, air pollutants, moisture, and changes of temperature. Sunlight is of particular significance as it often triggers polymer degradation [74]. Since the weatherability of a material solely relies on its resistance to all weather factors, the radiation from the sun, especially the UV part is mainly responsible for limiting the lifetime of materials exposed to the environment. Therefore organizing the scope of weathering test

natural weathering period. Their study showed that the real durability of olefin polymers may be much shorter than centuries. In less than 1 year the mechanical properties of all samples decreased virtually to zero, as a consequence of severe oxidative degradation, that resulted in substantial reduction in molar mass accompanied by a significant increase in content of the carbonyl groups.

4.1.2.3 Ozone-induced degradation

Ozone is an immensely reactive form of oxygen occurring around electrical discharges. It is also present in the atmosphere, but in small quantities. The presence of ozone, even in very small concentrations, in the atmosphere significantly increases the rate of polymeric materials aging [77]. Atmospheric ozone usually causes the degradation of polymers under conditions that may be considered as normal; when other oxidative aging processes are very slow and the polymer retains its properties for a rather longer time [78–80]. Exposure of polyolefins to ozone gas causes change in the mechanical properties of LLDPE; oriented PP. Degradation can also be induced deliberately in order to assist in structural determination. This structural determination includes the specification of molecular geometry; when feasible and necessary, the electronic structure of the target molecule or other solids can be determined.

Mechanism of ozone-induced degradation

The oxidation mechanism of polyolefin and other polymers in the presence of ozone is well reported [81–83]. In the presence of oxygen, almost all polymers degrade faster than in an inert environment. The presumed ozone oxidation mechanism is due to the radical-based oxidation process where atomic oxygen is initially formed by degradation of ozone [82]. An atomic oxygen arising from ozone decomposition attacks polymers, thereby producing carbon and hydroxyl radicals. The carbon radicle reacts almost immediately with the oxygen molecule, giving a peroxy radicle. The carbonyl oxide is considered to be the key intermediate in the C = C bond ozonolysis mechanism. The produced peroxy radicle further interacts with the PE to produce carbonyl groups in the chain [81]. The concentration of the peroxy groups depended on the ozone concentration and the exposure time of the surface to ozone [84].

Methods of ozone-induced degradation

Ozone testing is a method used to determine a rubber or polymers resistance to ozone degradation. The resistance level is determined by the physical appearance and the severity of the cracks on the surface of the material sample. The polymers samples are placed in a special chamber that exposes them to ozone at a specified concentration, temperature and duration by doing a specification testing or standard. A sample that does not stand up to the effects of ozone exposure will crack at the surface and sometimes break in two. During this test a material sample will undergo accelerated time/exposure ozone tests. The results of these tests are used to predict the reaction of a material sample under dynamic or static surface tensile strain conditions in an atmosphere containing specified levels of ozone. The extent of

reaction of polyolefins with ozone depends on the extent of agitation of the slurry, the slurry temperature, solid consistency, and ozone concentration in the gas. Because these tests are accelerated and only simulate long-term outdoor ozone exposure, actual real-world exposure results may vary [85,86].

4.1.2.4 *Mechanochemical degradation*

Mechanochemical degradation of polymers is an aspect of polymer degradation that takes place under mechanical stress and by strong ultrasonic irradiations. The molecular chains breakdown as a result of a mechanical force or under shear; this process is often aided by oxidation which is known as mechanochemical degradation. This type of degradation is common in machining process, such as mastication, grinding, and ball milling [87]. Rubber mastication, which leads to chain breakage and development of plasticity under shear, is an example of mechanochemical degradation. Mastication of rubber in the atmosphere of nitrogen at ordinary temperature does not change the plasticity and MW appreciably, but with the presence of oxygen, degradation occurs immediately and rapidly. Under mechanical shear the rubber molecules break into radicals and react with oxygen in the atmosphere leading to permanent chain breakage. In nitrogen, however, the primary radicals formed under shear immediately recombine to give no effective chain breakage [88].

Mechanism of mechanochemical degradation

It is known that input of mechanical energy to polymers does not only produce mechanical effects, it does produce chemical effect too. This effect is called the mechanochemical effect. Polymeric materials show an exceptional range of mechanical responses, which depend on the chemical and physical structure of the polymer chains. The mechanical response of thermoplastic polymers is highly influenced by the molecular mass, chain entanglements, chain alignment, and degree of crystallinity. High intensity ultrasounds can induce mechanochemical degradation in polymeric materials. Polymer in such a case is subjected to very high vibrations, which are only mechanical forces. As ultrasonic waves pass through the solution, the localized shear gradient produces tear of molecules leading to chain scission and decrease in MW [35].

It has been reported that the superposition of ultrasonic waves in extrusion could greatly decrease the viscosity of polymer melts and improve production rate [89–91]. Ultrasonic oscillations can also greatly enhance the compatibility and mechanical properties of HDPE/PS blends due to the in situ formation of inter-chain copolymer of PS–HDPE. The effects of ultrasonic irradiation intensity and the depth of ultrasonic irradiation on the mechanochemical degradation of HDPE have been discussed [92]. The development of MWD of HDPE melt during ultrasonic degradation was also studied. The average MW of HDPE decreases with increasing of ultrasonic intensity. A further increase in trends of under-graded HDPE was observed with the increase of distance from ultrasonic probe tip, indicating that attenuation of ultrasonic intensity in HDPE melt is very quick. It was

found that the weight average MW and MWD of HDPE depend, strongly on the time of irradiation [92].

Methods of mechanochemical degradation

The method of ball milling is a widely used process in which mechanical force is used to achieve chemical processing and transformations. In the past eight decades, some work in understanding the response of polymeric materials to mechanical stress was published by Staudinger and Bondy [93], who observed a decrease in the MW of polymers in response to mastication. It was suggested that the MW reduction resulted from the homolytic carbon–carbon bond cleavage due to mechanical force. This suggestion was supported by electron spin resonance (ESR) experiments of polymers cleaved by ball milling [93]. Sohma [94] stated that polymer molecules in a liquid phase are scissioned by mechanical actions, such as either ultrasonic waves or high-speed stirring. Although the main chain scissions generate free radicals (mechano radicals) of polymers in the liquid phase, however, the lifetimes of these mechano radicals in a liquid phase are too short to be detected by the conventional ESR technique.

Polymers in an extruder are in a molten state and are under strong shearing forces, i.e., the mechanical forces that will break the molecule of polymers. The molten state is something between two extremes, i.e., a solid phase and an ordinary liquid of considerably less viscosity [94]. It has been found that mechanical degradation reduces the average MW of the polymer [95]. The mechanochemical degradation response of polymers to mechanical force is characterized [93] by a variety of measures, including tensile strength, failure strain, stress, fracture toughness (resistance to crack growth), and elastic modulus (initial slope of the stress–strain curve).

4.1.2.5 Biodegradation

Biodegradation can be defined as nature's way of recycling wastes, or breaking down organic matter into nutrients that can be used by other organisms, i.e., biodegradation is the disintegration of materials by fungi, algae, bacteria, and other biological means. Biodegradation is considered a type of degradation involving biological activity. Biodegradation is expected to be the major mechanism of loss for most chemicals released into the environment. This process refers to the degradation and assimilation of polymers by living microorganisms in order to produce degradation products [96]. Biodegradable materials degrade into biomass, carbon dioxide, and methane. In the case of synthetic polymers, microbial utilization of its carbon backbone as a carbon source is required [97]. It has been stated that research has focused on developing biodegradable polymers since most of the polymers are resistant to degradation [98]. The newly developed polymers are degraded and catabolized ultimately to carbon dioxide and water by bacterial and fungi under natural environment. During the degradation process, they should not generate any harmful substances.

Polymers degrade in microbial environments either by anaerobic or aerobic biodegradation and sometimes, a combination of the two. Aerobic biodegradation is the degradation of polymer material by microorganisms in the presence of oxygen with the subsequent conversion of carbon into carbon dioxide, biomass, and by-products. On the other hand, anaerobic biodegradation is the degradation of polymer material by microorganisms in the absence of oxygen with the subsequent conversion of carbon into carbon dioxide, methane or other hydrocarbons, biomass and by-products [97]. The biodegradation that occurs in each environment is characterized by the total carbon conservation. The mass balance equation for aerobic biodegradation of polymers [97] is given in Eq. (4.17):

$$C_T = \text{CO}_2 + C_R + C_B \quad (4.17)$$

where C_T is the total carbon content of the polymer material, C_R is any residue of the polymer that is left or any by-product that is formed during the degradation process, CO_2 is the measurable gaseous product, and C_B is the biomass produced by the microorganisms through reproduction and growth. For the anaerobic environment the total carbon equation can be written as shown in Eq. (4.18).

$$C_T = \text{CO}_2 + \text{CH}_4 + C_R + C_B \quad (4.18)$$

In this process the gaseous product is divided between carbon dioxide and methane. Both anaerobic and aerobic degradation can occur simultaneously in some environments. The process of mineralization occurs during the conversion of biodegradable materials or biomass to gases (such as carbon dioxide, methane, and nitrogen compounds), water, salts, minerals, and residual. Mineralization is complete when all the biodegradable materials or biomass are consumed and all the carbon is converted to carbon dioxide [99].

The important bacteria in the biodegradation process include, inter alia, *Bacillus* (capable of producing thick-walled endospores that are resistant to heat, radiation, and chemical disinfection), *Pseudomonas*, *Klebsiella*, *Actinomycetes*, *Nocardia*, *Streptomyces*, *Thermoactinomycetes*, *Micromonospora*, *Mycobacterium*, *Rhodococcus*, *Flavobacterium*, *Comamonas*, *Escherichia*, *Azotobacter*, and *Alcaligenes* (some of them can accumulate polymer up to 90% of their dry mass) [97,100,101]. Fungi that are active in the biodegradation process are *Sporotrichum*, *Talaromyces*, *Phanerochaete*, *Ganoderma*, *Thermoascus*, *Thielavia*, *Paecilomyces*, *Thermomyces*, *Geotrichum*, *Cladosporium*, *Phlebia*, *Trametes*, *Candida*, *Penicillium*, *Chaetomium*, and *Aerobasidium* [102,103].

Polyolefin polymers are hydrophobic with high MW and are therefore not easily degraded by abiotic or biotic factors. These molecules are unable to enter microbial cells to be digested by intracellular enzymes due to their massive size and they are inaccessible to the action of extracellular enzymes produced by microorganisms due to their excellent barrier properties. Exposure to UV and heat is known to promote degradation of most polymers, however, polyolefins degrade very slowly under environmental conditions [104]. Abiotic and biotic degradation of PEs using

plastic bags of HDPE and LLDPE formulated with prooxidant additives as test materials have been evaluated. These packaging materials were exposed to natural weathering and periodically analyzed with respect to changes in mechanical and structural properties. After a year of exposure, residue samples of the bags were incubated in substrates (compost of urban solid waste, perlite, and soil) at 58°C and at 50% humidity. The biodegradation of the materials was estimated by their mineralization to CO₂. The molar mass of the prooxidant-activated PE decreased and oxygen incorporation into the chains increased significantly during natural weathering. These samples showed a mineralization level of 12.4% after 3 months of incubation with compost. Higher extents of mineralization were obtained for saturated humidity than for natural humidity. The growth of fungi of the genera *Aspergillus* and *Penicillium* was observed on PE films containing prooxidant additives exposed to natural weathering for 1 year or longer. Conventional PE films exposed to natural weathering showed marginally little biodegradation [105].

Oxo-biodegradations

Oxo-biodegradable process involves the transition of metals (some of which are regulated) that theoretically foster oxidation and chain scission in plastics when exposed to heat, air, and/or light. Thus oxo-biodegradable polymers contain prooxidants and pro-degrading compounds [105] that are integrated into the polymer chain in order to accelerate thermo or photo-oxidation [105,106]. These prooxidants are metal ions or oxides, such as titanium oxide, that catalyze photo- or thermo-oxidation of the polymer [105–108]. During photodegradation (pro-oxidant photocatalytic oxidation), free radicals obtained from the reactions catalyzed by pro-oxidant causes polymer chain scission [106,107], speeding up microbial degradation [106]. UV light serves as a catalyst that speeds up the process of photocatalytic oxidation [108]. Literature has reported that polymers that degrade by peroxidation followed by bioassimilation of the oxidation products (oxo-biodegradable polymers) are in general more environmental acceptable (“green”) than some biologically produced hydro-biodegradable polymers [109].

Microbial degradation

The use of bioremediation and biotransformation methods to harness the naturally occurring ability of microbial xenobiotic metabolism to degrade, transform, or accumulate environmental pollutants is known as microbial degradation. PO are characteristically inert and are resistant to microbial attack, leading to their accumulation in the environment. Several studies have investigated the biodegradability of polyolefins containing pro-oxidants in the presence of microbial consortium present in the environment and the selected microbial species in defined medium under controlled laboratory conditions [110–114]. Microbial populations that have the ability of degrading contaminants in the subsurface depend on a variety of physical, chemical, and biological factors that influence their metabolic activity, their growth, and their existence. The characteristics and the properties of the environments in which the microorganisms function have a serious impact on the microbial population, the

rate of microbial transformations, the pathways of products of biodegradation, and, of course, the persistence of contaminants.

The microbial degradation process of polymers is initiated by the secretion of enzymes which cause a chain cleavage of the polymer into monomers [115]. During microbial activity, the microorganisms release protein structures [21], called enzymes; these enzymes are responsible for metabolism or transformation/breakdown of a substance into another (enzymatic dissimilation of the macromolecules from the chain ends). The microorganisms participating in the degrading process attack the surface and settle in a biofilm-like colony, which produces alterations as it comes into contact with the polymer [116]. Biofilms are embedded in the polymer at source, consisting basically of extracellular polysaccharides, proteins, and microorganisms [21,116]. In general, bacteria, fungi, alga, and protozoa may be identified in biofilms. The formation of biofilms is a prerequisite to substance corrosion and/or material deterioration. Some polymers are susceptible to direct biodegradation via enzymes and/or microorganisms, while others may allow degradation only after a hydrolytic stage or scission of the oxidant chain [117].

Generally, an increase in the MW results in a decline of polymer degradability by microorganisms. In contrast, monomers, dimers, and oligomers of a polymer's repeating units are much easily degraded and mineralized. High MWs result in a sharp decrease in solubility making them unfavorable for microbial attack because bacteria require the substrate to be assimilated through the cellular membrane and then further degraded by cellular enzymes [118]. During degradation, exoenzymes from microorganisms breakdown complex polymers yielding smaller molecules of short chains, e.g., oligomers, dimers, and monomers, that are small enough to pass the semipermeable outer bacterial membranes to be utilized as carbon and energy sources. The process is called depolymerization [118]. It is now widely accepted that abiotic oxidative degradation of high MW polyolefin into low MW compounds is necessary to facilitate action of microorganisms and/or enzymes [104].

Enzymatic biodegradation

Enzymes are biological macromolecules that speed up chemical reactions without themselves undergoing any permanent change. The molecules at the beginning of the process upon which enzymes may act are called substrate and the enzyme converts these into different molecules, known as product. Enzymes are very selective in their choice substrates, so that they bind to the specific substrates, thereby lowering the activation energy and thus inducing an increase in the reaction rates in an environment otherwise unfavorable for chemical reactions. Some enzymes do not need any additional component for their optimal activity and others require nonprotein molecules called cofactors, to be bound for activity. Inorganic cofactors include metal ions such as sodium, potassium, magnesium, or calcium and organic cofactors, also known as coenzymes [104].

Substrates of MW higher than the cut off limit of the various transport systems have to be depolymerized by enzymes outside the cell membrane before entrance and terminal mineralization can complete the degradation process. Enzymes are transported across the membrane but those remaining in the periplasm or anchored

to the cell wall are called ectoenzymes, while those excreted into the surrounding media are called extracellular enzymes [119]. Extracellular enzymes may be excreted intentionally by living cells, enter the media by lysis or cell damage, or can result from grazing activity by zooplankton and protozoan [120]. High MW polymers are not easily susceptible to enzymatic biodegradation as they are unable to enter microbial cells due to their large size. In order to accomplish scission, microorganisms secrete specific enzymes or generate free radicals, which act on polymer chains and break them down into oligomers, dimers, and/or monomers [104].

Mechanism of biodegradation

Common mechanisms of biodegradation that involve bioassimilation from the “ends” of substrate molecules do exist. The primary mechanism for the biodegradation of polymer with high MW is the oxidation or hydrolysis by enzyme in order to create functional groups that improve its hydrophilicity. Consequently the main chains of polymer are degraded, thereby resulting in a polymer of low MW and feeble mechanical properties, thus, making it more accessible for further microbial assimilation [121]. Since commercial polyolefins have relatively high molar mass values, there are very few ends of molecules accessible on or near the surfaces of materials made from these resins [19]. It has however been observed that the oxidation products of polyolefins are biodegradable [122–124]. Such products have molar mass values that are significantly reduced, and they incorporate polar, oxygen-containing groups such as acid, alcohol, and ketone [125]. This is the basis for the term oxo-biodegradable polyolefins [19]. The biodegradation of polyolefins always follows photodegradation and chemical degradation.

PE is one of the synthetic polymers that exhibit high hydrophobic level and high MW. Naturally, it is not biodegradable. Therefore their use in the production of packing materials and disposal pose serious environmental problems. In order to make PE biodegradable, modification of its crystalline level, MW and mechanical properties that are responsible for PE resistance towards degradation is required [126]. This can be achieved by improving PE hydrophilic level and/or reducing its polymer chain length by oxidation in order to be accessible for microbial degradation [127]. The degradation of PE can occur by different molecular mechanisms; chemical, thermal, photo, and biodegradation [119]. It is known that biodegradation of PE occurs by two mechanisms: hydro-biodegradation and oxo-biodegradation. These two mechanisms agree with the modifications due to the two additives, i.e., pro-oxidant and starch used in the synthesis of biodegradable PE. In case of the pro-oxidant additive, biodegradation occurs following photodegradation and chemical degradation. If the pro-oxidant is a metal combination, after transition, metal catalyzed thermal peroxidation, biodegradation of low MW oxidation products occurs sequentially. The most commonly used additives are stearate (St) complexes of transition metals such as zinc (ZnSt), copper (CuSt), silver (AgSt), cobalt (CoSt), nickel (NiSt), manganese (MnSt), chromium (CrSt), and vanadium (VSt), or alkaline earth metals such as magnesium (MgSt). Starch blended with PE has a continuous starch phase that makes the material hydrophilic and therefore, catalyzed by

amylase enzymes. Microorganisms can easily access, attack, and remove this part. Thus the hydrophilic PE as matrix continues to be hydro-biodegraded [128].

PP films and bioriented polypropylene are widely used in packaging and in a variety of other applications due to their great potential in terms of barrier properties, brilliance, dimensional stability, and processability. As the use of the material widens so does the amount of waste disposed off into the environment [5,129]. PP biodegradation is possible by microorganisms; this process takes a long time, i.e., over hundreds of years to fully decompose. The amorphous regions of PP are the most susceptible to degradation and the impurities in the polymeric material can act as a catalyst for photodecomposition. The energy absorbed by means of heat, light, mechanical strain, etc. causes the β -scission, and the peroxide and hydroperoxides radicals generated catalyze the process [130–132]. Owing to the presence of hydrogen linked to a tertiary carbon in the backbone chain, PP degrades preferentially by chain scission with an overall shift of the MWD curve towards lower values [133]. As the total weight of the polymer used for gel permeation chromatography (GPC) measurements is kept constant the area under the MWD curve is also kept constant. The fragments of chains formed during scission are shorter than the original chains and so during the (GPC) run they will be excluded from the higher MW side, thereby reducing the weight fraction $[dwt/d(MW)]$ at this point. They will be retained for a long time in the GPC, while columns elute with other short chains, thereby increasing the original weight fraction at this particular MW [133].

Methods of biodegradation

The usage of certain enzymes and organisms to degrade polymers are classified as methods of biodegradation of polymers [98]. Appropriate selection of test procedure based on the nature of plastic and the climatic conditions of the study environment are the most important factors in the determination of biodegradation. Respirometry tests can be used for aerobic microbes. During respirometry tests, a solid waste sample is first placed in a container with microorganisms and soil, and then the mixture is aerated. Over the course of several days, microorganisms digest the sample bit by bit and produce carbon dioxide and the resulting amount of CO_2 serves as an indicator of degradation. Biodegradability can also be measured by anaerobic microbes and the amount of methane or alloy that they are able to produce. A lot of test methods have been developed by the International Standard Organization (ISO) in order to assess the potential biodegradability of plastics [134] and by the American Society for Testing and Materials (ASTM) [135].

Biodegradation can also be characterized with loss of weight. During degradation the mass of the material may undergo changes, and these changes can be monitored by comparing the mass before and after the degradation period. The material should be dried to a constant mass before measuring the initial weight of the sample in order to avoid residual moisture in the samples. The drying temperature should not exceed the temperature at which the materials undergo irreversible changes (e.g., melting temperature). After degradation the sample should be washed thoroughly with distilled or deionized water in order to remove traces of soluble degradation products, such as, enzymes, salts, or other impurities and then dried under

vacuum conditions until constant weight is attained. The extent of degradation is commonly determined by calculating the percentage weight loss [136].

4.1.2.6 Catalytic degradation

Catalytic degradation of plastic waste offers considerable advantages when compared to pure thermal degradation, as the latter demands relatively high temperatures and its products require further processing for their quality to be upgraded [137]. The advantages of catalytic degradation are (1) the low cracking temperature due to low activation energy and a short cracking time is required, (2) the high cracking ability of plastics, (3) the low concentration of solid residue in the product, and (4) the narrow product distribution with peaks of light hydrocarbons in the boiling point range of motor fuel and a high selectivity to liquid products [138]. Thus the extreme effect of catalyzed decomposition of polymers has necessitated wave of research in the area of catalysis and polymer degradation. Catalytic degradation occurs at considerably low temperatures [139] and forms hydrocarbons in the range of motor engine fuel [140,141] and thereby eliminating the necessity of further processing. In such a recycling process, liquid fuel is the most valuable product.

Catalytic cracking applied to the breakdown of polyolefins has focused mainly on polymer transformation into gaseous and liquid products of interest. For example, research has shown that for PE, the mesoporous material Al-MCM-41 produces hydrocarbons within the gasoline fraction while ZSM-5 governs the cracking towards light compounds with a large production of gaseous and aromatic hydrocarbons [142]. When Al-MCM-41 is used as a catalyst, the cracking occurs by a mechanism of random scission as a result of its large pore size and medium acidity. The zeolite HZSM-5, on the other hand, results in an end-chain cracking pathway as a result of its small pore size and strong acidity [142]. It has been proven that the catalyst's particle size is very important in catalytic degradation; this was confirmed by analyzing nanocrystalline zeolite ZSM-5 samples. A high cracking activity due to their large external surface and low diffusional constraint was observed [142]. Furthermore, researchers have studied beta zeolites and found that the particles with the smallest crystal size (~ 100 nm) give the best performance due to the bigger surface area and higher production of liquid compounds [143,144]. The addition of a catalyst not only improves the quality of products obtained from pyrolysis of plastic wastes, lowers the temperature of decomposition, but also enable a given selectivity to a certain product to be achieved [35].

Mechanism of catalytic degradation

Demirbas [145] investigated the catalytic degradation of polyolefin using the TGA as a potential method for screening catalysts and have found that the presence of catalyst led to a decrease in the apparent activation energy. Different mechanisms (ionic and free radical) for plastic pyrolysis proposed by different scientists are as given below.

Electrophilic catalysts cause marked changes in the kinetics of degradation of polyolefins. There is a change in the gross mechanism, accompanied by a considerable increase in the rate and selectivity of the process [146]. The electrophilic

catalytic degradation of polyolefins that occurs by a cationic mechanism [147] is very interesting from the theoretical viewpoint as an example of the decomposition of polymer products by terminal group or random mechanisms. In the last three decades, studies on the catalytic degradation of polyolefins in the presence of MAlCl_4 complexes, a cationic process mechanism, have been carried out and interpreted on the basis of a possible single-electron oxidation of primary radicals formed by the action of heat on the polymer [146].

1. Random thermal decomposition, with preference occurring at the weakest bonds, e.g. (Fig. 4.11)
2. A redox reaction with the formation of the polymer carbocation; it is a mechanism which would seem plausible only if M^+ is relatively easily reduced (Fig. 4.12).
3. Depolymerization of the macroions with formation of monomer (Fig. 4.13):
4. Chain transfer to polymer with further depolymerization of the macroions starting from end groups (Fig. 4.14):

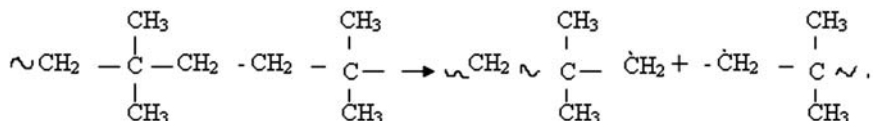


Figure 4.11 Random thermal decomposition at the weakest bond.

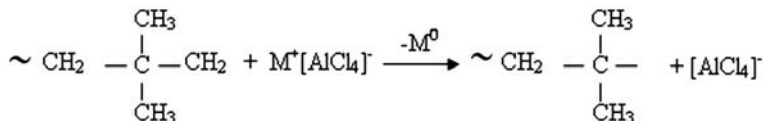


Figure 4.12 A redox reaction with the formation of the polymer carbocation.




Figure 4.13 Depolymerization of the macroions with formation of monomer.

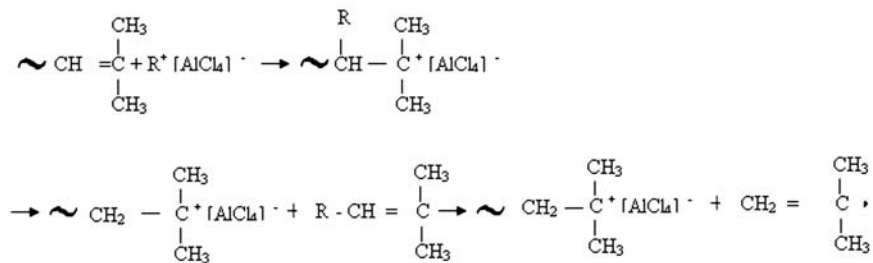


Figure 4.14 Chain transfer to polymer with further depolymerization of the macroions starting from end groups.

In catalysis by the hydrates of MAlCl_4 salts the polyolefin degradation process is initiated at the active site $\text{H} + [\text{MAlCl}_4 \cdot \text{OH}]$ —having the structure as shown in Fig. 4.15.

The hydrate can initiate the degradation randomly along the chain and preferentially at end groups. The interaction of the catalyst with the weak bonds of the polymer chain is determined by the structure of the polyolefin. In PE the degradation process is initiated mainly at the vinylidene and trans-vinylene internal double bonds. The main initiation sites along the chain in butyl rubber are the coupling points of the isobutylene fragments with the isoprene units. End group initiation proceeds through the end double bonds [146]. It can be completely stated that the processes of initiation of electrophilically catalyzed polyolefin degradation may be expressed by the following structures:

1. End group processes, where R denotes CH_3 and H for (polyisobutylene, butyl rubber), and PE, respectively (Fig. 4.16).
2. Random hydride abstraction followed by chain cleavage (Fig. 4.17):
3. Or proton addition followed by chain cleavage (which is more probable for isobutylene–isoprene copolymer and PE) (Fig. 4.18):

It can be concluded that the electrophilic degradation of different polyolefins is initiated by a few common pathways. Degradation may start either at double bond end groups or at weak bonds along the chain. The path of the chain degradation reaction is determined by the structure of the polyolefin.

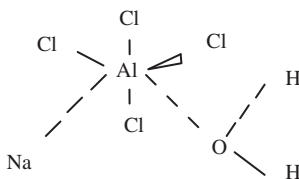


Figure 4.15 Structure of polyolefin degradation process is initiated at the active site $\text{H} + [\text{MAlCl}_4 \cdot \text{OH}]$.




Figure 4.16 End group processes.




Figure 4.17 Random hydride abstraction.

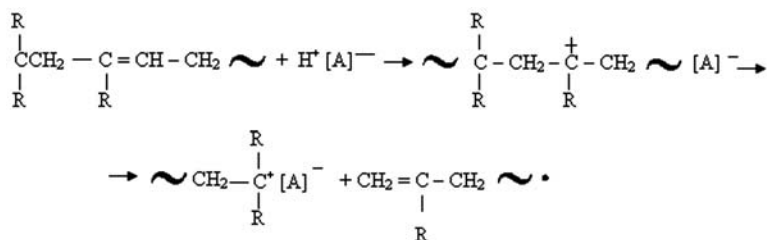


Figure 4.18 Proton addition followed by chain cleavage.

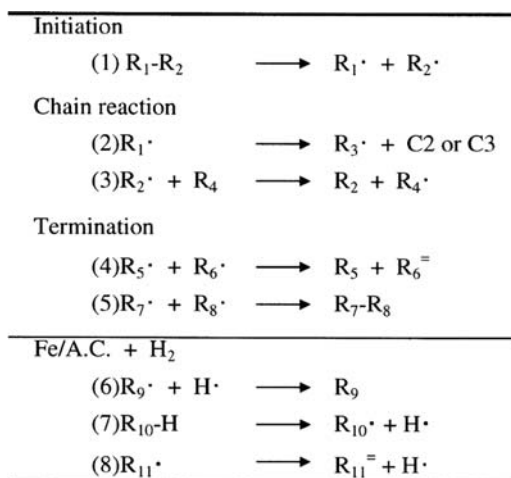


Figure 4.19 The sequence of radical chain reactions [148].

Sekine and Fujimoto [148] investigated the function of Fe and activated carbon (AC) as a catalyst by comparing Fe/AC with Fe/SiO₂ or AC. Furthermore, the effect of H₂ as a reaction gas on the product distribution in the catalytic degradation of PP was investigated. The reaction mechanism shown in Fig. 4.19, explains the reactions since Fe/AC is neither an acidic nor a basic catalyst, but a neutral catalyst. Initially (1) the random scission of the C–C bond of the main chain occurs with heat, to produce hydrocarbon radicals (HCRs). This process initiates the reaction. Then, (2) the HCR decomposes to produce small hydrocarbons such as propylene, followed by β-scission or (3) pulls out H radicals from other hydrocarbons to produce a new HCR. The former is called intramolecular radical transfer, and the latter is called intermolecular radical transfer. The three processes stated above are chain reactions. The termination reactions are (4) disproportionation or (5) recombination of two HCRs. In these mechanisms, (1) and (2) are the reactions in which the MWs decrease, (3) and (4) show no change, and (5) is the reaction in which, no MWs increase. In the case of catalytic degradation with Fe/AC in a H₂ atmosphere, (6) is

the hydrogenation of HCR (and olefin) and the pulling out of the H radical from hydrocarbon (7) or HCR (8) by AC. They concluded that supported Fe promotes H₂ consumption to decompose solid residues, and AC support degrades heavy oil to produce light oil. As a result, using Fe/AC as a catalyst gives the maximum yield of the liquid product.

Methods of catalytic degradation

The Taguchi technique is a method used for the designing of experiments to investigate how different parameters affect the mean and variance of a process performance characteristic that defines how well the process is functioning. The Taguchi method involves reducing the variation in a process through robust design of experiments (DOEs). The overall objective of the method is to produce high quality product at low cost to the manufacturer [149]. In literature, parameters such as temperature, catalyst concentration, and catalyst type have been identified. These parameters influence the decomposition of waste PP in a batch process and the Taguchi method was used to optimize the process parameters for the production of liquid fuel from waste PP. With the help of regression modeling an equation was developed for the yield of liquid fuel as a function of temperature, catalyst concentration, and catalyst type [149]. Researchers have further used the Taguchi experimental design to obtain optimum condition on catalytic degradation of the polymers [150]. The purpose of their research was to determine the maximum quantity of gasoline production from the degradation of mixed PE and PP using the Taguchi technique as a DOE method. Their findings suggested that the Taguchi is the most promising DOE method in order to investigate the optimum condition to produce a maximized factor such as gasoline. Their second major finding was that ~51% of the polymers can be degraded to gasoline components which can be used as automobile fuel. Finally, Taguchi suggested that 420°C and 50% catalyst is the most promising condition for maximum production of the gasoline from 40%, 20%, and 40% HDPE, PP, and LDPE as mixed polymers, respectively [150].

Catalytic degradation of plastic sample can also be performed in a batch autoclave. In order to determine the effect of temperature and a new catalyst on converting the polyolefins in present of PVC into liquid fuel, the semibatch reactor with ambient atmospheric conditions was designed. Also factorial design was employed as the DOE's method. The analysis of variance for the liquid and the gas showed that the main effects of temperature, catalyst percentage and PVC composition are significant. Also there is a significant interaction between temperature and catalyst percentage to liquid and gas production. Similarly, survey of interaction among the other factors indicated that there is not a significant interaction [151]. The effects of catalysts on the catalytic degradation of polymer have also been investigated by contacting melted polymers with catalyst in fixed bed reactors [152,153], heating mixtures of polymer, and catalyst powders in reaction vessels [154,155], and passing the products of polymer pyrolysis through fixed bed reactors containing cracking catalysts [156].

4.1.3 Factors affecting polyolefins degradation

4.1.3.1 Chemical composition

Chemical composition of polyolefins or polyolefins-based products play a very relevant role in their degradation. The presence of complete long carbon chains in the thermoplastic polyolefins makes these polymers nonsusceptible to degradation by microorganisms. Despite this the inclusion of hetero-groups such as oxygen in the polymer chains, polymeric substances are made labile to thermal degradation and biodegradation [38]. This is because many unsaturated polymers can undergo degradation from a range of sources, such as oxygen absorption, which leads to the release of organic peroxides. Linear saturated polyolefins are resistant to oxidative degradation. The presence of unsaturation in the polymer chain makes them susceptible to oxidation, for example natural rubber is more susceptible to degradation than PE [157].

4.1.3.2 Size of molecules/molecular structure

Literatures have shown that degradation rate is dependent on the size of the polyolefin being studied. Hydrogen has been used as a chain-transfer agent to control the molecular mass of the polymer for the commercial production of polyolefins such as PP and PE [158,159]. The particle size distribution of polymer particles was shifted to lower sizes by increasing the hydrogen concentration [159]. The size of the molecules in the polymers affects their mechanical degradation, thermal degradation, and biodegradation. These degradations increase as the size of the molecule decreases [38]. Paik and Kar [160,161] discovered that the particle size of PP and PE influences the thermal stability of these polymers, but they did not consider the molecular mass of the samples. Abbas-Abadi et al. [162] investigated the molecular mass of particle size on the thermal degradation of a commercial HDPE powder and they found that the biggest particles (> 200 nm) with highest molecular mass maintained superior thermal stability of these particles. Their results showed that molecular mass is not the only key factor and in smaller sizes, bulk density, and heat transfer can affect the thermal stability.

Structure has a strong influence on the other properties of polyolefins. Thermal oxidation is complex process, including chain oxidation of HCRs, destruction of macrochains and structure formation (crosslinking, crystallization). Thermal oxidation is accompanied by structural–physical processes, leading to structure change (structural reconstruction) under the action of high temperature. The mechanism of these processes will depend on the polymer's morphology and in turn, will influence the oxidation kinetics. The effect of a polymer crystallites in vacuum and on air: the effect of high temperature may lead to perfection of crystallites structure, rise of temperature and melting heat, at the same time at long high temperature effect the destruction of chains occurs and crystallites are decomposed [163].

4.1.3.3 *Molecular weight*

The MW is also important for biodegradability because it determines many physical properties of the polymer. Increasing the MW of the polymer decreased its degradability [164]. It has been reported in the literature that some microorganisms, for their growth, attack and utilize faster, polyolefins with low MW when compared to high MW polyolefins [165]. Linear polyolefins with MW lower than ~ 620 support microbial growth [166]. Degradation of plastic polymers can further lead to low MW polymer fragments, such as monomers and oligomers can lead to the formation of new end groups, especially carboxylic acids [167]. As the MW of the polymers is reduced, the material becomes brittle [168] and it is more susceptible to fragmentation which makes a higher surface area available for further reactions. Owing to the high MW and the lack of functional groups biodegradation of long polyolefin chains is limited. [169,170]. Therefore high MW PE, PP, and PS polymers must be broken down by abiotic degradation to smaller pieces before biodegradation at a measurable rate takes place. If the polymers are too large, they cannot pass through the microbial cellular membranes [171].

4.1.3.4 *Functionality*

Polymers bearing polar functionalized side groups are highly desired materials, due to their unique and rapidly expanding range of material properties. When compared to their nonfunctionalized analogues they exhibit beneficial properties with respect to adhesion, toughness, print/paintability, miscibility, and rheological properties [172].

Nonfunctionalized polyolefins (i.e., polyethylene and polypropene) have found their way in many (commodity) applications due to their outstanding properties, such as solvent resistance and thermal stability. Nowadays, these materials can easily be obtained in large scales and at low cost with very high precision of the polymer microstructures. However, due to the lack of functional groups in these polymers, they perform badly when surface chemistry is involved [173]. Thus functional polyolefins such as polyethylene or polypropene that bear functional groups are highly desired materials, due to their beneficial surface properties. The incorporation of only a small amount of functionalized monomers, randomly placed in the polymer backbone, has a large effect on the surface properties of the resulting polymers, while the beneficial properties of the original nonfunctionalized polyolefins are retained [174,175]. The properties of the resulting materials can be further tuned by varying the structure of the functional groups, the amount of incorporation and the distribution of the polar functionalities along the polymer chain [173].

The choice of materials that will be incorporated onto PO is very important. Introduction of carbonyl groups in PO makes these polymers susceptible to photodegradation. As the number of chromophores increases the rate of photodegradation increases due to the extra sites, which are available to absorb more photons and to initiate the reaction for degradation. PO undergo slow sulfonation and oxidative degradation by reagents based on concentrated sulfuric acid. In chromic acid,

sulfonation results, in the more rapid oxidative degradation of PP with a slower attack on PE [35]. Obtaining functionalized polymers via direct copolymerization of nonfunctionalized olefins and polar vinyl monomers is of particular interest, since the control over the amount of polar monomers and their distribution along the chain could in principle be achieved by exploiting the reactivity differences of both monomers [175–177].

4.1.4 Controlling polyolefins degradation rate

4.1.4.1 Effect of pigments and dyes

Organic pigments and dyes are widely used in the coloration of polymer materials for many commercial applications. However, the presence of dyes and pigments can dramatically influence the chemistry of oxidation, degradation, and stabilization processes involved in a polymer and will quite often dominate the stability of the end-product. For example, by absorbing and/or scattering of UV light, pigments can induce a marked protective effect. The absorption of light by organic dyes and pigments is followed by various chemical and physical interactions which result from the dye or pigment molecules being promoted to an excited state which is more reactive than the ground state [77].

Pigments are colored, white or black materials, which are practically insoluble in the medium in which they are applied. Pigment is incorporated into the polymer by a dispersion process and forms in the material, a separate phase. They are conveniently classified as either inorganic or organic types. The properties of a pigment are primarily dependent on its chemical structure, i.e., the way in which the molecules pack in their crystal lattice [178]. Certain pigments, e.g., copper phthalocyanine, exist in different polymorphic forms with significantly different optical and stability properties. Other important factors, especially in influencing the strength or intensity of color of pigments, are particle shape and size.

The patent US 4360606 discussed organic dyes being used as photosensitizers [179]. Examples, such as acridine orange and yellow, congo red, crystal violet, brilliant green, bromothymol blue, alizarin, azure B, *N,N*-dimethyl-*p*-phenylazoaniline, and methylene blue, were given. The chemical structures of some of these dyes show some comparability to some of the structures listed as prodegradants, for example, alizarin is based on an anthraquinone type structure. Most other dyes contain highly conjugated unsaturated ethylene double bond groups [104]. In addition to organic dyes, inorganic pigments such as TiO₂ and ZnO that are often added to whiten the polymer can influence the degradation rate. As mentioned in the earlier section of this report, the photo activity of these additives is dependent on particle size, surface treatment, and crystalline form as well as any metal ion dopants that may be used [104].

Investigations on pigment–polymer stability interactions have been carried out with polyolefins, but there are limited studies which actually indicate that the pigments can have effect on the light stability of other polymers too [77]. Black, brown, and red pigments were recommended to improve color and physical

properties of Acrylonitrile-Butadiene-styrene rubber under weather aging. In rigid PVC, most pigments contributed to improved light stability on outdoor exposure. It was found that the surfaces degraded a lot faster than the bulk of the polymer with only minor differences in surface protection by the various organic and inorganic pigments (phthalocyanine blue, iron oxide red, channel black, P. Red 48, P. Yellow 83) [180–182].

4.1.5 Controlling environmental degradation of polyolefins

PO are known to degrade by an oxo-biodegradation mechanism and there is a single standard test method developed and published, namely, ASTM D6954-04, is a standard guide for exposing and testing plastics that degrade into the environment by a combination of oxidation and biodegradation. This guide provides a framework to compare and rank controlled laboratory rates of degradation and the degree of physical property changes of polymers by thermal and photo-oxidation processes and the biodegradation and ecological impacts in defined applications and the disposal environments after degradation. There are conditions selected for oxidation (UV or thermal at 20–70°C) in order to speed up the degradation likely to occur in a chosen application and disposal environment. The resulting residues from abiotic oxidation are then exposed to appropriate disposal or use environments in standard biometric test methods in order to measure the rate and degree of biodegradation. Lastly, the end-residues must be submitted to aquatic and terrestrial toxicity tests (E 1440, OCED guideline 207, and OCED guideline 208) in order to ensure that they are environmentally benign and not persistent [77]. Each degradation stage during polyolefins processes should be independently evaluated in order to allow a combined evaluation of polyolefins environmental performance under controlled laboratory settings. According to the standard of the control of environmental degradation of polyolefins the results of laboratory exposure cannot be directly extrapolated to estimate absolute rate of deterioration by the environment because the acceleration factor is material dependent and can be significantly different for each material and for different formulations of the same material. However, the exposure of a similar material of known outdoor performance (as a control) at the same time as the test specimens, allows comparison of the durability relative to that of the control under the test conditions [77].

In a growing number of cases the controlled degradation of a polymer in the environment is the desired result in the polymer processing industries. Electron irradiation technique is a well-known technique for crosslinking, graft-linking, and polymerization in the polymer industry [183]. Controlling the degree of degradation in the environment, with a consistent MWD of polymers, savings achieved in the use of chemicals (in conventional methods), reduced costs and environmentally friendly processes are the beneficial effects of using radiation technology in the polymer industries. Efforts should thus, be expanded to reducing the cost of irradiation required in such technologies. For example, advantages of employing high energy radiation to crosslink PE are that: (1) it can be performed at room temperature, (2) it offers increased flexibility in product processing, (3) varying degrees of

cure can be obtained without changing the product formulation, and (4) no impurities in the form of catalyst fragments are introduced into the material. In addition the production rate is higher and not subject to as many potential equipment problems as the thermal process [184].

Future progress in the capability to control the radiation-induced degradation of polymers is dependent on the understanding of the fundamental processes underlying degradation phenomena. Radiation degradation mechanisms are exceedingly complex, and constitute numerous chemical reaction sequences that result in changes to molecular structure. Significant changes in material morphology can also occur. The economics of controlled degradation process depends strongly on the doses involved to achieve a certain degree of MW change. The anticipated level of degradation should therefore be achieved at the lowest possible doses. The use of some oxidizing agents in small amounts has proven to help in reducing the required doses to economically acceptable lower levels [185].

4.1.6 Challenges for new generation of polyolefins

New generation of polyolefins plays a major role in the environmental issue and every progress achieved for them is a substantial progress for the whole issue. The modern approach to environmental issues deeply involves a wide sector of materials. Beside the several aspects that common to other parts of the processing industry, such as the use of friendly chemicals, clean and safe processes, and very low or zero emissions, other questions must be taken into consideration. It is highly desirable that the material does not have any negative effect on the environment during processing and during its transformation into articles or components. Again, it is very important to avoid similar negative effects on polyolefins at the end of their life [186].

Polyolefin-based materials are widely used in almost every aspect of processing industries due to their excellent properties, the ease of processing, recyclability, and of course a good performance cost. Compounding ingredients, such as mineral fillers, glass fibres, elastomers, flame retardants, pigments, or carbon black, are incorporated into the polymer according to its future application. With regards to this composition the analysis of polymeric materials turns out to be a challenging analytical task. Stabilizers are used at various stages of a polymer life cycle. It starts with controlling reaction rates or avoiding early polymerization in the actual polymer formation. Thus the analysis of stabilizers is very significant on multiple levels. Firstly, it is evident that the quantity of stabilizers is a matter of analytical concern because the concentration of these stabilizers determines how long a polymer will be stabilized sufficiently; thus formulating these stabilizers can be challenging. Secondly, stabilizers might be degraded by reactions unrelated to any stabilization. This decreases the concentration of intact stabilizer in the polymer and is hence undesirable. A knowledge on the formation of the degradation products helps to identify these degradation pathways of the stabilizers and to avoid them [187]. Lastly, degradation products of stabilizers generated when protecting the polymer

should be identified in order to have a better insight into involved reactions. If they are quantified, it is possible to determine the original level of stabilization.

4.1.7 Long-term performance of polyolefins in different environments

In the aspect of polyolefins processing; material performance has evolved significantly. This has enabled the demonstration and the validation of long-term performance of these new materials. Understanding the mechanisms of aging for any material and the key factors influencing the performance of polyolefins in their end use, is very important in knowing the capacity of how the material will be best applied and in the development of the methodologies that will be used in projecting the long-term performance of the product in service.

Antioxidants, UV stabilizers, and other protective additives have been developed in the past in order to improve the long-term durability of polyolefins, particularly in the outdoor environment. It is important for polyolefins to retain its useful properties through one or more fabrication procedures, e.g., extrusion, blending, injection molding, and palletizing and the final product must have a reasonable storage life. It is the end of the product service life that the controlled lifetime of polyolefins must degrade in whatever environment it is discarded [188]. The long-term performance of stabilized polyolefins in different environments has been studied with a focus on antioxidant consumption and migration [189]. The study was divided into two parts: In the first part, the migration behavior of three similar bifunctional phenolic antioxidants in two types of PE, in different media, was studied. Focus was then set on the antioxidants migration behavior due to factors such as media, antioxidant structure, morphology, and surface properties of the PE. The author [189] found that the structure of the antioxidants was similar; still the surrounding media had to be taken into account as a factor to influence the migration behavior. The more polar antioxidant showed a fast loss to the surrounding medium in the shape of water, both water saturated with air and water saturated with nitrogen. The chemical consumption of antioxidant was observed and the direct presence of oxygen as in air was the opposite of inert atmosphere, this was not playing a significant role in the migration behavior of antioxidant. The presence of oxygen however, as in water saturated with air, when compared to water saturated with nitrogen gas, had an impact on the migration behavior with an increase of loss of antioxidant due a high loss rate from the polymer boundary. The linear polyethylene samples showed in all cases, the fast loss of antioxidant when compared with the branched (BPE) samples. The large molecular size of the phenolic antioxidants was suggested as a reason. The amorphous area next to the crystal lamellae, interfacial component, was suggested to be more difficult to penetrate for the diffusant due to its large size and rigidity.

In the second part, polyolefin, pressurized pipes were exposed to chlorinated water at elevated temperatures. The author found that the PE pipes were stabilized with hindered phenols and phosphates. Measurement of the oxidation induction

time, using the DSC showed that the stabilizing system was rapidly consumed, chemically by the action of chlorinated water. Extensive polymer degradation was confined strictly to the surface and to the amorphous phase of the semicrystalline polymer. The growth of the highly degraded layer was constant in time. For the poly butene-1 (PB-1) pipes the chlorinated water caused an early depletion of the antioxidant system, with polymer degradation at the inner wall material, resulting to an early pipe failure. The reduction in the antioxidant concentration was essentially independent of the chlorine concentration in the range 0.5–1.5 ppm of Cl. The lifetime shortening in the isotactic poly(butene-1) pipes exposed to chlorinated water (0.5–3 ppm) was approximately by a factor of 10 with respect to that obtained with pure water. The lifetime shortening was significant even at low chlorine concentrations (0.5 ppm) and a further increase in chlorine content led only to a moderate additional decrease of lifetime [189].

4.1.8 Conclusion

Plastic wastes are of universal concern because of their long-term environmental and economic impacts and waste management problem. Degradation of plastic waste by various means and further assimilation into the environment is one of the ways that can be employed to curtail waste management problems. The degradation of polyolefins materials is caused by exposure to various factors such as heat, irradiation ozone, UV light, mechanical stress, and microbes. Degradation is further promoted by oxygen, humidity, and strain and led to such negative effects as brittleness, cracking, and fading. The mechanism of polymer degradation is highly complicated, involving simultaneous formation and decomposition of hydroperoxides. Understanding the mechanism of polymer degradation can go a long way in assisting researchers and the technologists to induce the different types of degradation in polyolefins. The addition of additives in polymers and the capacity to know the various factors responsible for these degradations could help to intensify these degradations.

References

- [1] Ulrich H. Introduction to industrial polymers. 2nd Ed. Munich: Carl, Hanser Verlag; 1993. p. 188.
- [2] Barlow A. The chemistry of polyethylene insulation. IEEE Electr Insul Mag 1991;7 (1):8–19.
- [3] Harding KG, Dennis JS, Von Blottnitz H, Harrison STL. Environmental analysis of plastic production processes: comparing petroleum-based polypropylene and polyethylene with biologically-based poly- β -hydroxybutyric acid using life cycle analysis. J Biotechnol 2007;130:57–66.
- [4] Ramano U, Garbassi F. The environmental issues: a challenge for new generation polyolefins. Pure Appl Chem 2000;72(7):1383–8.

- [5] Majumda J, Cser F, Jollands MC, Shanks RA. Thermal properties of polypropylene post-consumer waste (PP PCW). *J Ther Anal Calorimet* 2004;78:849–63.
- [6] Karpukhin ON, Siobodetskaya EM. Kinetics of the photochemical oxidation of polyolefins. *Russ Chem Rev* 1973;42(3):173–89.
- [7] Scott G. *Polymers and the environment*. Cambridge: RSC Paperbacks; 1999.
- [8] Swift G, Wiles DM. Biodegradable and degradable polymers and plastics in landfill sites. In: Kroschwitz JI, editor. *Encyclopedia of polymer science and technology*. Hoboken, NJ: John Wiley & Sons; 2004. p. 40–50.
- [9] Sudhakar M, Doble M, Murthy PS, Venkatesan R. Marine microbe-mediated biodegradation of low- and high-density polyethylenes. *Int Biodeterior Biodegrad* 2008;61:203–13.
- [10] Ojeda T, Freitas A, Birck K, Dalmolin E, Jacques R, Bento F, Camargo. Degradability of linear polyolefins under natural weathering. *Polym Degrad Stab* 2011;703–7.
- [11] Zhu X, Guo Z, Cen W, Mao B. Ethylene polymerization using improved polyethylene catalyst. *Chin J Chem Eng* 2011;19(1):52–6.
- [12] Kutz M. *Hand book of materials selection*. New York: John Wiley and Sons; 2002. p. 347.
- [13] Francis V. Modification of low linear polyethylene for improved photo and biodegradation. Ph.D. Thesis, Faculty of Technology, Department of Polymer Science and Rubber Technology, Kerala, India; 2012.
- [14] Lundbäck M. Doctoral thesis, environments including chlorinated water: antioxidant consumption, migration, and polymer degradation. School of Chemical Science and Engineering KTH Fibre and Polymer Technology, Germany; 2005.
- [15] Edward N, Peters. Thermoplastics, thermosets and elastomers—descriptions and properties. In: Kutz M, editor. *Mechanical engineers' handbook*, fourth edition, vol. 1: materials and engineering mechanics. USA: John Wiley & Sons; 2015. p. 357 (Chapter 9).
- [16] Encyclopedia Britannica, Polypropylene chemical compound. <http://global.britannica.com/science/polypropylene> [assessed 23.03.16]
- [17] The Essential Chemical Industry on Line by The University of York. <http://www.essentialchemicalindustry.org/polymers/polypropene.html> [assessed 23.03.16].
- [18] Sudhakar M, Bhaduri S, Uppara PM, Doble M. Approaches to enhance the biodegradation of polyolefins. *Open Environ Eng* 2009;2:68–80.
- [19] Wiles DM, Scott G. Polyolefins with controlled environmental degradability. *Polym Degrad Stab* 2006;91:1581–92.
- [20] Grassie N, Scott G. *Polymer degradation and stabilization*. New York, NY: Cambridge University Press; 1985.
- [21] Longo C, Savaris M, Zeni M, Brandalise RN, Grisa AMC. Degradation study of polypropylene (PP) and bioriented polypropylene (BOPP) in the environment. *Mater Res* 2011;14(4):442–8.
- [22] Chiellini E, Corti A, D'Antone S, Baciù R. Oxo-biodegradable carbon backbone polymers—oxidative degradation of polyethylene under accelerated test conditions. *Polym Degrad Stab* 2006;91:2739–47.
- [23] Alwai KBM. Thermal degradation and morphology of polymer blends comprising poly(ϵ -caprolactone) and epoxidized natural rubber with addition of phenol as catalyst. Bachelor of Science (hons.) chemistry faculty of applied science. Universiti Teknologi Mara Malaysia; 2009.
- [24] Westerhout RWJ, Waanders J, Kuipers JAM, Van Swaaij WPM. Kinetics of the low-temperature pyrolysis of polyethene, polypropene, and polystyrene modeling, experimental determination, and comparison with literature models and data. *Ind Eng Chem Res* 1997;36:1955–64.

- [25] Gersten J, Fainberg V, Hetsroni G, Shindler Y. Kinetic study of the thermal decomposition of polypropylene, oil shale, and their mixture. *Fuel* 2000;1679–86.
- [26] Ceamanos J, Mastral JF, Millera A, Aldea ME. Kinetics of pyrolysis of high density polyethylene. Comparison of isothermal and dynamic experiments. *J Anal Appl Pyrol* 2002;63:93–110.
- [27] Gao Z, Amasaki I, Nakada M. A thermogravimetric study on thermal degradation of polyethylene. *Anal Appl Pyrol* 2003;67:1–9.
- [28] Gao Z, Kaneko T, Amasaki I, Nakada M. A kinetic study of thermal degradation of polypropylene. *Polym Degrad Stab* 2003;80:269–74.
- [29] Ofoma I. Catalytic pyrolysis of polyolefins. Masters of science in chemical and biomolecular engineering. Atlanta, GA: Georgia Institute of Technology; 2006.
- [30] Murichan N, Cherntongchai P. Kinetic analysis of thermal degradation of polyolefin mixtures. *Int J Chem Eng Appl* 2014;5(2):169–75.
- [31] Aboulkas A, El harfi K, El Bouadili A. Thermal degradation behaviors of polyethylene and polypropylene. Part I: pyrolysis kinetics and mechanisms. *Energy Conver Manage* 2010;51:1363–9.
- [32] Kim S, Kim Y-C. Using isothermal kinetic results to estimate the kinetic triplet of the pyrolysis of high density polyethylene. *J Anal Appl Pyrol* 2005;73:117–21.
- [33] Kim S, Kavitha D, Yu TU, Jung J-S, Song J-H, Lee S-W, et al. Using isothermal kinetic results to estimate kinetic triplet of pyrolysis reaction of polypropylene. *J Anal Appl Pyrol* 2008;81:100–5.
- [34] Corrales T, Catalina F, Peinado C, Allen NS, Fontan E. Photooxidative and thermal degradation of polyethylenes: interrelationship by chemiluminescence, thermal gravimetric analysis and FTIR data. *J Photochem Photobiol A Chem* 2002;147: 213–24.
- [35] Singh B, Sharma N. Mechanistic implications of plastic degradation. *Polym Degrad Stab* 2008;93:561–84.
- [36] Murata K, Hirano Y, Sakata Y, Azhar Uddin Md. Basic study on a continuous flow reactor for thermal degradation of polymers. *J Anal Appl Pyrol* 2002;65:71–90.
- [37] Zuev VV, Bertini F, Audisio G. Investigation on the thermal degradation of acrylic polymers with fluorinated side-chains. *Polym Degrad Stab* 2006;91(3):512–16.
- [38] Gowariker VR, Viswanathan NV, Sreedhar J. *Polymer science*. New Delhi, India: New Age International (P) Limited Publishers; 2000. p. 263–85.
- [39] Paabo MA, Levin BC. Literature of the chemical nature and toxicity of the thermal decomposition products of polyethylenes. *Fire Mater* 1987;11:55–70.
- [40] Aguado J, Serrano DP, Miguel GS. European trends in the feedstock recycling of plastic wastes. *Global NEST J* 2007;9(1):12–19.
- [41] Kumar S, Pandaa AK, Singh R. A review on tertiary recycling of high-density polyethylene to fuel. *Resour Conserv Recycl* 2011;53:893–910.
- [42] Ahmad MB, Gharayebi Y, Salit MS, Hussein MZ, Ebrahimiasl S, Dehzang A. Preparation, characterization and thermal degradation of polyimide (4-APS/BTDA)/SiO₂ composite films. *Int J Mol Sci* 2012;13:4860–70.
- [43] Morancho JM, Ramis X, Fernández X, Cadenato A, Salla JM, Vallès A, et al. Calorimetric and thermogravimetric studies of UV-irradiated polypropylene/starch-based materials aged in soil. *Polym Degrad Stab* 2006;91:44–51.
- [44] Halket JM, Zaikin VG. Derivatization in mass spectrometry 7. On-line derivatisation/ degradation. *Eur J Mass Spectromet* 2006;12(1):1–13.
- [45] Ma X-M, Lu R, Miyakoshi T. Application of pyrolysis gas chromatography/mass spectrometry in lacquer research: a review. *Polymers* 2014;6:132–45.

- [46] Herreraa M, Matuschek G. Fast identification of polymer additives by pyrolysis-gas chromatography/mass spectrometry. *J Anal Appl Pyrol* 2003;70:35–42.
- [47] Onwudili JA, Insura N, Williams PT. Composition of products from the pyrolysis of polyethylene and polystyrene in a closed batch reactor: effects of temperature and residence time. *J Anal Appl Pyrol* 2009;86:293–303.
- [48] Kumar S, Singh RK. Recovery of hydrocarbon liquid from waste high density polyethylene by thermal pyrolysis. *Braz J Chem Eng* 2011;28(4):659–67.
- [49] Yan G, Jing X, Wen H, Xiang S. Thermal cracking of virgin and waste plastics of PP and LDPE in a semi-batch reactor under atmospheric pressure. *Energy Fuels* 2015;29:2289–98.
- [50] Feldman D. Polymer weathering: photo-oxidation. *J Polym Environ* 2002;10(4):163–73.
- [51] Sai N, Leung K, Zádord J, Henkelman G. First principles study of photo-oxidation degradation mechanisms in P3HT for organic solar cells. *Phys Chem Chem Phys* 2014;16:8092–9.
- [52] Rabek JF. Photostabilization of polymers: principles and applications. England: Elsevier Science Publisher LTD; 1990. p. 5–16.
- [53] Javaid HK, Neaz A. Photo-oxidative degradation of recycled, reprocessed hdpe: changes in chemical, thermal and properties. *Bulg J Phys* 2003;30:158–69.
- [54] Vašek L. Photodegradation of polyolefins. Bachelor Thesis, Faculty of Technology, Tomas Bata University in Zlín; 2006.
- [55] Sheldrick GE, Vogl O. Induced photodegradation of styrene polymers: a survey. *J Polym Eng Sci* 2004;16(2):65–73.
- [56] Andrady AL, Pegram JE, Tropsha Y. Changes in carbonyl index and average molecular weight on embrittlement of enhanced photo-degradable polyethylene. *J Environ Degrad Polym* 1993;1:171–9.
- [57] Abadal M, Cermak R, Raab M, Verney V, Commereuc S, Fraisse F. Study on photo-degradation of injection moulded (beta)-polypropylene. *Polym Degrad Stab* 2006;91(3):459–63.
- [58] Andrady AL, Hamid SH, Hu X, Torikai A. Effects of increased solar ultraviolet radiation on materials. *J Photochem Photobiol B Biol* 1998;46:96–103.
- [59] Santos LC, Schmitt CC, Poli AL, Neumann MG. Photo-Fenton degradation of poly(ethyleneglycol). *J Braz Chem Soc* 2011;22(3):540–5.
- [60] Chiron S, Fernandez-Alba A, Rodriguez A, Carcia-Calvo E. Pesticide chemical oxidation: state-of-the-art. *Water Res* 2002;34:366–77.
- [61] Sörensen M, Zurell S, Frimmel FH. Degradation pathway of the photochemical oxidation of ethylenediaminetetraacetate (EDTA) in the UV/H₂O₂-process. *Acta Hydrochim Hydrobiol* 1998;26:109–15.
- [62] Yang R, Liu Y, Yu J, Wang K. Thermal oxidation products and kinetics of polyethylene composites. *Polym Degrad Stab* 2006;91:1651–7.
- [63] Cruz-Pinto JJC, Carvalho MES, Ferreira JFA. The kinetics and mechanism of polyethylene photo-oxidation. *Die Angewandte Makromolekulare Chemie* 1994;216(1):113–33.
- [64] Jakubowicz I, Yarahmadi N, Arthurson V. Kinetics of abiotic and biotic degradability of low-density polyethylene containing prodegradant additives and its effect on the growth of microbial communities. *Polym Degrad Stab* 2011;96:919–28.
- [65] Tang L, Sallet D, Lemaire J. Photochemistry of polyundecanamides. 1. Mechanisms of photooxidation at short and long wavelengths. *Macromolecules* 1982;15:1432–7.
- [66] François-Heude A, Richaud E, Desnoux E, Colin X. A general kinetic model for the photothermal oxidation of polypropylene. *J Photochem Photobiol A Chem* 2015;296:48–65.

- [67] Cunliffe AV, Davis A. Photo-oxidation of thick polymer samples part II: the influence of oxygen diffusion on the natural and artificial weathering of polyolefins. *Polym Degrad Stab* 1982;4:17–37.
- [68] Furneaux GC, Ledbury KJ, Davis A. Photo-oxidation of thick polymer samples part I: the variation of photo-oxidation with depth in naturally and artificially weathered low density polyethylene. *Polym Degrad Stab* 1981;3:431–42.
- [69] Audouin L, Langlois V, Verdu J, de Bruijn JCM. Role of oxygen diffusion in polymer ageing: kinetic and mechanical aspects. *J Mater Sci* 1994;29:569–83.
- [70] Kiil S. Model-based analysis of photoinitiated coating degradation under artificial exposure conditions. *J Coat Technol Res* 2012;9:375–98.
- [71] Wypych G. Handbook of material weathering. 2nd ed. ChemTec Publishing; 1995. ISBN: 1-895198-12-7.
- [72] Ranby B, Rabek JF. Photodegradation, photo-oxidation and photostabilization of polymers. Toronto, Ontario: John Wiley & Sons Ltd; 1975 ISBN: 0-471-70788-0.
- [73] Chodák I. Crosslinking of polypropylene; polypropylene-an A–Z reference. Berlin, Germany: Kluwer Academic Publishers; 1999 ISBN: 0-412-80200-7.
- [74] Sommer A, Zirngiebl E, Kahl L, SchGnfelder M. Studies in accelerated weathering. Part II. Ultrafast weathering—a new method for evaluating the weather resistance of polymers. *Prog Org Coat* 1991;19:79–87.
- [75] Kamal MR. Effect of variable in artificial weathering on the degradation of selected plastics. *Polym Eng Sci* 1966;333–7.
- [76] Lundin T, Cramer SM, Falk RH, Felton C. Weathering of natural fiber filled polyethylene composites. *J Mater Civ Eng* 2004;16(6):547–55.
- [77] Marzec A. The effect of dyes, pigments and ionic liquids on the properties of elastomer composites. *Polymers*. Université Claude Bernard - Lyon I; 2014.
- [78] Cataldo F, Ricci G, Crescenzi V. Ozonization of atactic and tactic polymers having vinyl, methylvinyl, and dimethylvinyl pendant groups. *Polym Degrad Stab* 2000;67: 421–6.
- [79] Cataldo F. Ozone interaction with conjugated polymers-I. Polyacetylene. *Polym Degrad Stab* 1998;60:223–31.
- [80] Cataldo F. Ozone interaction with conjugated polymers-II. Polyphenylacetylene. *Polym Degrad Stab* 1998;60:233–7.
- [81] Yumauchi J, Akiyoshi Y, Ikemoto K, Matsui T. Reaction mechanism for ozone oxidation of polyethylene as studied by ESR and IR spectroscopies. *Bull Chem Soc Jpn* 1991;64:1173–7.
- [82] Lohith MN, Kuriakose G, Al-Shahrani S, Al-Mattam M, Mydeen S. The effect of ozone ageing on the chemical, physical and barrier properties of packaging films. Indianapolis: SPE ANTEC™; 2016. p. 1514–7.
- [83] Peeling J, Jazsar MS, Clark DT. An ESCA study of the surface ozonation of polystyrene film. *J Polym Sci Polym Chem Ed* 1982;20(7):1797–805 (1982).
- [84] Fujimoto K, Takebayashi Y, Inoue H, Ikada Y. Ozone-induced graft-polymerization onto polymer surface. *J Polym Sci A Polym Chem* 1993;31(4):1035–43.
- [85] Smithers R. <http://www.smithersrapra.com/testing-services/resources/standard-test-protocols/astm/astm-d1149> [assessed 23.08.16]
- [86] Material Testing. Ozone testing services, <https://www.element.com/materials-testing-services/ozone-testing-services> [assessed 23.08.16].
- [87] Mitchell BS. Kinetics process in materials. An introduction to materials engineering and science for chemical and materials engineers. New Jersey: John Wiley & Sons Inc; 2003. p. 215–79.

- [88] Tyan FY. A study of the thermal ageing of carboxylated nitrile rubber latex thin films. Master of Science Theses, Universiti Tunku Abdul Rahman; 2013.
- [89] Chen G, Guo S, Li H. Ultrasonic improvement of rheological behavior of polystyrene. *J Appl Polym Sci* 2002;84:2451–60.
- [90] Chen G, Guo S, Li H. Ultrasonic improvement of the compatibility and rheological behaviour of high-density polyethylene/polystyrene blends. *J Appl Polym Sci* 2002;86:23–32.
- [91] Peng B, Wu H, Bao W, Guo S, Chen Y, Huang H, et al. Effects of ultrasound on the morphology and properties of propylene-based plastomer/nanosilica composites. *Polym J* 2011;43:91–6.
- [92] Li Y, Li J, Guo S, Li H. Mechanochemical degradation kinetics of high-density polyethylene melt and its mechanism in the presence of ultrasonic irradiation. *Ultrason Sonochem* 2005;12:183–9.
- [93] Staudinger H, Bondy HF. Uber isoprene und Kautschuk 19 Mittel: Uber die molekulgrosse des kautschks und der Ber. *Dtsch Chem Ges* 1930;63:734.
- [94] Sohma J. Mechano-radical formation in polypropylene by an extruder action and its after-effects. *Colloid Polym Sci* 1992;270:1060–5.
- [95] Baranwal K. Mechanochemical degradation of an EPDM polymer. *J Appl Polym Sci* 2003;12(6):1459–69.
- [96] Leja K, Lewandowicz G. Polymer biodegradation and biodegradable polymers—a review. *Polish J Environ Study* 2010;19(2):255–66.
- [97] Jayasekara R, Harding I, Bowater I, Lonergan G. Biodegradability of selected range of polymers and polymer blends and standard methods for assessment of biodegradation. *J Polym Environ* 2005;13:231–51.
- [98] Premraj R, Doble M. Biodegradation of polymers. *Indian J Biotechnol* 2005;4:186–93.
- [99] Siotto M, Tosin M, Innocenti FD, Mezzanotte V. Mineralization of monomeric components of biodegradable plastics in preconditioned and enriched sandy loam soil under laboratory conditions. *Water Air Soil Pollut* 2011;221:245–54.
- [100] Gautam R, Bassi AS, Yanful EK. A review of biodegradation of synthetic plastic and foams. *Appl Biochem Biotechnol* 2007;14(1):85–108.
- [101] Kanaly RA, Harayama S. Biodegradation of high molecular-weight polycyclic aromatic hydrocarbons by bacteria. *J Bacteriol* 2000;8:2059–67.
- [102] Gautam R, Bassi AS, Yanful EK, Cullen E. Biodegradation of automotive waste polyester polyurethane foam using *Pseudomonas chlororaphis* ATCC55729. *Int Biodeterior Biodegrad* 2008;60:245–9.
- [103] Gracida J, Alba J, Cardoso J, Perez-Guevara F. Studies of biodegradation of binary blends of poly(3-hydroxybutyrate-co-3-hydroxyvalerate) (PHBV) with poly(2-hydroxyethylmetacrilate) (PHEMA). *Polym Degrad Stab* 2004;83:247–53.
- [104] Ammala A, Bateman S, Dean K, Petinakis E, Sangwan P, Wong S, et al. An overview of degradable and biodegradable polyolefins. *Progress Polym Sci* 2011;36:1015–49.
- [105] Ojeda TFM, Dalmolin E, Forte MMC, Jacques RJS, Bento FM, Camargo FAO. Abiotic and biotic degradation of oxo-biodegradable polyethylenes. *Polym Degrad Stab* 2009;94:965–70.
- [106] Koutny M, Sancelme M, Dabin C, Pichon N, Delort AM, Lamaire J. Acquired biodegradability of polyethylenes containing pro-oxidant additives. *Polym Degrad Stab* 2006;91:1495–503.
- [107] Miyazaki K, Shibata K, Nakatani H. Preparation of degradable polypropylene by an addition of poly (ethylene oxide) microcapsule containing TiO₂. Part III: Effect of

- existence of calcium phosphate on biodegradation behavior. *Polym Degrad Stab* 2011;96:1039–46.
- [108] da Luz JMR, Paes SA, Bazzolli DMS, Totola MR, Demuner AJ, Kasuya MCM. Abiotic and biotic degradation of oxobiodegradable plastic bags by *Pleurotus ostreatus*. *PLoS One* 2014;9(11):1–17.
- [109] Arnaud R, Dabin P, Lemaire J, Al-Malaika S, Chohan S, Coker M. Photooxidation and biodegradation of commercial photodegradable polyethylenes. *Polym Degrad Stab* 1994;46:211–24.
- [110] Jakubowicz I. Evaluation of degradation of biodegradable polyethylene (PE). *Polym Degrad Stab* 2003;80(1):39–43.
- [111] Sivan A, Szanto M, Pavlov V. Biofilm development of the polyethylene-degrading bacterium *Rhodococcus ruber*. *Appl Microbiol Biotechnol* 2006;72:346–52.
- [112] Konduri MKR, Anupam KS, Vivek JS, Kumar DBR, Narasu ML. Synergistic effect of chemical and photo treatment on the rate of biodegradation of high density polyethylene by indigenous fungal isolates. *Int J Biotechnol Biochem* 2010;6:157–74.
- [113] Singh V, Dubey M, Bhadauria S. Microbial degradation of polyethylene (low density) by *aspergillus fumigatus* and *penicillium* sp. *Asian J Exp Biol Sci* 2012;3(3) 498-550
- [114] Sowmya HV, Krishnappa R, Thippeswamy B. Low density polythene degrading fungi isolated from local dumpsite of Shivamogga district. *Int J Biomed Res* 2014;2 (2):39–43.
- [115] Lau AK, Cheuk WW, Lo KV. Degradation of greenhouse twines derived from natural fibers and biodegradable polymer during composting. *J Environ Manag* 2009;90: 668–71.
- [116] Fleming HC. Relevance of biofilms for the biodeterioration of surfaces of polymeric materials. *Polym Degrad Stab* 1998;59:309–15.
- [117] Albertsson AC, Karlsson S. Macromolecular architecture-nature as a model for degradable polymers. *J Macromol Sci A Pure Appl Chem* 1996;33(10):1571–9.
- [118] Shah AA, Hasan F, Hameed A, Ahmed S. Biological degradation of plastics: a comprehensive review. *Biotechnol Adv* 2008;26:246–65.
- [119] Chróst RJ. Microbial ectoenzymes in aquatic environments. In: Overbeck J, Chróst RJ, editors. *Aquatic Microbial Ecology: Biochemical and Molecular Approaches*. New York: Springer Verlag; 1990:1990
- [120] Chróst RJ. Environmental control of the synthesis and activity of aquatic microbial ectoenzymes. In: Chróst RJ, editor. *Microbial Enzymes in Aquatic Environments*. New York: Springer Verlag; 1991:Brock/Springer Series in Contemporary Bioscience
- [121] Huang J, Shetty AS, Wang M. Biodegradable plastics: a review. *Adv Polym Technol* 1990;10:23–30.
- [122] Arnaud R, Dabin P, Lemaire J, Al-Malaika S, Chohan S, Coker M. Photooxidation and biodegradation of commercial photodegradable polyethylenes. *Polym Degrad Stab* 1994;46(2):211–24.
- [123] Albertsson A-C, Barenstedt C, Karlsson S, Lindberg T. Degradation product pattern and morphology changes as means to differentiate abiotically and botically aged degradable polyethylene. *Polymer* 1995;36:3075–83.
- [124] Weiland M, Daro A, David C. Biodegradation of thermally oxidized polyethylene. *Polym Degrad Stab* 1995;48:275–89.
- [125] Wiles DM. In: Smith R, editor. *Biodegradable polymers for industrial applications*. Cambridge: Woodhead Publishing; 2005 [chapter 3]
- [126] Albertsson AC, Barenstedt C, Karlsson S. Abiotic degradation products from enhanced environmentally degradable polyethylene. *Acta Polym* 1994;45:97–103.

- [127] Bikiaris D, Aburto J, Alric I, Borredon E, Botev M, Betchev C. Mechanical properties and biodegradability of LDPE blends with fatty-acid esters of amylase and starch. *J Appl Polym Sci* 1999;7:1089–100.
- [128] Bonhomme S, Cuer A, Delort AM, Lemaire J, Sancelme M, Scott C. Environmental biodegradation of polyethylene. *Polym Degrad Stab* 2003;81:441–52.
- [129] Marcilla A, Gomez A, Reyes-Labarta JA, Giner A. *Polym Degrad Stab* 2003;80:233–40.
- [130] Whiteley KS, Heggs TG, Koch H, Mawer RL. Polyolefins. *Ullmann's encyclopedia of industrial chemistry*. New York: Elsevers, VCH; 1982. p. 487.
- [131] Billingham NC, Calved PD. *An introduction-degradation and stabilization of polyolefins*. London: Applied Science Publishers; 1983.
- [132] Hinsken H, Moss S, Pauquet JR, Zweifel H. Degradation of polyolefins during melt processing. *Polym Degrad Stab* 1991;34:279–93.
- [133] Canevarolo SV. Chain scission distribution function for polypropylene degradation during multiple extrusions. *Polym Degrad Stab* 2000;709:71–6.
- [134] Physical-chemical properties. International Standard Organization methods, http://www.iso.org/iso/iso_catalogue/catalogue_tc/catalogue_tc_browse.htm?commid=49318 [assessed 9.09.16].
- [135] The American Society for testing and materials (ASTM) methods. ASTM book of standards; 2005.08.03; Plastics (III): D5117.
- [136] Azevedo HS, Reis RL. Understanding the Enzymatic Degradation of Biodegradable Polymers and Strategies to Control Their Degradation Rate. In: Reis RL, Roman JS, editors. *Biodegradation system in tissue engineering and regenerative medicine*. Boca Raton, FL: CRS Press, Taylor & Francis Group; 2004 (Chapter 12)
- [137] Akpanudoh NS, Gobin K, Manos G. Catalytic degradation of plastic waste to liquid fuel over commercial cracking catalysts: effect of polymer to catalyst ratio/acidity content. *J Mol Catal A Chem* 2005;235:67–73.
- [138] Kpere-Daibo TS Plastic catalytic degradation study of the role of external catalytic surface, catalytic reusability and temperature effects. PhD thesis, Department of Chemical Engineering, University College London; 2009.
- [139] Manos G, Garforth A, Dwyer J. Catalytic degradation of high-density polyethylene on an ultrastable-Y zeolite. Nature of initial polymer reactions, pattern of formation of gas and liquid products, and temperature effects. *Ind Eng Chem Res* 2000;39:1203–8.
- [140] Manos G, Garforth A, Dwyer J. Catalytic degradation of high-density polyethylene over different zeolitic structures. *Ind Eng Chem Res* 2000;39:1198–202.
- [141] Sarker M, Rashid MM. Catalytic conversion of low density polyethylene and polyvinyl chloride mixture into fuel using Al_2O_3 . *Int J Mater Methods Technol* 2013;2:8–16.
- [142] García RA, Serrano DP, Otero D. Catalytic cracking of HDPE over hybrid zeolitic-mesoporous materials. *J Anal Appl Pyrol* 2005;74:379–86.
- [143] Lee YJ, Kim JH, Kim SH, Hong SB, Seo G. Nanocrystalline beta zeolite: an efficient solid acid catalyst for the liquid-phase degradation of high-density polyethylene. *Appl Catal B Environ* 2008;83:160–7.
- [144] Marcilla A, Gomez A, Menargues S, Garcia-Martinez J, Cazorla-Amoros D. Catalytic cracking of ethylenevinyl acetate copolymers: comparison of different zeolites. *J Anal Appl Pyrol* 2003;495–506.
- [145] Demirbas A. Biorefineries: current activities and future developments. *Energy Convers Manag* 2009;50:2782–801.

- [146] Ivanova SR, Gumerova EF, Minsker KS, Zaikov GE, Berlin AA. Selective catalytic degradation of polyolefins. *Prog Polym Sci* 1990;15:193–215.
- [147] Ivanova SR, Gumerova EF, Al Berlin AL, Minsker KS, Zaikov GE. Catalytic degradation of polyolefins—a promising method for the regeneration of monomers. *Russ Chem Rev* 1991;60(2):430–47.
- [148] Sekine Y, Fujimoto K. Catalytic degradation of PP with an Fe/activated carbon catalyst. *J Mater Cycles Waste Manag* 2003;5:107–12.
- [149] Pandaa AK, Singh RK. Optimization of process parameters by Taguchi method: catalytic degradation of polypropylene to liquid fuel. *Int J Multidisc Curr Res* 2013;1:50–8.
- [150] Roozbehani B, Sakaki SA, Shishesaz M, Abdollahkhani N, Hamedifar S. Taguchi method approach on catalytic degradation of polyethylene and polypropylene into gasoline. *Clean Technol Environ Policy* 2015;17:1873–82.
- [151] Batmani M, Shishesaz MR, Roozbehani B. Investigation of catalytic degradation of polyolefins in presence of polyvinylchloride via design of experiments. *Int J Sci Emerg Technol* 2013;3:256–63.
- [152] Ide S, Nanbu N, Kuroki T, Ikemura T. Catalytic degradation of polystyrene in the presence of active charcoal. *J Anal Appl Pyrol* 1984;6:69–80.
- [153] Lin YH, Yang MH. Catalytic conversion of commingled polymer waste into chemicals and fuels over spent FCC commercial catalyst in a fluidised-bed reactor. *Appl Catal B Environ* 2007;69:145–53.
- [154] Durmus A, Koc SN, Pozan GS, Kasgoz A. Thermal-catalytic degradation kinetics of polypropylene over BEA, ZSM-5 and MOR zeolites. *Appl Catal B Environ* 2005;61:316–22.
- [155] Li K, Lee WS, Yuan G, Lei J, Lin S, Weerachanchai P, et al. Investigation into the catalytic activity of microporous and mesoporous catalysts in the pyrolysis of waste polyethylene and polypropylene mixture. *Energies* 2016;9:431–46.
- [156] Manos G, Yusof IY, Papayannakos N, Gangas NH. Catalytic cracking of polyethylene over clay catalysts. Comparison with an ultra-stable Y zeolite. *Ind Eng Chem Res* 2001;40:2220–5.
- [157] Seymour Raymond B. Additives for polymers. *Introduction to polymer chemistry*. New York: McGraw-Hill Book Company; 1971. p. 268–71 [chapter 11]
- [158] Mori H, Endo M, Terano M. Study of activity enhancement by hydrogen in propylene polymerization using stopped-flow and conventional methods. *J Mol Catal A* 1999;145:211–20.
- [159] Seifali Abbas-Abadi M, Nekoomanesh Haghighi M, Bahri Laleh N, Akbari Z, Tavasoli MR, Mirjahanmardi SH. Polyolefin production using an improved catalyst system. *US2011/ 0152483*; 2011.
- [160] Paik P, Kar KK. Kinetics of thermal degradation and estimation of lifetime for polypropylene particles: effects of particle size. *Polym Degrad Stab* 2008; 93–24–35.
- [161] Paik P, Kar KK. Thermal degradation kinetics and estimation of lifetime of polyethylene particles: effects of particle size. *Mater Chem Phys* 2009;113:953–61.
- [162] Abbas-Abadi MS, Haghighi MN, Yeganeh H, Bozorgi B. The effect of melt flow index, melt flow rate, and particle size on the thermal degradation of commercial high density polyethylene powder. *J Therm Anal Calomet* 2013;114:1333–9.
- [163] Shibryaeva L. Thermal oxidation of polypropylene and modified polypropylene – structure effects. In: Dogan F, editor. *Polypropylene*. Rijeka, Croatia-European Union: InTech Publisher; 2012 (Chapter 5)

- [164] Tokiwa Y, Calabia BP, Ugwu CU, Aiba S. Biodegradability of plastics. *Int J Mol Sci* 2009;10:3722–42.
- [165] Buddy DR, Hoffman AS, Schoen FJ, Lemons JE. *Biomaterials science: an introduction to materials in medicine*. 3rd ed. USA: Academic Press; 2013. p. 190.
- [166] Haines JR, Alexander M. Microbial degradation of high-molecular-weight alkanes. *Appl Microbiol* 1974;28:1084–5.
- [167] Gewert B, Plassmann MM, MacLeod M. Pathways for degradation of plastic polymers floating in the marine environment: a critical review. *Environmental Sciences Processes and Impact*; 2015.
- [168] Summers JW, Rabinovitch EB. *Weathering of plastics*. Amsterdam: Elsevier; 1999. p. 61–8.
- [169] Jakubowicz I. Evaluation of degradability of biodegradable polyethylene (PE). *Polym Degrad Stab* 2003;80:39–43.
- [170] Chanda M. *Plastics technology handbook*. Boca Raton, FL: CRC Press/Taylor & Francis Group; 2007.
- [171] Shah AA, Hasan F, Hameed A, Ahmed S. Biological degradation of plastics: a comprehensive review. *Biotechnol Adv* 2008;26:246–65.
- [172] Franssen NMG, Reeka JHN, Bruin BD. Synthesis of functional ‘polyolefins’: state of the art and remaining challenges: review article. *Chem Soc Rev* 2013;42:5809–32.
- [173] Franssen NMG, Reeka JHN, Bruin BD. A different routh of functional polyolefins: olefins-carbene copolymerization. *Dalton Trans* 2013;42:9058–68.
- [174] Patil AO. Functional polyolefins. *Chem Innov* 2000;30:19–24.
- [175] Nakamura A, Ito S, Nozaki K. Coordination – insertion copolymerization of fundamental polar monomers. *Chem Rev* 2009;109:5215–44.
- [176] Padwa AR. Functionally substituted poly(0-olefins). *Progr Polym Sci* 1989;14: 811–13.
- [177] Boffa LS, Novak BM. Copolymerization of polar monomers with olefins. . .transition-metal complexes. *Chem Rev* 2000;100:1479–93.
- [178] Dopico-Garciãa MS, Lopez-Vilarino JM, Gonzaã lez-Rodriãguez MV. Antioxidant content of and migration from commercial polyethylene, polypropylene, and polyvinyl chloride packages. *J Agric Food Chem* 2007;55:3225–31.
- [179] Brock T, Groteklaes M, Mischke P. Organic coloured pigments. *Eur Coat J* 2002;6:64–6.
- [180] Tobias JW, Taylor LJ. Photodegradable polymer compositions. Pat US4360606, assigned to Owens-Illinois Inc; 1982.
- [181] Wijdekop M, Arnold JC, Evans M, John V, Lloyd A. Monitoring with reflectance spectroscopy the color change of PVC plastisol coated strip steel due to weathering. *Mater Sci Technol* 2005;21:791–7.
- [182] Iannuzzi G, Mattsson B, Rigdahl M. Color changes due to thermal ageing and artificial weathering of pigmented and textured ABS. *Polym Eng Sci* 2013;53: 1687–95.
- [183] Drobny JG. *Radiation technology for polymers*. 2nd ed. Florida, USA: CRC Press; 2003.
- [184] Barlow A, Biggs J, Maringer M. Radiation processing of polyolefins and compounds. *Radiat Phys Chem* 1977;9 685-669
- [185] International atomic energy agency. *Controlling of degradation effects in radiation processing of polymers*, Vienna, Austria; 2009, p. 1–5.
- [186] Romano U, Garbassi F. The environmental issue. A challenge for new generation polyolefins. *Pure Appl Chem* 2000;72(7):1383–8.

-
- [187] Reingruber E, Buchberger W. Analysis of polyolefin stabilizers and their degradation products: a review. *J Sep Sci* 2010;33:3463–75.
 - [188] Caruso MM, Davis DA, Shen Q, Odom SA, Sottos NR, White SR, et al. Mechanically-induced chemical changes in polymeric materials. *Chem Rev* 2009;109: 5755–98.
 - [189] Lundbäck M. Long-term performance of polyolefins in different environments including chlorinated water: antioxidants consumption and migration, and polymer degradation. Stockholm: KTH Fibre and Polymer Technology; 2005.

This page intentionally left blank