



1           The FN test (AASHTO 2007) is very important to pavement designers as FN of a mixture could  
2  
3 be used to aid in the characterization and selection of the best available materials for producing AC  
4  
5 mixtures that are resistant to rutting. FN has shown good correlation with field rutting of AC mixtures for  
6  
7 different traffic levels (Witczak 2007). FN has also been used to rank asphalt mixtures in terms of rutting  
8  
9 susceptibility in both laboratory tests and field performance (Mohammad et al. 2006).  
10

11           Rutting is believed to be affected by several AC properties in addition to temperature and loading  
12  
13 effects. To minimize the potential for rutting certain key factors affecting rutting need to be identified so  
14  
15 the design process could be optimized by modifying these important factors.  
16  
17

18           Kaloush (2001) showed that rutting is affected by mixture volumetric properties (including  
19  
20 effective asphalt content and air voids), binder viscosity, and testing temperature. Kvasnak et al. (2007)  
21  
22 identified several asphalt mixture properties that affect rutting (measured by FN) to include binder grade,  
23  
24 binder viscosity, asphalt content, testing temperature, nominal maximum aggregate size, voids in the  
25  
26 mineral aggregate, percentage passing sieves (No.4, No.16, No.200), and number of gyrations.  
27  
28

29           Rodezno et al. (2010) identified 12 parameters that affect rutting of asphalt mixtures in the  
30  
31 laboratory to include maximum shear stress, normal stress, testing temperature, binder viscosity,  
32  
33 aggregate gradation (percent retained on ¾-in, 3/8-in and No. 4 sieves), air voids, binder content,  
34  
35 effective binder content, voids in the mineral aggregate, and voids filled with asphalt. Models for  
36  
37 predicting FN were developed in these studies based on the aforementioned list of factors.  
38  
39

40           Another parameter that has been suggested as affecting rutting is dynamic modulus. However  
41  
42 there are no consensus regarding the effect of dynamic modulus on rutting (Birgisson and Roque 2004;  
43  
44 Zhou and Scullion 2007; Witczak et al. 2002; and Pellinen and Witczak 2002). Possible reasons for the  
45  
46 observed lack of consensus might be because reported testing conditions at which dynamic modulus for  
47  
48 rutting evaluation are selected varies among various investigators. Suggested ranges of testing frequencies  
49  
50 for evaluating dynamic modulus for rutting varies widely and was reported to range from 0.02 to 20 Hz  
51  
52 by Ekingen (2004). Shenoy and Romero (2002) suggested an approach to select a normalizing frequency  
53  
54 parameter corresponding to a reference dynamic modulus of 4 MPa to evaluate rutting in laboratory test  
55  
56 specimens.  
57  
58  
59  
60  
61  
62  
63  
64  
65

1           Witczak et al. (2002) and Pellinen and Witczak (2002) reported good correlation between  
2 dynamic modulus and rutting. Dynamic modulus obtained from unconfined compression tests at 54 °C  
3 and a t a frequency of 5 Hz was considered a good indicator of rutting based on the repeated load FN test.  
4  
5 Other studies have reported little to no correlation between dynamic modulus and rutting measured with  
6 the asphalt pavement analyzer (APA). Ullidtz (1987) found no good correlation between APA rut depth  
7 and dynamic modulus measured at 40°C and 1 Hz frequency as did Ekingen (2004) who compared  
8 dynamic modulus obtained at 1 Hz and 4 Hz and APA results. Mohammad et al. (2006) compared  
9 dynamic modulus measured at 54°C and 5 Hz loading frequency with rutting and reported that dynamic  
10 modulus could not differentiate between rutting susceptibility of the mixtures tested.  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20

21           In most of the aforementioned studies, the effect of gradation was not explicitly evaluated in  
22 conjunction with dynamic modulus which may help explain some of discrepancies observed in the  
23 reported relationship between dynamic modulus and rutting. Thus additional studies involving the  
24 evaluation of factors influencing rutting is still needed. Results of such studies may also be important in  
25 other areas as discussed next.  
26  
27  
28  
29  
30

31           The enormous list of factors identified as affecting rutting illustrates the difficulty one may  
32 encounter when attempting to optimize a given asphalt mixture for resistance against rutting. A close  
33 inspection of the factors affecting rutting identified in previous studies suggests these factors could be  
34 classified into two groups. First is the binder property controlling the viscoelastic and viscoplastic  
35 behavior, and second are aggregate properties including gradation that controls the elastic (and possibly  
36 plastic) behavior of the mix. Also because of the viscoelastic nature of asphalt mixture response to load,  
37 selection of a suitable dynamic modulus value (at a given testing temperature and frequency) for  
38 evaluating rutting remains a challenge to be solved. It is anticipated in this study that dynamic modulus  
39 and certain key gradation parameters could be used as surrogates for the numerous factors identified in  
40 previous studies to affect rutting of asphalt mixtures. By using only a few relevant material properties, it  
41 is hoped that the approach proposed in this study could lead to a more efficient and rational means of  
42 evaluating rutting during a routine mix design process. Prediction models utilizing the combined effects  
43 of dynamic modulus and certain gradation parameters will be developed to estimate FN of AC mixtures  
44 in the laboratory.  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

## **Purpose and Scope**

Numerous factors have been identified in past studies to account for the rutting behavior of asphalt mixtures. Because of the rather large number of identified factors, applying this knowledge to routine mix design could be quite difficult since a designer will have to control up to 15 or more different factors in order to produce a rut-resistance mix. If the number of factors affecting rutting could be narrowed down to a few important ones, a routine mix design process could be optimized. It is therefore important that a relationship between FN and key gradation and stiffness parameters which are known to affect rutting be established so that the prediction of rutting could be improved.

The main objective of this paper was to investigate rutting resistance of AC mixtures as a function of dynamic modulus and gradation and develop a mathematical relationship between them. The scope of the study was limited to 16 AC mixes including: eight dense-graded surface mixes of nominal maximum aggregate size (NMAS) of 9.5 mm and 12.5 mm; five dense-graded base mixes with an NMAS of 25.0 mm; and three stone asphalt matrix with an NMAS of 12.5 mm. All the tested specimens were produced according to Virginia specifications using plant-mixed laboratory-compacted asphalt mixtures. Predictive models relating FN to dynamic modulus and gradation were developed based on the 16 mixtures considered. The strong dependence of FN on dynamic modulus and gradation observed in the 16 mixtures was verified using published data on 12 different mixtures.

## **Methodology**

Sixteen AC mixtures consisting of 13 dense-graded mixtures and three stone matrix asphalt (SMA) were tested using the dynamic modulus and FN tests. The mixtures were selected to be as representative as possible of the commonly used AC mixtures in Virginia. The mixtures contained RAP amounts ranging from 0 to 25% by weight. Three different binder types were used (PG 64-22 for mixes with A designation; PG 70-22 for mixes with D designation; and PG 76-22 for mixes with E designation and containing polymer modified-asphalt). Mixes A, D, and E are designed for pavements carrying up to 3 million ESALs, 3-10 million ESAL and > 10 million ESAL, respectively (VDOT, 2006).

## **Materials Sampling and Collection**

1 As stated above, samples of the most commonly used mixture types were collected from around  
2 the Commonwealth of Virginia. Majority of the mixes sampled were surface mix (SM) followed by base  
3 mix (BM), and SMA mixes.  
4  
5

6  
7  
8 Details of the mixtures sampled including the asphalt binder grade, amount of RAP, and mixture  
9 source are shown in Table 1. All samples were plant-mixed and were sampled loose at the project site and  
10 sent to laboratory for further processing and testing. Samples were stored in a temperature controlled  
11 environment in sealed containers before testing. Additional details about the mixtures including key  
12 gradation parameters and mixture volumetrics are shown in Table 2 and Table 3, respectively. The loose  
13 mixtures were processed into compacted specimens for mechanical testing as detailed in subsequent  
14 sections under laboratory testing. The main mechanical laboratory tests conducted included dynamic  
15 modulus and flow tests using an asphalt material performance tester (AMPT).  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25

### 26 **Laboratory Compaction Methods**

27  
28

29 A Superpave gyratory compactor was used to fabricate specimens used for the dynamic modulus and the  
30 FN tests. The mixtures for the various tests were compacted to a target air void level of  $7\pm 0.5\%$ . This was  
31 accomplished by determining the compaction height needed to obtain the required target air void content.  
32  
33 It was determined that the base mixes (NMA 25.0 mm) required to be compacted to a height of 200 mm  
34 while the SM and SMA mixes (9.5 mm and 12.5 mm NMA) required to be compacted to height of 175  
35 mm. Next a coring rig was used to obtain the required 150 mm tall by 100 mm diameter specimen from  
36 the gyratory compacted specimen for testing. The same specimens were used for both the dynamic  
37 modulus and the FN test since the former is considered a non-destructive test.  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47

### 48 **Dynamic Modulus Tests**

49  
50

51 Dynamic modulus tests were performed with an IPC AMPT according to AASHTO TP62. Tests were  
52 performed on 100 mm diameter by 150 mm tall specimens in the uniaxial compressive mode. Tests were  
53 conducted at 5 temperatures ranging from  $-10^{\circ}\text{C}$  to  $54^{\circ}\text{C}$  and six loading frequencies ranging from 0.1 Hz  
54 to 25 Hz. To insure against damage to the test samples, the tests were conducted starting from the coldest  
55 to the warmest temperature. In addition, at each testing temperature, the tests were performed starting  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

1 from the highest to the lowest frequency. Load levels were selected in such a way that at each  
2  
3 temperature-frequency combination, applied strain was in the range of 75-125 micro-strain. This was  
4  
5 done to ensure that testing was conducted in the linear viscoelastic range of the AC mixes, a necessary  
6  
7 requirement for a valid dynamic modulus test. Stress versus strain values were captured continuously and  
8  
9 used to calculate dynamic modulus values. Dynamic modulus was computed automatically by the test  
10  
11 software. Results at each temperature-frequency combination for each mixture type are reported for three  
12  
13 replicate specimens.  
14

### 15 **FN tests**

16  
17  
18  
19  
20 The FN tests were performed on 100 mm diameter by 150 mm tall specimens using NCHRP Project 9-19  
21  
22 procedures. An IPC UPM AMPT with 25-kN load cell was used. Tests were performed on specimens  
23  
24 that were previously used for the dynamic modulus tests. The FN tests involved subjecting a specimen of  
25  
26 asphalt concrete specimens to a repeated haversine axial compressive load pulse of 0.1 sec every 1.0 sec.  
27  
28 The test is conducted at a temperature that represents the expected pavement temperature at the site and  
29  
30 layer of the pavement section. In this study the FN test was conducted at 54°C which represents the 50%  
31  
32 reliability maximum high pavement temperature as determined using the LTPPBind software (Pavement  
33  
34 Systems 2005) for locations in the southeastern portion of the US. The FN tests were all performed in the  
35  
36 unconfined mode using a deviatoric stress of 206 kPa. The tests were continued to 10,000 cycles or a  
37  
38 permanent strain of five percent whichever came first.  
39  
40  
41  
42  
43

### 44 **Results and Discussion**

45  
46  
47 In this section, the effects of dynamic modulus and gradation on rutting are evaluated. First dynamic  
48  
49 modulus data at five temperatures and six testing frequencies for each of the 16 mixtures are presented. A  
50  
51 mastercurve consisting of dynamic modulus values was developed for each mixture and plotted to  
52  
53 illustrate the temperature and frequency dependency of the asphalt mixtures and how it may complicate  
54  
55 the choice of a dynamic modulus value to use for evaluating rutting. Next the results of the FN tests are  
56  
57 presented with an illustration of how the FN is determined numerically using standard AASHTO TP62  
58  
59 procedures. Finally predictive equations relating FN to dynamic modulus and gradation parameters are  
60  
61  
62  
63  
64  
65

1 presented and discussed. The sections concludes with an attempt to verify the models developed for  
2  
3 predicting FN as a function of dynamic modulus and gradation, using 12 mixtures from previously  
4  
5 published research.  
6  
7

## 8 **Dynamic Modulus Tests**

9

10  
11 Results for the sixteen different asphalt mixtures tested in uniaxial compression mode at five temperatures  
12 (-10°C, 4°C, 20°C, 38°C, and 54°C) and six frequencies (25 Hz, 10 Hz, 5 Hz, 1 Hz, 0.5 Hz, and 0.1 Hz)  
13  
14 are shown in Figures 1 through 3. The results are grouped according to the type of the mixture (SM, BM,  
15  
16 SMA) as defined above.  
17  
18

19  
20 The mean dynamic modulus data for each mixture type show a decreasing trend with an increase  
21  
22 in temperature. The trend is reversed when considering frequency as dynamic modulus values increased  
23  
24 with increasing frequency. The change in dynamic modulus with temperature is however not consistent  
25  
26 among the various mixtures. For example in Figure 1 specimen 08-1045D is ranked the highest in terms  
27  
28 of stiffness among the surface mixes at each testing temperature. This is not the case for the SMAs as  
29  
30 specimen 08-1025E which was ranked the stiffest at the coldest temperature ended as the softest ranked  
31  
32 mixtures at the higher testing temperatures which might be due to polymer modification as all mixtures  
33  
34 with the “E” designation are required to contain polymer-modified asphalt binder. This is an example of  
35  
36 difficulty one may encounter if the evaluation of rutting is based solely on dynamic modulus  
37  
38 measurements.  
39  
40  
41  
42

43 For all the mixtures, the amount of RAP appears to have a significant effect on dynamic modulus  
44  
45 values in both expected and unexpected ways. The clearest example of the positive effect of RAP on  
46  
47 rutting can be seen in the surface mixes where the stiffest surface mix at the highest temperature for the  
48  
49 surface mixes was 08-1045D which also contained the highest (20%) RAP amount for this class of  
50  
51 mixture. The trend is confounded in the BM and SMA mixes probably due to the effect of the different  
52  
53 binder grades (polymer-modified) used in these mixtures. The foregoing analysis which shows different  
54  
55 temperature susceptibility in the various mixes suggest the need to combine the effect of temperature and  
56  
57 loading rate in a more formal way. The combined effects of temperature and frequency on dynamic  
58  
59 modulus was characterized by constructing master curves using the concept of the time-temperature  
60  
61  
62  
63  
64  
65

1 superposition principle. The time-temperature superposition principle simply implies test data obtained at  
2 low temperatures is equivalent to data obtained at high frequencies and vice versa.  
3  
4

5 The data at the five testing temperatures and six testing frequencies for each mix were combined  
6 to construct dynamic modulus master curves. A sigmoidal model (Equation 1) was used to describe the  
7 mastercurves at a reference temperature of 20°C. A non-linear analysis was performed using a  
8 commercially available optimization routine (Microsoft Excel Solver) to obtain the model parameters of  
9 the master curve by minimizing the sum of squares of error between the predicted and the measured  
10 dynamic modulus values. Dynamic modulus mastercurves for the mixtures are shown in Figures 1  
11 through 3 plotted on a semi-log scale.  
12  
13  
14  
15  
16  
17  
18  
19  
20

21 There are several reasons for constructing dynamic modulus master curves for asphalt mixtures in  
22 this study. First a master curve of dynamic modulus provides the ability to predict dynamic modulus at  
23 temperatures and /or frequencies which will be difficult or impossible to determine in the laboratory due  
24 to equipment limitations or time constraints. Another advantage of a master curve relates to the ability to  
25 model pavements across all possible pavement climatic and loading conditions. A master curve is also  
26 useful for ranking mixture performance. For instance in Figures 1 through 3, mixtures with higher  
27 dynamic modulus at lower (reduced) frequencies (equivalent to high test temperatures) would be expected  
28 to exhibit better rutting potential than mixtures with lower dynamic modulus values. Similarly mixtures  
29 having low stiffness at high reduced frequencies (equivalent to low temperatures) are expected to be more  
30 resistant to low temperature cracking. As would be shown below, mixtures such as 09-1049A which  
31 plotted lowest at low reduced frequency also showed low FN values. However it should be noted this  
32 observation is too simplistic as some of the plots cross each other and therefore the magnitude of dynamic  
33 modulus values alone may not be enough for ranking rutting performance. This was a major motivation of  
34 this study.  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51

52 The type of aggregate structure (dense-graded vs. gap-graded) appears to be related to the level of  
53 stiffness of the mix. Gap-graded SMA mixes tested in this study appeared to be softer than the dense-  
54 graded mixes as the three most softest mixes were all SMA mixes. It should be noted that all the SMA  
55 mixes were either “D” or “E” suggesting mixes which likely used polymer-modified asphalt binders. It is  
56 also interesting to note the effect of RAP on SMA stiffness; of the three SMA mixes, the stiffest (08-  
57  
58  
59  
60  
61  
62  
63  
64  
65



1 1025E) contained 10% RAP while the other two had no RAP. Another observation was that the SMA  
2  
3 mixes appear to be significantly softer at low temperatures but of comparable stiffness to most of the  
4  
5 dense-graded mixes at high test temperatures.  
6  
7  
8  
9

$$\log(E^*) = \delta + \frac{\alpha}{1 + e^{(\beta + \gamma(\log f_r))}} \quad (1)$$

10  
11  
12  
13  
14 where

15  
16  $f_r$  = loading frequency at the reference temperature,

17  
18  $\delta$  = minimum value of dynamic modulus,

19  
20  $\delta + \alpha$  = maximum value of dynamic modulus, and

21  
22  $\beta, \gamma$  = parameter describing the shape of the sigmoidal function.  
23  
24  
25

## 26 **FN Tests Results**

27

28  
29 Results of flow number tests performed at 54°C are presented in this section. During the test,  
30  
31 axial strain and cumulative number of load cycles were monitored continuously by the FN test software.  
32  
33 From the results, plots of rate of change of strain with number of cycles could be constructed. Figure 4 is  
34  
35 a typical plot of accumulated strain versus number of loading cycles obtained for the mixtures.  
36  
37  
38

39  
40 Three stages are typically identified from the plot of permanent strain versus loading cycle. These  
41  
42 three stages have been classified as primary, secondary and tertiary (Witczak and Sullivan 2002). The  
43  
44 primary flow is characterized by a decrease in the strain rate with time. The secondary flow phase is  
45  
46 characterized by a relatively constant strain rate. The tertiary flow follows the secondary phase and begins  
47  
48 when the strain rate begins to increase. At the tertiary stage, the specimen undergoes significant  
49  
50 deformation with individual aggregates within the aggregate skeleton moving past each other (Kanitpong  
51  
52 and Bahia 2005 and Little et al. 1993). FN is the cycle number at the initiation of tertiary flow (Witczak  
53  
54 2007).  
55

56  
57 The FN is determined mathematically as the cycle number at which the strain rate is a minimum.  
58  
59 For this study, the Francken model (Biligiri et al. 2007) as implemented in the AMPT software and shown  
60  
61  
62  
63  
64  
65

1 in Equations 2 and 3 were used estimate the FN. FN is defined as the point where Equation 3 changes  
2  
3 from negative to positive.  
4

5 Table 4 shows summarized results of flow number tests results obtained for each mix. The results  
6  
7 represent average FN for three replicate specimens for each mixture type. Also shown in Table 4 are the  
8  
9 variability in test results represented by the coefficient of variation (COV) which ranged from 1.9 to 38.0  
10  
11 percent. This level of variability are within previously reported ranges by investigators. For the mixtures  
12  
13 considered, FN ranged from about 600 to about 8400. In general the stiffer mixes with high dynamic  
14  
15 modulus values appear to exhibit higher FN which is to be expected.  
16  
17

18 The dense-graded mixes (BM and SM) exhibited relatively high rutting resistance compared with  
19  
20 the SMA as evidenced by the higher FN values. However most of SMA mixtures sustained almost double  
21  
22 the accumulated strain at FN compared to the dense-graded mixes. The average FN values for the dense-  
23  
24 graded mixtures were 5211 and 1379 for mixtures containing PG 70-22 (D mixes) and PG 64-22 (A  
25  
26 mixes) binders, respectively. It must also be noted that all D mixes contained between 10 to 20 percent  
27  
28 RAP while the RAP amount for the A mixes ranged from 0 to 25%. The effect of RAP in these mixtures  
29  
30 appear to be an increase in FN. For the dense-graded mixtures there appears to be no statistically  
31  
32 significant difference between SM and BM mixes (p-value = 0.357). The major distinction between the  
33  
34 SM and BM is the nominal maximum aggregate size (NMAS). The fact that FN is not significantly  
35  
36 different irrespective of NMAS suggest, the parameter may not be an important factor in rutting for the  
37  
38 mixtures considered in this study. In other words, NMAS is may not be a good indicator of rutting  
39  
40 resistance of AC considered in this study.  
41  
42  
43  
44

$$\varepsilon_p(N) = AN^B + C(e^{DN} - 1) \quad (2)$$

$$\frac{\partial^2 \varepsilon_p}{\partial N^2} = A * B * (B - 1) * N^{B-2} + C * D^2 * e^{DN} \quad (3)$$

45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56 where:

57  $\varepsilon_p$  = Permanent strain from the flow number test,  
58  
59  
60  
61  
62  
63  
64  
65

1 N = number of loading cycles,

2  
3 A, B, C, and D = regression constants, and

4  
5  
6  $\frac{\partial^2 \varepsilon_p}{\partial N^2}$  = second derivative of permanent strain versus N.  
7  
8

9  
10 **Rutting as a Function of Dynamic Modulus and Gradation**  
11

12  
13 It is a generally accepted fact that rutting of asphalt mixtures is affected by both stiffness and gradation.  
14  
15 However the effects of stiffness as measured by dynamic modulus and gradation are not commonly  
16  
17 evaluated together. The coupled effects of dynamic modulus and gradation has not received much  
18  
19 attention in the published research. In order to determine if a relationship exists between dynamic modulus  
20  
21 and gradation on the one hand and rutting (measured by FN), an analysis was conducted on the results of  
22  
23 the 16 different asphalt mixtures that were evaluated in this study.  
24  
25

26  
27 Multiple linear regression analyses were conducted to determine promising models for predicting  
28  
29 FN as a function of dynamic modulus and gradations for each mix type using a commercially available  
30  
31 statistical analysis software (SAS, 2007). A significance level of 0.05 was assumed for all the statistical  
32  
33 analyses. As mentioned previously, dynamic modulus testing was conducted at five testing temperatures  
34  
35 and six loading frequencies. The challenge was to find which temperature-frequency combination yielded  
36  
37 dynamic modulus values most correlated with rutting. In addition, gradation parameters (percent passing  
38  
39 various sieves) as well as key volumetric properties (percent air voids, effective asphalt content, voids in  
40  
41 mineral aggregates, etc) were used for developing the models. To accomplish this objective, several  
42  
43 statistical analyses involving dynamic modulus values at five loading frequencies and testing temperature  
44  
45 of 38°C was conducted. The testing temperature of 38°C was chosen because it is close to the effective  
46  
47 temperature for permanent deformation (El-Basyouny and Jeong, 2009). Criteria for selecting the most  
48  
49 promising model was based on several key statistics including R<sup>2</sup>, Mallows' Cp, and MSE. The model  
50  
51 with the lowest Cp value approximately equal to the number of model parameters for all possible  
52  
53 combinations of model variables was considered the most adequate. The selected model had a high R<sup>2</sup>  
54  
55 (=0.91), the lowest Cp (=9.8) and the lowest MSE. The p-value for the model was less than 0.0001 as  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

1 indicated in Table 5. The Cp value of 9.8 was less than the number of variables in the model suggesting a  
2 possible high predictive ability.  
3

4  
5 The result of the statistical analyses showing predicted model parameters and key statistics for the  
6 most promising model is summarized in Table 5. The analyses showed (as indicated by p-values less than  
7 0.05) that dynamic modulus values obtained at 38°C and loading frequencies 10.0, 1.0, and 0.1 Hz  
8 showed some potential as predictive parameters for FN. Also key gradation parameters (percent passing  
9 various sieve sizes) showed significant effect on FN. Mixture volumetrics including air void and voids in  
10 mineral aggregate (VMA) were also found to be significant factors. These gradation parameters as well as  
11 the dynamic modulus obtained at 38°C, were selected to develop model parameters for the functional  
12 form shown in Equation 4.  
13  
14  
15  
16  
17  
18  
19  
20  
21

22  
23 Equation 4 could be considered a first-order multiple regression model. For such models one  
24 could attach some meaning to the various  $\beta$ -parameters. The parameter  $\beta_0$  is the y-intercept and represents  
25 the expected value of FN when dynamic modulus and the gradation parameters are all zero. Obviously  $\beta_0$   
26 could only be used for prediction purposes in this study and not for interpretation since neither dynamic  
27 modulus nor the gradation parameters in Equation 4 could be zero for AC mixtures. The remaining  $\beta$   
28 parameters ( $\beta_1$  through  $\beta_{10}$ ) are the so called partial slopes. Each  $\beta_i$  ( $i=1$  to 10) represents a unit change in  
29 FN for a unit increase in one of the variables when all other variables are held constant. Thus it could be  
30 hypothesized that if the effects of these parameters are additive, FN could be influenced (increase or  
31 decrease) by varying dynamic modulus and gradation parameters. Additional studies are required to  
32 verify this.  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45

46 Figure 5 compares the measured FN and the predicted FN using Equation 4 for the model  
47 parameters detailed on Table 5. It can be seen from Figure 5 that the models predicted FN of the mixtures  
48 quite well for the mixtures considered in this study. The results show that FN could be considered as a  
49 function of dynamic modulus and certain gradation parameters with some level of certainty ( $\alpha = 0.05$ ) for  
50 the mixtures considered in this study. The functional form of the model (Equation 4) is potentially  
51 important as it could allow FN to be computed knowing only dynamic modulus and readily available  
52 gradation parameters. Thus during the mix design process, several different mixtures could be evaluated  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

1 for rutting without the need to perform the time-consuming FN tests. FN tests could then be limited to the  
2  
3 most promising mix design. The equation may also be quite useful during mix design process as the  
4  
5 parameters such as dynamic modulus and gradation could be quantitatively varied to produce rut-resistant  
6  
7 mixes. The models could also be used as a basis for using dynamic modulus and gradation as a quality  
8  
9 control / quality assurance (QC/QA) tool.  
10

$$11 \quad FN = \beta_0 + \sum_{i=1}^{10} \beta_i \chi_i \quad (4)$$

12 where:

13 FN = flow number at 54.4°C,

14  $\chi_1$  = percent air voids,

15  $\chi_2$  = percent passing 19.0 mm sieve,

16  $\chi_3$  = percent passing 12.5 mm sieve,

17  $\chi_4$  = percent passing 9.5 mm sieve,

18  $\chi_5$  = percent passing 4.75 mm sieve,

19  $\chi_6$  = percent passing 2.36 mm sieve,

20  $\chi_7$  = dynamic modulus at 38°C and 10 Hz in MPa,

21  $\chi_8$  = dynamic modulus at 38°C and 1 Hz in MPa,

22  $\chi_9$  = dynamic modulus at 38°C and 0.1 Hz in MPa,

23  $\chi_{10}$  = percent voids in mineral aggregate (VMA), and

24  $\beta_i$  = regression parameters.

## 25 **Verification of FN as Function of Dynamic Modulus and Gradation**

26 The preceding results and discussions suggest some evidence of FN as a function of dynamic modulus  
27 and gradation for 16 AC mixtures exists. The veracity of the relationship relating FN to dynamic modulus  
28 and gradation obtained in the current study was investigated using data from two previously published  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

1 research studies (Cooper 2008, Mohammad et al. 2006) on 12 mixtures from Louisiana. These data were  
2  
3 chosen because the testing conditions used in both studies are comparable to that used in the current  
4  
5 study. Specifically the FN was obtained at 54°C using a deviator stress of 207 kPa under unconfined  
6  
7 conditions in both of the aforementioned studies. Dynamic modulus data at 38°C as well as mixture  
8  
9 volumetric properties were also available from the above-mentioned references. Six AC mixtures of a  
10  
11 similar binder grade but different gradations were selected from Mohammad et al. (2006) while the six  
12  
13 mixtures reported on by Cooper (2008) containing crumb rubber-modified asphalt form the remainder.  
14  
15 Pertinent details of the mix properties used are shown in Table 6.  
16  
17

18  
19 Figure 6 shows the comparison of measured FN (from Mohammad et al. 2006 and Cooper 2008) and  
20  
21 predicted FN (using the approach developed in current study). The observed correlation between  
22  
23 predicted and measured FN was quite good ( $R^2=0.84$ ) as shown in Figure 6. Given the rather high  
24  
25 variability reported by Mohammad et al. and the fact that rubber modified binders were used by Cooper),  
26  
27 the correlation between measured FN and predicted FN shown in Figure 6 appears to show some  
28  
29 evidence of the veracity of the relationship developed in this study for describing FN as a function of  
30  
31 dynamic modulus and gradation.  
32  
33

34  
35 The results show a promising approach for estimating FN and hence rutting in AC mixtures using  
36  
37 fundamental mixture properties such as dynamic modulus and gradation. Further study aimed at utilizing  
38  
39 the rather strong correlation of FN to dynamic modulus and gradation observed in this paper for use  
40  
41 during routine mix design and QC/QA purposes is recommended as very limited mixtures were  
42  
43 considered in this study. Given the number of variables (10) used in the models presented in this study, a  
44  
45 study involving a larger number of mixtures should be used to validate the models.  
46  
47

## 48 49 **Summary and Conclusions**

50  
51  
52 This study was conducted to investigate rutting resistance of AC mixtures as a function of dynamic  
53  
54 modulus and gradation. FN tests conducted at 54°C were used to simulate rutting in 16 AC mixtures in  
55  
56 the laboratory.  
57  
58  
59  
60  
61  
62  
63  
64  
65

- 1 • FN was affected by RAP amount, binder type, and mixture type. FN for dense-graded mixtures  
2 (SM and BM) was in general higher than for comparable SMA mixtures. It must however be  
3 noted that a very limited number of SMA mixtures were tested in this study.  
4  
5  
6  
7  
8 • A model of FN as a function of dynamic modulus and gradation developed during this study was  
9 found to have good predictive value as indicated by the low  $C_p$ , and high  $R^2$  obtained from  
10 statistical analyses .  
11  
12  
13  
14 • The high predictive ability of the models developed in this study relating dynamic modulus and  
15 gradation to FN suggests these two mixture properties should be considered as potential  
16 specification parameters for the mix design process as well as field QC/QA activities. The  
17 possibility of predicting rutting resistance of asphalt mixtures from dynamic modulus and  
18 gradation has many potential practical implications and requires further investigation.  
19  
20  
21  
22  
23  
24  
25

## 26 **Acknowledgements**

27  
28  
29  
30 The authors acknowledges assistance of the following Virginia Transportation Research Council  
31 personnel to this study: Donnie Dodds and Troy Deeds for material testing.  
32  
33  
34

## 35 **References**

- 36  
37  
38  
39 American Association of State Highway and Transportation Officials (AASHTO). (2007). "AASHTO TP  
40 62 standard method of test for determining dynamic modulus of hot-mix asphalt (HMA)."  
41  
42 *American Association of State Highway and Transportation Officials*. Washington, D.C.  
43  
44  
45  
46 Biligiri, K. P., Kaloush, K. E., Mamlouk, M. S., and Witczak, M. W. (2007). "Rational modeling of  
47 tertiary flow for asphalt mixtures." *Transportation Research Record: Journal of the*  
48 *Transportation Research Board, Transportation Research Board of the National Academies, No.*  
49 *2001, 63-72*, Washington, D.C.  
50  
51  
52  
53  
54  
55 Birgisson, B., and Roque, R., Kim, J., Pham, L.V. (2004). "The use of complex modulus to characterize  
56 the performance of asphalt mixtures and pavements in Florida." *Final Report*, Report No. 4910-  
57 4504-784-12, pg. 298, Florida Department of Transportation, Tallahassee, FL.  
58  
59  
60  
61  
62  
63  
64  
65

- 1 Birgisson, B., and Roque, R. (2005). "Evaluation of the gradation effect on the dynamic modulus."  
2  
3 *Transportation Research Record: Journal of the Transportation Research Board, Transportation*  
4 *Research Board of the National Academies, No.1929, 193-199, Washington, D.C.*  
5  
6  
7  
8 Cooper, S. B. (2008). "Characterization of HMA mixtures containing high recycled asphalt pavement  
9 content with crumb rubber additives." PhD Thesis, Louisiana State University, Baton Rouge,  
10 Louisiana.  
11  
12  
13  
14 Ekingen, E.R. (2004). "Determining gradation and creep effects in mixtures using the complex modulus  
15 test." M.S. Thesis, University of Florida, Gainesville, FL.  
16  
17  
18  
19 El-Basyouny, M.M., and Jeong, M.G. (2009). "Effective Temperature for Analysis of Permanent  
20 Deformation and Fatigue Distress on Asphalt Mixtures" *Transportation Research Record:*  
21 *Journal of the Transportation Research Board, Transportation Research Board of the National*  
22 *Academies, No.2127, 155-163, Washington, D.C*  
23  
24  
25  
26  
27  
28 Kanitpong, K., and Bahia, H. (2005). "Relating adhesion and cohesion of asphalts to the effect of  
29 moisture on laboratory performance of asphalt mixtures." *Transportation Research Record:*  
30 *Journal of the Transportation Research Board, Transportation Research Board of the National*  
31 *Academies, No. 1901, 33-43.*  
32  
33  
34  
35  
36  
37 Kvasnak, A., Robinette, C. J., and Williams, R. C. (2007). "Statistical development of a flow number  
38 predictive equation for the mechanistic-empirical pavement design guide." TRB 86th Annual  
39 Meeting Compendium of Papers CD-ROM , Paper #07-1000, 18p, Transportation Research  
40 Board.  
41  
42  
43  
44  
45  
46 Pavement Systems. (2005). "LTPPBIND. , v. 3.1 beta." *Pavement Systems, LLC, Bethesda, Md., 2005.*  
47  
48  
49 Mohammad, L.N., Wu, Z., Obularreddy, S., Cooper, S., and Abadie, C. (2006). "Permanent deformation  
50 analysis of hot-mix asphalt mixtures with simple performance tests and 2002 mechanistic-  
51 empirical pavement design software." *Transportation Research Record: Journal of the*  
52 *Transportation Research Board, Transportation Research Board of the National Academies, No.*  
53 *1970, pp. 133-142.*  
54  
55  
56  
57  
58  
59 Pellinen, T. K., and Witczak M. W. (2002). "Use of stiffness of hot-mix asphalt as a simple performance  
60 test." *Transportation Research Board TRB 2002 Annual Meeting, Washington, D.C.*  
61  
62  
63  
64  
65



1 SAS Institute Inc. SAS, Version 9.1.3. Cary, N.C., 2007.

2  
3 Shenoy, A., and P. Romero. (2002). "Standardized procedure for analysis of dynamic modulus |E\*| data  
4 to predict asphalt pavement distresses. *Transportation Research Record: Journal of the*  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

1789, pp. 173–182.

Witczak, M. W. (2007). "Specification criteria for simple performance tests for rutting." *National Cooperative Highway Research Program, Report No. NCHRP Report 580, Washington, D.C.*

Witczak, M. W., and Sullivan, B. (2002). "Superpave support and performance models management." *National Cooperative Highway Research Program, 465.*

Witczak M.W, Kaloush K, Pellinen T., El-Basyouny M., Quintus H.V. (2002). "Simple Performance Test for Superpave Mix Design." *NCHRP Report 465*, National Cooperative Highway Research Program, pp.6.

Zhou, F., and Scullion, T. (2007). "Preliminary field validation of simple performance tests for permanent deformation: case study." *Transportation Research Record: Journal of the Transportation Research Board, Transportation Research Board of the National Academies, No. 1832/2003*, 209-216.

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

Table 1. Plant-mixed loose asphalt mixtures sampled for testing

Mix type	Mix ID	% RAP	Binder grade	District
Surface mixes	08-1019D	15	PG 70-22	Culpeper
	08-1043A	0	PG 64-22	NOVA
	08-1045D	20	PG 70-22	NOVA
	08-1047D	10	PG 70-22	Hampton Road
	08-1036D	10	PG 70-22	Staunton
	08-1052E	12	PG 76-22	Hampton Road
	08-1055D	25	PG 70-22	Lynchburg
	09-1001E	15	PG 76-22	Fredericksburg
	Base mixes	08-1044A	20	PG 64-22
09-1049A		15	PG 64-22	Bristol
09-1051D		15	PG 70-22	Bristol
09-1053D		15	PG 70-22	Bristol
09-1056A		25	PG 64-22	Richmond
Stone matrix asphalt mixes	08-1012E	0	PG 76-22	Fredericksburg
	08-1025E	10	PG 76-22	Fredericksburg
	08-1046D	0	PG 70-22	Hampton Road

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

Table 2. Mixture gradation parameters

Mix ID	Sieve size (mm)										
	25	19	12.5	9.5	4.75	2.36	1.18	0.6	0.3	0.15	0.075
08-1019D	100	100	99.9	97.2	60.5	40.6	29.0	19.6	12.1	8.4	5.8
08-1043A	100	100	98.8	91.9	58.3	41.9	30.1	20.4	13.0	8.7	5.8
08-1045D	100	100	99.8	91.8	40.5	24.4	18.3	14.0	9.8	6.4	4.2
08-1047D	100	100	100.0	95.3	66.6	47.9	37.8	27.5	16.0	9.6	6.6
08-1036D	100	100	96.8	84.2	51.6	33.2	25.4	20.8	13.5	7.9	5.6
08-1052E	100	100	96.6	86.1	61.1	37.7	23.1	15.1	10.6	8.2	6.8
08-1055D	100	100	96.5	84.7	50.2	42.5	35.0	24.1	12.3	7.7	5.2
09-1001E	100	100	94.6	83.2	57.6	39.8	29.2	20.0	11.4	6.9	4.6
08-1044A	99	91.2	56.3	42.0	28.7	22.9	19.0	14.6	9.7	6.4	4.4
09-1049A	98.5	91.8	74.2	64.1	39.8	24.6	16.8	12.9	10.5	8.7	7.0
09-1051D	95.8	90.1	68.7	58.1	37.0	24.5	16.8	12.6	10.1	8.3	6.8
09-1053D	97.4	89.1	70.1	58.1	37.9	24.9	17.0	12.9	10.4	8.4	6.9
09-1056A	92.7	76.4	56.6	49.9	37.5	29.0	21.7	16.2	11.6	8.5	6.3
08-1012E	100	100	89.3	67.0	26.2	19.6	17.8	16.8	16.0	14.5	11.3
08-1025E	100	100	90.0	63.0	25.6	19.3	17.4	16.0	14.8	13.7	11.4
08-1046D	100	99.8	83.9	61.7	23.8	14.2	11.8	10.2	8.7	7.6	5.8

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

Table 3. Mixture volumetric properties

Mix type	Mix ID	P <sub>b</sub> (%)	AV (%)	VMA (%)	VFA(%)
Surface mixes	08-1019D	5.4	6.8	16.6	74.5
	08-1043A	5.6	7.1	16.9	76.9
	08-1045D	4.4	7.8	20.3	52.5
	08-1047D	5.4	6.9	15.8	76.4
	08-1036D	5.7	7.0	15.5	79.7
	08-1052E	5.9	7.1	17.2	74.9
	08-1055D	5.6	7.0	16.3	74.5
	09-1001E	5.2	6.8	17.0	70.6
	08-1044A	4.5	6.9	15.0	74.1
Base mixes	09-1049A	4.9	7.6	14.9	71.3
	09-1051D	4.7	7.6	14.1	73.1
	09-1053D	5.0	6.0	14.1	77.8
Stone matrix asphalt mixes	09-1056A	4.6	7.0	12.7	76.5
	08-1012E	6.5	7.0	18.2	88.5
	08-1025E	6.5	7.5	18.2	83.2
	08-1046D	7.1	7.8	23.3	63.0

P<sub>b</sub> = Asphalt content; AV = air voids; VMA = voids in mineral aggregate;  
VFA = voids filled with asphalt

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

Table 4. Flow number test results

Mix type	Mix ID	Flow Number (FN)		Strain at FN (microstrain)	
		Mean	COV (%)	Mean	COV (%)
Surface mixes	08-1019D	3,373	13.2	9,180	7.0
	08-1043A	702	23.6	11,649	20.4
	08-1045D	4,385	10.5	5,809	61.7
	08-1047D	7438	25.5	7,214	42.0
	08-1036D	6,910	1.9	13,253	5.4
	08-1052E	5,753	24.6	11,937	1.4
Base mixes	08-1055D	1,133	4.6	9,627	8.0
	09-1001E	8,414	17.6	7,320	26.5
	08-1044A	2,623	38.2	15,637	13.7
	09-1049A	1,624	7.9	16,627	2.6
	09-1051D	6,454	4.1	13,930	6.5
	09-1053D	6,781	9.8	11,444	13.4
Stone matrix asphalt mixes	09-1056A	566	19.7	12,966	9.5
	08-1012E	2,810	6.0	26,586	9.5
	08-1025E	4,330	26.8	21,510	3.2
	08-1046D	1,631	27.0	10,533	6.3

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

Table 5. Model parameters describing FN as a function of dynamic modulus and gradation  
Analysis of Variance

Source	DF	Sum of squares	Mean square	F Value	Pr > F
Model	10	260913334	26091333	38.33	<.0001
Error	36	24507811	680773		
Corrected Total	46	285421145			

Variable	Parameter Estimate	Standard Error	Type II SS	F Value	Pr > F
$\beta_0$	32498	5258.5133	26000305	38.19	<.0001
$\beta_1$	-2764.1649	549.3629	17235001	25.32	<.0001
$\beta_2$	-196.2659	75.5706	4591835	6.75	0.0135
$\beta_3$	546.6656	87.074	26832942	39.42	<.0001
$\beta_4$	-550.099	68.7912	43532909	63.95	<.0001
$\beta_5$	484.8973	40.0825	99630672	146.35	<.0001
$\beta_6$	-416.2817	44.4777	59633772	87.6	<.0001
$\beta_7$	-11.2714	1.4536	40934038	60.13	<.0001
$\beta_8$	31.6091	4.3491	35961313	52.82	<.0001
$\beta_9$	-18.1238	3.8087	15415436	22.64	<.0001
$\beta_{10}$	-358.5415	151.0725	3834512	5.63	0.0231

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

Table 6. Data used for verification of FN as a function of dynamic modulus and gradation (data after Mohammad et al., 2006; Cooper, 2008)

Mix ID	Sieve size (mm)											E*  (MPa)
	25	19	12.5	9.5	4.75	2.36	1.18	0.6	0.3	0.15	0.075	
64 CO	100	98	77	61	41	29	21	15	8	6	4.6	248
70 CO	100	98	77	61	41	29	21	15	8	6	4.6	324
76 CO	100	98	77	61	41	29	21	15	8	6	4.6	400
76 CRM	100	98	77	61	41	29	21	15	8	6	4.6	317
76 RAP 15	100	95	77	60	37	28	21	16	9	6	4.5	241
64 RAP 40	100	95	77	60	37	28	19	15	9	6	4.5	593
I-10 Vintage	100	100	93	71	30	20	17	15	12	10	8.0	600
I-10 Egan BC	96	87	68	59	35	23	17	13	7	4	2.6	900
LA 964 BC	96	83	65	59	47	35	26	20	11	6	4.1	900
LA 964 WC	100	98	83	73	50	35	25	18	12	6	4.5	500
US 190 BC	97	84	65	59	47	35	26	20	11	6	4.1	700
I-Egan WC	100	100	98	89	50	29	19	13	10	8	6.5	600

|E\*| = dynamic modulus

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

### **List of Figures**

Fig. 1. Dynamic modulus of surface mixes.

Fig. 2. Dynamic modulus of base mixes.

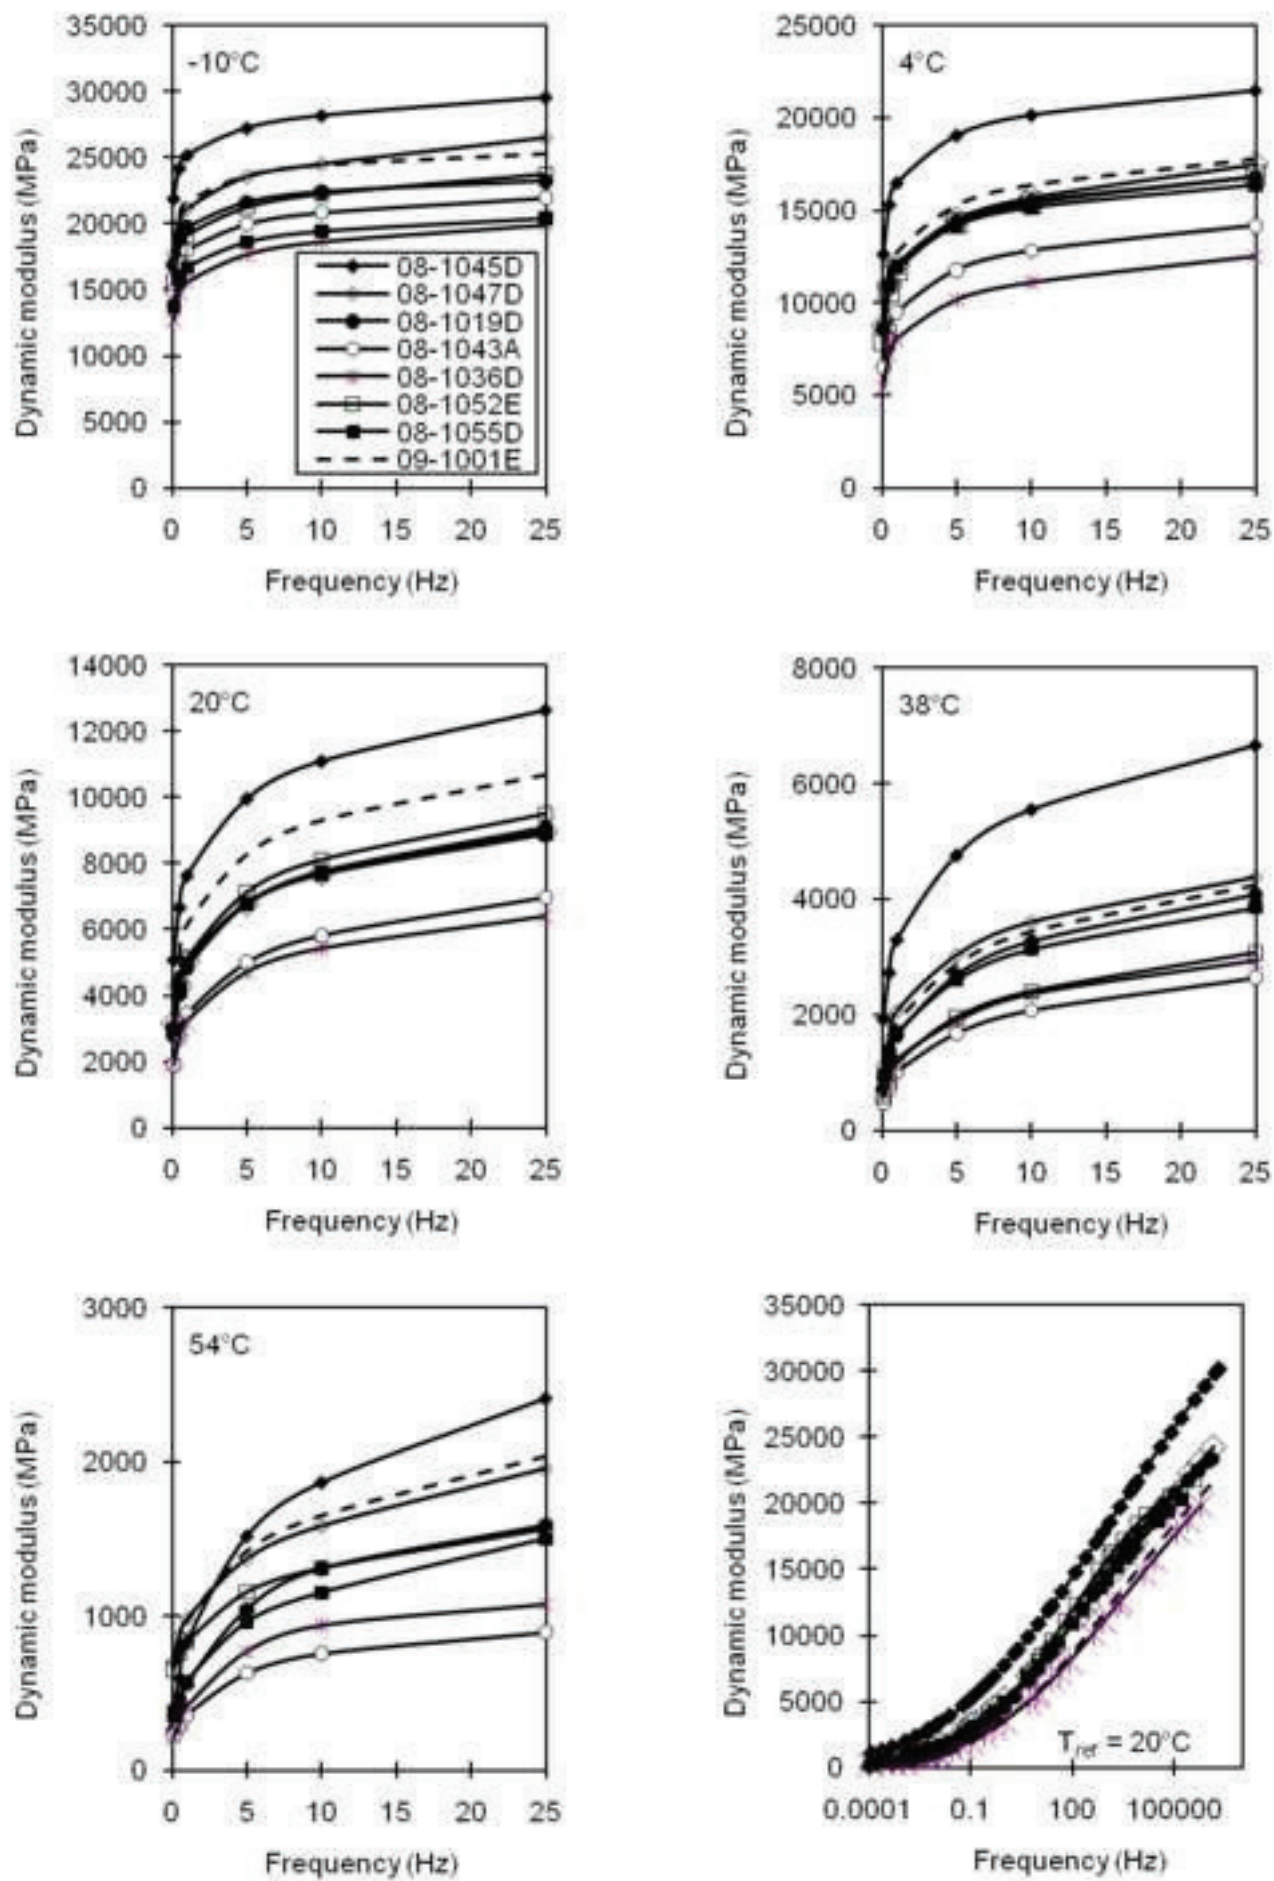
Fig. 3. Dynamic modulus of stone matrix asphalt mixes.

Fig. 4. Flow number test results for a typical asphalt mix.

Fig. 5. Comparison of measured FN and predicted FN for the 16 different AC mixtures tested.

Fig. 6. Comparison of measured and predicted FN for 12 mixtures indicating strong dependence of FN on dynamic modulus and gradation of AC mixtures (measured data after Mohammad et al., 2006 and Cooper, 2008).



**Fig 1**[Click here to download high resolution image](#)

**Fig 2**

[Click here to download high resolution image](#)

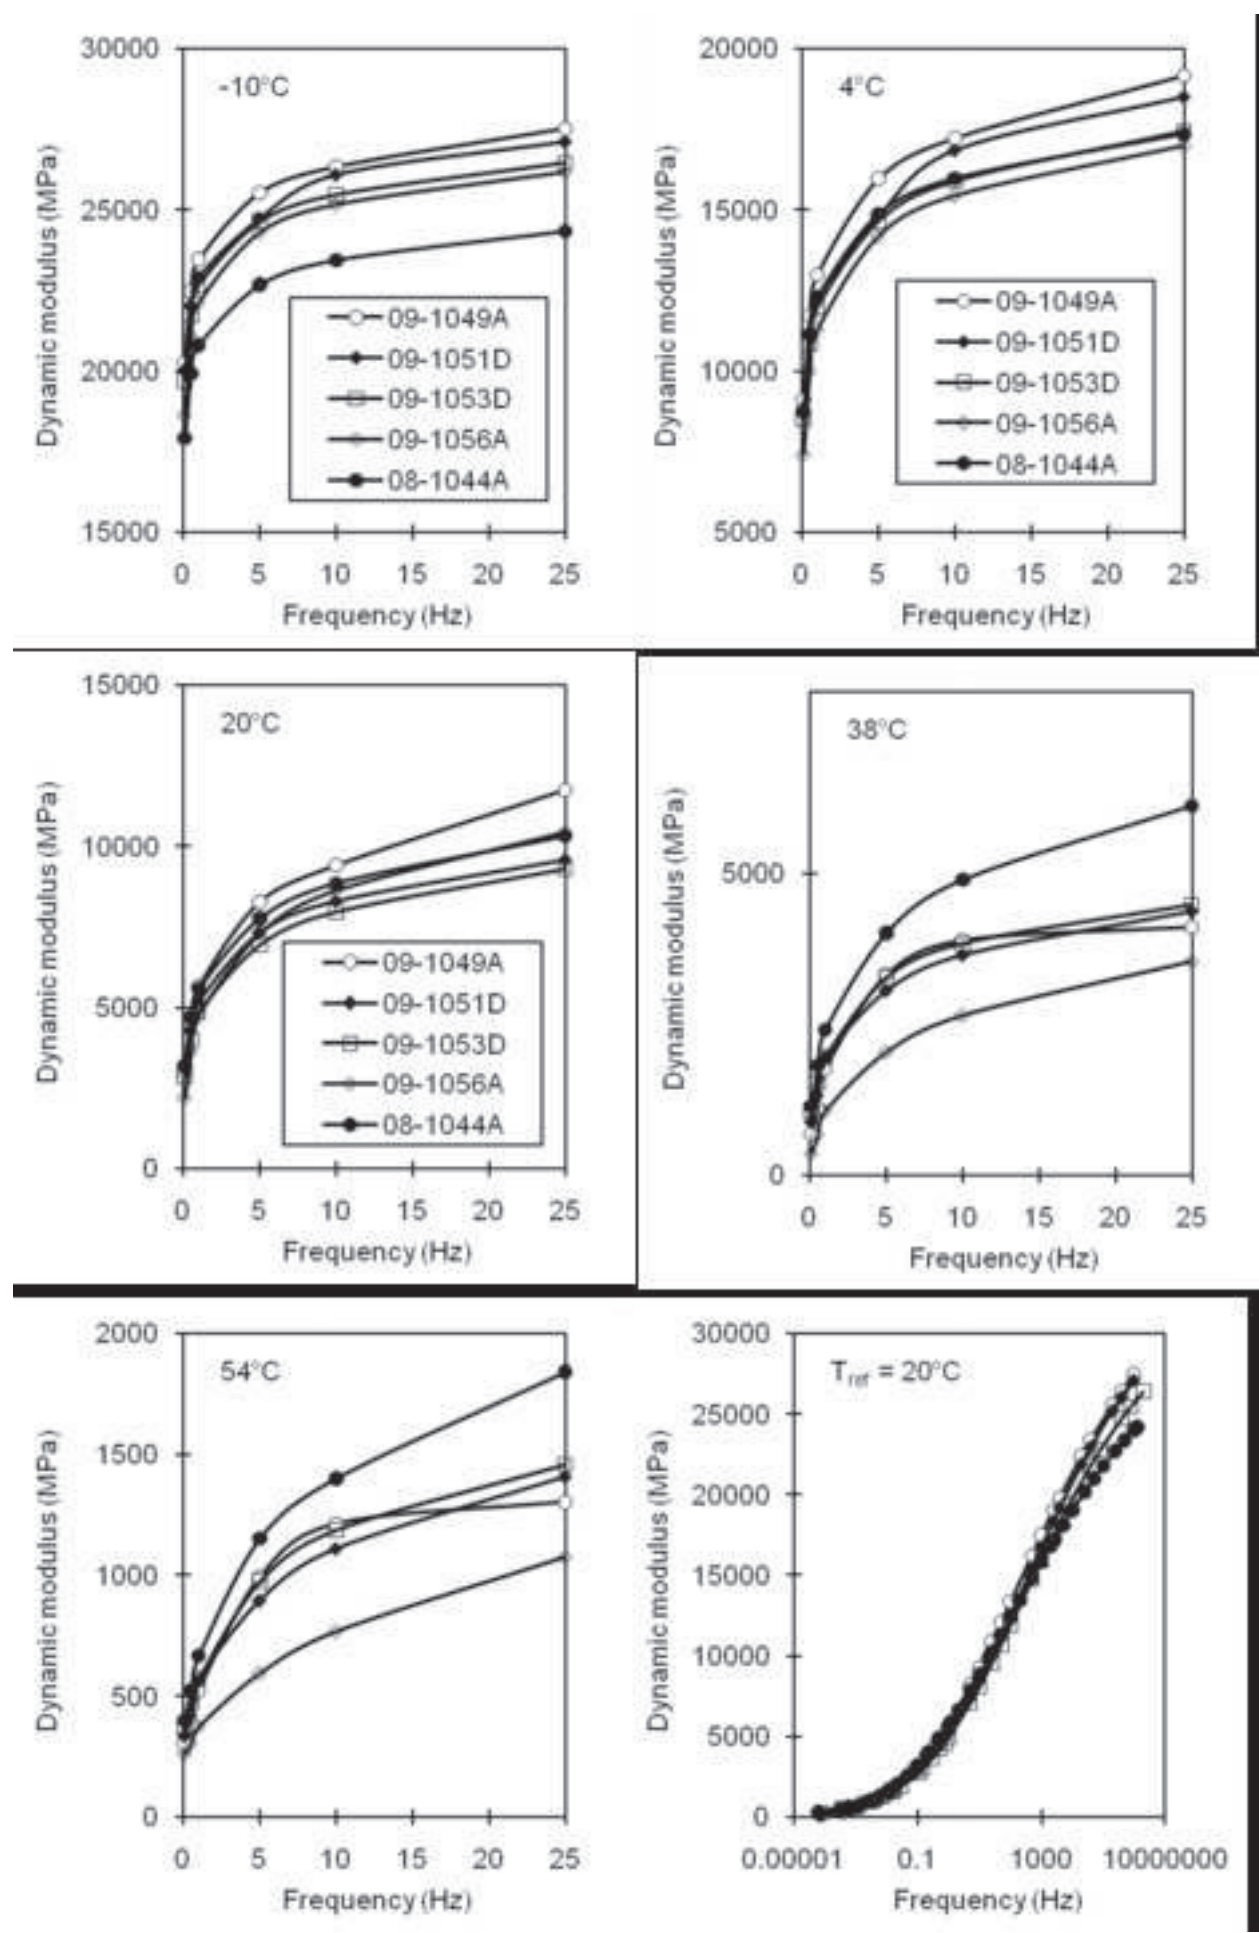


Fig 3  
[Click here to download high resolution image](#)

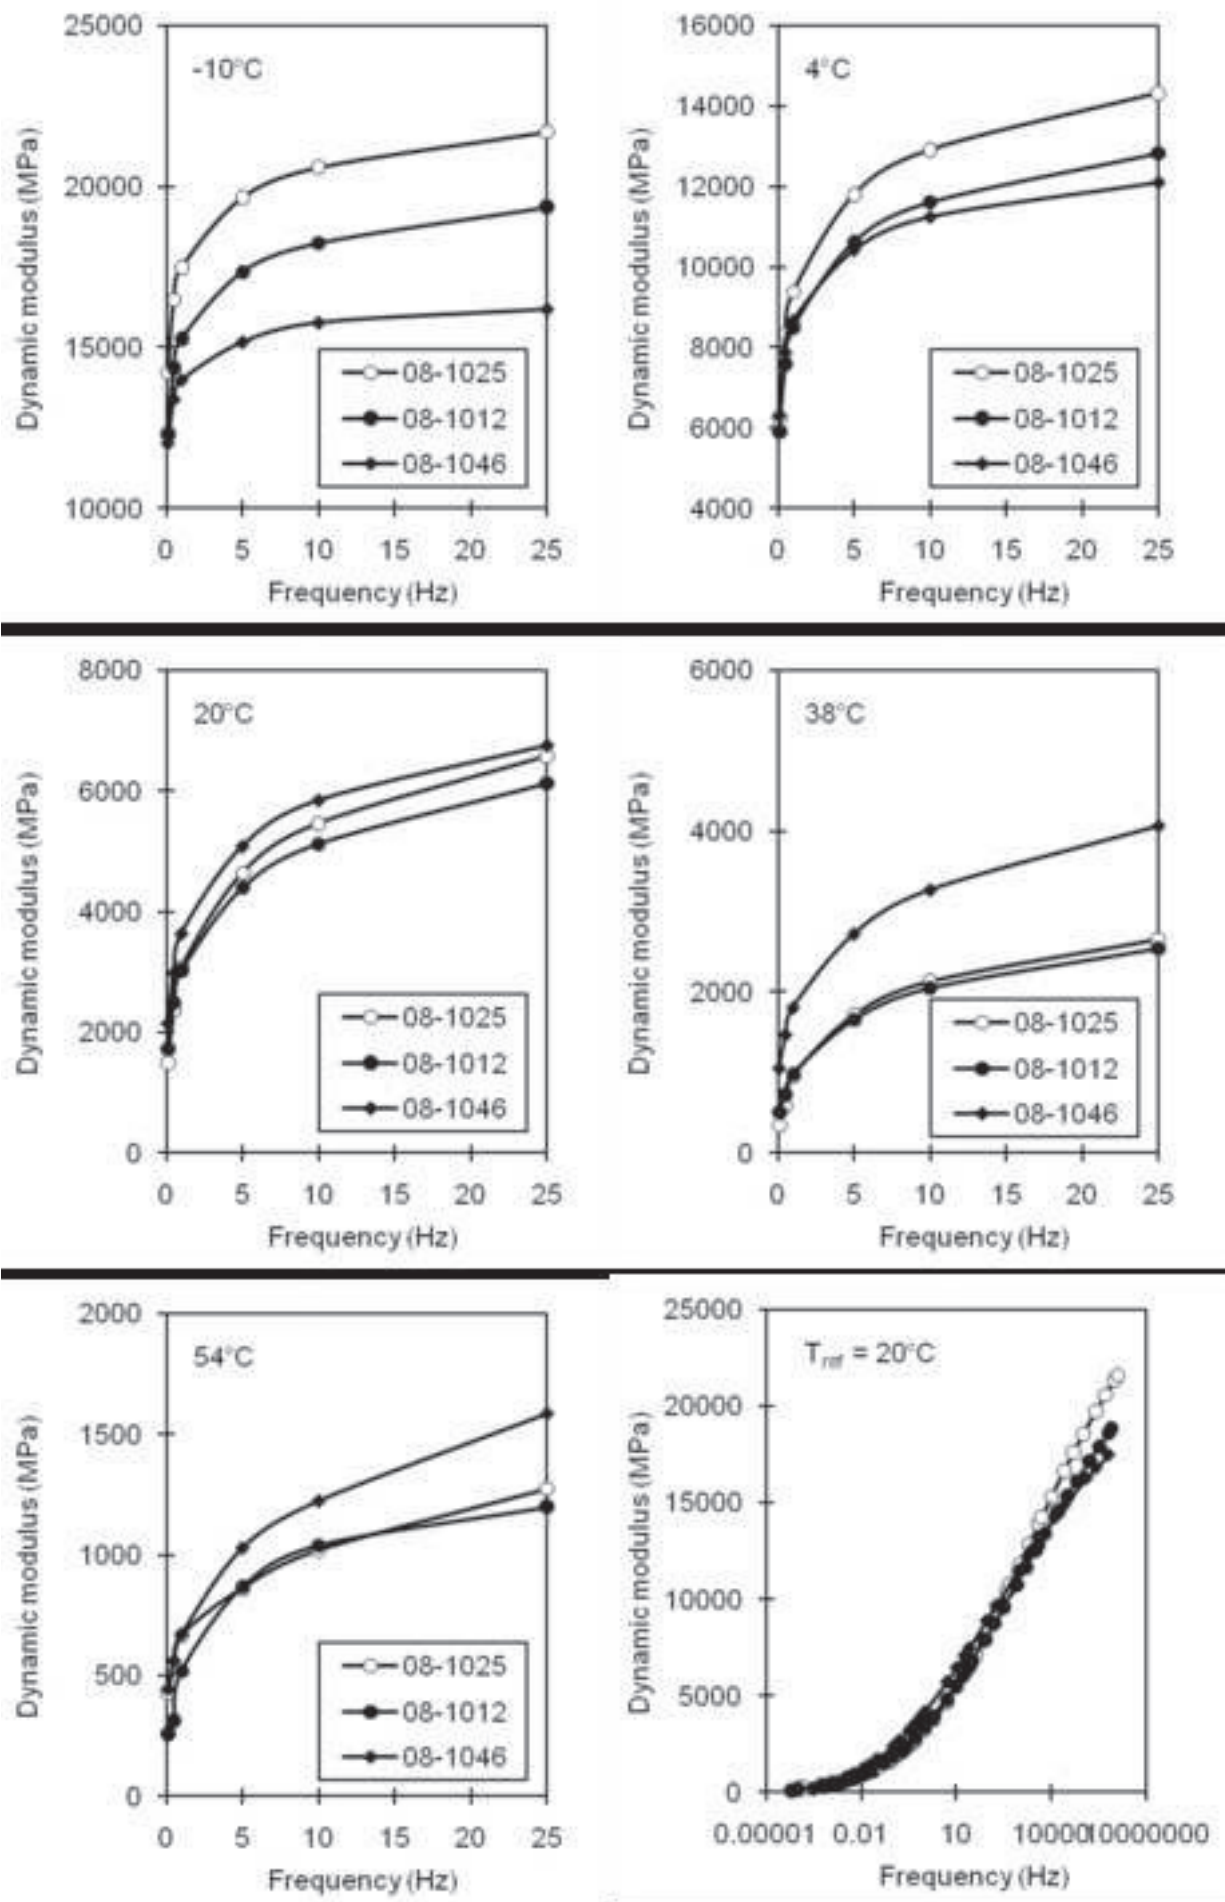


Fig 4  
Click here to download high resolution image

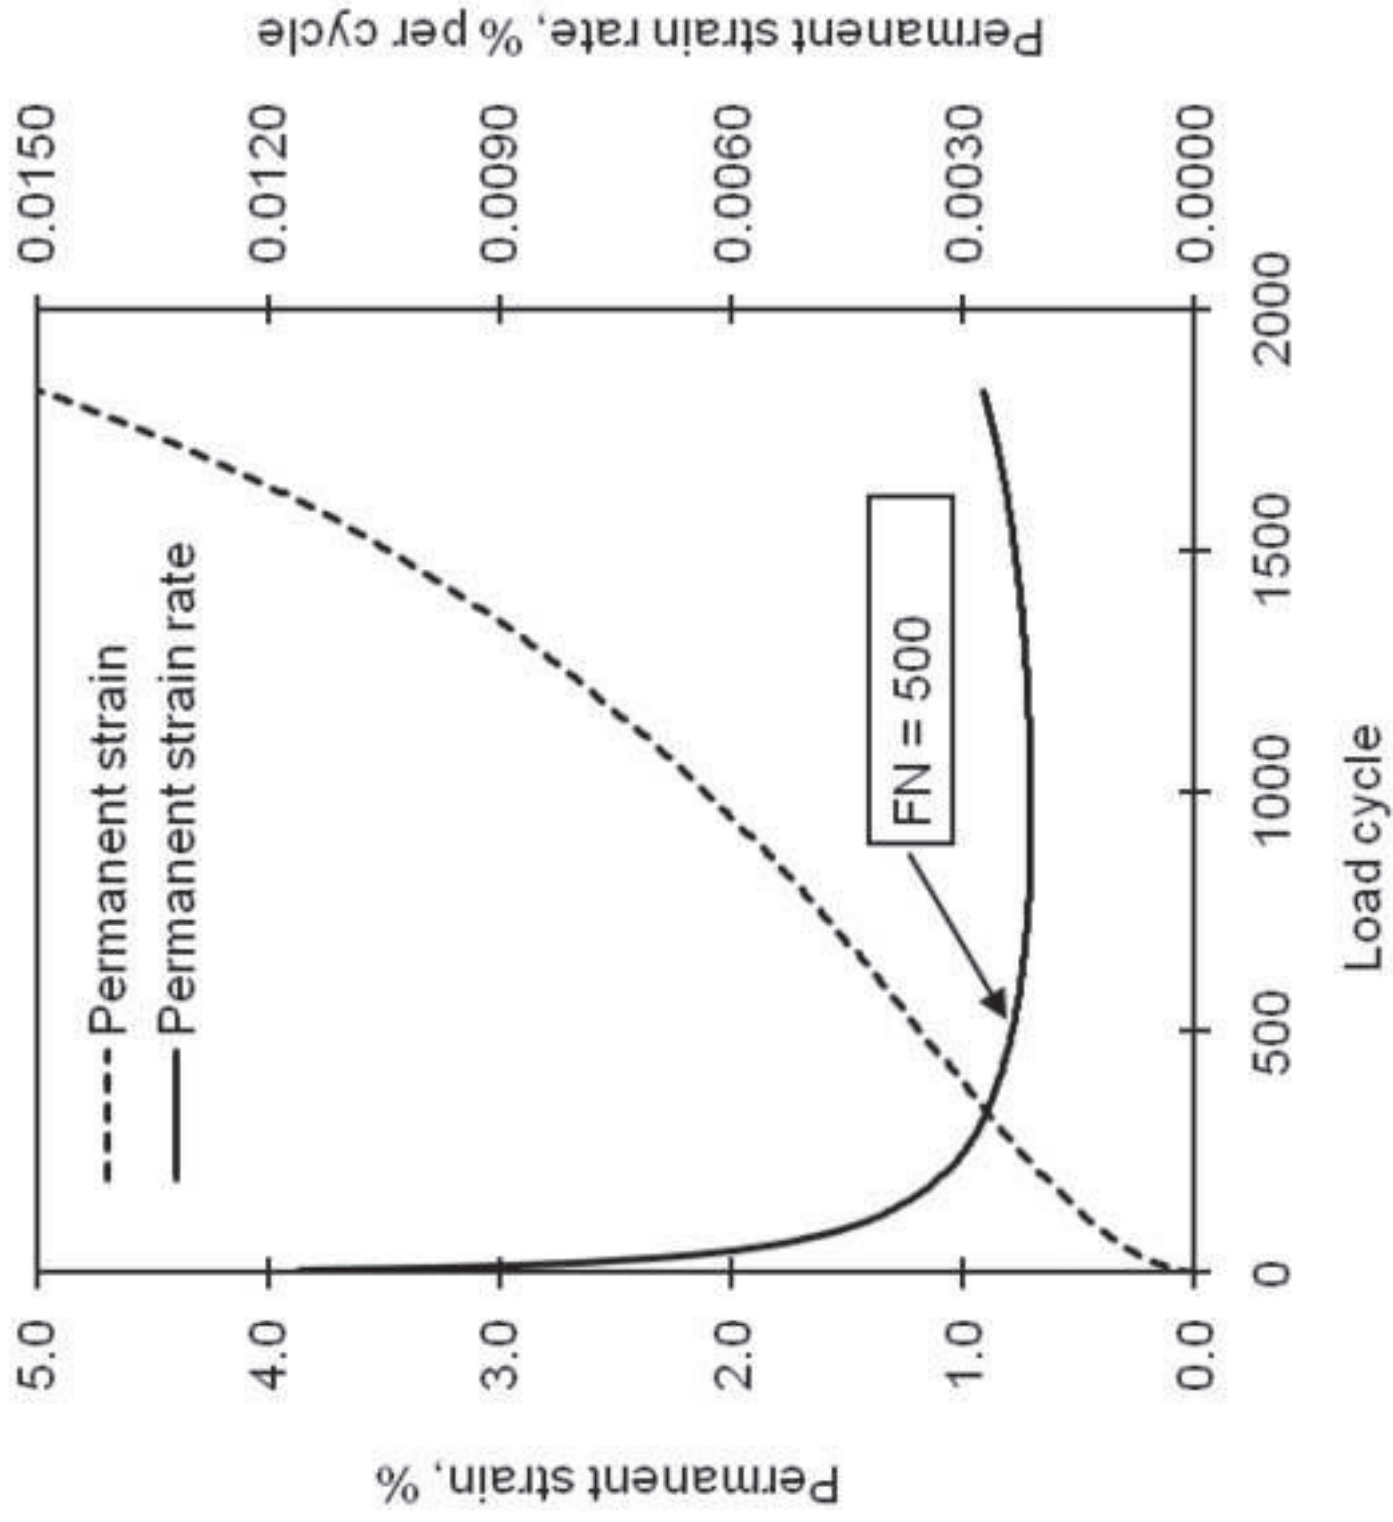


Fig 5  
Click here to download high resolution image

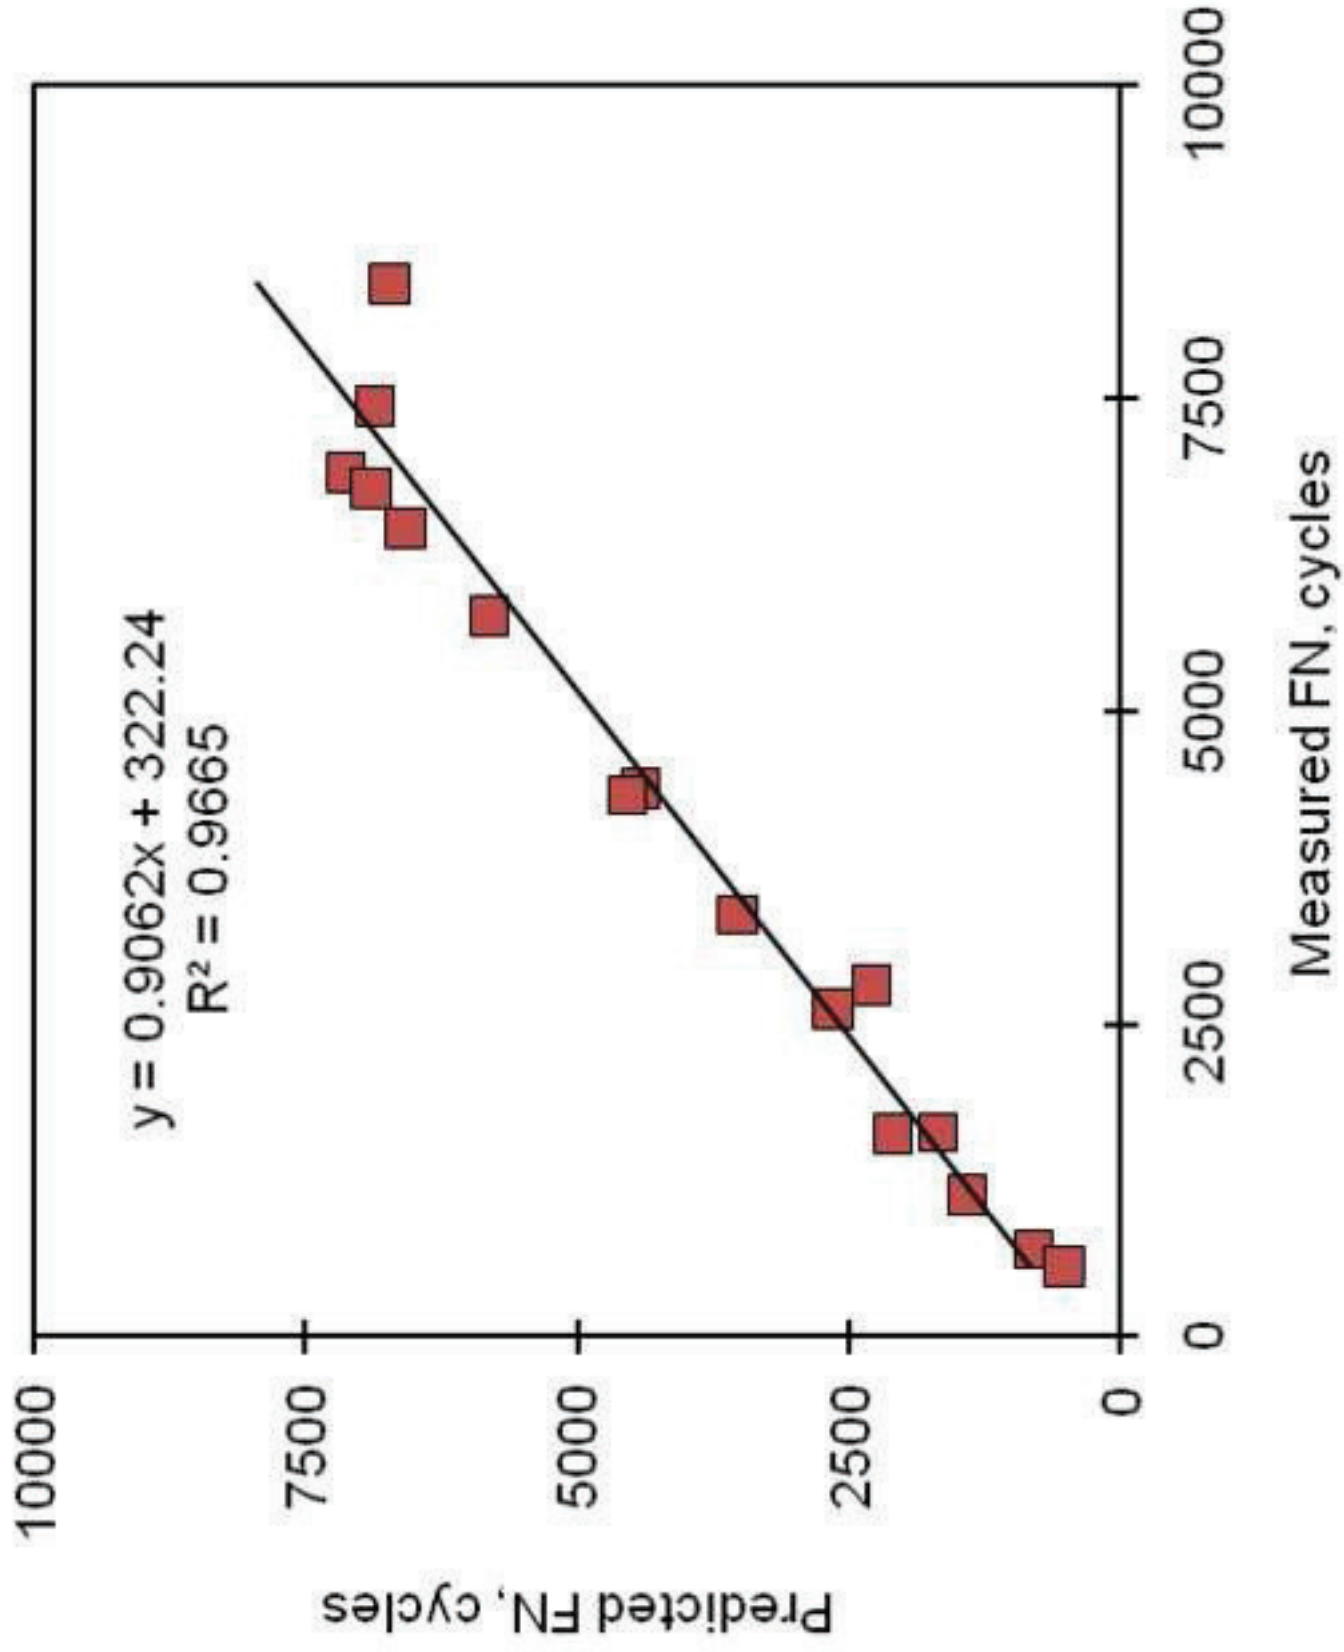


Fig 6  
Click here to download high resolution image

