

# UNIVERSITY OF BIRMINGHAM

## Research at Birmingham

### Microwave characterisation of carbon nanotube powders

Childs, Peter; Odili, Ifesinachi; Porch, A

DOI:

[10.1186/1556-276X-7-429](https://doi.org/10.1186/1556-276X-7-429)

#### *Document Version*

Publisher's PDF, also known as Version of record

#### *Citation for published version (Harvard):*

Childs, P, Odili, DI & Porch, A 2012, 'Microwave characterisation of carbon nanotube powders', *Nanoscale Research Letters*, vol. 7, no. 1, pp. 429. <https://doi.org/10.1186/1556-276X-7-429>

[Link to publication on Research at Birmingham portal](#)

#### **General rights**

Unless a licence is specified above, all rights (including copyright and moral rights) in this document are retained by the authors and/or the copyright holders. The express permission of the copyright holder must be obtained for any use of this material other than for purposes permitted by law.

- Users may freely distribute the URL that is used to identify this publication.
- Users may download and/or print one copy of the publication from the University of Birmingham research portal for the purpose of private study or non-commercial research.
- User may use extracts from the document in line with the concept of 'fair dealing' under the Copyright, Designs and Patents Act 1988 (?)
- Users may not further distribute the material nor use it for the purposes of commercial gain.

Where a licence is displayed above, please note the terms and conditions of the licence govern your use of this document.

When citing, please reference the published version.

#### **Take down policy**

While the University of Birmingham exercises care and attention in making items available there are rare occasions when an item has been uploaded in error or has been deemed to be commercially or otherwise sensitive.

If you believe that this is the case for this document, please contact [UBIRA@lists.bham.ac.uk](mailto:UBIRA@lists.bham.ac.uk) providing details and we will remove access to the work immediately and investigate.

**NANO EXPRESS**

**Open Access**

# Microwave characterisation of carbon nanotube powders

Adrian Porch<sup>1</sup>, Daniel I Odili<sup>2</sup> and Peter A Childs<sup>2\*</sup>

## Abstract

We have used a 3-GHz microwave host cavity to study the remarkable electronic properties of metallic, single-walled carbon nanotubes. Powder samples are placed in its magnetic field antinode, which induces microwave currents without the need for electrical contacts. Samples are shown to screen effectively the microwave magnetic field, implying an extremely low value of sheet resistance ( $< 10 \mu\Omega$ ) within the graphene sheets making up the curved nanotube walls. Associated microwave losses are large due to the large surface area, and also point to a similar, very small value of sheet resistance due to the inherent ballistic electron transport.

**PACS:** 73.63.Fg, 72.80.Rj, 78.70.Gq

**Keywords:** Carbon nanotubes, Microwave, Screening

## Background

There has been intensive research on the characterisation and application of carbon nanotubes for next-generation electronic devices [1]. Ballistic conduction along single-walled metallic nanotubes is predicted theoretically and has been experimentally verified. Clearly, this has enormous impact for electronic devices fabricated using these remarkable materials, but there are problems in characterising the electronic properties using conventional (i.e. DC) techniques. This is mainly due to the need to make electrical contacts with the ends of the nanotube, which suppresses the measured conductivity, and is further complicated by inter-tube contacts. For example, it has been found that thin film samples have sheet resistances limited by the large junction resistances between adjacent nanotubes [2].

In this context, we propose a new method to characterise the electronic properties of metallic nanotubes using microwaves as a means of exciting currents, thus negating the requirement for electrical contacts. The method is fast and is performed on a powder sample, so it allows rapid measurements of large numbers of samples and permits *in situ* changes in electronic properties (e.g. due to surface adsorption of chemical species) without the need to remove the sample from the apparatus. Previous microwave studies of carbon nanotube materials have

ranged from the screening efficiency of thin films [3] to the microwave excitation of single nanotubes [4]. In our experiments, powder samples are placed in a region of high microwave magnetic field in a microwave cavity (here, a 3-GHz copper hairpin), and the sample properties are determined using the cavity perturbation technique. We have used a similar method to measure the electronic properties of a range of other material systems (e.g. metal-loaded zeolites [5]).

## Methods


Powdered nanotube samples were obtained from Thomas Swan & Co. Ltd. (County Durham, UK), prepared by thermal CVD at 800°C, giving a mix of semiconducting and metallic single-walled nanotubes. Figure 1 shows the scanning electron microscope (SEM) image of the nanotubes before and after manual grinding. The long nanotubes are broken into smaller segments confirming the production of short carbon nanotubes, which has been previously reported using the ball milling technique.

Analysis of the transmission electron microscope (TEM) images shown in Figure 2 suggests the nanotubes have diameters ranging from 1.2 to 1.7 nm and lengths of 100 nm to 4  $\mu\text{m}$ . Scanning transmission microscopy (STEM) of the nanotubes shows that there are iron (Fe) impurities on the surface of the nanotubes. Energy dispersive X-ray spectroscopy gives atomic percent ratios of 96.5:2.7:0.8 for C:O:Fe, respectively. Samples were loaded into low-loss quartz tubes (inner diameter of 1.3 mm

\* Correspondence: p.a.childs@bham.ac.uk

<sup>2</sup>School of Electronic, Electrical and Computer Engineering, University of Birmingham, Pritchatts Road, Birmingham B15 2TT, UK

Full list of author information is available at the end of the article

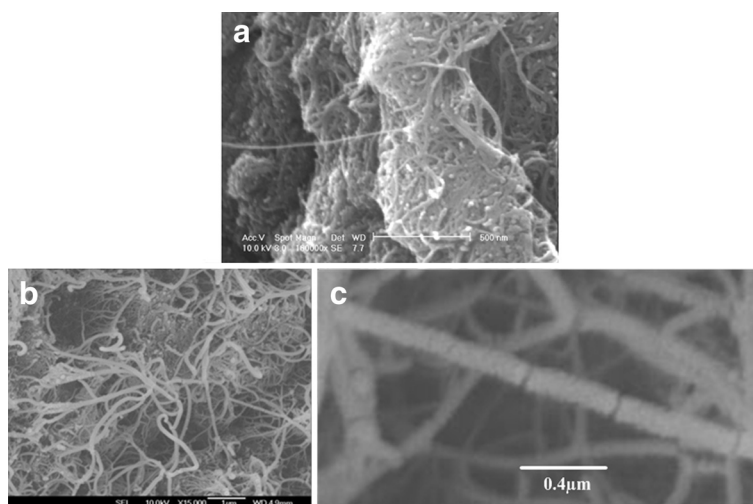

**Figure 1** SEM image of the nanotubes used in this experiment. (a) Before and (b,c) after manual grinding.


and wall thickness 0.35 mm) and placed parallel to the microwave magnetic field in the 3-GHz quarter-wave copper hairpin cavity, shown in Figure 3.

The hairpin itself is a 1-mm thick copper strip, with a width of 5 mm, bent into a U shape of length 23 mm and plate separation of 5 mm. The expected resonant frequency of the fundamental mode of the hairpin is, therefore,  $f_0 \approx c/4L \approx 3.26$  GHz, in practise about 10% lower due to the end effects of electric and magnetic fields spilling outside of the structure. The microwave magnetic field is largest at the short-circuit end of the hairpin, where the field is also approximately uniform and runs parallel to the plate surfaces. The sample is inserted into this region. The hairpin is surrounded by a cylindrical radiation shield, of length twice that of the hairpin (i.e. 50 mm) and inner radius of 15 mm. This reduces the radiation losses from the hairpin and, thus, preserves a high quality factor, which is desirable for measuring the additional microwave loss contributed by the sample. Microwave power is coupled in and out of


the hairpin using an identical pair of loop-terminated RG405 microwave coaxial cables which couple to the microwave magnetic field at the hairpin's short-circuit end. The transmitted microwave power (i.e.  $|S_{21}|^2$ ) is measured in the frequency domain using an Agilent E5071B network analyser with computer control (Agilent Technologies, Inc., CA, USA). The unloaded quality factor  $Q$  of the empty cavity is around 1,500, i.e. large for its small volume ( $\approx 600$  mm<sup>3</sup>), thus enhancing the sample filling factor for more sensitive measurements of its electronic properties. Cavity couplings are kept weak (i.e. insertion loss  $> 30$  dB at resonance), so that only minor correction factors are needed to extract unloaded  $Q$  factors from the raw data.

## Results and discussion

Microwave results for a nanotube sample are shown in Figure 4, compared with a similar volume of graphite powder. Remarkably, this nanotube sample exhibits screening of the microwave magnetic field. This is

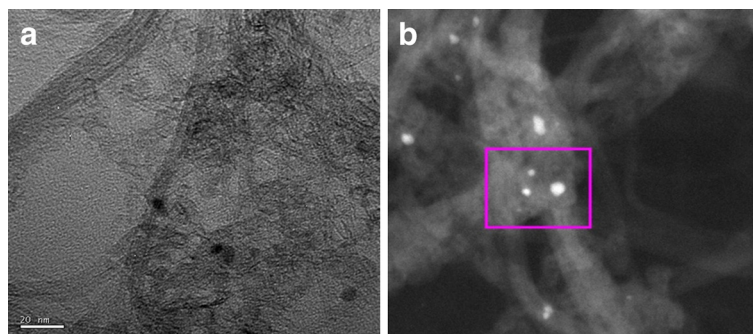

**Figure 2** TEM and STEM images of nanotubes. (a) TEM image of the nanotubes; dark spots (impurities). (b) STEM image; evidence of Fe content (inset).

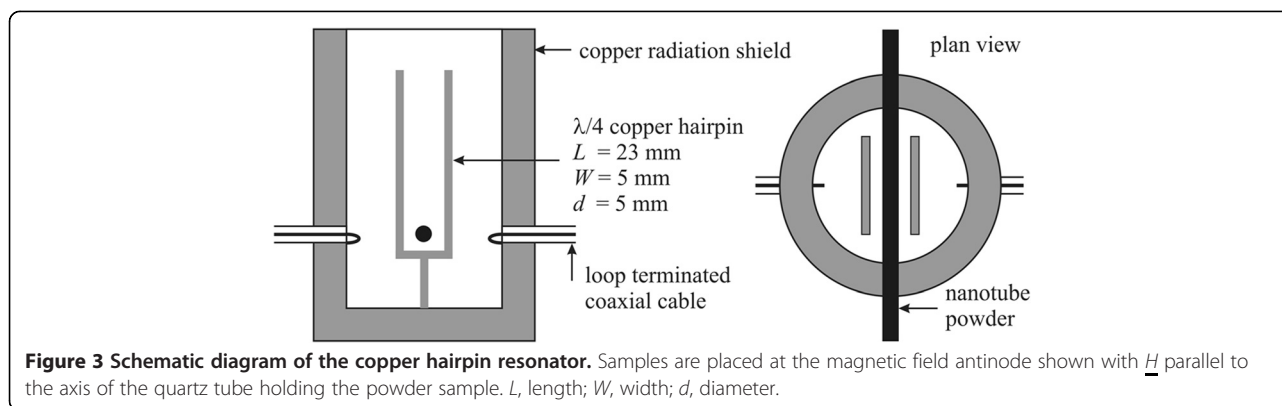

evidenced by an increased resonant frequency of  $\Delta f_0 = 9.0 \pm 0.3$  MHz relative to the empty tube. There are also very large microwave losses, evidenced by an increased 3-dB bandwidth of  $\Delta f_B = 18 \pm 1$  MHz. Such screening is usually observed only in powdered (or bulk) metals and of conductivity large enough for the mean particle size to become much greater than the microwave skin depth. As can be seen from the data of Figure 4, the conductivity of graphite is not high enough to observe any such screening; rather, it exhibits the response typical of a lossy dielectric (i.e. a broadened 3-dB bandwidth with no frequency shift, indicative of full sample penetration by the microwave magnetic field).

To analyse this data, we use standard cavity perturbation theory, which assumes a small sample filling fraction within the cavity [6]. For the  $\underline{H}$ -field applied parallel to the nanotube axis (Figure 5a), the main results are the following:

$$\frac{\Delta f_0}{f_0} \approx -\frac{\omega^2 \tau^2}{1 + \omega^2 \tau^2} \frac{V_s}{2V_{\text{eff}}} \quad (1a)$$

$$\frac{\Delta f_B}{f_0} \approx \frac{\omega \tau}{1 + \omega^2 \tau^2} \frac{V_s}{V_{\text{eff}}} \quad (1b)$$

where  $V_s$  is the total sample volume;  $V_{\text{eff}}$ , effective cavity volume; and  $\tau$ , relaxation time, defined via

$$V_{\text{eff}} = \int_{\text{cavity}} (H/H_0)^2 dV \approx LWd/2, \quad (2)$$


$$\tau = \mu_0 a / 2R_{\text{sq}}$$


with  $a$  being the average nanotube radius,  $H_0$  the local magnetic field strength at the sample and  $R_{\text{sq}}$  the sheet resistance of graphene walls of the nanotubes. As can be seen from Figure 5, both axial and radial components of  $\underline{H}$  relative to the nanotube axis will be screened if the sheet resistance is low enough. Effective screening only occurs in the limit when  $\omega \tau > 1$ , i.e. when  $R_{\text{sq}} < \mu_0 a \omega / 2$ .

A separate calibration experiment involved the insertion of small copper spheres of radii 330  $\mu\text{m}$  into the same  $\underline{H}$ -field position as for the sample. The observed frequency increase of  $\Delta f_0 = 1.30 \pm 0.01$  MHz per sphere allows us to determine experimentally  $V_{\text{eff}} = 270 \pm 2$   $\text{mm}^3$ , comparing well with the expected value of  $LWd/2 \approx 290$   $\text{mm}^3$ . Thus, the observed nanotube frequency shift corresponds to an effective screened volume of  $\approx 1.7$   $\text{mm}^3$ .

### Conclusions

The inner tube volume within the cavity is  $\approx 6.6$   $\text{mm}^3$ , of which  $\approx 0.40$   $\text{mm}^3$  is nanotube material (i.e. a packing fraction of about 6% by volume, based on the sample mass of 1.3 mg). From this, we conclude that the magnetic field is effectively screened within this low density powder, both from within the nanotubes themselves and from a much larger volume ( $\times 3$ ) in the space outside. For this to happen, we also conclude that the nanotube

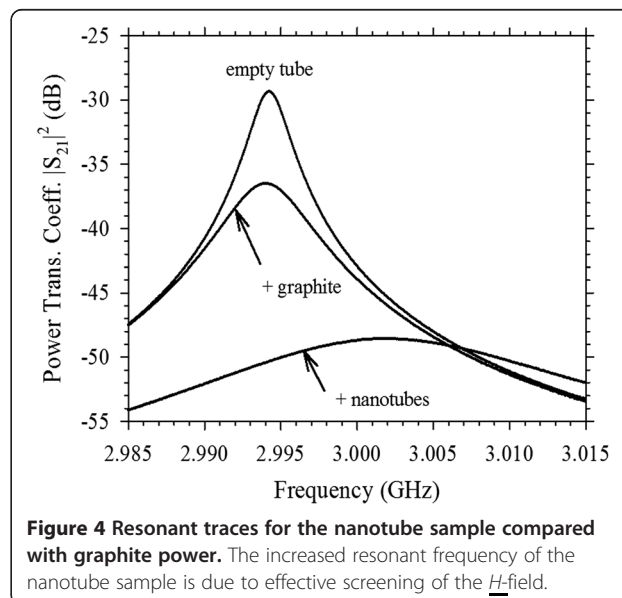

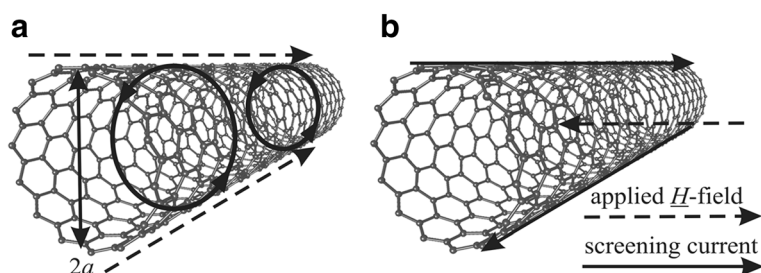

**Figure 5** Screening currents for the microwave  $H$ -field. Applied (a) parallel and (b) perpendicular to the nanotube axis.

sheet resistance must be extremely small, i.e. an upper limit of  $R_{sq} \approx 10 \mu\Omega$  based on a mean nanotube radius of  $a \approx 0.7$  nm. Since a trace of metallic Fe is present in the sample, it is prudent to quantify how much this contributes to the microwave screening. The 0.8% atomic ratio of Fe atoms corresponds to a volume of about  $0.006 \text{ mm}^3$ . This is likely to be dispersed as very small particles of radii less than  $1 \mu\text{m}$ . Given that the skin depth of Fe at 3 GHz at room temperature is about  $2.8 \mu\text{m}$ , we would not expect such small particles to screen the microwave magnetic field. Even if the Fe formed a single large particle, which gives rise to the greatest screened volume, the contribution to increase in resonant frequency will be only 0.6% of that observed for the whole CNT sample. Hence, we conclude that the screening effect of the Fe is negligible.

Does such a small value of  $R_{sq}$  contradict the observation of the large microwave losses of Figure 4? The answer can be found in the huge surface area of carbon nanotube powders, e.g. our 1.3-mg sample has a total surface area  $S \approx 1.1 \text{ m}^2$ . Sheet resistance can be extracted from Equation 1b in the limit of strong screening  $\omega\tau \gg 1$ , resulting in  $R_{sq} \approx 2\pi\mu_0 V_{eff} \Delta f_B / S \approx 30 \mu\Omega$ . Therefore, these two independent measurements (one of microwave screening, the other of microwave loss) both point to very small values of sheet resistance due to ballistic transport. In experimental studies of carbon nanotube films, the sheet resistance is found to be of the order of  $1 \text{ k}\Omega$  [7] with similar results for graphene films [8]. In these studies, the intrinsic sheet resistance of the carbon nanotubes can be difficult to extract from the measurements as charge transport is limited by contacts between the nanotubes. Other types of measurement such as the optical conductivities reported in [8] do not circumvent this problem as they characterise relatively large areas of the films. In theoretical studies of devices based on discrete carbon nanotubes and of carbon nanotube films, charge transport is often assumed to be ballistic, and therefore, the sheet resistance is zero. Ballistic transport has been observed in ohmically contacted

metallic single wall carbon nanotubes having lengths less than approximately 300 nm [9].

Not all of the nanotube powders studied to date show such striking behaviour, so future experiments will concentrate on systematic studies of a wider range of materials (semiconducting and metallic), over a wider range of frequencies (particularly from kilohertz to megahertz), also trying to identify the nature of the defects giving rise to the finite sheet resistance. Indeed, isolating metallic samples is, itself, an important problem, and the method we have proposed here may serve as a means of quantifying the volume fraction of metallic nanotubes within a given powder.

#### Competing interests

The authors declare that they have no competing interests.

#### Authors' contributions

AP and DIO carried out the microwave measurements, and DIO characterized the sample. AP and PAC conceived of the study and completed the analysis. All authors read and approved the final manuscript.

#### Author details

<sup>1</sup>School of Engineering, Cardiff University, Newport Road, Cardiff CF24 3AA, UK. <sup>2</sup>School of Electronic, Electrical and Computer Engineering, University of Birmingham, Pritchatts Road, Birmingham B15 2TT, UK.

Received: 22 March 2012 Accepted: 3 July 2012

Published: 1 August 2012

#### References

- Anantram MP, Léonard F: **Physics of carbon nanotube electronic devices.** *Rep Prog Phys* 2006, **69**:507.
- Fuhrer MS, Nygård J, Shih L, Forero M, Yoon Y-G, Mazzone MSC, Choi HJ, Ihm J, Louie SG, Zettl A, McEuen PL: **Crossed nanotube junctions.** *Science* 2000, **290**:288.
- Xu H, Anlage SM, Hu L, Gruner G: **Microwave shielding of transparent and conducting single-walled carbon nanotube films.** *Appl Phys Lett* 2007, **90**:183119.
- Yu Z, Burke PJ: **Microwave transport in metallic single-walled carbon nanotubes.** *Nano Lett* 2005, **5**:1403.
- Anderson PA, Armstrong AR, Barker PD, Edmondson MJ, Edwards PP, Porch A: **Rubidium doped zeolite rho: structure and microwave conductivity of a metallic zeolite.** *Dalton Trans* 2004, **19**:3122.
- Klein O, Donovan S, Dressel M, Grüner G: **Microwave cavity perturbation technique.** *Int J Infrared Millimeter Waves* 1993, **14**:2423.
- Shin DH, Shim HC, Song J-W, Kimb S, Hana C-S: **Conductivity of films made from single-walled carbon nanotubes in terms of bundle diameter.** *Scr Mater* 2009, **60**:607.

8. De S, Coleman JN: Are there fundamental limitations on the sheet resistance and transmittance of thin graphene films? *ACS Nano* 2010, **4**(5):2713.
9. Javey A, Guo J, Paulsson M, Wang Q, Mann D, Lundstrom M, Dai H: High-field quasiballistic transport in short carbon nanotubes. *Phys Rev Lett* 2004, **92**(1):106804.

doi:10.1186/1556-276X-7-429

**Cite this article as:** Porch *et al.*: Microwave characterisation of carbon nanotube powders. *Nanoscale Research Letters* 2012 **7**:429.

**Submit your manuscript to a SpringerOpen<sup>®</sup> journal and benefit from:**

- ▶ Convenient online submission
- ▶ Rigorous peer review
- ▶ Immediate publication on acceptance
- ▶ Open access: articles freely available online
- ▶ High visibility within the field
- ▶ Retaining the copyright to your article

---

Submit your next manuscript at ▶ [springeropen.com](http://springeropen.com)

---