

UNIVERSITY OF BIRMINGHAM

Research at Birmingham

Direct Visualization of Size-Controlled Au₃₉ Clusters Supported on Hydroxyapatite by AC-STEM

Han, Yisong; Liu, Y; Xie, S; Tsukuda, T; Li, Zi

DOI:

[10.1017/S1431927611010191](https://doi.org/10.1017/S1431927611010191)

License:

None: All rights reserved

Document Version

Publisher's PDF, also known as Version of record

Citation for published version (Harvard):

Han, Y, Liu, Y, Xie, S, Tsukuda, T & Li, Z 2011, 'Direct Visualization of Size-Controlled Au₃₉ Clusters Supported on Hydroxyapatite by AC-STEM', *Microscopy and Microanalysis*, vol. 17, no. S2, pp. 1864-1865.
<https://doi.org/10.1017/S1431927611010191>

[Link to publication on Research at Birmingham portal](#)

Publisher Rights Statement:

© Cambridge University Press

Eligibility for repository checked July 2014

General rights

Unless a licence is specified above, all rights (including copyright and moral rights) in this document are retained by the authors and/or the copyright holders. The express permission of the copyright holder must be obtained for any use of this material other than for purposes permitted by law.

- Users may freely distribute the URL that is used to identify this publication.
- Users may download and/or print one copy of the publication from the University of Birmingham research portal for the purpose of private study or non-commercial research.
- User may use extracts from the document in line with the concept of 'fair dealing' under the Copyright, Designs and Patents Act 1988 (?)
- Users may not further distribute the material nor use it for the purposes of commercial gain.

Where a licence is displayed above, please note the terms and conditions of the licence govern your use of this document.

When citing, please reference the published version.

Take down policy

While the University of Birmingham exercises care and attention in making items available there are rare occasions when an item has been uploaded in error or has been deemed to be commercially or otherwise sensitive.

If you believe that this is the case for this document, please contact UBIRA@lists.bham.ac.uk providing details and we will remove access to the work immediately and investigate.

Direct Visualization of Size-Controlled Au₃₉ Clusters Supported on Hydroxyapatite by AC-STEM

Y. Han,¹ Y. Liu,² S. Xie,² T. Tsukuda^{2,3} and Z.Y. Li¹

^[1] Nanoscale Physics Research Laboratory, School of Physics and Astronomy, University of Birmingham, Birmingham B15 2TT, UK

^[2] Catalysis Research Center, Hokkaido University, Nishi 10, Kita 21, Sapporo 001-0021, Japan

^[3] CREST, Japan Science and Technology Agency, Kawaguchi, Saitama 332-0012, Japan

In recent years, there has been growing evidence indicating that the size of gold (Au) clusters in the regime of less than 2 nm has a significant influence on their catalytic performances. Despite lively debates on the fundamental issues relating to the driving force for this size-dependent phenomenon, there is neither resolution nor consensus in general. Here we take up the challenges of synthesizing monodispersed Au clusters as well as correlating the atomic structures at atomic resolution with the catalytic properties of these clusters. A series of Au_n ($n = 10, 18, 25$ and 39) clusters with atomically controlled sizes on a solid support, hydroxyapatite (HAP) (Ca₁₀(PO₄)₆(OH)₂), were synthesized successfully by Tsukuda's group. A strong size-dependence of Au_n has been demonstrated for the aerobic oxidation, with Au₃₉/HAP showing the highest activity [1]. The goal of the present study is to link directly the catalytic properties with cluster structures at atomic-details, via high-angle annular dark field (HAADF) imaging using aberration-corrected scanning transmission electron microscopy (AC-STEM).

Fig. 1 shows a typical STEM micrograph of Au₃₉/HAP, taken by a 200 kV JEM-2100F STEM (University of Birmingham, UK), fitted with a CEOS probe corrector. To minimize e-beam influence to both the clusters and the HAP substrate, HAADF-STEM images were acquired under a medium magnification of $\times 10M$ using a pixel time of 20 μs . To gain insight into size-dependent atomic structures on these samples, we have performed detailed intensity analysis of the HAADF-STEM images. First, the background of each cluster was subtracted individually with reference to its surround areas. The integrated intensity of each cluster was then recorded and plotted in Figure 2, where evenly spaced peaks in the histogram were evident. Using single Au atoms from the micrograph as a calibrator and assuming that multiple scattering effects may be neglected [2,3], the first peak in Fig. 2 can be associated with the intensities due to ~ 40 Au atoms. This value is in close agreement with the core size of glutathionate-protected Au₃₉ clusters used as precursor of the catalysts [4]. Consequently, the evenly spaced peaks in Fig. 2 can be associated with multiples of single clusters, indicating that a substantial fraction of clusters have aggregated by fusion. Although we cannot differentiate at this stage whether the aggregation happened during calcination at 300°C or sample aging at room temperature, the presence of clear integer multiples suggests that the aggregation is not via an Ostwald ripening process. Together with the catalytic and optical measurements [1], the present AC-STEM study suggests that the aggregated clusters are likely to have retained the memory of initial cluster size. The work provides extremely invaluable feedback to control the dispersion and morphology of clusters, typical characteristics crucial to the performance of catalysts of oxide-supported metal catalysis, which is a primary goal of catalyst design.

References

- [1] Y. Liu, H. Tsunoyama, T. Akita, S. Xie, T. Tsukuda, Aerobic Oxidation of Cyclohexane Catalyzed by Size-Controlled Au Clusters on Hydroxyapatite: Size Effect in the Sub-2nm Regime, *ACS Catalysis* 1 (2011) 2-6.
- [2] Z.Y. Li, N.P. Young, M. Di Vece, S. Palomba, R.E. Palmer, A.L. Bleloch, B.C. Curley, R.L. Johnston, J. Jiang, J. Yuan, Three-dimensional Atomic-scale Structure of Size-selected Gold Nanoclusters, *Nature* 451 (2008) 46-48.
- [3] Z. Wang, O. Toikkanen, F. Yin, Z.Y. Li, B.M. Quinn, R.E. Palmer, Counting the atoms in Support, Monolayer-Protected Gold Clusters, *J. Am. Chem. Soc.* 132 (2010) 2854-2855.
- [4] Y. Negishi, K. Nobusada, T. Tsukuda, Glutathione-Protected Gold Clusters Revisited: Bridging the Gap between Gold(I) – Thiolate Complexes and Thiolate-Protected Gold Nanoclusters, *J. Am. Chem. Soc.* 127 (2005) 5261-5270.
- [5] YH and ZYL acknowledge the Engineering and Physical Sciences Research Council (UK) and the Birmingham Science City project (AWM) for support. The work was partially supported by a CREST grant from JST, Japan.

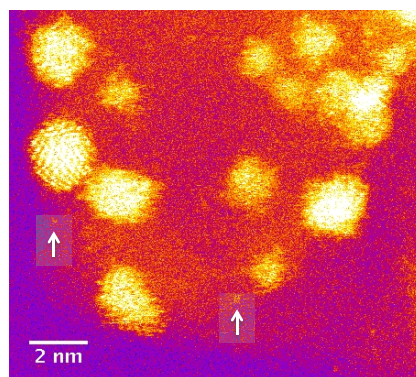


Figure 1. High-resolution STEM image of Au₃₉ clusters on hydroxyapatite, where single Au atoms are visible (two of which are marked by arrows).

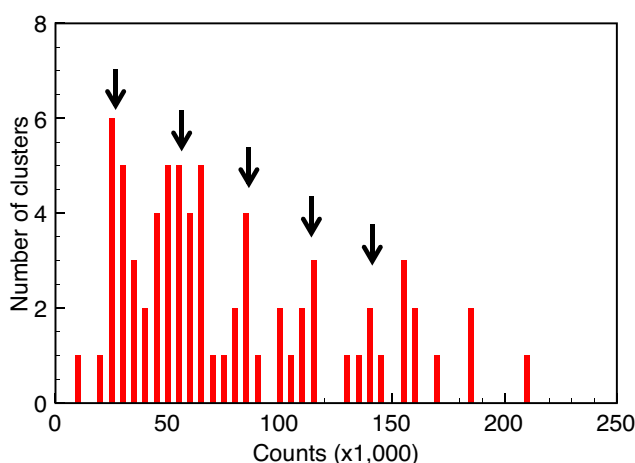


Figure 2. Histogram showing the integrated intensities of the Au₃₉ clusters. The first peak (at ~27,000 count rate) was interpreted to originate from the Au₃₉ monomers. The other peaks occur away from the first peak at a regular basis, due to the presence of a large number of aggregates.

Reproduced with permission of the copyright owner. Further reproduction prohibited without permission.