

UNIVERSITY OF BIRMINGHAM

Research at Birmingham

Pd-Cu-M (M= Y, Ti, Zr, V, Nb, and Ni) alloys for the hydrogen separation membrane

Nayebossadri, Shahrouz; Speight, John; Book, David

DOI:

[10.1021/acsami.6b12752](https://doi.org/10.1021/acsami.6b12752)

License:

None: All rights reserved

Document Version

Peer reviewed version

Citation for published version (Harvard):

Nayebossadri, S, Speight, J & Book, D 2016, 'Pd-Cu-M (M= Y, Ti, Zr, V, Nb, and Ni) alloys for the hydrogen separation membrane', ACS Applied Materials & Interfaces, vol. 9, no. 3, pp. 2650-2661.
<https://doi.org/10.1021/acsami.6b12752>

[Link to publication on Research at Birmingham portal](#)

Publisher Rights Statement:

This document is the unedited Author's version of a Submitted Work that was subsequently accepted for publication in ACS Applied Materials and Interfaces, copyright © American Chemical Society after peer review. To access the final edited and published work see <http://pubs.acs.org/doi/abs/10.1021/acsami.6b12752>

General rights

Unless a licence is specified above, all rights (including copyright and moral rights) in this document are retained by the authors and/or the copyright holders. The express permission of the copyright holder must be obtained for any use of this material other than for purposes permitted by law.

- Users may freely distribute the URL that is used to identify this publication.
- Users may download and/or print one copy of the publication from the University of Birmingham research portal for the purpose of private study or non-commercial research.
- User may use extracts from the document in line with the concept of 'fair dealing' under the Copyright, Designs and Patents Act 1988 (?)
- Users may not further distribute the material nor use it for the purposes of commercial gain.

Where a licence is displayed above, please note the terms and conditions of the licence govern your use of this document.

When citing, please reference the published version.

Take down policy

While the University of Birmingham exercises care and attention in making items available there are rare occasions when an item has been uploaded in error or has been deemed to be commercially or otherwise sensitive.

If you believe that this is the case for this document, please contact UBIRA@lists.bham.ac.uk providing details and we will remove access to the work immediately and investigate.

Article

Pd-Cu-M (M= Y, Ti, Zr, V, Nb, and Ni) alloys for hydrogen separation membrane

Shahrouz Nayeboossadri, John D. Speight, and David Book

ACS Appl. Mater. Interfaces, **Just Accepted Manuscript** • DOI: 10.1021/acsami.6b12752 • Publication Date (Web): 19 Dec 2016Downloaded from <http://pubs.acs.org> on January 13, 2017**Just Accepted**

“Just Accepted” manuscripts have been peer-reviewed and accepted for publication. They are posted online prior to technical editing, formatting for publication and author proofing. The American Chemical Society provides “Just Accepted” as a free service to the research community to expedite the dissemination of scientific material as soon as possible after acceptance. “Just Accepted” manuscripts appear in full in PDF format accompanied by an HTML abstract. “Just Accepted” manuscripts have been fully peer reviewed, but should not be considered the official version of record. They are accessible to all readers and citable by the Digital Object Identifier (DOI®). “Just Accepted” is an optional service offered to authors. Therefore, the “Just Accepted” Web site may not include all articles that will be published in the journal. After a manuscript is technically edited and formatted, it will be removed from the “Just Accepted” Web site and published as an ASAP article. Note that technical editing may introduce minor changes to the manuscript text and/or graphics which could affect content, and all legal disclaimers and ethical guidelines that apply to the journal pertain. ACS cannot be held responsible for errors or consequences arising from the use of information contained in these “Just Accepted” manuscripts.

Pd-Cu-M (M= Y, Ti, Zr, V, Nb, and Ni) alloys for hydrogen separation membrane

Shahrouz Nayebossadri*, John D. Speight, David Book

School of Metallurgy and Materials, University of Birmingham,

Edgbaston, Birmingham, B15 2TT, UK

E-mail: s.nayebossadri@bham.ac.uk

Tel: (+44) (0) 121 414 5213

Abstract

Self-supported fcc Pd-Cu-M (M= Y, Ti, Zr, V, Nb, and Ni) alloys were studied as potential hydrogen purification membranes. The effects of small additions (1–2.6 at.%) of these elements on the structure, hydrogen solubility, diffusivity, and permeability were examined. Structural analyses by XRD showed fcc phase for all alloys with induced textures from cold rolling. Heat treatment at 650 °C for 96 h led to the re-orientation in all alloys except Pd-Cu-Zr alloy, exhibiting the possibility to enhance the structural stability by Zr addition. Hydrogen solubility was almost doubled in the ternary alloys containing Y and Zr compared to Pd_{65.1}Cu_{34.9} alloy at 300 °C. It was noted that hydrogen diffusivity is decreased upon additions of these elements compared to Pd_{65.1}Cu_{34.9} alloy, with Pd-Cu-Zr alloy showing the lowest hydrogen diffusivity. However, the comparable hydrogen permeability of Pd-Cu-Zr alloy with the corresponding binary alloy, as well as its highest hydrogen permeability amongst the studied ternary alloys at temperatures higher than 300 °C suggested that hydrogen permeation of these alloys within the fcc phase is mainly dominated by hydrogen solubility. Hydrogen flux variations of all ternary alloys were studied and compared with Pd_{65.1}Cu_{34.9} alloy under 1000 ppm H₂S+H₂ feed gas. Pd-Cu-Zr alloy showed superior resistant to the sulphur poisoning probably due to the less favourable H₂S-surface interaction and more importantly slower rate of bulk sulfidation as a result of improved structural stability upon Zr addition. Therefore, Pd-Cu-Zr alloys may offer new potential hydrogen purification membranes with improved chemical stability and hydrogen permeation compared to the binary fcc Pd-Cu alloys.

Keywords: Hydrogen separation, Metallic membranes, Pd-based membranes, Pd-Cu,

Ternary alloys

1. Introduction

Amongst Metal-Hydrogen systems, palladium-hydrogen (Pd-H) system is one of the most extensively studied system¹. Hydrogen separating membrane developed based on the dense palladium (Pd) metal offers excellent permeability for hydrogen as a result of the solution-diffusion mechanism². Despite unique ability of palladium to permeate hydrogen, the use of the pure palladium membrane is hindered because the Pd-H system shows two distinct immiscible α (interstitial hydrogen solid solution at temperatures and pressures below 300 °C and 2MPa) and β (palladium hydride) phases. Hydrogenation of Pd results in almost 10% increase in the lattice volume due to the phase transition. The volume increase inevitably creates high levels of stress leading to the structural distortion, deformation and finally membrane failure²⁻⁴. Furthermore, the metallic nature of pure Pd makes it susceptible to surface poisoning by impurity gases⁵⁻⁷. These problems, as well as the high cost of Pd have led to the exploration of a wide variety of Pd-alloy membranes⁸⁻¹⁰.

Amongst these alloys, the lower cost and some tolerance to the surface poisoning as demonstrated by the face centered cubic (fcc) structure of palladium-copper (Pd-Cu thereafter) signifies the importance for further development of this alloy¹¹⁻¹⁹. The permeability of Pd-Cu alloys is significantly depending on the Cu concentration and therefore the structure of the alloy^{11,20}. For example, the reported hydrogen permeability value for the Pd₄₇Cu₅₃ (at.%) alloy at 350 °C¹¹ with a CsCl-type ordered bcc structure²⁰ exceeds than that of pure Pd. High hydrogen permeability in the bcc phase of the Pd-Cu alloy is attributed to almost two times faster hydrogen diffusion in the ordered bcc phase compared to the fcc phase of Pd-Cu alloy at ambient temperature.^{11-12,15}

Nevertheless, hydrogen permeability in the bcc phase of the Pd-Cu alloy is highly sensitive to the gas impurities. It was shown that whilst Pd₄₇Cu₅₃ alloy could easily become impermeable to hydrogen under 1000 ppm H₂S, an increase in the temperature could improve

1
2
3 the alloy's tolerance to the sulphur poisoning as a result of structural transition from bcc to
4 fcc structure^{19,21}. It was shown²² that the complete suppression of hydrogen flux only takes 5
6 minutes after exposing the bcc Pd₄₇Cu₅₃ alloy to 1000 ppm H₂S at 350 °C. The formation of
7 Pd–Cu–S layer on the surface of the Pd₄₇Cu₅₃ alloy was confirmed by X-ray Photoelectron
8 Spectroscopy (XPS) measurement which was suggested to be responsible for rapid decline in
9 the hydrogen flux²². Hydrogen flux at various temperatures through Pd–Cu membranes was
10 also studied when the membranes subjected to different H₂S concentrations²³. Low H₂S
11 concentrations were suggested to block the active surface sites required for hydrogen
12 dissociation, hence reducing the hydrogen flux. However, H₂S concentrations of
13 approximately 300 ppm at 450 °C were shown to trigger the sulfidation process, lattice
14 expansion and consequently permanent failure in the Pd–Cu membranes regardless of the
15 exposure time.
16
17
18
19
20
21
22
23
24
25
26
27
28

29 Pd₇₀Cu₃₀ thin film (~2µm) were also exposed to various H₂S concentrations of 2, 20
30 and 100 ppm at 450 °C and hydrogen flux was substantially reduced in all cases²⁴. The
31 hydrogen flux recovery tests showed that after removal of 2 ppm H₂S the hydrogen flux
32 could be fully recovered to its original value within 2 h. however, only 95 % of the original
33 hydrogen flux value was recovered within 2–3 h and 24 h after removal of 20 and 100 ppm
34 H₂S respectively²⁴. Iyoha et al.²⁵ experimentally investigated sulfidation of Pd₇₀Cu₃₀ alloy at
35 different H₂S to H₂ partial pressures and validated their thermodynamic calculations
36 indicating the required H₂S concentration for the formation of Pd₄S and Cu₂S sulphides
37 within a temperature range of 77 to 977 °C in this alloy. However, SEM and EDS analyses
38 revealed extensive Cu segregation at the surface of Pd–Cu alloys, altering the surface
39 chemical composition, and leading to the formation of non–ideal solid solution in Pd–Cu
40 alloys. Hence, some deviation in the calculated thermodynamic values required for the
41 sulfidation of Pd–Cu alloys was observed. It has been shown⁵ that surface segregation can be
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3 encouraged when the metallic membrane is interacting with the gas species with a high
4 tendency for surface adsorption, *e.g.* sulphur. Consequently, sulfidation may promote surface
5 segregation of some particular elements in the alloy and irreversibly altering the surface
6 structure, surface chemical composition and eventually ceasing hydrogen permeation through
7 the membrane²⁶. Nevertheless, controlled surface segregation of the alloying elements can be
8 useful to alleviate sulfidation. For instance, Pd–Au membranes show a higher resistance to the
9 sulphur poisoning when compared to the other Pd–based membranes^{6,27,28}. It is suggested
10 that a high Au tendency for surface segregation causes a higher Au concentration on the
11 alloy's surface, leading to an increased sulphur tolerance^{29,30}. This promotes the formation of
12 dilute Pd structures less favourable for sulphide phase formation in agreement with the
13 theoretical study indicating that H₂S dissociation is much less favourable on Au rich surfaces
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

In addition, the membrane fabrication method seems to influence the membrane stability in H₂S containing atmosphere. It was shown that²³ electroless-plated Pd–Cu membranes fail at much lower H₂S concentrations when compared to the same cast and rolled membrane. This was attributed to the higher sticking coefficient of sulphur on the rougher surfaces as a result of greater surface area, more intrinsic stress and less uniform alloy composition of thin films compared to the cast and rolled foils. The effect of fabrication method was also investigated by Gade *et al.*²⁷ on the stability of a series of sputtered and cold rolled Pd–Au membranes in H₂S containing atmosphere. Membrane produced by magnetron sputtering underwent an irreversible loss of selectivity but cold worked membranes retained acceptable selectivity. This was related to the pattern of the grain boundaries which were perpendicular to the surface, hence conducting sulphur more deeply into the bulk. The thickness of the sputtered membrane was significantly decreased as a result

1
2
3 of palladium sulphide flake off the feed surface, a process which happened to a less extent for
4
5 the cold worked samples.
6

7 Ternary Pd–Cu–M alloys (M: metallic element) have been theoretically³²⁻³⁴ and
8
9 experimentally³⁵⁻⁴⁰ studied in order to improve the hydrogen permeability and thermal
10
11 stability. Hydrogen permeability showed to be improved after addition of some selected
12
13 metallic elements. However, the effects of these metallic elements were not necessarily
14
15 similar and even could be opposing on the hydrogen solubility and diffusivity of the alloy.
16
17 Recently, we also investigated⁴⁰ structure and hydrogen permeability of Pd–Cu alloys after
18
19 addition of a small amount of Ag. Whilst Ag addition always resulted in a lower diffusion
20
21 coefficient, it could always increase hydrogen solubility in the Pd–Cu–Ag samples compared
22
23 to Pd–Cu alloys. Effects of the Ag additions on the hydrogen permeability of Pd–Cu–Ag
24
25 alloys with bcc and (bcc+fcc) structures were investigated. It was proposed, that is the
26
27 hydrogen diffusion which mostly controls hydrogen permeability in the bcc phase and
28
29 therefore an enhancement in solubility may be only beneficial in improving hydrogen
30
31 permeability when the fcc phase exists.
32
33
34
35

36 It seems that the general approach to increase the hydrogen flux and reduce the cost of
37
38 the fcc Pd–Cu alloys is through fabrication of ternary Pd–Cu thin film alloys. However, the
39
40 desired resistance to surface poisoning needs to be maintained and fortified in the case of Pd–
41
42 Cu thin films. A possible method may be adding elements, which show a preferential
43
44 segregation leading to a less S–surface interaction. However, preferential segregation may be
45
46 detrimental to the long term stability requirement of the membrane, causing degradation in
47
48 the membrane properties similar to the flake off problem observed for Au addition²⁷. Hence,
49
50 in this study we try to stabilise the alloy structure in order to minimise the segregation and
51
52 possibly alleviating the interaction between alloy and sulphur. The effects of selected
53
54 additional elements on the hydrogen solubility, diffusivity, and permeability of the fcc Pd–
55
56
57
58
59
60

1
2
3 Cu–M (M= Y, Ti, Zr, V, Nb, and Ni) alloys are investigated. In addition, the performance of
4
5 these alloys under the hydrogen feed gas atmosphere containing 1000 ppm H₂S are monitored
6
7 and possible effects of additional elements are discussed.
8

9 10 **2. Materials and method**

11 The starting elements, palladium powder with a purity of 99.9985% and copper wire
12
13 (1mm in diameter) with a purity of 99.9% were purchased from Alfa Aesar and Sigma
14
15 Aldrich respectively. Pd–Cu alloy buttons with fcc structure (each weighing approximately
16
17 2.5 g) were prepared by arc melting after loading into a water–cooled copper hearth. A rotary
18
19 pump was used to create a vacuum (approximately 10⁻² mbar) which was then flushed with
20
21 argon three times before being filled with 0.8 bar of argon. The Pd–Cu alloy buttons were
22
23 turned into the foils by cold rolling and then additional elements (Y, Ti, Zr, V, Nb, and Ni)
24
25 were deposited on the foils surface using a Closed Field Unbalanced Magnetron Sputter Ion
26
27 Plating (CFUBMSIP) system supplied by Teer Coatings Ltd. The sputtering chamber was
28
29 evacuated to approximately 10⁻⁶ mbar and refilled with ultra–high purity argon prior to the
30
31 deposition. The target to substrate distance was kept constant and a sample rotation of 5 rpm
32
33 was selected. Concentrations of the additional elements were calculated from the weight gain
34
35 of the samples. Samples were re-melted for 3 times and then cold rolled to foils with the
36
37 aimed thickness of 100 microns. The rolled alloys were heat treated at 650 °C for 96 h under
38
39 vacuum (10⁻⁵ mbar) to ensure the homogeneity of the membranes.
40
41
42
43
44

45 Structural analysis were performed by a Bruker D8–Advanced diffractometer using
46
47 monochromatic CuK α radiation ($\lambda = 1.54056 \text{ \AA}$). Temperature dependence structural analysis
48
49 was performed using an Anton Parr XRK900 high–temperature sample cell. Structural
50
51 evolutions of alloys were monitored under 5 bar flowing hydrogen (100 ml/min) and a
52
53 heating rate of 2 °C min⁻¹. JEOL 6060 Scanning Electron Microscopy (SEM) equipped with
54
55
56
57
58
59
60

1
2
3 an INCA 300 Energy Dispersive Spectroscopy (EDS) was used for compositional analysis
4
5 and thickness measurements.
6

7
8 Hydrogen flux was measured through membrane disks, cut off from the rolled foils
9
10 with an area of 2.54 cm². Membrane disks were cleaned in acetone and mounted in the
11
12 hydrogen permeation system designed and built in the authors group ⁴¹. Membranes sealed
13
14 between a knife-edge and an annealed copper gasket and a leak test was performed under 5
15
16 bar pressure differential using nitrogen gas (99.95%), supplied by BOC. The pressure
17
18 increase in the downstream side of the membrane was monitored by a pressure transducer
19
20 with an accuracy of ±0.25%. All samples were gas tight before starting the experimental
21
22 work as no pressure increase was observed in the downstream side of the membrane after at
23
24 least 2 h. The system was de-gassed under 10⁻⁵ mbar vacuum prior to hydrogen (99.99995%,
25
26 BOC) admittance. The feed gas was controlled using Brooks 5850S Mass Flow Controller
27
28 (MFC) calibrated over a range of 6–600 ml min⁻¹ with an accuracy of ±6 ml min⁻¹. Another
29
30 Brooks 5850S MFC was used on the bleed side ensuring continuous hydrogen flow on the
31
32 upstream side of the membrane. A constant hydrogen pressure of 6.18 was used on the
33
34 upstream side and the downstream pressure was maintained at 1 bar during hydrogen
35
36 permeation measurements using a back pressure regulator followed by a Brooks 5850S MFC
37
38 to measure the permeated gas flow. The membranes temperatures as well as upstream and
39
40 downstream temperatures were increased by a heating rate of 2 °C min⁻¹ using an Elite
41
42 Thermal Systems Ltd. split furnace. The stability of the membranes under gas streams
43
44 containing H₂S were examined by switching the pure hydrogen feed (200 ml min⁻¹) to the
45
46 1000±10 ppm H₂S+H₂ gas mixture at 450 °C purchased from BOC.
47
48
49
50

51
52 Hidden Isochema Intelligent Gravimetric Analyser (IGA) to measure hydrogen solubility
53
54 in foils under a constant hydrogen pressure. The foils surfaces were lightly ground and
55
56 washed in acetone before loading into the IGA. Samples with a weight of approximately
57
58
59
60

1
2
3 100±7 mg were loaded and subjected to the hydrogen pressures of 6.18 and 1 bar to resemble
4
5 the condition used for hydrogen permeation measurements. The weight changes were
6
7 recorded from room temperature to 450 °C hence, enabling to calculate H/M atomic ratios.
8
9 H/M gradients through the thickness of membrane were determined by subtracting H/M
10
11 atomic ratios calculated at 6.18 and 1 bar, similar to the procedure used elsewhere⁴². The
12
13 above procedure has been repeated at least 4 times for each sample to ensure the
14
15 reproducibility of results. Hydrogen concentration gradients were calculated knowing the
16
17 H/M gradients, density, and the molecular weight of the alloys.
18
19

20
21 Fick's first law was used to calculate the hydrogen diffusion coefficients in the foils
22
23 according to the following equation⁴²:
24

$$J = D A \Delta c/x \quad (1)$$

25
26
27
28
29 Where J is hydrogen flux, D is diffusion constant, A is surface area of membrane, Δc
30
31 hydrogen concentration gradient and x is the membrane thickness.
32
33

34 **3. Results**

35 **3.1 Structural and compositional analyses**

36
37
38 Fig. 1 (a–g) shows the XRD patterns of Pd–Cu and Pd–Cu–M alloys after fabrication
39
40 and following vacuum heat treatment at 650 °C for 96 h. All the as–fabricated alloys
41
42 demonstrate a relatively wide XRD patterns belonging to fcc structure. The structural
43
44 similarity in all alloys after fabrication indicate that the presence of a small amount of
45
46 additional elements do not encourage the formation of a new phase in Pd–Cu–M alloys.
47
48 Whilst random orientation of grains in powdered Pd–Cu alloy results in a XRD pattern with a
49
50 highest reflection intensity along (111) plan³⁸, a preferential orientation along the (220) plan
51
52 can be observed for the as–fabricated Pd–Cu alloy in Fig. 1a, possibly due to the cold rolling
53
54 process. Similar preferential orientation along the (220) plan can be observed in the XRD
55
56
57
58
59
60

1
2
3 patterns of the other Pd–Cu–M alloys after fabrication except the ones containing Nb and Y,
4 where preferential orientations along the (111) plane seems to be dominated (Fig 1 b–g). The
5 effects of the vacuum heat treatment at 650 °C for 96 h on the structure of the same samples
6 are shown in in Fig. 1 (h–n). The alloys initial fcc structure seems to remain intact after the
7 heat treatment. However, the XRD patterns of the heat treated alloys become sharper possibly
8 as a result of grain growth and stress relief. A small shoulder at higher 2θ values also seems
9 to appear after annealing the Pd–Cu and ternary alloys containing Y, Nb and Ni probably as a
10 result of compositional inhomogeneity on the top layer of these alloys due to the surface
11 segregation of the alloying elements. Preferential orientations along (111) plane are observed
12 for all the annealed samples, except ternary alloys containing V and Zr, indicating the thermal
13 structural rearrangements of the samples by local atomic diffusion. Interestingly, whilst a new
14 preferential orientation along (200) plan can be seen for Pd–Cu–V alloy (Fig. 1l), Pd–Cu–Zr
15 alloy retains its structure and preferential orientation along the (220) plan (Fig. 1n) after
16 annealing. This may refer to the structural stability of this alloy and minimal local atomic
17 diffusion at the performed annealing condition.

18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36 Atomic compositions of the annealed samples were analysed by EDS, averaging
37 various (at least three readings) area scans ($>10^3 \mu\text{m}^2$) of cross section and the results are
38 listed in Table 1. No significant variations in the composition were observed across the alloys
39 cross section indicating the homogeneity of the alloys (Table S1 in supporting information).
40 EDS analyses further confirms the fcc structure of all alloys as observed by XRD in Fig. 1,
41 giving elemental compositions in the fcc region of the Pd–Cu phase diagram²⁰. The Pd
42 atomic composition (x_{Pd}) in Pd–Cu alloys can be calculated from equation (2) by knowing
43 the fcc lattice constant (a)^{14,16}:

$$a_{\text{fcc}} = 0.36462 + (2.44 \times 10^{-4}) x_{\text{Pd}} \quad (2)$$

1
2
3 Using this method we have calculated the atomic composition for palladium in the Pd–Cu
4 alloy to be $x_{\text{Pd}}=65.5$ at%, which is very close to the value obtained by EDS analysis.

5
6
7 However, it has been noted⁴⁰ that equation (2) is not applicable for the ternary Pd–Cu alloys
8 as it overestimates the Pd content due to the lattice expansion induced by additional elements.
9
10 Hence, in this work alloys compositions from EDS analyses are used to compare the
11
12 properties and performance of the ternary alloys against each other and the Pd–Cu alloys with
13
14 a same Pd content.
15
16
17

18
19 Effects of the additional elements on lattice size can be investigated by comparing
20
21 lattice parameters of the Pd–Cu–M alloys with the previously reported^{14,16,46-48} lattice
22
23 parameters of Pd–Cu alloys plotted in Fig. 2 as a function of Pd concentration. The
24
25 effectiveness of the Ag additions in expanding the lattice parameter of Pd–Cu–Ag alloys has
26
27 been shown by theoretical calculation³⁴ and also experimentally confirmed^{36,40}. It can be
28
29 seen in Fig. 2 that the lattice parameter calculated for our Pd–Cu sample shows an excellent
30
31 agreement with the reported values. Fig. 2 also shows that the lattice parameters of all ternary
32
33 alloys are greater than the binary alloys with a same Pd content except Pd–Cu–Ni alloy,
34
35 which shows almost a similar lattice parameter compared to the binary alloy. The highest
36
37 lattice expansion of 0.31 % is observed by substituting small amounts of Cu for Y in the Pd–
38
39 Cu–Y alloy. This is to be expected, because Y shows the biggest atomic size difference (1.80
40
41 Å) with Cu (1.35 Å), amongst the additional elements used in this study. Here, identical
42
43 lattice parameter with the Pd–Cu alloy can be observed when Cu is replaced by Ni with a
44
45 similar atomic radius. In contrast, the Pd–Cu–V sample shows a lattice expansion of almost
46
47 0.16 % compared to the binary alloy, despite the fact that V has a similar atomic radius to Cu.
48
49 Although the variation in the lattice parameters of the Pd–Cu–M alloys may be mainly
50
51 controlled by the atomic radius of the substitutional atoms for Cu, other factors may also
52
53 contribute to the observed lattice expansions. Size factor anomalies have been reported in the
54
55
56
57
58
59
60

1
2
3 lattice parameters of some α phase Pd alloys⁴⁹. It was noted that despite a very similar
4
5 atomic radius for Th (Thorium) and Y, palladium lattice expanded to a larger extent upon Th
6
7 addition⁵⁰. This effect was attributed to the to the more rapid filling of vacant Pd 4d states by
8
9 the tetravalent Th as compared to trivalent Y. Similarly, the higher lattice expansion observed
10
11 in the case V may originate from its higher effective valence electron (Table 1) as compared
12
13 to Ni.
14
15

16 17 **3.2 Solubility and diffusivity**

18
19 Hydrogen solubility gradients ($\Delta H/M$ atomic ratio) of the annealed binary and ternary
20
21 alloys are shown as a function of temperature in Fig. 3a–g (Table S2 in supporting
22
23 information for hydrogen solubility data points). A common feature of the curves is that they
24
25 all show a small initial increase (maximum) in the range 20–50 °C and a subsequent sharp
26
27 decrease in $\Delta H/M$ upon increasing the temperature to around 100 °C. For all the alloys there
28
29 are only small variations in $\Delta H/M$ from 100 to 450 °C, which hydrogen solubility values
30
31 higher than 300 °C mainly contribute to the hydrogen permeation (will be shown later). Pd–
32
33 Cu alloys with more than 30 at% Cu effectively suppress the α to β phase transition at room
34
35 temperature⁴⁶. Hence, the reported hydrogen solubility values in Fig. 3 should relate to the
36
37 dilute hydrogen solution, *i.e.* α phase. Fig. 3a shows a $\Delta H/M$ value of ~ 0.014 at room
38
39 temperature for Pd_{65.1}Cu_{34.9} sample, which is in a good agreement with the presently reported
40
41 range for dilute hydrogen solution in Pd–Cu alloys^{15, 51, 52}. Whilst, the observed $\Delta H/M$
42
43 maximum at the beginning of heating process can be related to the improved hydrogen
44
45 absorption kinetics and therefore hydrogen saturation in the Pd–Cu and Pd–Cu–M alloys, the
46
47 subsequent sharp decrease observed between 50–100 °C probably originates from an increase
48
49 in the hydrogen absorption equilibrium pressure at higher temperatures. The $\Delta H/M$ value at
50
51 300 °C for the Pd_{65.1}Cu_{34.9} sample is less than half the value observed at room temperature
52
53
54
55
56
57
58
59
60

1
2
3 and shows small fluctuations by increasing temperature to 450 °C. The effects of Ti and Nb
4
5 additions (Fig. 3b–c) on the hydrogen solubility seem to be insignificant when compared to
6
7 the Pd_{65.1}Cu_{34.9} sample at 300 °C. However, increasing temperature to 450 °C leads to the
8
9 lower $\Delta H/M$ values for ternary alloy containing Nb compared to the ternary alloy with Ti and
10
11 Pd_{65.1}Cu_{34.9} sample. Hydrogen solubility value for the ternary alloy with Ni in Fig. 3d is
12
13 almost half the value observed for Pd_{65.1}Cu_{34.9} sample at 300 °C and remains constant upon
14
15 increasing temperature to 450 °C. In Pd–Cu alloys, an increase in the Cu concentration is
16
17 expected to reduce hydrogen solubility^{46,53,54}. Smaller $\Delta H/M$ values of ternary alloys
18
19 containing Ti, Nb and Ni at 300–450 °C temperature range compared to the Pd_{65.1}Cu_{34.9}
20
21 sample may be therefore attributed to their higher Cu concentrations. Nevertheless, none of
22
23 the Ti, Nb and Ni elemental additions shows a significant effect for improving the hydrogen
24
25 solubility. Furthermore, the effect of Ni in reducing the hydrogen solubility by stabilising α
26
27 phase in Pd–Cu–Ni alloys was reported³⁵. This effect is also reflected in our result as the
28
29 ternary alloy containing Ni (Fig. 3d) exhibits the lowest hydrogen solubility compared to the
30
31 ternary alloys containing Ti and Nb. In addition, although the ternary alloy containing V (Fig.
32
33 3e) has a lower Cu content compared to the Pd_{65.1}Cu_{34.9} sample, it shows smaller $\Delta H/M$
34
35 values at temperatures higher than 300 °C. Thus, it can be concluded that V addition also has
36
37 a limiting effect on the hydrogen solubility.

38
39
40
41
42
43
44 Interestingly, additions of Y and Zr seem to significantly increase the hydrogen
45
46 solubility in the ternary alloys (Fig. 3 f and g), despite their higher Cu concentrations
47
48 compared to the Pd_{65.1}Cu_{34.9} alloy. Whilst, the $\Delta H/M$ values for ternary alloys containing Y
49
50 and Zr are about 2 times more than the Pd_{65.1}Cu_{34.9} alloy at room temperature, their $\Delta H/M$
51
52 values show slightly less than 2 order increase in magnitude at 300 °C (Fig.3f–g and Table
53
54 S1). Furthermore, Pd–Cu–Y alloy shows a higher $\Delta H/M$ value at room temperature compared
55
56
57
58
59
60

1
2
3 to Pd–Cu–Zr alloy. However, a higher $\Delta H/M$ value can be seen for the Pd–Cu–Zr alloy at
4
5 temperatures higher than 300 °C compared to the Pd–Cu–Y alloy. Variation of hydrogen
6
7 solubility in Pd–Cu–M (M: additive metal) alloys were also investigated by Density
8
9 Functional Theory (DFT) calculations³² and it was suggested that addition of M (M: Nb, Zr,
10
11 Ti, and V) elements leads to a less favourable hydrogen binding in Octahedral sites (O sites)
12
13 in fcc structure. Our results appears to confirm the DFT calculations in the case of hydrogen
14
15 solubility reduction observed by adding V, Ni and the fact that no appreciable hydrogen
16
17 solubility improvement was achieved by Ti and Nb additions. However, we may suggest Y
18
19 and Zr additions result in a significant improvement in the hydrogen solubility.
20
21
22

23 Hydrogen diffusion coefficients of the Pd–Cu and Pd–Cu–M alloys are shown in Fig.
24
25 4 as a function of reciprocal temperature (Table S3 in supporting information for hydrogen
26
27 diffusion coefficient data points). Hydrogen diffusion coefficient values for the Pd_{65.1}Cu_{34.9}
28
29 alloy vary from 1.9×10^{-5} to 5.7×10^{-5} over the 300 to 450 °C temperature range. These values
30
31 are within the reported range for fcc Pd–Cu alloys^{1, Error! Reference source not found., 55, 57}. All ternary
32
33 alloys show a lower diffusion coefficient compared to the Pd_{65.1}Cu_{34.9} alloy within the studied
34
35 temperature range except Ni, which shows a comparable diffusion coefficient to the
36
37 Pd_{65.1}Cu_{34.9} alloy at 450 °C. Whilst, ternary alloy containing Ni shows the least reduction in
38
39 diffusion coefficient, ternary alloys containing Zr shows the greatest decreases in diffusion
40
41 coefficient compared to the Pd_{65.1}Cu_{34.9} alloy. The correlation between Cu concentration and
42
43 hydrogen diffusivity in fcc Pd–Cu alloys were theoretically investigated^{55, 57} and it was
44
45 shown that hydrogen diffusivity decreases with increasing Cu content. However, this effect is
46
47 temperature dependent as the decrease in the hydrogen diffusivity becomes less significant
48
49 with increasing temperature. Furthermore, room temperature hydrogen diffusivity in Pd–Cu
50
51 alloys was suggested^{Error! Reference source not found.} to be determined by structural transformations
52
53 rather than Cu concentrations either in its bcc or fcc phase. Here, it seems that adding the
54
55
56
57
58
59
60

selected elements reduce the hydrogen diffusivity in the ternary alloys within the studied temperature range. This effect is similar to the previously observed effect of Ag addition for the reduced hydrogen diffusivity in Pd–Cu–Ag alloys⁴⁰. This assumption is further supported by the lower hydrogen diffusion of Pd–Cu–V alloy, despite its lower Cu content compared to the Pd_{65.1}Cu_{34.9} alloy. Also, a noticeable difference between the hydrogen diffusivities of the ternary alloys with a very similar Cu content (ternary alloys containing Ti, Nb, Y, and Zr) suggests different potentials of these elements to restrain the hydrogen diffusivity.

3.3 Hydrogen permeability

It is known that the rate of hydrogen dissociation and recombination on the surface of thick (>10 micron) Pd and Pd alloy membranes is considerably faster when compared to the rate of hydrogen diffusion through the bulk of these membrane⁴. Hence, hydrogen permeability can be determined by equation (3).

$$J = \emptyset \frac{P_1^n - P_2^n}{l} \quad (3)$$

Where J is the hydrogen flux ($\text{mol m}^{-2} \text{s}^{-1}$), \emptyset is hydrogen permeability ($\text{mol m}^{-1} \text{s}^{-1} \text{Pa}^{-0.5}$), P_1 and P_2 are hydrogen pressures (Pa) on the upstream and downstream sides of the membrane respectively, n is pressure exponent, which is 0.5 for bulk diffusion, and l is the membrane thickness (m).

Hydrogen permeability of the alloys studied here are compared with the literature reported hydrogen permeability of the corresponding Pd–Cu alloys at 350 °C^{11,13} in Fig 5. Hydrogen permeability of our Pd_{65.1}Cu_{34.9} alloy shows an excellent match with the reported literature value. Whilst ternary alloys containing Zr and Y show almost similar hydrogen permeability to their corresponding binary alloys, Pd–Cu–Ti alloy seems to have slightly lower hydrogen permeability in comparison to its binary alloy. Ternary alloys containing Ni, Nb, and V also show lower hydrogen permeabilities compared to their binary alloys. In addition, hydrogen permeability measurements of the ternary alloys between 300–500 °C are

1
2
3 shown in Fig. 6a–f (also Table S4 of supporting information). Ternary alloys containing Zr
4
5 and Y show the highest hydrogen permeability within the studied temperature range
6
7 respectively, despite their inferior hydrogen diffusivity values amongst the ternary alloys
8
9 (Fig. 4). On the other hand, whilst Pd–Cu–Ni alloy showed the highest hydrogen diffusivity
10
11 value (Fig. 4) compared to the other ternary alloys, its hydrogen permeability in Fig. 6c is
12
13 lower than that of ternary alloys containing Zr and Y, which may be as a result of the marked
14
15 effect of Ni in reducing the hydrogen solubility (Fig 3d). Thus, it seems that variations in the
16
17 hydrogen permeabilities of the studied ternary alloys are mainly dominated by the variations
18
19 of the hydrogen solubility rather than diffusivity. It was previously shown that whilst
20
21 hydrogen solubility enhancement in the fcc Pd–Cu alloys could significantly improve the
22
23 hydrogen permeation, variation in the hydrogen diffusivity had a less significant effect on the
24
25 overall hydrogen permeation⁴⁰. Similar effects are observed here (Fig. 5 and Fig.6) where
26
27 ternary alloys containing Zr and Y, with the highest hydrogen solubilities amongst the ternary
28
29 alloys studied, showed comparable hydrogen permeabilities to their corresponding binary
30
31 alloys and higher hydrogen permeabilities than the other ternary alloys despite their lowest
32
33 hydrogen diffusivity. Nevertheless, it has been noted that the contribution of bulk diffusion
34
35 processes can be minimised by reducing the thickness of the membrane to less than 10 μm ⁴.
36
37 It has also been reported that³⁸ hydrogen permeability in thin film ($\sim 2 \mu\text{m}$) Pd₇₃Cu₂₆Y₁ alloy
38
39 could be increased by as much as 45% compared to corresponding Pd–Cu binary alloy. Thus,
40
41 the significant enhancements in the hydrogen solubility achieved by Zr and Y suggest these
42
43 elements are effective alloying elements to improve hydrogen permeability in the fcc phase
44
45 of Pd–Cu alloys, providing that the contribution of the bulk diffusion could be minimised by
46
47 a thickness reduction of the membrane.
48
49
50
51
52
53
54
55
56
57
58
59
60

3.4 Membrane poisoning by H₂S

Figure 7 shows the relative hydrogen flux of the studied membranes after switching pure hydrogen feed gas to H₂+1000 ppm H₂S gas mixture at 450 °C after completing hydrogen permeation measurements. Pd–Cu–Ni alloy shows inferior stability under H₂S containing atmosphere as the minimum hydrogen flux observed after 6 h is suppressed upon 8 h of H₂S exposure. Pd–Cu–V alloy shows only slightly better stability compared to Pd–Cu–Ni alloy with a slower rate of hydrogen flux reduction. Ternary alloys containing Ti, Y, and Nb show almost a similar stability compared to the Pd_{65.1}Cu_{34.9} alloy. Interestingly, Pd–Cu–Zr alloy shows a noticeable stability improvement in comparison with the Pd_{65.1}Cu_{34.9} alloy. Whilst the relative hydrogen flux through Pd_{65.1}Cu_{34.9} and ternary alloys containing Ti, Y, and Nb is halved by falling to 50% of its original value after 8 h of H₂S exposure, the relative hydrogen flux in Pd–Cu–Zr alloy only falls to 65% of its original value. In addition, hydrogen flux is only reduced to less than 10% after 3 h of H₂S exposure in Pd_{65.1}Cu_{34.9} and ternary alloys containing Ti, Y, Nb, and Zr, whereas ternary alloys containing Ni and V show instant hydrogen flux reductions. Reduction in the surface catalytic activity of Pd in Pd–based membranes, as a result of sulphur adsorption on the surface, is known^{59,6} to be the responsible mechanism for initial decay in hydrogen flux after starting H₂S exposure. Nevertheless, hydrogen flux only ceases after the subsequent growth of surface sulphides and bulk sulfidation of the membrane. Hence, the minimal reduction in hydrogen flux observed in Pd_{65.1}Cu_{34.9} and ternary alloys containing Ti, Y, Nb, and Zr up to 3 h of H₂S exposure may be related to the limited hydrogen dissociation on the membranes surface. Additionally, the formation and growth of less hydrogen permeable sulphides⁵⁹ is probably the dominant mechanism for higher rate of hydrogen reduction and its complete suppression at prolonged H₂S exposure. On the other hand, ternary alloys containing V and Ni seem more prone to S–surface interaction leading to the enhanced blocking of catalytic active sites for hydrogen

dissociation as well as formation and growth of sulphide phases. The dependency of sulfidation process in Pd–Cu alloys to the H₂S:H₂ ratio and the operation temperature has been previously shown^{23,25}. The high concentration of H₂S in our feed gas satisfies the thermodynamic requirement²⁵ for sulfidation in all the studied Pd–Cu alloys. XRD patterns in Fig. 8a–g show the structure of the alloys after H₂S exposure. All samples show the formation of Pd₄S/Cu₂S sulphides after H₂S exposure. Whilst formation of Pd₄S phase as a dominant phase is thermodynamically predicted²⁵ at the current experimental condition, Fig. 8a–g shows that Pd₄S is not the main sulphide phase. Studies^{23,25} show a high affinity of Cu to sulphur may lead to Cu segregation in H₂S exposed Pd–Cu alloys, drifting the alloy composition from ideal solid solution. Similarly, Cu₂S seems to be the dominant sulphide phase in all our H₂S exposed alloys. Cu segregation toward the surface of the alloys also leads to the formation Cu rich Cu–Pd (Cu–Ti in Pd–Cu–Ti alloy) phases. Nevertheless, Pd–Cu–Zr alloy seems to be more resistant to the Cu segregation and therefore sulfidation as a result of its structural stability. Interestingly, Fig. 8g shows Pd–Cu–Zr alloy preserves its texture along (220) plane after H₂S exposure, further reflecting the structural stability of this alloy. The structural stability of this alloy can significantly slow down the Cu segregation throughout H₂S exposure which seems to have a primary role on alloys sulfidation. Overall, a small amount of Zr in Pd–Cu–Zr alloy may effectively induce structural stability as reflected by stable (220) texture and sluggish sulfidation kinetic.

4 Discussion

The effects of elemental Ag addition on the hydrogen diffusivity and solubility of fcc and bcc Pd–Cu alloys were extensively investigated in our previous report⁴⁰ using theoretical studies considering hydrogen diffusivity and solubility mechanisms in bcc and fcc alloys^{32-34,48}. Unlike the identical effects of additional elements used in this study for decreasing hydrogen diffusivity, their effects on hydrogen solubility seem to be more complex.

1
2
3 It is known that hydrogen atoms can occupy either Octahedral (O site), or Tetrahedral
4 (T site) site in the disordered fcc Pd–Cu alloys. At high temperatures, hydrogen diffuses by
5 hopping through various O and T sites after overcoming a Transition State (TS) energy
6 barrier^{33,48}. The disordered nature of the fcc phase implies the existence of various
7 energetically distinct sites with varying diffusion activation energies. Thus, hydrogen
8 diffusion is controlled by both binding energies and the transitions state energies for
9 individual hops^{34,48}. DFT calculations show³⁴ that replacing a small amount of Ag for Cu in
10 Pd–Cu fcc phase results in more favourable hydrogen bonding in interstitial sites. In addition,
11 TS energy for an alloy is not constant but, rather determines by the alloy's composition at
12 near atomic neighbour level⁵⁸. This was theoretically shown³⁴ to be true in Pd–Cu–Ag alloys
13 by observation of a higher activation energy barrier for hydrogen hopping through TS having
14 one or more Ag atoms. Furthermore, TS energy can be influenced by lattice size variation as
15 a consequence of alloying⁵¹. Whilst expanded lattice is suggested to reduce the activation
16 energy, *i.e.* an increase in the rate of hydrogen hopping, the reverse is true for lattice
17 contraction. However, despite the observed lattice expansions for the Pd–Cu–Ag alloys lower
18 hydrogen diffusivity values were constantly observed at high temperatures compared to
19 binary alloys⁴⁰, which may indicate a minimal effect of lattice expansion on the overall
20 hydrogen diffusivity in such a ternary alloy. Also, it was suggested⁵¹ that alloying with
21 additional elements having a larger atomic size compared to the alloys constituent elements
22 can increase T site energy and therefore encouraging direct hydrogen hopping between two O
23 sites. Therefore, reductions in hydrogen diffusivities observed in Fig. 4 may be attributed to
24 the influence of alloying elements on ease of hydrogen hopping and its preferred route by
25 affecting O sites, T sites and TS energies as a result of altering local atomic compositions.
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52

53 The dependence of hydrogen solubility on lattice size in Pd–alloys have been reported
54
55
56^{33,38}. For example, isoelectronic Pd–Y₈ and Pd–Ag₂₄ alloys show higher hydrogen solubility
57
58
59
60

1
2
3 than pure Pd where their lattice size is 29% and 5% larger than pure Pd respectively ⁴². In
4
5 addition, similar improvement in hydrogen solubility was theoretically predicted due to the
6
7 lattice expansion in Pd–Cu–Ag alloys ³⁴. However, it is known that changes in hydrogen
8
9 solubility cannot be described solely based on the variation in lattice size ^{34,40}. Subsequently,
10
11 other factors such as the accessibility of free atomic sites for hydrogen occupancy ^{34,60},
12
13 chemical potential of alloys–hydrogen system ⁴⁴ and the effect of solute valence electrons
14
15 ^{49,50,61} were envisaged to play an important role for hydrogen solubility. For example, it was
16
17 suggested that ⁶⁰ increasing alloying atoms in the nearest neighbours (NN) favours hydrogen
18
19 absorption only up to a certain extent that is 50% of total capacity of NN. This was further
20
21 confirmed ³⁴ in Pd–Cu–Ag alloys where an increase in Ag content led to less favourable
22
23 binding energies of hydrogen in O sites. The existence of more Ag in NN shell of the
24
25 interstitial site in Pd–Cu–Ag alloy could limit the accessibility of the free inferential space for
26
27 hydrogen occupation. Furthermore a stronger interaction between alloys and hydrogen is
28
29 known to encourage hydrogen solubility in Pd alloys ⁴⁴. This can be translates into the
30
31 chemical potential of alloy–hydrogen system depending on ionic diameter and interaction
32
33 free energy of hydrogen–solute metal pair. Finally, the electronic effect of additional
34
35 elements on the hydrogen solubility was assumed to be mainly dominated by solute valence
36
37 electrons as hydrogen solubility decreased once more Pd 4d-bands were occupied in spite of
38
39 additional lattice expansion ^{49,50,61}. Additionally, small changes in alloys charge density
40
41 which is a function of atomic size of alloying elements and their and electronegativity, may
42
43 have an impact on the stability of hydrogen in different interstitial sites ⁶².
44
45
46
47
48

49
50 In this study, low concentrations of additional elements were chosen with the purpose
51
52 of minimising their limiting effects on the accessibility of free interstitial sites for hydrogen
53
54 occupation. Atomic radius, effective valence, and enthalpy of hydride formation for
55
56 additional elements in this study (Y, Ti, Zr, V, Nb, and Ni) are listed in Table 1. If the
57
58
59
60

1
2
3 observed hydrogen solubility values for Pd–Cu–Zr sample at temperatures higher than 100
4
5 °C is excluded (which will be discussed later), the Pd–Cu–Y alloy shows the highest
6
7 hydrogen solubility values. It can be seen in Table 1 that yttrium best matches the
8
9 requirements for improved hydrogen solubility, having the largest atomic radius, the lowest
10
11 valence electron and highest affinity to hydrogen compared to other additional elements.
12
13 Similarly, Ni shows significant reduction in hydrogen solubility because of its minimal effect
14
15 for lattice expansion, higher valence electron compared to Cu and least interaction with
16
17 hydrogen. In general, it seems that the effects of these elements (except Zr) can be relatively
18
19 described by their ability to fulfil the mentioned requirements for improving hydrogen
20
21 solubility.
22
23
24

25 Lower hydrogen solubility values at temperatures below 100 °C can be observed for
26
27 Pd–Cu–Zr sample when compared to the ternary alloy containing Y with almost identical Pd
28
29 and Cu contents. This may be expected from smaller lattice expansion achieved by Zr
30
31 addition, its higher effective valence and less interaction with hydrogen compared to Y.
32
33 However, once the temperature is increased above 100 °C, Pd–Cu–Zr sample shows higher
34
35 hydrogen solubility values. Higher hydrogen solubility values of Pd–Cu–Zr versus Pd–Cu–Y
36
37 sample at higher temperatures may be explained by the contribution of other factors
38
39 influencing the overall hydrogen solubility. For instance, it is known that ^{63,64} an increase in
40
41 the defect density within the microstructure can substantially enhance hydrogen solubility
42
43 due to the trapping effect. Dislocations, point defects, and precipitate-matrix areas, which are
44
45 introduced into the microstructure by various techniques such as plastic deformation and heat
46
47 treatment, can significantly increase hydrogen solubility, although these features are
48
49 detrimental to diffusivity. Dilute additions of Zr in a pure aluminium matrix have been shown
50
51 ⁶⁵ to improve the thermal stability and retention of small grains of the sample up to
52
53 temperatures higher than 300 °C. Also, solution hardening and consequent thermal cyclic
54
55
56
57
58
59
60

1
2
3 stability was reported in Cu–Zr alloys⁶⁶. Minute solubility of Zr in Cu led to precipitation,
4
5 which could effectively stabilise the microstructure. Similarly, structural stabilisation was
6
7 observed in our Pd–Cu–Zr sample after heat treating under vacuum (Fig. 1n) and under H₂S
8
9 containing atmosphere (Fig. 8g). In addition, we have investigated the structural stability of
10
11 Pd–Cu–Zr sample under hydrogen atmosphere at various temperatures in Fig. 9. It can be
12
13 seen that Pd–Cu–Zr sample retains its (220) texture up to temperatures as high as 600 °C,
14
15 which implies to microstructural stability of the sample. Hence, the greater stability of
16
17 hydrogen solution at higher temperatures in the Pd–Cu–Zr sample could be due to the
18
19 trapping of a proportion of the hydrogen atoms by lattice defects induced by cold rolling.
20
21

22
23 Chemical composition (surface reactivity) and electronic structure of Pd–based
24
25 membranes can be altered by alloying^{7,31,67}. Hence, alloying can have a notable effect on the
26
27 performance of the membrane under impurity gases. For instance, whilst Pd has a stronger
28
29 interaction with S compared to Cu, weaker S absorption energies are in general observed on
30
31 the Pd–Cu alloys surfaces⁵. Alloying effect in Pd–Cu alloys was also studied by Ling *et al.*⁶⁸
32
33 and binding sites were shown to be spatially heterogeneous in Pd₇₅Cu₂₅ alloy when compared
34
35 to pure Pd. Although these binding sites share a similar geometry, the atomic composition
36
37 varies locally. In addition, electronic structure of Pd and Pd alloys may have a substantial
38
39 effect on the S–surface interaction^{5,7,31}. Pd–Cu–Zr alloy with the preserved (220) texture may
40
41 possess a different surface atomic composition as a result of Zr addition. Thus, S–surface
42
43 interaction may become less favourable in this alloy as Zr addition can potentially create new
44
45 binding sites on the surface with distinctive binding energies. Moreover, the structural
46
47 stability of Pd–Cu–Zr alloy may also improve resistance to sulphur poisoning by reducing the
48
49 elemental segregation under H₂S containing atmosphere. We may suggest that limited atomic
50
51 diffusivity of Pd and especially Cu in Pd–Cu–Zr alloy can significantly retard the surface and
52
53 bulk sulfidation kinetic in this alloy.
54
55
56
57
58
59
60

1
2
3 In general, it seems that the structural stabilisation induced by adding a third element
4 is a useful strategy for designing novel Pd–Cu–M (M: additional element) membranes with
5 improved H₂S resistance. However, elemental alloying additions should also satisfy the
6 requirements for improved hydrogen permeation through the membrane. We recently
7 reported the improved resistance of Pd–Cu–Zr alloy to the sulphur poisoning⁶⁹. The present
8 work suggests the effects of Zr addition on the structure, surface properties and thermal
9 stability of both bcc and fcc Pd–Cu alloys need to be further investigated and optimised.

18 5. Conclusions

20 Pd–Cu–M (M= Y, Ti, Zr, V, Nb, and Ni) alloys with a small amount (1–2.6 at.%) of
21 M elements were investigated as potential hydrogen purification membranes. Structural
22 analyses by XRD suggested Zr addition improves structural stability in Pd–Cu–Zr alloy,
23 leading to the preserved surface texture (induced by cold rolling) after heat treatment at 650
24 °C for 96 h. The greatest lattice expansion was observed with Y addition, which could be
25 explained by its bigger atomic size compared to Cu. However, variations in the lattice
26 parameters upon addition of Ni and V with a similar atomic size to Cu suggested possible
27 contributions from the solute valence electrons to the lattice size. Hydrogen solubilities of the
28 ternary alloys were measured and significant increase in the hydrogen solubility values were
29 noted for the ternary alloys containing Y and Zr. Whilst, V and Ni seemed to reduce the
30 hydrogen solubility, no significant effect on the hydrogen solubility was observed by Ti and
31 Nb additions. The effects of small additions of third elements on the hydrogen solubility
32 seemed to be related to a combination of their atomic size, valence electron and their affinity
33 to hydrogen, except for the Pd–Cu–Zr sample. Higher hydrogen solubility observed at
34 temperatures above 100 °C for Pd–Cu–Zr sample, when compared to Pd–Cu–Y, was
35 attributed to the hydrogen trapping by relatively stable defective sites as a result of structural
36 stability induced by Zr addition. Furthermore, additions of all the alloying elements decreased
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3 the hydrogen diffusivity by increasing the required energy for hydrogen hopping within the
4
5 bulk of the samples with Zr having the greatest and Ni showing the least effect. The
6
7 comparable hydrogen permeabilities of ternary alloys containing Zr and Y to the respecting
8
9 binary alloys despite their reduced hydrogen diffusivity, further confirmed that hydrogen
10
11 permeability in fcc phase of Pd–Cu alloys is mainly dominated by hydrogen solubility. A
12
13 superior resistance to sulphur poisoning was observed for the Pd–Cu–Zr alloy when exposed
14
15 to 1000 ppm H₂S+H₂ gas mixture. This was attributed to the preserved texture and changes to
16
17 the alloy electronic structure as a result of a small Zr addition. Nevertheless, we may propose
18
19 that the structural stability of Pd–Cu–Zr alloy plays a key role for improving the alloy
20
21 resistance to sulphur poisoning by limiting the atomic diffusion and segregation of Pd and Cu
22
23 elements, slowing surface and bulk sulfidation kinetic.
24
25
26

27 **Supporting Information**

28
29 Cross sectional EDS analyses of annealed alloy, hydrogen solubility values of
30
31 Pd_{65.1}Cu_{34.9} and ternary Pd–Cu–M alloys, hydrogen diffusivity values of Pd_{65.1}Cu_{34.9} and
32
33 ternary Pd–Cu–M alloys, hydrogen permeability values of Pd_{65.1}Cu_{34.9} and ternary Pd–Cu–M
34
35 alloys
36
37
38

39 **Acknowledgments**

40
41 Supports from the EPSRC SUPERGEN Delivery of Sustainable Hydrogen
42
43 (EP/G01244X/1), the Birmingham Science City Hydrogen Energy projects and the Hydrogen
44
45 and Fuel Cell Research Hub are gratefully acknowledged.
46
47
48

49 **References:**

- 50
51 1. Alefeld, G.; Völkl, J.; (Eds.) Hydrogen in Metals I and II, Springer-Verlag, Berlin,
52 1978.
53 2. Dittmeyer, R.; Höllein, V.; Duab, K. Membrane Reactors for Hydrogenation and
54 Dehydrogenation Processes Based on Supported Palladium J. Mol. Catal. A: Chem.
55 2001, 173, 135-184
56 3. Knapton, A.G. Palladium Alloys for Hydrogen Diffusion Membranes Platinum Met.
57 Rev. 1977, 21, 2, , 44-50
58
59
60

4. Yun, S.; Oyama, S. T.; Correlation in Palladium Membranes for Hydrogen Separation: A review *J. Membr. Sci.* 2011, 375, 28-45
5. Alfonso, D. R.; Cugini, A. V.; Sholl, D. S. Density Functional Theory Studies of Sulphur Binding on Pd, Cu and Ag and Their Alloys *Surf. Sci.* 2003, 546, 12-26
6. Gabitto, J. F.; Tsouris, C. Sulphur Poisoning of Metal Membranes for Hydrogen Separation *IRECHE* 2009,1, 5, 394-411
7. Ozdogan, E.; Wilcox, J. Investigation of H₂ and H₂S Adsorption on Niobium- and Copper Doped Palladium Surfaces *J. Phys. Chem. B* 2010, 114, 12851-12858
8. Paglieri, S.N.; Way, J.D. Innovation in Palladium Membrane Research *Sep. Purif. Methods* 2002, 31, 1, 1-169
9. Basile, A.; Gallucci, F.; Tosti, S. Synthesis, Characterisation, and Application of Palladium Membranes *Membr. Sci. Technol.* 2008, 13, 255-323
10. Gallucci, F.; Fernandez, E.; Corengia, P.; Annaland, M. V. S. Recent Advances on Membrane Reactors for Hydrogen Production *Chem. Eng. Sci.* 2013, 92, 40-66
11. . McKinley, D. L. Methods for Hydrogen Separation and Purification US patent 1969, 3,439,474
12. Roa, F.; Block, M. J.; Way, J. D. The Influence of Alloy Composition on the H₂ flux of Composite Pd-Cu Membranes *Desalination* 2002,147 , 411-416
13. Howard, B. H.; Killmeyer, R. P.; Rothenberger, K. S; Cugini, A.V.; Morreale, B. D.; Enick, R. M.; Bustamante, F. Hydrogen Permeance of Palladium-Copper Alloy Membranes Over a Wide Range of Temperatures and Pressures *J. Membr. Sci.* 2004, 241, 207-218
14. Yuan, L.; Goldbach, A.; Xu, H. Segregation and H₂ Transport Rate Control in Body-Centered Cubic PdCu Membranes *J. Phys. Chem. B* 2007, 111, 10952-10958
15. Opalka, S. M.; Huang, W.; Wang, D.; Flanagan, T.B.; LØvvik, O.M.; Emerson, S.C.; She, Y.; Vanderspurt, T. H. Hydrogen Interaction with the PdCu Ordered B2 alloy *J. Alloys Compd.* 2007, 44-447, 583-587
16. Yuan, L.; Goldbach, A.; Xu, H. Real-Time Monitoring of Metal Deposition and Segregation Phenomena During Preparation of PdCu Membranes *J. Membr. Sci.* 2008, 322, 39-45
17. Yuan, L.; Goldbach, A.; Xu, H. Permeation Hysteresis in PdCu Membranes *J. Phys. Chem. B* 2008,112, 12692-12695
18. Goldbach, A.; Yuan, L.; Xu, H. Impact of the fcc/bcc Phase Transition on the Homogeneity and Behavior of PdCu Membranes *Sep. Purif. Technol.* 2010,73, 65-70
19. Morreale, B. D.; Ciocco, M. V.; Howard, B. H.; Killmeyer, R. P.; Cugini, A. V.; Enick, R. M. Effect of Hydrogen-Sulfide on the Hydrogen Permeance of Palladium-Copper Alloys at Elevated Temperatures *J. Membr. Sci.* 2004, 241, 219-224
20. Subramanian, P.R.; Laughlin, D.E. Cu-Pd (Copper-Palladium) *J. Phase Equilib.* 1991, 12, 2, 231-243 piper
21. Kamakoti, P.; Morreale, B. D.; Ciocco, M.V.; Howard, B.H.; Killmeyer, R.T. Cugini, A.V.; Sholl, D.S. Prediction of Hydrogen Flux Through Sulphur-Tolerant Binary Alloy Membrane *Science* 2005, 307, 569-573
22. O'Brien, C P.; Howard, B. H.; Miller, J. B.; Morreale, B. D. Gellman, A. J. Inhibition of Hydrogen Transport Through Pd and Pd₄₇Cu₅₃ Membranes by H₂S at 350 °C *J. Membr. Sci.* 2010, 349, 380-384
23. Kulprathipanja, A.; Alptekin, G.O.; Falconer, J.L.; Way, J.D. Pd and Pd-Cu Membrane: Inhibition of H₂ Permeation by H₂S *J. Membr. Sci.* 2005, 254, 49-62
24. Peters, T.A.; Kaleta, T.; Stange, M. Bredesen, R. Hydrogen Transport through a Selection of Thin Pd-Alloy Membranes: Membrane Stability, H₂S Inhibition, and

- 1
2
3 Flux Recovery in Hydrogen and Simulated WGS Mixtures Catal. Today 2012, 193, 8-
4 19
- 5 25. Iyoha, O.; Enick, R.; Killmeyer, R.; Morreale, B. The Influence of Hydrogen Sulphide
6 to Hydrogen Partial Pressure Ratio on the Sulfidization of Pd and 70 mol% Pd-Cu
7 Membranes J. Membr. Sci. 2007, 305, 77-92
- 8 26. Opalka, S. M.; Løvvik, O. M.; Emerson, S. C.; She, Y.; Vanderspurt, T. H.
9 Electronic Origins for Sulphur Interactions with Palladium Alloys for Hydrogen-
10 Selective Membranes J. Membr. Sci. 2011, 375, 96-103
- 11 27. Gade, S. K.; DeVoss, S. J.; Coulter, K. E.; Paglieri, S. N.; Alptekin, G. O.; Way, J. D.
12 Palladium-Gold Membranes in Mixed Gas Streams with Hydrogen Sulphide: Effect
13 of Alloy Content and Fabrication Technique J. Membr. Sci. 2010, 378, 35-41
- 14 28. Chen, C. H.; Ma, Y. H. The Effects of H₂S on the Performance of the Pd and Pd/Au
15 Composite Membrane J. Membr. Sci. 2010, 362, 535-544
- 16 29. Braun, F.; Miller, J. B.; Gellman, A. J.; Traditi, A. M.; Fleutot, B.; Kondratyuk, P.;
17 Cornaglia, L.M. PdAgAu Alloy with High Resistance to Corrosion by H₂S Int. J.
18 Hydrogen Energy 2012, 37, 18547-18555
- 19 30. Venezia, A. M.; La Parola, V.; Nicoli, V.; Deganello, G. Effect of Gold on the HDS
20 Activity of Supported Palladium Catalysts J. Catal. 2002, 212, 56-62
- 21 31. Hyman, M. P.; Loveless, B. T.; Medlin, J. W. A Density Functional Theory Study of
22 H₂S Decomposition on the (111) Surfaces of Model Pd-Alloys Surf. Sci. 2007, 601,
23 5382-5393
- 24 32. Kamakoti, P.; Sholl, D.S. Towards First Principles-Based Identification of Ternary
25 Alloys for Hydrogen Purification Methods J. Membr. Sci. 2006, 279, 94-99
- 26 33. Semidey-Flecha, L.; Ling, C.; Sholl, D.S. Detailed First Principles Models of
27 Hydrogen Permeation Through PdCu-Based Ternary Alloys J. Membr. Sci. 2010,
28 362, 384-392
- 29 34. Ling, C.; Semidey-Flecha, L.; Sholl, D. S. First Principles Screening of PdCuAg
30 Ternary Alloys as H₂ Purification Membranes J. Membr. Sci. 2011, 371, 189-196
- 31 35. Ryi, S. K.; Park, J. S.; Kim, S. H.; Kim, D. W.; Moon, J. W. Long Term Hydrogen
32 Permeation Tests of Pd-Cu-Ni/PNS with Temperature Cycles from Room
33 Temperature to 773K J. Membr. Sci. 2007, 306, 261-266
- 34 36. Tarditi, A. M.; Braun, F.; Cornaglia, L. M. Novel PdAgCu Ternary Alloys: Hydrogen
35 Permeation and Surface Properties. Appl. Surf. Sci. 2011, 257, 6626
- 36 37. Tarditi, A. M.; Cornaglia, L. M. Novel PdAgCu Ternary Alloys as Promising
37 Materials for Hydrogen Separation Membranes: Synthesis and Characterisation Surf.
38 Sci. 2011, 605, 62-71
- 39 38. Peters, T. A.; Kaleta, T.; Stange, M.; Bredesen, R. Development of Thin Binary and
40 Ternary Pd-Based Alloys Membranes for Use in Hydrogen Production J. Membr. Sci.
41 2011, 383, 124-134
- 42 39. Dogan, Ö. N.; Hu, R.; Song, X.; Chen, S.; Gao, M. C. Ordered Bcc Phases in a Cu-
43 Pd-Mg Hydrogen Separation Membrane Alloy J. Alloys Compd. 2012, 528, 10-15
- 44 40. Nayebossadri, S.; Speight, J.; Book, D. Effects of Low Ag Additions on the Hydrogen
45 Permeability of Pd-Cu-Ag Hydrogen Separation Membranes J. Membr. Sci. 2014,
46 451, 216-225
- 47 41. Fletcher, S. Thin-Film Palladium-Yttrium Membranes for Hydrogen Separation. PhD
48 thesis, University of Birmingham, 2009
- 49 42. Hughes, D. T.; Harris, I. R. A Comparative Study of Hydrogen Permeabilities and
50 Solubilities in Some Palladium Solid Solution Alloys J. Less-Common Met. 1978, 61,
51 P9-P21
- 52 43. Slater, J. C. Atomic Radii in Crystals J. Chem. Phys. 1964, 41, 3199-3204
- 53
54
55
56
57
58
59
60

- 1
 - 2
 - 3
 - 4
 - 5
 - 6
 - 7
 - 8
 - 9
 - 10
 - 11
 - 12
 - 13
 - 14
 - 15
 - 16
 - 17
 - 18
 - 19
 - 20
 - 21
 - 22
 - 23
 - 24
 - 25
 - 26
 - 27
 - 28
 - 29
 - 30
 - 31
 - 32
 - 33
 - 34
 - 35
 - 36
 - 37
 - 38
 - 39
 - 40
 - 41
 - 42
 - 43
 - 44
 - 45
 - 46
 - 47
 - 48
 - 49
 - 50
 - 51
 - 52
 - 53
 - 54
 - 55
 - 56
 - 57
 - 58
 - 59
 - 60
44. Ramaprabhu, S. Thermodynamics and Stability of Dissolved Hydrogenation in Pd Rich Binary Pd_{1-x}Z_x and Ternary Pd_{1-x}Z_xZ'_y Solid Solution Alloys Int. J. Hydrogen Energy 1998, 23, 9, 787-795
45. Wang, Y.B.; Northwood, D. O. Calculation of the Enthalpy of Metal Hydride Formation J. Less-Common Met. 1987, 135, 239-245
46. Burch, R.; Buss, R.G. Absorption of Hydrogen by Palladium-Copper Alloys J. Chem. Soc., Faraday Trans. 1975, 1, 71, 913-921
47. Fisher, D., Chisdes, D.M.; Flanagan, T. B. Solution of Hydrogen in Palladium/Copper Alloys. J. Solid State Chem. 1977, 20, 149-158
48. Kamakoti, P.; Sholl, D.S.; A Comparison of Hydrogen Diffusivities in Pd and CuPd Alloys Using Density Functional Theory J. Membr. Sci. 2003, 225, 145-154
49. Harris, I. R.; Norman, M. Observation on the Lattice Spacing of some α Pd-X Solid Solutions and some Pd₃X Phases J. Less-Common Met. 1970, 22, 127-130
50. Doyle, M. L.; Harris, I. R. Palladium–Rare Earth Alloys: Their Order-Disorder Transformations and Behaviour with Hydrogen Platinum Met. Rev. 1988, 32, 3, 130-140
51. Semidey-Flecha, L.; Sholl, D. S. Combining Density Functional Theory and Cluster Expansion Methods to Predict H₂ Permeance Through Pd-Based Binary Alloy Membranes J. Chem. Phys. 2008, 128, 144701-144710
52. Martin, M. H.; Galipaud, J.; Tranchot, A.; Roué, L.; Guay, D. Measurements of Hydrogen Solubility in CxPd100-x Thin Films, Electrochim Acta 2013, 90, 615-622
53. Burch, R.; Buss, R. G. Pressure Composition Isotherms in the Palladium–Copper–Hydrogen System Solid State Commun. 1974, 15, 407-409
54. Flanagan T. B.; Chisdes, D. M. Solubility of Hydrogen (1 atm, 298 K) in some Copper/Palladium Alloys Solid State Commun. 1975, 16, 529-532
55. Kamakoti, P.; Sholl, S. Ab Initio Lattice-Gas Modelling of Interstitial Hydrogen Diffusion in CuPd Alloys Phys. Rev. B 2005, 71, 14301-14309
56. Piper, J. Diffusion of Hydrogen in Copper-Palladium Alloys J. Appl. Phys. 1966, 37, 2, 715-721
57. Qin, L.; Jiang, C. First-Principles Based Modelling of Hydrogen Permeation Through Pd–Cu alloys Int. J. Hydrogen Energy 2012, 37, 17, 12760-12764
58. Sonwane, C. G.; Wilcox, J.; Ma, Y. H. Achieving Optimum Hydrogen Permeability in PdAg and PdAu alloy J. Chem. Phys. 2006, 125, 184714-184724
59. Morreale, B.D.; Howard, B.H.; Iyoha, O.; Enick, R.M.; Ling, C.; Sholl, D.S. Experimental and Computational Prediction of the Hydrogen Transport Properties of Pd₄S Ind. Eng. Chem. Res. 2007, 46, 19, 6313-6319
60. Sonwane, C.G.; Wilcox, J.; Ma, Y. H.; Solubility of Hydrogen in PdAg and PdAu Binary Alloys Using Density Functional Theory J. Phys. Chem. B 2006, 110, 24549-24558
61. Fort, D.; Farr, J. P. G.; Harris, I. R. A Comparison of Palladium–Silver and Palladium–Yttrium Alloys as Hydrogen Separation Membranes J. Less-Common Met. 1975, 39, 293-308
62. Aboud, S.; Wilcox, J. A Density Functional Study of the Charge State of Hydrogen in Metal Hydrides J. Phys. Chem. C 2010, 114, 10978-10985
63. Dos Santos, D. S.; De Miranda, P. E. V. Hydrogen Solubility in Amorphous and Crystalline Materials Int. J. Hydrogen Energy 1998, 23, 11, 1011-1017
64. Smith, D. A.; Jones, I. P.; Harris, I. R. Lattice Order and Hydrogen Solubility in Pd₇Ce J. Less-Common Met. 1984, 103, 33-43

- 1
- 2
- 3 65. Hasegawa, H.; Komura, S.; Utsunomiya, A.; Horita, Z.; Furukawa, M.; Nemoto, M.;
- 4 Langdon, T. G. Thermal Stability of Ultrafine-Grained Aluminium in the Presence of
- 5 Mg and Zr Additions Mater. Sci. Eng., A 1999, 265, 188-196
- 6
- 7 66. Canadinc, D.; Niendorf, T.; Maier, H. J. A Comprehensive Evaluation of Parameters
- 8 Governing the Cyclic Stability of Ultrafine-Grained fcc Alloy Mater. Sci. Eng., A
- 9 2011, 528, 6345-6355
- 10
- 11 67. Gao, H.; Lin, Y. S.; Li, Y.; Zhang, B. Chemical Stability and its Improvement of
- 12 Palladium-Based Metallic Membranes Ind. Eng. Chem. Res. 2004, 43, 6920-6930
- 13
- 14 68. Ling, C.; Sholl, D. S. Using First Principles Calculations to Predict Surface
- 15 Resistances to H₂ Transport through Metal Alloy Membrane J. Membr. Sci. 2007,
- 16 303, 162-172
- 17
- 18 69. Nayeboossadri, S.; Speight, J. D; Book, D. A Novel Pd–Cu–Zr Hydrogen Separation
- 19 Membrane with a High Tolerance to Sulphur Poisoning. Chem. Commun. 2015, 51,
- 20 15842-15845
- 21
- 22
- 23
- 24
- 25
- 26
- 27
- 28
- 29
- 30
- 31
- 32
- 33
- 34
- 35
- 36
- 37
- 38
- 39
- 40
- 41
- 42
- 43
- 44
- 45
- 46
- 47
- 48
- 49
- 50
- 51
- 52
- 53
- 54
- 55
- 56
- 57
- 58
- 59
- 60

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Figures:

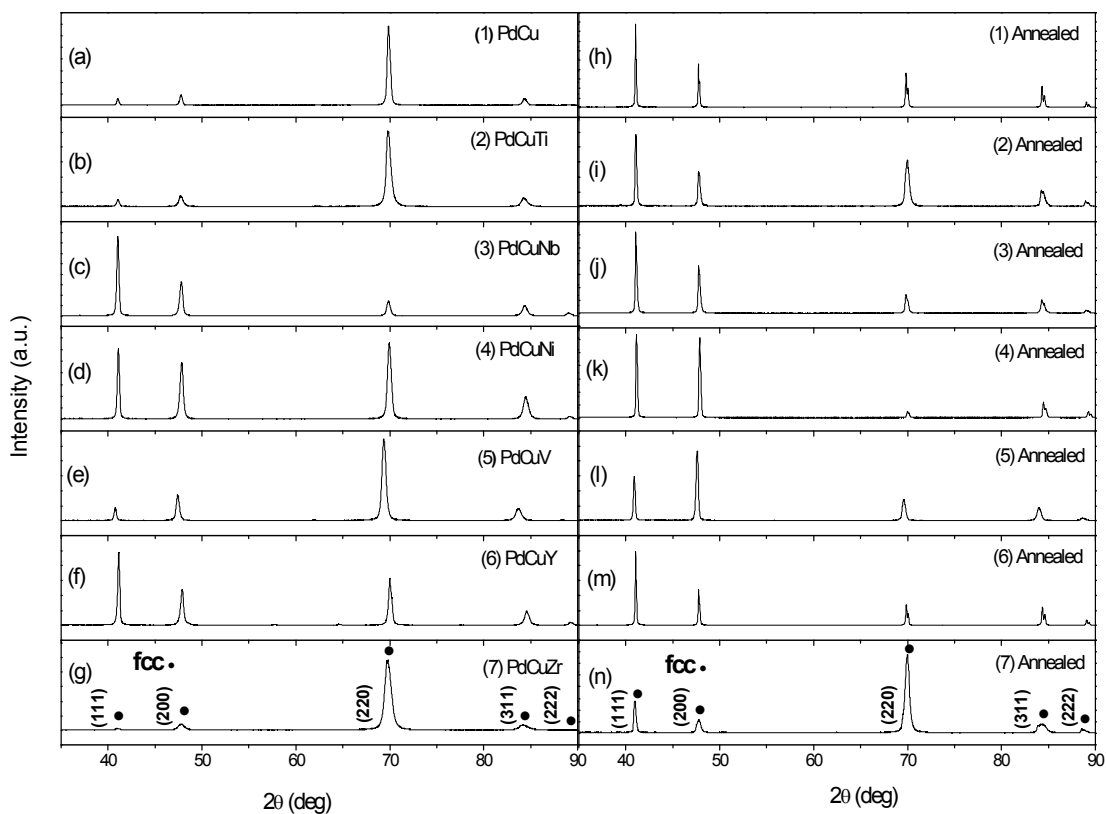


Figure 1: XRD patterns of as fabricated (a) Pd_{65.1}Cu_{34.9} and Pd–Cu–M alloys with (b) Ti, (c) Nb, (d) Ni, (e) V, (f) Y, and (g) Zr. XRD diffraction patterns of annealed (h) Pd_{65.1}Cu_{34.9} and Pd–Cu–M alloys with (i) Ti, (j) Nb, (k) Ni, (l) V, (m) Y, and (n) Zr at 650 °C for 96 h under vacuum.

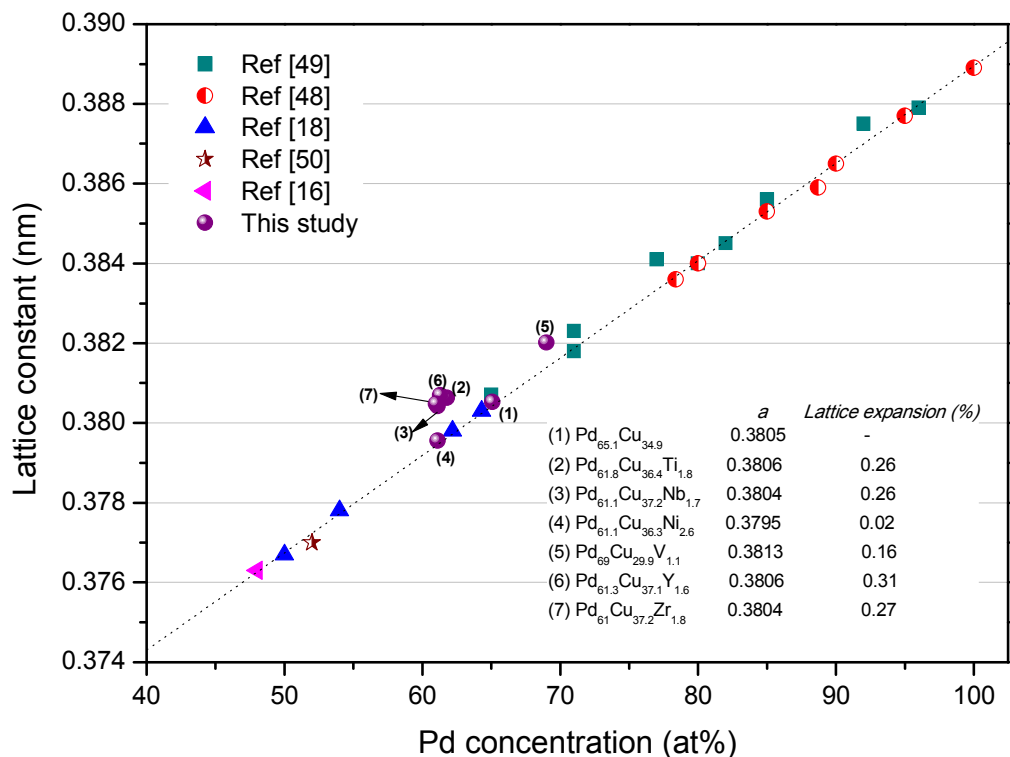


Figure 2: Lattice parameters of the fcc Pd-Cu alloys as a function of Pd concentration. Lattice parameters for the Pd_{65.1}Cu_{34.9} and Pd-Cu-M (M= Y, Ti, Zr, V, Nb, and Ni) alloys are included for comparison. Also, lattice expansions values are listed inset. Dotted line is a guide to the eye.

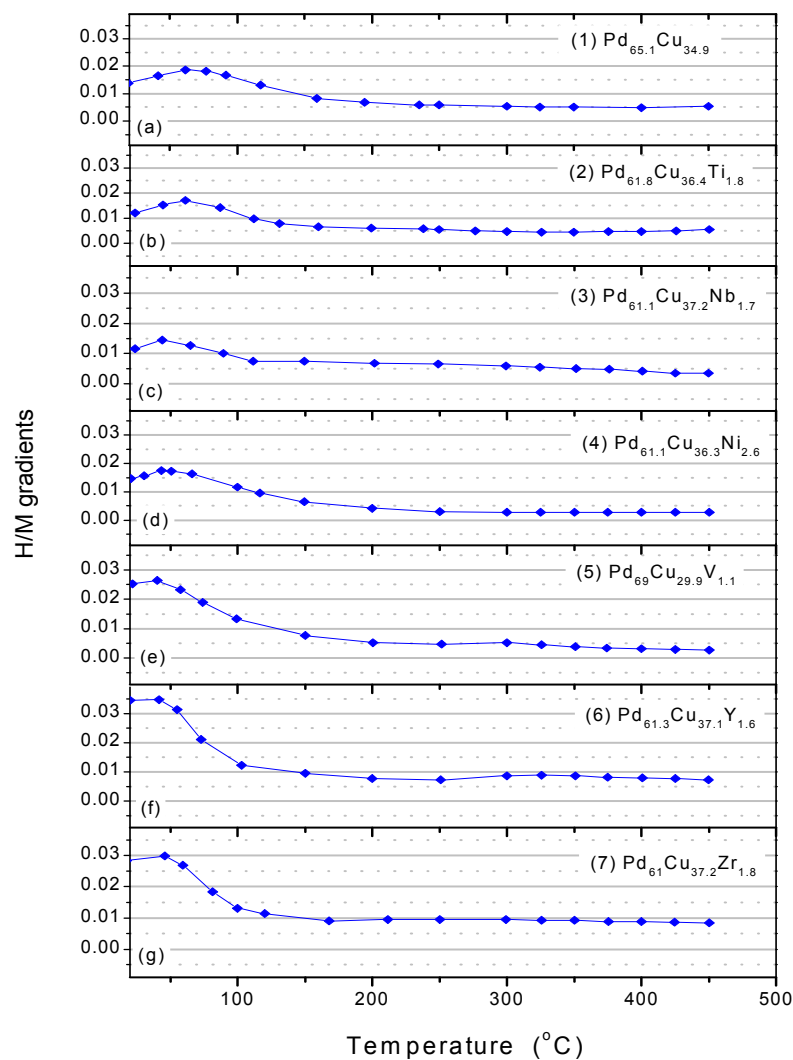


Figure 3: H/M gradients through the thickness of (a) Pd_{65.1}Cu_{34.9} and Pd–Cu–M alloys with (b) Ti, (c) Nb, (d) Ni, (e) V, (f) Y, and (g) Zr from room temperature to 450 °C. H/M gradients were determined by subtracting H/M atomic ratios measured at 6.18 and 1 bar. A heating rate of 1 °C min⁻¹ was applied. Data points are connected by guide lines.

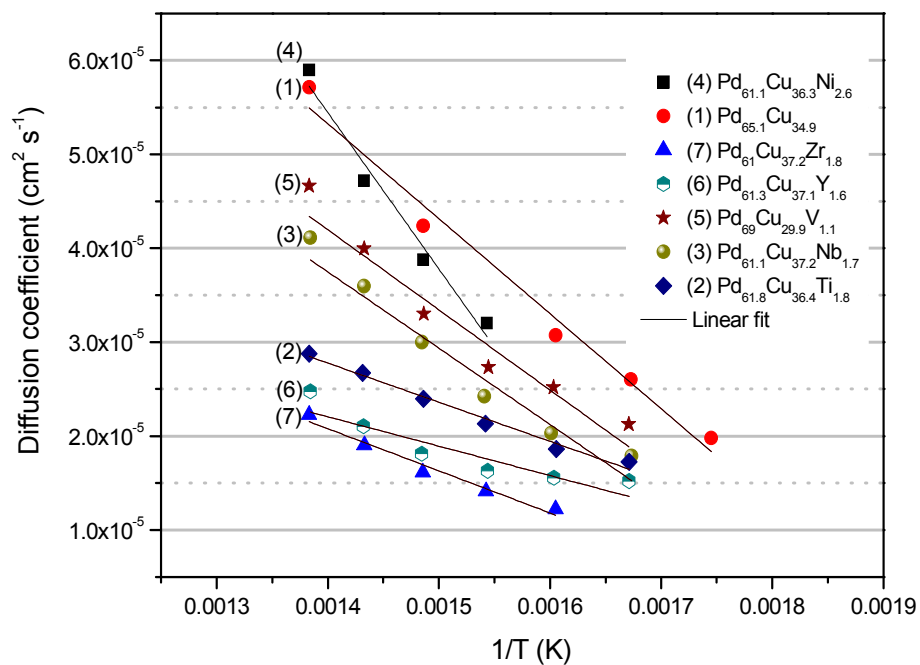


Figure 4: Hydrogen diffusion coefficients D as a function of inverse temperature for the $\text{Pd}_{65.1}\text{Cu}_{34.9}$ and Pd-Cu-M ($M = \text{Y, Ti, Zr, V, Nb, and Ni}$) alloys. Data points are connected by guide lines.

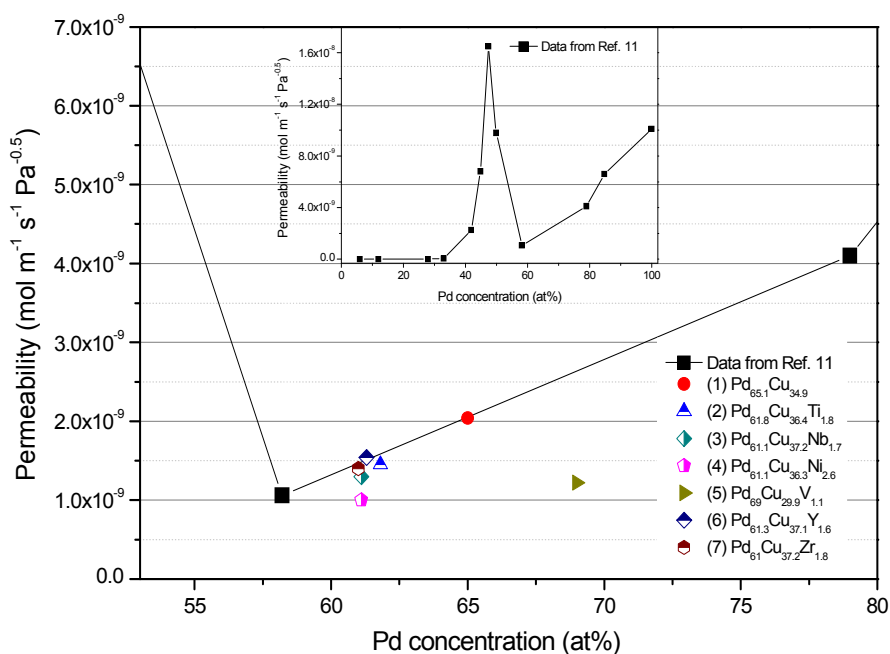


Figure 5: Comparing hydrogen permeability values of $\text{Pd}_{65.1}\text{Cu}_{34.9}$ and Pd-Cu-M ($M = \text{Y, Ti, Zr, V, Nb, and Ni}$) alloys to their respective binary alloys at 350°C . The inset graph is hydrogen permeability values of the Pd-Cu alloys as a function of Pd concentration at 350°C . Solid line is guide for the eye.

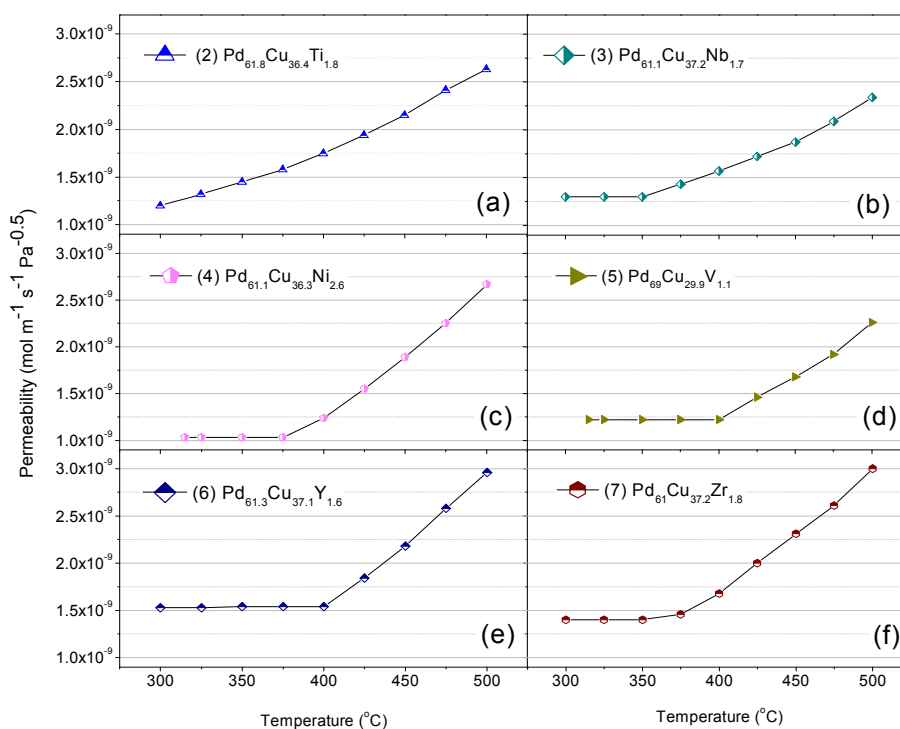


Figure 6: Hydrogen permeability profiles of Pd-Cu-M alloys with (a) Ti, (b) Nb, (c) Ni, (d) V, (e) Y, and (f) Zr additional elements as a function of temperature. A heating rate of $2^{\circ}\text{C min}^{-1}$ was applied with a constant hydrogen pressures of 6.18 and 1 bar on the feed and permeate sides respectively.

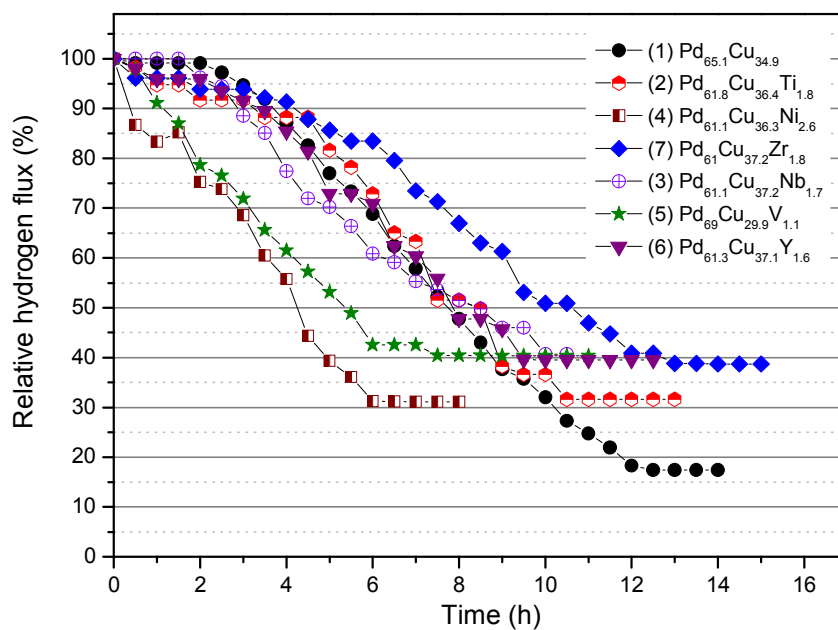


Figure 7: Sulphur poisoning of Pd_{65.1}Cu_{34.9} and Pd-Cu-M (M= Y, Ti, Zr, V, Nb, and Ni) alloys at 450 °C. The feed gas contains 1000 ppm H₂S+H₂.

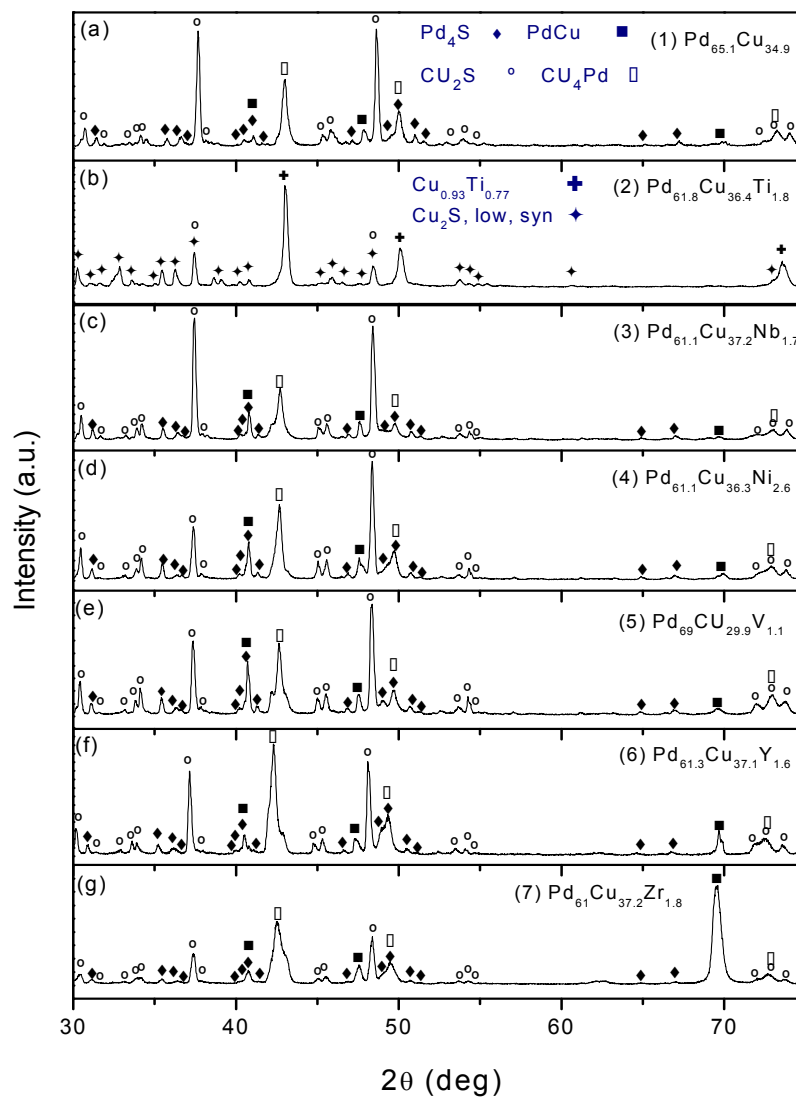


Figure 8: XRD patterns of (a) $\text{Pd}_{65.1}\text{Cu}_{34.9}$ and Pd–Cu–M alloys with (b) Ti, (c) Nb, (d) Ni, (e) V, (f) Y, and (g) Zr additional elements after exposure to 1000 ppm $\text{H}_2\text{S} + \text{H}_2$ at 450 °C.


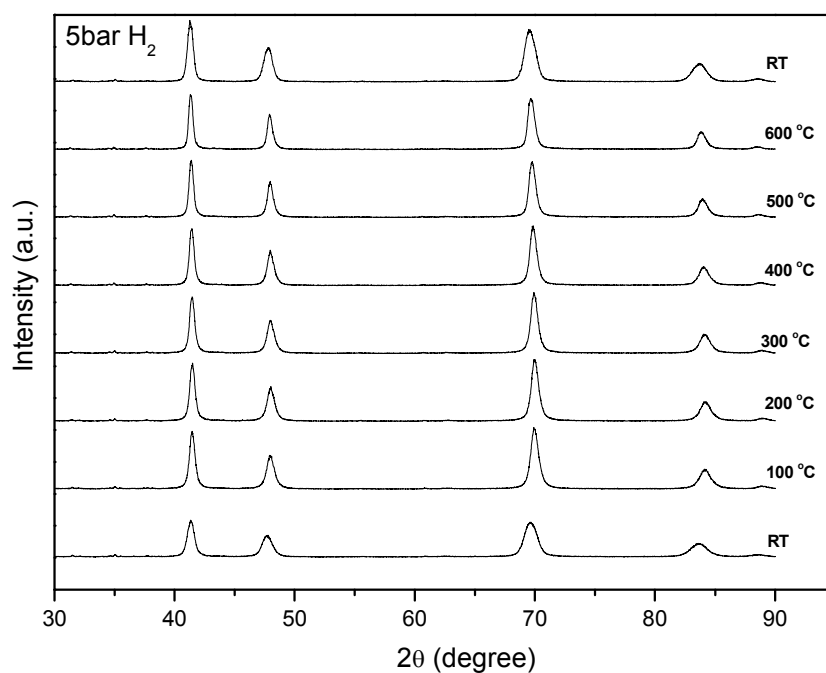


Figure 9: Evolution of the *in-situ* XRD patterns for Pd-Cu-Zr alloy under 5 bar hydrogen pressure. XRD patterns were collected at room temperature and the subsequent 100 °C increment steps to 600 °C, where the samples was cooled down to the room temperature before collecting the final XRD pattern.

Tables:

Table 1: EDS analyses of the Pd_{65.1}Cu_{34.9} and Pd–Cu–M (M= Y, Ti, Zr, V, Nb, and Ni) alloys annealed at 650 °C for 96 h. Also, atomic radii ⁴³, valence ⁴⁴, enthalpy for M–H formation ⁴⁵, and foils thicknesses are included.

Sample	EDS (at%)			Atomic radius of M (Å)	Effective valence of M	Enthalpy of M-H formation (kJ/g atom)	Foil thickness (μm)	alloy phase
	Pd	Cu	M					
(1) PdCu	65.1±0.1	34.9±0.1	-	Pd:1.40 Cu:1.35	Cu:1		97	fcc
(2) PdCuTi	61.8±0.2	36.4±0.4	1.8±0.3	1.40	4	-42	91.4	fcc
(3) PdCuNb	61.1±0.6	37.2±0.6	1.7±0.1	1.45	5	-20	113	fcc
(4) PdCuNi	61.1±0.5	36.3±0.5	2.6±0.2	1.35	4	-1	83	fcc
(5) PdCuV	69±0.4	29.9±0.3	1.1±0.4	1.35	5	-18	98	fcc
(6) PdCuY	61.3±0.5	37.1±0.4	1.6±0.3	1.80	3	-72	123	fcc
(7) PdCuZr	61±0.4	37.2±0.5	1.8±0.4	1.55	4	-55	112.5	fcc

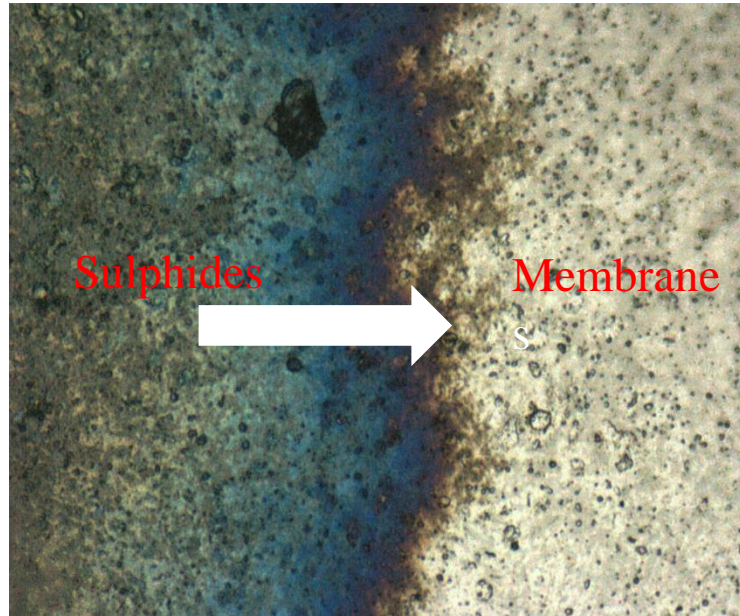

26
27 Progressive formation of sulphides on the
28 surface of membrane
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43

