

Engineering Conferences International ECI Digital Archives

Nanomechanical Testing in Materials Research and
Development V

Proceedings

Fall 10-4-2015

Micromechanical behavior of thermal barrier coatings after isothermal oxidation

Carlos Serna

Universidad Nacional de Colombia, cmsernaz@unal.edu.co

Deiby Maya

Universidad Nacional de Colombia

Alejandro Toro

Universidad Nacional de Colombia

Juan Meza

Universidad Nacional de Colombia

Follow this and additional works at: http://dc.engconfintl.org/nanomechtest_v



Part of the [Materials Science and Engineering Commons](#)

Recommended Citation

[1] M. Ciniviz, E. Canli, H. Kose, M. S. Salman, and O. Solmaz, "Ceramic Coating Applications and Research Fields for Internal Combustion Engines," in *Ceramic Coatings - Applications in Engineering*, INTECH Open Access Publisher, 2012, pp. 195–234. [2] A. G. Evans and J. W. Hutchinson, "The thermomechanical integrity of thin films and multilayers," *Acta Metall. Mater.*, vol. 43, no. 7, pp. 2507–2530, Jul. 1995

This Abstract and Presentation is brought to you for free and open access by the Proceedings at ECI Digital Archives. It has been accepted for inclusion in *Nanomechanical Testing in Materials Research and Development V* by an authorized administrator of ECI Digital Archives. For more information, please contact franco@bepress.com.

Abstract

Thermal protection of metallic components by Thermal Barrier Coatings, TBCs, is widely used in rocket engines, aircraft industry and gas turbines for power generation; this technology reduces substrates temperature up to 165°C. Apart from thermal protection they can also protect against abrasion, oxidation and corrosion.

This work reports on the mechanical characterization of APS 6-8 wt.% Yttria Stabilized Zirconia (YSZ) as top layer, bonded by an HVOF NiCoCrAlY layer to a superalloy substrate (Inconel 625), using micro- and nano-indentation techniques on test specimens after heat treatment at 1100°C and different exposure times (0, 200, 400, 600, 800, 1000, and 1700 hours).

The fracture toughness of the ceramic coating was measured through IF method, in conjunction with failure statistics, proved to be a powerful tool that helps to understand microstructural and mechanical evolution of the coating due to high temperature exposition.

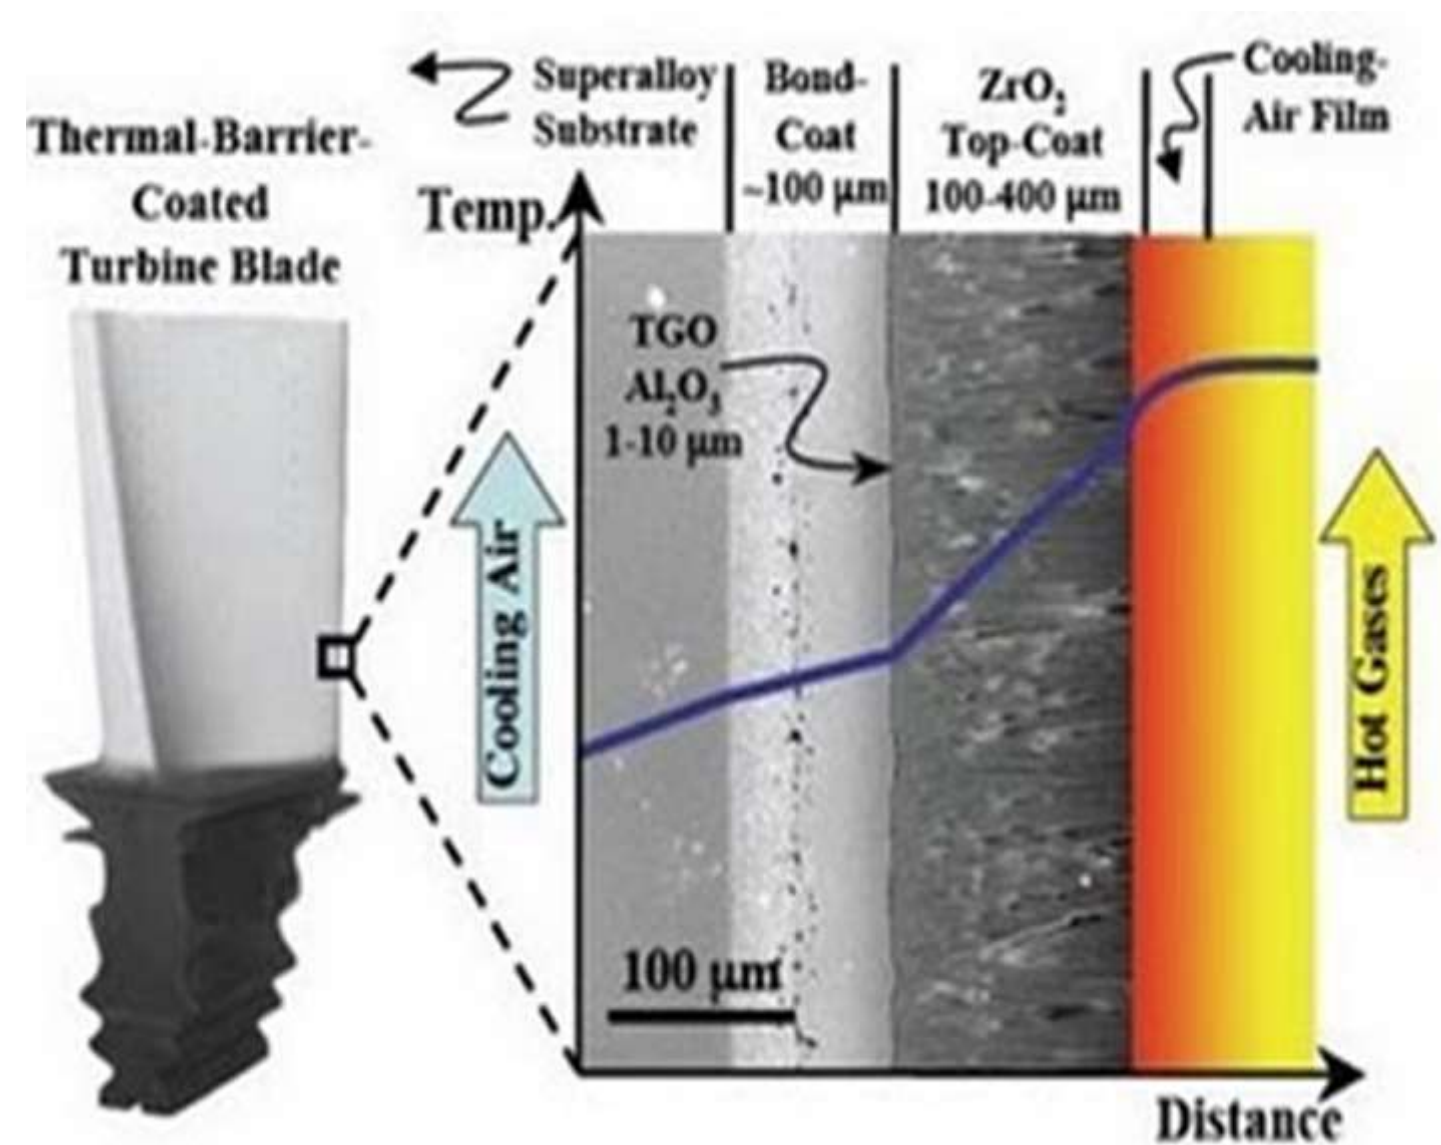


Fig. 1. Schematic of a TBC's general structure [1].

Materials and Methods

Test specimens, with dimensions of 1.7 x 1.7 cm, were heat treated at 1100°C during 0, 200, 400, 600, 800, 1000, and 1700 hours respectively, then they were mounted in phenolic resin, and samples were extracted for metallographic preparation: Grinding with sand paper N° 400 and 600 (during 15 min); polishing with diamond suspension of 12, 6, 3 μm (during 15 min) and 1 μm (during 60 min), keeping a pressure of 37.5±3.54 KPa.

Nano- and micro-indentation techniques were carried out on the cross-sections to measure elastic modulus, hardness, and fracture toughness. OM and SEM microscopy were used to measure the size and shape of the indentations, the state, evolution, and morphology of the cracks; and the general structural aspects of the ceramic coating. The fracture toughness (K_{1c}) of the TC was evaluated with the James Lankford model.

$$K_{1c} = 0.0363 \left(\frac{E}{H}\right)^{\frac{2}{5}} \left(\frac{P}{a^{1.5}}\right) \left(\frac{a}{c}\right)^{1.56}$$

A method employing Weibull statistics was applied to evaluate results from K_{1c} values:

$$P(K_{1c}) = 1 - e^{-\left(\frac{K_{1c}}{K_0}\right)^m}$$

where m , is the Weibull modulus, and K_0 is the characteristic fracture toughness.

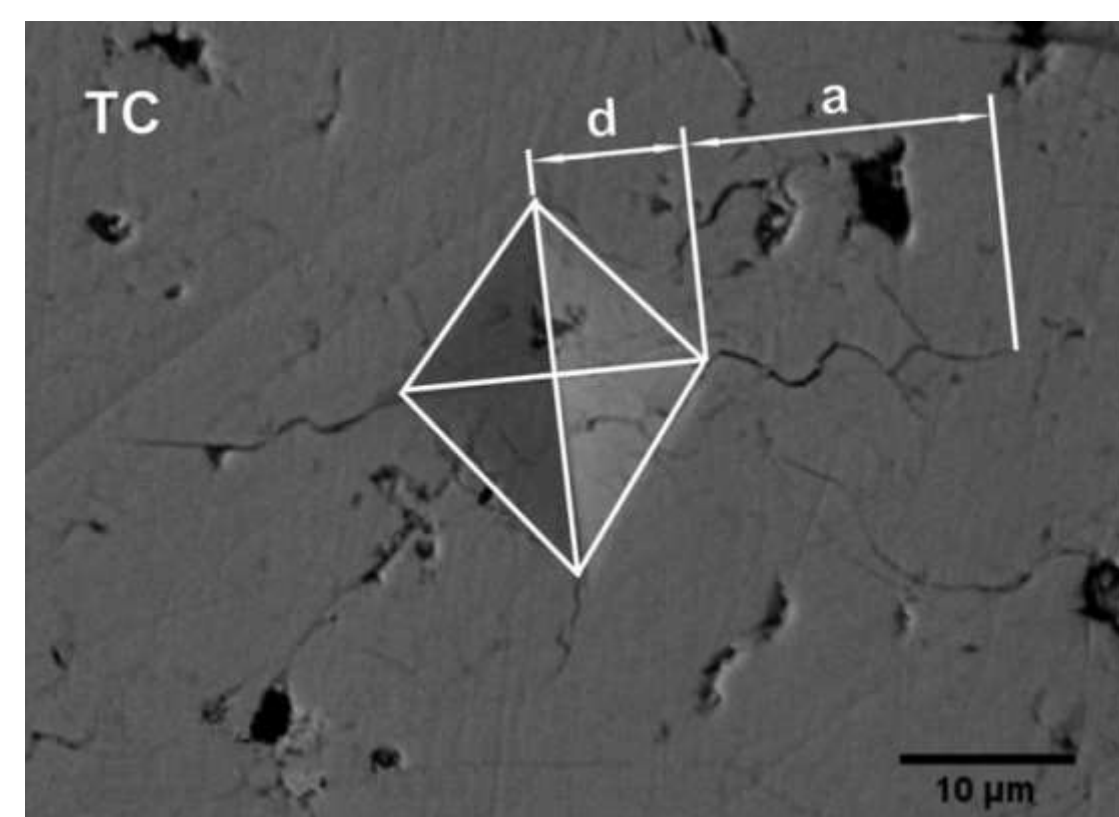


Fig. 2. Vickers indentation of a heat treated sample (1100°C, 1700 h).

Results

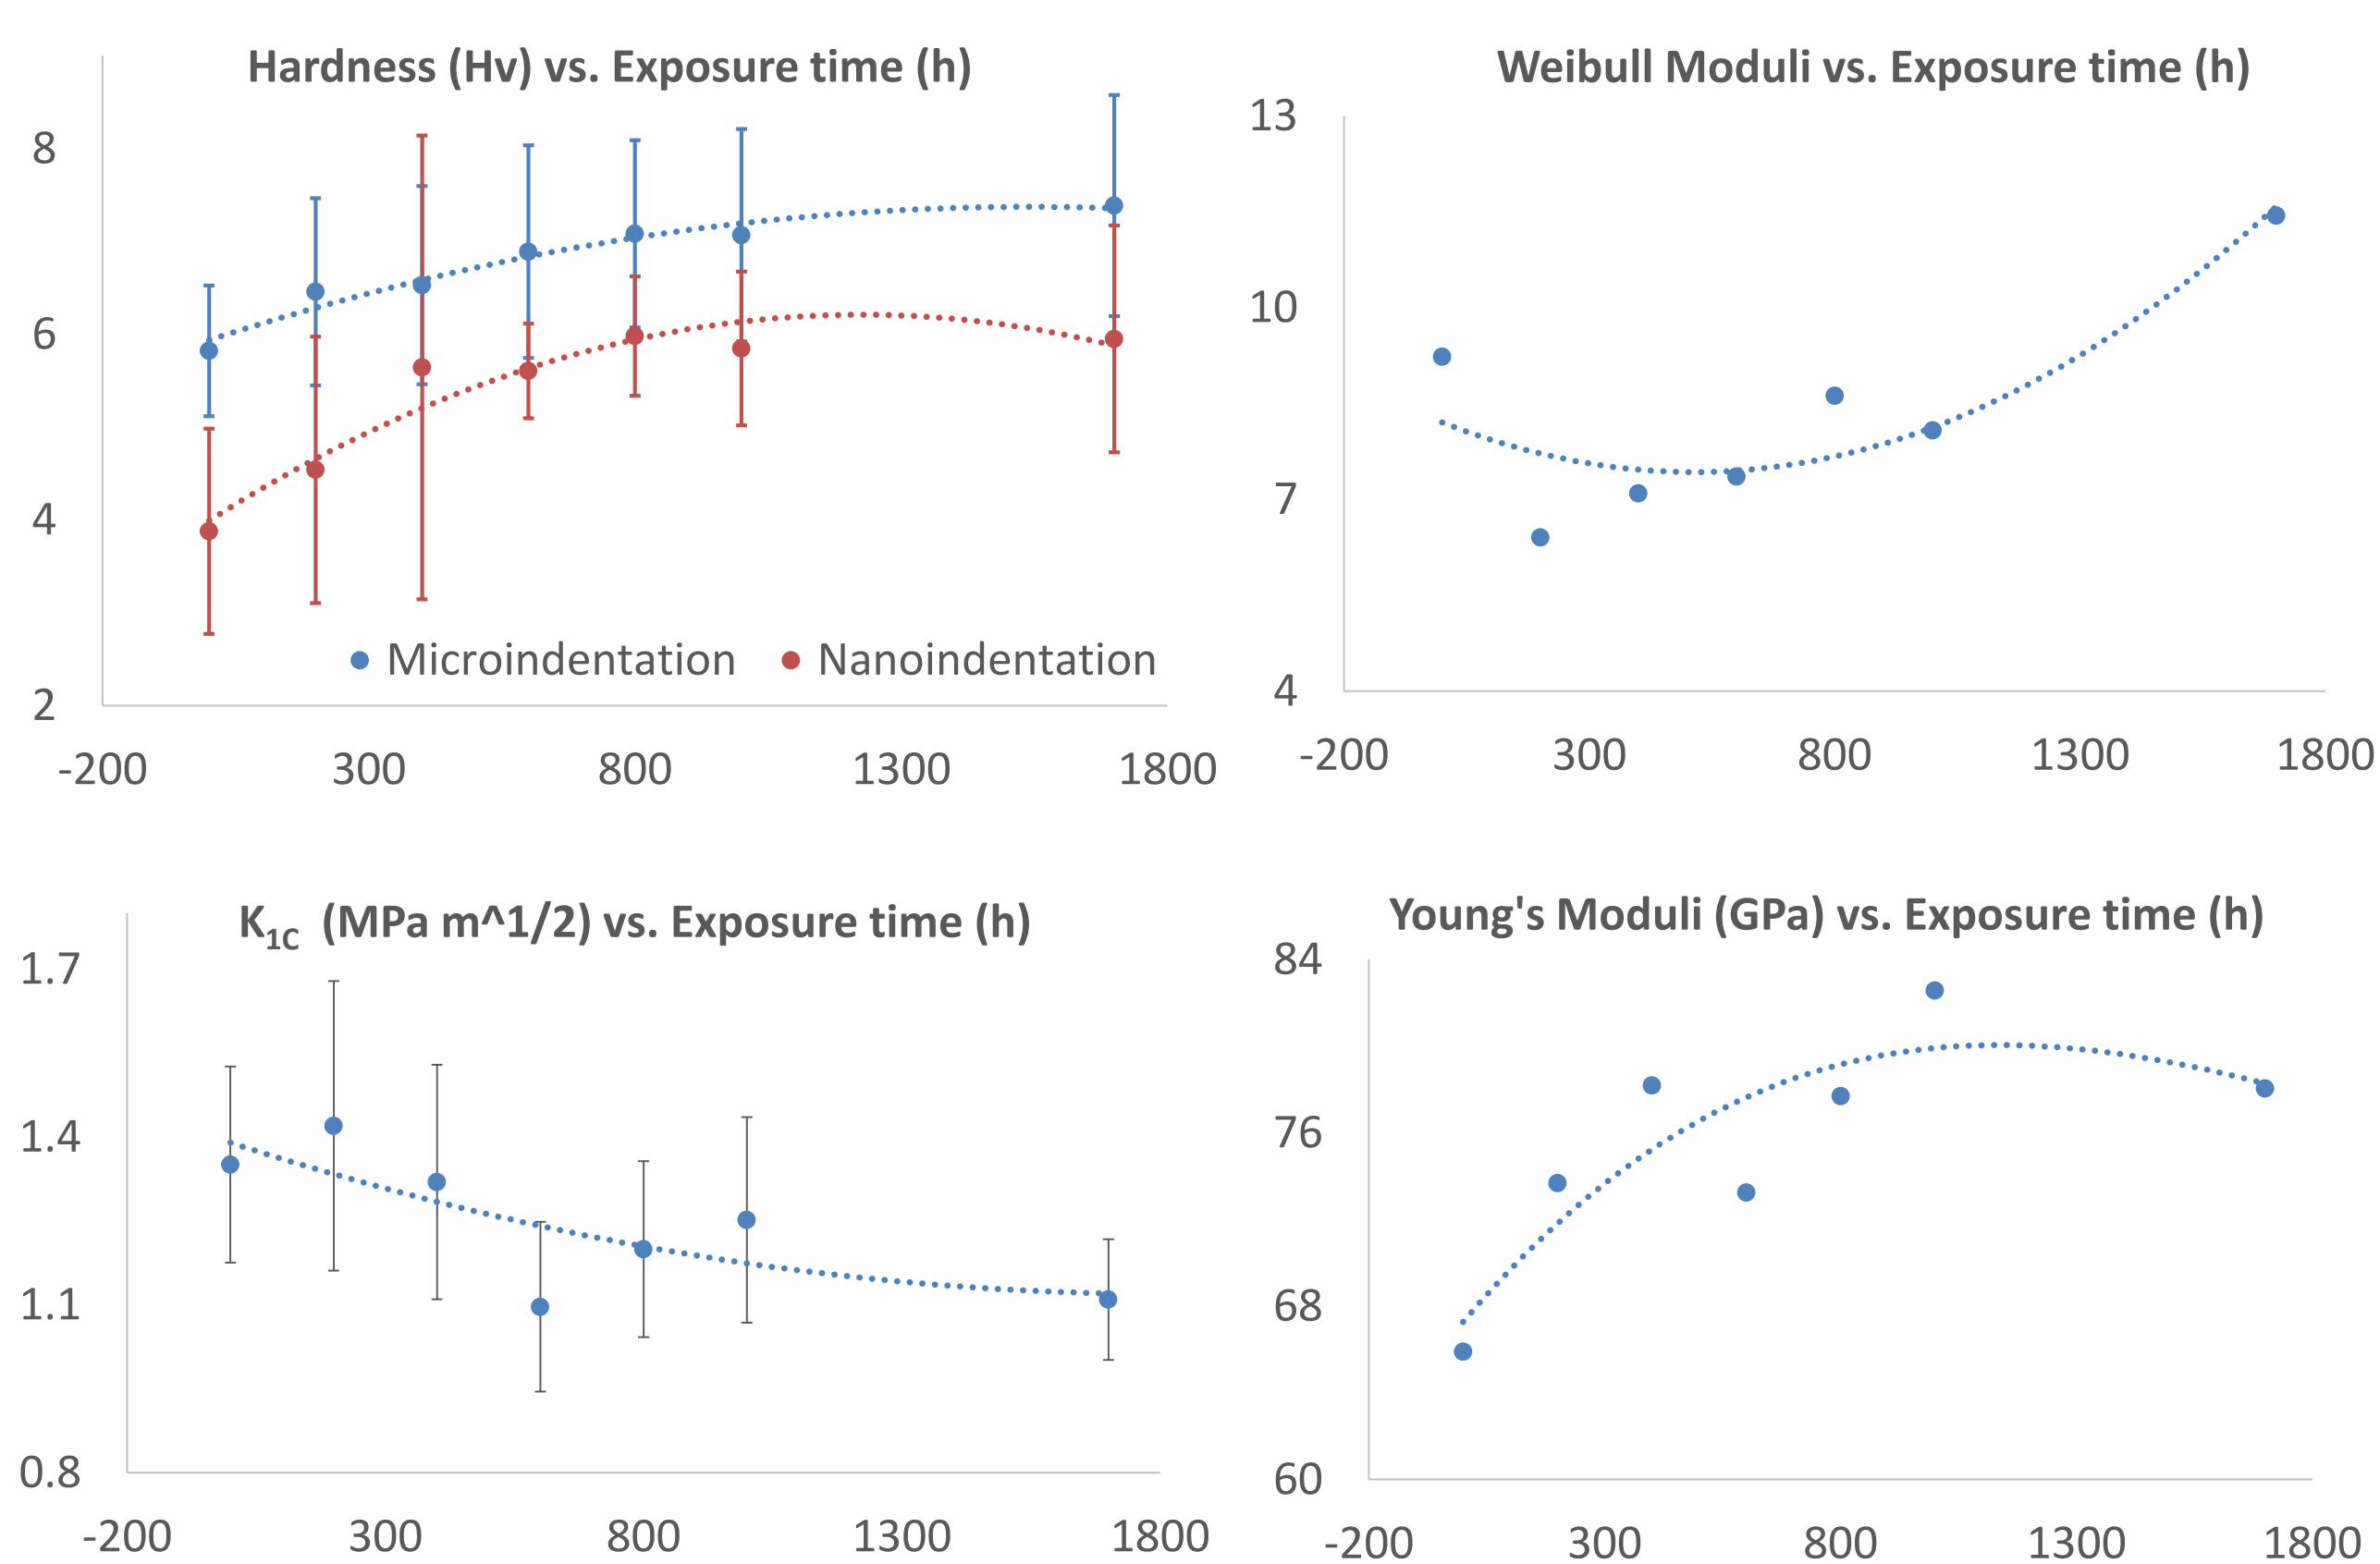


Fig. 3. Hardness, fracture toughness, Weibull and Young's moduli of TBCs, at 1100°C at different times.

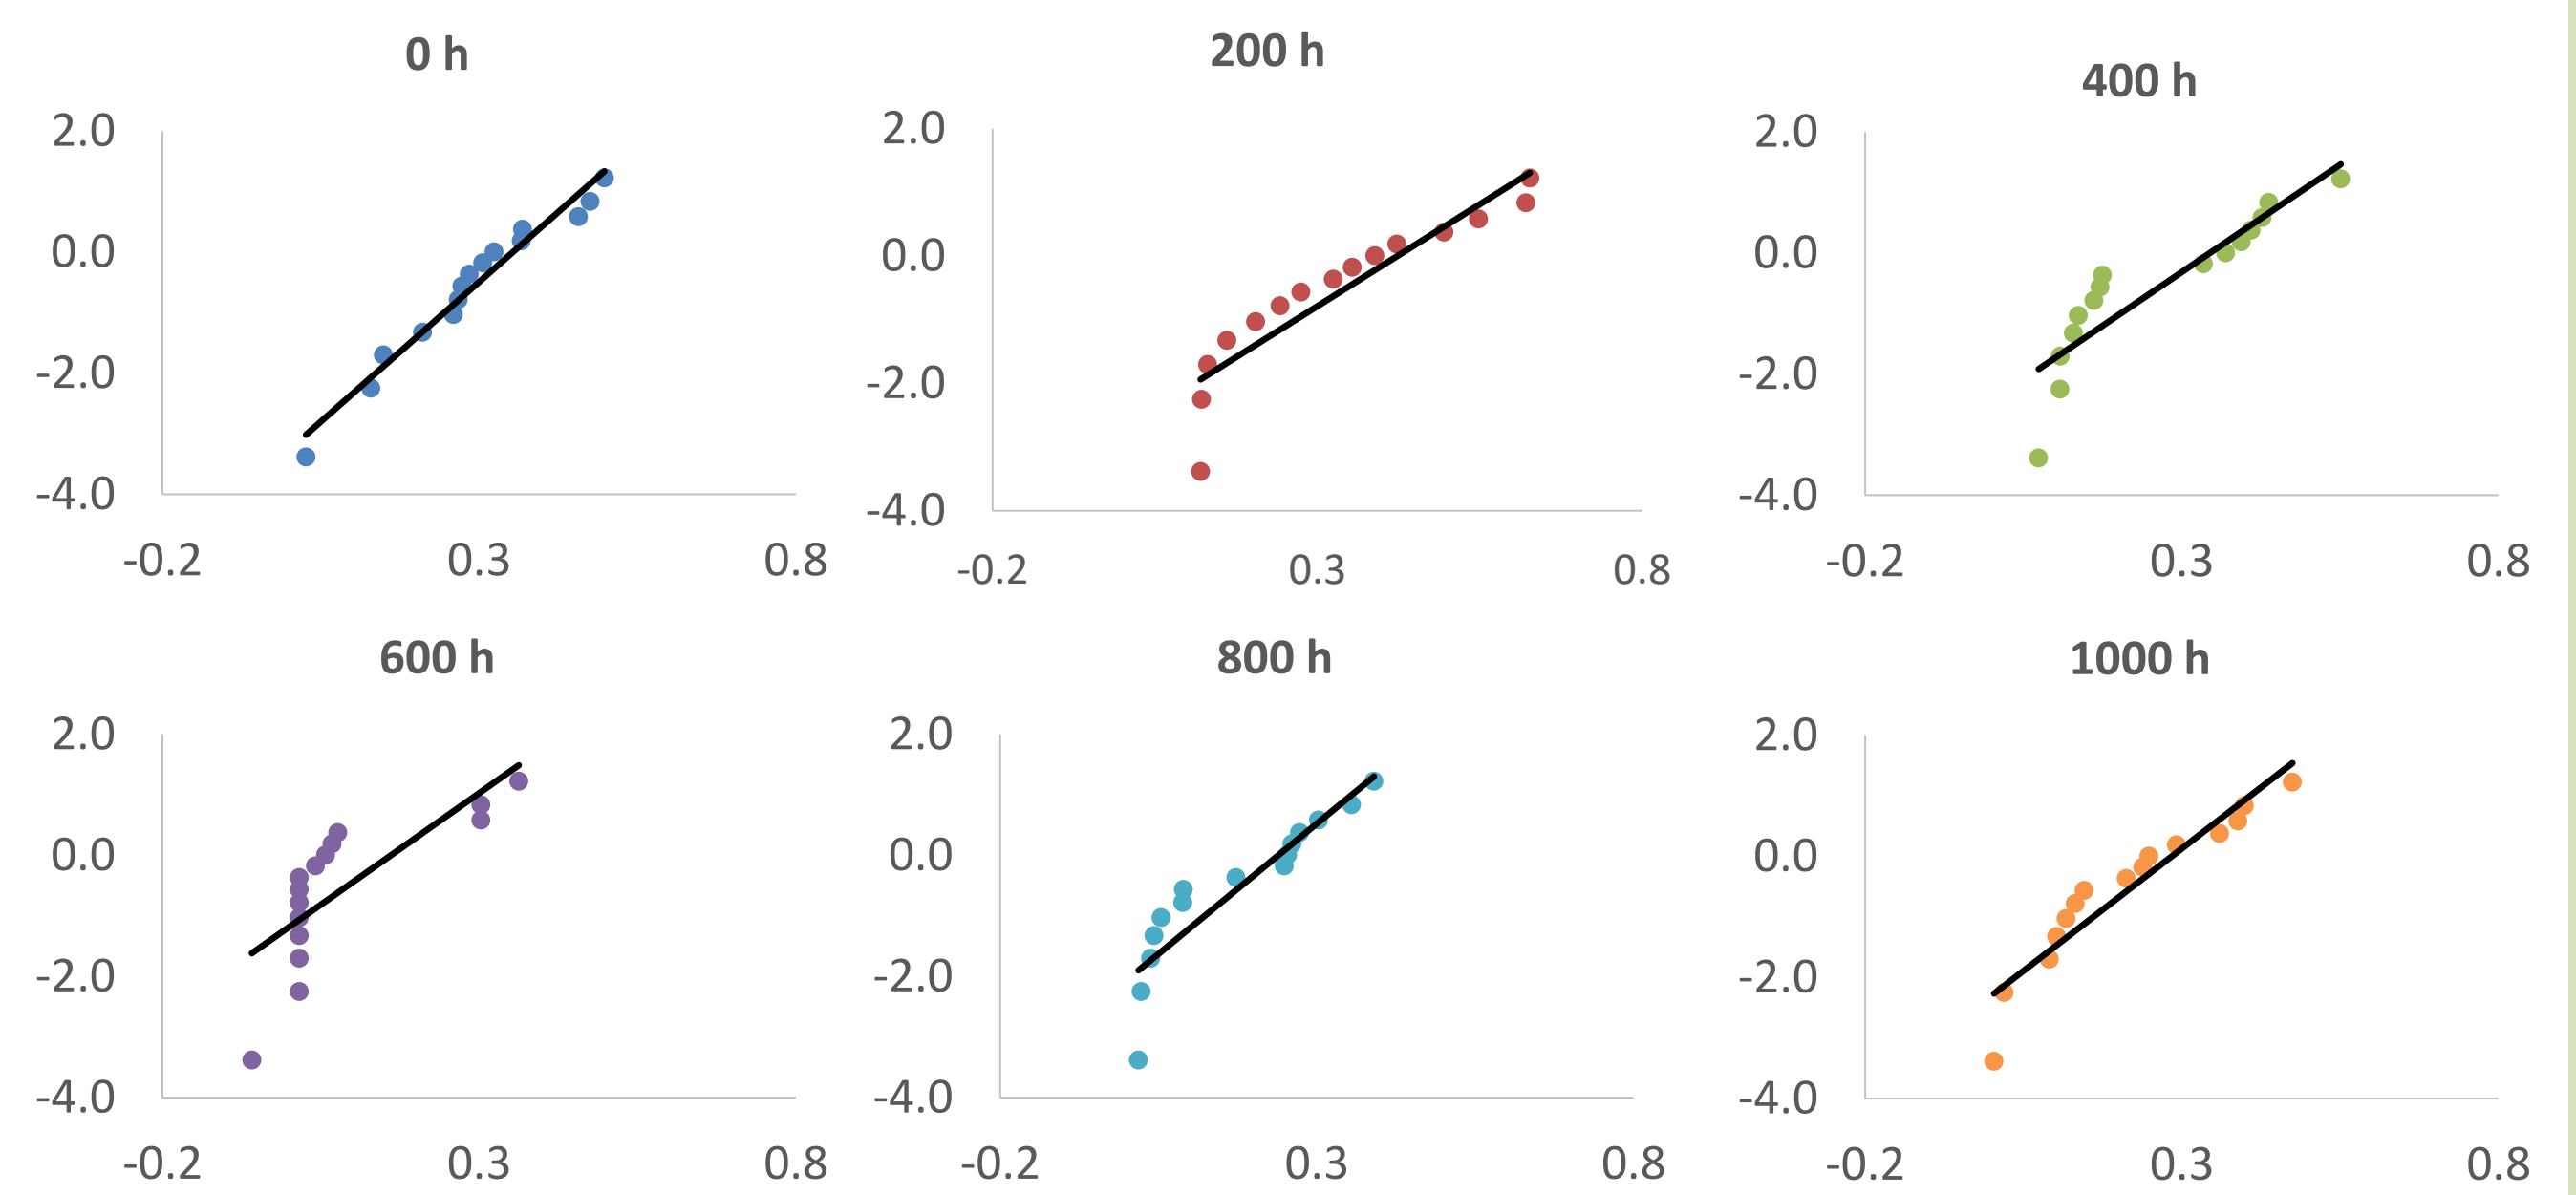


Fig. 4. Weibull plots for fracture toughness - $\ln\ln(1/(1-P(K_{1c})))$ vs $\ln K_{1c}$.

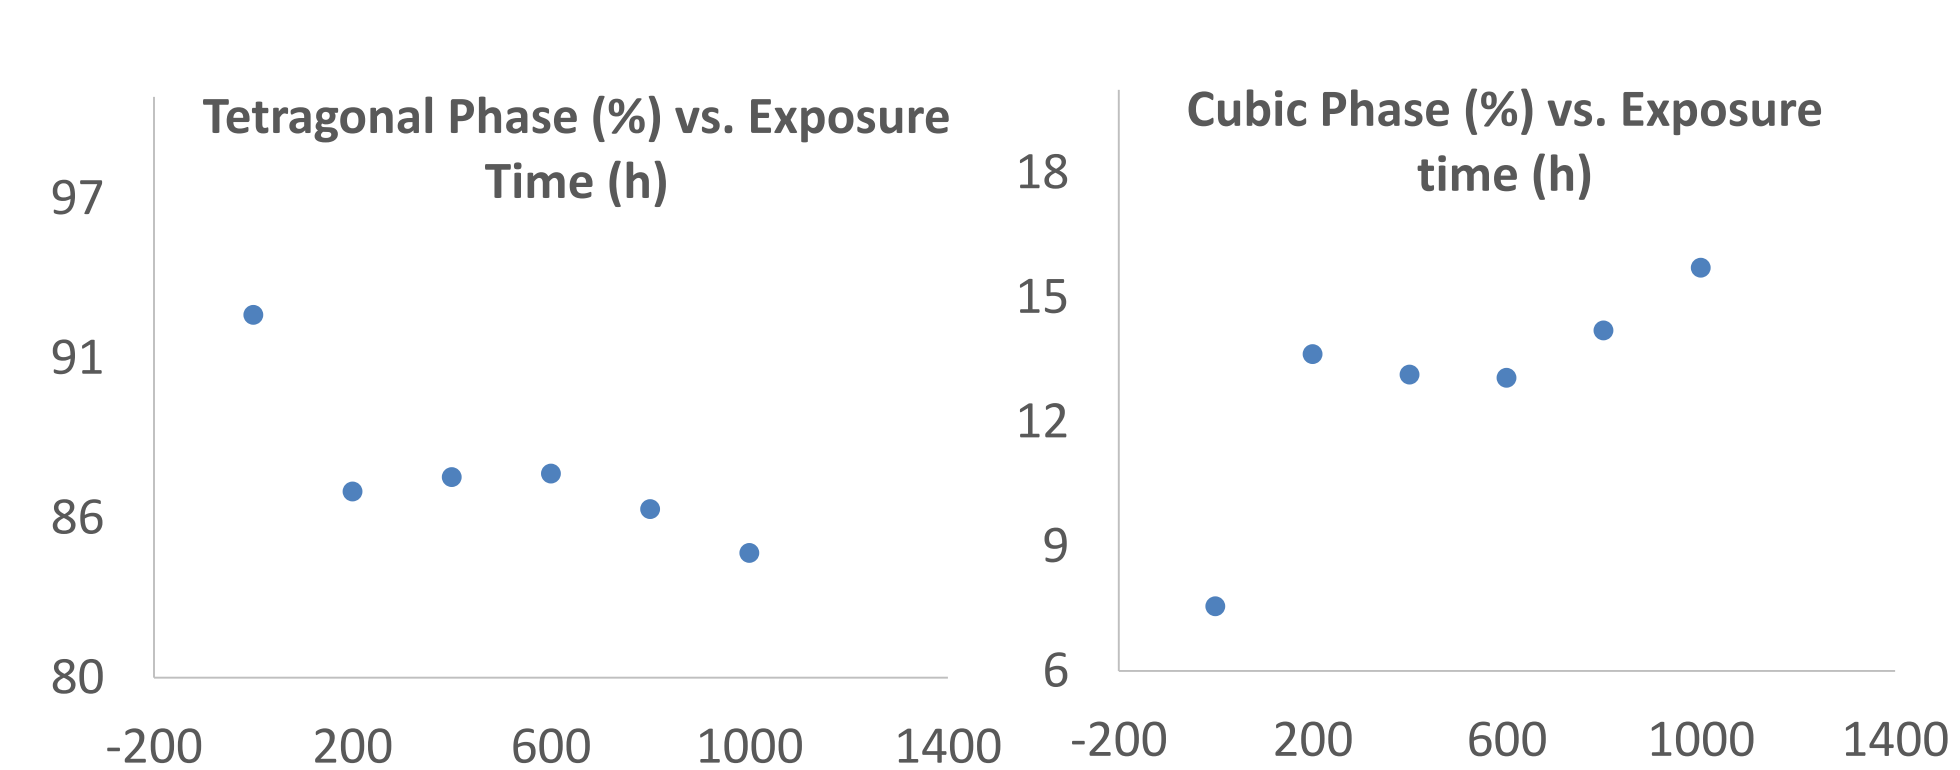


Fig. 5. Quantification of tetragonal and cubic phases by Rietveld method [2].

Time (h)	m	K_0
0	9.2	26.0
200	6.4	15.0
400	7.1	11.5
600	7.4	3.2
800	8.6	12.9
1000	8.1	9.9
1700	11.4	5.5

Table 1. Weibull parameters at different exposure times.

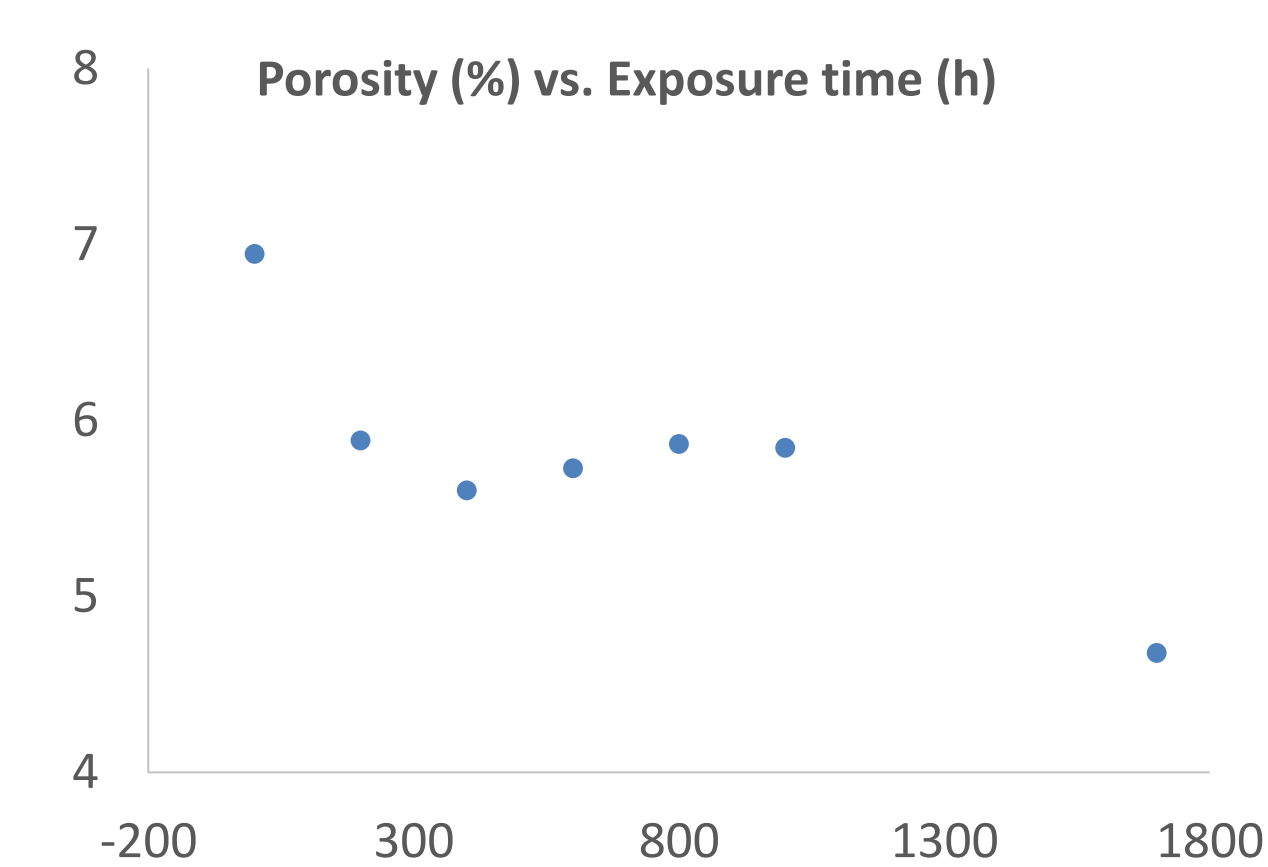


Fig. 6. Porosity content vs. Exposure time [2].

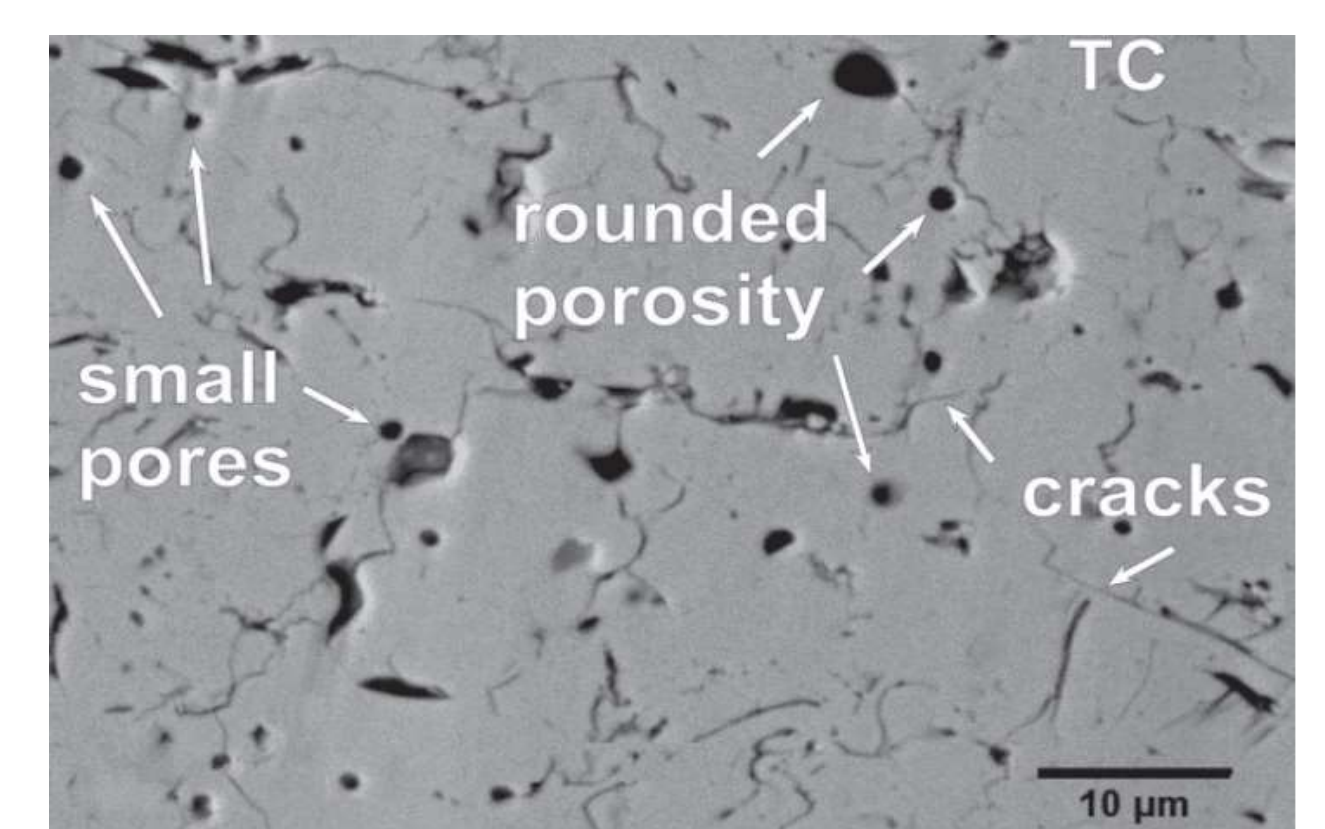


Fig. 7. Cross-section of the TC heat treated sample at 1100°C during 1700 h.

Conclusions


- From 0 up to 600 hours of heat treatment, before the formation of the monoclinic phase, hardness and Young's modulus of the TC rapidly grew up; this is explained by the sintering phenomena. Further from the 600 hours, the hardness continued growing up, but the young's modulus got to a steady state due to competition between sintering mechanism and phase transformations (where sintering tried to augment E and phase transformation tried to reduce it).
- The fracture toughness decreased with exposition time up to 23% showing a detriment of the ceramic layer. The Lankford Model gave results similar to those found in the literature for the 6-8 wt.% YSZ, showing a reliable method.
- After indentations, the direction in which radial cracks spread was ruled by the TC microstructure (parallel to the TC/TGO).
- In general K_{1c} data follows the Weibull's equation. However, between 400 and 600°C, the data do not conform with weibull's equation due to their scatteredness; this can be explained by the fact that the material undergoes structural transformation that is caused by phase changes, sintering, and evolution of residual stresses.
- The IF method, in conjunction with failure statistics, has proven to be a powerful tool for the assessment of the microstructural behavior, showing the trend of the densification due to sintering.

ACKNOWLEDGEMENTS

The authors wish to acknowledge the opportunity to participate in the **Nanomechanical Testing in Materials Research and Development V** (An ECI Conference Series). The results presented herein were possible thanks to the financial support given by Empresas Públicas de Medellín, EPM, through their project "Protección y Recuperación de Componentes de la Ruta de Gases Calientes de Turbinas a Gas Clase F Mediante Aplicación de Revestimientos de Barrera Térmica - TBC", by Universidad Nacional de Colombia, and by the Laboratorio de Tribología y Superficies.

Contact

Carlos Serna
Universidad Nacional de Colombia
Email: cmsernaz@unal.edu.co
Phone: 57-3044235586

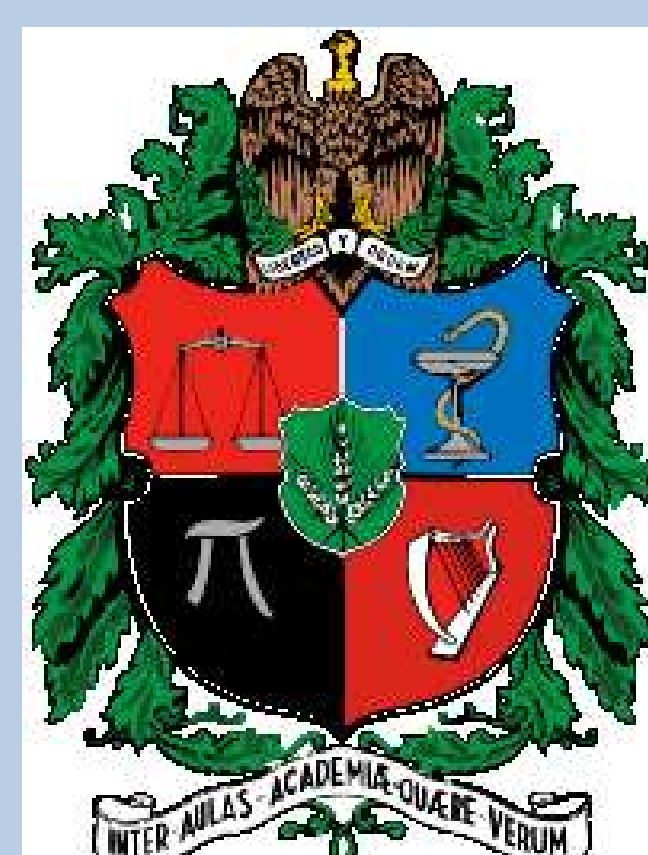

References

- N. P. Padture, "Thermal Barrier Coatings for Gas-Turbine Engine Applications," Science (80-.), vol. 296, no. 5566, pp. 280-284, Apr. 2002.
- J. D. Osorio, D. Maya, A. C. Barrios, A. Lopera, F. Jiménez, J. M. Meza, J. P. Hernández-Ortiz, and A. Toro, "Correlations between microstructure and mechanical properties of air plasma-sprayed thermal barrier coatings exposed to a high temperature," J. Am. Ceram. Soc., vol. 96, no. 12, pp. 3901-3907, 2013.
- A. G. Evans and J. W. Hutchinson, "The thermomechanical integrity of thin films and multilayers," Acta Metall. Mater., vol. 43, no. 7, pp. 2507-2530, Jul. 1995.
- J. Lankford, "Indentation microfracture in the Palmqvist crack regime: implications for fracture toughness evaluation by the indentation method," J. Mater. Sci. Lett., vol. 1, no. 11, pp. 493-495, Nov. 1982.
- M. Ciniviz, E. Canli, H. Kose, M. S. Salman, and O. Solmaz, "Ceramic Coating Applications and Research Fields for Internal Combustion Engines," in Ceramic Coatings - Applications in Engineering, INTECH Open Access Publisher, 2012, pp. 195-234.
- A. Rico, J. Gómez-García, C. J. Múñez, P. Poza, and V. Utrilla, "Mechanical properties of thermal barrier coatings after isothermal oxidation. Depth sensing indentation analysis," Surf. Coatings Technol., vol. 203, no. 16, pp. 2307-2314, 2009.
- C. Lu, R. Danzer, and F. D. Fischer, "Fracture statistics of brittle materials: Weibull or normal distribution," Phys. Rev. E - Stat. Nonlinear, Soft Matter Phys., vol. 65, no. 6, pp. 1-4, 2002.
- C.-D. Lai, Generalized Weibull Distributions. Springer, 2014.
- A. Dey, A. K. Mukhopadhyay, S. Gangadharan, M. K. Sinha, and D. Basu, "Weibull modulus of nano-hardness and elastic modulus of hydroxyapatite coating," J. Mater. Sci., vol. 44, no. 18, pp. 4911-4918, 2009.