

**Exploring the electrochromic properties of poly(thieno[3,2-b]thiophene)s decorated with electron-deficient side groups**

Shao, Shan; Shi, Jingjing; Xu, Panpan; He, Yaowu; Ghosh, Sanjay; Zhu, Xiaosi; Perepichka, Igor; Murtaza, Imran; Meng, Hong

Polymer Chemistry

DOI:

[10.1039/C6PY01847E](https://doi.org/10.1039/C6PY01847E)

Published: 31/01/2017

Peer reviewed version

[Cyswllt i'r cyhoeddiad / Link to publication](#)

Dyfyniad o'r fersiwn a gyhoeddwyd / Citation for published version (APA):

Shao, S., Shi, J., Xu, P., He, Y., Ghosh, S., Zhu, X., Perepichka, I., Murtaza, I., & Meng, H. (2017). Exploring the electrochromic properties of poly(thieno[3,2-b]thiophene)s decorated with electron-deficient side groups. *Polymer Chemistry*, 2017(8), 769-784. <https://doi.org/10.1039/C6PY01847E>

Hawliau Cyffredinol / General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal ?

Take down policy


If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

Polymer Chemistry

Accepted Manuscript



This article can be cited before page numbers have been issued, to do this please use: S. Shao, J. Shi, I. Murtaza, P. Xu, Y. He, S. Ghosh, X. Zhu, I. F. Perepichka and H. Meng, *Polym. Chem.*, 2016, DOI: 10.1039/C6PY01847E.

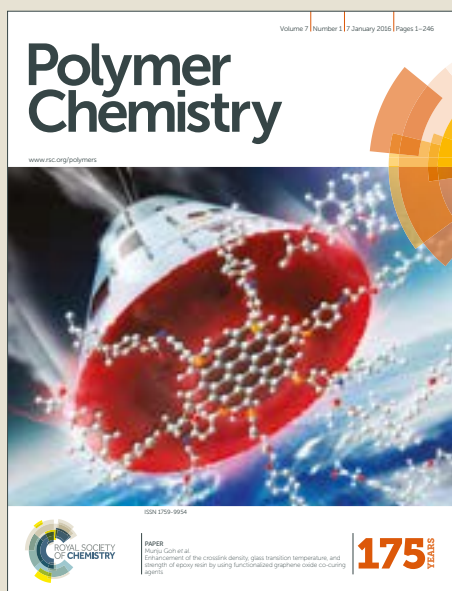

This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [author guidelines](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the ethical guidelines, outlined in our [author and reviewer resource centre](#), still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

Exploring the electrochromic properties of poly(thieno[3,2-*b*]thiophene)s decorated with electron-deficient side groups[†]

Shan Shao,^a Jingjing Shi,^a Imran Murtaza,^{b,c} Panpan Xu,^a Yaowu He,^a Sanjay Ghosh,^d Xiaosi Zhu,^a Igor F. Perepichka^{*d} and Hong Meng^{*a,b}

^aSchool of Advanced Materials, Peking University Shenzhen Graduate School, Shenzhen 518055, China. Tel: (86)-18565807998, E-mail: menghong@pkusz.edu.cn

^bKey Laboratory of Flexible Electronics (KLOFE) & Institute of Advanced Materials (IAM), Jiangsu National Synergetic Innovation Center for Advanced Materials (SICAM), Nanjing Tech University (Nanjing Tech), 30 South Puzhu Road, Nanjing 211816, China

^cDepartment of Physics, International Islamic University, Islamabad 44000, Pakistan

^dSchool of Chemistry, Bangor University, Deiniol Road, Bangor LL57 2UW, United Kingdom. E-mail: i.perepichka@bangor.ac.uk

ABSTRACT: Two novel thieno[3,2-*b*]thiophene (TT)/3,4-ethylenedioxythiophene(EDOT)-based compounds of 2,5-(EDOT-TT-EDOT) type bearing electron-withdrawing side groups (4-cyanophenyl or 4-pyridyl) at 3,6-positions of TT moiety have been synthesized. Their electropolymerization lead to electroactive conjugated polymers, **P(CNPh-ETTE)** and **P(Py-ETTE)**, which possess electrochromic properties changing the color from purple to pale grey-blue or from sand brown to pale grey-green, respectively. Cyclic voltammetry and spectroelectrochemical experiments reveal that functionalization with electron-withdrawing side groups decreases HOMO and LUMO energy levels and contract the band gap of materials. Both new polymers demonstrated extremely short response times of 0.9–1.1 s for bleaching and 0.34–0.35 s for coloring. **P(CNPh-ETTE)** and **P(Py-ETTE)** polymers showed reasonably good contrast (16–23%) and coloration efficiency (120–190 cm²/C) in the visible region (at the maxima of their π - π^* transitions, 540/570 nm), and high contrast and coloration efficiency in the near-infrared region (50–62% and 324–440 cm²/C at 1500 nm, respectively). While the stability of pyridine-functionalized polymer, **P(Py-ETTE)**, was shown to be low (with unstable charge-discharge characteristics, presumably due to protonation of the pyridine ring during redox process), **P(CNPh-ETTE)** demonstrated superior electrochromic performance retaining 91–96% of its electroactivity after 2000 cycles between –0.5 and +1.0 V. DFT calculations on these and related EDOT–TT–EDOT polymers reported by us early have been presented and analyzed to understand the structure-property relationships in this class of electrochromic polymers.

Introduction

Electrochromism is defined as the phenomenon displayed by electrochromic materials that exhibit reversible and stable changes of optical properties (transmittance, reflectance and absorbance) accompanied by the phenomenon of color change when an external electrical stimulus is applied. Hitherto, electrochromic devices (ECDs) fabricated with electrochromic (EC) materials have been utilized in numerous applications such as self-darkening mirrors,¹ smart windows,² displays,³ data storage devices,⁴ sunglasses,⁵ electrochromic fabrics,^{6,7} and others. Semiconductive conjugated polymers are attractive materials for applications in organic electronic devices such as organic photovoltaic cells (OPV),^{8,9} field-effect transistors (OFET),^{10,11} light-emitting diodes (OLED),^{12–14} sensors^{15,16} and ECDs.^{17,18} Compared to inorganic EC materials and small organic molecule EC materials, using conjugated polymers (CPs) as active layers in ECDs has many advantages such as low cost production, high

[†] Electronic supplementary information (ESI) available: DFT calculations on oligomers and polymers with EDOT-TT-EDOT motif; synthesis and characterization of studied monomers and intermediates; copies of ¹H NMR spectra; CV, SEC and SEM data. See DOI: ###

optical contrast, fast switching speed, high coloration efficiency, good optical memory and ease in tailoring their color by structural modifications.

Thieno[3,2-*b*]thiophene (TT) regarded as “star molecule” is widely applied in organic electronic domain. Compared to thiophene, fused TT moiety possess a larger extent of conjugation to give polymers with lower band gap and higher charge carrier mobility.^{19–22} 3,4-Ethylenedioxythiophene (EDOT) is a commercially available and oxidatively polymerizable donor which is polymerized to form PEDOT polymer at relatively low applied potentials.^{23,24} The band gap of PEDOT is of 1.6 eV²³ and the films of the PEDOT polymer change the color from a deep blue in the neutral state to a transmissive sky-blue in the oxidized state.²⁵ In 2010, Skabara et al. reported the compound with EDOT–TT–EDOT motif which showed intramolecular noncovalent S··O interactions (2.87 Å) which planarized the system. The polymer electrochemically obtained from this monomer was electroactive and showed low band gap comparable with PEDOT (1.74 eV from optical measurements and 1.53 eV from electrochemistry).²⁶

Recently, our group has designed novel compounds of EDOT-TT-EDOT type, with different attachments of EDOT units to the TT core, i.e. at 2,5- or 3,6-positions of TT. It has been demonstrated that the polymer obtained from the conjugated 2,5-isomer had a lower band gap (1.82 eV) and showed better EC performance compared to the 3,6-isomer (2.00 eV), in which the conjugation was interrupted at the TT moiety (see also discussion on this issue in the computational section of this paper).²⁷ It was also shown that tetra-EDOT substituted TT monomers can be electropolymerized at either 2,5- or both 2,5- and 3,6- sites depending on the applied potentials giving the polymers with substantially different EC properties.²⁸ Electropolymerization of 2,5-isomers of EDOT-TT-EDOT monomers occurs at lower potentials giving polymers with interesting EC properties. As such, our work on this class of polymers was expanded by exploiting 3,6-sites for further tuning the EC properties of polymers. Different electron donating aryl groups have been introduced as a side functionalization of the polymers resulting in materials with a band gap of ca. 1.8 eV and EC switching on oxidation from blue to transparent near colorless.²⁹ Such type of functionalization not only effect on the energy levels and the band gap of the materials to tune their color changes in ECD but can also change the morphology of materials affecting the other important characteristics of devices (charge/discharge, memory, response time and stability). However, there are no reports on EC materials based on thieno[3,2-*b*]thiophene with electron acceptor groups at the 3,6-sites, while this information would be important for deeper understanding the structure-property relationship and the role of electronic effects in this class of materials on their EC behavior.

Donor-acceptor (D–A) concept in conjugated polymers, introduced by Havinga³⁰ is now widely used in design of novel materials for a wide range of electronic applications. It is especially efficient for reducing and fine tuning the band gap of conjugated polymers to design low band gap polymers for OPV or in OLED with tailored color emission, as well as in design of EC materials. Apart of conventional D–A polymers with alternating the donor and the acceptor fragments in the polymer backbone, side group functionalization has also been used for color modification of EC materials.³¹ Owing to the strong electron-withdrawing character of the pyridine ring and cyanogroup, the pyridyl-based^{32,33} or cyano-based³⁴ D–A structures exhibit several advantages in organic electronics, for example lower band gap, deeper HOMO–LUMO levels and improved short-circuit currents in OPV.

In this paper, two novel polymeric materials based on EDOT-TT-EDOT repeating units decorated with electron-withdrawing 4-cyanophenyl or 4-pyridyl substituents at the positions 3,6- of the TT moiety (**P(CNPh-ETTE)** and **P(Py-ETTE)**, Chart 1), have been synthesized and their EC characteristics have been studied to make a step forward in design of EC materials with tailored properties. Particularly, we have demonstrated that while the effect of side electron-withdrawing groups toward band gap contraction is weaker than their incorporation into the main polymer chain, it is a useful approach for modification of a color palette and other properties of EC materials. Thus, **P(CNPh-ETTE)** polymer showed improved stability and short response time compared to its analog with phenyl group, **P(Ph-ETTE)**. We have also supplemented our experimental results on these and previously studied EDOT-TT-EDOT polymers^{27–29, 35} by DFT calculations for deeper understanding the structure-property relationships in this class of EC materials.

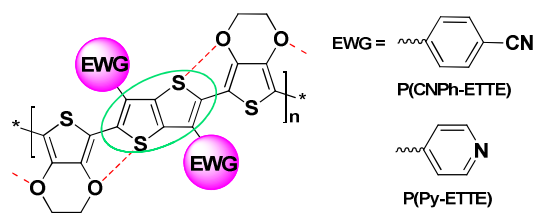


Chart 1. Novel electrochromic polymers **P(CNPh-ETTE)** and **P(Py-ETTE)** where EWG stands for the electron-withdrawing group.

Experimental

Materials

All starting materials were purchased from Energy Chemical, except $\text{Pd}(\text{PPh}_3)_4$ catalyst which was purchased from TCI. Acetonitrile (ACN), dichloromethane (DCM), chloroform (CHCl_3), and tetrahydrofuran (THF) were dried and distilled over calcium hydride under nitrogen. Dioxane, *N,N*-dimethylformamide (DMF) and toluene were dried over 4 Å molecular sieves. 3,6-Dibromothiopheno[3,2-*b*]thiophene (**1**)³⁶ and 2-tributylstannyl-3,4-ethylenedioxythiophene (**5**)³⁷ were synthesized according to the literature procedures.

Instruments

¹H NMR measurements were carried out on a Bruker Advance III nuclear magnetic resonance spectrometer operating at 400 MHz in deuteriochloroform (CDCl_3). Mass spectra were measured on an HRMS Thermo Q-Exactive mass spectrometer. Electron absorption UV–Vis–NIR spectra of the polymeric films were measured on a Lambda 750 spectrophotometer. Electrochemical studies were carried out using a CHI620E electrochemical workstation. The thickness of polymeric films was measured with VK-X200 3D laser scanning confocal microscope. Atomic force microscopy (AFM) images were obtained on a MultiMode 8 Bruker AFM using the tapping mode. Scanning electron microscopy (SEM) images were obtained on a Carl Zeiss ZEISS SUPRA® 55 SEM instrument.

Electrochemistry and spectroelectrochemistry

Electrochemical experiments (electropolymerization, cyclic voltammetry (CV) of monomers and polymers, and chronoamperometry) were performed in a standard three-electrode cell scheme using a silver wire as the pseudo-reference electrode, a platinum wire as the counter electrode and an ITO-coated glass slide or a Pt disk ($d = 2$ mm) as the working electrode. Electropolymerization of the monomers (**Py-ETTE** or **CNPh-ETTE**, 0.6 mM solutions) was performed in anhydrous solvents (DCM/THF, 60/40 v/v for **CNPh-ETTE** or CHCl_3/ACN , 75/25 v/v for **Py-ETTE**) with 0.1 M tetrabutylammonium hexafluorophosphate (TBAPF_6) as the supporting electrolyte at a scan rate of 100 mV/s for 20 cycles under ambient conditions. Under the repetitive CV cycling between the potentials of the neutral (ca. $-0.8 \dots +0.2$ V) and oxidized states (ca. +1.2 V) of the monomers, the colored polymer films were electrodeposited on the Pt disk electrode. Cyclic voltammograms of the polymer films were obtained using the same electrode setup in the monomer-free ACN solution containing 0.1 M TBAPF_6 under nitrogen atmosphere. For spectroelectrochemical experiments (SEC), the polymer films were electrodeposited in the same fashion on an ITO-coated glass electrode and their UV-Vis-NIR spectra at different applied potentials were recorded. The potentials were calibrated versus ferrocene/ferrocenium redox pair (Fc/Fc^+) as an internal standard, which showed the half-wave potential $E_{1/2} = +0.52$ V versus the Ag wire pseudo-reference electrode in $\text{ACN}/\text{TBAPF}_6$ (0.1 M) at 100 mV/s (Fig. S18, ESI). The coloration efficiency (CE) was estimated as a ratio of a change in an optical density of the polymer film between the neutral and doped (colored and bleached) states [$\Delta\text{OD} = \text{OD}_{\text{red}} - \text{OD}_{\text{ox}} = \log(T_{\text{ox}}/T_{\text{red}})$] and the amount of injected/ejected charges per unit area (C/cm^2) ($Q_d = Q/A$, A is an area of the polymer film) at a given wavelength: $\text{CE} = \Delta\text{OD}/Q_d$. Here OD and T are optical densities and transmittances, respectively; subscripts “red” and “ox” denote neutral (colored) and oxidized (bleached) states.

Computational methodology

Computational studies were carried out using density functional theory (DFT) with the Gaussian 09³⁸ package of programs. The geometries were fully optimized for isolated molecules in a gas phase, with no constraints unless otherwise stated (see ESI). Becke's three-parameter hybrid exchange functional³⁹ with the Lee–Yang–Parr gradient-corrected correlation functional (B3LYP)⁴⁰ and Pople's 6-31G split valence basis set supplemented by d-polarization functions for heavy atoms were employed. The restricted Hartree-Fock formalism was used. The electronic structures of B3LYP/6-31G(d) optimized geometries were calculated at the same level of theory. The Molecular orbital density plots have been prepared with GaussView software v5.0.8 at 0.015 isovalues for the surfaces. Optimization of the geometries of the polymers and calculation of their electronic structures were performed using periodic boundary conditions formalism (PBC) at PBC/B3LYP/6-31G(d) level, which generally gives a good estimate of the band gaps of conjugated polymers, including polythiophenes.^{41–43} The PBC calculated HOCO/LUCO energies (highest occupied / lowest unoccupied crystal orbitals) and the band gaps (E_g) were compared with the results based on the oligomers approach of extrapolations of HOMO/LUMO energies (highest occupied / lowest unoccupied molecular orbitals) to the infinite length chain showing good coincidence.

Results and discussion

DFT studies

To understand the structural effect in the polymers with EDOT–TT–EDOT motif, particularly the effect of 3,6-substituents R in 2,5-bis(EDOT)-TT polymers **P(R-ETTE)** (Chart 2) on their geometries, HOMO/LUMO energy levels and the band gaps, we have performed DFT calculations for corresponding oligomers (with $n = 1–6$; up to $n = 10$ in some cases) at B3LYP/6-31G(d) level. The data on the chain length dependences were extrapolated to infinite number of monomer units in the chain ($n = \infty$) and the results were compared with calculations of corresponding polymers by PBC formalism at the same level of theory.

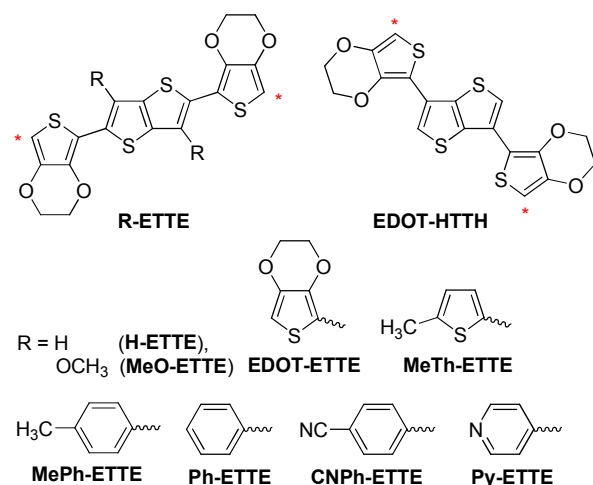


Chart 2. Structures of monomers, oligomers and polymers with EDOT–TT–EDOT motif studied by DFT. Asterisks show the places of connections for oligomers and polymers. In the text, acronyms **(R-ETTE)_n** / **P(R-ETTE)** and **(EDOT-HTTE)_n** / **P(EDOT-HTTH)** are used for corresponding oligomers and polymers. Calculations for **MeTh-ETTE** and **MePh-ETTE** with methyl groups were done to model corresponding polymers with hexyl substituents recently studied in Ref. 29.

Unsubstituted **(H-ETTE)_n** oligomers adopt planar structures due to attractive non-covalent S···O interactions in both EDOT–EDOT and TT–EDOT fragments of the molecules which act to enforce the planarity (see Fig. 1a and Fig. S1a in ESI for hexamer). For the optimized structures, the interatomic S···O distances in both fragments are significantly shorter than the sum of van der Waals radii for sulphur and oxygen ($1.80 + 1.52 = 3.32 \text{ \AA}$) and are in the range of $2.94–2.96 \text{ \AA}$, which is close to the single crystal X-ray diffraction data for short S···O contacts in **R-ETTE** monomer with $R = C_{16}H_{33}$ (2.87 \AA),²⁶ in EDOT–EDOT ($2.91–2.93 \text{ \AA}$)⁴⁴ and EDOT-thiophene oligomers

(2.96, 3.02).⁴⁵ This leads to very planar structure of the main chain: for longer oligomers, the dihedral angles between the TT and EDOT moieties are very small (1–3° for the hexamer and 0.5–1.5° for the decamer). The HOMO and LUMO orbital energies and the HOMO–LUMO gap (ΔE_{HL}) show typical asymptotic dependence on the length chain with saturation at $n \sim 10$ (Fig. 2). As commonly observed for conjugated oligomers,⁴⁶ plots versus reciprocal number of the chain length, $1/n$, are linear for shorter oligomers but tend to deviate from linearity and to saturate for $n > 6$ (Fig. S6 and S7, ESI). We have found that they correlate linearly with empirical parameter $1/n^{1.5}$ and the extrapolated values to $n = \infty$ excellently coincide with HOCO and LUCO energies and the band gaps (E_g) for polymer **P(H-ETTE)** (Fig. 2).⁴⁷

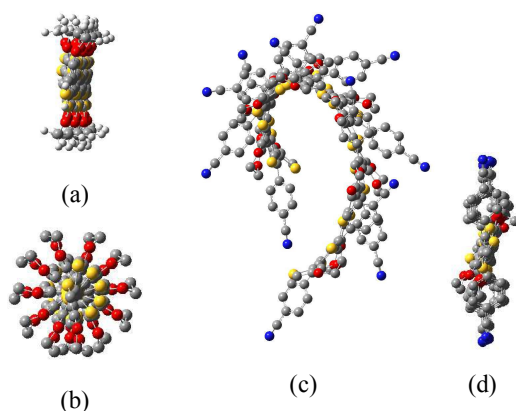


Fig. 1 B3LYP/6-31G(d) optimized geometries of hexamers: (a) **(H-ETTE)₆**, (b) helix conformation of **(EDOT-HTTH)₆**, (c,d) helix and planar conformations of **(CNPh-ETTE)₆**. Views along the oligomers chains are shown; hydrogen atoms in (b-d) are omitted for clarity.

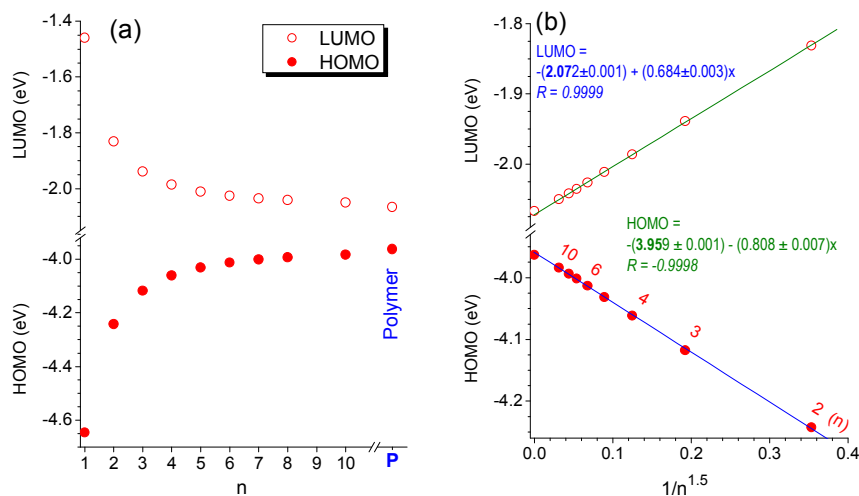


Fig. 2 Chain length dependences of HOMO and LUMO energies for B3LYP/6-31G(d) optimized geometries of **(H-ETTE)_n** oligomers and for **P(H-ETTE)** (by PBC). The lines correspond to linear fitting of the energies vs $1/n^{1.5}$.

Similar planar conformations were found for optimized geometries of **(MeO-ETTE)_n** oligomers (see Fig. S1b in ESI for hexamer), in which case short $S \cdots O$ distances of 2.94–2.96 Å were also found (including $S \cdots OMe$ contacts), although the dihedral angles between the TT and EDOT moieties were slightly larger (3–5° for the hexamer). Compared to **(H-ETTE)_n** oligomers, in its isomer with 3,6-linkage of EDOT to the TT moiety, **(EDOT-HTTH)_n**, the increased steric repulsions between the TT and EDOT rings led to an increased dihedral

angles of $\sim 14\text{--}16^\circ$. Therefore, depending on the signs of the two dihedral angles at the EDOT–TT–EDOT fragment, the oligomers adopted different conformations: twisted conformation to form a helix in the case of the same signs of the dihedrals and planar conformation in the case of the opposite signs of the dihedrals (Fig. 1b and Fig. S2 in ESI). The helix conformation was found to be of lower energy by 5.0 kJ/mol.

An introduction of 3,6-substituents sterically disturbed the main chain of $(\mathbf{R}\text{-ETTE})_n$ oligomers leading to increased dihedral angles in the EDOT–TT–EDOT fragments (Tables S1 and Fig S9 in ESI). Here again, depending on the signs of the rotation at the both sides of the TT moiety, the oligomers adopted helix or planar conformations (Fig. 1c,d and Fig. S3–S5 in ESI). Therefore, calculations have been performed for both conformers to compare their stabilities. In most the cases, the helix conformation was found to be more stable than planar one (by 15.4–16.7 kJ/mol for hexamers with $R = \text{Ph}$, CNPh and Py, and by 3.2 kJ/mol for $R = \text{MeTh}$). For $(\mathbf{EDOT}\text{-ETTE})_n$, planar conformations were found to be more stable (by 3.0 kJ/mol for hexamer). In the helix conformations of $(\mathbf{R}\text{-ETTE})_n$, the EDOT–TT dihedral angles in the backbone were found to be $\sim 19\text{--}26^\circ$ (for hexamers) in the case of $R = \text{MePh}$, Ph, CNPh and Py and somewhat lower ($\sim 6\text{--}14^\circ$) for $R = \text{EDOT}$ and MeTh. Large dihedral angles between the side R groups and the TT moiety ($52\text{--}58^\circ$ for $R = \text{MePh}$, Ph, CNPh, Py and $61\text{--}71^\circ$ for $R = \text{EDOT}$ and MeTh) indicate that they are relatively weakly conjugated to the main chain of the oligomers (and polymers). Also, planar conformations showed somewhat lower EDOT–TT dihedral angles in the backbone and larger dihedral angles between the TT moiety and the side R groups (Table S1 and Fig. S9 in ESI).

In the case of thiophene-substituted oligomers $(\mathbf{R}\text{-ETTE})_n$ ($R = \text{EDOT}$ and MeTh), HOMO and LUMO energy levels for both conformations are almost the same. For $R = \text{Ph}$, CNPh and Py, the difference in energy levels between the helix and planar conformations became larger: the helix conformations showed lower both HOMO and LUMO, and slightly larger HOMO–LUMO energy gaps compared to corresponding planar conformations (Fig. 3). The largest differences were observed for $(\mathbf{CNPh}\text{-ETTE})_n$ oligomers. Thus, for hexamer $(\mathbf{CNPh}\text{-ETTE})_6$ these differences between the helix and planar conformations were found to be -0.13 eV, -0.06 eV and $+0.06$ eV for HOMO, LUMO and ΔE_{HL} , correspondingly (Fig. 3, Tables S1 and Fig. S9 in ESI).

Similarly to unsubstituted oligomers $(\mathbf{H}\text{-ETTE})_n$, with an increase of the chain length of oligomers $(\mathbf{R}\text{-ETTE})_n$, an asymptotic increase of the HOMO and decrease of the LUMO were observed versus n for both helix and planar conformations, with nice linear correlations ($R = 0.996\text{--}0.9999$) versus $1/n^{1.5}$ (Fig. 3). For planar conformations, these linear plots extrapolated to $n = \infty$ excellently coincided with the HOCO and LUCO energies calculated for polymers by PBC approach, whereas extrapolated (to $n = \infty$) HOMO and LUMO energies for helix conformations gave somewhat lower energies (by 0.05–0.12 eV and 0.03–0.08 eV, respectively) (Fig. 3; for other oligomers and polymers see Tables S2, S3 and Fig. S6–S8 in ESI).

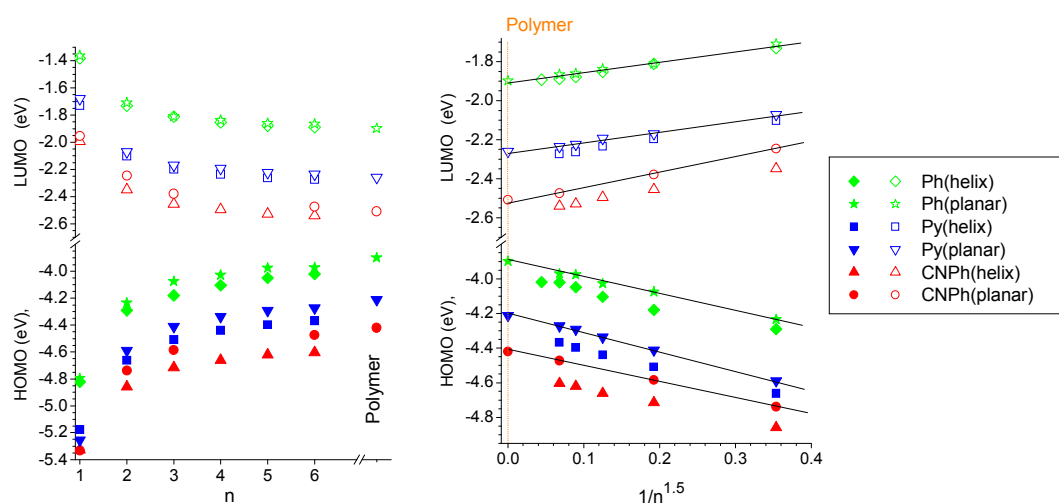


Fig. 3 Chain length dependences of HOMO and LUMO energies for B3LYP/6-31G(d) optimized geometries of helix and planar conformations of $(\mathbf{R}\text{-ETTE})_n$ oligomers ($R = \text{Ph}$, CNPh, Py) for corresponding polymers $\mathbf{P}(\mathbf{R}\text{-ETTE})$ (by PBC). The lines correspond to linear fitting of energies vs $1/n^{1.5}$.

Considering that the HOMO and LUMO energy levels of the oligomers became close to saturation at $n \sim 6$ (Fig. 2 and 3), the hexamers $(\mathbf{R-ETTE})_6$ and $(\mathbf{EDOT-HTTH})_6$ represent sufficiently long conjugated structures to model the localization of frontier orbitals in corresponding polymers. Figure 4 shows HOMO and LUMO orbital densities in $(\mathbf{H-ETTE})_6$ and $(\mathbf{CNPh-ETTE})_6$ hexamers. Distribution of both HOMO and LUMO orbital densities in planar conformation of $(\mathbf{CNPh-ETTE})_6$ is very similar to unsubstituted hexamer $(\mathbf{H-ETTE})_6$ with delocalization along the main chain and with higher orbital densities in the middle part of the molecules. Helix conformation of $(\mathbf{CNPh-ETTE})_6$, which is energetically preferential, show the same fashion and degree of delocalization of HOMO and LUMO orbitals on the π -system of the backbone. Almost no frontier orbital coefficients were observed on the side 4-cyanophenyl groups in $(\mathbf{CNPh-ETTE})_6$. Thus, the electron-withdrawing 4-cyanophenyl side groups electronically effect on the frontier orbital energy levels, decreasing both LUMO and HOMO orbital energies, but do not participate in the orbital delocalization. The effect on the LUMO is somewhat larger than on HOMO resulting in some energy gap contraction in $(\mathbf{CNPh-ETTE})_6$ compared to its analog $(\mathbf{Ph-ETTE})_6$ (by 0.07 eV and 0.11 eV, for helix and planar conformations, respectively; Table S1, ESI). Similar orbitals density distribution is observed for other $(\mathbf{R-ETTE})_6$ oligomers where highly distorted side groups are not involved in HOMO/LUMO delocalization (Fig. S9, ESI). In the case of $(\mathbf{EDOT-HTTH})_6$ with 3,6-linkage of the main chain, the distribution of HOMO and LUMO orbital densities is different clear showing an interruption of the conjugation at the TT unit, with no HOMO/LUMO coefficients at the central C=C atoms of the TT moiety and, accordingly, substantially lower HOMO and higher LUMO energy levels for these oligomers compared to others (Fig. S9 and S10, ESI).

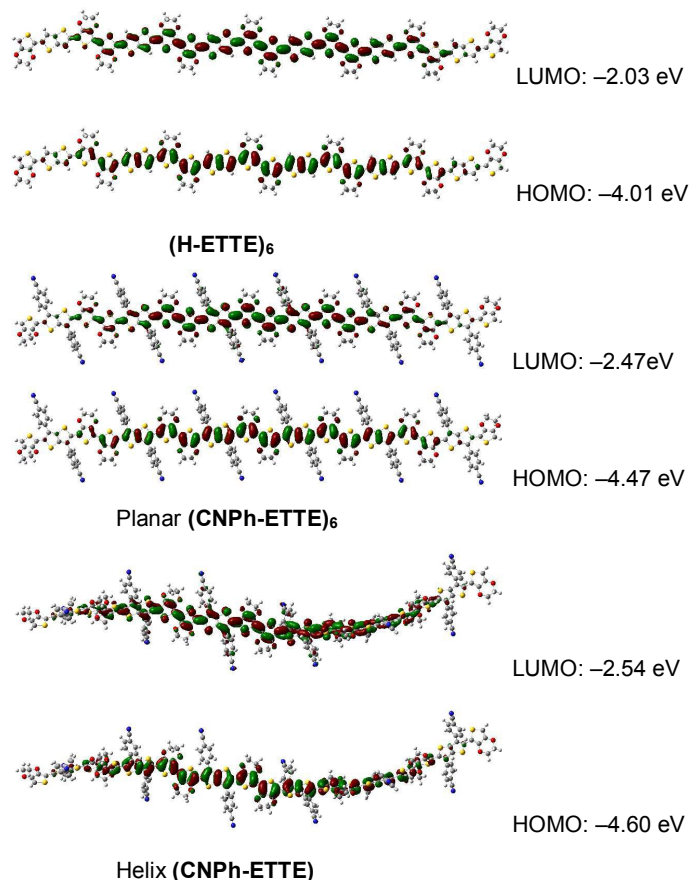


Fig. 4 HOMO and LUMO energies and orbital coefficients for $(\mathbf{H-ETTE})_6$ and $(\mathbf{CNPh-ETTE})_6$ (in both the helix and the planar conformations) from B3LYP/6-31G(d) calculations. For other hexamers, see Fig. S9 in ESI.

Figure 5 summarizes the results on variations in frontier orbital energy levels for structures shown in Chart 2, from monomers (HOMO, LUMO) to polymers (HOCO, LUCO) (see also Fig. S10 in ESI). Electron donating MeO group and thiophene substituents (EDOT, MeTh) increase the HOCO energies of polymers by 0.1–0.14 eV,

but have weaker effect on the band gaps, which are in the range of 1.90–1.93 eV. As expected, Ph group has smaller effect on the HOCO but give somewhat wider band gap for polymer **P(Ph-ETTE)** of 2.00 eV. An introduction of electron withdrawing CNPh and Py substituents substantially decrease both the HOCO and LUCO energy levels and leads to some band gap contraction due to somewhat higher effect on LUCO than on HOCO energy levels (1.91 eV for **P(CNPh-ETTE)**). It should be noted that because computations have been performed in a gas phase, the results characterise electronic states of isolated chains of the oligomeric/polymeric molecules. Solid state effects, intermolecular interactions and morphology of experimentally studied polymers might additionally affect the properties of materials.

Structural isomer of **P(H-ETTE)** with 3,6-linkage in the main polymer chain, i.e. **P(EDOT-HTTH)**, shows lower HOCO (by 0.4 eV) and higher LUCO (by 0.65 eV) resulting in substantially larger (by 1.05 eV) $E_g = 2.95$ eV (Fig. 5). The reason for that is an interrupted conjugation at the TT moiety along the backbone as clear seen from the HOMO/LUMO orbital distribution in the hexamer **(EDOT-HTTH)₆** (Fig. S9, ESI). There are no HOMO or LUMO orbital densities on the central C=C π -bond of the TT moiety and the delocalization of the π -orbitals along the main chain is limited by two EDOTs and two halves of neighboring TT units. Experimentally found values for electrochemically prepared polymers from **EDOT-HTTH** and **H-ETTE** monomers gave substantially smaller difference in their band gap of 0.18 eV only ($E_g = 2.00$ eV and 1.82 eV, respectively).²⁷ This might indicate that electropolymerization of **EDOT-HTTH** occurred not only at the EDOT sites but (partly) at the 2,5-CH of the TT unit extending the conjugation length of resulting material.


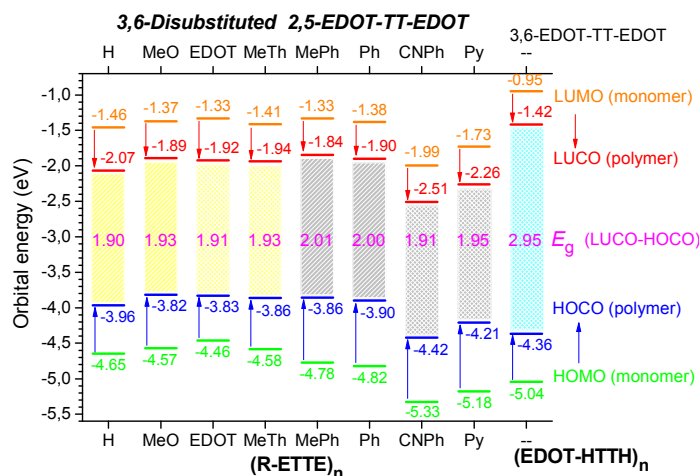


Fig. 5 Evolution of the frontier orbital energy levels from monomers (HOMO, LUMO) to polymers (HOCO, LUCO) and the band gaps of different polymers at B3LYP/6-31G(d) optimized geometries (by PBC for polymers).

Monomer Synthesis

The synthetic route to the target monomers is depicted in Scheme 1. Synthesis of the monomer **Ph-ETTE** by this scheme was recently reported by us.²⁹ We have applied this route to the monomers **CNPh-ETTE** and **Py-ETTE** with electron-withdrawing groups. Suzuki coupling of 3,6-dibromothiopheno[3,2-*b*]thiophenes (**1**)³⁶ with 4-cyanophenyl- or 4-pyridylboronic acids did not worked well in DMF or toluene (in contrast to synthesis of **2a**), but the reflux in dioxane with Pd(PPh₃)₄ as catalyst gave us the desired compounds **2b,c**. Bromination of **2a** (and its analogs with 4-hexylphenyl and 5-hexyl-thienyl groups) with *N*-bromosuccinimide (NBS) proceeded smoothly in chloroform-acetic acid mixture at room temperature to give **3a** with a high yield of 95%.²⁹ Electron-withdrawing substituents at position 3,6- substantially decrease the reactivity of the TT moiety and bromination required overnight heating (at 100°C or at reflux) in DMF to obtain compounds **3b,c** in moderate yields of 60–74 %. Their Stille coupling with 2-tributylstannyl-EDOT (**5**) resulted in the target monomers

CNPh-ETTE and **Py-ETTE** as a greenish-yellow and light yellow solid, respectively. Both monomers have poor solubility in common organic solvents (**Py-EDOT** < **PhCN-EDOT** ~ 2 mM in DCM).

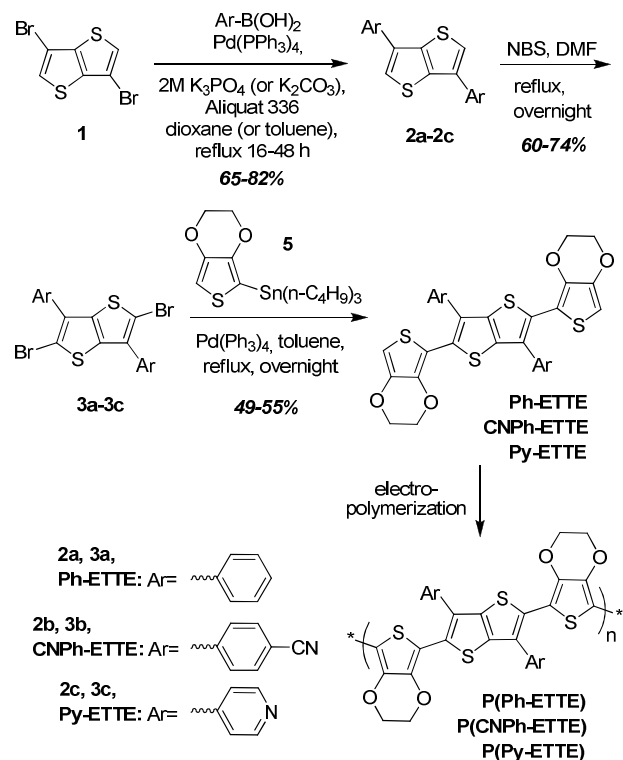

Scheme 1. Synthesis of monomers **Ar-ETTE** and their electropolymerization to **P(Ar-ETTE)**.

Electrochemical Polymerization

The oxidative electropolymerization of monomers **CNPh-ETTE** and **Py-ETTE** (~0.6 mM concentration) was carried out in a potentiodynamic conditions in a mixed solvent (DCM/THF, 60/40 v/v for **CNPh-EDOT** and CHCl_3/ACN , 75/25 v/v for **Py-EDOT**) containing 0.1 M TBAPF₆ as supporting electrolyte. Due to the presence of electron-withdrawing groups, their oxidation appeared at higher potentials ($E_{\text{pa}}^{\text{ox}} = 0.83$ V and 1.11 V, $E_{\text{onset}}^{\text{ox}} = 0.92$ V and 0.80 V, for **CNPh-ETTE** and **Py-ETTE**, respectively) compared to **Ph-ETTE** ($E_{\text{pa}}^{\text{ox}} = 0.80$ V, $E_{\text{onset}}^{\text{ox}} = +0.69$ V²⁹).

Repetitive cyclic voltammetry (CV) scanning between the -0.8 V and $+1.2$ V (for **CNPh-ETTE**) or between the -0.2 and 1.2 V (for **Py-ETTE**) resulted in progressive growth of the new CV waves at lower potentials than oxidation potentials of the monomers indicating on the growing the electroactive polymer films on the Pt electrode surface (Fig. 6a,b).

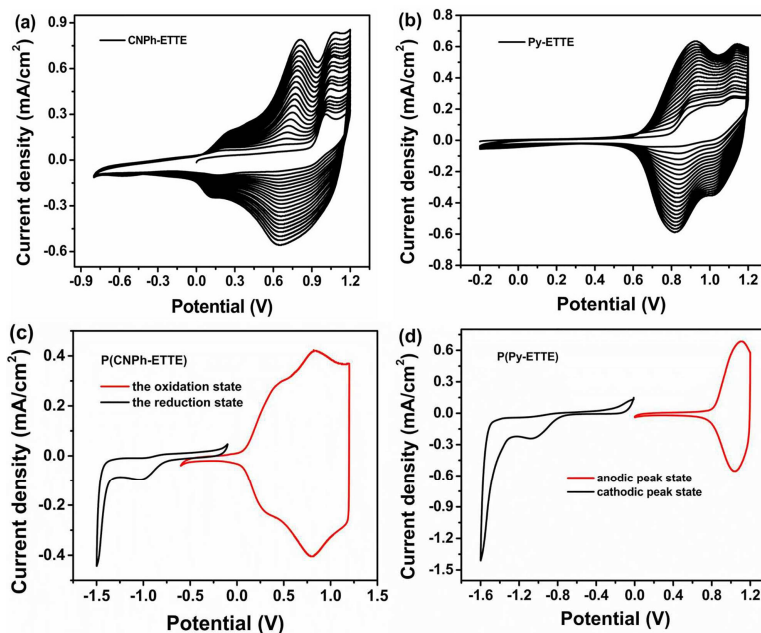


Fig. 6 Potentiodynamic electrochemical polymerization of 0.6 mM monomers: (a) **CNPh-ETTE** (DCM/THF, 60/40, v/v) and (b) **Py-ETTE** (CHCl_3/ACN , 75/25, v/v) with TBAPF_6 (0.1 M) on Pt disk electrode at 100 mV/s (20 cycles are shown). Cyclic voltammograms of electrodeposited polymer films on Pt disk electrode in a monomer-free $\text{ACN}/\text{TBAPF}_6$ (0.1 M) solution at 100 mV/s under nitrogen atmosphere: (c) **P(CNPh-ETTE)** and (d) **P(Py-ETTE)**. Potentials are vs Ag wire.

After electrochemical polymerization, the deposited polymer films were rinsed with ACN to remove the monomers and the electrolyte and their electrochemical response was tested by CV in $\text{ACN}/\text{TBAPF}_6$ (0.1 M) for both p- and n-doping processes (Fig. 6c,d). Polymer **P(CNPh-ETTE)** films showed reversible p-doping with two well-defined reversible redox couples at $E_{\text{pa}}^{\text{ox}}/E_{\text{pc}}^{\text{ox}} = 0.43/0.28$ V and $0.83/0.80$ V versus Ag wire pseudo-reference electrode, which can be attributed to the formation of polarons and bipolarons charge carriers.⁶ Its onset oxidation potential of $E_{\text{onset}}^{\text{ox}} = 0.09$ V is only slightly higher than that of **P(Ph-ETTE)** (0.07 V).²⁹ Apparently, the **P(Py-ETTE)** films showed p-doping at substantially higher potentials with a onset of $E_{\text{onset}}^{\text{ox}} = 0.83$ V (one reversible wave with $E_{\text{pa}}^{\text{ox}}/E_{\text{pc}}^{\text{ox}} = 1.11/1.04$ V). This unexpected result can not be explained by electron-withdrawing character of the 4-pyridyl substituent, which is weaker accepting group compared to 4-cyanophenyl group (compare the HOMO of **CNPh-ETTE** and **Py-ETTE** monomers and polymers in Fig. 5). We rationalize this observation as partial protonation of pyridine rings in **P(Py-ETTE)** during electropolymerization process. Oxidative coupling of the monomer units during electropolymerization results in formation of protons. Pyridine groups present in the monomer **Py-ETTE** and polymer **P(Py-ETTE)** can partially trap these protons before they are reduced at the counter electrode. So, such partial protonation of the pyridine groups might decrease the HOMO energy level of the resulting polymer, as well the degree of polymerization and quality of the polymer films. To check this hypothesis, we treated the **P(Py-ETTE)** film with hydrazine hydrate to deprotonate/dedope the polymer. This treatment resulted in pronounced cathodic shift of **P(Py-ETTE)** oxidation potential to $E_{\text{onset}}^{\text{ox}} = 0.53$ V in the first CV cycle, which, however, returned back to its original value of +0.81 V on further cycling (Fig. S19, ESI). This might indicate that initially deprotonated/dedoped polymer film undergoes (partial) protonation during anodic cycling, perhaps, by protons formed by an oxidation of traces of water⁴⁸ to be present in the film (or in the solvent). Thiophene-pyridine copolymers with pyridine ring in the main chain have been previously studied,^{49–51} and it was shown that the pyridine ring is sufficiently basic to be protonated.⁵¹ Such protonation, however, was not observed when the pyridine ring is inserted in the polymer backbone as a chalcogenodiazolo[3,4-c]pyridine moiety, in which case the basicity of a pyridine ring is substantially decreased, so the polymer is not protonated on electropolymerization or on cycling.^{52, 53}

Both **P(CNPh-ETTE)** and **P(Py-ETTE)** polymers showed irreversible n-doping in cathodic scans with onset reduction potentials of -1.37 V and -1.49 V, respectively (Fig. 6c,d and Fig. S20 in ESI).⁵⁴ The difference between

the reduction potentials of **P(CNPh-ETTE)** and **P(Py-ETTE)** of 0.12 V is in reasonable agreement with the difference in their LUMO energy levels from DFT (0.25 eV, Fig. 5). Irreversible reduction peaks were decreased gradually on cycling indicating on the instability of the polymers toward n-doping, presumably due to the high reactivity of the reduced forms of the polymers⁴⁹ which are degraded by traces of oxygen and/or water.⁴⁸

Cyclic voltammograms of electrodeposited polymer films at different scan rates (from 50 to 500 mV/s) are shown on Fig. 7a,b. The anodic (j_{pa}) and cathodic (j_{pc}) peak current densities for the p-doping/dedoping processes showed excellent linear dependences ($R \geq 0.999$) versus the potential scan rate indicating that both the redox processes are non-diffusional and the polymeric films are well adhered to the Pt electrode surface (Fig. 7c,d).

Also, the amount of a charge and discharge remain constant even at high scan rates, confirming good charging and discharging (doping/dedoping) ability of the polymers.⁵⁵ Moreover, the calculated ratios of anodic/cathodic peak current densities ($j_{pa}/j_{pc} = 1.04$ for **P(CNPh-ETTE)** and 1.27 for **P(Py-ETTE)**, Fig. 7) were smaller than that observed for **P(Ph-ETTE)** films ($j_{pa}/j_{pc} = 1.36$).²⁹ For **P(CNPh-ETTE)**, j_{pa}/j_{pc} is very close to 1, indicating on its excellent reversibility during p-doping/dedoping, which was confirmed by stability test (see below). Surprisingly that **P(Py-ETTE)** showed relatively good reversibility of p-doping/dedoping (as follows from the linear dependences of j_{pa} and j_{pc} vs the scan rate and its j_{pa}/j_{pc} ratio, Fig. 7b,d), although longer stability tests indicated on its degradation (discussed below).

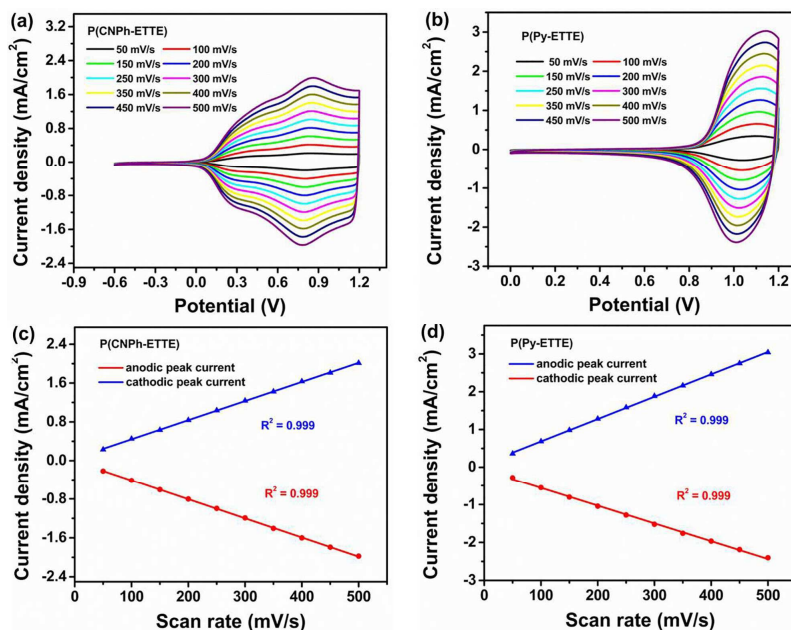


Fig. 7 Cyclic voltammograms (a,b) and scan rate dependences of current densities at peak currents (b,d) of polymeric films on Pt disk electrode in a monomer-free ACN/TBAPF₆ (0.1 M) solution at different scan rates from 50 to, 100, 150, 200, 250, 300, 350, 400, 450 and 500 mV/s: (a,c) **P(CNPh-ETTE)** from -0.6 to 1.2 V; (b,d) **P(Py-ETTE)** from 0 to 1.2 V.

Spectroelectrochemistry and Colorimetry

The spectroelectrochemical experiments (SEC) were carried out to explore the optical changes of the polymer films on p-doping. The films of **P(CNPh-ETTE)** and **P(Py-ETTE)** were electrodeposited potentiodynamically (20 cycles) from their monomer solutions on indium tin oxide (ITO) coated glass slides in the same conditions as described above for CV studies (Fig. S21, ESI). The thicknesses of the films measured by laser scanning confocal microscopy were 100 nm for **P(CNPh-ETTE)** and 105 nm for **P(Py-ETTE)**.

Figure 8 shows SEC properties of the polymers and corresponding colors of the films. In their neutral forms, polymers **P(CNPh-ETTE)** and **P(Py-ETTE)** showed broad structureless $\pi-\pi^*$ transition absorption bands peaked at 580 nm and 545 nm, respectively. Compared to these polymers with electron-withdrawing 3,6-substituents, **P(Ph-ETTE)** polymer in its neutral form demonstrated bathochromically shifted, vibronically resolved absorption

bands peaked at 585 and 638 nm (with a shoulder at 550 nm)²⁹ (Fig. S22a, ESI; compare also the spectra of their monomers in Fig. S23). On applying anodic potentials (from -0.5 to 1.2 V for **P(CNPh-ETTE)** and from -0.2 to $+1.2$ V for **P(Py-ETTE)**), the main peaks of the neutral polymers disappear on the cost of growing polaronic and bipolaronic absorptions of the p-doped polymers in the near infrared (NIR) region.

Quantitatively, the CIE 1976 color coordinates ($L^*a^*b^*$) were measured to track the color changes in the SEC experiments (Fig. 8). In the neutral state (at -0.2 V), **P(CNPh-ETTE)** showed a purple color ($L^*a^*b^* = 35.7, 4.4, -2.5$) and **P(Py-ETTE)** showed a sand-like brown color ($L^*a^*b^* = 39.6, 1.5, -1.4$). When the potentials were raised to $+(0.3-0.4)$ V for **P(CNPh-ETTE)** or $+(0.5-0.6)$ V for **P(Py-ETTE)**, new absorption bands in the NIR region started to appear that corresponded to the formation of charge carriers (polarons and bipolarons) in the materials in accordance with CV data described above. Further increase of the applied potential resulted in a decrease of the absorptions of the neutral polymers and progressive growth of polaronic and bipolaronic bands, which underwent hypsochromic shifts at higher potentials (polaronic band: $1100 \rightarrow 790$ nm and $1060 \rightarrow 770$ nm; bipolaronic band: $\geq 2000 \rightarrow 1300$ nm and $\geq 2000 \rightarrow 1500$ nm, for **P(CNPh-ETTE)** and **P(Py-ETTE)**, respectively; Fig. 8a,b). It should be noted, that the polaronic state bands did not disappear (and their intensities were not decreased) even at high applied potential of $+1.2$ V. This is contrasting with SEC behavior of **P(Ph-ETTE)**, in which case the initially growing polaronic band was hypsochromically shifted ($1070 \rightarrow 870$ nm) reaching the maximum intensity at $+0.7$ V, and then disappeared on the cost of continuing growing of a broad bipolaronic band at higher wavelengths (Fig. S22, ESI).

This difference in SEC behavior and in polaronic band transformations for **P(Ph-ETTE)** and for polymers with electron-withdrawing groups (**P(CNPh-ETTE)** and **P(Py-ETTE)**) defines their different electrochromic properties. **P(Ph-ETTE)** showed deep-blue to transparent EC transition from the neutral to fully oxidized state with $L^*a^*b^*$ evolutions from $(30.5, 3.9, -8.9)$ to $(33.9, -4.0, -13.5)$. The presence of polaronic band in the fully oxidized **P(CNPh-ETTE)** and **P(Py-ETTE)**, blue tail of which is extended to the visible region of the spectrum, led to different color changes. In the fully oxidized state (at $+1.2$ V), **P(CNPh-ETTE)** showed a pale grey-blue hue (max absorbance in the NIR is ~ 0.5 , $L^*a^*b^* = 44.1, -2.4, 4.1$) with residual absorption in the long wavelength visible region of the spectrum. **P(Py-ETTE)** showed the pale grey-green hue in the oxidized state (max absorbance in the NIR is ~ 0.61 , $L^*a^*b^* = 48.4, 3.1, 8.9$), again with some residual long-wavelength absorption in the visible region.

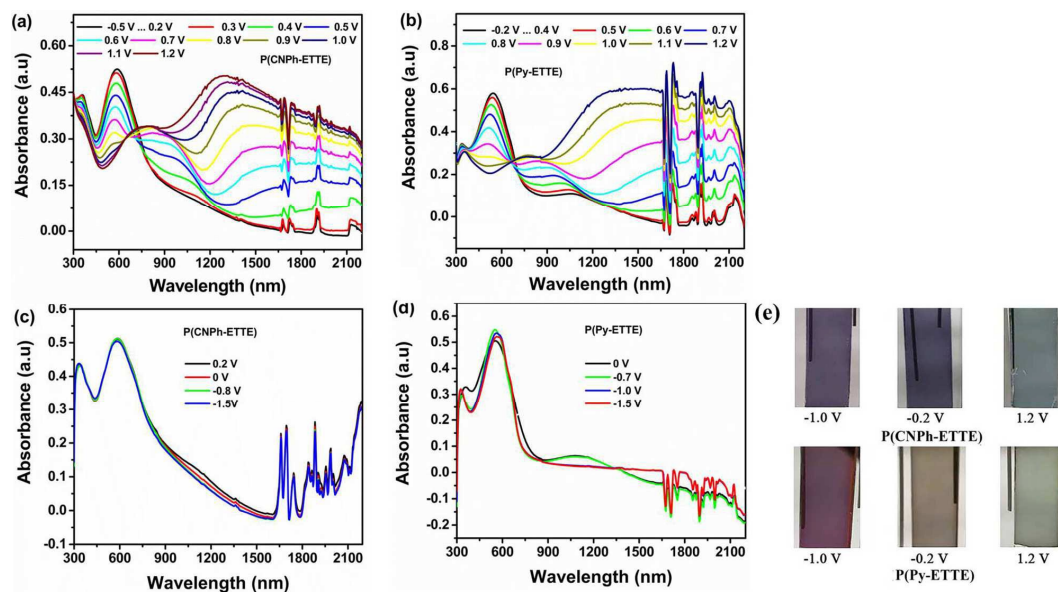


Fig. 8 Spectroelectrograms of polymer films deposited on ITO-coated glass slides in a monomer-free ACN/TBAPF₆ (0.1 M) solution: (a) **P(CNPh-ETTE)** between -0.5 and 1.2 V (oxidation); (b) **P(Py-ETTE)** between -0.2 and 1.2 V (oxidation); (c) **P(CNPh-ETTE)** at $0.2/0/-0.8/-1.5$ V ; (d) **P(Py-ETTE)** at $0/-0.7/-1.0/-1.5$ V ; (e) pictures of the films of **P(CNPh-ETTE)** (thickness, 100 nm) and **P(Py-ETTE)** (thickness, 105 nm) on ITO-coated glass slides at different potentials.

It is evident from the Fig. 8a,b that at low positive or even at negative potentials (−0.5 to +0.2 V) there is a small amount of oxidation states in the neutral **P(CNPh-ETTE)** and **P(Py-ETTE)** polymers, which appear as weak polaronic absorptions in the NIR region. This is sometimes observed in EC conducting polymers when they can not be fully dedoped from the trapped charges^{56,57} and is most likely caused by doping the low-oxidation polymer films with atmospheric oxygen.⁵⁸ While electropolymerization was done under nitrogen atmosphere, the SEC experiments in our setup were not performed *in situ* (the ITO slide with polymer film was removed from the cell, washed, and then placed into the SEC cell of the spectrophotometer for measurements), so some oxidation/doping by an air might occur.

To check the possibility of full dedoping of the polymers and to verify whether the polymers have n-type behavior, we have performed SEC experiments at negative potentials. In the range of 0 to −0.7 V, the **P(Py-ETTE)** film still had a light-brown hue absorbing at $\lambda_{\max} \sim 545\text{--}550$ nm and weak NIR absorption from trapped charge sites. Applying more negative potentials (−1.0 V or below) resulted in full dedoping of the polymer and disappearance of its polaronic band (Fig. 8d). This is accompanied with a minor bathochromic shift of the main band to $\lambda_{\max} = 560$ nm and irreversible color change to purple-red ($L^*a^*b^* = 42.4, 7.4, 3.1$) (Fig. 8d,e). No further changes in spectra or film color were observed on applying more negative potentials down to −1.5 V. In contrast to **P(Py-ETTE)**, we were unable to fully dedope the **P(CNPh-ETTE)** polymer even at the very negative potentials. At −1.5 V it still showed polaronic absorption as a tail to the neutral polymer band in the NIR region (∼900–1400 nm) implying small amount of deeply trapped charges (Fig. 8c). The color of the polymer film was the same at −0.2 and −1.0 V, and almost no spectral changes were observed in the visible and NIR regions from 0 to −1.5 V for this polymer (Fig. 8c,e).

The band gap estimated from the onset absorption of the fully dedoped **P(Py-ETTE)** at −1.0 V was found 1.72 eV,⁵⁹ i.e. somewhat lower than that for **P(Ph-ETTE)** (1.80 eV).²⁹ The band gap decrease of 0.08 eV is in good agreement with DFT calculations on these polymers (0.05 eV, Fig. 5). For **P(CNPh-ETTE)**, DFT predicts slightly lower band gap (by 0.04 eV compared to **P(Py-ETTE)**). Its experimental determination from our SEC data (Fig. 8a) gave the value of 1.54 eV, i.e. substantially lower than that for **P(Py-ETTE)** and **P(Ph-ETTE)**. Although the decrease in the band gap from **P(Ph-ETTE)** to **P(CNPh-ETTE)** is expected and supported by DFT calculations, taking into account that we were unable to achieve full dedoping of **P(CNPh-ETTE)** (so, some polaronic absorption was still present in the polymer), one should take care with the accuracy of the given value, as the contraction of the band gap might be somewhat overestimated.⁵⁹ This is common problem with estimation of the band gaps of conducting polymers with trapped charges from optical data, when full dedoping of the material can not be achieved.²³ The electrochemical and optical properties of both **P(CNPh-ETTE)** and **P(Py-ETTE)** polymers are summarized in Table 1 and their CIELAB color coordinates are given in Table 2.

Table 1. Electrochemical and optical properties of electrosynthesized polymers in films.

Polymer	$E_{\text{onset}}^{\text{ox}}$ (eV)	$E_{\text{onset}}^{\text{red}}$ (eV)	λ_{max} (nm)	λ_{onset} (nm)	$E_{\text{HOMO}}^{\text{a}}$ (eV)	$E_{\text{LUMO}}^{\text{b}}$ (eV)	$E_{\text{g}}^{\text{opt c}}$ (eV)
P(CNPh-ETTE)	0.09	−1.37	580	804 ^d	−4.37	−2.83	1.54 ^d
P(Py-ETTE)	0.83	−1.49	545	720 ^e	−5.11	−3.39	1.72 ^e (1.67) ⁵⁹
P(Ph-ETTE) ²⁹	0.07	–	585, 638	690	−4.35	−2.55	1.80

^a $E_{\text{HOMO}} = -E_{\text{onset}}^{\text{ox}}$ [vs Fc/Fc⁺] + 4.8 (eV).⁶⁰ ^b $E_{\text{LUMO}} = (E_{\text{HOMO}} + E_{\text{g}}^{\text{opt}})$.⁶⁰ ^c $E_{\text{g}}^{\text{opt}} = 1240/\lambda_{\text{onset}}$, where the λ_{onset} is obtained from the absorption edge of the polymers in their neutral state. ^dEstimated at applied potentials of −0.5 to +0.2 V, where full dedoping was not achieved, showing some polaronic absorption (Fig. S24, ESI). ^eEstimated at applied potential of −1.0 V; at more positive potentials, full dedoping was not observed as evidenced by small polaronic peak at ca 1000 nm that gave lower $E_{\text{g}}^{\text{opt}}$ estimations (Fig. S24, ESI).⁵⁹

Table 2. CIE colorimetric data, optical contrast, coloration efficiency and response time of electrosynthesized polymers in films.

Polymer	CIE 1976 color space, $L^*/a^*/b^*$		Optical contrast ΔT , % (λ , nm) ^a	Coloration efficiency CE, cm ² /C, (λ , nm) ^a	Response time, s	
	Neutral state	Oxidized state			Oxidation (bleaching)	Reduction (coloring)
P(CNPh-ETTE)	35.7/4.4/−2.5	44.1/−2.4/4.1	23 (570), 62 (1500)	120 (570), 440 (1500)	0.90	0.34
P(Py-ETTE)	39.6/1.5/−1.4	48.4/3.1/8.9	16 (540), 50 (1500)	190 (540), 324 (1500)	1.10	0.35
P(Ph-ETTE) ²⁹	30.5/3.9/−8.9	33.9/−4.0/−13.5	71 (590), 60 (1500)	309 (590), 174 (1500)	1.80	1.10

^aWavelengths at which ΔT and CE have been measured are given in the parentheses.

Electrochromic switching and the coloration efficiency

For deeper understanding of the electrochromic properties of synthesized polymers, their optical contrast, coloration efficiency and response time were investigated by Vis-NIR spectroscopy (Table 2). The optical contrast of the polymers ΔT (i.e. the differences in transmittances between the neutral and oxidized states) was estimated at two wavelengths: at the main absorptions of the polymers in the visible region and at the absorption of bipolarons in the NIR region (570/1500nm for **P(CNPh-ETTE)** and 540/1500 nm for **P(Py-ETTE)**, Fig. 9a,b). The switching studies were performed using a square wave potential step method with a residence time of 10 s, and the response time (defined as the time required to reach 90% of the full response) was calculated from chronoamperometry measurements (Fig. 9c,d). For **P(CNPh-ETTE)**, the optical contrast estimated by monitoring the transmittance difference between the neutral and oxidized states was 23% at 570 nm and 62% at 1500 nm, with the response times of 0.90 s for bleaching and 0.34 s for coloring. **P(Py-ETTE)** exhibited an optical transmittance contrast of 16% at 540 nm and 50% at 1500 nm, requiring 1.1 s for bleaching and 0.35 s for coloring. For both polymers, the response times are lower than that for reference polymer **P(Ph-ETTE)** (1.80 s for bleaching and 1.10 s for coloring, Table 2²⁹). The favorably high optical contrasts for studied polymers in the NIR region implies that the polymers might be promising candidates for potential applications, such as thermal emissivity applications.⁶¹

The coloration efficiency (CE) is an important parameter of electrochromic materials characterizing the changes in optical densities of materials between the colored and bleached forms as a function of injected/ejected charges. We have estimated the CE values for studied polymers in the visible and in the NIR region from the transmittance profiles of **P(CNPh-ETTE)** and **P(Py-ETTE)**, and compared them with previously studied polymer **P(Ph-ETTE)** (Table 2). In the visible region, the CE of **P(CNPh-ETTE)** and **P(Py-ETTE)** are reasonably high (120 and 190 cm²/C, respectively), comparable with that for a benchmark electrochromic polymer PEDOT (183 cm²/C),⁶² although they are lower than that for **P(Ph-ETTE)** (309 cm²/C). However, in NIR region the coloration efficiencies of **P(CNPh-ETTE)** and **P(Py-ETTE)** are substantially higher (440 and 324 cm²/C, respectively), exceeding that of **P(Ph-ETTE)** (174 cm²/C). For comparison **P(EDOT-ETTE)** polymer showed CE of 148 cm²/C (560 nm) and 235 cm²/C (1600 nm).²⁷ Related polymers of EDOT-X-EDOT type with an electron-deficient heterocyclic moiety X, showed lower (or comparable) coloration efficiencies, e.g. for X = benzo-2,1,3-thiadiazole: 86 cm²/C (428 nm), 109 cm²/C (1100 nm),⁶⁰ X = pyrido-2,1,3-thiazole: 154 cm²/C (431 nm), 257 cm²/C (1337 nm),⁶⁰ X = pyrido-2,1,3-selanzole: 60 cm²/C (433 nm), 144 cm²/C (1200 nm).⁵² X = *N*-alkylbenzotriazole (with an additional dialkoxythiophene moiety in the backbone): 236–335 cm²/C (584–590 nm), 339–426 cm²/C (1600 nm).⁶³

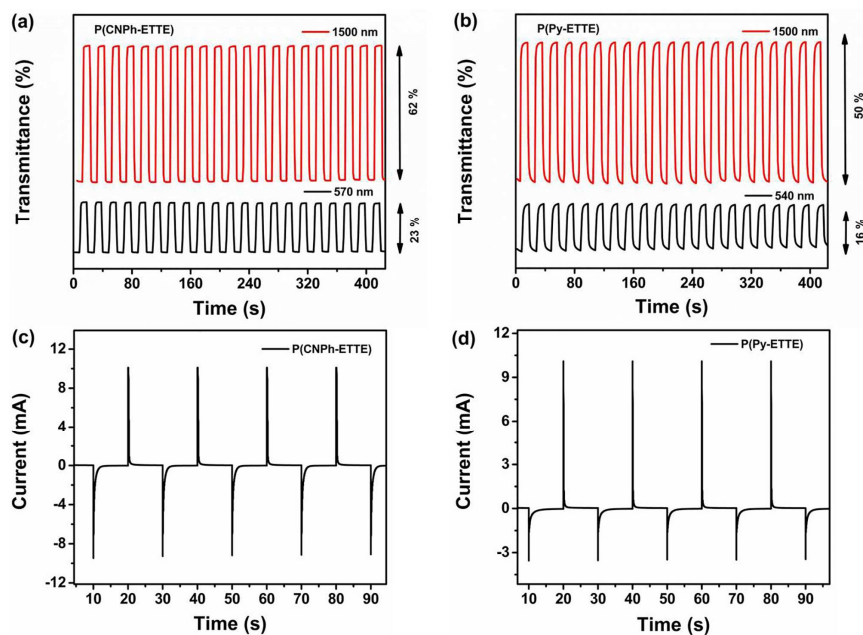


Fig. 9 Optical transmittance changes for polymer films on ITO-coated glass slides in ACN/TBAPF₆ (0.1 M): (a) **P(CNPh-EDOT)** at 570 and 1500 nm, (b) **P(Py-ETTE)** at 540 and 1500 nm. Chronoamperometry with a 10 s delay for each potential: (c) **P(CNPh-ETTE)** between -0.5 and 1.0 V; (d) **P(Py-ETTE)** between -0.2 and 1.2 V.

Morphology of the Electropolymerized Films

The surface morphologies of the polymer films were probed using the atomic force microscopy (AFM) and scanning electron microscopy (SEM). AFM measurements were performed in the glove box under N₂ atmosphere. Fig. 10a,b show AFM images and Fig. 10b,d show SEM images, for **P(CNPh-ETTE)** and **P(Py-ETTE)**, respectively. **P(Py-ETTE)** film has homogeneous and flat surface covered with nanometer-scale round bulbs of about 200 nm with the RMS (root-mean-square) roughness of around 12.5 nm. The surface of **P(CNPh-ETTE)** shows rod-like objects displaying network structure with the RMS roughness of around 32.7 nm. On a macro level, the **P(CNPh-ETTE)** film displays quite rough and interconnected network forming very porous polymer structure (Fig. S25, ESI). Such a porous network structure facilitates reversible doping/dedoping transformations that can explain the relative high stability and fast response time of this polymer.⁶⁴ Both RMS values are higher than in reference polymer **P(Ph-ETTE)** (10.5 nm).²⁹

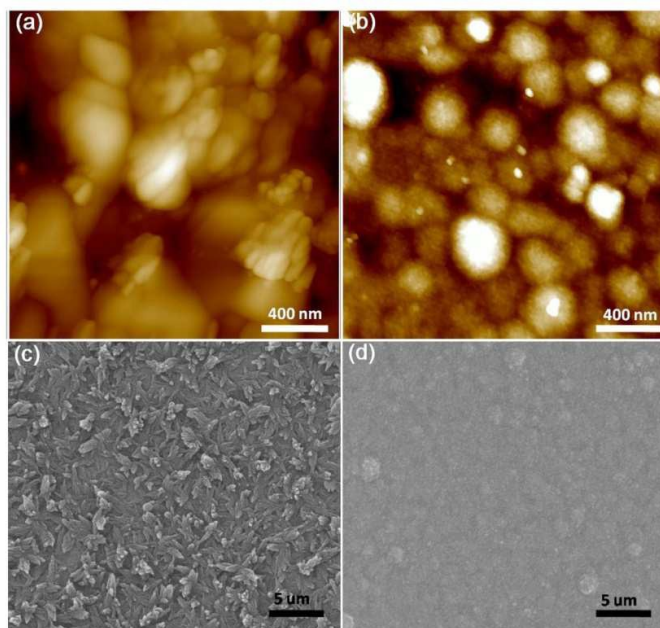


Fig. 10 AFM (a,b) and SEM (c,d; magnification of 25000 \times) topography images of polymer-coated ITO films: (a,c) **P(CNPh-ETTE)**; (b,d) **P(Py-ETTE)**.

Stability

The cycling life time is an important parameter for the electrochromic applications. To explore the stability, the polymer films electrodeposited on Pt electrode were swept repeatedly between the neutral and oxidized states using cyclic voltammetry in ACN/TBAPF₆ (0.1 M) at a scan rate of 150 mV/s under ambient condition (Fig. 11). When scanned between -0.6 V and $+1.2$ V, the redox activity of the **P(CNPh-ETTE)** film remained 95% after 100 cycles and 75% after 1500 cycles (Fig. 11a) (the stability is estimated basing on the peak current ratio). In these conditions, the **P(Ph-ETTE)** film showed substantially poorer stability with progressive decreasing the charge/discharge currents and it retained of only 84% and 30% of its initial activity after 100 and 1000 cycles, respectively (Fig. 11c).

When **P(CNPh-ETTE)** and **P(Ph-ETTE)** are p-doped at high applied potential of $+1.2$ V (Fig. 11a,c), the polymers are overoxidized, which might lead to an irreversible changes in the polymer backbone.⁶⁵ It is known that an overoxidation decreases the redox stability of conducting polymers. Therefore, we repeated the stability tests limiting the maximal applied potentials just above the second oxidation peaks, at which full p-doping of **P(CNPh-ETTE)** and **P(Ph-ETTE)** are already observed. Cycling **P(CNPh-ETTE)** between -0.5 and $+1.0$ V demonstrated excellent stability of its p-doping/dedoping and the polymer retained over 90% of its electroactivity after 2000 cycles (96% and 91% as measured at the first and the second peak currents, j_{pa1} and j_{pa2} , respectively; 94–96% as measured by integration of either p-doping or p-doping/dedoping curves) (Fig. 11b). In the case of **P(Ph-ETTE)**, decreasing the potential range in cycling to 0.90/0.85/0.80 V also improved the redox stability of the polymer, but it was still substantially lower than that of **P(CNPh-ETTE)** (Fig. 11d; Fig. S26 in ESI). Thus, even when cycling to a maximum potential of $V_{max} = 0.8$ V (i.e. just above the second peak in CV), a pronounced decrease in the redox activity of **P(Ph-ETTE)** was observed remaining only 54% of its electroactivity after 2000 cycles.

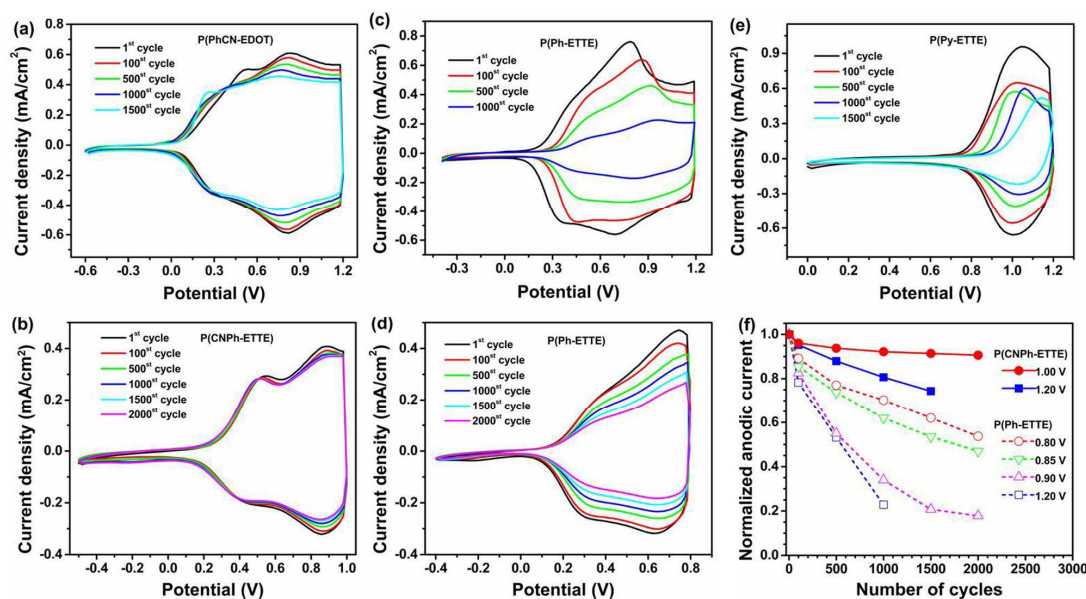


Fig. 11 Stability tests for polymer films on the Pt electrode using CV method in a monomer-free ACN/TBAPF₆ (0.1 M) solution at 150 mV/s under ambient condition: **P(CNPh-ETTE)**, cycled 1500 times between -0.6 and 1.2 V (a) and 2000 times between -0.5 and 1.0 V (b); **P(Ph-ETTE)**, cycled 1000 times between -0.4 and 1.2 V (c) and 2000 times between -0.4 and 0.8 V (d); **P(Py-ETTE)**, cycled 1500 times between 0 and 1.2 V (e). (f) Dependences of anodic current densities (shown on graphs (a-d) and in Fig. S26, normalized to the maximum of the peak current j_{pa} at the 1st cycle) for **P(CNPh-ETTE)** and **P(Ph-ETTE)** versus number of cycles, tested at different potential ranges (maximal potentials are shown on the graph).

The differences in stabilities to p-doping/dedoping for **P(CNPh-ETTE)** and **P(Ph-ETTE)** are clear seen from comparison of the evolution of the current densities at the maxima of their second oxidation waves (normalized to the peak currents at the first cycle) on cycling (Fig. 11f) that confirms the superior stability of **P(CNPh-ETTE)** over **P(Ph-ETTE)**. The reason for such a drastic difference between the structurally close polymers is not fully understood, and requires more detailed studies (possibly, with further variations in substituents at the phenyl ring of **P(Ar-ETTE)**), but we can speculate that it is related to the morphology of the films. From DFT calculations, the geometric and electronic structures of the isolated polymer chains for both polymers are quite close, therefore the electron-withdrawing effect of the side cyano groups on the polymer backbone is unlikely responsible for the observed differences. On the other hand, **P(CNPh-ETTE)** showed more rough rod-like porous structure (Fig. 10a,c and Fig. S25a in ESI) compared to **P(Ph-ETTE)**.²⁹ For structurally related poly(3,4-phenylenedioxythiophene), PheDOT,⁶⁶ it was demonstrated that even small changes in the structure by functionalization of the monomer at the benzene ring lead to drastic changes in the electrodeposited films morphology and surface properties⁶⁷ (see also Ref. 68). It is generally accepted that the polymer films with more open morphology, which provides smaller diffusion distance for dopant ions possess shorter switching times.⁶⁹ Thus, comparative studies on stability of electrochromic poly(3,4-alkylenedioxythiophenes) showed that more porous morphology (by bulky substituents) reduces the number of trapped ion pairs after redox process cycling.⁶⁴ Very recently, Xu and co-workers have studied the long-term stability and the deterioration mechanism of electrochromic poly(3,4-(2,2-dimethylpropylenedioxy)thiophene), **PProDOT-Me2**, on redox cycling between the neutral and p-doped states.⁷⁰ Analysis of thin films of **PProDOT-Me2** by SEM and XPS revealed that the film morphology was changed from a loose irregular network to a compact structure with fibres covered by ions from the electrolyte (ClO_4^- and Li^+) as a result of chemisorption and physisorption during cycling. The adsorbed ions decreased the number of electroactive sites and blocked ion migration channels. Cross-section SEM images and XPS data indicated that trapped electrolyte ions cover the polymer surface more efficiently than inside the film, forming a compact structure and blocking the channels for the injection/ejection of ClO_4^- ions from electrolyte, thus decreasing the lifetime of EC material.

Relatively low charge/discharge stability was observed for **P(Py-ETTE)** film, which possessed only 68% and 54% of electroactivity retained after 100 and 1500 cycles, respectively. Besides that, the anodic peak current of **P(Py-ETTE)** drifted seriously during the cycling process. The poor stability of p-doped states of thiophene, selenophene and pyrrole copolymers with pyridine moiety in the backbone has been reported previously.⁵⁰ We assume that the poor stability of **P(Py-ETTE)** is ascribed to the (partial) protonation of the pyridine rings of the polymer during cycling, which might cause deep trapping the charges and ions in the material and decrease its electroactivity.⁶⁴

Conclusions

In conclusion, two novel electropolymerizable monomers basing on 2,5-(EDOT-TT-EDOT) motif, functionalized with electron-deficient 4-cyanophenyl and 4-pyridyl side groups in the positions 3,6- of the central TT moiety, **CNPh-ETTE** and **Py-ETTE**, have been successfully synthesized. Their electrochemical polymerization lead to electroactive, cathodically coloring electrochromic polymers **P(CNPh-ETTE)** and **P(Py-ETTE)**. Electron deficient side groups decrease the energies of both HOMO and LUMO orbitals of the polymers (located on the main chain of the polymers) and their somewhat stronger influence on the LUMO results in a band gap contraction of the materials compared to the reference polymer with phenyl side groups, **P(Ph-ETTE)** (from 1.80 eV to 1.54–1.72 eV). In combination with different behavior of the polaronic bands formed in the p-doping process of **P(CNPh-ETTE)** and **P(Py-ETTE)** compared to **P(Ph-ETTE)**, this define their different electrochromic behavior as demonstrated in spectroelectrochemical experiments. While **P(Ph-ETTE)** shows deep-blue to transparent EC transition on p-doping, polymers with electron-deficient groups, **P(CNPh-ETTE)** and **P(Py-ETTE)**, demonstrate purple to pale grey-blue and sand brown to pale grey-green color changes. Both **P(CNPh-ETTE)** and **P(Py-ETTE)** demonstrate extremely short switch times of 0.9–1.1 s for bleaching and 0.34–0.35 s for coloring. They show moderate contrast in visible region (16–23% at the maxima of their absorption) and favourably good contrast in NIR region of 50–62% (at 1500 nm). Both **P(CNPh-ETTE)** and **P(Py-ETTE)** show reasonably high coloration efficiencies in the visible region, at maxima of their absorption (120 and 190 cm²/C, respectively) and even higher CE in the NIR region (440 and 324 cm²/C, respectively, at 1500 nm). Possible protonation of pyridine rings during the electropolymerization of **Py-ETTE** and at p-doping/dedoping cycling of **P(Py-ETTE)** decreases the quality of the polymer films and their stability as electrochromic materials on cycling. On the other hand, **P(CNPh-ETTE)** demonstrates superior stability of the color switch retaining 91–96% of its electroactivity after 2000 cycles between –0.5 and +1.0 V. n-Doping of the polymers results in irreversible color changes and degradations of the polymers. Performed DFT calculations on these and related polymers with EDOT-TT-EDOT motif gave some deeper insights into the structural effects of this class of EC polymers on their geometric and electronic structures, particularly on the effects of 3,6-substitution with different side groups. These computational data together with experimental studies on **P(CNPh-ETTE)** and **P(Py-ETTE)** broaden the vision on design of the new promising conjugated electrochromic polymers with tailored properties.

Acknowledgements

This work were financially supported by Shenzhen Key Laboratory of Organic Optoelectromagnetic Functional Materials of Shenzhen Science and Technology Plan (ZDSYS20140509094114164), the Shenzhen Peacock Program (KQTD2014062714543296), Shenzhen Science and Technology Research Grant (JCYJ20140509093817690, JCYJ20160331095335232), Nanshan Innovation Agency Grant (No. KC2015ZDYF0016A), Guangdong Key Research Project (Nos. 2014B090914003, 2015B090914002), Guangdong Talents Project, National Basic Research Program of China (973 Program, No. 2015CB856505), Natural Science Foundation of Guangdong Province (2014A030313800), Guangdong Academician Workstation (2013B090400016). IFP thanks to the Santander Universities Research Mobility Award to support his visit to Shenzhen.

References and Notes


1. D. R. Rosseinsky and R. J. Mortimer, *Adv. Mater.*, 2001, **13**, 783–793.

2. M.-H. Yeh, L. Lin, P.-K. Yang and Z. L. Wang, *ACS Nano*, 2015, **9**, 4757–4765.
3. J. Remmele, D. E. Shen, T. Mustonen and N. Fruehauf, *ACS Appl. Mater. Interfaces*, 2015, **7**, 12001–12008.
4. G. Sonmez and H. B. Sonmez, *J. Mater. Chem.*, 2006, **16**, 2473–2477.
5. A. M. Osterholm, D. E. Shen, J. A. Kerszulis, R. H. Bulloch, M. Kuepfert, A. L. Dyer and J. R. Reynolds, *ACS Appl. Mater. Interfaces*, 2015, **7**, 1413–1421.
6. B. Karabay, L. C. Pekel and A. Cihaner, *Macromolecules*, 2015, **48**, 1352–1357.
7. (a) W. M. Kline, R. G. Lorenzini and G. A. Sotzing, *Color. Technol.*, **130**, 73–80. (b) H. Yu, S. Shao, L. Yan, H. Meng, Y. He, C. Yao, P. Xu, X. Zhang, W. Hu and W. Huang, *J. Mater. Chem. C*, 2016, **4**, 2269–2273.
8. P.-L. T. Boudreault, A. Najari and M. Leclerc, *Chem. Mater.*, 2011, **23**, 456–469.
9. J. Chen and Y. Cao, *Acc. Chem. Res.*, 2009, **42**, 1709–1718.
10. J. Mei and Z. Bao, *Chem. Mater.*, 2014, **26**, 604–615.
11. N. Stutzmann, R. H. Friend and H. Sirringhaus, *Science*, 2003, **299**, 1881–1884.
12. (a) D. F. Perepichka, I. F. Perepichka, H. Meng and F. Wudl, In *Organic Light-Emitting Materials and Devices*; Z. Li, H. Meng (Eds.); CRC Press: Boca Raton, FL, 2007, Chapter 2, pp 45–293. (b) A. C. Grimsdale, K. L. Chan, R. E. Martin, P. G. Jokisz and A. B. Holmes, *Chem. Rev.*, 2009, **109**, 897–1091. (c) I. F. Perepichka, D. F. Perepichka, H. Meng and F. Wudl, *Adv. Mater.*, 2005, **17**, 2281–2305.
13. L. Chen, B. Zhang, Y. Cheng, Z. Xie, L. Wang, X. Jing and F. Wang, *Adv. Funct. Mater.*, 2010, **20**, 3143–3153.
14. A. P. Kulkarni, C. J. Tonzola, A. Babel and S. A. Jenekhe, *Chem. Mater.*, 2004, **16**, 4556–4573.
15. H. Peng, L. Zhang, C. Soeller and J. Trivas-Sejdic, *Biomaterials*, 2009, **30**, 2132–2148.
16. D. T. McQuade, A. E. Pullen and T. M. Swager, *Chem. Rev.*, 2000, **100**, 2537–2574.
17. C. M. Amb, A. L. Dyer and J. R. Reynolds, *Chem. Mater.*, 2011, **23**, 397–415.
18. M. Higuchi, Y. Akasaka, T. Ikeda, A. Hayashi and D. G. Kurth, *J. Inorg. Organomet. Polym Mater.*, 2009, **19**, 74–78.
19. (a) I. McCulloch, M. Heeney, M. L. Chabinyc, D. DeLongchamp, R. J. Kline, M. Cölle, W. Duffy, D. Fischer, D. Gundlach, B. Hamadani, R. Hamilton, L. Richter, A. Salleo, M. Shkunov, D. Sparrowe, S. Tierney, and W. Zhang, *Adv. Mater.*, 2009, **21**, 1091–1109. (b) P. J. Skabara, In: *Handbook of Thiophene-Based Materials: Applications in Organic Electronics and Photonics*; I. F. Perepichka and D. F. Perepichka (Eds), **2009**, John Wiley & Sons, Vol. 1, pp. 219–254.
20. M. E. Cinar and T. Ozturk, *Chem. Rev.*, 2015, **115**, 3036–3140.
21. W. T. Neo, Q. Ye, T. T. Lin, S. J. Chua and J. Xu, *Sol. Energy Mater. Sol. Cells*, 2015, **136**, 92–99.
22. E. Rustamli, S. Goker, S. Tarkuc, Y. A. Udum and L. Toppare, *J. Electrochem. Soc.*, 2015, **162**, G75–G81.
23. L. Groenendaal, G. Zotti, P. H. Aubert, S. M. Waybright and J. R. Reynolds, *Adv. Mater.*, 2003, **15**, 855–879.
24. C. Kvarnström, H. Neugebauer, S. Blomquist, H. J. Ahonen, J. Kankare and A. Ivaska, *Electrochim. Acta*, 1999, **44**, 2739–2750.
25. J. Roncali, P. Blanchard and P. Frère, *J. Mater. Chem.*, 2005, **15**, 1589–1610.
26. G. J. McEntee, P. J. Skabara, F. Vilela, S. Tierney, I. D. W. Samuel, S. Gambino, S. J. Coles, M. B. Hursthouse, R. W. Harrington and W. Clegg, *Chem. Mater.*, 2010, **22**, 3000–3008.
27. X. Zhu, Y. Zhu, I. Murtaza, J. Shi, Y. He, P. Xu, M. Zhu, O. Goto and H. Meng, *RSC Adv.*, 2016, **6**, 75522–75529.
28. J. Shi, X. Zhu, P. Xu, M. Zhu, Y. Guo, Y. He, Z. Hu, I. Murtaza, H. Yu, L. Yan, O. Goto, H. Meng, *Macromol. Rapid Commun.* 2016, **37**, 1344–1351.

29. P. Xu, I. Murtaza, J. Shi, M. Zhu, Y. He, H. Yu, O. Goto and H. Meng, *Polym. Chem.*, 2016, **7**, 5351–5356.
30. E. E. Havinga, W. ten Hoeve, H. Wynberg, *Synth. Met.*, 1993, **55–57**, 299–306.
31. L. Beverina, G. A. Pagani and M. Sassi, *Chem. Commun.*, 2014, **50**, 5413–5430.
32. Y. Sun, S.-C. Chien, H.-L. Yip, Y. Zhang, K.-S. Chen, D. F. Zeigler, F.-C. Chen, B. Lin and A. K. Y. Jen, *J. Mater. Chem.*, 2011, **21**, 13247–13255.
33. H. Zhou, L. Yang, S. C. Price, K. J. Knight and W. You, *Angew. Chem. Int. Ed.*, 2010, **49**, 7992–7995.
34. W. Li, L. Yan, H. Zhou and W. You, *Chem. Mater.* 2015, **27**, 6470–6476.
35. M. Zhu, W. Li, P. Xu, J. Shi, S. Shao, X. Zhu, Y. Guo, Y. He, Z. Hu, H. Yu, Y. Zhu, I. F. Perepichka and H. Meng, *Sci. China Chem.*, 2016, **59**, in press (accepted 27 September, 2016).
36. L. S. Fuller, B. Iddon, K. A. Smith, *J. Chem. Soc., Perkin Trans. 1*, 1997, 3465–3470.
37. S. M. Link, M. Scheuble, M. Goll, E. Muks, A. Ruff, A. Hoffmann, T. V. Richter, J. T. Lopez Navarrete, M. C. Ruiz Delgado and S. Ludwigs, *Langmuir*, 2013, **29**, 15463–15473.
38. Gaussian 09, Revision A02, M. J. Frisch, G. W. Trucks, H. B. Schlegel, G. E. Scuseria, M. A. Robb, J. R. Cheeseman, G. Scalmani, V. Barone, B. Mennucci, G. A. Petersson, H. Nakatsuji, M. Caricato, X. Li, H. P. Hratchian, A. F. Izmaylov, J. Bloino, G. Zheng, J. L. Sonnenberg, M. Hada, M. Ehara, K. Toyota, R. Fukuda, J. Hasegawa, M. Ishida, T. Nakajima, Y. Honda, O. Kitao, H. Nakai, T. Vreven, J. A. Montgomery Jr., J. E. Peralta, F. Ogliaro, M. J. Bearpark, J. Heyd, E. N. Brothers, K. N. Kudin, V. N. Staroverov, R. Kobayashi, J. Normand, K. Raghavachari, A. P. Rendell, J. C. Burant, S. S. Iyengar, J. Tomasi, M. Cossi, N. Rega, N. J. Millam, M. Klene, J. E. Knox, J. B. Cross, V. Bakken, C. Adamo, J. Jaramillo, R. Gomperts, R. E. Stratmann, O. Yazyev, A. J. Austin, R. Cammi, C. Pomelli, J. W. Ochterski, R. L. Martin, K. Morokuma, V. G. Zakrzewski, G. A. Voth, P. Salvador, J. J. Dannenberg, S. Dapprich, A. D. Daniels, Ö. Farkas, J. B. Foresman, J. V. Ortiz, J. Cioslowski and D. J. Fox, Gaussian, Inc., Wallingford CT, 2009
39. (a) A. D. Becke, *Phys. Rev. A*, 1988, **38**, 3098–3100. (b) A. D. Becke, *J. Chem. Phys.*, 1993, **98**, 5648–5652.
40. C. Lee, W. Yang and R. G. Parr, *Phys. Rev. B*, 1988, **37**, 785–789.
41. E. Poverenov, Y. Sheynin, N. Zamoshchik, A. Patra, G. Leitius, I. F. Perepichka and M. Bendikov, *J. Mater. Chem.*, 2012, **22**, 14645–14655.
42. S. S. Zade, N. Zamoshchik and M. Bendikov, *Acc. Chem. Res.*, 2011, **44**, 14–24.
43. S. S. Zade and M. Bendikov, *Org. Lett.*, 2006, **8**, 5243–5246.
44. (a) M. Turbiez, P. Frère and J. Roncali, *J. Org. Chem.* **2003**, *68*, 5357–5360. (b) P. Leriche, M. Turbiez, V. Monroche, P. Frère, P. Blanchard, P. J. Skabara and J. Roncali, *Tetrahedron Lett.*, 2003, **44**, 649–652. (c) J.-M. Raimundo, P. Blanchard, P. Frère, N. Mercier, I. Ledoux-Rak, R. Hierle and J. Roncali, *Tetrahedron Lett.*, 2001, **42**, 1507–1510. (d) K. M. N. de Silva, E. Hwang, W. K. Serem, F. R. Fronczek, J. C. Garno and E. E. Nesterov, *ACS Appl. Mater. Interfaces*, 2012, **4**, 5430–5441.
45. M. Turbiez, P. Frère, M. Allain, C. Videtot, J. Ackermann and J. Roncali, *Chem. Eur. J.*, 2005, **11**, 3742–3752.
46. J. Gierschner, J. Cornil and H.-J. Egelhaaf, *Adv. Mater.* 2007, **19**, 173–191.
47. In more precise approach, the band gap of a conjugated polymer (and in similar fashion its HOMO and LUMO energy levels) can be expressed in terms of H. Kuhn's equation: $E_g = h^2(N + 1)/8md^2(N + l)^2 + V_0(1 - 1/N)$, where h is Planck's constant, m is electron mass, d is the averaged C–C and C=C bond lengths, N is the number of π -electrons, l is the effective length of the π -conjugated system, and V_0 is the constant corresponding to the band gap at infinite length: (a) H. Kuhn, *J. Chem. Phys.* 1949, **17**, 1198–1212. (b) H. Kuhn and C. Kuhn, *Chem. Phys. Lett.*, 1993, **204**, 206–210. (c) G. Taubmann, *J. Chem. Educ.* 1992, **69**, 96–97. (d) J. S. de Melo, L. M. Silva, L. G. Arnaut and R. S. Becker, *J. Chem. Phys.* 1999, **111**, 5427–5433.
48. S. M. Link, M. Scheuble, M. Goll, E. Muks, A. Ruff, A. Hoffmann, T. V. Richter, J. T. Lopez Navarrete, M. C.

- Ruiz Delgado and S. Ludwigs, *Langmuir*, 2013, **29**, 15463–15473.
49. C. J. DuBois and J. R. Reynolds, *Adv. Mater.*, 2002, **14**, 1844–1846.
50. I. H. Jenkins, U. Salzner and P. G. Pickup, *Chem. Mater.*, 1996, **8**, 2444–2450.
51. D. J. Irvin, C. J. DuBois, Jr. and J. R. Reynolds, *Chem. Commun.*, 1999, 2121–2122.
52. S. Ming, S. Zhen, X. Liu, K. Lin, H. Liu, Y. Zhao, B. Lu and J. Xu, *Polym. Chem.*, 2015, **6**, 8248–8258.
53. (a) B. Lu, S. Ming, K. Lin, S. Zhen, H. Liu, H. Gu, S. Chen, Y. Li, Z. Zhu and J. Xu, *New J. Chem.*, 2016, **40**, 8316–8323. (b) H. Zhao, D. Tang, J. Zhao, M. Wang and J. Dou, *RSC Adv.*, 2014, **4**, 61537–61547.
54. For the reduction processes, smaller peaks at ca. $-(1-1.2)$ V are observed due to traces of an oxygen in the polymers films. This is particularly confirmed by minor peaks in the NIR region present in the dedoped polymers at $-0.4/+0.2$ V (see Spectroelectrochemistry section).
55. J. A. Kerszulis, C. M. Amb, A. L. Dyer and J. R. Reynolds, *Macromolecules*, 2014, **47**, 5462–5469
56. J. F. Mike, L. Shao, J.-W. Jeon and J. L. Lutkenhaus, *Macromolecules*, 2014, **47**, 79–88.
57. E. N. Esmer, S. Tarkuc, Y. A. Udum and L. Toppare, *Mater. Chem. Phys.*, 2011, **131**, 519–524.
58. K. Ogawa and S. C. Rasmussen, *Macromolecules*, 2006, **39**, 1771–1778.
59. Estimation of the $E_{\text{g}}^{\text{opt}}$ for **P(Py-ETTE)** at $-0.2 \dots +0.3$ V where minor polaronic band is still present, gave lower value of 1.67 eV, underlying the uncertainty of the $E_{\text{g}}^{\text{opt}}$ determination for not fully dedoped polymers and possible errors. One should be care when using the literature data with the band gap estimations of partly doped polymers.
60. S. Ming, S. Zhen, K. Lin, L. Zhao, J. Xu and B. Lu, *ACS Appl. Mater. Interfaces*, 2015, **7**, 11089–11098.
61. T. T. Steckler, P. Henriksson, S. Mollinger, A. Lundin, A. Salleo and M. R. Andersson, *J. Am. Chem. Soc.*, 2014, **136**, 1190–1193.
62. C. L. Gaupp, D. M. Welsh, R. D. Rauh and J. R. Reynolds, *Chem. Mater.*, 2002, **14**, 3964–3970.
63. W. T. Neo, L. M. Loo, J. Song, X. Wang, C. M. Cho, H. S. O. Chan, Y. Zong and J. Xu, *Polym. Chem.*, 2013, **4**, 4663–4675.
64. J.-H. Huang, C.-Y. Hsu, C.-W. Hu, C.-W. Chu and K.-C. Ho, *ACS Appl. Mater. Interfaces*, 2010, **2**, 351–359.
65. S. A. Sapp, G. A. Sotzing and J. R. Reynolds, *Chem. Mater.*, 1998, **10**, 2101–2108.
66. (a) S. Roquet, P. Leriche, I. Perepichka, B. Jusselme, E. Levillain, P. Frère and J. Roncali, *J. Mater. Chem.*, 2004, **14**, 1396–1400. (b) I. F. Perepichka, S. Roquet, P. Leriche, J.-M. Raimundo, P. Frère and J. Roncali, *Chem. Eur. J.*, 2006, **12**, 2960–2966.
67. (a) C. R. Szczepanski, I. M'Jid, T. Darmanin, G. Godeau and F. Guittard, *J. Mater. Chem. A*, 2016, **4**, 17308–17323. (b) T. Darmanin, J.-P. Laugier, F. Orange and F. Guittard, *J. Colloid Interface Sci.*, 2016, **466**, 413–424.
68. T. Darmanin and F. Guittard, *Progr. Polym. Sci.*, 2014, **39**, 656–682.
69. (a) H. Yashima, M. Kobayashi, K. B. Lee, D. Chung, A. J. Heeger and F. Wudl, *J. Electrochem. Soc.*, 1987, **134**, 46–52. (b) A. A. Argun, P. H. Aubert, B. C. Thompson, I. Schwendeman, C. L. Gaupp, I. Hwang, N. J. Pinto, D. B. Tanner, A. G. MacDiarmid and J. R. Reynolds, *Chem. Mater.*, 2004, **16**, 4401–4412.
70. S. Guan, A. S. Elmezayyen, F. Zhang, J. Zheng and C. Xu, *J. Mater. Chem. C*, 2016, **4**, 4584–4591.

Table of Contents

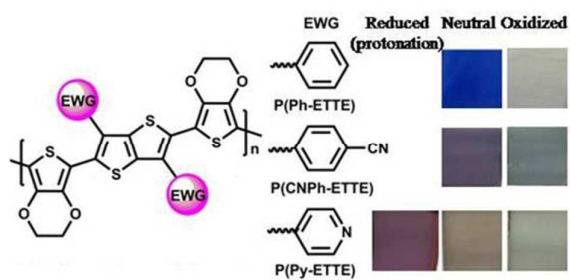

Electron-deficient cyanophenyl side groups decrease the response time and drastically improve the stability of electrochromic polymers.