

## Research Article

# Antibacterial and Antibiofilm Activities of the Photothermal Therapy Using Gold Nanorods against Seven Different Bacterial Strains

Juan Carlos Castillo-Martínez,<sup>1</sup> Gabriel Alejandro Martínez-Castañón,<sup>1</sup>  
Fidel Martínez-Gutiérrez,<sup>2</sup> Norma Verónica Zavala-Alonso,<sup>1</sup> Nuria Patiño-Marín,<sup>1</sup>  
Nereyda Niño-Martínez,<sup>3</sup> V. Zaragoza-Magaña,<sup>4</sup> and C. Cabral-Romero<sup>4</sup>

<sup>1</sup>Ciencias Odontológicas, Facultad de Estomatología, UASLP, Avenida Manuel Nava No. 2, Zona Universitaria, CP 78290, SLP, Mexico

<sup>2</sup>Facultad de Ciencias Químicas, UASLP, Avenida Manuel Nava S/N, Zona Universitaria, CP 78290, SLP, Mexico

<sup>3</sup>Facultad de Ciencias, UASLP, Avenida Salvador Nava No. 2, Zona Universitaria, CP 78290, SLP, Mexico

<sup>4</sup>Facultad de Odontología, Universidad Autónoma de Nuevo León, UANL, CP 64460, Monterrey, NL, Mexico

Correspondence should be addressed to Gabriel Alejandro Martínez-Castañón; [mtzcastanon@ciencias.uaslp.mx](mailto:mtzcastanon@ciencias.uaslp.mx) and C. Cabral-Romero; [claudiohubble@hotmail.com](mailto:claudiohubble@hotmail.com)

Received 25 February 2015; Accepted 16 April 2015

Academic Editor: Andrea Falqui

Copyright © 2015 Juan Carlos Castillo-Martínez et al. This is an open access article distributed under the Creative Commons Attribution License, which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

The objective of this work was to determine the bactericidal and antibiofilm activities of gold nanorods (AuNRs) using plasmonic photothermal therapy (PPTT) against oral microorganisms. AuNRs were synthesized by the seed and growth solution method and the gold nanoclusters were characterized with a size of  $33.2 \text{ nm} \pm 2.23$  length and  $7.33 \text{ nm} \pm 1.60$  width. The efficacy of PPTT related to its temperature was done reaching  $67^\circ\text{C}$ . Minimum inhibitory concentration (MIC) and minimum bactericide concentration (MBC) of AuNRs and AuNRs PPTT were determined against *Enterococcus faecalis*, *Staphylococcus aureus*, *Streptococcus mutans*, *Streptococcus sobrinus*, *Streptococcus oralis*, *Streptococcus salivarius*, and *Escherichia coli* growth. The antibiofilm activity of AuNRs was explored by fluorescence microscopy. After experimental analyses, AuNRs PPTT shows better results in MICs and MBCs, when it was compared with AuNRs alone. The laser employed to activate the AuNRs had no antibacterial effect against oral microbes. The MICs and MBCs values were higher for *S. aureus* and *E. coli* and lower against *S. oralis*. Surprisingly, the AuNRs alone presented a high antibiofilm activity, inhibiting the biofilm formation of *S. mutans*. Altogether, these results strongly suggest that AuNRs could be an interesting option to control oral biofilms.

## 1. Introduction

Photodynamic therapy (PDT) is an effective treatment to kill both eukaryote and prokaryote cells [1, 2]. It uses a drug called photosensitizer and a particular type of light. When photosensitizer is exposed to a specific wavelength of light, it produces a form of oxygen that kills nearby cells. However, it is useless on infected areas without oxygen such as dentinal tubules and roots. The plasmonic photothermal therapy (PPTT) could be more efficient to eliminate microorganisms through its local hyperthermia mechanism [3]. PPTT has been important in the last years in the medicine

field due to its capacity of absorbing visible light. At the same time, gold nanoparticles with nonspherical shape, such as gold nanorods, and polygonal particles have the capacity of absorbing near-infrared (NIR) light that is within an appropriate wavelength window for therapeutic applications. One of the potential applications of gold nanoparticles with NIR absorption capabilities is in the hyperthermia. Hyperthermia can be used as a possible mechanism to kill bacteria selectively by combining the use of laser and functional gold nanoparticles. When nanorods are in contact with the bacterial cells and this is followed by laser irradiation, the overheating effects can rapidly destroy the bacterial cells

[4, 5]. The position of the plasmon maximum is related to the particle size (larger diameter results in a longer wavelength) and the peak width to size dispersion [6]. Knowing this, we can increase the antimicrobial potential of nanoparticles to lyse entire bacterial communities.

The increasing development of multidrug-resistant strains among pathogen microbes has become one of most important problems in medicine worldwide [7]. Great advances in nanotechnology have provided a solid foundation for using nanoparticles (NPs) in the fight against pathogen microorganisms, including multidrug resistant bacteria [8–11]. Several studies have investigated the efficacy of PDT for disinfection of oral pathogens; however the use of PPTT against oral pathogens has not been enough explored. In this work we reported the bactericidal activity of gold nanorods against oral microorganisms. In this work the minimum inhibitory concentration (MIC) and minimum bactericide concentration (MBC) of the AuNRs combined with PPTT on seven different strains of oral bacteria were determined. Additionally the antibiofilm properties of AuNRs were analyzed by fluorescence microscopy.

## 2. Materials and Methods

**2.1. Gold Nanorods Synthesis.** For the preparation of AuNRs, seed and growth solutions were made using the method reported by Nikoobakht and El-Sayed (2003) as briefly described below [12]. Seed solution: 5 mL of  $5 \times 10^{-4}$  M HAuCl<sub>4</sub> solution was added to 5 mL of 0.20 M CTAB solution. To this solution, under magnetic stirring, 0.60 mL of ice-cold NaBH<sub>4</sub> was added. The stirring continued during 2 additional minutes. Growth solution: 0.35 mL of 0.0040 M AgNO<sub>3</sub> solution and 5 mL of  $1 \times 10^{-3}$  M of HAuCl<sub>4</sub> solution were mixed with 5 mL of 0.20 M CTAB solution. After gently mixing, 70  $\mu$ L of 0.0788 M ascorbic acid solution was added. To form AuNRs the final step was the addition of 12  $\mu$ L of the seed solution to the growth solution at 27–30°C. The color of the solution gradually changed within 10–20 min. After the synthesis, centrifugation at 13000 rpm at 25°C for 30 minutes was used to eliminate unreacted CTAB and other subproducts of the reaction [13].

**2.2. Characterization of AuNRs.** Vis-NIR absorption spectra were obtained using a CHEMUSB4-VIS-NIR (Ocean optics) spectrophotometer. Transmission electron microscopy (TEM) images were obtained before and after irradiation of AuNRs with the NIR laser to observe any structural changes using a JEOL JEM1230 microscope operating at an acceleration voltage of 100 kV. TEM images of the prepared NRs were used for the size distribution measurements; the size of 200 particles was measured to obtain the average size.

**2.3. Light Source.** A NIR laser (Quantum IR 810, Laser Systems) with a wavelength of 810 nm and a 200 mW broadcast power was used for all experiments.

**2.4. Characterization of Photothermal Efficiency of AuNRs.** Temperature test was done applying the 810 nm NIR laser for 20 minutes to 50 mL of deionized water and centrifuged

AuNRs. Evaluation of the temperature was done every 30 seconds with a digital thermometer (FLUKE SI II) and the subsequent observation of the nanorods using the TEM [14].

**2.5. Antibacterial Activity of AuNRs by Microdilution Assay.** Strains of *Enterococcus faecalis* (ATCC 29212), *Staphylococcus aureus* (ATCC 29213), *Streptococcus mutans* (ATCC 25175), *Streptococcus sobrinus* (ATCC 27351), *Streptococcus oralis* (ATCC 10557), *Streptococcus salivarius* (ATCC 7073), and *Escherichia coli* (ATCC 25922) were used at 0.5 of the McFarland Scale as determined with a Spectronic 21D spectrophotometer (Milton Roy). To determine MIC and MBC we employed the broth microdilution method according to the NCCLS 2003 standard in three groups: group 1: AuNRs, group 2: AuNRs with PPTT, and group 3: NIR laser. Concentrations of AuNRs ranged from 196 to  $0.37 \mu\text{g}\cdot\text{mL}^{-1}$ ; 100  $\mu$ L of bacterial suspension was added to each well (approximately  $2 \times 10^4$  CFU $\cdot\text{mL}^{-1}$  in each well) [15]. The MIC was read after 24 h of incubation at 37°C. In some cases (groups 2 and 3), laser was applied in each well during 20 minutes. After determining the MIC, Each bacteria was extended on agar plates to determine the MBC. The agar plate was incubated at 37°C for 24 hours to determine the cutoff. All experiments were repeated three times to ensure the veracity of results.

**2.6. SEM Observation of Enterococcus faecalis.** After *E. faecalis* treatment with the AuNRs and AuNRs PPTT, *E. faecalis* dispersion was passed through a syringe filter (0.2  $\mu$ m of pore size) and then they were fixed, dehydrated, and gold sputtered to observe them in a JEOL JSM-6510 scanning electron microscope.

**2.7. Antibiofilm Activity of Gold Nanorods.** With the intention to evaluate the ability of AuNRs for killing cells associated with oral biofilms, the antibiofilm activity of AuNRs was evaluated by fluorescence microscopy. The protocol for this study was as described above with a slight modification. In this study, the inoculums (*S. mutans*, *S. gordonii*, and *S. aureus*) maintained at 37°C were exposed to 150  $\mu\text{g}/\text{mL}$  as final concentration of AuNRs at varying time intervals such as 0 and 18 hours after inoculation. As a positive inhibition control, 1.2  $\mu\text{g}/\text{mL}$  of chlorhexidine was used. After incubation for 24 hours, the cells were stained with 20  $\mu\text{M}$  SYTO 9 (green fluorescent nucleic acid stain for living cells (Invitrogen, Carlsbad, CA)) [16, 17] and allowed to stand for 30 minutes at room temperature in the dark. Subsequently, the cells were gently washed with sterile water and observed under fluorescence microscopy at 485 nm (Thornwood, NY). The images were analyzed by using AxioVision software (Thornwood, NY).

## 3. Results

**3.1. Synthesis and Characterization of AuNRs.** Figure 1 shows TEM images of the AuNRs before and after irradiation with the NIR laser; the as synthesized AuNRs show a uniform size distribution with a size of  $33.2 \pm 2.23$  nm length and  $7.33 \pm 1.60$  nm width (Figure 1(a)). In the Vis-NIR absorption spectrum, transversal and longitudinal plasmon peaks were

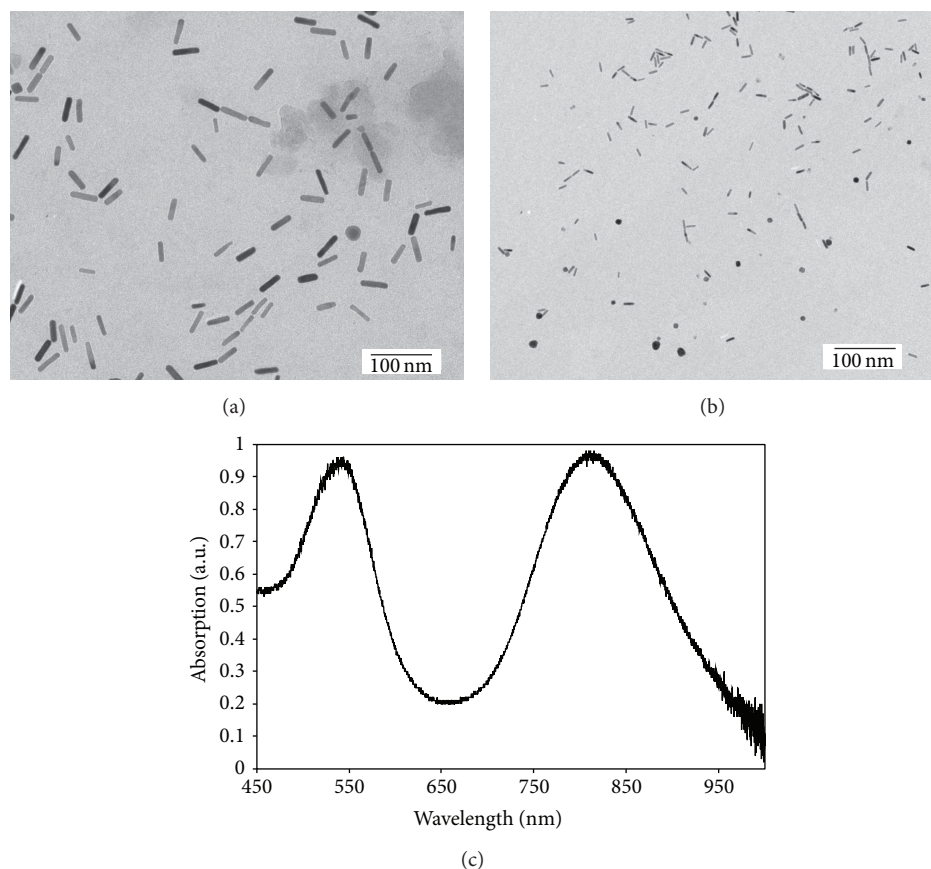


FIGURE 1: Characterization of gold nanorods. (a) TEM image of AuNRs: it clearly shows the rod shape of these nanostructures. (b) TEM image of AuNRs after laser exposition showing no changes in the morphology of gold nanorods. (c) Vis-NIR absorption spectrum: transversal and longitudinal plasmon peaks were observed at 540 nm and 810 nm, respectively.

observed at 540 nm and 810 nm, respectively (Figure 1(c)). No structural changes were found in AuNRs after 20 minutes of laser irradiation (Figure 1(b)).

The characterization of the photothermal efficiency of AuNRs is shown in Figure 2. A maximum temperature of 67°C was obtained within 15 minutes of laser application; after that time the temperature was constant until the experiment was completed (20 minutes).

**3.2. Antibacterial Test.** The results of the antibacterial test are presented as average values in Table 1 and Figure 3. MIC values ranged from 0.45 to 6.88  $\mu\text{g}\cdot\text{mL}^{-1}$ ; and MBC values ranged from 0.83 to 10.84  $\mu\text{g}\cdot\text{mL}^{-1}$ . The MIC and MBC are lower for the AuNRs combined with PPTT if compared with AuNRs. The laser group has no antibacterial effect. For a given group, the MIC and MBC are higher for *S. aureus* and *E. coli* and lower for *S. oralis*.

In order to determine whether the gold nanorods are immediately effective for the bacterial growth inhibition an experiment with different analysis times at 0, 5, 15, 30, and 60 minutes was performed; results are shown in Figure 4, as we can see gold nanorods are able to Lower the bacteria population as low as 30% since the 5 minutes of contact.

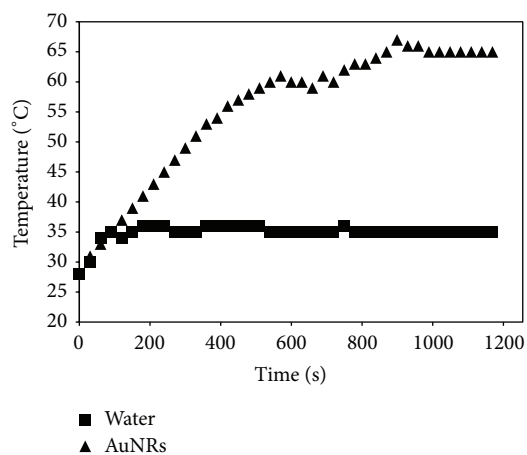


FIGURE 2: Characterization of the photothermal efficiency of AuNRs. A maximum temperature of 67°C was obtained within 15 minutes of laser application; after that time the temperature was constant until the experiment was completed (20 minutes).

Figures 5(b) and 5(c) show SEM images of *E. faecalis* after their treatment with AuNRs and AuNRs PPTT, respectively; compared with a control group (bacteria without any

TABLE 1: Minimum inhibitory concentration (MIC) and minimum bactericide concentration (MBC) of AuNRs and AuNRs PPTT.

| Microorganisms       | MIC                | MIC range | MBC                 | MBC range |
|----------------------|--------------------|-----------|---------------------|-----------|
| AuNRs                |                    |           |                     |           |
| <i>E. faecalis</i>   | <b>1.41 ± 0.69</b> | 1.50–0.37 | <b>4.7 ± 1.64</b>   | 6.12–3.0  |
| <i>S. aureus</i>     | <b>6.52 ± 4.78</b> | 12.50–1.5 | <b>10.84 ± 6.81</b> | 24.5–1.5  |
| <i>S. mutans</i>     | <b>2.20 ± 1.19</b> | 3.00–0.37 | <b>5.08 ± 3.15</b>  | 12.5–3    |
| <i>S. sobrinus</i>   | <b>1.84 ± 1.75</b> | 6.12–0.37 | <b>2.86 ± 2.05</b>  | 6.12–0.75 |
| <i>S. oralis</i>     | <b>2.00 ± 0.75</b> | 3.00–1.5  | <b>2.5 ± 0.75</b>   | 3.0–1.5   |
| <i>S. salivarius</i> | <b>4.38 ± 4.51</b> | 12.25–1.5 | <b>6.09 ± 3.77</b>  | 12.25–3   |
| <i>E. coli</i>       | <b>6.88 ± 7.97</b> | 24.5–0.75 | <b>7.44 ± 7.54</b>  | 24.5–3    |
| AuNRs PPTT           |                    |           |                     |           |
| <i>E. faecalis</i>   | <b>0.45 ± 0.16</b> | 0.75–0.37 | <b>0.83 ± 0.25</b>  | 1.5–0.75  |
| <i>S. aureus</i>     | <b>3.9 ± 3.52</b>  | 12.5–1.5  | <b>6.12 ± 2.74</b>  | 12.5–3.0  |
| <i>S. mutans</i>     | <b>0.99 ± 0.81</b> | 3.0–0.37  | <b>2.17 ± 1.68</b>  | 6.1–0.75  |
| <i>S. sobrinus</i>   | <b>0.58 ± 0.20</b> | 0.75–0.37 | <b>1.04 ± 0.45</b>  | 1.5–0.75  |
| <i>S. oralis</i>     | <b>0.62 ± 0.19</b> | 0.75–0.37 | <b>0.87 ± 0.37</b>  | 1.5–0.37  |
| <i>S. salivarius</i> | <b>0.74 ± 0.46</b> | 1.5–0.37  | <b>1.16 ± 0.76</b>  | 1.5–0.75  |
| <i>E. coli</i>       | <b>1.25 ± 0.37</b> | 1.5–0.75  | <b>2.08 ± 0.90</b>  | 3.0–0.75  |

All values are expressed as  $\mu\text{g/mL}$ . The laser group shows no antibacterial effect.

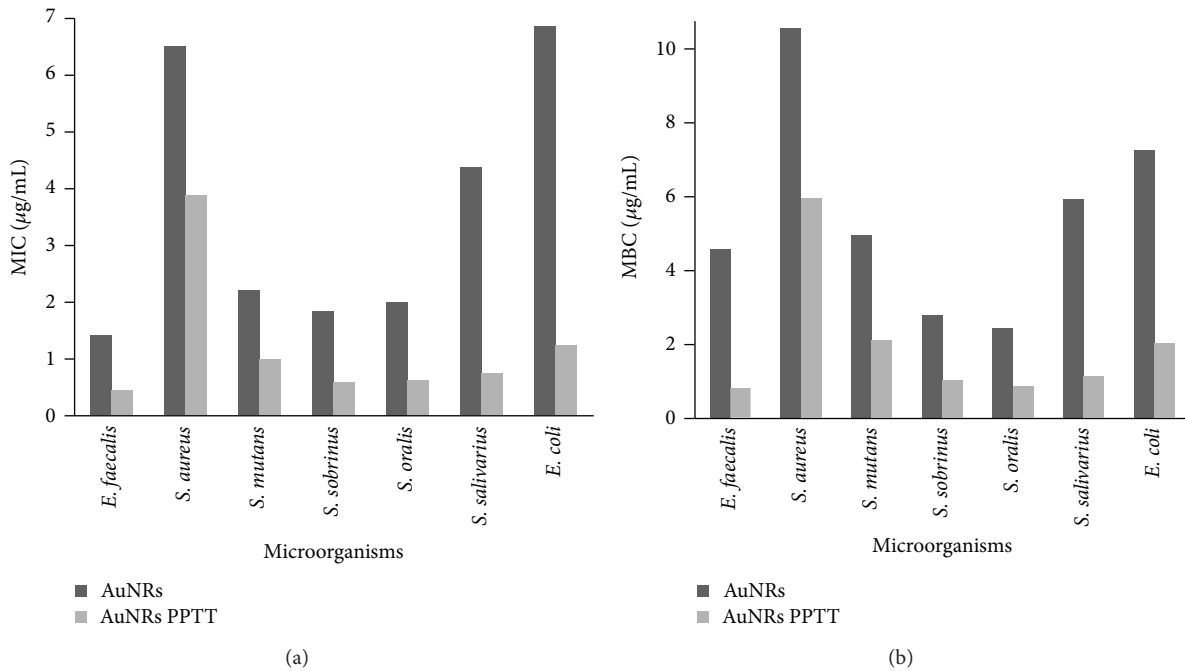


FIGURE 3: (a) Minimum inhibitory concentration and (b) minimum bactericide concentration of AuNRs and AuNRs PPTT.

treatment, Figure 5(a)) we can see that they have lost their morphology and volume, as a consequence of the damage in the bacteria surface.

**3.3. Antibiofilm Activity of Gold Nanorods.** In the previous experiments we measured the bactericidal activity of AuNRs. In order to analyze the possible biofilm inhibition of oral bacteria by gold nanorods, the antibiofilm activity of AuNRs was determined by fluorescence microscopy at different

postinoculation times. The results showed a complete inhibition of biofilm formation by chlorhexidine and AuNRs, compared to control (Figure 6). The results did not change when AuNRs were added at different postinoculation times. We tested the biofilm inhibitory activity at 0, 4, 8, and 18 hours postinoculation times, obtaining similar results, a dark background indicating the absence of living cells. These data indicate that AuNRs have an antibiofilm activity effective as chlorhexidine.

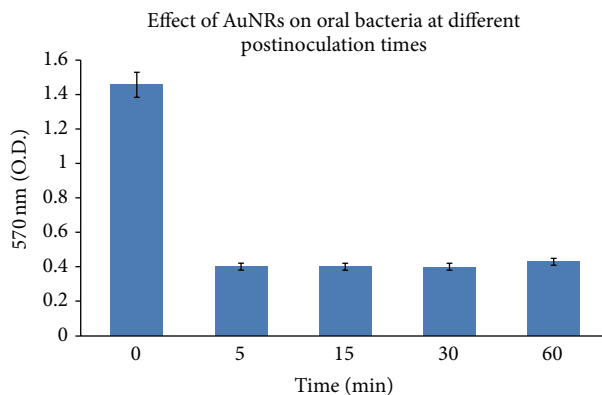


FIGURE 4: Bactericidal activity of AuNRs against oral bacteria growth. The Y-axis shows the optical density units of microbial growth. As growing control were used bacteria growing in culture media without inhibitor. AuNRs were used at final concentration of  $150 \mu\text{g}/\text{mL}$ . The bactericidal activity of AuNRs was measured after 5, 15, 30, and 60 minutes after exposition. All experiments were done in triplicate to assess the veracity of results.

#### 4. Discussion

Plasmon photothermal therapy has been extensively studied as an alternative technique in the biomedical area. Some studies have reported its effectiveness on the oral bacteria, but to our knowledge there are no reports presenting the minimum inhibitory concentration and minimum bactericide concentration of PPTT using gold nanorods. MacKey et al. described that plasmonic photothermal therapy using gold nanorods has a major effect related to the rod size; they determined that  $28 \times 8 \text{ nm}$  AuNRs are the most effective in the plasmonic photothermal heat generation [18]. This size is similar to the one obtained in our experiments ( $33 \times 7 \text{ nm}$ ) and this aspect ratio allowed us to overlap the 810 nm wavelength emission of the therapeutic laser with the transversal absorption plasmon of gold nanorods. When we irradiated 1 mL of gold nanorods with the 810 nm wavelength laser, this dispersion reached a temperature of  $70^\circ\text{C}$  and after this treatment nanorods were observed using TEM, keeping its morphology as can be shown in Figure 1(b), which is great, because it means they could be used several times in photothermal therapy [19].

The antibacterial effect of AuNRs and PPTT using AuNRs has already been studied. In this work, three groups were analyzed: AuNRs, PPTT with AuNRs, and laser group. Within our results, we found that in all cases AuNRs with PPTT present lower values in comparison with AuNRs alone (Table 1 and Figure 3). The MIC and MBC values were higher for *S. aureus* and *E. coli* and 3 times lower for *E. faecalis* and *S. oralis*. These differences could be due to divergence found in the cellular wall of each kind of bacteria. Mocan et al. reported a MIC for spherical gold nanoparticles against methicillin-resistant *S. aureus* with and without photoactivation of  $6.25$  and  $25 \mu\text{g}\cdot\text{mL}^{-1}$ , respectively. These values are higher than

those reported in this investigation, probably due to the higher photothermal activity of AuNRs [20].

In endodontics, NaClO is used as the routine disinfectant due to its high effectiveness; Heling obtained a MIC of  $1570 \mu\text{g}\cdot\text{mL}^{-1}$  for NaClO against *S. sobrinus*, *E. faecalis*, and *S. salivarius*, and  $3150 \mu\text{g}\cdot\text{mL}^{-1}$  against *S. mutans*; the minimum bactericide concentrations reported in the Heling work reach the  $25000 \mu\text{g}\cdot\text{mL}^{-1}$ ; our results using gold nanorods are at least 3 orders of magnitude lower [21]. Kim et al. claim that, when a dispersion of AuNRs is irradiated with a laser it reaches a temperature near  $70^\circ\text{C}$  and this temperature causes the *E. coli* lysis [6]; this temperature is very close to the temperature achieved in this study. Sean Norman et al. say that AuNRs PPTT produces a damage effect in the bacteria surface [5, 22] in our study; this could be the bactericide mechanism as confirmed by the SEM images.

In order to assess if, in parallel to its antimicrobial activity of AuNRs, gold nanorods had the potential to interfere with biofilm formation of oral bacteria, the antibiofilm activity of gold nanorods was studied. Surprisingly, the effect of AuNRs without PPTT on oral biofilm was their complete inhibition as can be observed in Figure 6. In the presence of chlorhexidine and AuNRs we just observed cellular debris on a dark background, mainly DNA of dead bacteria with accumulations of dye. Morphologically, these dye accumulations clearly differ from bacterial biofilm. This phenomenon was not changed if AuNRs were added at 0, 4, or 8 hours postinoculation times. These results are not strange; several early reports have described the antibiofilm properties of metal nanoparticles [8, 10, 11, 23]. Altogether, these results indicate that gold nanorods have an important antibiofilm activity to inhibit with biofilm formation of oral microorganisms.

#### 5. Conclusions

The AuNRs PPTT presented a higher antibacterial activity on seven different ATCC strains used in this work, having a synergic effect if compared with the AuNRs by its own. To our knowledge this is the first study to report the CMI and CMB (based on the CLSI standards) of the AuNRs PPTT with any of the seven different strains.

#### Conflict of Interests

The authors of this paper declare that there are no potential competing interests among authors of this work.

#### Acknowledgments

This work was partially supported by Consejo Nacional de Ciencia y Tecnología (CONACYT; Grants 169020 and 178261). Authors would like to thank Silvia Moya Campos and Rene Hernandez-Delgado from FO-UANL for their technical support. Financial support for the payment of

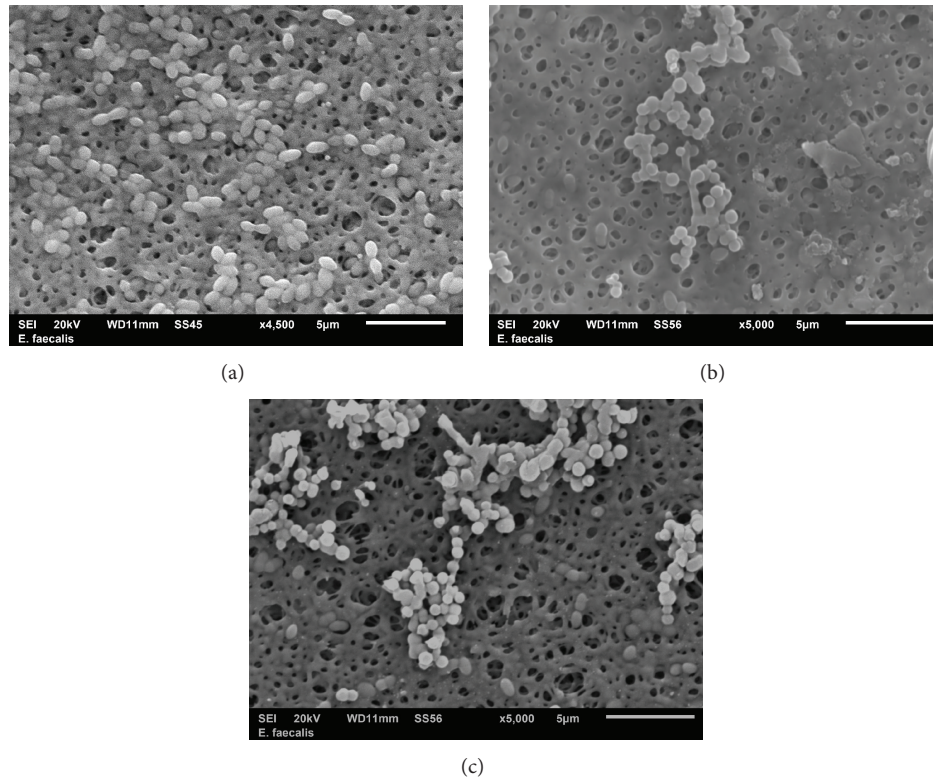


FIGURE 5: SEM images of *E. faecalis*. (a) Control group (bacteria without any treatment); (b) after their treatment with AuNRs; and (c) after their treatment with AuNRs PPTT.

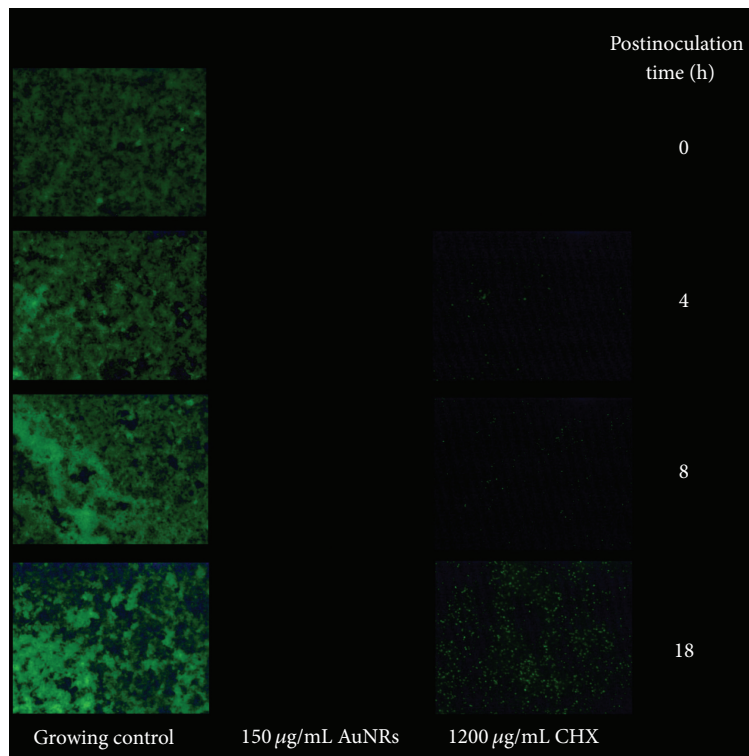


FIGURE 6: Inhibition of oral biofilm formation by gold nanorods using fluorescence microscopy. As growing control were used microorganisms growing in culture media without inhibitor and 1200 g/mL of chlorhexidine was employed as positive inhibition control. AuNRs were used at a final concentration of 150 µg/mL. All experiments were done in triplicate to assess the veracity of results.

the processing charges was made by Programa para el Desarrollo Profesional Docente para el Tipo Superior (PRODEP 2014).

## References

- [1] G. B. Kharkwal, S. K. Sharma, Y.-Y. Huang, T. Dai, and M. R. Hamblin, "Photodynamic therapy for infections: clinical applications," *Lasers in Surgery and Medicine*, vol. 43, no. 7, pp. 755–767, 2011.
- [2] S. K. Sharma, P. Mroz, T. Dai, Y.-Y. Huang, T. G. S. Denis, and M. R. Hamblin, "Photodynamic therapy for cancer and for infections: what is the difference?" *Israel Journal of Chemistry*, vol. 52, no. 8-9, pp. 691–705, 2012.
- [3] R. Fekrazad, F. Khoei, N. Hakimiha, and A. Bahador, "Photoelimination of *Streptococcus mutans* with two methods of photodynamic and photothermal therapy," *Photodiagnosis and Photodynamic Therapy*, vol. 10, no. 4, pp. 626–631, 2013.
- [4] W.-C. Huang, P.-J. Tsai, and Y.-C. Chen, "Functional gold nanoparticles as photothermal agents for selective-killing of pathogenic bacteria," *Nanomedicine*, vol. 2, no. 6, pp. 777–787, 2007.
- [5] R. Sean Norman, J. W. Stone, A. Gole, C. J. Murphy, and T. L. Sabo-Attwood, "Targeted photothermal lysis of the pathogenic bacteria, *Pseudomonas aeruginosa*, with gold nanorods," *Nano Letters*, vol. 8, no. 1, pp. 302–306, 2008.
- [6] C.-B. Kim, D. K. Yi, P. S. S. Kim, W. Lee, and M. J. Kim, "Rapid photothermal lysis of the pathogenic, bacteria, *Escherichia coli* using synthesis of gold nanorods," *Journal of Nanoscience and Nanotechnology*, vol. 9, no. 5, pp. 2841–2845, 2009.
- [7] H. M. Lode, R. Stahlmann, and M. Kresken, "Multiresistant pathogens—a challenge for clinicians," *Zentralblatt für Chirurgie*, vol. 138, no. 5, pp. 549–553, 2013.
- [8] R. Hernandez-Delgado, D. Velasco-Arias, J. J. Martinez-Sanmiguel et al., "Bismuth oxide aqueous colloidal nanoparticles inhibit *Candida albicans* growth and biofilm formation," *International Journal of Nanomedicine*, vol. 8, pp. 1645–1652, 2013.
- [9] L. F. Espinosa-Cristóbal, G. A. Martínez-Castañón, R. E. Martínez-Martínez, J. P. Loyola-Rodríguez, J. F. Reyes-Macías, and F. Ruiz, "Antibacterial effect of silver nanoparticles against *Streptococcus mutans*," *Materials Letters*, vol. 63, no. 29, pp. 2603–2606, 2009.
- [10] R. Hernandez-Delgado, D. Velasco-Arias, D. Diaz et al., "Zerovalent bismuth nanoparticles inhibit *Streptococcus mutans* growth and formation of biofilm," *International Journal of Nanomedicine*, vol. 7, pp. 2109–2113, 2012.
- [11] A. R. Badireddy, R. Hernandez-Delgado, R. I. Sánchez-Nájera, S. Chellam, and C. Cabral-Romero, "Synthesis and characterization of lipophilic bismuth dimercaptopropanol nanoparticles and their effects on oral microorganisms growth and biofilm formation," *Journal of Nanoparticle Research*, vol. 16, no. 6, pp. 1–12, 2014.
- [12] B. Nikoobakht and M. A. El-Sayed, "Preparation and growth mechanism of gold nanorods (NRs) using seed-mediated growth method," *Chemistry of Materials*, vol. 15, no. 10, pp. 1957–1962, 2003.
- [13] F. Scaletti, C. S. Kim, L. Messori, and V. M. Rotello, "Rapid purification of gold nanorods for biomedical applications," *MethodsX*, vol. 1, pp. 118–123, 2014.
- [14] M. Ramasamy, S. S. Lee, D. K. Yi, and K. Kim, "Magnetic, optical gold nanorods for recyclable photothermal ablation of bacteria," *Journal of Materials Chemistry B*, vol. 2, no. 8, pp. 981–988, 2014.
- [15] G. A. Martínez-Castañón, N. Niño-Martínez, F. Martínez-Gutierrez, J. R. Martínez-Mendoza, and F. Ruiz, "Synthesis and antibacterial activity of silver nanoparticles with different sizes," *Journal of Nanoparticle Research*, vol. 10, no. 8, pp. 1343–1348, 2008.
- [16] Y. Liu, D. A. Peterson, H. Kimura, and D. Schubert, "Mechanism of cellular 3-(4,5-dimethylthiazol-2-yl)-2,5-diphenyltetrazolium bromide (MTT) reduction," *Journal of Neurochemistry*, vol. 69, no. 2, pp. 581–593, 1997.
- [17] H. Yue, P. S. Eastman, B. B. Wang et al., "An evaluation of the performance of cDNA microarrays for detecting changes in global mRNA expression," *Nucleic Acids Research*, vol. 29, no. 8, article e41, 2001.
- [18] M. A. MacKey, M. R. K. Ali, L. A. Austin, R. D. Near, and M. A. El-Sayed, "The most effective gold nanorod size for plasmonic photothermal therapy: theory and *in vitro* experiments," *The Journal of Physical Chemistry B*, vol. 118, no. 5, pp. 1319–1326, 2014.
- [19] X. Huang, P. K. Jain, I. H. El-Sayed, and M. A. El-Sayed, "Plasmonic photothermal therapy (PPTT) using gold nanoparticles," *Lasers in Medical Science*, vol. 23, no. 3, pp. 217–228, 2008.
- [20] L. Mocan, I. Ilie, C. Matea et al., "Surface plasmon resonance-induced photoactivation of gold nanoparticles as bactericidal agents against methicillin-resistant *Staphylococcus aureus*," *International Journal of Nanomedicine*, vol. 9, no. 1, pp. 1453–1461, 2014.
- [21] I. Heling, "Bactericidal and cytotoxic effects of sodium hypochlorite and sodium dichloroisocyanurate solutions *in vitro*," *Journal of Endodontics*, vol. 27, no. 4, pp. 278–280, 2001.
- [22] Z. Fan, D. Senapati, A. K. Singh, and P. C. Ray, "Theranostic magnetic core-plasmonic shell star shape nanoparticle for the isolation of targeted rare tumor cells from whole blood, fluorescence imaging, and photothermal destruction of cancer," *Molecular Pharmaceutics*, vol. 10, no. 3, pp. 857–866, 2013.
- [23] J. S. Kim, E. Kuk, K. N. Yu et al., "Antimicrobial effects of silver nanoparticles," *Nanomedicine: Nanotechnology, Biology and Medicine*, vol. 3, no. 1, pp. 95–101, 2007.



**Hindawi**

Submit your manuscripts at  
<http://www.hindawi.com>

