



THE UNIVERSITY *of* EDINBURGH

Edinburgh Research Explorer

Visualized Effects of Oxidation and Temperature on Vortex-State Fe₃O₄ Particles Examined by Environmental TEM and Off-Axis Electron Holography

Citation for published version:

Almeida, TP, Muxworthy, AR, Williams, W, Kasama, T, Hansen, TW, Brown, PD, Kovács, A & Dunin-borkowski, RE 2018, 'Visualized Effects of Oxidation and Temperature on Vortex-State Fe₃O₄ Particles Examined by Environmental TEM and Off-Axis Electron Holography' *Microscopy and Microanalysis*, vol. 24, no. S1, pp. 950-951. DOI: 10.1017/S143192761800524X

Digital Object Identifier (DOI):

[10.1017/S143192761800524X](https://doi.org/10.1017/S143192761800524X)

Link:

[Link to publication record in Edinburgh Research Explorer](#)

Document Version:

Peer reviewed version

Published In:

Microscopy and Microanalysis

Publisher Rights Statement:

© Microscopy Society of America 2018

General rights

Copyright for the publications made accessible via the Edinburgh Research Explorer is retained by the author(s) and / or other copyright owners and it is a condition of accessing these publications that users recognise and abide by the legal requirements associated with these rights.

Take down policy

The University of Edinburgh has made every reasonable effort to ensure that Edinburgh Research Explorer content complies with UK legislation. If you believe that the public display of this file breaches copyright please contact openaccess@ed.ac.uk providing details, and we will remove access to the work immediately and investigate your claim.



Visualized Effects of Oxidation and Temperature on Vortex-State Fe₃O₄ Particles Examined by Environmental TEM and Off-Axis Electron Holography

Trevor P. Almeida^{1,2}, Adrian R. Muxworthy², Wyn Williams³, Takeshi Kasama⁴, Thomas W. Hansen⁴, Paul D. Brown⁵, András Kovács⁶ and Rafal E. Dunin-Borkowski⁶

¹SUPA, School of Physics and Astronomy, University of Glasgow, G12 8QQ, UK.

²Department of Earth Science and Engineering, South Kensington Campus, Imperial College London, London, SW7 2AZ, UK.

³School of GeoSciences, University of Edinburgh, Edinburgh, UK.

⁴Center for Electron Nanoscopy, Technical University of Denmark, DK-2800 Kgs. Lyngby, Denmark.

⁵Department of Mechanical, Materials & Manufacturing Engineering, University of Nottingham, University Park, Nottingham, NG7 2RD, UK.

⁶Ernst Ruska-Centre for Microscopy and Spectroscopy with Electrons and Peter Grünberg Institute, Forschungszentrum Jülich, 52425 Jülich, Germany.

Introduction

Magnetic minerals in rocks record the direction and intensity of the ambient magnetic field during formation, providing, for example, varied information about the geomagnetic field and past tectonic plate motions. Magnetite (Fe₃O₄) is arguably the most important naturally occurring magnetic mineral on Earth due to its high abundance and strong, dominating magnetisation and is therefore crucial to the field of palaeomagnetism. Oxidation of Fe₃O₄ to other iron oxides, such as γ -Fe₂O₃, is of interest as it effects the stability of the remanent signal of the Earth's magnetic field. Signals in Fe₃O₄ grains are acquired in the direction of the geomagnetic field as they cool below their Curie temperature (T_C) of ~ 580 °C. In order to reliably interpret palaeomagnetic measurements, the effects of chemical alteration and thermal variation on remanent magnetisation must be fully understood. Most models of such processes only exist for uniformly-magnetized grains, termed single domain (SD), whereas magnetic signals from rocks are often dominated by larger grains with non-uniform domains such as vortex states, termed pseudo-SD (PSD) grains. In order to fully understand the remanent behaviour of these non-ideal palaeomagnetic recorders, it is necessary to examine the effects of oxidation and heating on their PSD magnetic domain states directly. The transmission electron microscopy (TEM) techniques of off-axis electron holography and environmental TEM (ETEM) allow for magnetic imaging of nanoscale minerals during *in situ* heating in controlled atmospheres¹. Here, the first use of off-axis electron holography to examine local changes in remanent and saturation magnetization in vortex-state Fe₃O₄ grains during *in situ* heating under vacuum and oxygen atmosphere is presented.

Methods/Materials

Synthetic Fe₃O₄ particles in the PSD size range (< 200 nm) were heated *in situ* in an (E)TEM to a temperature of 700 °C under vacuum or in 9 mbar of O₂ atmosphere. Off-axis electron holograms were acquired at 300 kV in Lorentz mode in Titan 80-300 TEMs equipped with electron biprisms and recorded using charge-coupled device cameras, with each particle magnetized in opposite directions, in order to determine the mean inner potential contribution to the phase. For the investigation of the effect of oxidation, electron holograms were acquired after magnetisation reversal had been performed, both before and after heating to 700 °C using a Protochips heating holder. Oxidation of the Fe₃O₄ particles was investigated using electron energy-loss spectroscopy (EELS), through close examination of the Fe $L_{2,3}$ edges¹. In order to examine the thermoremanent behaviour of the Fe₃O₄ particles, after initial magnetisation reversal at room temperature holograms were acquired in magnetic-field-free conditions in 100 °C intervals during *in situ* heating from 100 to 700 °C using a DensSolutions heating holder and again upon cooling^{2,3}. The mean inner potential contribution to the phase was acquired separately at each temperature and subtracted from the original phase images to allow the construction of magnetic induction maps that are representative of the true remanent state.

Results and Discussion

Figure 1 illustrates the effect of accelerated oxidation on the magnetization of an elongated (~ 250 nm long, ~ 150 nm wide) Fe_3O_4 grain¹. A bright-field (BF) TEM image (Fig. 1a) shows a native smooth-surfaced Fe_3O_4 grain, while complementary EELS analysis of the Fe 2p $L_{2,3}$ edge (Fig. 1b; blue spectrum) is in good agreement with that expected for Fe_3O_4 . Examination of the EEL spectra after *in situ* heating revealed pre- and post- peaks close to the Fe 2p $L_{2,3}$ edge (Fig. 1b; red, arrowed) that are indicative of oxidation. The effect of oxidation on the magnetism of the grain was examined using off-axis electron holography, in the form of reconstructed magnetic induction maps. The Fe_3O_4 grain exhibited a change in magnetisation direction from before (Fig. 1c) to after (Fig. 1d) oxidation.

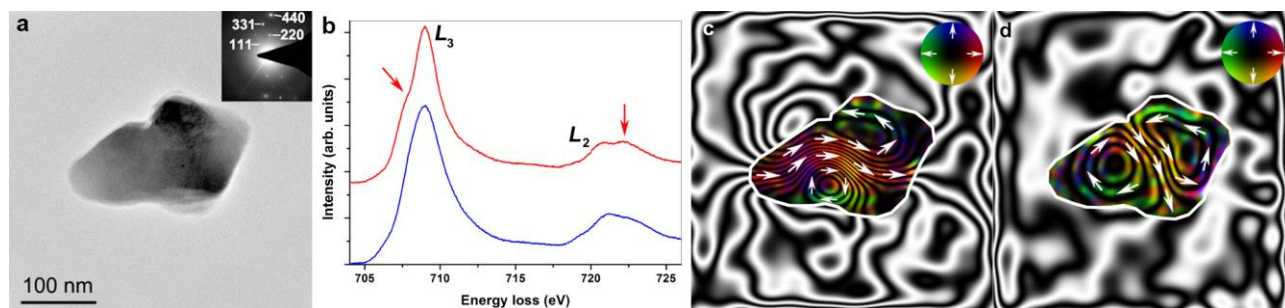


Figure 1 (a) TEM image of an Fe_3O_4 particle and (b) EEL spectra acquired before (blue) and after (red) oxidation. (c, d) Magnetic induction maps of the particle (c) before and (d) after oxidation¹.

The thermomagnetic behavior of a small PSD Fe_3O_4 grain is presented in Fig. 2. A BF TEM image (Fig. 2a) shows the grain to be ~ 180 nm in length along its major axis². Magnetic induction maps recorded during *in situ* heating to just below T_C reveal the thermal stability of the vortex-state PSD grain. The vortex core in the small Fe_3O_4 grain (denoted ‘v’) rotates from its initial state at 20 °C (Fig. 2b) to become aligned to the major axis of the grain at 550 °C (Fig. 2c), close to its T_C of ~ 580 °C. It then recovers its initial state on cooling back to 20 °C.

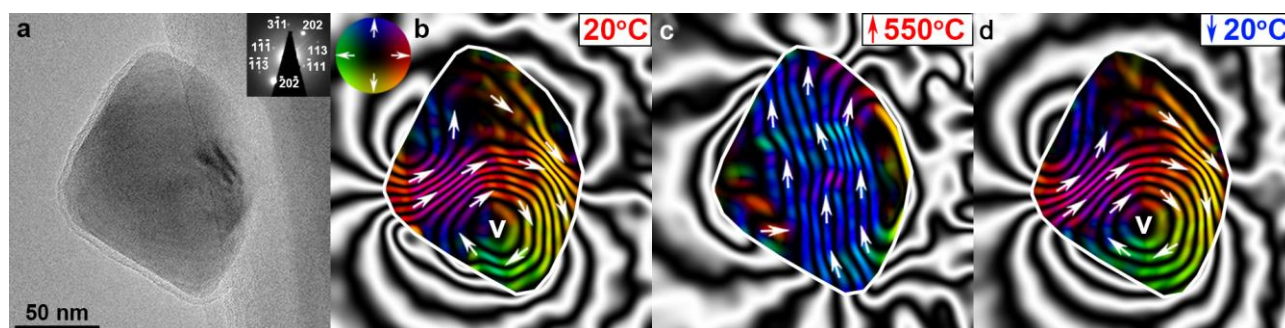


Figure 2 (a) TEM image of an Fe_3O_4 particle, shown alongside magnetic induction maps recorded at (b) 20 °C; (c) during *in situ* heating to 550 °C; and (d) after cooling back to 20 °C.

Based on the present study, we infer that *in situ* heating in an O_2 atmosphere does indeed induce changes in both the strength and the direction of the vortex core in PSD Fe_3O_4 grains, confirming that oxidation can modify the original stored magnetic information. Furthermore, we show spatially resolved magnetic information from individual Fe_3O_4 grains as a function of temperature, which has been previously inaccessible. The Fe_3O_4 grain shown in Fig. 2 exhibits a dynamic movement of its magnetic vortex structure approaching T_C , but recovers its original state upon cooling. Hence, we demonstrate that vortex-state Fe_3O_4 grains, which have undergone heating events, are indeed reliable recorders of paleodirectional and paleointensity information.

References

- [1] T. P. Almeida et al., *Nat. Commun.* 5, 5154 (2014).
- [2] T. P. Almeida et al., *Sci. Adv.*, 2, e1501801 (2016).
- [3] T. P. Almeida et al., *Geophys. Res. Lett.*, 43, 8426-8434 (2016).