

Environmental Science and Pollution Research

Photocatalytic Porcelain Grés Large Slabs digitally coated with AgNPs-TiO₂

--Manuscript Draft--

Manuscript Number:	ESPR-D-18-05560R3
Full Title:	Photocatalytic Porcelain Grés Large Slabs digitally coated with AgNPs-TiO ₂
Article Type:	Research Article
Corresponding Author:	Claudia L. Bianchi Università di Milano Milano, ITALY
Corresponding Author Secondary Information:	
Corresponding Author's Institution:	Università di Milano
Corresponding Author's Secondary Institution:	
First Author:	Claudia L. Bianchi
First Author Secondary Information:	
Order of Authors:	Claudia L. Bianchi Giuseppina Cerrato Carlo Pirola Federico Galli Valentino Capucci
Order of Authors Secondary Information:	
Funding Information:	
Abstract:	TiO ₂ is employed as both photocatalytic and structural materials, leading to its applications in external coatings or in interior furnishing devices, including cement mortar, tiles, floorings and glass supports. The authors have already demonstrated the efficiency of photoactive micro-sized TiO ₂ and here its industrial use is reported using the digital printing to coat porcelain grés slabs. Many advantages are immediately evident, namely rapid and precise deposition, no waste of raw materials, thus positively affecting the economy of the process. Data for the thin films deposited by digital printing were compared with those obtained for the conventional spray method. The use of metal-doped TiO ₂ is also reported so that the photoactivity of these materials can be exploited even under LED light. The digital inkjet printed coatings exhibited superior photocatalytic performance owing to both higher exposed surface area and greater volume of deposited anatase, as well as the greater areal distribution density of thinly and thickly coated regions. Moreover, the presence of TiO ₂ doped silver increased the efficiency of the materials in NO _x degradation both under UVA and LED lights.
Response to Reviewers:	Manuscript Number: ESPR-D-18-05560R2 We would like to thank the reviewers for their pertinent comments. Below, we have answered in detail . Reviewer #2: 1.The paper still needs to be carefully revised before it can be published. There are too many grammatical mistakes in the paper, and many sentences are difficult to understand. For example: Page 4, "----, which is pure anatase as of its crystallographic structure." "AgNps-doped TiO ₂ was prepared following two different routes" "The second preparation employs----" Page 5, the sentence of "Fig.2 reports the excellent photocatalysts distribution -----" is not easy to understand. Page 10, the first sentence of paragraph 2, "The characterization -----", is not easy to

	<p>understand.</p> <p>The manuscript has been thoroughly emended by a native English colleague: we hope that the present version fulfils the linguistic standards. We also tried to clarify all the sentences indicated by the Reviewer (and many others as well) that seemed to be not so clear at first sight.</p> <p>2.The inserted EDS spectrum is too small to be seen. We moved the inserted EDS image outside, in order to make it better visible (now it has become figure 1c)</p> <p>3.The particle size of the original TiO₂ powder is 110~130nm, but why the prepared TiO₂ particle on tile surface is much smaller than 100nm (about 40nm, as shown in Figure 2)? The phase transform temperature of TiO₂ from anatase to rutile is known at about 550 °C. It seems that TiO₂ on tile surface have changed after treatment at 680°C. We thank the reviewer for this indication, as the reported figures retained a bad mistake in the marker. Now we replaced the two pictures with the two original ones. The rutile transformation depends by many factors, mainly the size of the TiO₂ particles. Examples in literature indicate transition even above 850°C. In our case, we checked carefully the temperature with EXAFS measurements made at the synchrotron facilities in Grenoble (and published several years ago) that ensured that in our samples only the anatase phase was and is present.</p> <p>4.The average amount of TiO₂ coated on the tile surface is determined to be 20 g m⁻² by using the EDX analysis. How to get this data by using the EDX analysis? How about Ag and Si? What is the amount of TiO₂ coated on the tile surface by using the spray technology? 20 g/m² is also a value fixed by the digital printed machine. The sentence inside the manuscript was modified to better clarify this point. Si comes from the ink and Ag depends on the production usually from 4 to 8% (wt). The amount of TiO₂ with the spray technology was already published and reported in ref. Bianchi 2016.</p> <p>5.There are many types of LED lamp. Some of them even only emit ultraviolet light. The range of light emission and light intensity of the used LED should be given. In our case the lamp is a commercial one. All the commercial lamps have no UV. In our case, the range is from 420 to 780 nm as reported in the manuscript.</p> <p>6.The author said that "photodegradation under LED as the only source of light is impossible with naked TiO₂ because of its wide band gap of 3.2 eV", however, the sprayed coated tile doesn't have but the digitally printed tile has the photocatalytic activity for NO_x degradation under LED light, what is the difference of the two sample? 10% of activity is really a low value and is given only by the fact that the used TiO₂ is a commercial one and it is active by an irradiation larger than the traditional 380 nm but in a range 360-410 nm, with a slight tale over 400 nm. If you check the behaviour of the well-known standard P25 you can obtain more or less the same results.</p>
Additional Information:	
Question	Response
§Are you submitting to a Special Issue?	Yes
(If "yes") Please select a Special Issue from the following list: as follow-up to "§Are you submitting to a Special Issue?"	SI: SPEA10

Manuscript Number: ESPR-D-18-05560R2

We would like to thank the reviewers for their pertinent comments. Below, we have answered to each in detail in red.

Reviewer #2: 1. The paper still needs to be carefully revised before it can be published. There are too many grammatical mistakes in the paper, and many sentences are difficult to understand.

For example: Page 4, "----, which is pure anatase as of its crystallographic structure."

"AgNps-doped TiO₂ was prepared following two different routes"

"The second preparation employs----"

Page 5, the sentence of "Fig.2 reports the excellent photocatalysts distribution -----" is not easy to understand.

Page 10, the first sentence of paragraph 2, "The characterization -----", is not easy to understand.

The manuscript has been thoroughly emended by a native English colleague: we hope that the present version fulfils the linguistic standards.

We also tried to clarify all the sentences indicated by the Reviewer (and many others as well) that seemed to be not so clear at first sight.

2. The inserted EDS spectrum is too small to be seen.

We moved the inserted EDS image outside, in order to make it better visible (now it has become figure 1c)

3. The particle size of the original TiO₂ powder is 110~130nm, but why the prepared TiO₂ particle on tile surface is much smaller than 100nm (about 40nm, as shown in Figure 2)? The phase transform temperature of TiO₂ from anatase to rutile is known at about 550 °C. It seems that TiO₂ on tile surface have changed after treatment at 680°C.

We thank the reviewer for this indication, as the reported figures retained a bad mistake in the marker. Now we replaced the two pictures with the two original ones.

The rutile transformation depends by many factors, mainly the size of the TiO₂ particles. Examples in literature indicate transition even above 850°C. In our case, we checked carefully the temperature with EXAFS measurements made at the synchrotron facilities in Grenoble (and published several years ago) that ensured that in our samples only the anatase phase was and is present.

4. The average amount of TiO₂ coated on the tile surface is determined to be 20 g m⁻² by using the EDX analysis. How to get this data by using the EDX analysis? How about Ag and Si? What is the amount of TiO₂ coated on the tile surface by using the spray technology?

20 g/m² is also a value fixed by the digital printed machine. The sentence inside the manuscript was modified to better clarify this point.

Si comes from the ink and Ag depends on the production usually from 4 to 8% (wt).

The amount of TiO₂ with the spray technology was already published and reported in ref. Bianchi 2016.

5. There are many types of LED lamp. Some of them even only emit ultraviolet light. The range of light emission and light intensity of the used LED should be given.

In our case the lamp is a commercial one. All the commercial lamps have no UV. In our case, the range is from 420 to 780 nm as reported in the manuscript.

6. The author said that "photodegradation under LED as the only source of light is impossible with naked TiO₂ because of its wide band gap of 3.2 eV", however, the sprayed coated tile doesn't have but the digitally printed tile has the photocatalytic activity for NO_x degradation under LED light, what is the difference of the two sample?

10% of activity is really a low value and is given only by the fact that the used TiO₂ is a commercial one and it is active by an irradiation larger than the traditional 380 nm but in a range 360-410 nm, with a slight tale over 400 nm.

If you check the behaviour of the well-known standard P25 you can obtain more or less the same results.

[Click here to view linked References](#)

Photocatalytic Porcelain Grés Large Slabs digitally coated with AgNPs-TiO₂

Claudia L. Bianchi^{*,1}, Giuseppina Cerrato², Carlo Pirola¹, Federico Galli¹, Valentino Capucci³

¹Università di Milano, Dipartimento di Chimica, Via Golgi 19, 20133 Milano, Italy

²Università di Torino, Dipartimento di Chimica & NIS Interdept. Centre, Via P. Giuria 7, 10125 Torino, Italy

³IrisCeramica Group, Via Ghiarola Nuova 119, 41042 Fiorano M.se (MO), Italy

[*claudia.bianchi@unimi.it](mailto:claudia.bianchi@unimi.it)

Abstract

TiO₂ is employed as both photocatalytic and structural materials, leading to its applications in external coatings or in interior furnishing devices, including cement mortar, tiles, floorings and glass supports. The authors have already demonstrated the efficiency of photoactive micro-sized TiO₂ and here its industrial use is reported using the digital printing to coat porcelain grés slabs. Many advantages are immediately evident, namely rapid and precise deposition, no waste of raw materials, thus positively affecting the economy of the process. Data for the thin films deposited by digital printing were compared with those obtained for the conventional spray method. The use of metal-doped TiO₂ is also reported so that the photoactivity of these materials can be exploited even under LED light. The digital inkjet printed coatings exhibited superior photocatalytic performance owing to both higher exposed surface area and greater volume of deposited anatase, as well as the greater areal distribution density of thinly and thickly coated regions. Moreover, the presence of TiO₂ doped silver increased the efficiency of the materials in NO_x degradation both under UVA and LED lights.

Keywords:

Micro-sized TiO₂; photocatalysis; building materials; porcelain grés materials; Ag-doping; digital printing; LED light; NO_x

1. Introduction

Concern for the impact of air quality on human health has been increasing for many decades (Fullerton 2008, Kurmi 2010). A 2014 World Health Organization (WHO) health report (WHO 2014) states that there were about 7 million deaths globally from air pollution, 60% of which due to indoor

1 pollution, 53% were from outdoor pollution, and the overlap of 14% was from a combination of the
2 two. Furthermore, the effects of air pollution on the welfare and survival of native flora and fauna
3 remain topical issues. In general, air pollution can be addressed by the two different approaches of
4 either prevention or elimination (Ren 2017). In the latter case, there is an imperative request to both
5 develop new and improve existing techniques for the destruction of air pollutants.
6

7
8
9 Contrary to what is generally assumed, air in several indoor environments is often more polluted than
10 outdoor, because of the many sources of indoor pollution, which include mold and pollen, tobacco
11 smoke, household products and pesticides, and materials usually used in buildings such as
12 formaldehyde and organic compounds in general. Health effects from indoor air pollutants generally
13 occur after long or repeated exposure and they can be severely debilitating or fatal: moreover, mainly
14 in the urban areas in more developed Countries, population spends most of the time in closed rooms,
15 houses, offices and schools (80-90% of a day).
16
17

18
19
20
21
22 There is still uncertainty about the level of concentrations that can produce specific health problems.
23 However, it is accepted that even low concentrations of some ubiquitous pollutants can be very
24 dangerous, often causing undesired effects on health from sensory discomfort to serious consequences
25 for physical conditions.
26
27

28
29 Photocatalysis is one of the most promising methods to purify air. For this reason, photocatalytic
30 materials and technologies for air purification have emerged as some of the most intensively
31 examined approaches to this end (Ren 2017, Zhao 2003, Mo 2009, Huang 2016, Chen 2009). Titania
32 (TiO_2) is one of the most suitable semiconductor materials for such photocatalytic applications owing
33 to its photocatalytic activity, chemical and environmental stabilities, nontoxicity, and economy.
34 Among the three TiO_2 polymorphs (i.e., anatase, rutile, brookite), anatase is recognised as being the
35 most effective photocatalyst (Hanaor 2011).
36
37

38
39
40
41
42 New class of building materials can be a good tool to play an active role in environment remediation.
43 At the beginning of the industrial productions, porcelain grés tiles were considered as just a technical
44 material, aesthetically not very beautiful. Today, thanks to new industrial production methods, both
45 properties and appearance of these materials completely fit the market requests. In particular, the
46 possibility to prepare slabs of large sizes is the new frontier of building materials.
47
48

49
50
51 However, it is time to go further the simple sustainable materials and to produce cements and tiles
52 and in general building materials no longer inert but able to "work" to improve the well-being of
53 people living in those spaces. In fact, besides the noteworthy architectural features, new surface
54 properties can be introduced in the last generation of eco-active materials. In particular, deposition of
55 TiO_2 transforms the traditional ceramic surface into a photocatalytic eco-active material able to (i)
56 reduce polluting molecules present in air and water, (ii) to eliminate bacteria and (iii) to reduce the
57
58
59
60
61
62
63
64
65

1 surface dirt thanks to the self-cleaning property. The standard requirements of the porcelain grés with
2 respect to hardness, lack of porosity, vitrified surface, durability typical of a porcelain grés product
3 do not change with the addition of the photocatalytic coating.
4

5 The digital printing was exploited as a new tool to manufacture photocatalytic tiles even of very large
6 size (150x300 cm). Conventional spray coating and dip coating methods are basic techniques,
7 typically involving aqueous suspensions, applied to substrates over relatively large areas. In contrast,
8 digital inkjet printing is more sophisticated, involving piezoelectric heads with precise directional
9 deposition of an aqueous/organic suspension with an electrostatic field; details of the process are
10 available elsewhere (Bianchi 2018). Micro-TiO₂ was industrially formulated in a tailored ink,
11 digitally printed at the tiles surface, fired in industrial kiln at 680°C and cleaned with a rotating wire
12 brush to remove the TiO₂ fraction weakly stuck at the ceramic surface. In the formulation, a
13 commercial micro-TiO₂ (Kronos, characterized by pure anatase and a not coated surface) was
14 employed avoiding the use of traditional nano-sized TiO₂ in powdery form, thus preventing possible
15 side effects on human health due to both use and exposure to nanoparticles mainly during the
16 manufacture process.
17

18 A frequent criticism to photocatalytic materials concerns their use only in the presence of sunlight or
19 traditional artificial lamps, but not with the recent LED lights that have a type of radiation
20 incompatible with the activation of traditional TiO₂. All the photocatalytic processes are inexorably
21 turned off when the material is illuminated by LED lights and, even more so, when in darkness. For
22 this reason, the commercial micro-sized TiO₂ was decorated with Ag nanoparticles (Ag-NPs) to
23 enhance its activity even in the visible region (Cerrato 2019).
24

25 Seery and co-authors reported about Ag modified TiO₂ materials with increased visible light activity
26 compared to bare TiO₂ (Seery 2007) due to the surface plasmon band of Ag, which absorbs in the
27 visible spectrum (Nolan 2010). The scientific literature is rich of both procedures and data on the
28 synthesis of Ag-NPs supported on TiO₂. Examples include impregnation from Ag colloidal
29 dispersions (Yu 2017) or from Ag inorganic salts (Amruta 2016), electrostatic self-assembly (Li
30 2017), photo-reduction of Ag salts (Milosevic 2017), or ultrasound-assisted synthesis (Stucchi 2018).
31 The photocatalytic properties of commercial digitally coated slabs, photoactivated both with bare
32 TiO₂ and AgNPs-TiO₂, were verified in laboratory using NO_x as model pollutant, to evaluate the
33 good performance of the ceramic slabs to tackle the environmental pollution both under UV and under
34 a commercial LED lamp. The presence of the dopant metal allows the material to act also as
35 antibacterial both in the UV or LED light and in the dark, by eliminating one of the negative features
36 of photocatalytic building materials that has so far limited their use on a large scale.
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

2. Materials and methods

The support was a micrometric pure anatase TiO₂ (K1077, KRONOS Worldwide, Inc.), as assessed by its crystallographic structure: we thoroughly characterized it in previous works (Bianchi 2015) and its main features are here below summarized (Table 1).

Table 1. Characteristics of Kronos 1077 TiO₂ Powder

Characteristic	Units	Value
Mineralogy	wt%	≥98.5 Anatase
pH	--	7.0 – 8.5
Brightness	--	97.0 – 97.8
True Density	kg/m ³	3800
Particle Size Range	nm	110 – 130
Surface Area	m ² ·g ⁻¹	12
Optical Indirect Band Gap	eV	3.15
Band gap	eV	3.15
XPS (OH/O _{TOT})		0.32

2.1 AgNPs and AgNPs-TiO₂ preparation

AgNps-doped TiO₂ was prepared following two different synthetic procedures. The first one implied to start from silver nitrate (AgNO₃, ACS Reagent, ≥99%). The other reagents were polyvinylpyrrolidone (PVP40, average mol wt 40,000) and ammonia (NH₃, ≥99%). The preparation

1 of the AgNPs sol is reported elsewhere (Minozzi 2018). The second preparation was carried out
2 starting from a commercial AgNPs solution (Fluka).
3

4
5 In both cases, the final product was obtained by simple wet-impregnation of the AgNPs sol with the
6
7 microsized TiO₂ K1077 for 24 h at room temperature and final calcination at 450°C for 2 h.
8
9

10 11 12 13 14 *2.2 Industrial ceramic tiles production*

15
16
17 Tiles under investigation were commercial porcelain grès large slabs, manufactured by IrisCeramica
18
19 Group. Industrial porcelain-grès tiles are produced under high pressure by dry-pressing finely
20
21 processed ceramic raw materials with large proportions of quartz, feldspar, and other fluxes and
22
23 finally fired at high temperatures (1200– 1300 °C) in a kiln. Commercial photoactive porcelain-grès
24
25 tiles were subsequently covered at the surface with a mixture of either pure TiO₂ (product label:
26
27 digital Active) or TiO₂ doped with AgNps (product label: Active 2.0), mixed with a tailored SiO₂-
28
29 based ink by digital printing (Projecta Engineering, Italy) (Bianchi 2018). To ensure the requested
30
31 product stability, at the end of the preparation procedure, the tiles were treated at high temperature
32
33 (680 °C) for 80 min and then brushed to remove the powder present at the sample surface and not
34
35 completely stuck. The temperature was precisely chosen to maintain the anatase form of the
36
37 semiconductor and allow the vitrification of the tile surface (Bianchi 2018).
38
39
40
41
42
43
44
45
46
47

48 *2.3 Sample Characterization*

49
50
51 Micro-sized powders were characterized by Transmission Electron Microscopy (TEM). Images
52
53 (either conventional or in high resolution) have been obtained by means a Jeol JEM 3010 UHR
54
55 instrument, equipped with a LaB₆ filament (operating at 300 kV) and an Oxford INCA X-ray energy
56
57 dispersive spectrometer (X-EDS) with a Pentafet Si(Li) detector. Samples were “dry” dispersed on
58
59 lacey carbon Cu grids.
60
61

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

Furthermore, tiles were characterized by SEM and EDX analyses, using a Field Emission Gun Electron Scanning Microscopy LEO 1525, metallization with Cr. Elemental composition was determined using Bruker Quantax EDS.

2.4 Photocatalytic tests

The photocatalytic activity of the samples was tested for NO_x degradation. Their efficiency was monitored using a setup precisely described elsewhere (Ardizzone 2007) operating in static condition. Photocatalytic degradations were conducted in a Pyrex glass cylindrical reactor with an effective volume of 20 L. The gaseous mixture in the reactor was obtained by mixing NO₂ (0.6% in nitrogen) with air humidified at 40%. It is important to underline that we start from an inlet gas of pure NO₂ pulsed into the reactor that, as soon as it comes into contact in the air already present, reaches the chemical equilibrium between NO and NO₂. In this way all the photocatalytic tests have been made using a mixture of NO and NO₂ in air. Two initial concentrations of NO_x in the reactor were tested: 1000 ppb in order to follow the same pollutant concentration requested by the ISO 22197-1:2016 rules (ISO 2016) and 500 ppb for the tests performed under LED light.

Photon sources were provided by a 500W iron halogenide lamp (Jelosil, model HG 500) emitting in the 320–400 nm wavelength range (UV-A) with a specific UV power on the surface of the samples of 20Wm⁻² and by a commercial LED lamp (Philips) emitting >420 nm wavelength irradiating 1000 lux. In all cases, UV and LED lights emissions were measured using a photo radiometer (Delta Ohm – HD2101.2 model).

NO_x photocatalytic tests were performed at 25°C for 6 h. The actual concentration of pollutants (NO, NO₂ and consequently their sum, i.e. NO_x) in the reactor was determined directly by chemiluminescence (Teledyne, Mod. 200E).

3. Results and discussion

Conventional and HR-TEM images of the various samples have been obtained and the relevant results are summarised in Figure 1.

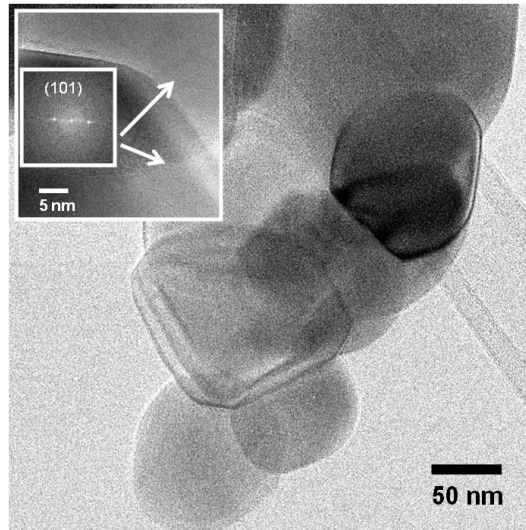


Figure 1a. TEM images of the plain micrometric TiO₂.

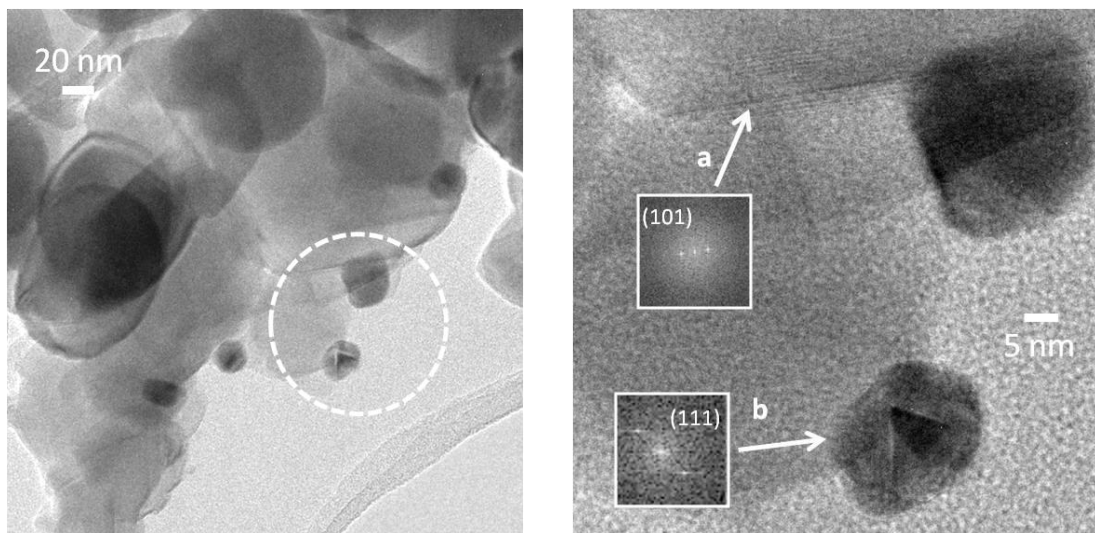


Figure 1b. TEM images of AgNPs-doped TiO₂. Left-hand section: low magnification image. Right-hand image: high magnification image and electron diffraction patterns.

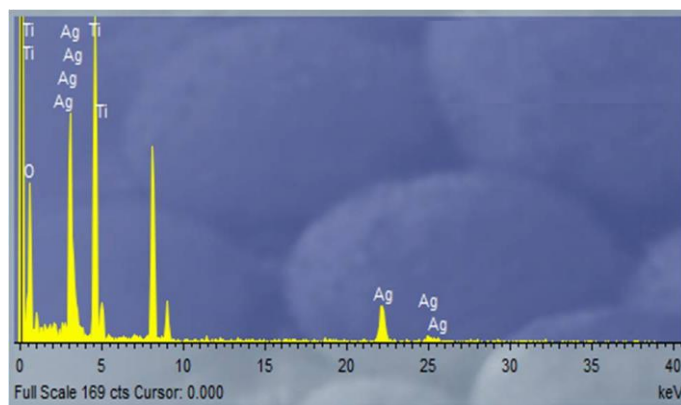


Figure 1c. EDS spectrum relative to the left-hand image reported in figure 1b

The morphological features of plain micrometric TiO_2 remains unchanged after the addition of Ag species as it can be observed in Figure 1a. Both at low magnification (main image) and at high magnification (inset to Figure 1a), large and ordered micro-crystals are evident, almost all exhibiting smooth edges and a 100-130 nm average size dimension. The inspection of the fringe patterns indicated by the arrows (and of the relevant electron diffraction) indicates that the family of planes most frequently exposed is the (101) of the TiO_2 anatase phase [ICDD 21-1272]. As for the samples containing Ag species (see Figure 1b), no morphological peculiarities could be singled out for what concerns the TiO_2 support, indicating that the addition of Ag brings about no changes on it. On the other hand, the presence of Ag species is well assessed by (i) the EDS spectrum reported in the left-hand image of Figure 1b, and (ii) also by the inspection of the fringe patterns/electron diffraction marked with b (see the right-hand image): the crystal planes put into evidence are those related to the (111) family of metallic Ag [ICDD 01-0783] and the average dimensions of these metal particles resides in the nanometric range, being located in the 10-20 nm.

The particles distribution on the ceramic surface was evaluated by SEM analysis. Fig.2 reports that, by means of the digital printing process, it has been possible to disperse in a uniform way the micro-sized particles of the photocatalyst at the surface of the tiles, thank for the ink containing the TiO_2 powder (K1077) and delivered by the printing heads.

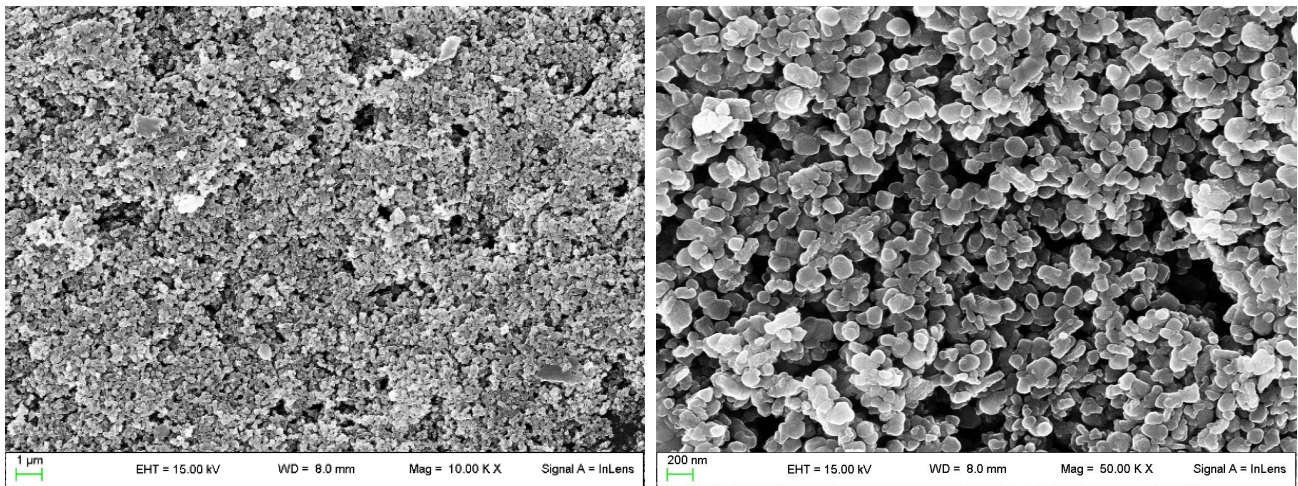


Figure 2 - SEM images of AgNPs-doped TiO₂ coated on the ceramic surface obtained after digital printing process. Left-hand section: low magnification image (10 KX). Right-hand image: high magnification (50 KX).

The single element distribution can be appreciated by EDX characterization carried out during the SEM analysis (Fig.3). Both Ag and Ti are homogeneously dispersed on the tiles surface with some small voids in the Ti presence due to the peculiar tile texture. In fact, the black spots are raised areas of tile structure where TiO₂ has been partially removed by the industrial brushing process carried out downstream to the production and aimed at the removal of the excess photocatalyst powder not perfectly adhered to the ceramic surface. The average amount of TiO₂ coated on the tile surface as 20 g m⁻² as fixed by the digital printer and confirmed by EDS measurements.

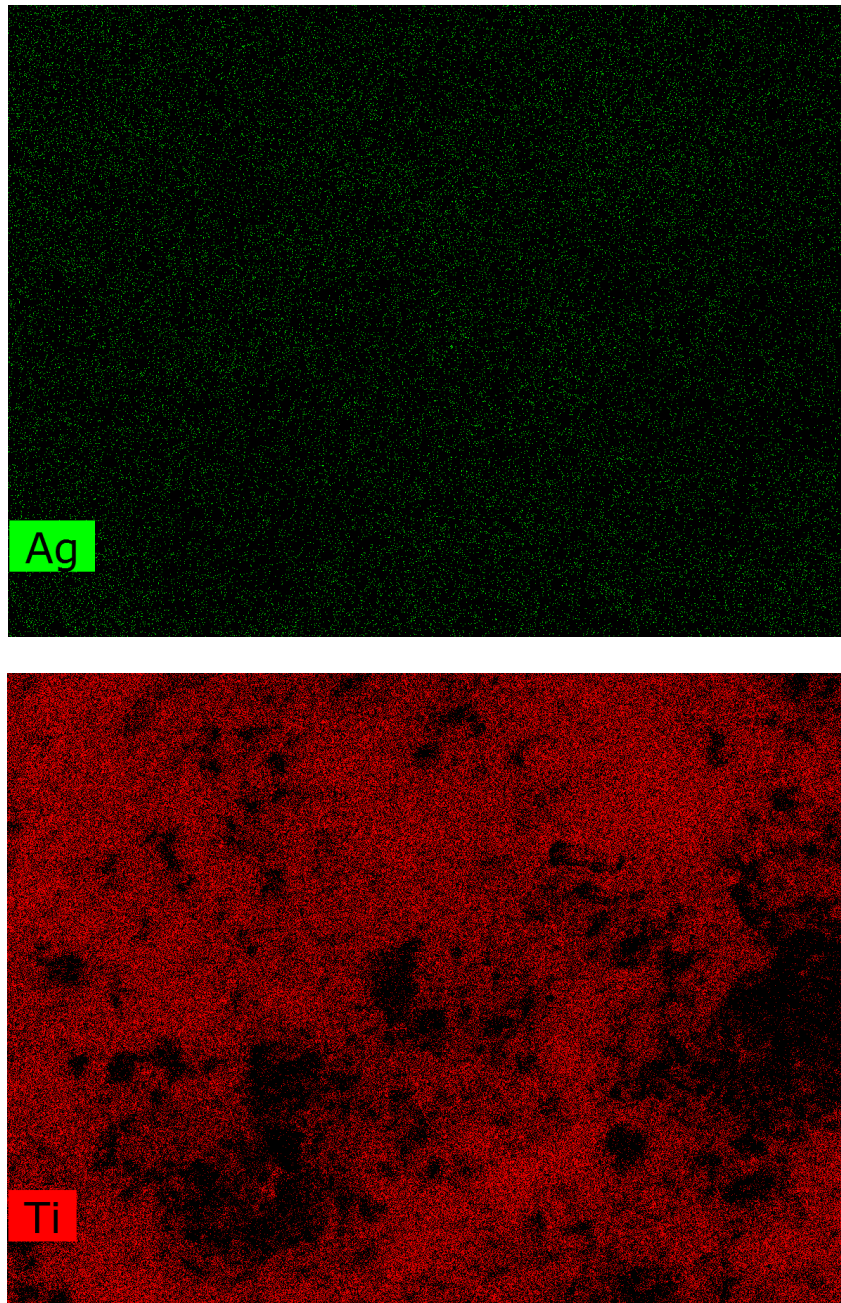


Figure 3 - EDX images of AgNPs-doped micro-sized TiO₂ coated on the ceramic surface obtained after digital printing process. 1) Ag distribution: green spots 2) Ti distribution: red spots

The characterisation results obtained so far in terms of uniformity of the photocatalyst on the surface allow us to predict that the activity towards the NO_x degradation of the ceramic slabs produced with the digital technology (digital Active) can be considerably higher than that obtained with the tiles produced with the old spray technology (spray Active). In addition, the new slabs produced with the

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

K1077 doped with AgNPs (Active 2.0) show, as foreseen by the tests on the photocatalyst in powdery form (Bianchi CL 2018a) that the Ag brings about a beneficial effect in terms of greater efficiency of the ceramic as anti-pollutant material under UVA lights (Fig.4).

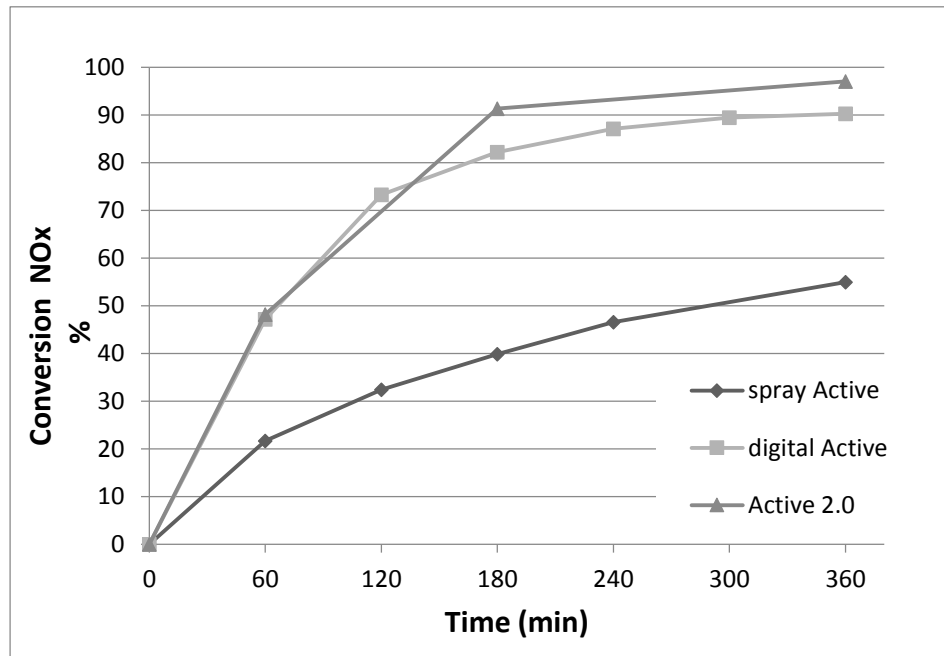


Figure 4 – NOx (1000 ppb) conversion vs time. Tests performed on industrially produces ceramic tiles using: ▲ AgNPs-K1077 digitally printed (Active 2.0); ■ K1077 digitally printed (digital Active); ♦ K1077 coated by spray on the ceramic surface (spray Active).

It is possible to observe that the NOx photoabatement greatly increased from 56 to 90% on passing from spraying technology to digital printing, indicating that the latter allowed a greater uniformity in the surface distribution of the photocatalyst. The presence of the decoration with AgNPs on the K1077 has even more increased the effectiveness of ceramic material up to 96% NOx conversion with UVA lamp.

The general mechanism of NOx oxidation by photocatalysis implies their oxidation to either nitric or nitrous acids by active oxygen species produced on the TiO₂ surface. In particular, in a previous work

1 we investigated the NO_x photodegradation with micrometric TiO₂ using a 60x60 cm tiles activated
2 with TiO₂ (Bianchi 2016). As expected, the reaction follows a pseudo first order respect to both NO
3 and NO₂ to form oxidized species (i.e., NO₃⁻).
4
5
6

7 The major challenge for photocatalytic construction materials lies in their activity even in visible
8 light, and even more so under LED lights where UVA radiation is zero, light source increasingly used
9 both indoors and outdoors for reasons of energy saving.
10
11
12
13

14 Tests carried out on the K1077 powders doped with AgNPs demonstrated the efficacy of the
15 photocatalyst even under LED lights and, for this reason, specific tests were carried out with the same
16 type of light source at 1000 lux also on ceramic tiles (see Table 2). No photoactivity was obtained for
17 the old technology via spray coating, but this is also negligible even via digital printing using the
18 commercial TiO₂. On the contrary, it is possible to observe a good NO_x degradation even in the
19 absence of UVA irradiation for the ceramic surface coated with K1077 doped with AgNPs,
20 confirming the results obtained with the photocatalyst in powder form (Cerrato 2019).
21
22
23
24
25
26
27
28
29
30
31
32

33 Visible light is insufficient to excite electrons from the valence band to the conduction band.
34 Photodegradation under LED as the only source of light is impossible with naked TiO₂ because of its
35 wide band gap of 3.2 eV. Ag nanoparticles absorb visible light due to the plasmonic resonance;
36 moreover, by settling on the TiO₂ surface they create a junction permitting the electron transfer from
37 Ag to TiO₂ and the number of electrons available at the surfaces increases. Consequently, the
38 concentration of photo-generated species at the TiO₂ surfaces is higher and the oxidation and
39 reduction more likely to occur (Stucchi, 2018).
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

Table 2 – NOx degradation (500 ppb) under LED light after 6 h

Sample	NOx degradation under LED light (%)
Ceramic tile sprayed coated with K1077	0%
Ceramic slab digitally printed with K1077	10%
Ceramic slab digitally printed with AgNPs-K1077	46%

4. Conclusions

The digital inkjet printed coatings employed in the present research activity has been demonstrated to possess superior photocatalytic performance owing to both higher exposed surface area and greater volume of deposited anatase, as well as a greater areal distribution density of thinly and thickly coated regions. Moreover, the presence of Ag-NPs has been found to greatly increase the efficiency of the materials in NOx degradation both under UVA and LED lights: this aspect has been thoroughly investigated also in the case of large ceramic slabs, prepared with the same digital printing technology, leading to very interesting results opening the door for antipollution applications in real environment.

5. References

- Amruta S, Vidya SK (2016) Photocatalytic degradation of phenol using Ag core-TiO₂ shell (Ag@TiO₂) nanoparticles under UV light irradiation. *ESPR* 23(20): 20055-20064
- Ardizzone S, Bianchi CL, Cappelletti G, Gialanella S, Pirola C, Ragaini V (2007) Tailored anatase/brookite nanocrystalline TiO₂. The optimal particle features for liquid and-gas-phase photocatalytic reactions. *J Phys Chem C* 111:13222–31.
- Bianchi CL, Pirola C, Galli F, Stucchi M, Morandi S, Cerrato G, Capucci V (2015) Nano and micro-TiO₂ for the photodegradation of ethanol: experimental data and kinetic modelling. *RSC Adv.* 5:53419-53425

1 Bianchi CL, Pirola C, Stucchi M, Sacchi B, Cerrato G, Morandi S, Di Michele A, Carletti A, Capucci
2 V (2016) A New Frontier of Photocatalysis Employing Micro-Sized TiO₂: Air/Water Pollution
3 Abatement and Self-Cleaning/Antibacterial Applications in Semiconductor Photocatalysis -
4 Materials, Ch. 23, 2016, pp. 635-666, Mechanisms and Applications, InTech
5
6
7 Bianchi CL, Pirola C, Galli F, Vitali S, Minguzzi A, Stucchi M, Manenti F, Capucci V (2016) NO_x
8 degradation in a continuous large-scale reactor using full-size industrial photocatalytic tiles. Catal Sci
9 & Tech 6: 2261-2267
10
11
12
13 Bianchi CL, Pirola C, Stucchi M, Cerrato G, Galli F, Di Michele A, Biella S, Chen WF, Koshy P,
14 Sorrell C, Capucci V (2018) Photocatalytic TiO₂: From Airless Jet Spray Technology to Digital Inkjet
15 Printing. In Titanium Dioxide - Material for a Sustainable Environment, Yang D (ed.), ISBN: 978-1-
16 78923-327-8, Ch. 14: 261-279. <http://dx.doi.org/10.5772/intechopen.72790>
17
18
19
20
21 Cerrato P, Galli F, Boffito DC, Operti L, Bianchi CL (2019) Correlation preparation
22 parameters/activity for microTiO₂ decorated with SilverNPs for NO_x photodegradation under LED
23 light. Appl. Catal. B: Eng, under review
24
25
26
27
28 Chen J, Poon CS (2009) Photocatalytic Construction and Building Materials: From Fundamentals to
29 Applications. Build. Environ. 44 [9]: 1899-1906
30
31
32 Fullerton DG, Bruce N, Gordon SB (2008) Indoor Air Pollution from Biomass Fuel Smoke Is a Major
33 Health Concern in the Developing World. Trans. Roy. Soc. Trop. Med. Hyg. 102 [9]: 843-851.
34
35
36
37 Hanaor DA, Sorrell CC (2009) Review of the Anatase to Rutile Phase Transformation. J. Mater. Sci.
38 46 [4]: 855-874
39
40
41 Huang Y, Ho SSH, Lu Y, Niu R, Xu L, Cao J, Lee S (2016) Removal of Indoor Volatile Organic
42 Compounds via Photocatalytic Oxidation: A Short Review and Prospect. Molecules 21 [56]: 20-40
43
44
45 ISO (2016) <https://www.iso.org/standard/65416.html>
46
47
48 Kurmi OP, Semple S, Simkhada P, Smith WCS, Ayres JV (2010) OPD and Chronic Bronchitis Risk
49 of Indoor Air Pollution from Solid Fuel: A Systematic Review and Meta-Analysis. Thorax 65 [3]:
50 221-228
51
52
53
54 Li Y, Wang P, Huang C, Yao W, Wu Q, X Q (2017) Synthesis and photocatalytic activity of ultrafine
55 Ag₃PO₄ nanoparticles on oxygen vacated TiO₂. Appl. Catal. B: Environ. 205: 489-497
56
57
58
59
60
61
62
63
64
65

1
2 Milosevic M, Saponjic Z, Nunney T, Deeks C, Radoicic M, Mitric M, Radetic T (2017) In situ
3 photoreduction of Ag⁺-ions on the surface of titania nanotubes deposited on cotton and cotton/PET
4 fabrics. *ESPR* 24(3): 1597-1610

5
6 Minozzi F, Bianchi CL, Pellini R, Capucci V (2018) Patent WO2016157155

7
8
9 Mo J, Zhang Y, Xu Q, Lamson JJ, Zhao R (2009) Photocatalytic Purification of Volatile Organic
10 Compounds in Indoor Air: A Literature Review. *Atmos. Environ.* 43 [14]: 2229-2246

11
12 Nolan TN, Seery MK, Hinder SJ, Healy LF, Pillai SC (2010) A systematic study of the effect of silver
13 on the chelation of formic acid to a titanium precursor and the resulting effect on the anatase to rutile
14 transformation of TiO₂. *J. Phys. Chem. C* 114: 13026–13034.

15
16
17 Ren H, Koshy P, Chen WF, Qi S, Sorrell CC (2017) Photocatalytic Materials for Air Purification J.
18 *Hazard. Mater.* 325: 340-366

19
20
21 Seery MK, George R, Floris P, Pillai SC (2007) Silver doped titanium dioxide nanomaterials for
22 enhanced visible light photocatalysis. *J. Photochem. Photobiol. A* 189: 258–263

23
24
25 Stucchi M, Bianchi CL, Argirusis C, Pifferi V, Neppolian B, Cerrato G, Boffito DC (2018)
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

Ultrasound assisted synthesis of Ag-decorated TiO₂ active in visible light. *Ultrason* 40(A): 282-288

World Health Organization, 2014
<http://www.who.int/phe/healthtopics/outdoorair/databases/FINALHAPAAPBoD24March2014.pdf?ua=1>).

Yu A, Wang Q, Wang J, Chang C (2017) Rapid synthesis of colloidal silver triangular nanoprisms
and their promotion of TiO₂ photocatalysis on methylene blue under visible light. *Catal. Commun.*
90: 75–78.

Zhao J, Yang X (2003) Photocatalytic Oxidation for Indoor Air Purification: A Literature Review.
Build. Environ. 38 [5]: 645-654