



Arz, M., Annibale, V., Kelly, N., Hanna, J. V., & Manners, I. (2019). Ring-Opening Polymerization of Cyclic Phosphonates: Access to Inorganic Polymers with a PV–O Main Chain. *Journal of the American Chemical Society*, 141(7), 2894-2899.
<https://doi.org/10.1021/jacs.8b13435>

Peer reviewed version

Link to published version (if available):
[10.1021/jacs.8b13435](https://doi.org/10.1021/jacs.8b13435)

[Link to publication record in Explore Bristol Research](#)
PDF-document

This is the author accepted manuscript (AAM). The final published version (version of record) is available online via ACS at <https://pubs.acs.org/doi/abs/10.1021/jacs.8b13435> . Please refer to any applicable terms of use of the publisher.

University of Bristol - Explore Bristol Research

General rights

This document is made available in accordance with publisher policies. Please cite only the published version using the reference above. Full terms of use are available:
<http://www.bristol.ac.uk/red/research-policy/pure/user-guides/ebr-terms/>

Ring-Opening Polymerization of Cyclic Phosphonates: Access to Inorganic Polymers with a P^V-O Main Chain

Marius I. Arz,¹ Vincent T. Annibale,¹ Nicole L. Kelly,^{2,3} John V. Hanna² and Ian Manners^{1,4*}

¹School of Chemistry, University of Bristol, Cantock's Close, Bristol, BS8 1TS, UK

²Department of Physics, University of Warwick, Gibbet Hill Rd., Coventry, CV4 7AL, UK

³MAS CDT, Senate House, University of Warwick, Coventry, CV4 7AL, UK


⁴Department of Chemistry, University of Victoria, Victoria, BC V8W 3V6, Canada

Supporting Information Placeholder

ABSTRACT: We describe a new class of inorganic polymeric materials featuring a main chain consisting of P^V-O bonds and aryl side groups, which were obtained with >70 repeat units by ring-opening polymerization of cyclic phosphonates. This monomer-polymer system was found to be dynamic in solution enabling selective depolymerization under dilute conditions, which can be tuned by varying the substituents. The polymers show high thermal stability to weight loss and can be easily fabricated into self-standing thin films. Structural characterizations of the cyclic 6- and 12-membered ring precursors are also described.

The development of new polymers based on p-block elements is of continued interest due to the possibility to find materials with unique properties which may lead to new applications in polymer and material science.^[1,2] For example, polysiloxanes [SiRR'-O]_n (**A**, Chart 1) evolved from their early discovery as a laboratory curiosity to widely used versatile materials, mainly resulting from the fruitful interplay of the unique features imposed by the Si-O main chain and the tuneable carbon-based (organic) side chains.^[3] In this context, polymers consisting of a main chain of alternating P-O bonds with modifiable organic side chains such as polyphosphonates of type [-P(O)R-O-]_n (**B**, Chart 1) may as well exhibit interesting properties, but have only been briefly noted in the literature.

Chart 1. Different types of inorganic polymers relevant to this work^a

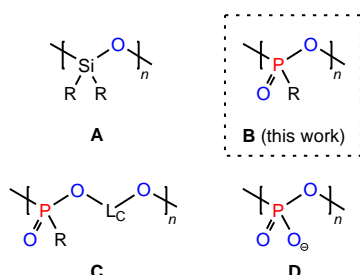

^a L_c = carbon-based linker.


An early report from 1963 described the insoluble material obtained from dehydrochlorination of MePOCl₂ and MePO(OH)₂ as polymeric [-P(O)Me-O-]_n, but no characterization was provided.^[4] The formation of poorly characterized polymers of type **B** as decomposition products of transiently generated dioxophosphoranes (RPO₂) under pyrolytic conditions was also mentioned.^[5] Polyphosphonates **B** can be regarded as hybrids between polyphosphoesters [-P(O)R-O-L_c-O-] (**C**, Chart 1; L_c = carbon-based linker), an emerging class of flame-retardant polymers recently recognized for their promising biomedical applications,^[6,7] and ionic polyphosphates [PO₃]_nⁿ⁻ (**D**, Chart 1), which are applied in diverse areas ranging from cation sequestering, fertilizers, flame retardants and in biomedicine.^[8] Analogies with polynucleotides, which also possess P-O units in the main chain, are also intriguing. These considerations all suggest that polyphosphonates **B** are interesting synthetic targets with potentially useful properties.

The polymers of type **B** are polymeric derivatives of cyclic phosphonates, which remained surprisingly unexplored since the early discovery of "PhPO₂" by Michaelis and Rothe in 1892.^[9] Only two cyclic phosphonates, specifically the six-membered rings (tBuPO₂)₃^[10] and [(2-MeO-C₆H₄)PO₂]₃,^[11] have been previously structurally characterized by single-crystal X-ray diffraction analysis (XRD). Notably, (nPrPO₂)₃ (T3P©) is used as a particularly mild dehydration reagent for various synthetic applications,^[12] but little is known about the structure of this reagent.^[8b] The related polyphosphates [-P(OR')(O)-O-]_n (so-called "Langheld esters" with R' = alkyl or silyl group) also find use as mild dehydration reagents, but consist of complex mixtures of short-chain cycles and oligomers.^[13] Herein, we demonstrate that the ring-opening polymerization (ROP) of cyclic phosphonates leads to high molar mass polyphosphonates of type **B** with >70 repeat units.

ROP of inorganic heterocycles provides an important route to high molar mass polymers based on p-block elements.^[1-3,14] As a prerequisite to an exploration of a ROP

route to polyphosphonates using sterically demanding substituents, we synthesized the cyclic monomers (RPO₂)₃ [**1R**₃; R = Ph (**1Ph**₃), 4-tBu-C₆H₄ (**1^tBuAr**₃), Mes (**1Mes**₃), 4-tBu-2,6-Me₂-C₆H₂ (**1^tBuAr'**₃)] via the dehydrochlorination of phosphonic dichlorides RPOCl₂ and phosphonic acids RPO(OH)₂ in refluxing toluene (Scheme 1). After workup, the compounds **1R**₃ were isolated as hydrolytically sensitive, colourless solids and fully characterized by solution NMR spectroscopy, single-crystal XRD, ESI-MS, FT-IR spectroscopy and elemental analysis (see SI, section 3).^[15]


Scheme 1. Synthesis of the cyclic phosphonates 1R₃^a

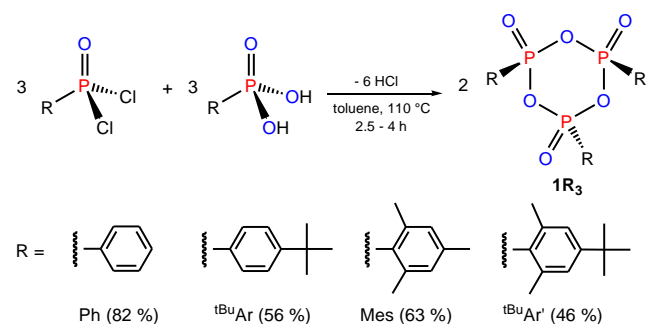

^ayields are given in brackets.

Single crystal XRD analyses of **1Mes**₃, **1^tBuAr**₃ and **1^tBuAr'**₃ confirmed that these cyclic phosphonates consist of six-membered (PO)₃ rings in the solid state, which adopt boat conformations with one aryl substituent in *trans* orientation [Figure 1, a)]. In contrast, crystallisation of **1Ph**₃ yielded reproducibly minor quantities of single crystals consisting of the 12-membered ring **1Ph**₆ [Figure 1, b)], which represents the first example of a neutral (PO)_n ring with n > 3 [ionic cyclophosphates (PO₃)ⁿ⁻ (“metaphosphates”) were structurally characterized for ring sizes up to n = 12].^[16]

Figure 1. Molecular structures of **1Mes**₃ (a) and **1Ph**₆ (b) in the single crystal; H atoms omitted for clarity.

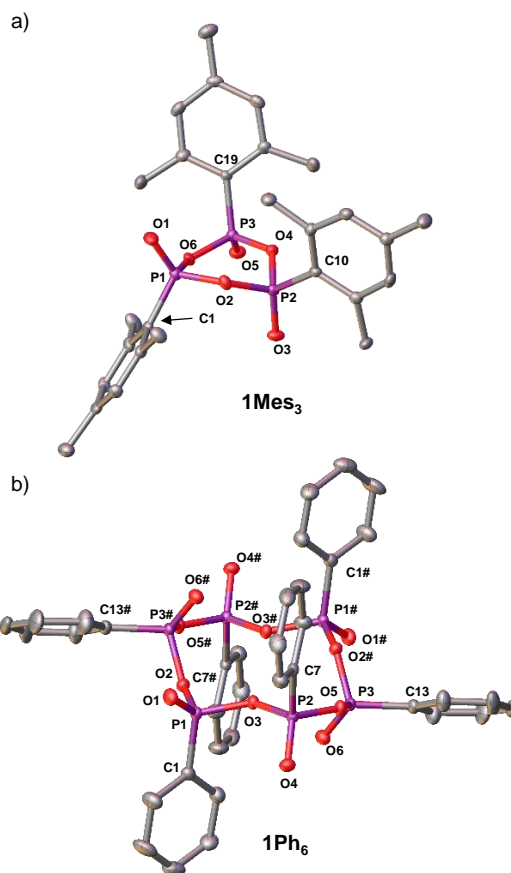


¹H, ¹³C and ³¹P NMR spectroscopy in CDCl₃ and toluene-*d*₆ revealed that all cyclotriphosphonates **1R**₃ consist of six-membered rings with time-averaged C_s symmetry in solution, leading to diagnostic AB₂ patterns in the ³¹P{¹H} NMR spectra in the range of 0.8 – 4.1 ppm. Minor signals of low intensity (<10 %) were also visible in the ³¹P{¹H} NMR spectra in several instances (see SI, section 3), which could be attributed to oligomeric **1R**_n species. We speculate that one of these species could be the cyclohexaphosphonate **1R**₆, which was also found in the single crystal structure of **1Ph**₆. This is corroborated by the ESI-MS spectra obtained from CH₂Cl₂ solutions of **1R**₃, which showed the expected ion peaks for the cyclotriphosphonates **1R**₃ and also intense ion peaks for the cyclohexaphosphonates **1R**₆.

The dynamic covalent chemistry of the cyclotriphosphonates **1R**₃ in solution was further investigated by mixing **1Ph**₃ and **1Mes**₃ in CDCl₃, which led to highly complex ³¹P{¹H} NMR spectra after ca. 24 h at ambient temperature, suggesting that ring-opening / ring-closure equilibria occur in solution leading to substituent scrambling, as further confirmed by ESI-MS (see SI, section 3.5). In comparison, variable temperature ¹H and ³¹P NMR spectroscopy of 0.5 M solutions of **1R**₃ in CDCl₃ revealed no significant changes in the temperature range of –60 °C to +52 °C.

Studies of the cyclic precursors **1R**₃ by Differential Scanning Calorimetry (DSC) suggested that melting of **1R**₃ is accompanied by thermally-induced ROP leading to the polymers **1R**_n. In each case, the first heating cycles of **1R**₃ displayed an intense endothermic signal characteristic of a melting of the material, and a small ROP exotherm was discernible (except for **1^tBuAr'**₃). The melting transition was absent in the subsequent heating cycles and instead a new deflection associated with a change in gradient emerged,

which is diagnostic of a glass transition, providing an indication for the formation of polymeric $1R_n$. The glass transition temperatures (T_g) of the materials differed significantly depending on the aryl group [$T_g = 66$ ($1Ph_n$), 103 ($1^{tBu}Ar_n$), 133 ($1Mes_n$), 140 °C ($1^{tBu}Ar'_n$)], whereby higher degrees of substitution lead to larger T_g values, probably due to enhanced rigidity of the polymer chains.^[17]


Scheme 2. Synthesis of the polymers $1R_n$ via thermal ROP of $1R_3$.

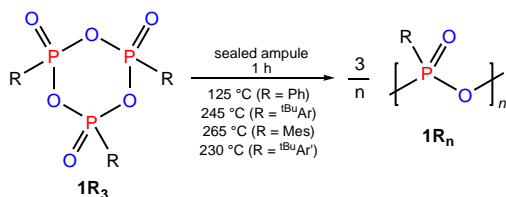

The preparative synthesis of the polymers $1R_n$ was achieved by thermal ROP of the cyclic precursors $1R_3$ (Scheme 2). The monomers were heated slightly above the temperature of melting of $1R_3$ as previously determined by DSC, which led to a considerable increase of the viscosity of the melt. After keeping the materials under thermal ROP conditions for 1 h and cooling to ambient temperature, glassy solids were obtained. These solids showed only the previously observed glass transitions for $1R_n$ in the DSC analysis and distinct changes were observed for the $\nu(P-O)$ absorption bands in the ATR FT-IR spectra, which can be explained by the changes in the P–O bond energies due to ROP (see SI, section 4). Slow decomposition to the corresponding phosphonic acids occurred upon exposure of the polymers $1R_n$ to atmospheric moisture, but the materials were found to be indefinitely stable under a dry nitrogen atmosphere at ambient temperature.

The polymer $1Ph_n$ was found to be insoluble in common organic solvents, whereas $1^{tBu}Ar_n$ readily dissolved in $CDCl_3$, toluene or hexane, but rapidly depolymerised in solution to the cyclic precursor $1^{tBu}Ar_3$ according to 1H and ^{31}P NMR spectroscopy, preventing further analysis of these materials by solution-based techniques. By contrast, the 1H and ^{31}P NMR spectra of the polymers $1Mes_n$ and $1^{tBu}Ar'_n$ (data discussed below) containing sterically more congested side chains with methyl groups in the *ortho* positions showed only slow depolymerization to the cyclic precursors $1Mes_3$ and $1^{tBu}Ar'_3$ in solution ($t_{1/2} > 15$ days), suggesting that these polymers are kinetically trapped in solution by the presence of the bulkier side groups. The identity of the polymers $1Ph_n$ and $1^{tBu}Ar_n$ was further corroborated by their solid state ^{31}P CP-MAS NMR spectra [Figure 2, a)], showing broad isotropic ^{31}P resonances at 1.3 ppm and 0.2 ppm, respectively. These signals are similar to the ^{31}P NMR signals of $1Mes_n$ and $1^{tBu}Ar'_n$ in the solid state [$\delta_{iso} = 0.3$ ppm ($1Mes_n$), -1.5 ppm ($1^{tBu}Ar'_n$)]. In $CDCl_3$ solution, the polymers $1Mes_n$ and $1^{tBu}Ar'_n$ give rise to broad resonances in the 1H and $^{13}C\{^1H\}$ NMR spectra and three broad signals are observed in the $^{31}P\{^1H\}$ NMR spectra ($\delta = -1.3 - 1.5$ ppm) with a rough intensity distribution of 2:1:1 [Figure 2, b)] assigned to *rm/mr* and either *mm* or *rr* triads, respectively, suggesting the presence of stereoirregular atactic polymer chains, as expected from the forcing conditions of the thermal ROP.^[18] Notably, the much broader ^{31}P NMR signals of the polymers $1R_n$ appear in a similar spectral region to those of the cyclic monomers $1R_3$ in $CDCl_3$ (0.8 – 4.1 ppm).


Figure 2. a) Representative ^{31}P CP-MAS NMR spectrum of $1^{tBu}Ar_n$; the inset shows the isotropic ^{31}P NMR chemical shifts of all materials. b) $^{31}P\{^1H\}$ NMR spectrum of $1Mes_n$ in $CDCl_3$.

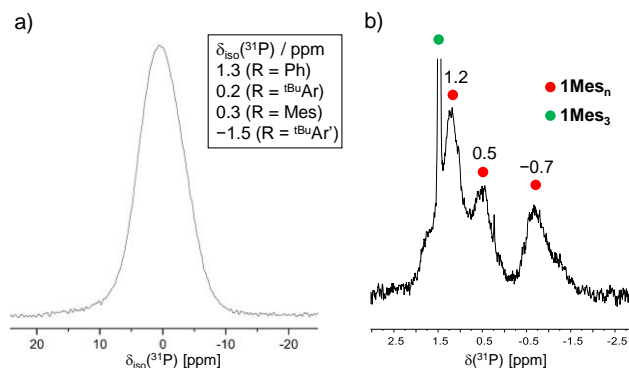

Further evidence for the assigned structure for $1Ph_n$ was provided by treatment of a suspension of $1Ph_n$ in $CDCl_3$ with 4-dimethylaminopyridine (4-dmap), leading to complete dissolution of all insoluble material due to selective formation of (4-dmap)PhPO₂ (**2Ph**; Figure 3),^[19] which is the Lewis base adduct of the transient dioxophosphorane PhPO₂,^[5c,20,21] i.e. the monomer unit of $1Ph_n$. The adduct **2Ph** as well as its derivative (4-dmap)MesPO₂ (**2Mes**) were subsequently synthesized from $1R_3$ and 4-dmap and fully characterized by XRD, NMR and elemental analysis (for details see SI, section 5). Remarkably, the adducts **2R** (R = Ph, Mes) exist in a dissociative equilibrium with $1R_3$ and free 4-dmap in $CDCl_3$ solution. The estimated equilibrium constants derived by NMR spectroscopy amount to $K = 1.11 \cdot 10^{-7}$ (**2Ph**) and $3.49 \cdot 10^{-4} \text{ mol L}^{-1}$ (**2Mes**). Attempts to abstract the 4-dmap substituent from **2R** with the Lewis-acidic boranes BPh₃ or B(C₆F₅)₃ resulted in either mixtures of mainly the six-membered rings $1R_3$ and (4-dmap)·BPh₃ or the “push-pull” adduct (4-dmap)PhPO₂[B(C₆F₅)₃] [**2Ph**·B(C₆F₅)₃, Figure 3], which was also isolated and fully characterized, but no formation of polymeric $1R_n$ was detected during these reactions by NMR spectroscopy.


Analysis of dilute solutions of $1Mes_n$ and $1^{tBu}Ar'_n$ in CH_2Cl_2 by dynamic light scattering (DLS) revealed the presence of particles with average hydrodynamic radii of 3.1 and 3.3 nm, respectively. These values corroborate the presence of polymeric material and can be roughly compared to polystyrene particles of similar size, which possess weight-average molecular weights (M_w) of 14,400 or 16,100 g mol⁻¹, corresponding to degrees of polymerization (DP_w) for $1Mes_n$ and $1^{tBu}Ar'_n$ of ca. 79 and 72 repeat units. These molecular weights are reasonably consistent with the MALDI-ToF mass spectra of $1Mes_n$ and $1^{tBu}Ar'_n$ [Figure, 4a)], which suggest an upper limit to the degree of polymerization of >70, corresponding to molecular weights of ca. 12,900 and 17,300 g mol⁻¹, respectively. A significant decrease of intensity towards high molar masses was observed in the MALDI-ToF mass spectra, which indicates that short-chain molecules are preferably ionized and the measured intensity distribution does not reflect the molecular weight distribution determined by DLS.

Figure 3. a) Reaction of **2Ph** with B(C₆F₅)₃ to give **2Ph**·B(C₆F₅)₃; b) Molecular structures by single crystal X-ray diffraction of b) **2Ph** and c) **2Ph**·B(C₆F₅)₃ (H atoms omitted for clarity).

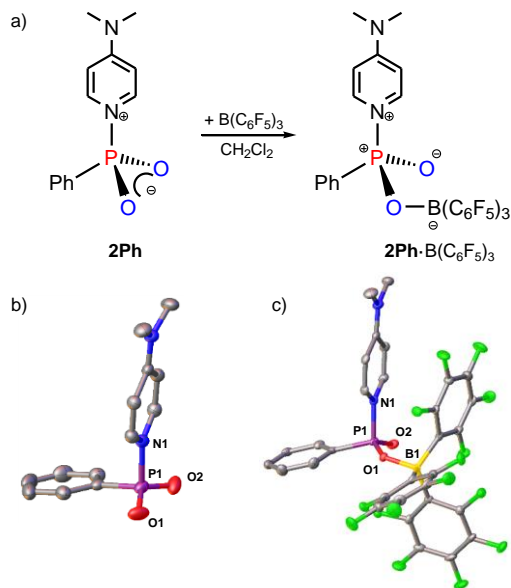

Thermal gravimetric analysis (TGA) revealed a high thermal stability to weight loss for the polymers **1R_n** with high $T_{5\% \text{ loss}}$ values, which range from ca. 310 – 380 °C (see SI, section 4). TGA also revealed low ceramic yields (ca. 10 %), indicating an almost complete thermal decomposition and vaporization of the materials at 575 °C. Initial studies aiming at the fabrication of the polymers revealed that self-standing films of **1Mes_n** can be prepared by drop-casting of a concentrated solution in 1,2-dichloroethane onto a Teflon mold [Figure, 4b)], providing evidence for the promising processability properties of these materials.

Figure 4. a) Representative MALDI-ToF mass spectrum of **1Mes_n** showing the presence of high molecular weight polymer; for details on the MALDI-ToF mass spectra of **1Mes_n** and **1^tBuAr'_n** see SI, sections 4.3 and 4.4. b) Free-standing film (12 mm × 12 mm) of **1Mes_n** prepared by drop-casting from 1,2-dichloroethane solution.

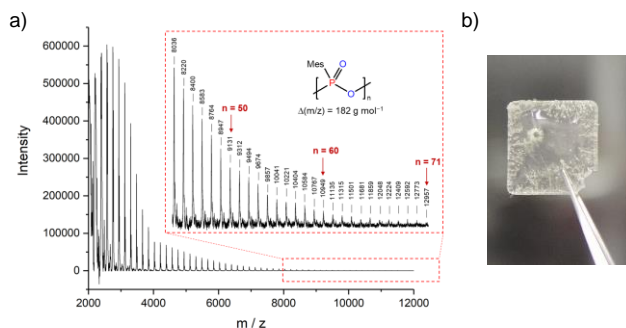

In summary, we have established synthetic access to novel polymers consisting of a P–O main chain and aryl groups at phosphorus via ROP of cyclic phosphonates. The relatively small ROP exotherms detected by DSC suggest that ΔH_{ROP}^0 is low for these materials, as expected for monomers with bulky substituents, rationalizing that ROP only occurs at high monomer concentration, i.e. in the melt phase. Careful adjustment of the side groups leads to significant changes in the properties of the polymers, including the solubility and the stability in solution towards depolymerization. This tuneable reversible depolymerization behaviour

in solution, which can be furthermore chemically triggered as demonstrated by the depolymerization upon addition of a Lewis-base, suggests potential for the development of recyclable materials.^[22] The simple fabrication, the high thermal stability and the large diversity of possible organic side groups opens up a large scope for future explorations of these new inorganic soft materials.

ASSOCIATED CONTENT

Supporting Information

The Supporting Information is available free of charge on the ACS Publications website.

Crystallographic data for MesPOCl₂, MesPO(OH)₂, **1Ph₆**, **1Mes₃**, **1^tBuAr'₃**, **1^tBuAr'₃**, **2Ph**, **2Mes** and **2Ph·B(C₆F₅)₃** (also deposited with Cambridge Structural Database under the deposition numbers CCDC 1882836 – 1882844) (CIF)

Details of syntheses, characterization and analytical data of starting materials, cyclic monomers and polymers including single-crystal XRD studies (PDF)

AUTHOR INFORMATION

Corresponding Author

*ian.manners@bristol.ac.uk, imanners@uvic.ca

Notes

The authors declare no competing financial interests.

ACKNOWLEDGMENT

M.I.A. acknowledges the Alexander von Humboldt foundation for a Feodor Lynen research fellowship, V.T.A. thanks the European Union for a Marie Curie Fellowship (H2020-MSCA-IF-2016_748371) and N.L.K. thanks EPSRC for a PhD studentship through the EPSRC Centre for Doctoral Training in Molecular Analytical Science (EP/L015307/1). J.V.H. thanks the EPSRC, the University of Warwick and the Birmingham Science City Program for partial funding of the solid state NMR infrastructure at Warwick. The latter program accessed the Birmingham Science City Advanced Materials Project 1: Creating and Characterising Next Generation Advanced Materials, which derived support from Advantage West Midlands (AWM) and the European Regional Development Fund (ERDF). I.M. thanks the Canadian government for a Canada 150 Research Chair and the University of Bristol for support. We also thank Dr. H. A. Sparkes for crystallographic contributions and R. L. N. Hailes for help with the MALDI-ToF MS measurements.

REFERENCES

- Reviews: (a) Mark J. E.; Allcock, H. R.; West, R. *Inorganic Polymers*, 2nd ed.; Oxford University Press: New York, 2005. (b) Chivers, T.; Manners, I. *Inorganic Rings and Polymers of the p-Block Elements: From Fundamentals to Applications*, The Royal Society of Chemistry, Cambridge, 2009. (c) Jäkle, F. Advances in the Synthesis of Organoborane Polymers for Optical, Electronic, and Sensory Applications. *Chem. Rev.* **2010**, *110* (7), 3985 – 4022. (d) He, X.; Baumgartner, T. Conjugated main-group polymers for optoelectronics. *RSC Adv.* **2013**, *3* (29), 11334 – 113350. (e) Leitao, E. M.; Jurca, T.; Manners, I. Catalysis in service of main group chemistry offers a versatile approach to p-block molecules and materials. *Nat. Chem.* **2013**, *5* (10), 817 – 829. (f) Caseri, W. Poly-

- stannanes: processible molecular metals with defined chemical structures. *Chem. Soc. Rev.* **2016**, *45* (19), 5187 – 5199. (g) Priegert, A. M.; Rawe, B. W.; Serin, S. C.; Gates, D. P. Polymers and the p-block elements. *Chem. Soc. Rev.* **2016**, *45* (4), 922 – 953. (h) *Main Group Strategies towards Functional Hybrid Materials*; Jäkle, F., Baumgartner T., Eds.; John Wiley & Sons: Hoboken, NJ, 2018.
- (2) Selected recent developments: (a) Chung, W. J.; Griebel, J. J.; Kim, E. T.; Yoon, H.; Simmonds, A. G.; Jun Ji, H.; Dirlam, P. T.; Glass, R. S.; Wie, J. J.; Nguyen, N. A.; Guralnick, B. W.; Park, J.; Somogyi, A.; Theato, P.; Mackay, M. E.; Sung, Y.-E.; Char, K.; Pyun, J. The use of elemental sulfur as an alternative feedstock for polymeric materials. *Nat. Chem.* **2013**, *5* (6), 518 – 524. (b) Harypersad, S.; Foucher, D. Alternating polystannanes: syntheses and properties. *Chem. Comm.* **2015**, *51* (33), 7120 – 7123. (c) Ledoux, A.; Larini, P.; Boisson, C.; Monteil, V.; Raynaud, J.; Lacôte, E. Polyboramines for Hydrogen Release: Polymers Containing Lewis Pairs in their Backbone. *Angew. Chem. Int. Ed.* **2015**, *54* (52), 15744 – 15749. (d) Carrera, E. I.; Seferos, D. S. Semiconducting Polymers Containing Tellurium: Perspectives Toward Obtaining High-Performance Materials. *Macromolecules* **2015**, *48* (2), 297 – 308. (e) Matsumura, Y.; Ishidoshiro, M.; Irie, Y.; Imoto, H.; Naka, K.; Tanaka, K.; Inagi, S.; Tomita, I. Arsole-Containing π -Conjugated Polymer by the Post-Element-Transformation Technique. *Angew. Chem. Int. Ed.* **2016**, *55* (48), 15040 – 15043. (f) Lorenz, T.; Crumbach, M.; Eckert, T.; Lik, A.; Helten, H. Poly(p-phenylene iminoborane): A Boron-Nitrogen Analogue of Poly(p-phenylene vinylene). *Angew. Chem. Int. Ed.* **2017**, *56* (10), 2780 – 2784. (g) Cavaye, H.; Clegg, F.; Gould, P. J.; Ladyman, M. K.; Temple, T.; Dossi, E. Primary alkyl phosphine-borane polymers: Synthesis, low glass transition temperature, and a predictive capability thereof. *Macromolecules* **2017**, *50* (23), 9239 – 9248. (h) Press, E. M.; Marro, E. A.; Surampudi, S. K.; Siegler, M. A.; Tang, J. A.; Klauson, R. S. Synthesis of a Fragment of Crystalline Silicon: Poly(Cyclosilane). *Angew. Chem. Int. Ed.* **2017**, *56* (2), 568 – 572. (i) Thiedemann, B.; Gliese, P. J.; Hoffmann, J.; Lawrence, P. G.; Sönnichsen, F. D.; Staubitz, A. High molecular weight poly(*N*-methyl-*B*-vinylazaborine) – a semi-inorganic B–N polystyrene analogue. *Chem. Comm.* **2017**, *53* (53), 7258 – 7261. (j) Dück, K.; Rawe, B. W.; Scott, M. R.; Gates, D. P. Polymerization of 1-Phosphaisoprene: Synthesis and Characterization of a Chemically Functional Phosphorus Version of Natural Rubber. *Angew. Chem. Int. Ed.* **2017**, *56* (32), 9507 – 9511. (k) Pandey, S.; Lönnecke, P.; Hey-Hawkins, E. Phosphorus–Boron-Based Polymers Obtained by Dehydrocoupling of Ferrocenylphosphine–Borane Adducts. *Eur. J. Inorg. Chem.* **2014**, *2014* (14), 2456 – 2465. (l) Resendiz-Lara, D. A.; Stubbs, N. E.; Arz, M. I.; Pridmore, N. E.; Sparkes, H. A.; Manners, I. Boron-nitrogen main chain analogues of polystyrene: poly(*B*-aryl)aminoboranes via catalytic dehydrocoupling. *Chem. Comm.* **2017**, *53* (85), 11701 – 11704. (m) De Albuquerque Pinheiro, C. A.; Roiland, C.; Jehan, P.; Alcaraz, G. Solventless and Metal-Free Synthesis of High-Molecular-Mass Polyaminoboranes from Diisopropylaminoborane and Primary Amines. *Angew. Chem. Int. Ed.* **2018**, *57* (6), 1519 – 1522. (n) Adams, G. M.; Colebatch, A. L.; Skornia, J. T.; McKay, A. I.; Johnson, H. C.; Lloyd-Jones, G. C.; Macgregor, S. A.; Beattie, N. A.; Weller, A. S. Dehydropolymerization of H_3B-NMe_2 To Form Polyaminoboranes Using [Rh(Xantphos-alkyl)] Catalysts. *J. Am. Chem. Soc.* **2018**, *140* (4), 1481 – 1495. (o) Parke, S. M.; Hupf, E.; Matharu, G. K.; de Aguiar, I.; Xu, L.; Yu, H.; Boone, M. P.; de Souza, G. L. C.; McDonald, R.; Ferguson, M. J.; He, G.; Brown, A.; Rivard, E. Aerobic Solid State Red Phosphorescence from Benzobismole Monomers and Patternable Self-Assembled Block Copolymers. *Angew. Chem. Int. Ed.* **2018**, *57* (45), 14841 – 14846. (p) Meng, B.; Ren, Y.; Liu, J.; Jäkle, F.; Wang, L. p - π Conjugated Polymers Based on Stable Triarylborane with *n*-Type Behavior in Optoelectronic Devices. *Angew. Chem. Int. Ed.* **2018**, *57* (8), 2183 – 2187.
- (3) Mark, J. E.; Schaefer, D. W.; Lin, G. *The Polysiloxanes*, Oxford University Press: New York, 2015.
- (4) Cherbuliez, E.; Weber, G.; Rabinowitz, J. Note sur les anhydrides et monoesters méthane phosphoniques et dodécane phosphoniques. *Helv. Chim. Acta* **1963**, *46* (6), 2461 – 2464.
- (5) (a) Clapp, C. H.; Westheimer, F. H. Monomeric methyl metaphosphate. *J. Am. Chem. Soc.* **1974**, *96* (21), 6710 – 6714. (b) Sigal, I.; Loew, L. A phosphorus analog of α -pyrone and evidence for monomeric mesitylmetaphosphate. *J. Am. Chem. Soc.* **1978**, *100* (20), 6394 – 6398. (c) Quin, L. D. Practical aspects of the chemistry of metaphosphates and other transient dioxophosphoranes. *Coord. Chem. Rev.* **1994**, *137*, 525 – 559.
- (6) (a) Ranganathan, T.; Zilberman, J.; Farris, R. J.; Coughlin, E. B.; Emrick, T. Synthesis and Characterization of Halogen-Free Antiflammable Polyphosphonates Containing 4,4'-Bishydroxydeoxybenzoin. *Macromolecules* **2006**, *39* (18), 5974 – 5975. (b) Chen, L.; Wang, Y.-Z. Aryl Polyphosphonates: Useful Halogen-Free Flame Retardants for Polymers. *Materials* **2010**, *3* (10), 4746 – 4760. (c) Monge, S.; Cannicconi, B.; Graillet, A.; Robin, J.-J. Phosphorus-containing polymers: a great opportunity for the biomedical field. *Biomacromolecules* **2011**, *12* (6), 1973 – 1982. (d) Penczek, S.; Pretula, J. B.; Kaluzynski, K.; Lapienis, G. Polymers with Esters of Phosphoric Acid Units: From Synthesis, Models of Biopolymers to Polymer – Inorganic Hybrids. *Isr. J. Chem.* **2012**, *52* (3-4), 306 – 319. (e) Montebault, V.; Fontaine, L. In: *Phosphorus-Based Polymers: From Synthesis to Applications*; S. Monge, G. David, Eds.; The Royal Society of Chemistry: Cambridge, 2014, chapter 6, 97 – 124. (f) Steinbach, T.; Wurm, F. R. Poly(phosphoester)s: A New Platform for Degradable Polymers. *Angew. Chem. Int. Ed.* **2015**, *54* (21), 6098 – 6108. (g) Bauer, K. N.; Tee, H. T.; Velencoso, M. M.; Wurm, F. R. Main-chain poly(phosphoester)s: History, syntheses, degradation, bio- and flame-retardant applications. *Prog. Polym. Sci.* **2017**, *73*, 61 – 122.
- (7) Zhang, F.; Zhang, S.; Pollack, S. F.; Li, R.; Gonzalez, A. M.; Fan, J.; Zou, J.; Leininger, S. E.; Pavia-Sanders, A.; Johnson, R.; Nelson, L. D.; Raymond, J. E.; Elsabahy, M.; Hughes, D. M. P.; Lenox, M. W.; Gustafson, T. P.; Wooley, K. L. Improving paclitaxel delivery: in vitro and in vivo characterization of PEGylated polyphosphoester-based nanocarriers. *J. Am. Chem. Soc.* **2015**, *137* (5), 2056 – 2066.
- (8) (a) Rashchi, F.; Finch, J. A. Polyphosphates: A review their chemistry and application with particular reference to mineral processing. *Miner. Eng.* **2000**, *13* (10 – 11), 1019 – 35. (b) Omelon, S. J.; Grynypas, M. D. Relationships between Polyphosphate Chemistry, Biochemistry and Apatite Biomineralization. *Chem. Rev.* **2008**, *108* (11), 4694 – 4715. (c) Liu, G.; Chen, W.; Yu, J. A novel process to prepare ammonium polyphosphate with crystalline form II and its comparison with melamine polyphosphate. *Ind. Eng. Chem. Res.* **2010**, *49* (23), 12148 – 12155. (d) Morrissey, J. H.; Choi, S. H.; Smith, S. A. Polyphosphate: an ancient molecule that links platelets, coagulation, and inflammation. *Blood* **2012**, *119* (25), 5972 – 5979.
- (9) (a) Michaelis, A.; Rothe, F. Über die den Nitroverbindungen entsprechenden Phosphorderivate. *Ber. Dt. Chem. Ges.* **1892**, *25*, 1747 – 1752. (b) Cherbuliez E.; Baehler, B.; Hunkeler, F.; Rabinowitz, J. Recherches sur la formation et la transformation des esters XXVIII. Sur la phosphorylation des alcools par les oxydes phosphoniques. *Helv. Chim. Acta* **1961**, *44* (6), 1812 – 1815. (c) Moedritzer, K. Synthesis and Properties of Phosphinic and Phosphonic Acid Anhydrides. *J. Am. Chem. Soc.* **1961**, *83* (21), 4381 – 4384. (d) Baer, E.; Sarma, G. R. Phosphonolipids. XII. Synthesis of phosphonolipid metabolites. L-alpha-glyceryl(2-aminoethyl) phosphonate. *Can. J. Biochem.* **1967**, *45* (11), 1755 – 1761. (e) Bracher, S.; Cadogan, J. I. G.; Gosney, I.; Yaslak, S. The generation and trapping of a monomeric arylidioxophosphorane ('metaphosphonate'). *J. Chem. Soc., Chem. Commun.* **1983**, 857 – 858. (f) Kobayashi, S.; Chow, T. Y.; Kawabata, H.; Saegusa, T. Ring-opening copolymerization of 2,4-bisphenyl-1,3,2,4-dioxadiphosphetane-2,4-dioxide with oxetane via zwitterion intermediates. *Polym. Bull.* **1986**, *16* (4), 269 – 276. (g) Ueda, M.; Honma, T. Synthesis of polyamides by direct polycondensation with phenylphosphonic anhydride as an activating agent. *Makromol. Chem.* **1989**, *190* (7), 1507 – 1514. (h) Fuchs, S.; Schmidbaur, H. Phosphonic Acid Anhydrides [RPO]₂: Oligomerization and Structure. *Z. Naturforsch.* **1995**, *50b*, 855 – 858.
- (10) Diemert, K.; Kuchen, W.; Poll, W.; Sandt, F. A Convenient Synthesis of Phosphonic Anhydrides – Trimers [RPO]₃ (R = *tert*-Butyl, 2-Methylphenyl, 2,4,6-Trimethylphenyl): Their Structures and Reaction Products. *Eur. J. Inorg. Chem.* **1998** (3), 361 – 366.

- (11) Hettstedt, C.; Unglert, M.; Mayer, R. J.; Frank, A.; Karaghiosoff, K. Methoxyphenyl Substituted Bis(picoly)phosphines and Phosphine Oxides. *Eur. J. Inorg. Chem.* **2016**, (9), 1405 – 1414.
- (12) (a) Wissmann, H.; Kleiner, H.-J. New Peptide Synthesis. *Angew. Chem. Int. Ed. Engl.* **1980**, 19 (2), 133 – 134. (b) Basavaprabhu, T. M.; Vishwanatha, N. R. P.; Sureshbabu, V. V. Propanephosphonic Acid Anhydride (T3P®) - A Benign Reagent for Diverse Applications Inclusive of Large-Scale Synthesis. *Synthesis* **2013**, 45 (12), 1569 – 1601. (c) Pizova, H.; Bobal, P. An optimized and scalable synthesis of propylphosphonic anhydride for general use. *Tetrahedron Lett.* **2015**, 56 (15), 2014 – 2017.
- (13) (a) Langheld, K. Über Metaphosphorsäure-äthylester und dessen Anwendung in der organischen Chemie. *Chem. Ber.* **1910**, 43 (2), 1857 – 1860. (b) Burkhardt, G.; Klein, M. P.; Calvin, M. The Structure of the So-Called "Ethyl Metaphosphate" (Langheld Ester). *J. Am. Chem. Soc.* **1965**, 87 (3), 591 – 596. (c) van Wazer, J. R.; Norval, S. The Molecular Constitution of Methyl and Ethyl Polyphosphate and the Langheld Esters. *J. Am. Chem. Soc.* **1966**, 88 (19), 4415 – 4423. (d) Ogata, N.; Sanui, K.; Harada, M.; Direct polycondensation of nylon salts by polyphosphates and imidazole. *J. Polym. Sci. Part A* **1979**, 17 (8), 2401 – 2411. (e) Dixon, L. A. *Polyphosphate Ester*, in: *e-EROS Encyclopedia of Reagents for Organic Synthesis*, Wiley-VCH: Chichester, UK, 2001. (f) López, S. E.; Restrepo, J.; Salazar, J. Polyphosphoric Acid Trimethylsilylester: A useful Reagent for Organic Synthesis. *J. Chem. Res.* **2007**, 497 – 502.
- (14) For the ROP of phosphorus-containing heterocycles, see: (a) H. R. Allcock, H. R.; Kugel, R. L.; Valan, K. J. Phosphonitrilic Compounds. VI. High Molecular Weight Poly(alkoxy- and aryloxyphosphazenes). *Inorg. Chem.*, **1966**, 5 (10), 1709 – 1715. (b) Peckham, T. J.; Massey, J. A.; Honeyman, C. H.; Manners, I. Living Anionic Polymerization of Phosphorus-Bridged [1]Ferrocenophanes: Synthesis and Characterization of Well-Defined Poly(ferrocenylphosphine) Homopolymers and Block Copolymers. *Macromolecules* **1999**, 32, 2830 – 2837. (c) Sarbisheh, E. K.; Flores, J. E.; Zhu, J.; Müller, J. Insight into the Thermal Ring-Opening Polymerization of Phospha[1]ferrocenophanes. *Chem. Eur. J.* **2016**, 22 (47), 16838 - 16849.
- (15) The compounds **1Ph₃** and **1Mes₃** were reported in the literature (see refs. [8a,b,c,e,f,g,h] and [10]), but their characterization was either incomplete or ambiguous.
- (16) (a) Durif, A. *Crystal Chemistry of Condensed Phosphates*, Springer Science+Business Media: New York, 1995. (b) Haiduc, I. In: *Encyclopedia of Inorganic Chemistry*; R. B. King, Ed., John Wiley & Sons: Chichester, UK, 2006.
- (17) The presence of small amounts of cyclic monomer after thermal ROP potentially leads to lower T_g values due to plasticization. For a general discussion of the influence of bulky substituents on T_g values of polymers, see: Odian, G. *Principles of Polymerization*, 4th ed., John Wiley & Sons: Hoboken, New Jersey, 2004.
- (18) Hatada, K.; Kitayama, T. *NMR Spectroscopy of Polymers*, Springer-Verlag: Berlin, Heidelberg, 2004.
- (19) (a) Teichmann, H.; Schulz, J.; Wilbrandt, D. Ein neuer einfacher Zugang ZII Pyridinium-phosphor-betainen. *Z. Chem.* **1990**, 30, 18 – 19. (b) Teichmann, H.; Wilbrandt, D.; Schulz, J. Phosphorylations with ROP(X)C₁₂: A New Mechanistic Pathway. *Phosphorus, Sulfur, and Silicon* **1990**, 49/50, 251 – 254.
- (20) (a) Regitz, M.; Maas, G. *Short-lived phosphorus(V) compounds having coordination number 3*. In: *Organic Chemistry. Top. Curr. Chem.*; Springer: Berlin, Heidelberg, 1981, 97, 71 – 120. (b) Westheimer, F. H. Monomeric metaphosphates. *Chem. Rev.* **1981**, 81 (4), 313 – 326. (c) Menye-Biyogo, R.; Delpech, F.; Castel, A.; Gornitzka, H.; Rivièrè, P.; Ruthenium-stabilized low-coordinate phosphorus atoms: structural evidence for monomeric metaphosphate. *Angew. Chem. Int. Ed.* **2003**, 42 (45), 5610 – 5612. (d) Mardyukov, A.; Niedek, D.; Schreiner, P. R. Preparation and Characterization of Parent Phenylphosphinidene and Its Oxidation to Phenyldioxophosphorane: The Elusive Phosphorus Analogue of Nitrobenzene. *J. Am. Chem. Soc.* **2017**, 139 (14), 5019 – 5022. (e) Bockfeld, D.; Bannenberg, T.; Jones, P. G.; Tamm, M. N-Heterocyclic Carbene Adducts of Phenyldioxophosphorane and Its Heavier Sulfur and Selenium Analogues. *Eur. J. Inorg. Chem.* **2017** (28), 3452 – 3458.
- (21) For work on donor-stabilized P(V) cations see, for example: Weigand, J. J.; Burford, N.; Mahnke, D.; Decken, A. Coordination Complexes of the Dimethylthiophosphonium Cation and Ligand Exchange. *Inorg. Chem.* **2007**, 46 (19), 7689 – 7691.
- (22) Zhu, J.-B.; Watson, E. M.; Tang, J.; Chen, E. Y.-X. A synthetic polymer system with repeatable chemical recyclability. *Science* **2018**, 360 (6387), 398 – 403.

TOC Graphic

