

# Ionic Liquid Based Electrolytes for Dye Sensitized Solar Cells

Andreas Hofmann\*, Felix Kiliani\*, Thomas Hanemann\*,\*\*

\* Karlsruhe Institut für Technologie, Institut für Angewandte Materialien - Werkstoffprozessertechnik, Hermann-von-Helmholtz-Platz 1, 76344 Eggenstein-Leopoldshafen, Germany  
Andreas Hofmann, e-mail: [andreas.hofmann2@kit.edu](mailto:andreas.hofmann2@kit.edu), Tel. +49 (0)721-608-25920  
\*\* Universität Freiburg, Institut für Mikrosystemtechnik (IMTEK), Freiburg, Germany

## Summary

- New ionic liquid based electrolyte possesses better performance than commercial ionic liquid based one at 25°C
- Improved stability up to 600 h at 65°C demonstrated

## Motivation

Since the invention of the dye sensitized solar cell almost 20 years ago this very promising energy harvester suffers from the limited efficiencies around 12% considering lab-size cells and reduced long-term stability under environmental conditions. Especially the **presence of volatile electrolyte components** with considerable vapour pressure under operation conditions (20-80°C) during a sunny day can cause a pronounced negative impact on the device sealing stability. One possible solution to overcome the electrolyte volatility is the use of iodide-based **ionic liquids (IL)** in combination with low vapour pressure solvents like **propylene carbonate (PC)**. This mixture enables a **low electrolyte viscosity** which ensures a high ionic conductivity according to the Walden rule established in electrolyte development for lithium-ion-batteries.

## General electrolyte features

- High ionic conductivity
- Low viscosity (mPas-range)
- Good solubility for iodine enabling  $I_3^-$  complex
- Low vapour pressure under operation conditions (20-80°C)
- Long-term stability at 80°C


### Walden Rule

$$\lambda(T) \eta(T) = \text{const}$$

## Materials and Methods

### Reference electrolyte: IoLiLyte SP-163:

- 0.60 M 1-Butylmethylimidazolium iodide (BMIM-I)
- 0.03 M Iodine




- Additives:
  - 0.10 M Guanidinium thiocyanate
  - 0.50 M 4-*tert*-butylpyridine
- Solvent mixture: 85% Acetonitrile (bp.: 81°C)  
15% Valeronitrile (bp.: 139°C)

### New electrolytes:


- 1-Butylmethylimidazolium iodide (**BMIM-I**) or 1-Propylmethylimidazolium iodide (**PMIM-I**)

- Iodine
- Additives: same as in reference
- Solvent: Propylene carbonate **PC** (bp.: 240°C)




### Investigations on:

- Viscosity
- Ionic conductivity
- Functional tests in commercial DSSC at different temperatures




## Results

### Electrolyte viscosity

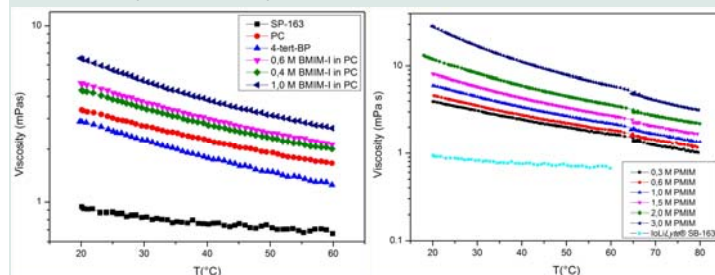


- All components possess a higher viscosity than the reference electrolyte, especially at low temperatures
- Increasing ionic liquid content increases viscosity

### Electrolyte conductivity

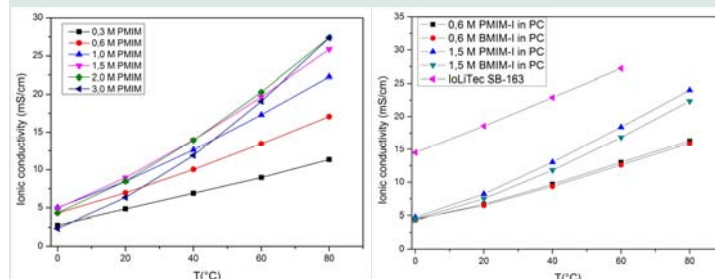

- Increasing ionic liquid content increases conductivity
- PMIM-I induces higher conductivity than BMIM-I
- Conductivity at 80°C comparable to reference at 60°C

### Functional tests in commercial DSSC @Solaronix

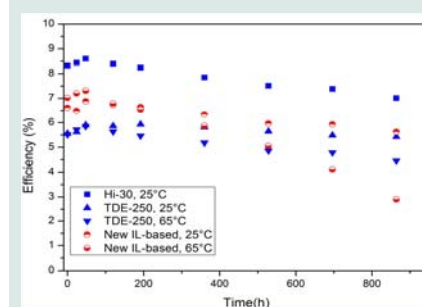

- Comparison with two commercial electrolytes, both from Solaronix
  - HI-30 (acetonitrile based)
  - TDE-250 (IL-based)
- Measurement temp.: 25°C, 65°C

- 25°C and 65°C: New electrolyte exhibits higher efficiency than commercial IL-based system
- 65°C: New electrolyte shows reduced long-term stability > 600h

## Conclusions

- Viscosity and ionic conductivity increases with IL content
- Molecular structure of the IL influences conductivity
- **New electrolyte composition with improved DSSC efficiencies even at elevated temperatures found**

## Acknowledgements

We gratefully acknowledge financial support from the Baden-Württemberg Stiftung and A. Hinsch (ISE) for fruitful discussions.