



You have downloaded a document from
RE-BUŚ
repository of the University of Silesia in Katowice

Title: Spin crossover in $\text{Cu}_x\text{Co}_y\text{Cr}_z\text{Se}_4$ semiconductors

Author: Ewa Maciążek, Tadeusz Groń, A.W. Pacyna, T. Mydlarz, Beata Zawisza, Józef Krok-Kowalski

Citation style: Maciążek Ewa, Groń Tadeusz, Pacyna A.W., Mydlarz T., Zawisza Beata, Krok-Kowalski Józef. (2011). Spin crossover in $\text{Cu}_x\text{Co}_y\text{Cr}_z\text{Se}_4$ semiconductors. "Acta Physica Polonica A" (Vol. 119, nr 5 (2011), s. 711-713).



Uznanie autorstwa - Użycie niekomercyjne - Bez utworów zależnych Polska - Licencja ta zezwala na rozpowszechnianie, przedstawianie i wykonywanie utworu jedynie w celach niekomercyjnych oraz pod warunkiem zachowania go w oryginalnej postaci (nie tworzenia utworów zależnych).



Spin Crossover in $\text{Cu}_x\text{Co}_y\text{Cr}_z\text{Se}_4$ Semiconductors

E. MACIĄŻEK^a, T. GROŃ^b, A.W. PACYNA^c, T. MYDLARZ^d, B. ZAWISZA^a
AND J. KROK-KOWALSKI^b

^aInstitute of Chemistry, University of Silesia, Szkolna 9, 40-006 Katowice, Poland

^bInstitute of Physics, University of Silesia, Uniwersytecka 4, 40-007 Katowice, Poland

^cThe Henryk Niewodniczański Institute of Nuclear Physics, Polish Academy of Sciences

E. Radzikowskiego 152, 31-342 Kraków, Poland

^dInternational Laboratory of High Magnetic Fields and Low Temperatures

Gajowicka 95, 53-529 Wrocław, Poland

Magnetization and magnetic susceptibility measured in the zero-field-cooled mode were used to study the spin crossover transition in polycrystalline $\text{Cu}_x\text{Co}_y\text{Cr}_z\text{Se}_4$ compounds. With increasing Co content a transition from ferromagnetic order via ferrimagnetic one to antiferromagnetic-like behaviour was observed. This transition is accompanied with a lowering symmetry from cubic to monoclinic and for the latter the spin crossover phenomenon occurs. These results are considered in a framework of the ligand-field split and the spin-orbit coupling.

PACS: 75.30.Wx, 75.50.Dd, 75.50.Ee

1. Introduction

Structural and electrical investigations carried out on the polycrystalline $\text{Cu}_{1-x}\text{Co}_x\text{Cr}_2\text{Se}_4$ compounds in the compositional range $0.0 \leq x \leq 1.0$ revealed semiconducting properties and a transformation from cubic spinel-type to monoclinic Cr_3S_4 -type structure above $x = 0.4$ [1]. Recently, the X-ray diffraction studies on the polycrystalline $\text{Cu}_{1-x}\text{Co}_x\text{Cr}_2\text{Se}_4$ system ($x = 0.0, 0.2, 0.4, 0.6, 0.8, 1.0$) proved the existence of the cubic spinel-type structure for $x \leq 0.2$ and the monoclinic Cr_3S_4 -type one for $x \geq 0.8$ [2]. CoCr_2Se_4 undergoes an order-disorder phase transition above 750 °C [2] and has a sharp peak in its susceptibility at 199 K suggesting antiferromagnetic (AFM) behaviour [3]. Electrical and magnetic studies carried out on single-crystalline non-stoichiometric $\text{Cu}_x\text{Co}_y\text{Cr}_z\text{Se}_4$ spinels showed ferromagnetic (FM) ordering and p -type metallic conductivity for $y = 0.06, 0.1$ and 0.11 as well as a ferrimagnetic behaviour and n -type electrical conductivity for $y = 0.23$ [4].

It is well known in literature that compounds containing transition metals with d^4 , d^5 , d^6 , and d^7 electron configurations usually are capable of forming either spin-free (high-spin, HS) or spin-paired (low-spin, LS) ground states, depending on the strength of the cubic ligand field, Δ , relative to the mean spin-pairing energy, \bar{P} [5]. Then, their magnetism follows the Curie-Weiss law. However, when $|\Delta - \bar{P}|$ becomes comparable to thermal energy, kT , both spin states HS and LS may be populated and cross over in thermal equilibrium. This

phenomenon is commonly known as spin crossover for that the Curie-Weiss law is not valid. So, the easiest way of following the spin conversion as a function of temperature is the measurement of the magnetic susceptibility [5].

It seems thus natural to expect a spin transition in the polycrystalline $\text{Cu}_x\text{Co}_y\text{Cr}_z\text{Se}_4$ system for higher Co content.

2. Experimental details

Powder samples of the $\text{Cu}_x\text{Co}_y\text{Cr}_z\text{Se}_4$ system were obtained as ceramics using a preparation method which is described in detail elsewhere [1]. Chemical composition of the compounds was determined by energy-dispersive X-ray fluorescence (EDXRF) spectrometry. The samples were excited by the Rh target X-ray tube (XTF 5011/75, Oxford Instruments, USA). The X-ray spectra of the samples were collected by thermoelectrically cooled Si-PIN detector (XR-100CR Amptek, Bedford, MA, USA) of 145 eV resolution at 5.9 keV. The EDXRF spectrometer is described in detail in Ref. [6]. The quantitative EDXRF analysis of samples was performed by fundamental parameters method based on the Sherman equation. The compositions studied in this paper are the same as reported in Ref. [1].

Magnetization and magnetic susceptibility were measured in the zero-field-cooled mode using a vibrating sample magnetometer with a step motor [7] at 4.2 K and in applied external magnetic fields up to 150 kOe and a Faraday type Cahn RG automatic electrobalance in the temperature range 4.2–400 K and at 800 Oe, respectively.

3. Results and discussion

Figure 1 shows the magnetization isotherms measured at 4.2 K. The spinel samples with low Co content up to $y = 0.25$ reach full saturation of $4.65 \mu_B/\text{f.u.}$ for $\text{Cu}_{0.93}\text{Co}_{0.15}\text{Cr}_{1.64}\text{Se}_4$ and of $4.35 \mu_B/\text{f.u.}$ for $\text{Cu}_{0.75}\text{Co}_{0.25}\text{Cr}_2\text{Se}_4$ at 140 kOe close to the theoretical value of $5 \mu_B$ per molecule for $\text{Cu}[\text{Cr}^{3+}\text{Cr}^{4+}]\text{Se}_4$ spinel [8]. In these spinels the magnetic moments order ferromagnetically and the Curie temperature T_C decreases from 390 K for $y = 0.15$ to 377 K for $y = 0.25$ (see Fig. 2). A pronounced decrease of saturation moment with increasing Co content suggests the LS state of the Co^{2+} ions, tetrahedrally coordinated, with spin $S = 1/2$ in the t_2 orbital (see Fig. 3), because the Cr^{3+} ions, octahedrally coordinated, with spin $S = 3/2$ in the t_{2g} orbital are always in the HS state. Eventually, a FM and AFM coupling between Co^{2+} and Cr^{3+} magnetic moments may occur, too.

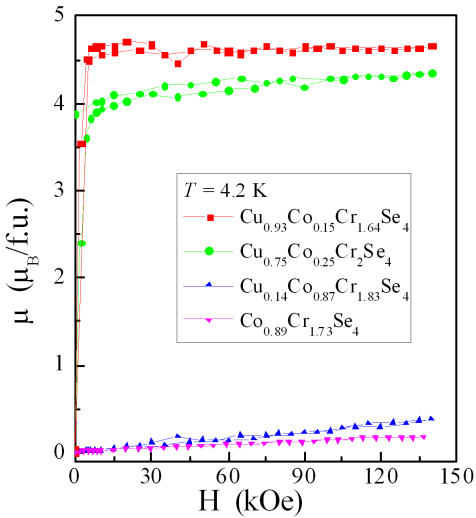


Fig. 1. Magnetic moment μ vs. magnetic field H for the $\text{Cu}_x\text{Co}_y\text{Cr}_z\text{Se}_4$ system at 4.2 K.

The monoclinic Cr_3S_4 -type structures with high Co content above $y = 0.8$ show a dramatically strong drop of magnetic moment up to $0.18 \mu_B/\text{f.u.}$ at 137 kOe for $y = 0.89$. They do not reveal both saturation and spontaneous magnetization (Fig. 1). The temperature dependence of magnetic susceptibility, $\chi_\sigma(T)$, depicted in Fig. 4 reveals ferrimagnetic order with $T_C = 133$ K and without a Curie–Weiss behavior in the temperature range 4.2–400 K for $\text{Cu}_{0.14}\text{Co}_{0.87}\text{Cr}_{1.83}\text{Se}_4$. Above T_C the $\chi_\sigma(T)$ curve shows minimum at $T_1 = 168$ K and maximum at $T_2 = 255$ K characteristic for a spin crossover transition. The non-linear dependence of $1/\chi_\sigma(T)$ at 800 Oe maybe a consequence of the strong dependence of the effective magnetic moment with temperature, which is experimentally observed in the compounds where the spin crossover phenomenon occurs [5]. Similar behavior is observed for $\text{Co}_{0.89}\text{Cr}_{1.73}\text{Se}_4$ depicted in Fig. 5. The temperature dependence of magnetic susceptibility, $\chi_\sigma(T)$,

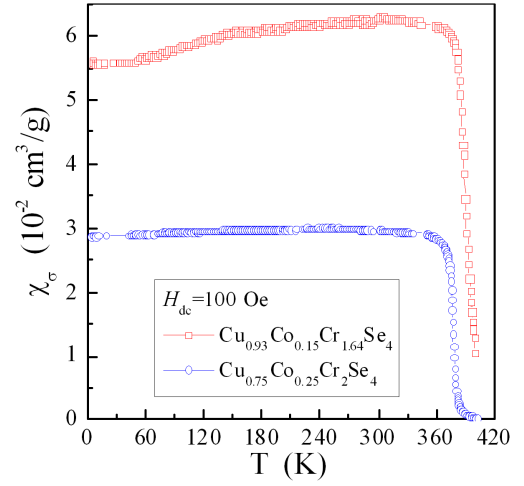


Fig. 2. The ZFC dc mass susceptibility χ_σ vs. temperature T for polycrystalline $\text{Cu}_{0.93}\text{Co}_{0.15}\text{Cr}_{1.64}\text{Se}_4$ and $\text{Cu}_{0.75}\text{Co}_{0.25}\text{Cr}_2\text{Se}_4$ ferromagnetic spinels recorded at $H_{dc} = 100$ Oe.

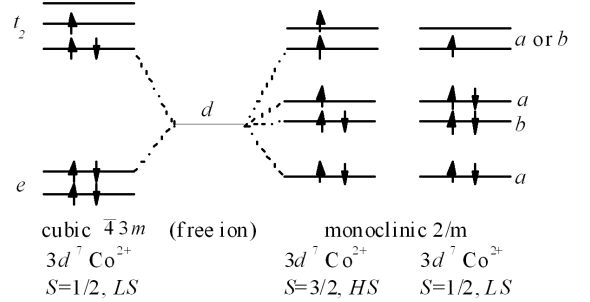


Fig. 3. The ligand–field split components showing the symmetry-lowered phase transitions in $\text{Cu}_x\text{Co}_y\text{Cr}_z\text{Se}_4$ for high Co content ($y \geq 0.8$).

reveals antiferromagnetic-like behaviour with $T_N = 6$ K and without a Curie–Weiss behavior in the temperature range 4.2–400 K. Above T_N the $\chi_\sigma(T)$ curve shows minimum at $T_1 = 118$ K and maximum at $T_2 = 286$ K.

These results seem to be connected with thermally induced LS–HS transitions in the $\text{Cu}_x\text{Co}_y\text{Cr}_z\text{Se}_4$ system for $y \geq 0.8$. For the Co^{2+} ion with $3d^7$ electronic configurations the multiplet width should be comparable to kT because the temperature dependence of magnetic susceptibility, described by the Curie–Weiss law is not obeyed and the magnetic moment is strongly lowered. Only a slight decrease in magnetic moment could be related to the magnetic moment of Co, which would be perpendicular to the magnetic moment of Cr. It takes into the effect that the longitudinal component of the moment of the Co ions becomes zero and only the Cr moment remains visible in the saturation state, as it was found for MnCr_2S_4 [9] and $\text{Mn}[\text{Cr}_{0.5}\text{Ga}_{1.5}]\text{S}_4$ [10].

At $T_2 = 255$ K for $\text{Cu}_{0.14}\text{Co}_{0.87}\text{Cr}_{1.83}\text{Se}_4$ and at $T_2 = 286$ K for $\text{Co}_{0.89}\text{Cr}_{1.73}\text{Se}_4$ thermal energy $kT_2 =$

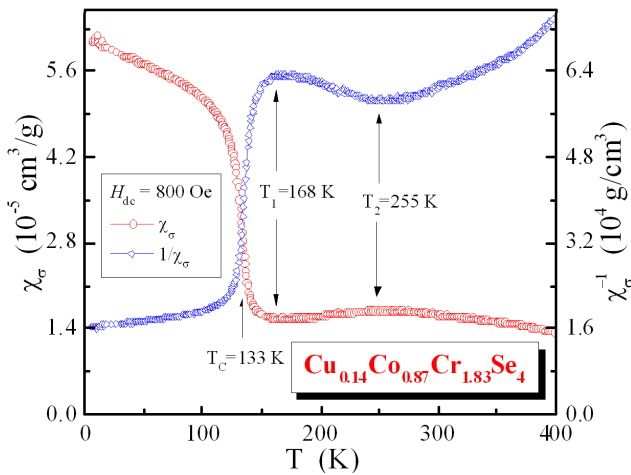


Fig. 4. The ZFC dc mass susceptibility χ_σ and $1/\chi_\sigma$ vs. temperature T for $\text{Cu}_{0.14}\text{Co}_{0.87}\text{Cr}_{1.83}\text{Se}_4$ recorded at $H_{\text{dc}} = 800$ Oe. T_C is the Curie temperature and T_1 and T_2 are temperatures characteristic for spin crossover transition.

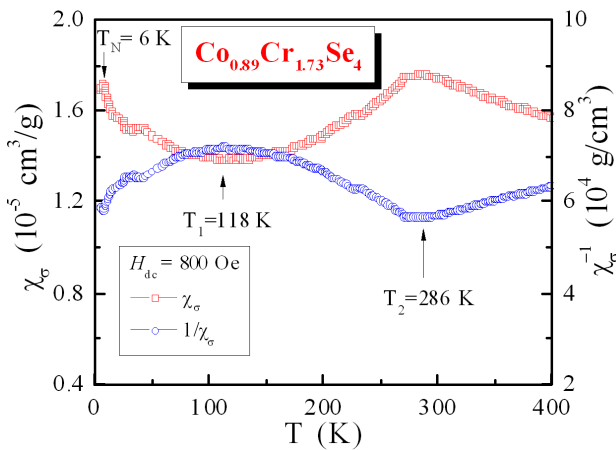


Fig. 5. The ZFC dc mass susceptibility χ_σ and $1/\chi_\sigma$ vs. temperature T for $\text{Co}_{0.89}\text{Cr}_{1.73}\text{Se}_4$ recorded at $H_{\text{dc}} = 800$ Oe. T_N is the Néel temperature and T_1 and T_2 are temperatures characteristic for spin crossover transition.

0.0213 eV and 0.0238 eV, respectively. These energies are over 20 times smaller in comparison with the tetrahedral orbital splitting of Co^{2+} ion, $\Delta_t = 0.5514$ eV. A lowering symmetry, displayed in Fig. 3, from cubic ($43m$) to monoclinic ($2/m$) [11] makes easier the spin crossover transitions as the orbital splitting is lowered giving the value $|\Delta - \bar{P}|$ comparable to kT . We suggest that the broad humps on the $\chi_\sigma(T)$ curves above the ordering temperature may correspond to the ${}^4T \leftrightarrow {}^2E$ spin crossover in cobalt(II).

4. Conclusions

We have observed an anomalous behaviour of the temperature dependence of magnetic susceptibility and magnetization of the $\text{Cu}_x\text{Co}_y\text{Cr}_z\text{Se}_4$ compounds for high cobalt content ($y \geq 0.8$) in comparison with low cobalt one ($y \leq 0.25$). The high content of the Co-ions weakens the FM long-range interactions. Therefore, with increasing Co content a transition from ferromagnetic order via ferrimagnetic one to antiferromagnetic-like behaviour is observed. This transition is accompanied with a lowering symmetry from cubic ($\bar{4}3m$) to monoclinic ($2/m$) and for the latter the spin crossover phenomenon occurs. The broad humps at 255 K for $\text{Cu}_{0.14}\text{Co}_{0.87}\text{Cr}_{1.83}\text{Se}_4$ and at 286 K for $\text{Co}_{0.89}\text{Cr}_{1.73}\text{Se}_4$ on the $\chi_\sigma(T)$ curves above the ordering temperature are characteristic for the HS–LS transitions. The nature of these transitions seems to be connected with the spin–orbit coupling giving the multiplet width comparable to thermal energy.

Acknowledgments

This work is partly founded from science grant No. N N204 289134.

References

- [1] E. Maciążek, A. Molak, T. Goryczka, *J. Alloys Comp.* **441**, 222 (2007).
- [2] V. Svitlyk, Y. Mozharivskiy, *Inorg. Chem.* **48**, 5296 (2009).
- [3] B.L. Morris, P. Russo, A. Wold, *J. Phys. Chem. Solids* **31**, 635 (1970).
- [4] T. Groń, E. Maciążek, J. Heimann, J. Kusz, I. Okońska-Kozłowska, K. Bärner, and Ch. Kleeberg, *Physica B* **254**, 84 (1998).
- [5] P. Gülich, *Spin Crossover in Iron(II)–Complexes in Structure & Bonding*, Vol. 44, Springer, Berlin 1981.
- [6] R. Sitko, B. Zawisza, E. Malicka, *Spectrochim. Acta B* **64**, 436 (2009).
- [7] V.I. Nizhankovskii, L.B. Lugansky, *Meas. Sci. Technol.* **18**, 1533 (2007).
- [8] O. Yamashita, Y. Yamaguchi, I. Nakatani, H. Watanabe, K. Masumoto, *J. Phys. Soc. Jpn.* **46**, 1145 (1979).
- [9] V. Tsurkan, M. Mücksch, V. Fritsch, J. Hemberger, M. Klemm, S. Klimm, S. Körner, H.-A. Krug, D. von Nidda, E.-W. Samusi, A. Scheidt, S. Loidl, R. Horn, Tidecks, *Phys. Rev. B* **68**, 134434 (2003).
- [10] T. Groń, J. Krok-Kowalski, A.W. Pacyna, T. Mydlarz, *J. Phys. Chem. Solids* **70**, 900 (2009).
- [11] C.F. van Bruggen, *Ann. Chim. Fr.* **7**, 171 (1982).