



BIROn - Birkbeck Institutional Research Online

Ruiz-Perez, L. and Hurley, C. and Tomas, Salvador and Battaglia, G. (2018) Separating extreme pH gradients using Amphiphilic Copolymer Membranes. *ChemPhysChem* 19 (16), pp. 1987-1989. ISSN 1439-7641.

Downloaded from: <http://eprints.bbk.ac.uk/23029/>

Usage Guidelines:

Please refer to usage guidelines at <http://eprints.bbk.ac.uk/policies.html> or alternatively contact lib-eprints@bbk.ac.uk.

Separating extreme pH gradients using amphiphilic copolymer membranes

Lorena Ruiz-Pérez*^[a] Claire Hurley,^[c] Salvador Tomas,^[d] and Giuseppe Battaglia*^[a]

Abstract:

Polymeric vesicles, also called polymersomes, are highly efficient biomimetic systems. They can generate compartmentalized volumes at the nanoscale supported by synthetic amphiphilic membranes that closely mimic their biological counterparts. Membrane permeability and the ability to separate extreme pH gradients is a crucial condition a successful biomimetic system must meet. We show polymersomes formed by polybutadiene-*b*-polyethylene oxide (PBd-*b*-PEO) amphiphilic block copolymers engineer robust and stable membranes that are able to sustain pH gradients of 10 for a minimum of 8 days. Cells endo-lysosomal compartments separate gradients between 3 and 1, while we generated a pH gradient of three folds as great. This feature clearly is of great importance for applications as nanoreactors and drug delivery systems where separating different aqueous volumes at nanoscale level is an essential requirement.

Amphiphilic block copolymers can self-assemble in water into well-ordered nanostructures.¹ These ordered nanostructures can be tuned over a wide variety of morphologies, ranging from discrete micelles and vesicles to continuous network structures.²

In particular, polymeric vesicles, also called polymersomes³ have been gaining more attention lately as they reassemble those arrangements generated by biological membranes in cellular compartmentation.^{4, 5} The capability to generate compartmentalized volumes at the nanoscale is one of the essential motifs used by cells in synthesizing biomolecules and performing the biochemical reactions required for their function.⁶ This motif has been recently mimicked using block copolymer vesicles as nanoreactors.⁷ In addition, polymeric vesicles offer

exceptional possibilities to devise nanocontainers with exciting applications in biomedicine, electronics, cosmetics and food science.⁷⁻¹¹

It has been reported that polymersomes can retain encapsulated molecules over a period of days to weeks.¹² Permeation through the vesicle membrane is the main effect that causes the loss of the encapsulated molecules. Consequently, evaluating the permeability of specific molecules is one of the most crucial measurements to fully characterize amphiphilic membranes. Water and ion permeabilities have been widely studied by different techniques such as membrane potential measurements,¹³ fluorescence quenching methods,¹⁴ micropipette aspiration techniques,¹⁵ and anti-Stokes Raman scattering.¹⁶ The permeability of more complex and nonionic molecules has been measured by NMR techniques.¹⁷ However, molecular exchange through amphiphilic membranes always takes place in an aqueous environment, and the permeating molecules undergo no great variation in their individual properties.

Here we demonstrate the ability of a polymersome membrane to sustain large pH gradients for a minimum period of eight days. Polymersomes were loaded with a pH sensitive highly water soluble porphyrine dye in aqueous solution at pH 2 and immersed in an alkaline supernatant at pH 12 for a period of eight days. The polymersome lumen pH was monitored via fluorescence measurement of the encapsulated dye. These were supported by measuring the supernatant pH upon polymersome osmolysis by sodium chloride addition.

Experimental Section

Polybutadiene-*b*-polyethylene oxide (PBd-*b*-PEO) block copolymer was synthesized via anionic polymerization using standard high vacuum techniques¹⁸ and characterized via NMR and SEC. The PEO molar and weight fractions present in the block copolymer were found to be $f_m=0.27$ and $f_{wt}=0.23$. M_n PBd 5000; M_n PEO 1500. The synthesis is given in detail in the supporting information. Polymersomes have previously been formed in water from PBd-*b*-PEO of these characteristics.³ Hereafter the term BDE1 will be used to refer to PBd (5kg/mol)-*b*-PEO (1.5Kg/mol). In order to monitor the polymersomes lumen pH, we encapsulated a porphyrine dye within the polymersomes. The fluorescence spectrum of this dye is sensitive to pH changes. The experimental procedure for encapsulation of porphyrine into BDE1 vesicles, fluorescence spectra and calibration of porphyrine, and porphyrine synthesis are provided in the supporting information.

Fig. 1 shows the peak ratios obtained from excitation spectra of pH 2 porphyrine loaded BDE1 polymersomes when immersed in a pH 12 solution for a period of 8 days. An example of the excitation spectra of porphyrine loaded BDE1 polymer vesicles in solution at a fixed pH 12

[a] Dr. L. Ruiz-Pérez and Prof. G. Battaglia
Department of Chemistry
University College London
20 Gordon street, WC1H 0AJ London, UK
E-mail: l.ruiz-perez@ucl.ac.uk and g.battaglia@ucl.ac.uk

[b] Dr. P. Chambon
Department of Chemistry
University of Liverpool
Crown Street, Liverpool L69 7ZD, United Kingdom
E-mail: p.chambon@liverpool.ac.uk

[c] Dr. C. Hurley
Department of Physics
University of Warwick
Coventry West Midlands CV4 7AL, United Kingdom
E-mail: c.r.hurley@warwick.ac.uk

[d] Dr. S. Tomás
Department of Biological Sciences
Birbeck, University of London
Malet Street, Bloomsbury London WC1E 7HX, United Kingdom
Email: s.tomas@bbk.ac.uk

during the first and eighth day can be seen in Fig.3 (a) and (b) (black line).

Using eq. (S1), provided in the supporting information, with $A_1=7.16$, $A_2=21.27$, $x_0=4.92$ and $D=1.21$ the polymersomes internal pH from the peak ratio values could be calculated. The vesicles internal pH is also plotted in Fig.1. It can be observed that the pH inside the polymersomes remained constant, within the experimental error, at a value of pH~ 2 (Fig.1). Such phenomenon was observed for a period of eight days. Hence, since the supernatant pH was fixed at 12 the system under study efficiently preserved pH gradients ΔpH of an order of $\Delta pH \sim 10$.

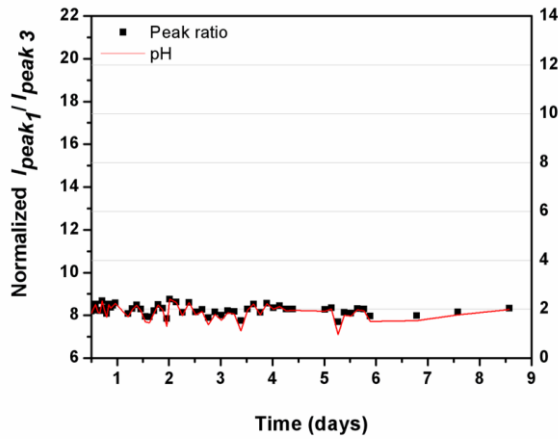


Figure 1. Peak ratios and polymersome internal pH obtained from excitation scans at a fixed emission $\lambda_{em}=720nm$ of pH 2 loaded porphyrine BDE1 polymersomes at pH 12 for a period of eight days.

Titration with NaCl solution was performed with the aim to match vesicle internal and supernatant pH. Approximately 60 mg/ml of NaCl were needed for the osmolysis of the polymersome membranes. Fig. 2 shows how the vesicle internal pH increased from approximately pH 2 to pH 7.7 upon addition of salt. The progressive raise in the polymersomes internal pH is caused by a progressive increase of the vesicle membrane's permeability to the supernatant.

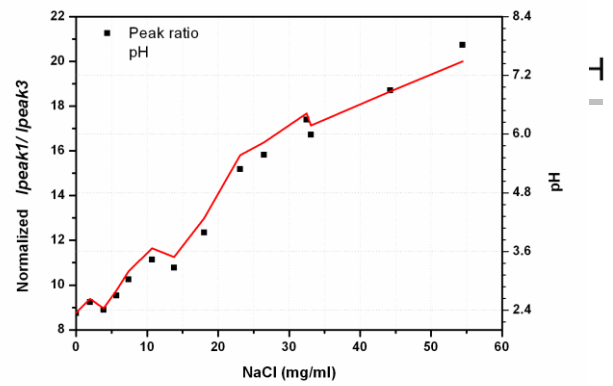


Figure 2. Peak ratios and polymersome internal pH obtained from excitation scans at a fixed emission $\lambda_{em}=720nm$ of pH 2 loaded porphyrine BDE1 polymersomes at pH 12 for a period of eight days.

60mg/ml of NaCl were added after the first and eighth day and excitation scans were taken, spectra are shown in Fig. 3 (a) and (b). After salt addition a significant increase in the *Peak 1* intensity at 416nm was observed for the first and eighth day respectively (Fig. 3 (a) and (b)). The peak ratios measured after salt addition for the first and eighth day could be translated into a polymersome internal pH of circa 7.6 according to the calibration graph and fit provided in the supporting information. Similarly, after salt addition the supernatant pH was measured during the first and eighth day respectively and was found to be approximately 7.8 for both cases. Indeed at this condition the polymersome internal pH, measured by fluorescence, matched the external pH. The decrease of this latter is due the release of the protons from the polymersomes lumen. This is further confirmed by the calculations provided in the supporting information that lead to equation (1):

$$pH_{final} = pH_{lumen} - \log\left(\frac{w_{copolymer}}{\rho_{PBD}}\right) \quad (1)$$

Where pH_{final} is the supernatant pH after osmolysis of the polymersomes, pH_{lumen} is the original pH within the polymersomes, $w_{copolymer}$ is the concentration of the copolymer, and ρ_{PBD} is the density of polybutadiene.

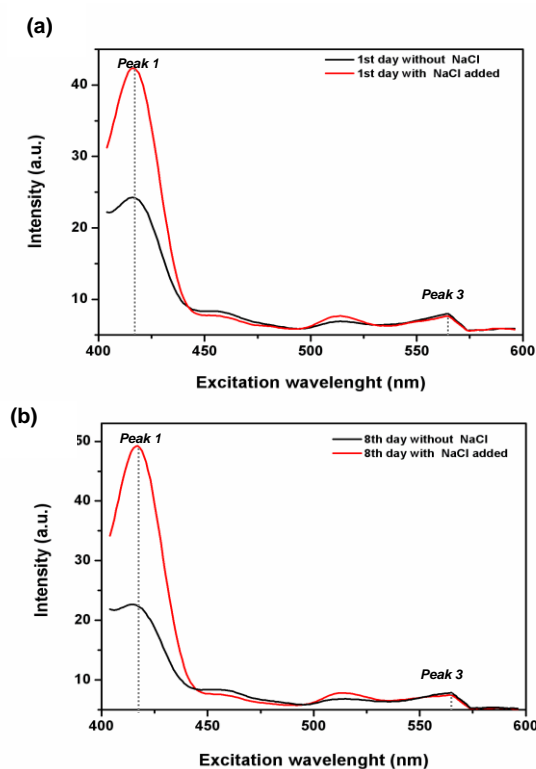


Figure 3 Excitation spectra at a fixed emission $\lambda_{em}=720\text{nm}$ for porphyrine loaded BDE1 vesicles at pH 12. The spectra before (black line) and after NaCl addition (red line) during the first and eighth day of measurements are shown in (a) and (b) respectively.

Separating extreme pH gradients is an essential condition used by cells within their endosomes and lysosomes to digest and metabolized any material that is internalised.⁶ Here we demonstrated an even larger pH gradient can be sustained by employing a more robust and stable membrane. Indeed endolysosomal compartments separate gradients between 3 and 1,⁶ while we generated a pH gradient of 10. This feature clearly augurs well for applications such as nanoreactors and any other where separating different aqueous volume at the nanoscale is of asset.

Acknowledgements

We thank Reckitt Benckiser for supporting this work.

Keywords: Polymersomes, pH gradient, Osmolysis, Polymeric membrane.

references

1. M. Massignani, H. Lomas and S. G. Battaglia, (New York, 2010), pp. 115–154, 229 pp., *Polymersomes: A synthetic biological approach to encapsulation and delivery*, Springer, New York, 2010.
2. G. Battaglia and A. J. Ryan, *Nature Materials*, 2005, **4**, 869-876.
3. B. M. Discher, Y. Y. Won, D. S. Ege, J. C.-M. Lee, F. S. Bates, D. E. Discher and D. A. Hammer, *Science*, 1999, **284**, 1143-1146.
4. G. Battaglia and A. J. Ryan, *J. Am. Chem. Soc.*, 2005, **127**, 8757-8764.
5. L. Ruiz-Perez, J. Madsen, E. Themistou, J. Gaitzsch, L. Messenger, S. P. Armes and G. Battaglia, *Polym. Chem.*, 2015, **6**, 2065-2068.
6. B. Alberts, A. Johnson, P. Walter, J. Lewis, M. Raff and K. Roberts, *Molecular Biology of the Cell*, Garland Science, Taylor & Francis Group, New York, USA, Fifth edn., 2008.
7. T. Smart, H. Lomas, M. Massignani, M. V. Flores-Merino, L. R. Perez and G. Battaglia, *Nanotoday*, 2008, **3**, 38-46.
8. C. LoPresti, H. Lomas, M. Massignani, T. Smart and G. Battaglia, *J. Mater. Chem.*, 2009, **19**, 3576 - 3590.
9. L. Ruiz-Pérez, L. Messenger, J. Gaitzsch, A. Joseph, L. Sutto, F. L. Gervasio and G. Battaglia, *Science Advances*, 2016, **2**, e1500948
10. J. Bain, L. Ruiz-Pérez, A. J. Kennerley, S. P. Muench, R. Thompson, G. Battaglia and S. S. Staniland, *Scientific Reports*, 2015, **5**.
11. A. Joseph, C. Contini, D. Cecchin, S. Nyberg, L. Ruiz-Perez, J. Gaitzsch1, G. Fullstone, X. Tian, J. Azizi, J. Preston, G. Volpe and G. Battaglia, *Science Advances*, 2017, **3**: e1700362, 1-12.
12. M. Antonietti and S. Forster, *Adv. Mater.*, 2003, **15**, 1323-1333.
13. J. M. Ward, *Plant Physiol.*, 1997, **114**, 1151-1159.
14. J. C. Mathai, G. D. Sprott and M. L. Zeidel, *J. Biol. Chem.*, 2001, **276**, 27266-27271.
15. K. Olbrich, W. Rawicz, D. Needham and E. Evans, *Biophys. J.*, 2009, **79**.
16. E. O. Potma, W. P. d. Boeij, P. J. M. V. Haastert and D. A. Wiersma, *Proc. Natl. Acad. Sci.*, 2001, **98**, 1577-1582.
17. A. Ruplecker, S. Forster, M. Zahres and C. Mayer, *J. Chem. Phys.*, 2004, **120**, 8740-8747.
18. N. Hadjichristidis, H. Iatrou, S. Pispas and M. Pitsikalis, *J. Polym. Sci., Part A: Polym. Chem.*, 2000, **38**, 3211-3234.

WILEY-VCH
