



This is a repository copy of *Protocol for tool wear measurement in micro-milling*.

White Rose Research Online URL for this paper:
<http://eprints.whiterose.ac.uk/139108/>

Version: Accepted Version

Article:

Alhadeff, L., Marshall, M., Curtis, D. et al. (1 more author) (2018) Protocol for tool wear measurement in micro-milling. *Wear*. ISSN 0043-1648

<https://doi.org/10.1016/j.wear.2018.11.018>

Article available under the terms of the CC-BY-NC-ND licence
(<https://creativecommons.org/licenses/by-nc-nd/4.0/>).

Reuse

This article is distributed under the terms of the Creative Commons Attribution-NonCommercial-NoDerivs (CC BY-NC-ND) licence. This licence only allows you to download this work and share it with others as long as you credit the authors, but you can't change the article in any way or use it commercially. More information and the full terms of the licence here: <https://creativecommons.org/licenses/>

Takedown

If you consider content in White Rose Research Online to be in breach of UK law, please notify us by emailing eprints@whiterose.ac.uk including the URL of the record and the reason for the withdrawal request.



eprints@whiterose.ac.uk
<https://eprints.whiterose.ac.uk/>

Protocol for Tool Wear Measurement in Micro-milling

L. Alhadeff, M.B. Marshall, D.T. Curtis, T. Slatter

Abstract

Micro-milling yields small accurate parts quickly for electromechanical, aerospace, and medical applications. Due to their small size, micro-tools wear quickly and unpredictably therefore tool wear is difficult to measure and is poorly understood, leading to excessive tool changes and reduced productivity. This paper, therefore, proposes a new protocol for micro-tool wear measurement to overcome these problems. A strict set of criteria as found in an ISO standard is impractical for micro-milling research. The method herein allows comparisons to be made across materials and situations and detailed are certain criteria that must be fulfilled to achieve this. To evaluate the protocol micro-tools were used to machine three materials: brass, titanium and Hastelloy; and wear curves produced. Using the described protocol, these wear curves can be analysed similarly to those for larger tools. Profile analysis of the slots machined provides valuable information about tool wear where direct measurement is impossible. This new protocol presents a novel method for analysing and reporting tool wear for micro-end-mills, allowing them to be compared under different machining conditions and/or milling different materials, something not afforded by existing machining standards. The information can then be transferred to industrial applications, extending tool life and improving process efficiency.

Nomenclature

x_{comp}	Total sliding distance
c_{inc}	Number of incomplete circles
c_{comp}	Number of complete circles
n_{rev}	Number of revolutions
D_{cap}	Engaged tool diameter
x_i	Sliding distance for incomplete circle
f_{cut}	Cutting frequency
n	Spindle speed
Z_c	Number of teeth
F_c	Cutting force
t	Cutting time
f_z	Feed rate
V_c	Cutting speed
F_c	Cutting Force
F_f	Feed Force
F_n	Normal Force

Table 1: Nomenclature used in this paper

1. Introduction

With increasing miniaturisation of engineered devices, micro-milling has emerged as one of the most popular processes for manufacturing small components because it is capable of rapidly producing

high integrity parts [1]. It is widely used in the medical and aerospace sectors, and in fields where miniaturised machine elements are commonplace such as watchmaking; optics and electronics; and micro-mould manufacturing [2]. Some of these areas only require softer materials such as copper and brass alloys to be machined. However, the medical and aerospace industries make use of materials such as titanium and high-performance superalloys. These are typically difficult-to-machine using macro-scale tools, but present further complexity in micro-milling as burring and crystal irregularities lead to fracture of the tools. Wear studies of micro tools are essential since it is very important to achieve a high-quality surface finish in many of these industries, either for aesthetic purposes or because the function of the components is impaired where surface finish is poor (such as where components have moving parts). Furthermore, worn tools cause increased burring [3, 4] which causes dramatic increases in cutting forces [5]. It is also very difficult to remove burrs from micro components using conventional methods [6]. The development of tool wear curves for different micro-milling situations enables the prediction of tool life, thus allowing the

tool to be used for the maximum possible length of time while maintaining a good surface finish. This maximises productivity and minimises costs. Historically, studies on micro tool wear have plotted tool wear against cutting distance or cutting time. Measurement of cutting distance moved by the tool relative to the workpiece or cutting time (i.e. when the tool is engaged) does not consider the different feed rates and speeds used for different materials, cannot be used to compare tool life of micro-tools between materials. As a result, the sliding distance for each tooth is used to measure tool wear against (as formally described in Section 3 of this paper). Furthermore, micro tool wear studies are inconsistent across the literature reviewed since different metrics are used to measure the wear of the tool: edge radius, flank wear and tool radius reduction being the most popular. To better standardise micro tool wear studies and understand the wear of micro tools, a protocol for measuring micro tools has been specified herein. The aim of the work presented here is therefore to propose a protocol for the measurement the wear of tools used in micro-milling that overcomes the issues of using existing methods that were primarily developed for macro-scale tools.

2. Background and State-of-the-Art

2.1. Micro-Milling

Micro-machining can be defined as the use of mechanical tools which have geometrically defined cutting edges to manufacture features which have dimensions in the order of micrometers ($1 \times 10^{-6} - 999 \times 10^{-6}\text{m}$) [7]. Micro-milling can be considered a subsection of micro-machining and, as with all micro-machining, produces very different results to conventional milling. There are several reasons for this [8], the first being that, relatively speaking, tools can appear blunt from the point of view of the workpiece material. If the depth of cut is much smaller than the cutting-edge radius, the tool is likely to rub along the surface of the workpiece and burnish it, rather than cutting it. Another problem is that due to their diameter, even fine-grained micro-milling cutters generally have low stiffness and poor resistance to fracture and so it can be difficult to study them for extended periods of time as the tools can fracture before significant wear has taken place (and even become lost). Finally, although on a macro-scale a polycrystalline structure

appears homogeneous, at the micro-scale grain sizes are relatively large when compared to the size of the tool and thus machining forces can be hugely variable. These effects combine to create an effect known as the size effect. This is defined as “the phenomenon whereby the reduction of the undeformed chip thickness to levels below the cutting edge radius, or grain size of the workpiece material begins to influence workpiece material deformation mechanisms, chip formation and flow” [9], that is to say that conventional macro-mechanics cannot be used to describe the system as simply reducing the scale does not produce a representative model.

2.2. Wear & Wear Measurement of Micro-Milling Tools

Typically, tool wear studies in milling follow the protocols laid out in standards such as ISO8688-1 and ISO8688-2 [10, 11]. These determine what parameters, materials and sizes of cut should be used and are generally used as benchmarking tests for the quality of tools. However, for micro-milling the ISO standards are not appropriate and thus adapted tests must be carried out [12]. There are some components which can be applied from the ISO standards. One such component is the terminology used to describe tool wear: this is useful as the wear of micro-tools can then be compared with that of macro tools.

These ISO standards also identify critical wear (i.e. the maximum acceptable wear of the tool). This is the point at which tool wear starts to increase rapidly towards the end of the tool life.

The wear of micro-tools is often much more poorly-described than that for macro-tools, and tool wear curves described using measurements of cutting edge radius and tool diameter do not typically yield traditional wear curves. Bahrudin et al. investigated flank wear behaviour of micro-milling tools of 0.5-1.5mm for titanium and H13 tool steel using a scanning electron microscope (SEM) against cutting time. Although they were able to produce wear curves for some of the tools investigated, this was not consistent across the entire range of tools and wear was only measured for one tooth of each tool. Since even a very small run-out has a very significant effect on tooth engagement for micro-tools, it is important to consider the wear on both teeth. They observed that surface finish was inconsistent over cutting time and inferred that this indicated an inconsistency in cut-

ting forces. They did not, however, measure the cutting forces directly.

Based on the issues with machining on a micro-scale especially regarding wear and fracture of tools, numerous studies have been carried out to investigate the effects of different parameters on micro tool wear. Increased cutting velocity increases tool wear [13] which is similar to conventional machining [14]. Moderate feed rates typically result in more stable forces which reduces tool wear (as opposed to very low or high feed rates), but only provided that they are not high enough to cause fracture [15]. Since the edge radius of micro-tools is comparable with the grain size of materials that are being machined, microstructure is important and materials with a higher elasticity result in more ploughing (rather than shearing) [16].

Chip formation differs from the conventional case: for a small feed per tooth, a chip is not seen with each pass of the tooth [8, 17], and instead burnishing or rubbing occurs. Premature tool failure is a common problem in micro-machining and this presents difficulties when measuring wear: whereas in conventional machining the tool fails as cutting edges break, with micro-tools the entire shaft often fractures [18] a result of excessive stress induced by the particular usage of the tool (for example, dulled or damaged cutting edges which cause forces to be higher than expected).

It is useful to consider cutting forces to better understand the point at which critical wear starts to take place. Particularly, total cutting force variation (magnitude) as the tool wears has not yet been considered in terms of tool wear studies. This is important because a high force magnitude indicates excessive vibrations which lead to an increased rate of tool wear. The first stages of the work carried out herein (described in Section 2.2) investigated the cutting forces as the tool wore, since in macro machining it is expected that cutting forces increase as tool wear increases [19].

To date, the most detailed curve produced using micro-tools used the surface finish of tools as a wear metric, citing that micro-tool wear is too difficult to measure [20]. The problem with this metric is that surface roughness is dependent on the sharpness of the tool, and whether rubbing or burnishing occurs. This means that if edge fractures occur at certain stages, or material builds up on the tool, the wear mechanisms taking place (e.g. degree of rubbing or shearing) can change. Thus, surface finish cannot be equated to tool wear.

Ucun et al. observed that the cutting edge radius does not give an adequate measure of tool wear, as over the lifetime of the micro-tool a new cutting edge is gradually formed, so that although cutting edge radius initially increases with tool radius decrease, it later decreases again [21]. They measured the diameter reduction for various tools under various cutting conditions but did not plot wear curves. The same method was used to measure tool wear on-line using a variety of sensors by Malekian et al. where similarly edge radius failed to describe the primary locations of wear for the tool, although it was a useful metric in terms of whether shearing or elastic deformation of the material occurs [22]. Measuring edge radius often shows increased wear with cutting distance but does not show similarities to conventional tool wear curves.

Flank wear, another possible metric for quantifying tool wear, was used by Aramcharoen et al. but as the primary aim of the study was to evaluate different coatings [23], no wear curve was produced and thus the usefulness of this measure in producing wear curves could not be assessed. Flank wear was also used as a measure of wear by Ding et al., along with edge radius, for micro-mills of 0.1mm in diameter, but no clear wear curve was seen (although wear clearly increased with cutting time) [24, 25], perhaps due to the extremely small size of the tools and a limited number of measurements. Elkaseer et al. modelled the effects of steel microstructure on tool wear but did not investigate the evolution of wear for the tools [16].

A more efficient approach was investigated by Filiz et al. whereby a reduction of channel width as a measurement of cutting edge radius [15] was used to investigate machinability of copper, which did not require the tools to be removed for measurement during machining. This is similar to measuring tool radius and does not give information about individual teeth or uneven tooth wear. However, a similar process is applicable to micro-milling, in the sense that channel profile can give an idea of tool wear and, providing an appropriate level of data is held relating tool wear to channel profile, can allow tools to be measured without removing them from the machine.

2.2.1. A Need for a Common Method

It has been noted by a number of authors that there is, compared with macro-milling, no established protocol for measurement of tools. This leads to a lack of existing data to compare studies with

which slows down the process of applying tools in an industrial context [26]. As previously described, flank wear and diameter are often used, but not always [27]. Wang et al. investigated cutting performance of cermet and coated WC end-mills in the machining of TC4 alloy, with tool wear being one of the metrics to assess the process [28]. They stated that because “in micro-milling, there are no unified methods to appraise tool wear”, width of micro-grooves was used as a measure of tool wear. This is clearly incomparable with measurement of the actual tool, and such a study could not be related to one that measures the flank and diameter of the tool. Clearly, the only way to achieve unification of these studies and compare them or combine them to benefit industry, is to define a standard protocol.

2.3. Preliminary Study

Initial trials were carried out on Brass (CuZn37), which plotted tool wear against cutting distance for AlTiN coated carbide tools. The results (Figure 1) showed that tool wear can be measured successfully using a SEM.

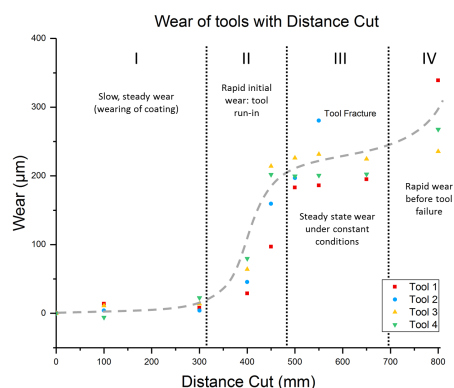


Figure 1: Wear of 0.5mm micro-end-mills cutting CuZn38. The wear is given in terms of total reduction in diameter.

The wear for the four tools can be examined in terms of zones. Initially, in Zone I (up to a cutting distance of 300mm), very little wear was observed, and it is likely that this is the distance at which the AlTiN coating was removed. The coating, which is widely-used in high-performance applications such as micro-milling [29], and survived well before this point because brass is a very soft, easy-to-machine material [15] that is well-suited to AlTiN coatings [30]. After this point, the tool wear shows the characteristic wear curve typically seen for macro-tools

[31]. This is not often seen in previous micro-mill wear studies due to under-sampling of the tool wear or inadequate measuring techniques. In Zone II, rapid wear of the tools was seen as the cutting edge was initially blunted from a very sharp point. During section III a relatively slow, steady increase in wear was seen. Finally, Zone IV showed an increase in wear as the tools became severely worn. Fracture of tools occurred in this stage (with the exception of one tool, which broke in Zone III). Using a SEM with the tool in the two orientations shown in Figure 2, it is possible to measure the tool wear using the protocol detailed in Section 3 (where the terminology used relates to the ISO standards). In reality, often more than one type of wear is seen (see Figure 3). It is important to note that these two angles are the minimum requirement to identify all the wear types described.

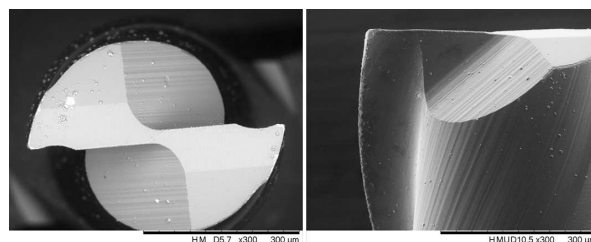


Figure 2: The two orientations in which tools were measured




Figure 3: An example of multiple types of wear occurring - here, VB and KT2 can be seen in purple, while CH and KT1 are seen in red, and VB is seen in blue.

The preliminary study and the difficulties encountered when measuring micro tool wear using only outside diameter highlighted the need to achieve a standardised protocol that would provide more information than simply current tool radius.

3. Development of Protocol

3.1. Purpose

In the light of the lack of work on standardising tool wear studies for micro-milling, it was decided

that a protocol for measuring tools should be established to aid future studies of the wear progression and underlying mechanisms in micro-milling in both conventional engineering materials such as steel, and in aerospace metals (such as titanium and nickel alloys). It is clear both from preliminary experimentation by the authors and a review of literature that the wear of micro tools can be directly observed using optical methods (SEM) to give a classical tool wear curve. However, aside from inconsistencies between studies and the need for standardisation if comparison between studies is to take place, there are some serious problems with methods such as measurement of tool radius, not least the fact that it does not consider uneven wear of the teeth: for example, were catastrophic wear to take place on one tooth while the other tooth remained unworn, the measurement would be the same as if the two teeth were worn moderately (see Figure 3). As a result of the preliminary work described in Section 2.3, it was established that a more precise measurement method for the wear of micro-tools is required to be developed and tested, with the intention that machining parameters and materials to cut should be flexible, but standard reporting methods should be used to allow comparison between studies.

Type of Wear	Code	Description	Image - Side View
Flank Wear	VB1	Describes uniform flank wear	Figure 4a
Face Wear	KT1	Face wear occurring only on tool face	Figure 4c
	KT2	Face wear intersecting flank wear	Figure 4d
Outside Edge Wear	OE	Outside edge wear seen - no chipping	Figure 4b
Chipping	CH	Breaking away of parts of the cutting edge	Figure 4e
Catastrophic Failure	CF	Failure of cutting part - for example, loss of tooth	Figure 4f

Table 2: Types of wear: classification.

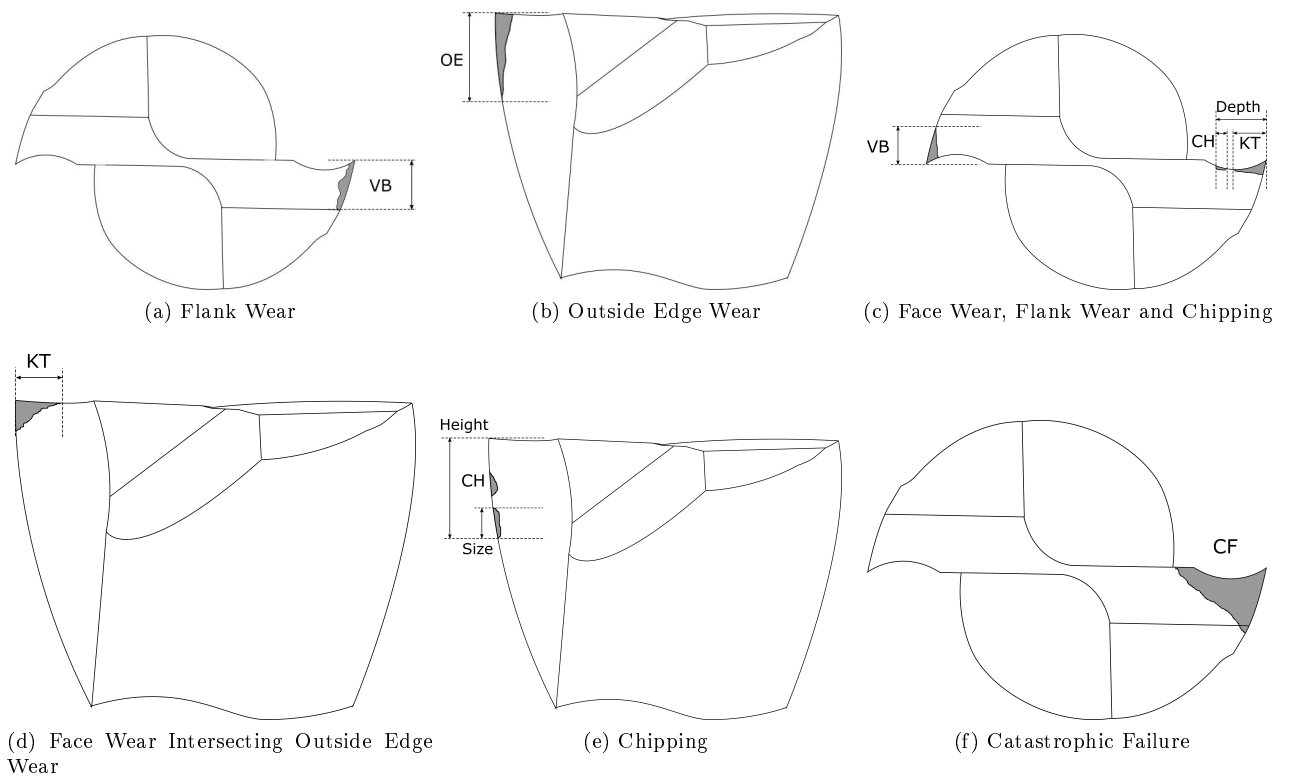


Figure 4: Types of Wear - graphical representation.

3.2. Definitions

Certain parameters must be defined when measuring wear on micro-end mills; including cutting edge radius, tool radius, and surface finish of workpiece, and similarly a qualitative indication of the wear mechanism(s). Cutting edge radius is defined as the radius seen on the cutting edge of the tool rake face. The tool radius is defined as half of the working diameter of the tool (for a 0.5mm end mill, this is 0.25mm). The surface finish of the workpiece is defined as the measured R_a value and the surface texture as the measured S_a value. Types of tool wear are based on ISO8688 [11] and adapted for small tools. These are categorised (Table 2) as Flank Wear (VB), Face Wear (KT), Outside Edge Wear (OE) Chipping (CH) and Catastrophic Failure (CF). By measuring tools in relation to these types of wear, direct comparison between studies can be made.

3.3. Materials: using Sliding Distance as a measure of Distance Cut

In the literature reviewed in Section 2, tool wear for micro-tools has been expressed in literature in terms cutting distance or material removal rate. While this method is useful for describing the useful life of a tool in a given material, it is very hard to compare wear of tools between materials because the difference in cutting feed and speed results in dramatically different sliding distances for different materials. The sliding distance of the teeth was calculated using

$$x_{comp} = \pi D_{cap} c_{comp} + \sum_1^{c_{inc}} x_i \quad (1)$$

where c_{inc} is the number of incomplete circles, calculated by $c_{inc} = \left(\frac{D_{cap}}{s} - D_{cap} \bmod 1 \right)$, c_{comp} is the number of complete circles, calculated by $c_{comp} = n_{rev} - c_{inc}$, D_{cap} is engaged tool diameter, and $\sum_1^{c_{inc}} x_i$ is the sum of the sliding distances for all the incomplete circles (Figure 5). This method is more useful in a tribological sense, but also allows tool wear for different materials to be compared even in the face of different cutting conditions. The value of x_{comp} was calculated using a Matlab program which established $\sum_1^{c_{inc}} x_i$.

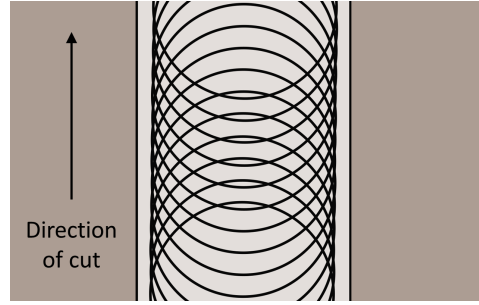


Figure 5: Path taken by milling cutter with tool starting and finishing clear of the work piece.

Use of sliding distance allows a more consistent metric to measure tool wear against than cutting distance or cutting time, as the amount of work carried out on the tool depends on spindle speed and feed rate. Conversion factors can be used to relate these sliding distances to either cutting distance or number of cuts given a known spindle speed and feed rate, allowing tool wear to be predicted under differing conditions.

3.4. Tool and Workpiece Preparation

Tools should be inspected before wear testing takes place to ensure minimum quality standards are met. For uncoated tools, an as received edge radius of $<0.1\mu\text{m}$ can reasonably be expected, while for coated tools it may be up to $0.2\mu\text{m}$. Grain size of the workpiece must be considered in terms of tool size, and these taken into account. No specification is given, but when comparing workpieces, the grain direction should be the same for each workpiece, and care should be taken where grain sizes are in the order of $0.1D$, where D is tool diameter, to ensure that workpiece grain sizes do not differ by more than $0.02D$. In addition, the following criteria regarding depth of cut [32] and unit removal [33] should be met. Unit Removal is defined by Taniguchi to be the amount of material removed per cut, having any of one, two or three dimensions [34]. These two criteria combine such that:

- edge radius $<$ depth of cut and
- edge radius $<$ unit removal $\times 10$

All workpieces should be faced off to ensure flatness perpendicular to the tool and fixed to the machine bed such that the surface is normal to the z-axis. Typically, flood or mist lubricant should be used to control machining temperatures, where the

pressure of this on the workpiece is monitored using a micro dynamometer or 3-component force link and taken into account when considering machining forces. Coolant method should be consistent across comparative studies.

3.5. Measurement of Tool

The micro tools should be measured both prior to testing and during testing. The basic equipment required for testing is as follows:

- Scanning electron microscope with both scattered and backscattered electron functionality.
- Optical profilometer (e.g. focus variation or white light interferometer).
- Ultrasound bath.
- Acetone.
- A compressed air source.
- A force cell for measuring lubricant pressure on workpiece.

During cutting, cutting forces should be measured to determine lubricant pressure as well as cutting forces. Tools should be removed at a pre-determined interval for measurement using an SEM. Before measuring using SEM, tools should be cleaned using acetone in an ultrasound bath and then dried using compressed air. Tools should be measured in two orientations, as shown in Figure 2 and it is possible to measure the tool wear using the protocol detailed in Table 2 (where the terminology used relates to the ISO standards). Often more than one type of wear is seen (see Figure 3). It is important to note that these two angles are the minimum requirement to identify all the wear types defined in the table. All wear measurements are expressed in terms of μm .

3.6. Measurement of Slot Profiles

The machined slots may be measured using one of two methods: either an image of the cross-section of the material should be taken, as in Figure 1; or a profilometer can be used to measure the slot profiles (Figure 2). If the latter is used, it is important to ensure that de-burring takes place as this will give inaccurate results. The de-burring must be carried out carefully and in such a way that there will be no further wear of the slots.



Figure 6: Image of cross section

Once measured, slot profiles can be described as seen in Figure 3, where W_{BT} and D_T are the theoretical width and depth of slot respectively, and W_B and D_A are the base width and actual depth. The depth of the slot may be a less reliable method of measuring flank wear than the width for measuring rake face wear, if the workpiece has not been faced off to a suitable flatness.

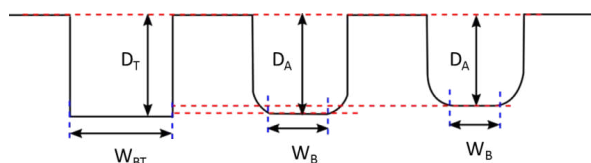


Figure 8: Slot profile measurement parameters

3.7. Criteria for Tool Life

Worn tools should be measured according to Section 3.5. Face wear of $0.2D$ should not be exceeded as this is considered catastrophic failure of the tool. For the purpose of wear measurement, measurement of face wear up to $0.2D$ will provide data into Zone III of the tool which exceeds practical use and allows the tool life criterion to be established.

3.8. Test Procedure

For wear testing, slots should be machined to a depth as specified in the data provided by the tooling supplier or manufacturer. The slot should begin outside the workpiece and run in the y -direction of cut.

3.8.1. Machine Tool Requirements

The machine tool should be a specialist micro-machining centre capable of reaching spindle speeds of 50,000 rpm or higher.

3.8.2. Measurement of Forces

In micro-milling applications, very small run-out leads to significant errors in engagement of teeth and uneven tooth wear. It is therefore always useful to examine the force signature for each tooth engagement to establish whether tooth engagement is equal.

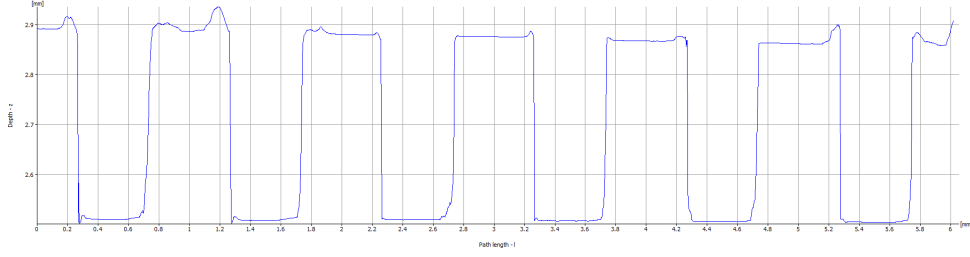


Figure 7: Cross-section measured using profilometer

As the forces measured in micro-milling are very small, it is useful to analyse forces using two different methods: measurement of the average cutting force and measurement of the amplitude of cutting force. The former is used to give a general picture of the cutting forces in the feed direction (denoted by Y in Figure 9), and simply averages (mean) the value of the signal over the specified cutting time. The latter is slightly more complex because it considers the range of the cutting forces experienced over the specified time. To do this accurately, the difference in engagement of the teeth must be accounted for by plotting the second term of the Fourier Transform. First the second Fourier coefficient, a_2 must be calculated as shown in Equation 2, where f_{cut} is the cutting frequency which is found by $f_{cut} = \frac{n}{60} \times Z_c$ where n is the spindle speed in rev/min and Z_c is number of cutting teeth.

$$a_2 = \frac{2}{x} \sum_{m=1}^x [F_c e^{(-i \cdot 2\pi f_t \cdot t)}] \quad (2)$$

F_c is the cutting force, t is the cutting time and x is the number of data points. Using the second coefficient, the real part of the second Fourier term can then be plotted against time, using Equation 3.

$$f(x) = \text{Re} [a_2 e^{(i \cdot 2\pi f_t \cdot t)}] \quad (3)$$

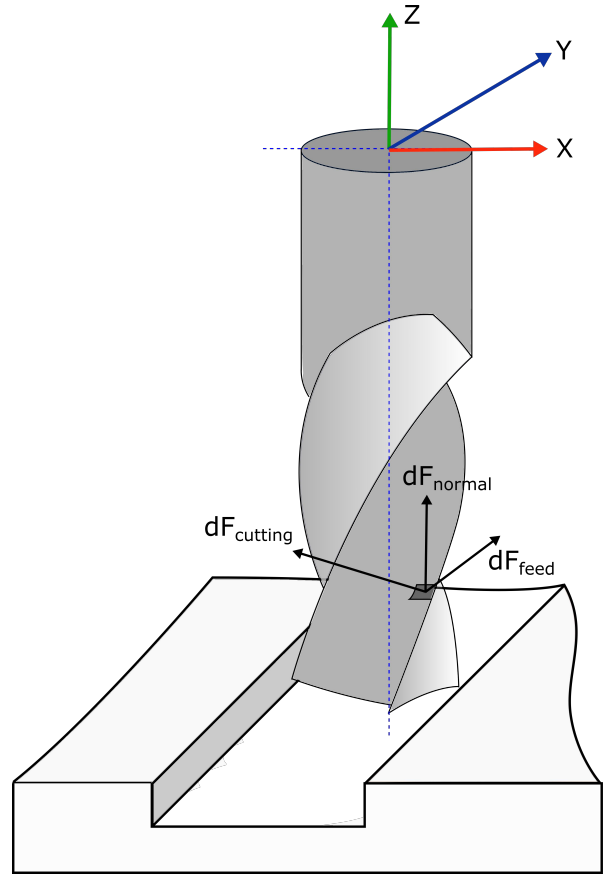


Figure 9: Forces exerted on the micro end mill.

3.9. Reporting of Results

Where tool wear evolution is plotted, wear should be reported in absolute terms relative to the original size of the tool (i.e. in μm). Sliding distance should be used for the x-axis, with a second axis being used as a conversion factor to cutting distance where required. An example of this is given in Figure 10. Tool wear should be identified as being in one of three zones:

I. Rapid initial wear

II. Steady state wear

III. Rapid wear before failure

The tool-life criterion can then be identified as the intersection between phases II and III.

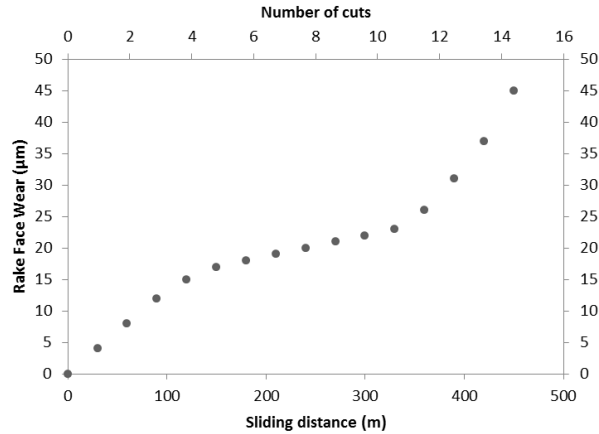


Figure 10: An example of the way in which results should be reported

4. Validation Tests

4.1. Materials and Methods

Once an acceptable wear testing protocol had been established, machining trials were designed to test the pertinence and consistency of the method. Three mechanically very different materials were used: brass (CuZn37), titanium grade 2 and Hastelloy (a nickel-molybdenum alloy containing zinc). Using three structurally disparate materials meant that a variety of wear mechanisms could be observed, representing a wide variety of industries. Tools were set up and measured as described in Sections 3.4-3.8. The trials took place on a KERN Evo micro-milling machine with a maximum spindle speed of 50,000 RPM. The tools used were commercially available 0.5mm AlTiN coated tungsten carbide end mills (SGS SER M2SM 0.5x3x0.8x38). Straight slots of 25mm in length were milled to a depth of 0.2mm. The workpiece and tool were flooded continuously throughout the cutting process using synthetic Hocut 768. The following machining parameters were used:

	Titanium grade 2	Hastelloy C276
Spindle speed (rpm)	25205	6786
Feed (m/min)	69	11
F_z (mm)	0.00136	0.00080
Radial depth of cut (mm)	0.5	0.5
Axial depth of cut (mm)	0.2	0.2
Sliding distance per 25mm length	14.06	23.75

Table 3: Parameters used in machining.

The different cutting speeds and feed rates used for each material can be accounted for through the use of sliding distance as the independent variable in reporting the results. The workpiece was mounted onto a 3-component force link (Kistler 9317C) (Figure 11) capable of measuring cutting forces in three dimensions (x, y, z) aligned with the major axes of the cutting process. This was connected to a National Instruments data acquisition system (DAQ) and. Kistler software was used to analyse the recorded data. After each cut was completed, the tools were imaged (by SEM) to measure the wear.

Results of this work were then used both to investigate the wear of the tools with a view to extending their useful life, and to confirm the testing protocol described.

4.2. Results - Observed S-Curves for Hastelloy, Titanium and Brass

4.2.1. Hastelloy

Figure 12 shows a tool wear curve for rake face wear due to cutting of Hastelloy C-276. Unfortunately, sampling rate in terms of measuring wear is less than desirable (wear measurement took place every 21.84m) and future studies were designed to measure the wear after a shorter sliding distance. For one of the teeth (where tooth number has no physical meaning), the following stages of wear can be seen: I. An initial rapid wear as the tool is run-in (this is shown in the yellow portion of the graph). II. Steady state wear (green). III. Rapid wear before tool failure (red). Occasionally, a region with apparently zero gradient is seen at the end of tool

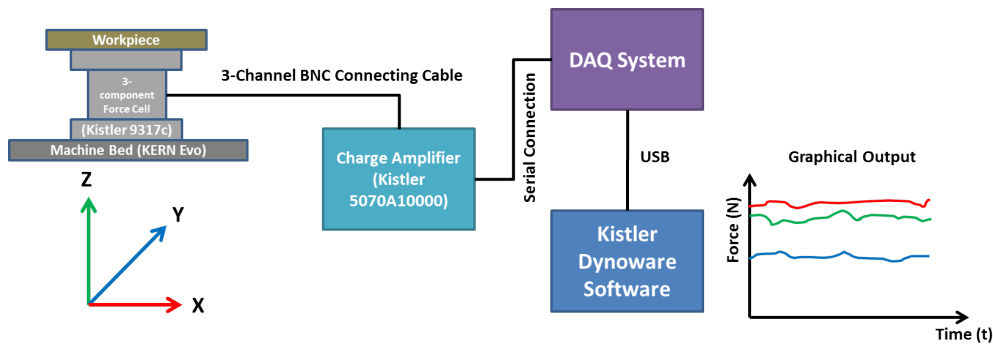


Figure 11: Schematic of the force measurement setup.

life, where wear has exceeded the length of the cutting edge: that is to say, the tool is no longer cutting effectively. At this point, rubbing and shaft failure occurs. The other tooth shows no apparent adherence to these stages, due to the initial state of the tool: this tooth was already rounded. This reinforces the need to initial inspection of tools to ensure they have met a minimum standard.

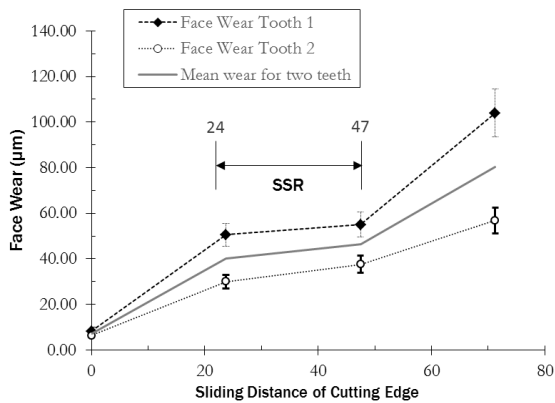


Figure 12: Tool wear curve measured for face wear of tool used to machine Hastelloy C-276.

The tool wear for one tooth was higher than that for the other. To understand this, the force signature of the tool was examined as seen in Figure 13. It can clearly be seen that one tooth has experienced more engagement than the other, and thus the cutting forces experienced are higher. There are two possible reasons for this: the first is that the initial wear on the second tooth is greater (and indeed this was verified by looking at images of the tool before cutting took place), and the second is that tool run-out causes uneven engagement of teeth. It is known that the machine spindle has some run out

from existing service data. This has been reported as being highly significant in micro-machining, in general, where the tools are smaller [32, 35] and this type of behaviour is typically seen in micro-milling, to the extent that sometimes only one tooth is engaged [36].

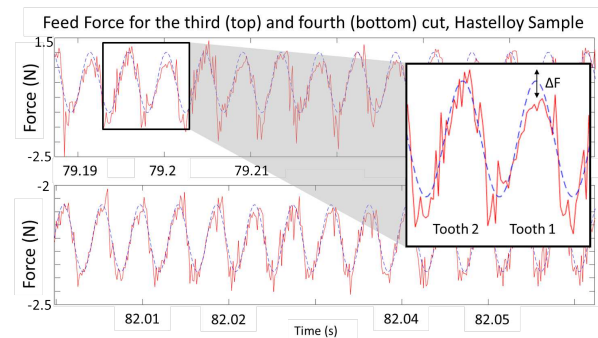


Figure 13: The force signature for the tool used to machine Hastelloy C-276.

The outside cutting edge data (Figure 14) showed little, if any, closeness to a traditional wear curve, resulting from the combined effects of too few measurement points for this tool, and the inherent volatility that is seen when measuring very small tools.

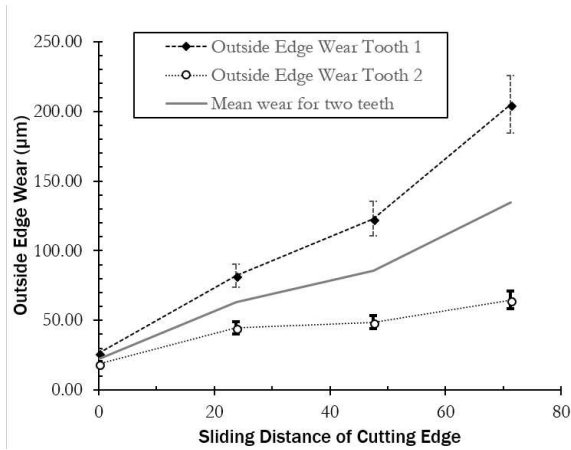


Figure 14: Tool wear curve measured for outside edge wear of tool used to machine Hastelloy C-276.

Flank wear (Figure 15) reveals a much more consistent result than face or outside edge wear and appears to lag behind face wear in terms of the wear stage. Here, initial quality of the tool is less significant since the flank face is set back from the leading edge of the tool, and both teeth show the first two stages of the classic wear curve.

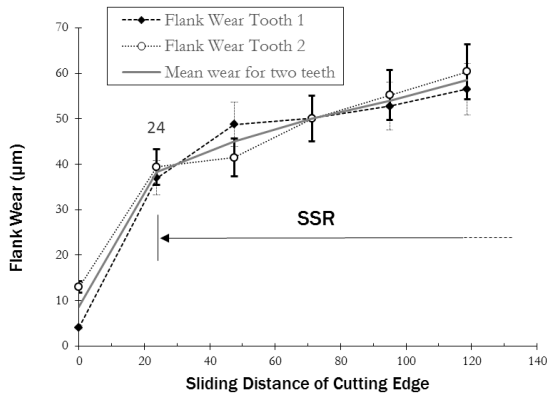


Figure 15: Tool wear curve measured for outside edge wear of tool used to machine Hastelloy C-276.

4.2.2. Titanium

For the tools used to cut titanium, the rake face wear curve (Figure 16) shows a typical s-curve up to approximately 130µm. Wear is steady between approximately 35µm and 90µm, after which it accelerates rapidly - thus the tool life criterion, defined as the point at which the tool begins to wear rapidly[12], is identified to be 90µm or 8% of the tool radius.

After 100µm of wear has occurred, the entire

cutting edge has been worn off and the tool can be considered to have failed. Tool shaft fracture may or may not occur at this point, depending on whether the centre of the tool remains engaged with the workpiece to an extent that a cut could be attempted.

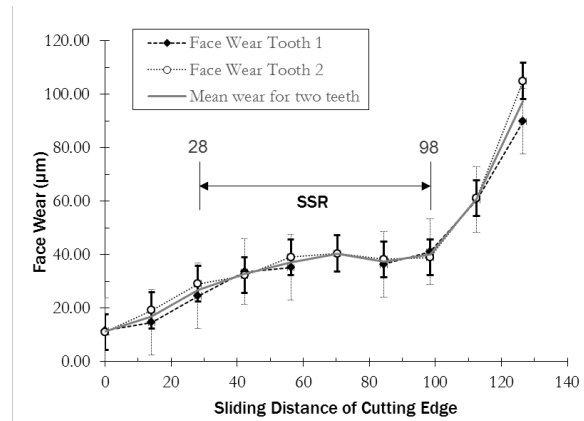


Figure 16: Tool wear curve measured for face wear of tool used to machine Ti grade 2.

As with the Hastelloy tools, outside edge wear (Figure 17) does not show a clear traditional wear curve. Abrasive wear continues to take beyond the depth of cut, because of swarf from the workpiece acting as a third body. This is evacuated by the lubricant (coolant) but rubs past the tool in this process. Wear appears to reach a steady state above a depth of 300µm, at which point the swarf is no longer travelling up the shaft and little contact between the tool and material takes place. Although outside edge wear is unable to provide a clear tool wear curve, chipping on the outside edge of the tool may affect the tool's ability to produce a good surface finish, or indeed the tool's ability to remove swarf. Thus, outside edge wear does provide some indication of impending tool failure.

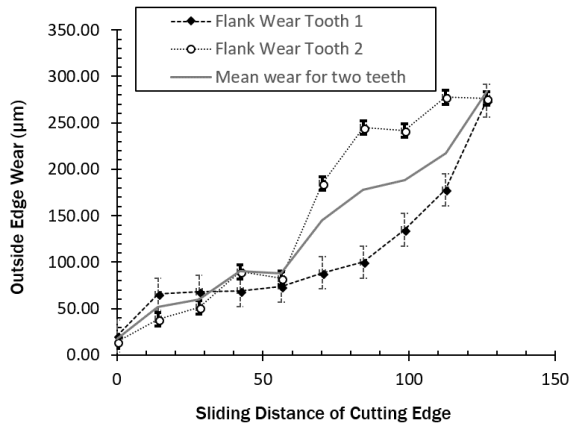


Figure 17: Tool wear curve measured for outside edge wear of tool used to machine Ti grade 2.

Flank wear, on the other hand, shows an S-curve as seen with face wear (Figure 18), with the only obvious difference being the point at which each wear stage is reached.

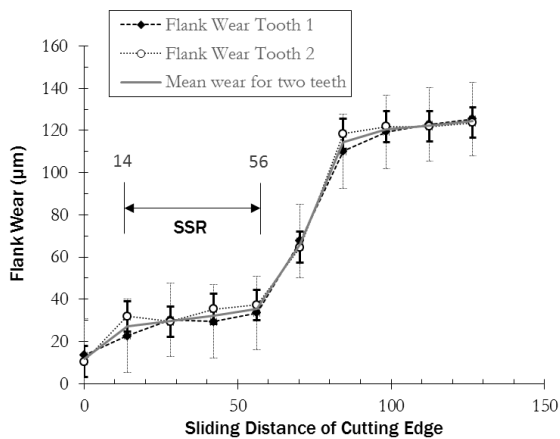


Figure 18: Tool wear curve measured for flank wear of tool used to machine Ti grade 2.

The shapes of the tool wear curves achieved are strikingly similar to conventional tool wear curves [37] - as previously noted by Bahrudin et al. [12] - in each case, a traditional s-curve is seen. This allows the critical wear point or tool life criterion to be identified as the point after which tool wear becomes intolerable. Depending on the required workpiece dimension tolerance, the actual tool wear volume that is acceptable may be less than this.

4.2.3. Brass

Two different types of tool were used to machine brass: those with no coating, and those with an Al-

TiN coating. The base tools were TiB_2 . As for Titanium and Hastelloy, as shape approximating an s-curve can be seen, although machining time was so short for the uncoated tools that data is limited. Comparison between the TiB_2 tools used to machine brass, and the tools which were coated with AlTiN clearly shows that the steady state portion of the graph is over twice the length for AlTiN coated tools than TiB_2 tools. Furthermore, the steady state region for the TiB_2 tools occurred at a higher level of wear. One of the TiB_2 tools fractured before rapid wear could be seen (Figure 19). Rake face wear is seen in the Figure, as the tool wear curve see for coated brass tools is taken from the preliminary study described in Section 2.3, during which only rake face wear was seen, and thus this is the only wear measurement that can be compared.

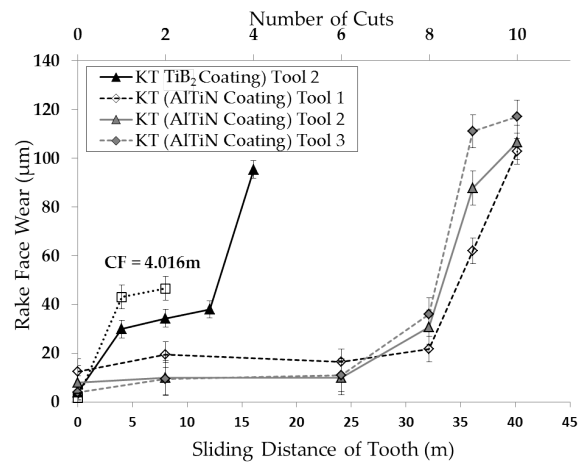


Figure 19: Rake face wear for uncoated and coated tools used to machine brass. CF indicates catastrophic tool failure.

5. Reflection on Protocol

Section 4.2 describes the results obtained using the protocol described in Section 3. Clear wear curves were seen using the imaging methods described for both rake face and flank wear. Other metrics, such as slot profile, which have been discussed in Section 2.2, were not able to provide as much information. This section considers each part of the protocol and its relative success, in order to determine which parts of the protocol can be concluded to be optimal when measuring tools.

5.1. Improvement of New Method over Tool Diameter

As discussed in Section 2, it is possible to describe the tool wear in terms of diameter reduction. However, in an addition to the fact that this does not take into account features such as tool geometry and uneven tooth wear, it can be seen from the tool wear curves in Section 4.2 that flank wear and face wear result in different points at which extreme wear begins to take place, and even outside edge wear, while not producing a curve, can provide information about tool chipping and imminent failure. The useful life of the tool should be identified as the point at which either flank or face wear reaches phase III, which in the case of the titanium workpiece was the flank wear. This is not reflected in a simple diameter measurement. Although measurement of diameter may be sufficient once tool life criterion is known, it cannot be used to determine it. The data arising from the use of the protocol described here allows the wear for each tooth to be measured for both tool flank and face such that a much clearer understanding of how the tools are wearing can be achieved, in a more consistent fashion, than has been previously carried out.

5.2. Efficacy of measuring slot profiles as a post-process tool wear method

Figure 20 shows the tool wear observed for a titanium sample using the method described in Section 3.6. Both wear to the flank and wear to the rake face can be seen.

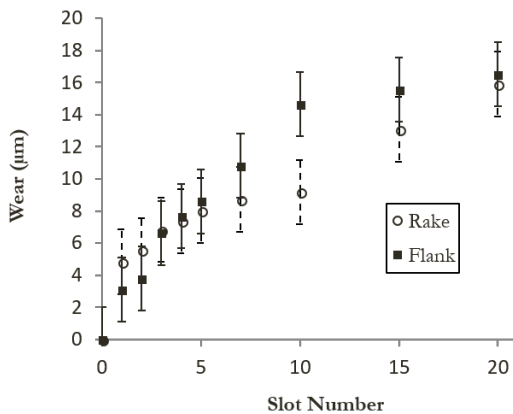


Figure 20: Tool wear curve measured using slot dimensions for Ti grade 2

One issue with this method was the fact that if the workpiece was removed after the initial levelling

stage; its orientation in the fixture was such that its surface was not completely perpendicular with respect to the tool. This led to an error in W_f and W_r , as can be seen in the Figure. The result of this is that absolute wear of the tools cannot be determined using this method. However, it is still possible to identify the steady state sections of the wear, which suggests that with refinement this method could be used as a quick method of analysing tool wear. Typically, an error in angle of workpiece would be very small.

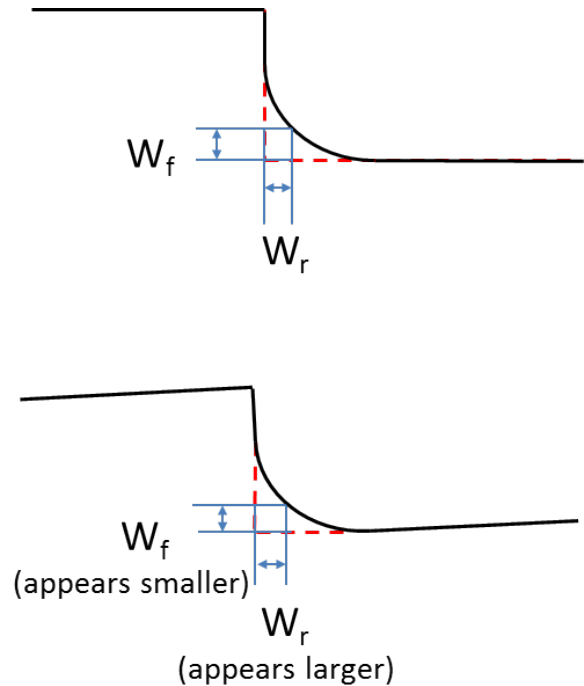


Figure 21: Possible sources of error when measuring slots

This method cannot be used where tools have been removed for measurement since relocation of the tool and workpiece causes the systematic error to become large and random, and the results become unreliable.

5.3. Sliding Distance Vs. Cutting Distance

As described in Section 3.3, sliding distance is more appropriate for plotting tool wear against than cutting distance or cutting time, as the amount of work carried out on the tool depends on spindle rotational speed (RPM) and feed rate.

When the tool wear for titanium and Hastelloy are compared as in Figure 22 using cutting distance, the tools used to cut Hastelloy enter the third wear

stage at approximately the same cutting distance that the tools used to cut titanium enter steady state wear. This comparison is misleading since the tools used to cut Hastelloy use lower feed rates and speeds due to Hastelloy's comparative resistance to cutting, and thus the graph plotted using sliding distance is more representative. Using sliding distance, it can be seen that even considering the higher sliding distance per cutting length for the tools used to cut Hastelloy, these tools wear much faster than those used for titanium.

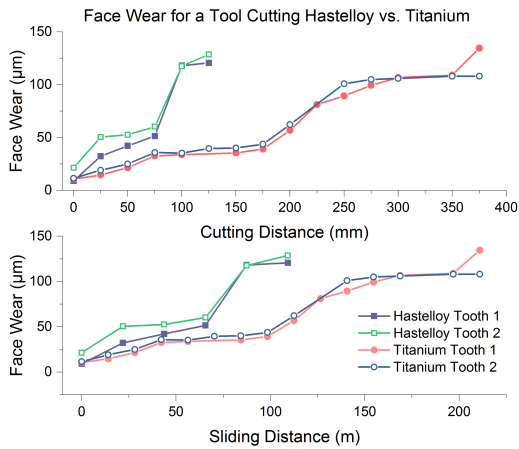


Figure 22: Possible sources of error when measuring slots

5.4. Direct Tool Measurement Vs. Slot Measurement

Figure shows the comparison between measurement of the slot profile for a tool used to cut titanium and the actual measurement of the tool. It can be seen that the slot measurement of rake face (measured using the method described in Section 3.6) does not accurately describe the tool wear curve for the tool, and therefore fails to produce the correct wear curve. This highlights the fact that although slot profile can be used as a fast method of identifying where wear has taken place, to obtain detailed information on tool wear direct measurement is needed.

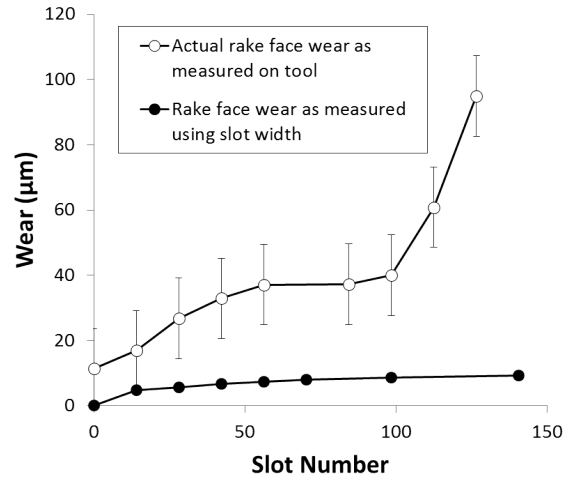


Figure 23: Possible sources of error when measuring slots

5.5. Rake Face Wear Vs. Cutting Forces

Rake face wear is compared with the feed component of cutting forces to the relationship between the two. This comparison is seen for Hastelloy is seen in Figure 24: Both teeth experienced similar wear for the rake face, with the transition between phase 1 and 2 (as described in Section 5) occurring at 22m of sliding distance, and the tool life criterion occurring at a sliding distance of 65m.

It can be seen for both sets of force data that both the average feed force and the range of feed forces (tool vibrations) initially increase with tool wear but that the rate of this increase plateaus with tool wear - this is consistent with the hypothesis that the tool is sufficiently worn that there is little engagement between tool and workpiece.

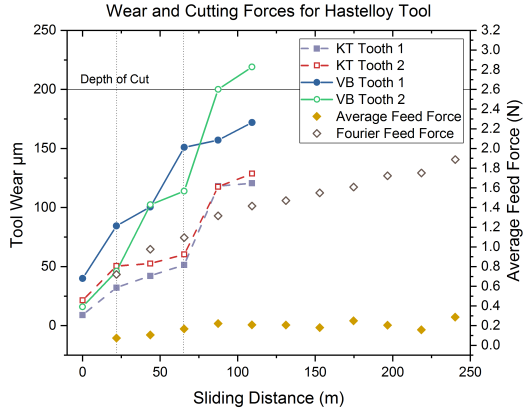


Figure 24: Wear in relation to cutting forces for a tool used to cut Hastelloy C-276

Compared with the data for Hastelloy, the tool used to cut the first titanium sample has significantly more data points. A clear S-curve is initially seen for face wear (Figure 25), with steady state wear occurring at a sliding distance of 42m and the tool life criterion occurring at a sliding distance of 99m. The curve then flattens out with reduced engagement and a dramatic wear increase is seen when tooth 1 fractures. Average feed force increases consistently, and interestingly continues to do so linearly with sliding distance even when the gradient of tool wear is at its lowest (i.e. in stage 2). The average feed force plateaus only when tool wear plateaus at the end of cutting due to lack of engagement. The Fourier transform of the force also starts by increasing linearly, but plateaus after the steady state region, likely because of reduced tool-workpiece contact.

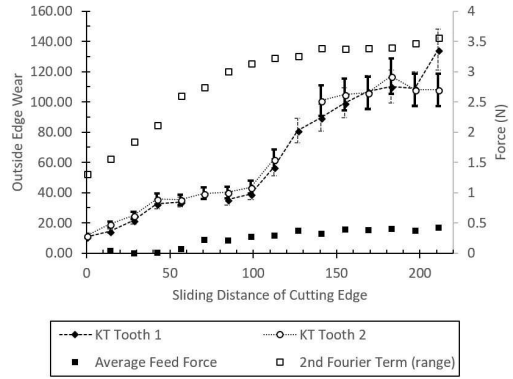


Figure 25: Wear in relation to cutting forces for a tool used to cut Ti grade 2

As well as initial edge rounding having much more significance for smaller tools, the coating thickness can be much more significant: both because it comprises more of the diameter of the tool (a thickness of $2\mu\text{m}$ represents 0.4% of the tool diameter as compared with 0.04% for a 5mm end mill) and because it increases the initial edge radius [38]. The issues with consistency in results discussed here indicate again the importance of ensuring that the tools are closely inspected before cutting takes place in future studies and reinforce the need for a standard protocol for micro tool wear measurement.

5.6. Force Signature - Looking at Uneven Engagement of Teeth

The force signature was investigated for each of the cuts made. Varying degrees of difference in force signal between teeth with seen, with an example for one of the Hastelloy cuts given in Figure 26.

The unanalysed force signature for the tools indicates that tooth wear engagement is often much more uneven than that seen for macro-milling tools. This has been seen before: Mativenga and Hon [39] reported an engagement difference of no more than 30%. However, this amounted to a force difference of approximately 20N. Similarly, Kim and Jeon observed a force difference of approximately 10N over a 50N range (<20% difference) for 8, 12 and 14mm end mills cutting Al6061-T6 aluminium alloy [40] but the magnitude of the forces is much lower in micro machining. Furthermore, tool run-out has much more significance for a smaller tool [32], as demonstrated by Figure 27. As previously discussed, uneven engagement of teeth caused by runout causes

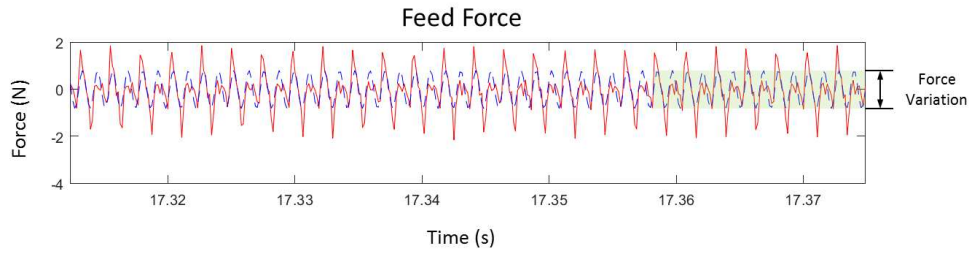


Figure 26: The fit made using the second term of the Fourier series.

different levels of wear to each tooth than that experienced by micro-milling. This results in a force signature that can be dramatically different for both teeth. Where the wear curve for each tooth is very similar, it should be expected that the force signature for each tooth is also similar


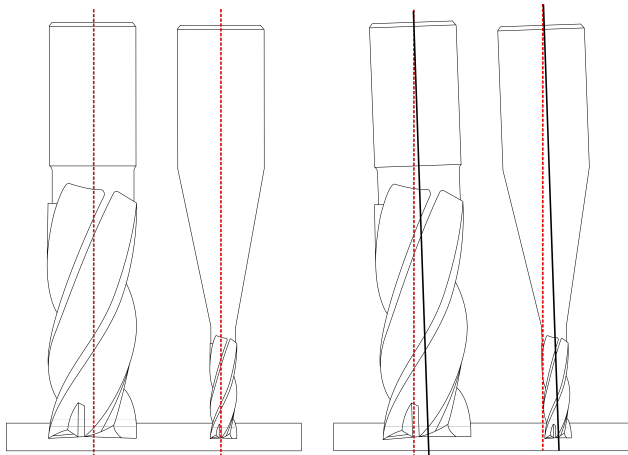


Figure 27: Effect of runout is magnified for a smaller tools.


5.7. Mechanism of Tool Breakage

One major consideration in micro-milling is the relative size of the workpiece grains in relation to the tools. Figure 28 shows (to approximate scale) the size of the grains for Hastelloy. Many of the grains are in the order of 10 μm , which is 2% of the tool's diameter. The structure appears inhomogeneous to the tool and thus the cutting forces can vary significantly from pass to pass. This causes sudden fracture to the teeth from time to time, rather than the smooth, even wear that would be expected in macro milling. To further understand

the mechanism of tool breakage, it is useful to look at the chips produced during the tool wear process.

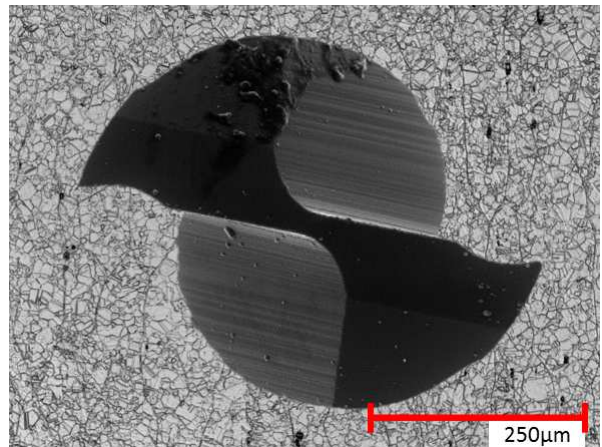

(a) Workpiece grain size is relatively large compared to the cutting edge.

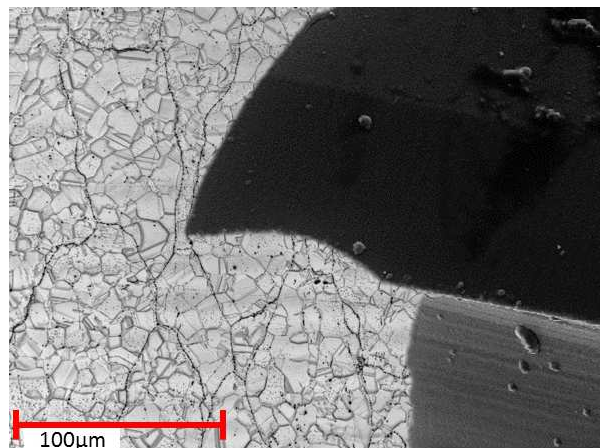

(b) Grain boundaries make the material appear inhomogeneous.

Figure 28: Grain sizes relative to tool size

Due to the very small size of the chips (typically the chips are no more than 200 μm in length and width) it is very difficult to collect and study them. However, some examples of chips for each material were collected directly from the work pieces. For both the titanium and the Hastelloy, serrated type chips were seen, of the type shown in Figure 22. Examples of both chips are given in Figure 21. The chip formation is an indicator of regions of intense shear followed by regions which are relatively undeformed. This results from high machining temperatures which are not dissipated quickly, as is common when cutting titanium and nickel alloys [41]. This can cause cutting edge attrition due to irregular flow of material as well as thermal fatiguing which results in chipping and cracking. The result of this can be the eventual catastrophic failure of the tools.


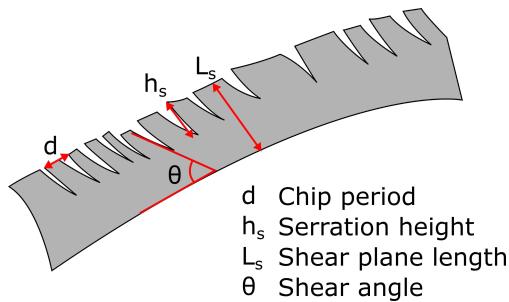



Figure 30: A serrated-type or discontinuous chip.

5.8. *Considering alternative coatings: an early investigation into extending tool life through coatings.*

Coating tools used to machine brass with AlTiN (Figure 19) in Figure 6 showed a dramatic lengthening of the steady state region of the tool wear curve for AlTiN coated tools. Additionally, the steady state occurred at a lower wear level for these tools. The latter result has previously been reported [15] but the lengthening of the curve is significant as it indicates a longer tool life. The early fracture of one of the TiB₂ tools is likely to have been caused by imperfections in the carbide material or excessive cutting forces generated by burring or larger crystals in the brass and serves as a reminder of the difficulty of measuring tools on the micro-scale and the importance of pre-inspection. This result suggests that even for softer metals such as brass, coating tools can significantly improve tool life. To a certain extent, this relates to cutting edge radius

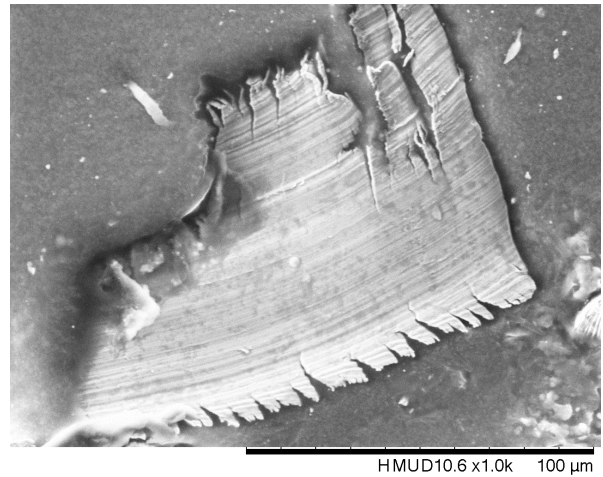

(a) Chip produced from machining of Hastelloy

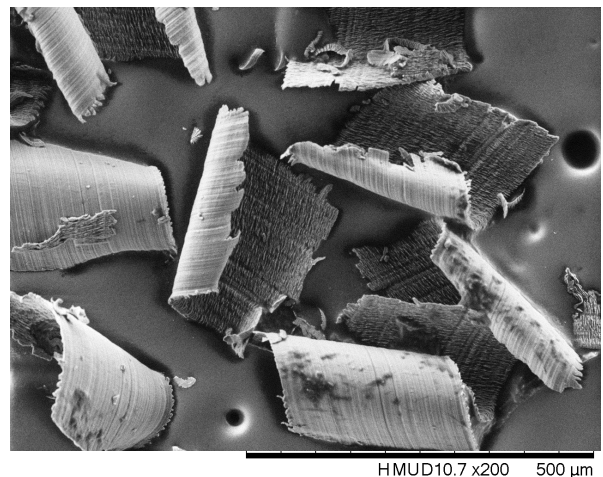

(b) Chip produced from machining of titanium

Figure 29: Chips produced in machining.

- the applied coating increases the cutting edge radius of the tools, and this cutting edge radius reduces stresses on the tools [42, 43]. This extension of tool life is worth investigating further.

6. Conclusions

Considering the difficulties encountered when comparing studies on tool wear in micro-end-milling, a protocol for measuring, characterising and reporting wear on sub-millimetre end mills is proposed. The purpose is to provide a method such that studies between different tool geometries and materials can reasonably be compared. Standardisation will make building on existing studies possible, while the characterisation of wear curves for different tools has direct applications in manufacturing for maximising process efficiency.

The results obtained in the validation wear tests have indicated that the wear measurement protocol proposed allows the wear curve of sub-millimetre micro end mills to be plotted, with the following points of note:

- I. Using the suggested protocol, stages of wear can be identified as with macro end mills, such that the wear of the tool is not allowed to go beyond the steady state region.
- II. Outside edge wear provides little information when studying the wear of micro end mills, due to the significant wear effects of chips sliding past these edges during machining. A combination of face wear and flank wear provides much more consistent data.
- III. By examining the tools using SEM techniques including backscattered electrons, and examining the chips, it is possible to understand the wear mechanisms taking place, which is useful when designing coatings for micro end mills.
- IV. It is common for the teeth of the tools to wear unevenly due to spindle run-out, which can lead to single tooth failure even relatively early in the tool wear curve. This highlights once again the importance of minimising this as compared with macro milling.
- V. Sliding distance presents a much more appropriate measure of reporting micro end mill wear than cutting distance or cutting time, since it considers cutting speeds and feed rates.

VI. Although there is scope for analysing channels and features in the workpiece as a method of tool wear measurement, which would dramatically speed up measurement time due to a single measurement rather than multiple removal of tools, this method is only able to provide information about the tools after the event and requires very strict machining to be of use. It is thus less robust for plotting wear curves than direct measurement of tools.

Based on literature reviewed in Section 2, there is scope for significant further investigation of coatings for larger micro-end-mills, since many tooling companies offer standard coated and uncoated micro-end-mills, but the research into coatings for micro end mills is significantly less extensive than that for larger end mills. Despite the disadvantages that coatings have (for example, increased cutting edge radius) there is opportunity for significantly extending tool life here.

As the tools tested were 500 μm diameter, further work should investigate the size limits of this protocol and establishing new methods where this protocol is no longer appropriate.

7. Acknowledgements

The authors wish to acknowledge the contribution of D.T. Curtis of the University of Sheffield Advanced Manufacturing Research Centre to discussions regarding tool wear prior to the conception of this work; the contribution of tools and expertise from Steve Neale at Kyocera-SGS; and the financial support of the EPSRC (EP/L016257/1) in this work.

8. References

References

- [1] M. Camara, J. C. Rubio, A. Abrão, and J. Davim, "State of the art on micromilling of materials, a review," *Journal of Materials Science & Technology*, vol. 28, no. 8, pp. 673–685, 2012.
- [2] K. Jemielniak and P. Arrazola, "Application of ae and cutting force signals in tool condition monitoring in micro-milling," *CIRP Journal of Manufacturing Science and Technology*, vol. 1, no. 2, pp. 97–102, 2008.
- [3] T. Özel, T. Thepsonthi, D. Ulutan, and B. Kaftanoğlu, "Experiments and finite element simulations on micro-milling of ti-6al-4v alloy with uncoated and cbn coated micro-tools," *CIRP Annals-Manufacturing Technology*, vol. 60, no. 1, pp. 85–88, 2011.

- [4] W. Bao and I. Tansel, "Modeling micro-end-milling operations. part i: analytical cutting force model," *International Journal of Machine Tools and Manufacture*, vol. 40, no. 15, pp. 2155–2173, 2000.
- [5] O. Ohnishi, H. Onikura, S.-K. Min, M. Aziz, and S. Tsuruoka, "Characteristics of grooving by micro end mills with various tool shapes and approach to their optimal shape," *Memoirs of the Faculty of Engineering, Kyushu University*, vol. 67, no. 4, pp. 143–151, 2007.
- [6] J. Chae, S. Park, and T. Freiheit, "Investigation of micro-cutting operations," *International Journal of Machine Tools and Manufacture*, vol. 46, no. 3, pp. 313–332, 2006.
- [7] P. Mativenga, *Micromachining*, pp. 873–877. Berlin, Heidelberg: Springer Berlin Heidelberg, 2014.
- [8] C.-J. Kim, M. Bono, J. Ni, *et al.*, "Experimental analysis of chip formation in micro-milling," *TECHNICAL PAPERS-SOCIETY OF MANUFACTURING ENGINEERS-ALL SERIES*, 2002.
- [9] A. Mian, N. Driver, and P. Mativenga, "Identification of factors that dominate size effect in micro-machining," *International Journal of Machine Tools and Manufacture*, vol. 51, no. 5, pp. 383–394, 2011.
- [10] International Standards Organisation, "Iso 8688-1: Tool life testing in milling- part 1: Face milling," 1989.
- [11] International Standards Organisation, "Iso 8688-2: Tool life testing in milling - part 2: End milling," 1989.
- [12] B. H. T. Baharudin, N. Dimou, and K. Hon, "Tool wear behaviour of micro-tools in high speed cnc machining," in *Proceedings of the 34th International MATADOR Conference*, pp. 111–118, Springer, 2004.
- [13] C. Li, X. Lai, H. Li, and J. Ni, "Modeling of three-dimensional cutting forces in micro-end-milling," *Journal of Micromechanics and Microengineering*, vol. 17, no. 4, p. 671, 2007.
- [14] K. Medicus, M. Davies, B. Dutterer, C. Evans, and R. Fielder, "Tool wear and surface finish in high speed milling of aluminum bronze," 2001.
- [15] S. Filiz, C. M. Conley, M. B. Wasserman, and O. B. Ozdoganlar, "An experimental investigation of micro-machinability of copper 101 using tungsten carbide micro-endmills," *International Journal of Machine Tools and Manufacture*, vol. 47, no. 7, pp. 1088–1100, 2007.
- [16] A. A. Elkaseer, S. Dimov, K. Popov, and R. Minev, "Tool wear in micro-endmilling: Material microstructure effects, modeling, and experimental validation," *Journal of Micro and Nano-Manufacturing*, vol. 2, no. 4, p. 044502, 2014.
- [17] M. Rahman, A. S. Kumar, and J. Prakash, "Micro milling of pure copper," *Journal of Materials Processing Technology*, vol. 116, no. 1, pp. 39–43, 2001.
- [18] I. Tansel, A. Nedbouyan, M. Trujillo, and B. Tansel, "Micro-end-milling-ii. extending tool life with a smart workpiece holder (swh)," *International Journal of Machine Tools and Manufacture*, vol. 38, no. 12, pp. 1437–1448, 1998.
- [19] P. Kolar, M. Sulitka, P. Fojtu, J. Falta, and J. Sindler, "Cutting force modelling with a combined influence of tool wear and tool geometry," *Manuf Technol*, vol. 16, no. 3, pp. 524–531, 2016.
- [20] H. Li, X. Lai, C. Li, J. Feng, and J. Ni, "Modelling and experimental analysis of the effects of tool wear, minimum chip thickness and micro tool geometry on the surface roughness in micro-end-milling," *Journal of micromechanics and microengineering*, vol. 18, no. 2, p. 025006, 2007.
- [21] I. Uzun, K. Aslantas, and F. Bedir, "An experimental investigation of the effect of coating material on tool wear in micro milling of inconel 718 super alloy," *Wear*, vol. 300, no. 1, pp. 8–19, 2013.
- [22] M. Malekian, S. S. Park, and M. B. Jun, "Tool wear monitoring of micro-milling operations," *Journal of Materials Processing Technology*, vol. 209, no. 10, pp. 4903–4914, 2009.
- [23] A. Aramcharoen, P. Mativenga, S. Yang, K. Cooke, and D. Teer, "Evaluation and selection of hard coatings for micro milling of hardened tool steel," *International Journal of Machine Tools and Manufacture*, vol. 48, no. 14, pp. 1578–1584, 2008.
- [24] K.-M. Li and S.-Y. Chou, "Experimental evaluation of minimum quantity lubrication in near micro-milling," *Journal of materials processing technology*, vol. 210, no. 15, pp. 2163–2170, 2010.
- [25] H. Ding, N. Shen, and Y. C. Shin, "Experimental evaluation and modeling analysis of micromilling of hardened h13 tool steels," *Journal of Manufacturing Science and Engineering*, vol. 133, no. 4, p. 041007, 2011.
- [26] J. Bai, Q. Q. Bai, and Z. Tong, "Experimental and multiscale numerical investigation of wear mechanism and cutting performance of polycrystalline diamond tools in micro-end-milling of titanium alloy ti-6al-4v," *International Journal of Refractory Metals and Hard Material*, 2018.
- [27] X. Teng, D. Huo, I. Shyha, W. Chen, and E. Wong, "An experimental study on tool wear behaviour in micro milling of nano mg/ti metal matrix composites," *International Journal of Advanced Manufacturing Technology*, 2018.
- [28] Y. Wang, B. Zou, C. Huang, Z. Liu, and P. Yao, "The micro-cutting performance of cermet and coated wc micro-mills in machining of tc4 alloy micro-grooves," *The International Journal of Advanced Manufacturing Technology*, 2018.
- [29] G. Strnad and J. Buhagiar, "Latest developments in pvd coatings for tooling," *Scientific Bulletin of the "Petru Maior" University of Targu Mures*, vol. 7, no. 1, p. 32, 2010.
- [30] K. A. Vikram, C. Ratnam, K. S. Narayana, and B. S. Ben, "Assessment of surface roughness and mrr while machining brass with hss tool and carbide inserts," 2015.
- [31] V. P. Astakhov and J. P. Davim, "Tools (geometry and material) and tool wear," *Machining: Fundamentals and Recent Advances*, pp. 29–57, 2008.
- [32] D. Dornfeld, S. Min, and Y. Takeuchi, "Recent advances in mechanical micromachining," *CIRP Annals-Manufacturing Technology*, vol. 55, no. 2, pp. 745–768, 2006.
- [33] T. Masuzawa, "State of the art of micromachining," *CIRP Annals-Manufacturing Technology*, vol. 49, no. 2, pp. 473–488, 2000.
- [34] N. Taniguchi, "Current status in, and future trends of, ultraprecision machining and ultrafine materials processing," *CIRP Annals-Manufacturing Technology*, vol. 32, no. 2, pp. 573–582, 1983.
- [35] F. Fang, H. Wu, X. Liu, Y. Liu, and S. Ng, "Tool geometry study in micromachining," *Journal of Micromechanics and Microengineering*, vol. 13, no. 5, p. 726, 2003.

- [36] J. Fleischer, M. Deuchert, C. Ruhs, C. Kühlewein, G. Halvadjisky, and C. Schmidt, "Design and manufacturing of micro milling tools," *Microsystem Technologies*, vol. 14, no. 9-11, pp. 1771–1775, 2008.
- [37] M. P. Groover, *Fundamentals of modern manufacturing: materials processes, and systems*. John Wiley & Sons, 2007.
- [38] S. Afazov, D. Zdebski, S. Ratchev, J. Segal, and S. Liu, "Effects of micro-milling conditions on the cutting forces and process stability," *Journal of Materials Processing Technology*, vol. 213, no. 5, pp. 671–684, 2013.
- [39] P. Mativenga and K. Hon, "An experimental study of cutting forces in high-speed end milling and implications for dynamic force modeling," *Journal of Manufacturing Science and Engineering*, vol. 127, no. 2, pp. 251–261, 2005.
- [40] D. Kim and D. Jeon, "Fuzzy-logic control of cutting forces in cnc milling processes using motor currents as indirect force sensors," *Precision Engineering*, vol. 35, no. 1, pp. 143–152, 2011.
- [41] W. Knight and G. Boothroyd, *Fundamentals of Metal Machining and Machine Tools, Third Edition*. Manufacturing engineering and materials processing, Taylor & Francis, 2005.
- [42] W. J. Endres and R. K. Kountanya, "The effects of corner radius and edge radius on tool flank wear," *Journal of Manufacturing Processes*, vol. 4, no. 2, pp. 89–96, 2002.
- [43] J. Fulemova and Z. Janda, "Influence of the cutting edge radius and the cutting edge preparation on tool life and cutting forces at inserts with wiper geometry," *Procedia Engineering*, vol. 69, pp. 565–573, 2014.