

Wear particles enhance autophagy through up-regulation of CD147 to promote osteoclastogenesis

Baohua Su¹, Deng Li¹, Jie Xu¹, Yingbin Zhang¹, Zhiqing Cai¹, Max Daniel Kauther², Ruofan Ma^{1*}

¹ Department of Orthopedics, Sun Yat-sen Memorial Hospital, Sun Yat-sen University, Guangzhou, China, 510120

² Department of Orthopedics and Trauma Surgery, University Hospital Essen, University of Duisburg-Essen, Hufelandstrasse 55, 45147 Essen, Germany

ARTICLE INFO

Article type:

Original article

Article history:

Received: Jan 23, 2018

Accepted: Mar 18, 2018

Keywords:

Autophagy
CD147
Osteoclastogenesis
Peri-implant osteolysis
RANKL

ABSTRACT

Objective(s): The study aimed to uncover the underlying mechanism linking wear particles to osteoclast differentiation, and we explored the effect of titanium particles of different sizes on CD147 expression and autophagy in macrophages.

Materials and Methods: Effects of titanium particles on CD147 and RANKL mRNA were detected by QPCR; protein level of CD147 and Beclin-1 were detected by Western blot; soluble RANKL were detected by ELISA. To determine the effect of CD147 and autophagy, KG-1a cells were transfected with siRNA-CD147 or treated with autophagy inhibitor CQ (chloroquine), and then co-cultured with different sizes of titanium particles.

Results: Our results showed that 0.2-1.2 μm and 1.2-10 μm titanium particles up-regulate CD147 to activate autophagy, which increase the level of soluble RANKL to promote osteoclastogenesis. Suppression of CD147 with siRNA could diminish particle-induced autophagy and soluble RANKL expression. In addition, CQ could dramatically reduce particle-induced soluble RANKL expression.

Conclusion: Our findings suggested a possible mechanism underlying wear debris-induced osteolysis and identified CD147 as a potential therapeutic target in aseptic loosening.

► Please cite this article as:

Su B, Li D, Xu J, Zhang Y, Cai Zh, Kauther MD, Ma R. Wear particles enhance autophagy through upregulation of CD147 to promote osteoclastogenesis. Iran J Basic Med Sci 2018; 21:806-812. doi: 10.22038/IJBMS.2018.29347.7093

Introduction

It has been well recognized that wear particles derived from implants have the potential to stimulate inflammation and osteoclast differentiation, which increase osteoclastic bone resorption and decrease osteoblastic bone formation. However, the underlying mechanism linking wear particles to osteoclast differentiation remains to be illustrated. Artificial joint replacement (AJR) is considered one of the most important treatment strategies for patients with end-stage joint disease. However, peri-implant osteolysis (PIO) and subsequent aseptic loosening of the implant are frequent complications which restrict the long-term success of the therapy (1). Titanium wear particles and other types of biomaterial wear byproducts derived from the bone-prosthesis interface are recognized to cause PIO, which then initiates aseptic loosening (2, 3). Although the precise mechanism by PIO is not clear, many studies have suggested that over-activation of osteoclasts and inflammatory responses play a critical role in PIO(4-6). In the periprosthetic tissue, wear particles could be recognized and phagocytosed by macrophages (7, 8), which stimulate macrophages, fibroblasts osteoblasts and T lymphocytes to produce high levels of proinflammatory cytokines and chemokines (9-11). Those proinflammatory cytokines can induce osteoclastogenesis and suppress osteoblast function (12, 13). In addition, wear particles also could enhance osteoclastic bone resorption by increasing the recruitment of osteoclast precursors, differentiation of osteoclast precursors, activation of osteoclasts, and

survival of osteoclasts (14-16). Furthermore, a growing number of research indicate the receptor activator of nuclear factor kappa B (RANK) and its ligand (RANKL) are essential for wear particle-induced osteolysis (17-19). RANK is a membrane-bound factor expressed on the surface of macrophages. RANKL could bind to RANK, then activate downstream signaling cascade pathways to promote the differentiation of bone marrow-derived macrophages to multinucleated osteoclasts (20, 21). Therefore, increased osteoclasts lead to bone resorption surrounding the implant.

Autophagy is a lysosomal degradation pathway, which is responsible for degrading and recycling protein aggregates, oxidized lipids, damaged organelles and intracellular pathogens (22, 23). Factors that induce cellular stress, such as hypoxia, accumulation of oxidative stress and caloric restriction, can induce autophagy (24, 25). In recent years, numerous studies show that autophagy is important to osteoclasts and bone resorption *in vitro* and *in vivo* (26-28). Resorptive activity is decreased when the autophagy is suppressed by bafilomycin in osteoclasts (29, 30). An increase in autophagy has been observed during osteoclastogenesis under hypoxia environment and increased oxidative stress (31). In addition, pharmacological and genetic inhibition of autophagy could reduce osteoclastogenesis and bone resorption, inhibiting bone loss caused by ovariectomy or glucocorticoid treatment in mice (32). With respect to wear particle-induced osteolysis, study have reported that CoCrMo metal particles stimulated autophagy in

*Corresponding author: Ruofan Ma. Department of Orthopedics, Sun Yat-sen Memorial Hospital, Sun Yat-sen University, Guangzhou, China, 510120. Tel/Fax: +86-2081332496; Email: maruofan_syx@163.com

osteoblasts and particle-induced osteolysis animal models (33). However, there is limited research focused on the relationship between autophagy and wear particle-induced osteoclastogenesis.

CD147 is also known as Basigin/Leukocyte Activation Antigen M6/EMMPRIN, which is a transmembrane glycoprotein belonging to the immunoglobulin superfamily (34). CD147 is involved in tissue remodeling, cancer progression and the synovial membrane of rheumatoid arthritis patients (35, 36). CD147 could enhance autophagy of HCC cells and favor HCC cell survival under cisplatin treatment (37). In addition, CD147 plays an important role in breast cancer-induced osteolytic lesions (38). In this case, the abnormal expression of CD147 could induce excessive osteoclast differentiation and bone resorption. Furthermore, some studies showed that CD147 could promote the formation of functional osteoclasts (39). Nevertheless, there is no report about the relationship between CD147 and wear particle-induced osteoclastogenesis.

In the present study, we hypothesized that titanium wear particles could increase the expression of CD147, which could activate autophagy in macrophages. Autophagy may promote the expression of RANKL and induce osteoclastogenesis, which consequently caused osteolysis. We tested and verified our hypothesis in the human acute myelogenous leukemia cell line KG-1a.

Materials and Methods

Cell culture

The cell line KG-1a (macrophage) was obtained from ATCC, USA; ATCC number: CCL-246TM. KG-1a cells were routinely maintained in Iscove's Modified Dulbecco's Medium (IMDM, Gibco, Grand Island, NY, USA) containing 20% heat inactivated fetal bovine serum (FBS, Gibco, Grand Island, NY, USA) in a humidified incubator at 37 °C in an atmosphere of 5% CO₂ (40).

Preparation of particles

Commercial pure titanium particles were purchased from Alfa Aesar (Ward Hill, MA, USA; 00681). The preparation of particles were as described previously (40), the particle size was <20 μm, all of the particles were diluted with pure water and filtered by Millipore filter membranes (Billerica, MA, USA) of a series of sizes (pore diameter: 0.2, 1.2, and 10 μm), three ranges of particle size, 0.2–1.2, 1.2–10, and >10 μm were obtained after filtration. Finally, all particles were washed with 70% ethanol for 24 hr at room temperature, then they were dried in a biological drying oven. The dried particles were sterilized with ethylene oxide.

According to particle weight and density, the concentration of the particles suspended in phosphate buffered saline (PBS) was adjusted to 5×10⁸ /ml. KG-1a cells were seeded in 6-well plates, 5 million cells per well, three ranges of particle (0.2–1.2, 1.2–10, and >10 μm) were added to the corresponding well, the ratio of particle count to cell count was 1000:1, 500:1, 100:1, 10:1, 1:1, 0:1, respectively, shaken gently for more than 15 mins to make the particles and KG-1a cells mix completely, then cultured with a humidified incubator at 37 °C in an atmosphere of 5% CO₂ (40).

Treatment with siRNA and Chloroquine (CQ)

SiRNA-CD147 and negative control siRNA were purchased from GenePharma (Shanghai, China; SG1062). Transfection was performed as described previously (40). KG-1a cells were transfected with siRNA-CD147 or negative control siRNA using Lipofectamine 2000 reagent (Invitrogen, Waltham, MA, USA; 11668019). 24 hrs post-transfection, the cells were incubated with 0.2–1.2 μm (at particle count to cell count ratio of 100:1) or 1.2–10 μm (at particle count to cell count ratio of 1000:1) titanium particles for 24 hr.

KG-1a cells were treated with 100 μM CQ (Sigma-Aldrich, St. Louis, MO, USA; C6628) for 24 hr, and then co-cultured with 0.2–1.2 μm (at particle count to cell count ratio of 100:1) or 1.2–10 μm (at particle count to cell count ratio of 100:1) titanium particles for 24 hr.

Quantitative real time PCR (qRT-PCR)

CD147 and RANKL mRNA levels were detected 6 hr after the incubation of particles and KG-1a cells. Quantitative real-time PCR was performed as described previously (40). Total RNA was extracted using TRIzol reagent (Invitrogen, Waltham, MA, USA; 15596026). Reverse transcription was performed with PrimeScriptTM RT reagent Kit and gDNA Eraser (Takara, Tokyo, Japan; RR047A) according to the manuscripts. The qRT-PCR was performed on MiniOpticonTM real-time PCR detection instrument (Bio-Rad, Hercules, CA, USA) with GoTaq[®] qPCR Master Mix ((Promega, Madison, WI, USA) following standard procedures. A housekeeping gene GAPDH was used as an internal control.

Western blot

Protein levels of CD147 and beclin-1 were detected 24 hr after the incubation of particles and KG-1a cells. The treated cells were lysed with RIPA containing proteinase and phosphatase inhibitors (Sigma-Aldrich, St. Louis, MO, USA; Y0001009). The protein was quantified with PierceTM BCA Protein Assay Kit (ThermoFisher, Waltham, MA, USA; 23227), separated by 12% SDS-PAGE electrophoresis and transferred to polyvinylidene fluoride (PVDF) membranes, as described previously (40). The membranes were blocked with 5% defatted milk for 1 hr, and then immunoblotted with anti-CD147 (Boster, California, USA; 1:500), anti-Becclin-1 (Boster, California, USA; 1:1000), and anti-GAPDH (Boster, California, USA; 1:1000) over night at 4 °C. The membranes were washed, and then incubated with specific secondary antibodies. Finally, the blots were visualized using chemiluminescence (ECL; Forevergen Biosciences Center, Guangzhou, China).

Enzyme-linked immunosorbent assay (ELISA)

The RANKL levels in the supernatants were detected using Human TNFSF11 ELISA Kit (Abcam, Cambridge, MA, USA; ab100749). The assay was performed as described previously (41). All procedures were performed according to the instructions.

After coating, plates were sequentially washed with PBST buffer and blocked with 1% BSA and incubated for 1 hr at 37 °C. Then, anti-ODF and HRP-conjugated antibody were sequentially added and incubated for 1 hr at 37 °C. The detection was achieved by adding

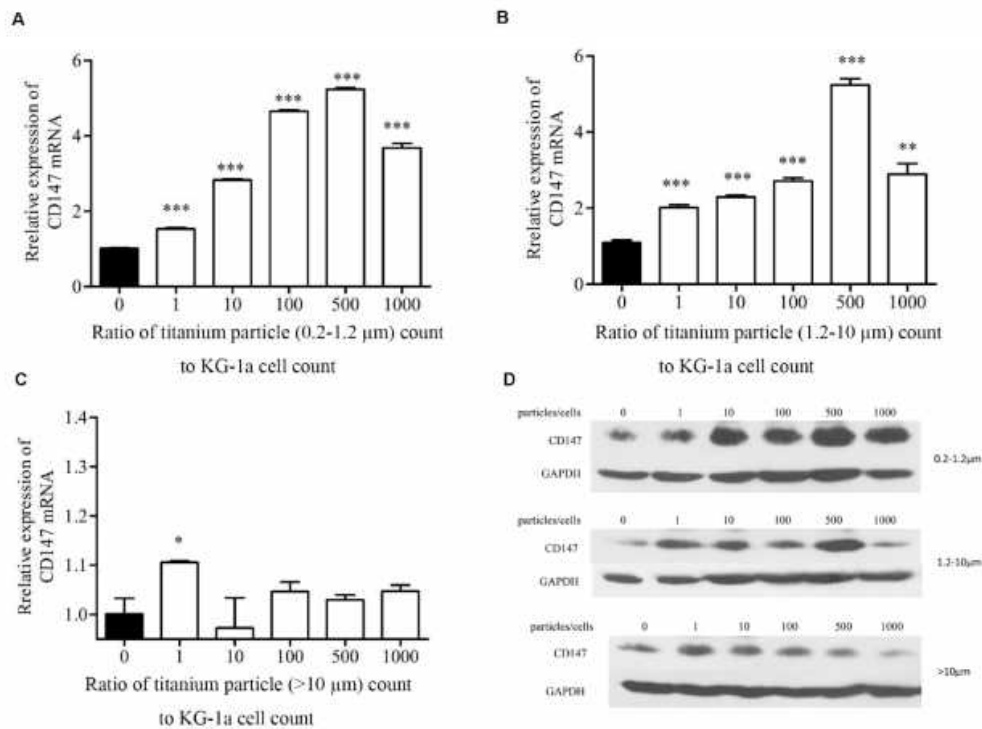


Figure 1. Effects of titanium particles on mRNA and protein level of CD147. QPCR showed the expression of CD147 mRNA in KG-1a cells co-cultured with 0.2–1.2 μm (A), 1.2–10 μm (B) and >10 μm (C) titanium particles; the protein level of CD147 in KG-1a cells co-cultured with 0.2–1.2, 1.2–10 and >10 μm titanium particles was detected by western blot (D). * $P < 0.05$; ** $P < 0.01$; *** $P < 0.001$

chromogenic substrate, 3,3',5,5'-tetramethylbenzidine (TMB). Absorbance was measured at 450 nm with an EnSpire multimode plate reader (Perkin Elmer, Waltham, Massachusetts).

Statistical analysis

All experiments were repeated at least three times. Data are presented as means \pm SD. Student's t-test (unpaired, two-tailed) analysis were carried out to evaluate differences between groups. $P < 0.05$ was considered statistically significant.

Results

Wear particles increase the expression of CD147

CD147 has been reported to play an important role in breast cancer-induced osteolytic lesions. To assess whether CD147 expression was altered by titanium particles in macrophages, KG-1a cells were co-cultured with 0.2–1.2 μm , 1.2–10 μm and bigger than 10 μm (>10 μm) titanium particles for 24 hr, KG-1a cells were seeded in 6-well plates, 5 million cells per well, three ranges of particles were added to the corresponding well, the ratio of particle count to cell count was 1000:1, 500:1, 100:1, 10:1, 1:1, 0:1, respectively. The mRNA and protein expression levels of CD147 were detected with qPCR and Western blot. As shown in Figure 1A, B and C, the mRNA of CD147 was significantly increased in the cells co-cultured with 0.2–1.2 μm and 1.2–10 μm particles, and showed dose-dependent increase with rising ratios; while >10 μm particles was slightly increased at 1:1 ratio compared with the control, and no significant increase in CD147 mRNA for any of the other treatment groups. The protein of CD147 was dramatically elevated when the cells were incubated with 0.2–1.2 μm and 1.2–

10 μm particles (Figure 1D). The western blot results implied that titanium particles sized 0.2–1.2 μm and 1.2–10 μm induced a dose-dependent increase of CD147 protein level with rising ratios. Nevertheless, >10 μm particles could not be able to significantly increase the CD147 protein level at different ratios (Figure 1D). These results indicated that titanium particles smaller than 10 μm were able to greatly increase the expression level of CD147 protein.

Down-regulation of CD147 suppressed wear particle-induced osteoclastogenesis

RANKL plays a key role in osteoclast development, thus we assessed whether titanium particles altered the expression of RANKL in macrophages. Under treatment of titanium particles, the mRNA of RANKL in KG-1a cells were detected with qPCR. Our results suggested that the mRNA of RANKL was significantly up-regulated in the KG-1a cells treated with 0.2–1.2 μm particles at 10:1 or higher ratios, 1.2–10 μm particles at 1:1 or higher ratios, and >10 μm particles at 1000:1 ratio (Figure 2A, C and E). To investigate whether titanium particles regulated RANKL secretion at the protein level, we evaluated soluble RANKL in supernatant of treated cells using ELISA. As shown in Figure 2B and D, at all ratios, titanium particles sized 0.2–1.2 μm and 1.2–10 μm were able to robustly increase the expression level of soluble RANKL. 4.3-fold and 2.2-fold up-regulation of soluble RANKL were observed in the cells, which were stimulated by 0.2–1.2 μm particles at 100:1 ratio and 1.2–10 μm particles at 1000:1 ratio, respectively. Titanium particles sized >10 μm could induce the expression of soluble RANKL only at ratios of 1:1 (1.5-fold), 500:1 (1.1-fold) and 1000:1 (1.6-fold) (Figure 2F). These results

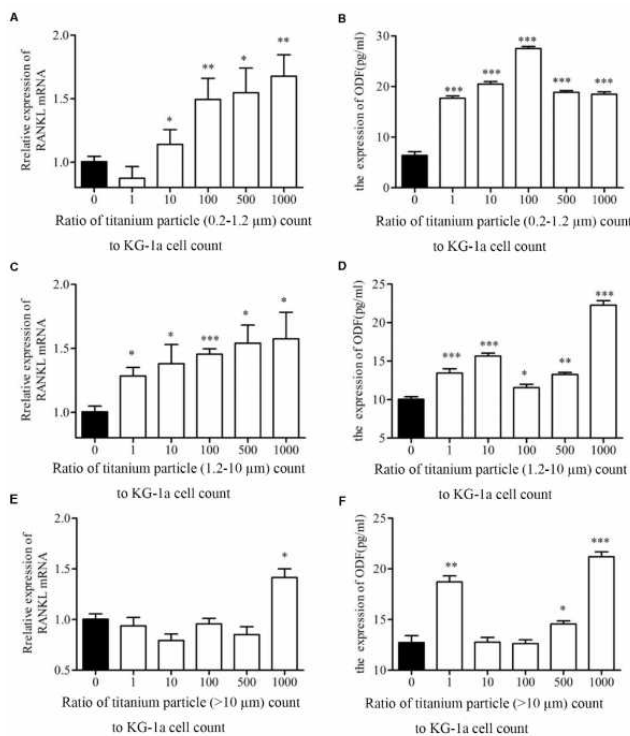


Figure 2. Effects of titanium particles on mRNA and soluble protein expression of RANKL. The mRNA of RANKL and soluble RANKL in KG-1a cells co-cultured with 0.2–1.2 μm (A, B), 1.2–10 μm (C, D) and >10 μm (E, F) titanium particles were detected by qPCR and ELISA respectively. **P*<0.05; ***P*<0.01; ****P*<0.001

showed different responses of macrophages to titanium particles of varying sizes, the titanium particles sized 0.2–1.2 μm and 1.2–10 μm exhibited more biological activity. Therefore, titanium particles sized 0.2–1.2 μm (at particle count to cell count ratio of 100:1) and 1.2–10 μm

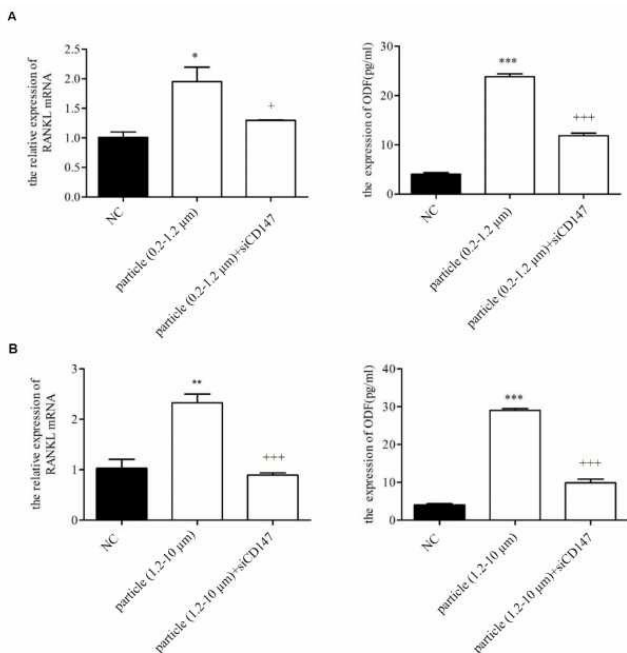


Figure 3. Effects of CD147 siRNA on mRNA and soluble protein expression of RANKL. The mRNA and soluble protein expression levels of RANKL in KG-1a cells co-cultured with CD147 siRNA and 0.2–1.2 μm (A), 1.2–10 μm (B) were detected by qPCR and ELISA respectively. NC: Normal control. **P*<0.05; ***P*<0.01; ****P*<0.001. +*P*<0.05; ++*P*<0.01; +++*P*<0.001

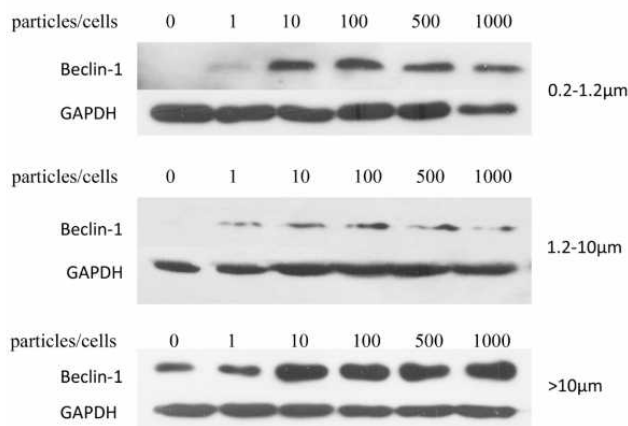


Figure 4. Effects of titanium particles on Beclin-1 protein expression. Protein levels of Beclin-1 in KG-1a cells co-cultured with 0.2–1.2 μm, 1.2–10 μm and >10 μm titanium particles were detected by western blot

(at particle count to cell count ratio of 1000:1) were selected for subsequent experiments.

To determine whether CD147 was involved in titanium particle-induced osteoclastogenesis, CD147 siRNA (si-CD147) was used to down-regulate CD147 expression during titanium particles treatment. The mRNA and soluble protein expression levels of RANKL were detected with qPCR and ELISA. As shown in Figure 3A and B, the effect of titanium particles on RANKL was indeed CD147 dependent because in cells in which CD147 was down-regulated by siRNA, titanium particles failed to stimulate both mRNA and soluble protein expression of RANKL.

Autophagy mediated wear particle-induced osteoclastogenesis

Previous studies have reported that metal particles could stimulate autophagy in osteoblasts. However, whether autophagy is involved in wear particle-induced osteoclastogenesis is unknown. Beclin-1 is fundamental for the formation of PI3K complexes, and acts at the initiation stage of autophagy. In the present study, we detected the protein expression levels of Beclin-1 in titanium particles treated KG-1a cells, and Beclin-1/GAPDH ratio was used as the indicator of autophagy. As shown in Figure 4, 0.2–1.2 μm and 1.2–10 μm titanium particles were able to robustly elevate the levels of Beclin-1. In >10 μm titanium particles treated cells, an increase of Beclin-1 was also observed, but showed no significant increase at 10:1 or higher ratios. Thus, titanium particles sized 0.2–1.2 μm (at particle count to cell count ratio of 100:1 ratio) and 1.2–10 μm (at particle count to cell count ratio of 100:1 ratio) were selected for subsequent experiments.

To investigate whether autophagy was required for titanium particle-induced osteoclastogenesis, qPCR and ELISA were performed to analyze the cells cotreated with titanium particles and autophagy inhibitor CQ. As shown in Figure 5, the up-regulation of RANKL mRNA was attenuated when the cells were treated with CQ. In addition, CQ treatment significantly suppressed the titanium particle-induced up-regulation of soluble RANKL protein in supernatants. These results suggested that autophagy was activated in response to 0.2–1.2 μm

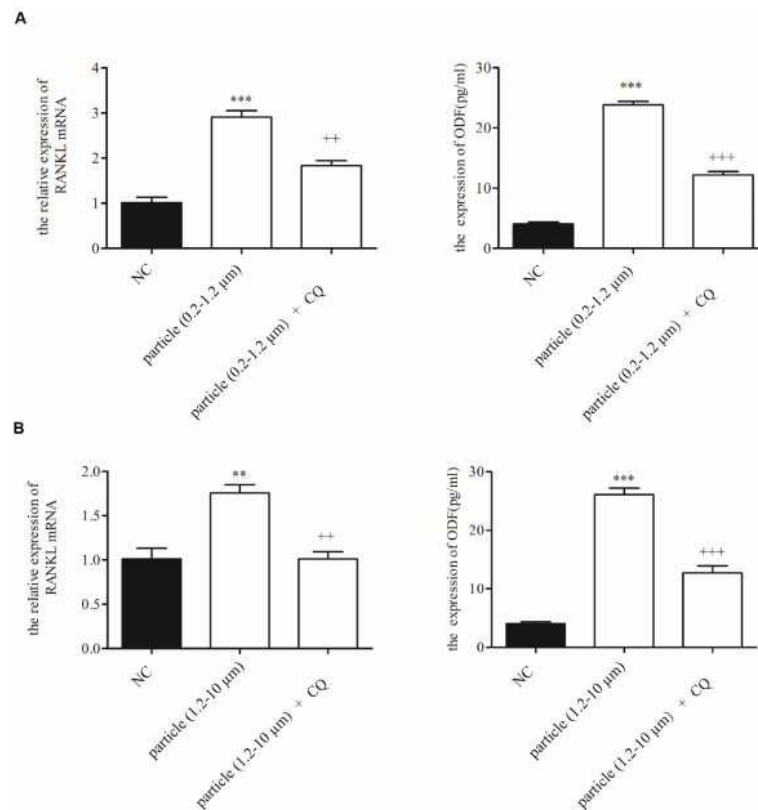


Figure 5. Effects of autophagy inhibitor CQ on mRNA and soluble protein expression of RANKL. The mRNA and soluble protein expression levels of RANKL in KG-1a cells cotreated with autophagy inhibitor CQ and 0.2-1.2 μm (A), 1.2-10 μm (B) were detected by qPCR and ELISA respectively. NC: Normal control. * $P < 0.05$; ** $P < 0.01$; *** $P < 0.001$. + $P < 0.05$; ++ $P < 0.01$; +++ $P < 0.001$

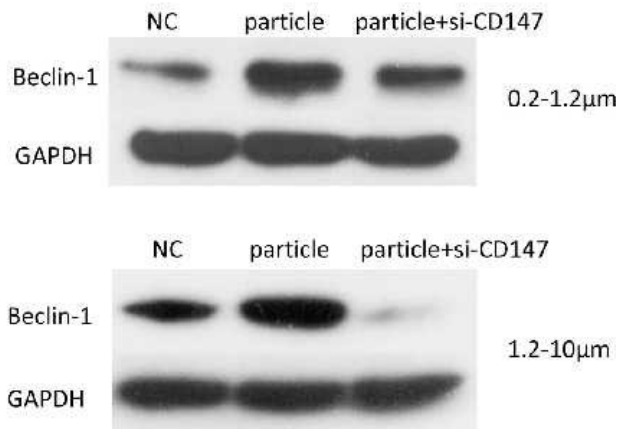


Figure 6. Effects of CD147 siRNA on Beclin-1 protein expression. Protein levels of Beclin-1 in KG-1a cells co-cultured with CD147 siRNA and 0.2-1.2 μm, 1.2-10 μm titanium particles were detected by Western blot

and 1.2-10 μm titanium particles, and involved in wear particle-induced osteoclastogenesis.

Down-regulation of CD147 suppressed wear particle-induced autophagy

Previous studies have suggested that CD147 was involved in starvation-induced autophagy in PC-3 cells. Thus, we sought to determine whether CD147 was essential for particle-induced autophagy in macrophages, the levels of Beclin-1 in siRNA and titanium particles co-treatment cells were detected via western blot. As shown in Figure 6, suppression

of CD147 significantly attenuated titanium particle-induced Beclin-1 expression. The results indicated wear particle-induced autophagy was mediated by CD147.

Discussion

Artificial joint replacement is considered as an effective treatment of end-stage joint diseases. However, wear particle-induced PIO and subsequent aseptic loosening remain the major cause of failed arthroplasty. Wear particles released from the bone-prosthesis interface are predominately phagocytosed by macrophages and alter the expression of genes in these cells, leading to the differentiation of macrophage precursors into giant cells or osteoclasts (42). RANKL regulates the osteoclast differentiation, the survival and function of mature osteoclasts. Thus, the level of RANKL is used as an indicator of how osteoclast differentiation can proceed (43). CD147 is a transmembrane glycoprotein and considered to function as an extracellular matrix metalloproteinase inducer. In the present study, we demonstrated that the size of titanium particles is a critical factor in macrophage activation. 0.2-1.2 μm and 1.2-10 μm titanium particles could increase the expression of CD147 and RANKL in KG-1a cells, inducing osteoclast differentiation. These results represented a slight reduction in the size of the most reactive particles compared with earlier studies, they were still within the phagocytosable size range identified previously to be the most biologically active (0.3-10 μm) (44). The largest (>10 μm) particles failed to stimulate the cells to produce CD147 and RANKL, which may be explained by the macrophages inability to phagocytose

the particles since they were too large. Furthermore, we showed that RANKL is a gene downstream of CD147. Knockdown of CD147 by specific siRNA mitigated the effects of titanium particles on expression of RANKL. These results suggested that titanium particles induce CD147, which may regulate RANKL, and thus promote osteoclast differentiation.

Autophagy is an evolutionarily conserved process, which is responsible for degrading and recycling protein aggregates, oxidized lipids, damaged organelles and intracellular pathogens. Factors that induce cellular stress, such as absence of nutrient, deficiency of oxygen and accumulation of oxidative stress, can activate autophagy. During initiation stage of autophagy, phagophore is formed, occurring with the formation of two multiprotein complexes: ULK1 (unc51-like autophagy activating kinase 1) protein kinase complex and the PI3KC3-C1 (class III phosphatidylinositol 3-kinase complex I) lipid kinase complex (45). Beclin-1 is fundamental for the formation of PI3K complexes and important for the initiation of autophagy (46). Numerous evidences suggests that nanomaterials can induce autophagy and inflammatory response in immune cells (47-49). Nanomaterials phagocytosed are perceived as foreign or aberrant by cells, then autophagy is activated to try to degrade foreign substances. Recently, it has been reported that an increase in autophagy occurs during osteoclastogenesis, and pharmacological and genetic inhibition of autophagy reduces osteoclastogenesis and bone resorption in mice (32). In this study, we showed that 0.2–1.2 μm and 1.2–10 μm titanium particles could elevate the levels of Beclin-1 to promote the formation of autophagosome. Moreover, with the autophagy inhibitor CQ, we uncovered that autophagy mediates the up-regulation of RANKL induced by titanium particles. These results implied 0.2–1.2 μm and 1.2–10 μm titanium particles could be phagocytosed by macrophages, and activate autophagy, leading to up-regulation of RANKL. The largest (>10 μm) particles showed more biocompatible, since they are too large to be phagocytosed.

CD147 is highly expressed on the cell surface of most of cancer cells, and promotes tumor invasion, metastasis and growth. Several researches show that CD147 is associated with autophagy in epithelial ovarian cancer cells (50), prostate cancer cells (51) and hepatocellular carcinoma (37). In present study, with the siRNA against CD147, we revealed that CD147 mediate the wear particle-induced autophagy.

Conclusions

The present study suggested that 0.2–1.2 μm and 1.2–10 μm titanium particles showed more biologically activity than >10 μm particles, and CD147 played a key role in autophagy and wear particle-induced osteoclastogenesis. Our results demonstrated that 0.2–1.2 μm and 1.2–10 μm titanium particles could stimulate the expression of CD147 to enhance autophagy, promoting osteoclastogenesis. More importantly, down-regulation of CD147 resulted in the significant decrease of autophagy and soluble RANKL protein in supernatants that were induced by 0.2–1.2 μm and 1.2–10 μm titanium particles. Our findings suggested a possible

mechanism underlying wear debris-induced osteolysis and identified CD147 as a potential therapeutic target in aseptic loosening.

Acknowledgement

This work was supported by Science and Technology Planning Project of Guangdong Province, China (2013B051000024, 2014A020212060, 2014A020215009), and the Science and Technology Planning Project of Guangzhou City, China (201803010011).

Conflict of Interest

The authors declare no conflict of interest.

References

- Urban RM, Hall DJ, Della Valle C, Wimmer MA, Jacobs JJ, Galante JO. Successful long-term fixation and progression of osteolysis associated with first-generation cementless acetabular components retrieved post mortem. *J Bone Joint Surg Am* 2012; 94:1877-1885.
- Athanasou NA. The pathobiology and pathology of aseptic implant failure. *Bone Joint Res* 2016; 5:162-168.
- Goodman SB. Wear particles, periprosthetic osteolysis and the immune system. *Biomaterials* 2007; 28:5044-5048.
- Hallab NJ, Jacobs JJ. Biologic effects of implant debris. *Bull NYU Hosp Jt Dis* 2009; 67:182-188.
- Crotti TN, Smith MD, Findlay DM, Zreiqat H, Ahern MJ, Weedon H, *et al.* Factors regulating osteoclast formation in human tissues adjacent to peri-implant bone loss: expression of receptor activator NF κ B, RANK ligand and osteoprotegerin. *Biomaterials* 2004; 25:565-573.
- Shen Z, Crotti TN, McHugh KP, Matsuzaki K, Gravalles EM, Bierbaum BE, *et al.* The role played by cell-substrate interactions in the pathogenesis of osteoclast-mediated peri-implant osteolysis. *Arthritis Res Ther* 2006; 8:R70.
- King S, Waddell JE, Boynton EL. Changes in macrophage morphology and prolonged cell viability following exposure to polyethylene particulate *in vitro*. *Microsc Res Tech* 2002; 57:523-529.
- Yagil-Kelmer E, Kazmier P, Rahaman MN, Bal BS, Tessman RK, Estes DM. Comparison of the response of primary human blood monocytes and the U937 human monocytic cell line to two different sizes of alumina ceramic particles. *J Orthop Res* 2004; 22:832-838.
- Wimhurst JA, Brooks RA, Rushton N. Inflammatory responses of human primary macrophages to particulate bone cements *in vitro*. *J Bone Joint Surg Br* 2001; 83:278-282.
- Ingham E, Green TR, Stone MH, Kowalski R, Watkins N, Fisher J. Production of TNF-alpha and bone resorbing activity by macrophages in response to different types of bone cement particles. *Biomaterials* 2000; 21:1005-1013.
- Merkel KD, Erdmann JM, McHugh KP, Abu-Amer Y, Ross FP, Teitelbaum SL. Tumor necrosis factor-alpha mediates orthopedic implant osteolysis. *Am J Pathol* 1999; 154:203-210.
- Ingham E, Fisher J. The role of macrophages in osteolysis of total joint replacement. *Biomaterials* 2005; 26:1271-1286.
- Nine MJ, Choudhury D, Hee AC, Mootanah R, Osman NAA. Wear debris characterization and corresponding biological response: artificial hip and knee joints. *Materials (Basel)* 2014; 7:980-1016.
- Sabokbar A, Fujikawa Y, Neale S, Murray DW, Athanasou NA. Human arthroplasty derived macrophages differentiate into osteoclastic bone resorbing cells. *Ann Rheum Dis* 1997; 56:414-420.
- Sabokbar A, Pandey R, Athanasou NA. The effect of particle size and electrical charge on macrophage-osteoclast differentiation and bone resorption. *J Mater Sci Mater Med* 2003; 14:731-738.

16. Bi Y, Van De Motter RR, Ragab AA, Goldberg VM, Anderson JM, Greenfield EM. Titanium particles stimulate bone resorption by inducing differentiation of murine osteoclasts. *J Bone Joint Surg Am* 2001; 83-a:501-508.
17. Ren W, Yang SY, Fang HW, Hsu S, Wooley PH. Distinct gene expression of receptor activator of nuclear factor-kappaB and rank ligand in the inflammatory response to variant morphologies of UHMWPE particles. *Biomaterials* 2003; 24:4819-4826.
18. Childs LM, Paschalis EP, Xing L, Dougall WC, Anderson D, Boskey AL, et al. In vivo RANK signaling blockade using the receptor activator of NF-kappaB: Fc effectively prevents and ameliorates wear debris-induced osteolysis via osteoclast depletion without inhibiting osteogenesis. *J Bone Miner Res* 2002; 17:192-199.
19. Granchi D, Amato I, Battistelli L, Ciapetti G, Pagani S, Avnet S, et al. Molecular basis of osteoclastogenesis induced by osteoblasts exposed to wear particles. *Biomaterials* 2005; 26:2371-2379.
20. Xing L, Xiu Y, Boyce BF. Osteoclast fusion and regulation by RANKL-dependent and independent factors. *World J Orthop* 2012; 3:212-222.
21. Asagiri M, Takayanagi H. The molecular understanding of osteoclast differentiation. *Bone* 2007; 40:251-264.
22. Maiuri MC, Kroemer G. Autophagy in stress and disease. *Cell Death Differ* 2015; 22:365-366.
23. Levine B, Klionsky DJ. Development by self-digestion: molecular mechanisms and biological functions of autophagy. *Dev Cell* 2004; 6:463-477.
24. Cuervo AM. Autophagy and aging: keeping that old broom working. *Trends Genet* 2008; 24:604-612.
25. Zhang H, Baehrecke EH. Eaten alive: novel insights into autophagy from multicellular model systems. *Trends Cell Biol* 2015; 25:376-387.
26. Pierrefite-Carle V, Santucci-Darmanin S, Breuil V, Camuzard O, Carle GF. Autophagy in bone: Self-eating to stay in balance. *Ageing Res Rev* 2015; 24:206-217.
27. Hocking LJ, Whitehouse C, Helfrich MH. Autophagy: a new player in skeletal maintenance?. *J Bone Miner Res* 2012; 27:1439-1447.
28. Shapiro IM, Layfield R, Lotz M, Settembre C, Whitehouse C. Boning up on autophagy: the role of autophagy in skeletal biology. *Autophagy* 2014; 10:7-19.
29. Zhao Y, Chen G, Zhang W, Xu N, Zhu JY, Jia J, et al. Autophagy regulates hypoxia-induced osteoclastogenesis through the HIF-1alpha/BNIP3 signaling pathway. *J Cell Physiol* 2012; 227:639-648.
30. DeSelm CJ, Miller BC, Zou W, Beatty WL, van Meel E, Takahata Y, et al. Autophagy proteins regulate the secretory component of osteoclastic bone resorption. *Dev Cell* 2011; 21:966-974.
31. Daroszewska A, van't Hof RJ, Rojas JA, Layfield R, Landao-Basonga E, Rose L, et al. A point mutation in the ubiquitin-associated domain of SQSM1 is sufficient to cause a Paget's disease-like disorder in mice. *Hum Mol Genet* 2011; 20:2734-2744.
32. Lin NY, Chen CW, Kagwiria R, Liang R, Beyer C, Distler A, et al. Inactivation of autophagy ameliorates glucocorticoid-induced and ovariectomy-induced bone loss. *Ann Rheum Dis* 2016; 75:1203-1210.
33. Wang Z, Liu N, Liu K, Zhou G, Gan J, Wang Z, et al. Autophagy mediated CoCrMo particle-induced peri-implant osteolysis by promoting osteoblast apoptosis. *Autophagy* 2015; 11:2358-2369.
34. Kanekura T, Miyauchi T, Tashiro M, Muramatsu T. Basigin, a new member of the immunoglobulin superfamily: genes in different mammalian species, glycosylation changes in the molecule from adult organs and possible variation in the N-terminal sequences. *Cell Struct Funct* 1991; 16:23-30.
35. Huet E, Vallee B, Szul D, Verrecchia F, Mourah S, Jester JV, et al. Extracellular matrix metalloproteinase inducer/CD147 promotes myofibroblast differentiation by inducing alpha-smooth muscle actin expression and collagen gel contraction: implications in tissue remodeling. *Faseb j* 2008; 22:1144-1154.
36. Gabison EE, Hoang-Xuan T, Mauviel A, Menashi S. EMMPRIN/CD147, an MMP modulator in cancer, development and tissue repair. *Biochimie* 2005; 87:361-368.
37. Wu B, Cui J, Yang XM, Liu ZY, Song F, Li L, et al. Cytoplasmic fragment of CD147 generated by regulated intramembrane proteolysis contributes to HCC by promoting autophagy. *Cell Death Dis* 2017; 8:e2925.
38. Rucci N, Millimaggi D, Mari M, Del Fattore A, Bologna M, Teti A, et al. Receptor activator of NF-kappaB ligand enhances breast cancer-induced osteolytic lesions through upregulation of extracellular matrix metalloproteinase inducer/CD147. *Cancer Res* 2010; 70:6150-6160.
39. Nishioku T, Terasawa M, Baba M, Yamauchi A, Kataoka Y. CD147 promotes the formation of functional osteoclasts through NFATc1 signalling. *Biochem Biophys Res Commun* 2016; 473:620-624.
40. Huang JB, Ding Y, Huang DS, Zeng WK, Guan ZP, Zhang ML. RNA interference targeting p110beta reduces tumor necrosis factor-alpha production in cellular response to wear particles in vitro and osteolysis in vivo. *Inflammation* 2013; 36:1041-1054.
41. Bu YM, Zheng DZ, Wang L, Liu J. Abrasive endoprosthetic wear particles inhibit IFN-gamma secretion in human monocytes via upregulating TNF-alpha-induced miR-29b. *Inflammation* 2017; 40:166-173.
42. Purdue PE, Koulouvaris P, Nestor BJ, Sculco TP. The central role of wear debris in periprosthetic osteolysis. *Hss j* 2006; 2:102-113.
43. Boyce BF, Xing L. Functions of RANKL/RANK/OPG in bone modeling and remodeling. *Arch Biochem Biophys* 2008; 473:139-146.
44. Green TR, Fisher J, Stone M, Wroblewski BM, Ingham E. Polyethylene particles of a 'critical size' are necessary for the induction of cytokines by macrophages in vitro. *Biomaterials* 1998; 19:2297-2302.
45. Florencio-Silva R, Sasso GR, Simoes MJ, Simoes RS, Baracat MC, Sasso-Cerri E, et al. Osteoporosis and autophagy: What is the relationship?. *Rev Assoc Med Bras (1992)* 2017; 63:173-179.
46. Fu LL, Cheng Y, Liu B. Beclin-1: autophagic regulator and therapeutic target in cancer. *Int J Biochem Cell Biol* 2013; 45:921-924.
47. Hussain S, Al-Nsour F, Rice AB, Marshburn J, Yingling B, Ji Z, et al. Cerium dioxide nanoparticles induce apoptosis and autophagy in human peripheral blood monocytes. *ACS Nano* 2012; 6:5820-5829.
48. Stern ST, Adisheshaiah PP, Crist RM. Autophagy and lysosomal dysfunction as emerging mechanisms of nanomaterial toxicity. *Part Fibre Toxicol* 2012; 9:20.
49. Nel A, Xia T, Madler L, Li N. Toxic potential of materials at the nanolevel. *Science* 2006; 311:622-627.
50. Hu Z, Cai M, Deng L, Zhu L, Gao J, Tan M, et al. The fucosylated CD147 enhances the autophagy in epithelial ovarian cancer cells. *Oncotarget* 2016; 7:82921-82932.
51. Fang F, Wang L, Zhang S, Fang Q, Hao F, Sun Y, et al. CD147 modulates autophagy through the PI3K/Akt/mTOR pathway in human prostate cancer PC-3 cells. *Oncol Lett* 2015; 9:1439-1443.