



Citation for published version:

Raithby, P, Hatcher, L, Skelton, J & Warren, MR 2019, 'Photocrystallographic Studies on Transition Metal Nitrito Metastable Linkage Isomers: Manipulating the Metastable State', *Accounts of Chemical Research*, vol. 52, no. 4, pp. 1079-1088. <https://doi.org/10.1021/acs.accounts.9b00018>

DOI:

[10.1021/acs.accounts.9b00018](https://doi.org/10.1021/acs.accounts.9b00018)

Publication date:

2019

Document Version

Peer reviewed version

[Link to publication](#)

Publisher Rights

CC BY

This document is the Accepted Manuscript version of a Published Work that appeared in final form in *Accounts of Chemical Research*, copyright © American Chemical Society after peer review and technical editing by the publisher. To access the final edited and published work see <https://pubs.acs.org/doi/10.1021/acs.accounts.9b00018>

University of Bath

General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

Take down policy

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

Photocrystallographic Studies on Transition Metal Nitrito Metastable Linkage Isomers: Manipulating the Metastable State

Lauren E. Hatcher,[†] Jonathan M. Skelton,[‡] Mark R Warren[§] and Paul R. Raithby[†]

[†]Department of Chemistry, University of Bath, Bath BA2 7AY, UK

[‡]School of Chemistry, University of Manchester, Oxford Road, Manchester M19 3PL, UK

[§]Research Complex at Harwell, Rutherford Appleton Laboratory, Harwell Oxford, Didcot, Oxfordshire OX11 0FA, UK

CONSPECTUS: The design of solid-state materials whose properties and functions can be manipulated in a controlled manner by the application of light, is an important objective in modern materials chemistry. When the material changes property or function, it is helpful if a simple measurable response, such as a change in color, can be detected. Potential applications for such materials are wide ranging, from data storage to smart windows. With the growing emphasis on solid-state materials that have two or more accessible energy states and which exhibit bistability, attention has turned to



transition metal complexes that contain ambidentate ligands that can switch between linkage isomeric forms when activated by light. Suitable ligands that show promise in this area include nitrosyls, nitro groups and coordinated sulfur dioxide molecules, each of which can coordinate to a metal center in more than one bonding mode. A nitrosyl normally coordinates through its N-atom (η^1 -NO) but when photoactivated can undergo isomerism and coordinate through its O atom (η^1 -ON). At a molecular level converting between these two configurations can act as an “on/off” switch. The analysis of such materials has been aided by the development of photocrystallographic techniques which allow the full three-dimensional structure of a single-crystal of a complex, under photoactivation, to be determined, when it is in either a metastable or short-lived excited state. The technique effectively brings the dimension of “time” to the crystallographic experiment, and brings us closer to being able to watch solid-state processes occur in real time.

In this Account we highlight the advances made in photocrystallography for studying solid-state, photoactivated linkage isomerism, and describe the factors that favor the switching process and which allow complete switching between isomers. We demonstrate that control of temperature is key to achieving either a metastable state or an excited state with a specific lifetime. We draw our conclusions from published work on the formation of photoactivated metastable states for nitrosyl and sulfur dioxide complexes and from our own work on photoactivated switching between nitro and nitrito groups. We show that efficient switching between isomers is dependent on the wavelength of light used, on the temperature at which the experiment is carried out, on the flexibility of the crystal lattice and both the electronic and steric environment of the ambidentate ligand undergoing isomerism. We have designed and prepared a number of nitro/nitrito isomeric metal complexes that undergo reversible 100% conversion between the two forms at temperatures close to room temperature. Through our fine control over the generation of the metastable states it should be possible to effectively “dial up” a suitable temperature to give a metastable or an excited state with a desired lifetime.

INTRODUCTION

Modern solid-state photochemistry commenced in the 1960s with the pioneering work of Cohen & Schmidt on irreversible [2+2] photodimerizations of *trans*-cinnamic acids which provided the impetus for much of the work that has followed.¹ Their *Topochemical Postulate* proposed that because of the restrictions imposed by the crystal lattice the reaction will follow a minimum energy pathway, undergoing the smallest amount of atomic movement possible in order to preserve the crystalline environment. The precept of the stabilizing effect of the crystal lattice has remained at the center of solid-state photochemistry ever since although the idea is largely qualitative. Later, Cohen introduced the idea of the *reaction cavity* as a more quantitative means of defining the changes that occur within a crystal as a result of photoactivation.² Since molecules that will directly undergo a solid-state photochemical reaction occupy a space of a certain size and shape in the starting crystal, the *reaction cavity* can be defined as the contact surface of molecules within the cavity with surrounding molecules in the crystal lattice. The *topochemical postulate* can then be interpreted to mean that reactions that occur under lattice control do so with minimal distortion of the surface of the *reaction cavity*. Ohashi subsequently showed that the *reaction cavity* displayed flexibility through the process of the reaction, and that changes in temperature could significantly affect the reaction; lowering the temperature causing lattice contraction, reducing the *cavity* size and thus “switching off” the reaction.³

In order to understand the mechanism of reactions in the solid state it would be enormously useful to watch reactions as they occur and to “see” the reaction intermediates in real time, using single-crystal crystallographic techniques, where the full three-dimensional picture of the structure is obtained. This was not possible in the early developments of the field of solid state photochemistry and only the structures of the starting material and reaction products could be determined.¹ However, since then many technological developments including the availability of high-intensity X-ray synchrotron⁴⁻⁶ sources, cryogenic technologies,^{7,8} high-power lasers⁹ and increased computing power, have made the study of solid-state chemical processes in real time, using crystallographic methods, a possibility. The term *photocrystallography* was coined by Coppens to mean the determination of the full three-dimensional structure of a molecule in a metastable or ES generated by light irradiation.^{10,11} The original definition was applied to single-crystal X-ray diffraction studies under photoactivation. However, the term is now loosely used to refer to photoactivated time-resolved single-crystal and powder diffraction studies where the ES species has a finite lifetime (minutes to picoseconds) or is metastable, in that there is no discernible decay of the ES species over the lifetime of the crystallographic experiment.^{12,13} The ES lifetime is temperature dependent, with the lifetime increasing continuously as the measurement temperature is reduced.¹⁴ The term *metastable limit* is used generally to describe a critical temperature above which the ES lifetime is shorter than the measurement timescale. For the *photocrystallographic* experiments described in this account we focus on single-crystal studies in which the processes are reversible, either with the excited state (ES) decaying back to the ground state (GS) in a short time, or when the temperature is raised above the *metastable limit*.


A. MOLECULAR PHOTOCRYSTALLOGRAPHY

The pioneering work on molecular *photocrystallography* was carried out by Coppens. He applied *photocrystallographic* methods to linkage isomers, these are coordination complexes that contain ambidentate ligands that can coordinate to the metal center in more than one coordination mode. Examples of these ligands include: nitrosyl groups (NO), which can coordinate through either the nitrogen atom or the oxygen atom; nitro groups (NO₂), which can also coordinate either through the nitrogen or one or both of the oxygen atoms; sulfur dioxide (SO₂) which can coordinate to the metal through either the sulfur or one of the oxygen atoms (Fig. 1). Crystallographic studies on these ligands are straightforward to carry out since their coordination modes change upon isomerization and the new atom positions are identifiable in electron density difference maps even if only partial isomerization occurs. Additionally, the ligands act as good reporter ligands in IR spectroscopy with


changes in the $\nu(\text{N-O})$ and $\nu(\text{S-O})$ stretches and the $\delta(\text{O-N-O})$ and $\delta(\text{O-S-O})$ bends providing very useful complementary information to the *photocrystallographic* studies.^{15,16}

The existence of complexes that display linkage isomerism in solution was established by Jørgensen¹⁷ in the late 19th Century. While the first linkage isomeric species were isolated by changing the reaction conditions to favor one isomer over another, conversion between the isomers could be achieved by applying energy from an external source, *e.g.* heat or light. Later spectroscopic studies indicated that the isomerization process occurred in the solid state, particularly if the structural rearrangements were modest.

(a) Nitrosyls

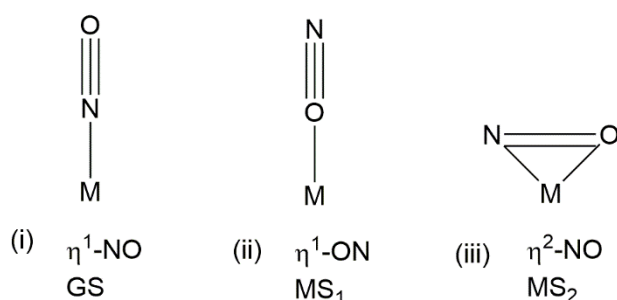

(b) Sulfur dioxide

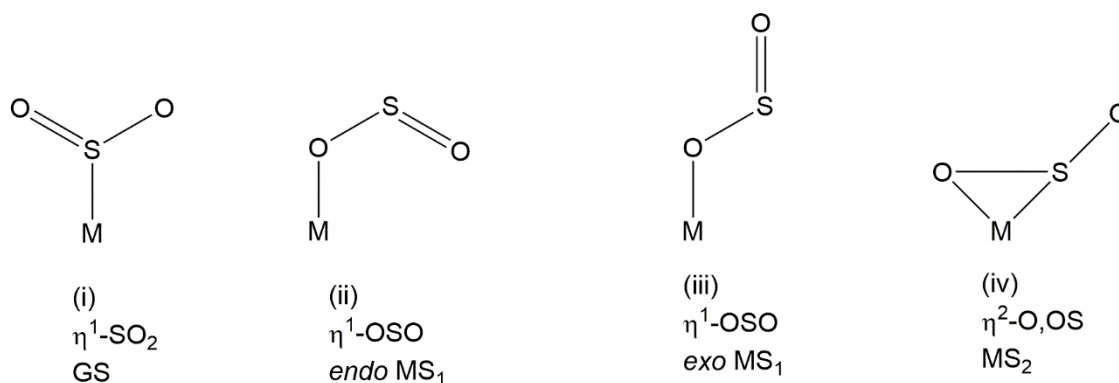

(c) Nitro/nitrito

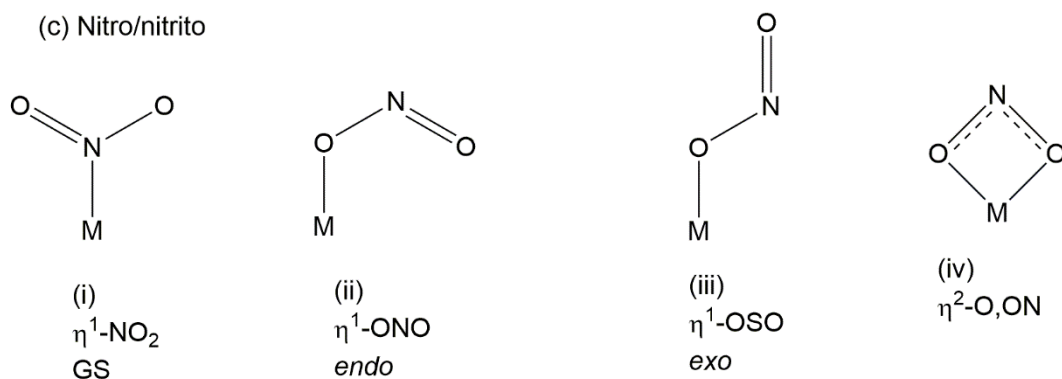


Figure 1. Selected isomeric configurations for (a) nitrosyls, (b) sulfur dioxide, and (c) nitro/nitrito ligands.

The fact that linkage isomerism occurs in the solid state inspired the idea that, with their two stable equilibrium states, these compounds might act as solid-state molecular switches with one isomer representing the “on” position and the other in the “off” position. This possibility suggests applications as photochromic and photorefractive materials for use in nonlinear optics and

holographic data storage,¹⁸⁻²⁰ as well as in developing a better understanding of processes such as light-induced NO-release²¹ for photodynamic therapy.²²

In this Account we highlight the advances in *photocrystallographic* studies of metastable linkage isomers and discuss the factors that allow us to manipulate the metastable state of transition metal nitrito complexes.

B. PHOTOCRYSTALLOGRAPHIC STUDIES ON NITROSYL AND SULFUR DIOXIDE LINKAGE ISOMERS

Initial solid-state studies on linkage isomerization involved sodium nitroprusside (SNP). Mössbauer spectroscopy was used to identify the presence of two unexpectedly long-lived isomers when a sample of SNP was irradiated with light.²³ The photoactivated isomers were metastable (MS) at cryogenic temperatures, which is a given isomer is stable indefinitely at low temperatures but returns to the original GS structure upon warming. A satisfactory explanation for the existence of two metastable isomers for SNP could not be resolved fully until Coppens carried out the first *photocrystallographic* study in 1997.¹¹ He established that photoactivation of SNP resulted in a change in the coordination mode of the NO ligand. Irradiation of a single-crystal using 488 nm light, at 50 K, resulted in a 37% conversion from the GS (η^1 -NO) form to a metastable form in which the nitrosyl had inverted its coordination mode to link through the oxygen (η^1 -ON) (Fig. 2). This isomer was designated MS₁. The ligand rearrangement was identified from an analysis of the anisotropic displacement parameters of the nitrosyl N and O atoms in the metastable state; they became more physically reasonable when the atomic scattering factors were reversed to give the isonitrosyl form. Subsequently, the same crystal, in the MS₁ state, was exposed to 1064 nm light, still at 50 K, and conversion to a new side-on bound isomer (η^2 -NO), designated MS₂, occurred. This isomer could be observed at a 10% conversion level.

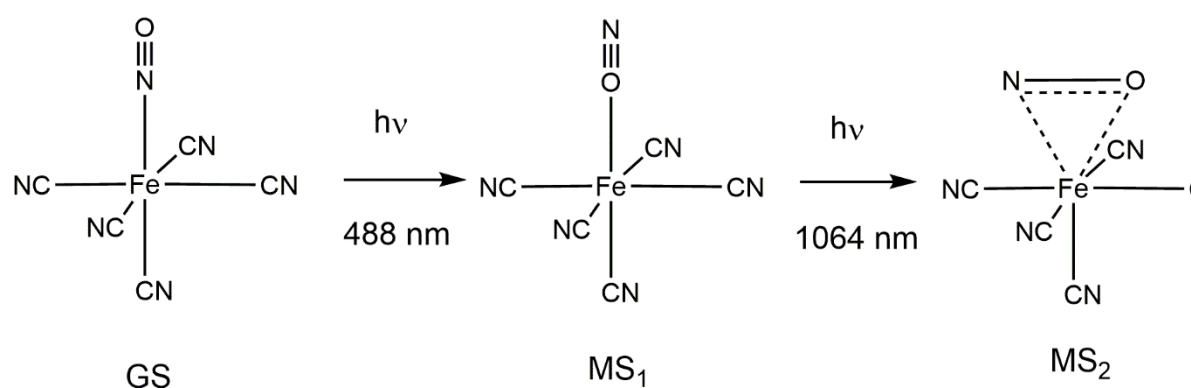


Figure 2. Solid-state linkage isomerism in the SNP anion. The GS η^1 -NO nitrosyl transforms to the η^1 -ON isonitrosyl and then to the η^2 -NO side-bound isomer.

Coppens expanded the range of ruthenium nitrosyl complexes that showed the formation of metastable linkage isomers under photoactivation, at low temperatures, in the solid state.²⁴⁻²⁶ All the systems showing evidence of the presence of the MS₁ and MS₂ species. He also showed that other metal nitrosyls exhibited photoactivated linkage isomerism,²⁷ and that dinitrogen ligands displayed “end-on” (η^1 -N₂) and metastable “side-on” (η^2 -N₂) isomers when irradiated at low temperature with 325 nm light.²⁸

In a parallel series of studies Schaniel and Woike extended the range of photoactive ruthenium nitrosyl and iron nitrosyl linkage isomers studied using powder and single-crystal X-ray diffraction studies coupled with detailed IR and DSC measurements and underpinned by computational studies. Their objective was to establish the factors that governed the level of interconversion between the ground and metastable states. All the systems studied essentially showed the presence of the (η^1 -ON) (MS₁) and (η^2 -NO) (MS₂) states under different illumination conditions, at different temperatures.

However, conversion levels were generally low in the solid state, below 50%. One exception is a *photocrystallographic* analysis of $[\text{RuCl}(\text{py})_4(\text{NO})][\text{PF}_6]_2 \cdot 0.5\text{H}_2\text{O}$ using laser light of 673 nm, at 80 K, which gave a 92% conversion to MS_1 that could then be converted to 48% of MS_2 using 980 nm light (Fig. 3).²⁹ Because of the high conversion obtained in this system a series of related complexes, with the general formula $[\text{RuX}(\text{py})_4(\text{NO})][\text{Y}]_2 \cdot n\text{H}_2\text{O}$ with different halide, pyridine ligands and counterions were studied and the results from *photocrystallography* and IR studies compared. The results showed that the shorter the distance between the counterion and the NO ligand in the GS structure the higher is the population of the photoinduced metastable state obtained. This suggests that the contacts between the counterion and the NO ligand are reduced in the metastable state reducing unfavorable packing effects within the crystal. It was also established that the lower the donating character of the ligand *trans* to the NO ligand the higher is the photoconversion yield.³⁰

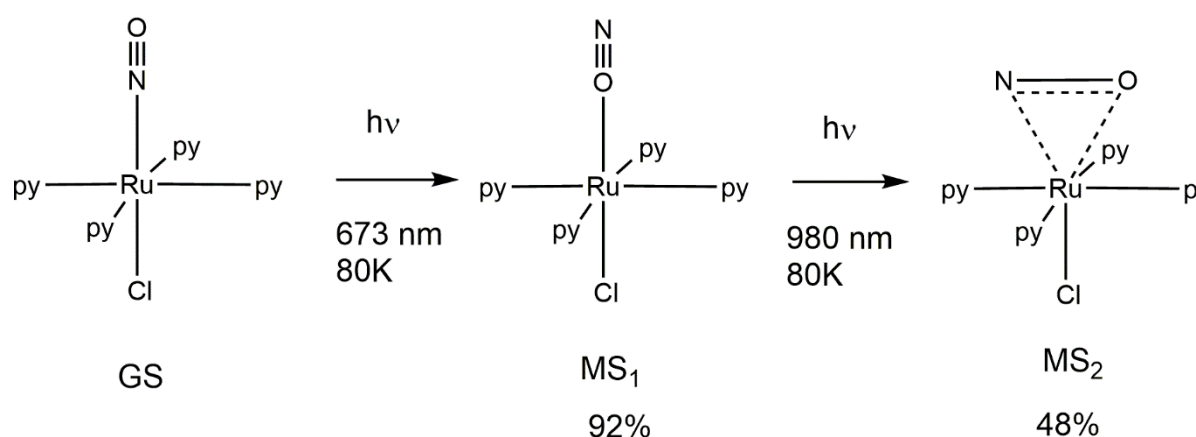


Figure 3. Photoactivated linkage isomerism in $[\text{RuCl}(\text{py})_4(\text{NO})][\text{PF}_6]_2 \cdot 0.5\text{H}_2\text{O}$ showing the MS_1 and MS_2 isomers

Another ambidentate ligand that has been studied *photocrystallographically* is sulfur dioxide. SO_2 can coordinate to a metal center as illustrated in Fig. 1. The most common coordination mode is $\eta^1\text{-SO}_2$ (Fig. 1(b), (i)) with the central sulfur atom bonded to the metal. The first evidence for linkage isomerism in transition metal SO_2 complexes came from spectroscopic studies carried out by Johnson and Drew.³¹ In solution-based photochemical IR studies on *trans*- $[\text{Ru}(\text{NH}_3)_4\text{Cl}(\text{SO}_2)]\text{Cl}$ and they observed changes in the $\nu(\text{SO}_2)$ upon irradiation with 365 nm light, at 195 K. They attributed these changes to the formation of a photoexcited, metastable, side-bound $\eta^2\text{-(O,SO)}$ isomer (Fig. 1(b), (iv)) which was later designated as MS_2 , to be consistent with the side-bound nitrosyl species described above.

The first crystallographic evidence for the side-bound $\eta^2\text{-(O,SO)}$ linkage isomer was obtained in 2002 when Coppens obtained the structure of the MS_2 isomer from a steady-state *photocrystallographic* study on *trans*- $[\text{Ru}(\text{NH}_3)_4\text{Cl}(\text{SO}_2)]\text{Cl}$ using 300-500 nm light at 150 K.^{32,33} The first *photocrystallographic* observation of a second type of SO_2 linkage isomerism occurred in 2006 when Bowes confirmed the presence of a bent $\eta^1\text{-OSO}$ isomer (Fig. 1(b), (ii)) in $[\text{Ru}(\text{NH}_3)_4(\text{H}_2\text{O})(\text{SO}_2)][\text{MeC}_6\text{H}_4\text{SO}_3]_2$ at 13 K, with a maximum conversion level of 36%.³⁴ This isomer was designated MS_1 by analogy to the $\eta^1\text{-ON}$ arrangement of the nitrosyl ligand.

Photocrystallographic studies on ruthenium-sulfur dioxide complexes were extended to systems with a series of different ligands *trans* to the coordinated SO_2 group and a range of counterions. These showed that the side-bound $\eta^2\text{-(O,SO)}$ isomer was readily formed with the bent $\eta^1\text{-OSO}$ isomer (MS_1) appearing at temperatures below 130 K. The isomerisations were strongly influenced by the environment around the SO_2 group, and by the electronic properties of the metal and the *trans* ligand.^{32,33,35,36} Again, conversion levels were generally below 50%.

One of the main reasons for undertaking *photocrystallographic* studies on transition metal linkage isomers is to produce new functional materials for “real world” applications. The

crystallographic studies act as benchmarks for the design of polycrystalline or amorphous materials. An obvious application for materials that can undergo photoactivated linkage isomerism is in the optoelectronics industry. Opto-electronic materials can provide light of desired wavelengths and provide binary data storage through their ability to exist in switchable “on/off” states, with, in principle, access to these applications at the molecular level.³⁷ In this context photoswitchable hybrid materials have been prepared successfully by embedding guanidinium nitroprusside (GuNP, $(\text{CN}_3\text{H}_6)_2[\text{Fe}(\text{CN})_5(\text{NO})]$) into the mesopores of xerogel monoliths. Irradiation of the structures with blue-green light results in 15% conversion of the ($\eta^1\text{-NO}$) isomer into the ($\eta^1\text{-ON}$) isomer.³⁸ The “fingerprint” of the embedded complex was confirmed by the analysis of neutron powder diffraction data.³⁹ The effect of the particle size of SNP embedded in silica xerogels has also been investigated using powder diffraction, absorption and IR spectroscopy. The electronic structure and the activation energies of the metastable isomers appear to be independent of particle size down to a single isolated molecule.⁴⁰

Sulfur dioxide metastable linkage isomers have also shown promise as functional materials. In $[\text{Ru}(\text{NH}_3)_4(\eta^1\text{-SO}_2)(3\text{-Cl-pyridine})][\text{tosylate}]_2$ a phototriggered molecular rotation of one of the counterion tosylate phenyl rings occurs, which can be described as a nanomechanical transduction. The decay of this anionic molecular rotor follows a non-traditional decay path.⁴¹ The complex $[\text{Ru}(\text{NH}_3)_4(\text{H}_2\text{O})(\text{SO}_2)][\text{MeC}_6\text{H}_4\text{SO}_3]_2$ which exhibits the side-on ($\eta^2\text{-OSO}$) coordination mode at temperatures between 100–250 K³⁴ has been incorporated into a polyvinyl alcohol (PVA) polymer host. This was achieved by the *in situ* reaction of *trans*- $[\text{Ru}(\text{NH}_3)_4(\text{SO}_2)\text{Cl}]\text{Cl}$ and *p*-toluenesulfonic acid in the PVA matrix, and an *in situ* precipitating crystallization. Transmission electron microscopy, diffraction and UV-vis spectroscopy indicated that the photoactivated linkage isomerization was uncompromised by inclusion in polymer thin films.⁴² The size of the crystallites were optimized within the polymer, having dimensions between 1-10 microns.

C. FACTORS FAVOURING THE FORMATION OF SOLID STATE METASTABLE LINKAGE ISOMERS

An analysis of the data obtained on the NO and SO₂ linkage isomers indicates that there are many complementary and opposing factors that determine whether or not linkage isomerism will occur in the solid state under photoactivation.

- 1) The isomerization is strongly dependent on the wavelength of light used, as has been seen for several of the systems,^{11,34} changing the wavelength causes one metastable state, *e.g.* ($\eta^1\text{-ON}$), to convert to another, *e.g.* ($\eta^2\text{-NO}$), or to revert to the GS.
- 2) The isomerization is also highly temperature dependent, with the metastable isomer reverting to the GS above a certain temperature, and there is a temperature range in which the ES has a finite lifetime.
- 3) For the isomerization to occur, the environment around the ligand undergoing the transformation is of key importance. There must be enough flexibility in the crystal lattice for the ligand to move and intermolecular interactions between the ligand and surrounding groups should not be strong. There is compelling evidence for this in the $[\text{RuX}(\text{py})_4(\text{NO})][\text{Y}]_2 \cdot n\text{H}_2\text{O}$ ³⁰ and $[\text{Ru}(\text{SO}_2)(\text{NH}_3)_4\text{X}]\text{Y}$ ³⁵ series investigated.
- 4) When considering single-crystal *photocrystallographic* studies, the GS and metastable structures need to be determined, so the isomerization must involve a single-crystal to single-crystal transformation. Therefore, the change in the unit cell dimension must be small so that little strain is placed on the crystal lattice. In all the examples discussed above the maximum change in cell volume is *ca.* 2%.
- 5) Electronic factors are also important in determining whether or not isomerization occurs. To trigger the photoconversion in the linkage isomers a metal-to-ligand charge transfer (MLCT) or a $d \rightarrow d$ transition must occur to change the bond between the ligand and the metal. This is usually assigned to a $\text{M}(d) \rightarrow \pi^*(\text{L})$ or a $\text{M}(d) \rightarrow d_{z^2}$ transition which changes the σ -bonding to the metal.⁴³
- 6) In terms of the energy surface of the transformation, the ES potential must exhibit a minimum close to the saddle point of the GS surface between the ground and metastable states, or a

cross surface, such that the relaxation from an ES into the metastable state can occur (Fig. 4).⁴³

- 7) Since the ground and metastable states will be formally in an equilibrium, depending on factors such as temperature and illumination, the depletion rate of the metastable state must be smaller than its population rate for the metastable state to be maintained.
- 8) One of the issues identified is the difficulty in achieving 100% conversion to one or more of the metastable states within the single-crystal. The majority of excitation levels are below 50%. In addition to points (1), (2), (3), (5), (6) and (7) above incomplete excitation may be caused by the penetration depth of the light used to photoactivate the crystals which is of course linked to their size. Light absorbed by the surface layers cannot be transmitted onwards and so is not available to excite molecules deeper in the crystal. Typically, single-crystals for these experiments have volumes between 0.001 – 0.06 mm³. While X-rays will pass through crystals of this size the light may be stopped within a few nm of the crystal surface if the wavelength of light used is close to the absorption λ_{\max} which for materials with strong charge transfer bands may have extinction coefficients that exceed 50,000 L mol⁻¹ cm⁻¹. This problem can be reduced if the irradiation wavelength is chosen to be in the tail of the absorption peak and then the absorption coefficients are reduced below 20 L mol⁻¹ cm⁻¹. In the successful experiments where high conversions occur light of a wavelength in the absorption tail has been used. Lack of penetration also depends on the relative positions of the absorption bands of the GS and ES molecules, since the ES species may absorb the same wavelengths as the GS complex, preventing light from penetrating the crystal fully, or by causing a reverse reaction.

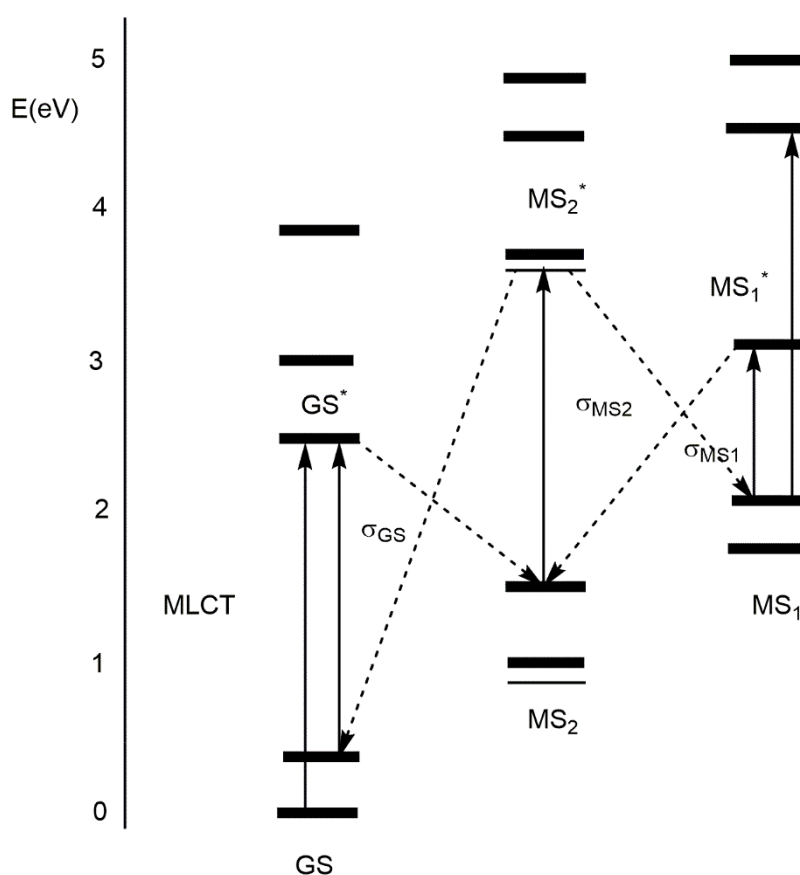


Figure 4. Diagram of the pathway for the formation of a metastable linkage isomer (example for a ML₅(NO) complex).⁴³ Adapted with permission from ref. 43. Copyright (2009) Royal Society of Chemistry.

Only if all or most of the factors are favorable can 100% conversion from the ground to the metastable (excited) state occur. However, complete conversion is important if solid-state linkage isomeric materials are to find real applications as molecular switches.

D. LINKAGE ISOMERS INVOLVING THE NO₂ GROUP

Another ligand that can undergo linkage isomerization in a complex is the nitro group. The NO₂ group can coordinate to a metal center through either the nitrogen atom (η^1 -NO₂ - nitro) or one or both of the oxygen atoms (η^1 -ONO or μ^2 -O,ON - nitrito). In the monodentate nitrito form the ligand can adopt either the *endo* form with the second oxygen pointing toward the metal center or the *exo* form where it points away (Fig. 1(c)). The ambidentate nature of the NO₂ group has been known since the time of Jørgensen¹⁷ with his pioneering studies on [Co(NH₃)₅(NO₂)]Cl₂. The solution-state photochemistry of nitro complexes was first established in 1944 when it was found that while individual nitro-(η^1 -NO₂) and nitrito-(η^1 -ONO) isomers could be prepared selectively under specific reaction conditions, conversion between the two forms could be photoinduced by irradiation of the nitro form under UV light.⁴⁴ Then in 1979 detailed powder X-ray diffraction studies on microcrystalline samples of [Co(NH₃)₅(NO₂)]Cl₂ showed that both thermal and photoactivated nitro-nitrito isomerization occurred.^{45,46} By following the gradual shift in peak positions in sequential powder patterns, which reflect the changes in crystallographic cell dimensions associated with the nitro-nitrito conversion, the level of interconversion could be assessed.

Prompted by the *photocrystallographic* studies on nitrosyl and sulfur dioxide linkage isomers we began a program to study photoactivated linkage isomerism in metal nitro compounds in 2007. Our dual aim was to design systems that underwent 100% conversion to the nitrito species and that the isomeric switch occurred near room temperature so that they might be useful for “real world” applications. The ideas on the design features required for good switchable materials ((1)-(8) above) were being developed during the latter half of the 2000s. Our initial strategy was to use bulky auxiliary ligands that would control the solid-state crystal packing and provide space within the lattice for the nitro → nitrito conversion to occur. We chose [Ni(dppe)(η^1 -NO₂)Cl] (dppe = 1,2-bis(diphenylphosphino)ethane) and studied its solid-state photoactivation using a combination of *photocrystallographic* and Raman methods.⁴⁷ The solid-state Raman spectrum recorded at 115 K, under 400 nm light, showed changes in the spectrum consistent with the formation of the nitrito isomer. In a *photocrystallographic* experiment irradiation of a single-crystal for 20 minutes with 400 nm LEDs, below 160 K, followed by a data collection without irradiation, resulted in a structure showing 100% conversion from the nitro form to the *endo*-nitrito form (Fig. 5). Raising the temperature of the sample above 160 K resulted in the regeneration of the GS structure. This process could be cycled more than 10 times without any observable crystal degradation. In these experiments we used 400 nm LEDs (Fig. 6) as the radiation source rather than lasers.⁴⁸ We found the use of LEDs to be advantageous since any sample heating issues resulting from the use of lasers were substantially reduced.

As a general point, the measure of whether 100% conversion to the metastable species in these studies had been achieved, is that in the final, crystallographically obtained, electron density difference map there should be no residual peaks corresponding to the GS ligand structure, and no significant residual electron density above approximately 1 eÅ⁻³. At this level the error on the percentage conversion is less than 5%.

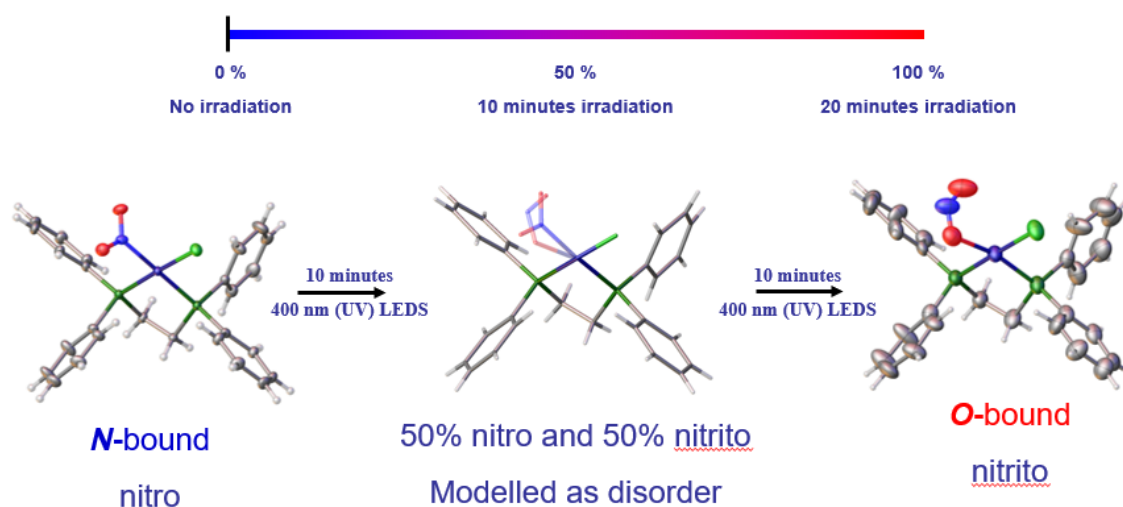


Figure 5. Reversible 100% conversion of $[\text{Ni}(\text{dppe})(\eta^1\text{-NO}_2)\text{Cl}]$ to $[\text{Ni}(\text{dppe})(\eta^1\text{-ONO}_2)\text{Cl}]$

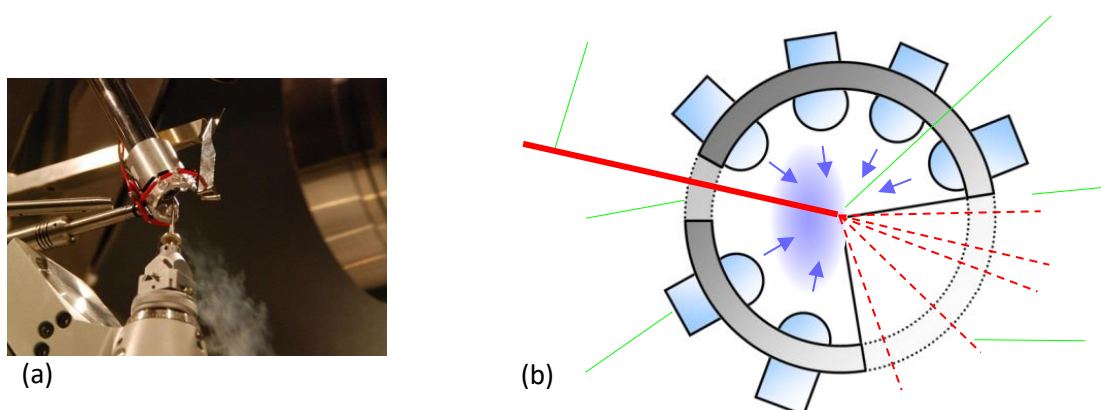


Figure 6. (a) LED holder mounted on diffractometer and (b) schematic showing the 6 LEDs in a ring 1 cm from the crystal

100% photocrystallographic nitro \rightarrow *endo*-nitrito conversion was also achieved by extending the range of bulky bidentate phosphine ligands used. With 400 nm LEDs, at 100 K, both *cis*- $[\text{Ni}(\text{dppe})(\text{NO}_2)_2]$ and *cis*- $[\text{Ni}(\text{dcpe})(\text{NO}_2)_2]$ ($\text{dcpe} = \text{C}_6\text{H}_{11}\text{PCH}_2\text{CH}_2\text{PC}_6\text{H}_{11}$; Cy = cyclohexyl) showed complete conversion to the metastable nitrito form.⁴⁹ Above 180 K the nitrito isomer reverted to the GS nitro isomer. The presence of other bulky chelating groups also facilitated the complete nitro \rightarrow *endo*-nitrito conversion.⁵⁰

An interesting feature of complexes that undergo nitro to nitrito linkage isomerism is that the interconversion can be controlled by temperature as well as by illumination. $[\text{Ni}(\text{Et}_4\text{dien})(\text{NO}_2)_2]$ ($\text{Et}_4\text{dien} = \text{N,N,N',N'}$ -tetraethyldiethylenetriamine) adopts *pseudo*-octahedral structure with the tridentate Et_4dien ligand in a meridional arrangement with one bidentate nitrito- $(\eta^2\text{-O,ON})$. The second nitro ligand is monodentate but is disordered at room temperature with the major 78% component adopting the nitro conformation and the minor 22% component in the nitrito conformation (Fig. 7).⁵¹ We discovered that slow cooling of a crystal of $[\text{Ni}(\text{Et}_4\text{dien})(\text{NO}_2)_2]$ to 160 K resulted in the complete removal of the nitrito component. Warming of the crystal to around 370 K affords an isomer ratio of 58:42 nitro:nitrito. Therefore, there is a thermally controlled equilibrium

between the two isomers, and the nitro form can be considered as the thermodynamic GS.⁵² In a photocrystallographic experiment with 500 nm LEDs, at 100 K, 100% conversion to the nitrito isomer was achieved after 2 hours, and when the temperature was raised to around 160 K the GS nitro isomer was regenerated.¹⁴

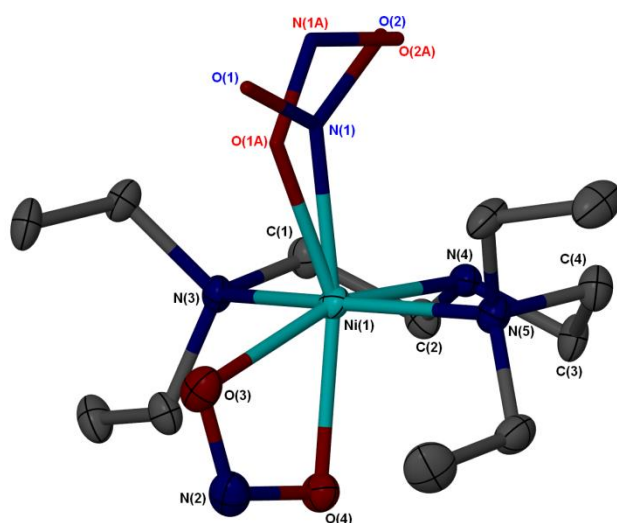


Figure 7. The disordered room temperature structure of $[\text{Ni}(\text{Et}_4\text{dien})(\text{NO}_2)_2]$

Because of the thermal and photo-control that we had established for $[\text{Ni}(\text{Et}_4\text{dien})(\text{NO}_2)_2]$ it was possible to undertake variable-temperature kinetic measurements in the 150-160 K range. This showed that the endo-nitrito decay is dependent on temperature and an activation energy of $E_{\text{act}} = 48.6(4) \text{ kJ mol}^{-1}$ (0.5 eV) was obtained. It was also possible, to carry out pseudo-steady-state *photocrystallography* experiments in which the illumination is continued during the crystallographic data collection. This experiment showed the presence of a previously unobserved *exo-nitrito* linkage isomer at temperature close to the metastable limit (Fig. 8).¹⁴ This isomer may be a transient state species.

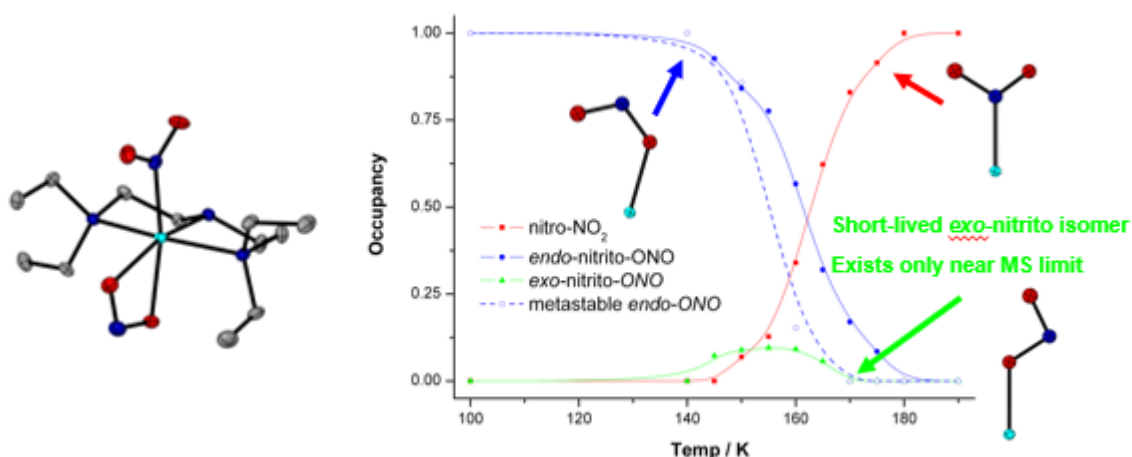


Figure 8. The results of the pseudo-steady-state experiment showing the formation of the transient *exo-nitrito* species (in green).

In an alternative strategy to probe the importance of the crystal environment in complexes that can undergo solid-state photoactivated linkage isomerism the two salts $[\text{Pd}(\text{Et}_4\text{dien})(\text{NO}_2)][\text{OTf}]$

and $[\text{Pt}(\text{Et}_4\text{dien})(\text{NO}_2)][\text{OTf}]$ have been investigated. Both the GS structures contain significant N-H...O hydrogen bonds involving a nitro O-atom. Irradiation with 400 nm LEDs, at 100 K, results in a mixture of both *endo* and *exo*-(η^1 -ONO) isomers and only overall conversion levels of 56% (Pd) and 29% (Pt) are observed. However, on warming to 150 K, when the Pd salt crystals are irradiated for 1 hour 100% conversion to the *endo*-(η^1 -ONO) form occurs. When the Pt salt is irradiated for 3 hours, at 200 K, 93% of the *endo*-(η^1 -ONO) form is obtained along with 7% of the ground-state. Variable temperature studies show that the metastable limit for the Pt complex is around 240 K while for the lighter Pd complex it is 190 K.⁵³ For both complexes the amine...NO₂ hydrogen bonds become longer at higher temperatures (Fig. 9). If the hydrogen bonds do inhibit photoisomerization at lower temperatures raising the temperature would facilitate isomerization, as is observed. Similarly, the volume of the *reaction cavity* should increase at higher temperatures. This suggests that temperature-regulated photo-activation may provide a new method to control single-crystal-to-single-crystal linkage isomeric transformations.

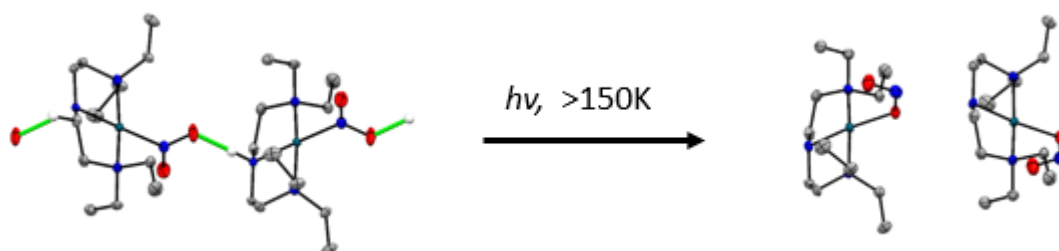


Figure 9. The loss of hydrogen-bonding in $[\text{Pd}(\text{Et}_4\text{dien})(\text{NO}_2)][\text{OTf}]$ as the temperature is increased to above 150K.

These series of studies on the nitro/nitrito linkage isomers suggest that using bulky auxiliary ligands or bulky counterions, which will strongly influence the crystal packing, will favor high levels of conversion to the metastable isomers. The electronic factors also seem to be acceptable for the isomerization to occur, although the kinetics for isomerization for complexes of the second and third row of the d-block are slower than those for the first row, with some of the conversions for the heavier metal complexes only occurring at higher temperatures. The objective remains, can complexes be engineered where 100% conversion occurs and switching is achieved close to room temperature?

The packing efficiency in the crystal structure of metal complexes can be further reduced by moving to ionic systems, cations and anions, one or both of which may contain bulky groups. In $[\text{Pd}(\text{Bu}_4\text{dien})(\eta^1\text{-NO}_2)][\text{BPh}_4]$ (Bu_4dien = N,N,N',N'-tetrabutyl-diethylenetriamine) 100% conversion to the metastable *endo*-nitro-(η^1 -ONO) isomer (Fig. 10) is achieved in only 15 minutes upon irradiation with 400 nm LEDs at 100 K⁵⁴ and, significantly, the system is metastable until 240 K. Under pseudo-steady-state *photocrystallographic* conditions the nitrito isomer is observed at temperatures up to 260 K. This result suggests that complexes containing heavier transition metals may raise the temperature of the metastable limit close to room temperature.

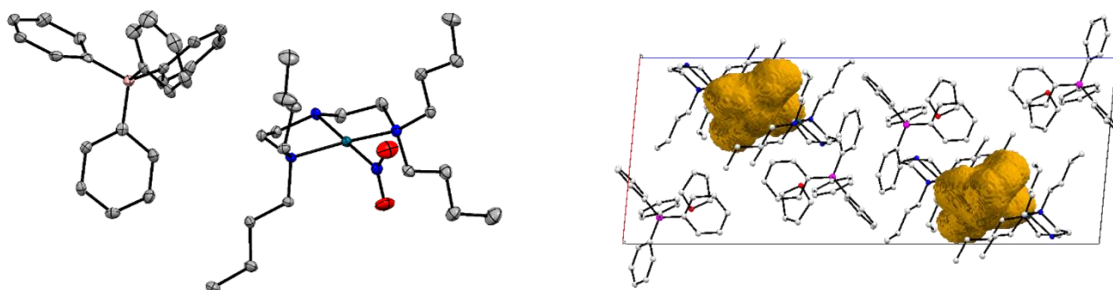


Figure 10. The structure of $[\text{Pd}(\text{Bu}_4\text{dien})(\eta^1\text{-NO}_2)][\text{BPh}_4]$ and a packing diagram showing the volume available to the nitro/nitrito group.

Because of the fine control over the generation of the metastable states in $[\text{Pd}(\text{Bu}_4\text{dien})(\eta^1\text{-NO}_2)][\text{BPh}_4]$ we have been able to extract quantitative kinetic information for both the excitation and decay processes from the data,⁵⁵ building on the previous kinetic studies on linkage isomers.^{14,36,54,56} We found that the photoactivation process is weakly temperature dependent, which may be due to the effect of the crystal environment on the isomerization process. However, the reverse decay process has an activation energy of $55 \pm 5 \text{ kJ mol}^{-1}$ and is strongly dependent on temperature, which leads to lifetimes that are tunable through several orders of magnitude by careful temperature control.⁵⁵ Over the temperature range 175–325 K the decay time, $t_{1/2}$, ranges from 10^7 sec to 100ms.⁵⁵ It should now be possible to effectively “dial up” a suitable temperature to give a desired ES lifetime. Because of the fine control over temperature vs. lifetime these linkage isomeric materials may prove to be useful benchmark materials for the development of time-resolved diffraction methodologies.

F. CONCLUDING REMARKS

Over the last two decades we and others have shown how it is possible to use photocrystallographic techniques to study photoactivated linkage isomerism in solid-state transition metal coordination complexes containing ambidentate ligands such as NO, NO₂ and SO₂. All these ligands have been shown to undergo isomerism to produce metastable isomers. The percentage of conversion achieved and the isomer obtained are strongly dependent on the wavelength of light used and the temperature at which the experiment is carried out. In all cases there is a temperature at which the *metastable limit* is reached above which the excited state has a finite lifetime before returning to the ground state. The interconversion is also dependent on the flexibility of the crystal lattice and on the steric and electronic environment of the ambidentate ligand and the metal center. There needs to be sufficient space in the lattice for the ligand to switch between one form and the other, and intermolecular interactions should either not be particularly strong or be flexible perhaps through a change in temperature.^{30,54}

For transition metal nitro/nitrito complexes the use of bulky bidentate phosphines and amines as auxiliary ligands, which are largely responsible for the crystal packing motif, favor high levels of conversion to the metastable state, as does the inclusion of bulky counterions when dealing with salts. Additionally, the inclusion of a second or third row transition metal in the complex favors a higher temperature for the isomerization to occur. In these cases, the decay process from the excited or metastable state back to the ground state has an activation energy of *ca.* 55 kJ mol^{-1} and is dependent on temperature, which leads to lifetimes that are tunable through several orders of magnitude by careful control of temperature. This should make accessing a particular GS lifetime a much more straightforward process.

With the design features that have been established it should be possible to convert the knowledge gained from the *photocrystallographic* studies to the design of switchable materials. Because of the relationship that we have established between temperature and lifetime in these linkage isomers they should be useful benchmark materials as time-resolved diffraction methodology continues to develop. The successful incorporation of some of the nitrosyl and sulfur dioxide linkage isomers into polymers and xerogels without the loss of their switching function^{40,42} suggests that these systems may have optical device applications. Schaniel *et al.* have shown that it is possible to write short-lived phase gratings with identically and orthogonally polarized waves using nanosecond laser pulses in crystals of iron nitrosyl complexes. The isomerization leads to a change of modulation of the polarizability and with it a measurable change in refractive index of the crystal.⁵⁷

AUTHOR INFORMATION

Corresponding Author

*E-mail: p.r.raithby@bath.ac.uk

ORCHID

Lauren E Hatcher: 0000-0002-1549-9727

Jonathan M Skelton: 0000-0002-0395-1202

Mark R Warren: 0000-0003-1326-0744

Paul R Raithby: 0000-0002-2944-0662

Notes

The authors declare no competing financial interest.

ACKNOWLEDGEMENTS

PRR is grateful to the Engineering and Physical Sciences Research Council (EPSRC) for continued funding (EP/K004956/1).

Biographical Information

Lauren Hatcher is a post-doctoral Research Fellow at the University of Bath working on aspects of time-resolved crystallography and crystallization methods.

Jonathan Skelton has recently been awarded a Research Fellowship at the University of Manchester. He is developing computational methods for modelling the behavior of dynamic materials.

Mark Warren completed his Ph D Degree at the University of Bath and after a post doc at Imperial College, London, is now a beamline scientist at the Diamond Light Source, on beamline I19.

Paul Raithby has been Professor of Inorganic Chemistry at the University of Bath since 2000. His research includes the synthesis and fabrication of new functional materials that have applications as switches and sensors.

REFERENCES

- (1) Cohen, M. D.; Schmidt, G. M. J. Topochemistry.1. Survey. *J. Chem. Soc.y* **1964**, 1996-2016.
- (2) Cohen, M. D. The Photochemistry of Organic Solids. *Angew. Chem. Int. Ed. Engl.* **1975**, *14*, 386-393.
- (3) Ohashi, Y.; Yanagi, K.; Kurihara, T.; Sasada, Y.; Ohgo, Y. Crystalline state reaction of cobaloxime complexes by x-ray exposure. 1. Direct observation of cobalt-carbon bond cleavage in [(R)-1-cyanoethyl][(S)-(-)-.alpha.-methylbenzylamine]bis(dimethylglyoximate)cobalt(III). *J. Am. Chem. Soc.* **1981**, *103*, 5805-5812.
- (4) Clegg, W. Synchrotron chemical crystallography. *J Chem Soc Dalton* **2000**, 3223-3232.
- (5) Neutze, R.; Moffat, K. Time-resolved structural studies at synchrotrons and X-ray free electron lasers: opportunities and challenges. *Current Opinion in Structural Biology* **2012**, *22*, 651-659.
- (6) Hatcher, L. E.; Raithby, P. R. Dynamic single-crystal diffraction studies using synchrotron radiation. *Coord. Chem. Rev.* **2014**, *277*, 69-79.
- (7) Howard, J. A. K.; Probert, M. R. Cutting-Edge Techniques Used for the Structural Investigation of Single Crystals. *Science* **2014**, *343*, 1098-1102.
- (8) Lee, R.; Howard, J. A. K.; Probert, M. R.; Steed, J. W. Structure of organic solids at low temperature and high pressure. *Chem. Soc. Rev.* **2014**, *43*, 4300-4311.
- (9) Coppens, P.; Fournier, B. New methods in time-resolved Laue pump-probe crystallography at synchrotron sources. *J. Sync. Rad.* **2015**, *22*, 280-287.
- (10) Coppens, P.; Fomitchev, D. V.; Carducci, M. D.; Culp, K. Crystallography of molecular excited states. Transition-metal nitrosyl complexes and the study of transient species. *J Chem Soc Dalton* **1998**, 865-872.
- (11) Carducci, M. D.; Pressprich, M. R.; Coppens, P. Diffraction studies of photoexcited crystals: Metastable nitrosyl-linkage isomers of sodium nitroprusside. *J. Am. Chem. Soc.* **1997**, *119*, 2669-2678.

- (12) Cole, J. M. Photocrystallography. *Acta Cryst. Sect. A* **2008**, *64*, 259-271.
- (13) Coppens, P.; Vorontsov, I.; Graber, T.; Gembicky, M.; Kovalevsky, A. Y. The structure of short-lived excited states of molecular complexes by time-resolved X-ray diffraction. *Acta Cryst. Sect. A* **2005**, *61*, 162-172.
- (14) Hatcher, L. E.; Christensen, J.; Hamilton, M. L.; Trincao, J.; Allan, D. R.; Warren, M. R.; Clarke, I. P.; Towrie, M.; Fuertes, S.; Wilson, C. C.; Woodall, C. H.; Raithby, P. R. Steady-State and Pseudo-Steady-State Photocrystallographic Studies on Linkage Isomers of Ni(Et₄dien)(η²-O,ON)(η¹-NO₂): Identification of a New Linkage Isomer. *Chem. Eur. J.* **2014**, *20*, 3128-3134.
- (15) Schaniel, D.; Cormary, B.; Malfant, I.; Valade, L.; Woike, T.; Delley, B.; Kramer, K. W.; Gudel, H. U. Photogeneration of two metastable NO linkage isomers with high populations of up to 76% in trans-[RuCl(py)₄(NO)][PF₆]₂·1/2H₂O. *Phys. Chem. Chem. Phys.* **2007**, *9*, 3717-3724.
- (16) Schaniel, D.; Mockus, N.; Woike, T.; Klein, A.; Sheptyakov, D.; Todorova, T.; Delley, B. Reversible photoswitching between nitrito-N and nitrito-O isomers in trans- Ru(py)₄(NO₂)₂. *Phys. Chem. Chem. Phys.* **2010**, *12*, 6171-6178.
- (17) Jörgensen, S. M. Zur Konstitution der Kobalt-, Chrom- und Rhodumbasen. *V. Zeit. für Anorg. Chem.* **1894**, *5*, 147-196.
- (18) Cole, J. M. Single-crystal X-ray diffraction studies of photo-induced molecular species. *Chem. Soc. Rev.* **2004**, *33*, 501-513.
- (19) Schaniel, D.; Imlau, M.; Weisemoeller, T.; Woike, T.; Kramer, K. W.; Gudel, H. U. Photoinduced nitrosyl linkage isomers uncover a variety of unconventional photorefractive media. *Adv. Mater.* **2007**, *19*, 723-726.
- (20) Sylvester, S. O.; Cole, J. M. Solar-Powered Nanomechanical Transduction from Crystalline Molecular Rotors. *Adv. Mater.* **2013**, *25*, 3324-3328.
- (21) Dieckmann, V.; Imlau, M.; Taffa, D. H.; Walder, L.; Lepski, R.; Schaniel, D.; Woike, T. Phototriggered NO and CN release from [Fe(CN)₅(NO)]²⁻ molecules electrostatically attached to TiO₂ surfaces. *Phys. Chem. Chem. Phys.* **2010**, *12*, 3283-3288.
- (22) Fry, N. L.; Mascharak, P. K. Photoactive Ruthenium Nitrosyls as NO Donors: How To Sensitize Them toward Visible Light. *Acc Chem. Res.* **2011**, *44*, 289-298.
- (23) Hauser, U.; Oestreich, V.; Rohrweck, H. D. On optical dispersion in transparent molecular systems. *Zeit. für Physik A Atoms and Nuclei* **1977**, *280*, 17-25.
- (24) Pressprich, M. R.; White, M. A.; Vekhter, Y.; Coppens, P. Analysis of a Metastable Electronic Excited-State of Sodium Nitroprusside by X-ray Crystallography. *J. Am. Chem. Soc.* **1994**, *116*, 5233-5238.
- (25) Fomitchev, D. V.; Coppens, P. X-ray diffraction analysis of geometry changes upon excitation: The ground-state and metastable-state structures of K₂ Ru(NO₂)₄(OH)(NO). *Inorg. Chem.* **1996**, *35*, 7021-7026.
- (26) Fomitchev, D. V.; Coppens, P.; Li, T. S.; Bagley, K. A.; Chen, L.; Richter-Addo, G. B. Photo-induced metastable linkage isomers of ruthenium nitrosyl porphyrins. *Chem. Commun.* **1999**, 2013-2014.
- (27) Coppens, P.; Novozhilova, I.; Kovalevsky, A. Photoinduced linkage isomers of transition-metal nitrosyl compounds and related complexes. *Chem. Rev.* **2002**, *102*, 861-883.
- (28) Fomitchev, D. V.; Bagley, K. A.; Coppens, P. The first crystallographic evidence for side-on coordination of N₂ to a single metal center in a photoinduced metastable state. *J. Am. Chem. Soc.* **2000**, *122*, 532-533.
- (29) Cormary, B.; Malfant, I.; Valade, L.; Cointe, M. B. L.; Toupet, L.; Todorova, T.; Delley, B.; Schaniel, D.; Mockus, N.; Woike, T.; Fejfarova, K.; Petricek, V.; Dusek, M. Ru(py)₄Cl(NO)(PF₆)₂·0.5H₂O: a model system for structural determination and ab initio calculations of photo-induced linkage NO isomers. *Acta Cryst. Sect. B.* **2009**, *65*, 787-787.
- (30) Cormary, B.; Ladeira, S.; Jacob, K.; Lacroix, P. G.; Woike, T.; Schaniel, D.; Malfant, I. Structural Influence on the Photochromic Response of a Series of Ruthenium Mononitrosyl Complexes. *Inorg. Chem.* **2012**, *51*, 7492-7501.

- (31) Johnson, D. A.; Dew, V. C. Photochemical Linkage Isomerization in Coordinated SO₂. *Inorg. Chem.* **1979**, *18*, 3273-3274.
- (32) Kovalevsky, A. Y.; Bagley, K. A.; Coppens, P. The first photocrystallographic evidence for light-induced metastable linkage isomers of ruthenium sulfur dioxide complexes. *J. Am. Chem. Soc.* **2002**, *124*, 9241-9248.
- (33) Kovalevsky, A. Y.; Bagley, K. A.; Cole, J. M.; Coppens, P. Light-Induced Metastable Linkage Isomers of Ruthenium Sulfur Dioxide Complexes. *Inorg. Chem.* **2003**, *42*, 140-147.
- (34) Bowes, K. F.; Cole, J. M.; Husheer, S. L. G.; Raithby, P. R.; Savarese, T. L.; Sparkes, H. A.; Teat, S. J.; Warren, J. E. Photocrystallographic structure determination of a new geometric isomer of [Ru(NH₃)₄(H₂O)(η¹-OSO)][MeC₆H₄SO₃]₂. *Chem. Commun.* **2006**, 2448-2450.
- (35) Phillips, A. E.; Cole, J. M.; d'Almeida, T.; Low, K. S. Effects of the reaction cavity on metastable optical excitation in ruthenium-sulfur dioxide complexes. *Phys. Rev. B* **2010**, *82*.
- (36) Phillips, A. E.; Cole, J. M.; d'Almeida, T.; Low, K. S. Ru-OSO Coordination Photogenerated at 100 K in Tetraammineaqua(sulfur dioxide)ruthenium(II) (±)-Camphorsulfonate. *Inorg. Chem.* **2012**, *51*, 1204-1206.
- (37) Cole, J. M. A new form of analytical chemistry: distinguishing the molecular structure of photo-induced states from ground-states. *Analyst* **2011**, *136*, 448-455.
- (38) Schuy, A.; Woike, T.; Schaniel, D. Photoisomerisation in single molecules of nitroprusside embedded in mesopores of xerogels. *J. Sol-Gel Sci. and Tech.* **2009**, *50*, 403-408.
- (39) Cervellino, A.; Schefer, J.; Keller, L.; Woike, T.; Schaniel, D. Identification of single photoswitchable molecules in nanopores of silica xerogels using powder diffraction. *J. Appl. Cryst.* **2010**, *43*, 1040-1045.
- (40) Tahri, Z.; Lepski, R.; Hsieh, K. Y.; Bendeif, E. E.; Pillet, S.; Durand, P.; Woike, T.; Schaniel, D. Properties of metastable linkage NO isomers in Na₂ Fe(CN)₅NO.2H₂O incorporated in mesopores of silica xerogels. *Phys. Chem. Chem. Phys.* **2012**, *14*, 3775-3781.
- (41) Sylvester, S. O.; Cole, J. M.; Waddell, P. G.; Nowell, H.; Wilson, C. SO₂ Phototriggered Crystalline Nanomechanical Transduction of Aromatic Rotors in Tosylates: Rationalization via Photocrystallography of Ru(NH₃)₄SO₂X tosylate₂ (X = pyridine, 3-Cl-pyridine, 4-Cl-pyridine). *J. Phys. Chem. C* **2014**, *118*, 16003-16010.
- (42) Cole, J. M.; Yeung, K. Y. M.; Pace, G.; Sylvester, S. O.; Mersch, D.; Friend, R. H. In situ synthesis, crystallisation, and thin-film processing of single crystals of trans- Ru(SO₂)(NH₃)₄(H₂O) p-TolSO₃)₂ bearing SO₂ linkage photo-isomers: towards optical device applications. *Crystengcomm* **2015**, *17*, 5026-5031.
- (43) Schaniel, D.; Woike, T. Necessary conditions for the photogeneration of nitrosyl linkage isomers. *Phys. Chem. Chem. Phys.* **2009**, *11*, 4391-4395.
- (44) Adell, B. Über die Geschwindigkeit der Umwandlung von Nitrito- in Nitropentamminkobalt(III)-chlorid. *Zeit. Anorg. Chem.* **1944**, *252*, 272-280.
- (45) Grenthe, I.; Nordin, E. Nitrito-nitro linkage isomerization in the solid state. 1. X-ray crystallographic studies of trans-bis(ethylenediamine)(isothiocyanato)nitrito- and trans-bis(ethylenediamine)(isothiocyanato)nitrocobalt(III) perchlorate and iodide. *Inorg. Chem.* **1979**, *18*, 1109-1116.
- (46) Grenthe, I.; Nordin, E. Nitrito-nitro linkage isomerization in the solid state. 2. A comparative study of the structures of nitrito- and nitropentaaminecobalt(III) dichloride. *Inorg. Chem.* **1979**, *18*, 1869-1874.
- (47) Warren, M. R.; Brayshaw, S. K.; Johnson, A. L.; Schiffers, S.; Raithby, P. R.; Easun, T. L.; George, M. W.; Warren, J. E.; Teat, S. J. Reversible 100% Linkage Isomerization in a Single-Crystal to Single-Crystal Transformation: Photocrystallographic Identification of the Metastable Ni(dppe)(η¹-ONO)Cl Isomer. *Angew. Chem. Int. Ed.* **2009**, *48*, 5711-5714.
- (48) Brayshaw, S. K.; Knight, J. W.; Raithby, P. R.; Savarese, T. L.; Schiffers, S.; Teat, S. J.; Warren, J. E.; Warren, M. R. Photocrystallography - design and methodology for the use of a light-emitting diode device. *J. Appl. Cryst.* **2010**, *43*, 337-340.

(49) Warren, M. R.; Easun, T. L.; Brayshaw, S. K.; Deeth, R. J.; George, M. W.; Johnson, A. L.; Schiffers, S.; Teat, S. J.; Warren, A. J.; Warren, J. E.; Wilson, C. C.; Woodall, C. H.; Raithby, P. R. Solid-State Interconversions: Unique 100% Reversible Transformations between the Ground and Metastable States in Single-Crystals of a Series of Nickel(II) Nitro Complexes. *Chem. Eur. J.* **2014**, *20*, 5468-5477.

(50) Bajwa, S. E.; Storr, T. E.; Hatcher, L. E.; Williams, T. J.; Baumann, C. G.; Whitwood, A. C.; Allan, D. R.; Teat, S. J.; Raithby, P. R.; Fairlamb, I. J. S. On the appearance of nitrite anion in [PdX(OAc)₂] and [Pd(X)(C[^]N)L] syntheses (X = OAc or NO₂): photocrystallographic identification of metastable Pd(η¹-ONO)(C[^]N)PPh₃. *Chem. Sci.* **2012**, *3*, 1656-1661.

(51) Laskar, I. R.; Das, D.; Mostafa, G.; Lu, T.-H.; Keng, T.-C.; Wang, J.-C.; Ghosh, A.; Chaudhuri, N. R. First report on thermally induced nitro → nitrito(O,O) linkage isomerization in diamine complexes of nickel(II) in the solid state: X-ray single crystal structural analyses of nitro and nitrito isomers. *New J. Chem.* **2001**, *25*, 764-768.

(52) Hatcher, L. E.; Warren, M. R.; Allan, D. R.; Brayshaw, S. K.; Johnson, A. L.; Fuertes, S.; Schiffers, S.; Stevenson, A. J.; Teat, S. J.; Woodall, C. H.; Raithby, P. R. Metastable Linkage Isomerism in [Ni(Et₄dien)(NO₂)₂]: A Combined Thermal and Photocrystallographic Structural Investigation of a Nitro/Nitrito Interconversion. *Angew. Chem. Int. Ed.* **2011**, *50*, 8371-8374.

(53) Hatcher, L. E.; Raithby, P. R. The impact of hydrogen bonding on 100% photo-switching in solid-state nitro–nitrito linkage isomers. *CrystEngComm* **2017**, *19*, 6297-6304.

(54) Hatcher, L. E. Raising the (metastable) bar: 100% photo-switching in [Pd(Bu₄dien)(η¹-O₂)]⁺ approaches ambient temperature. *CrystEngComm* **2016**, *18*, 4180-4187.

(55) Hatcher, L. E.; Skelton, J. M.; Warren, M. R.; Stubbs, C.; da Silva, E. L.; Raithby, P. R. Monitoring photo-induced population dynamics in metastable linkage isomer crystals: a crystallographic kinetic study of [Pd(Bu₄dien)NO₂]BPh₄. *Phys. Chem. Chem. Phys.* **2018**, *20*, 5874-5886.

(56) Kostin, G. A.; Borodin, A. O.; Mikhailov, A. A.; Kuratieva, N. V.; Kolesov, B. A.; Pishchur, D. P.; Woike, T.; Schaniel, D. Photocrystallographic, Spectroscopic, and Calorimetric Analysis of Light-Induced Linkage NO Isomers in RuNO(NO₂)₂(pyridine)₂OH. *Eur. J. Inorg. Chem.* **2015**, 4905-4913.

(57) Goukov, M.; Schaniel, D.; Woike, T. Pulse recording of thermal and linkage isomer gratings in nitrosyl compounds. *J. Opt. Soc. Am. B.* **2010**, *27*, 927-932.