Diphenylphosphinobenzoic Acids as Linkers in [2,4,6– $\{(C_{10}H_{21}O)_3C_6H_2NH\}_3C_3N_3$] Triazine Adducts with Metal Complex, which Self–Organize into Room Temperature Hexagonal Columnar Mesophases

Ana B. Miguel–Coello,¹ Manuel Bardají,^{1,*} Silverio Coco,^{1,*} Bertrand Donnio,^{2,3} Benoît Heinrich,² and Pablo Espinet^{1,*}

¹IU CINQUIMA/Química Inorgánica, Facultad de Ciencias, Universidad de Valladolid, E–47071 Valladolid, Spain.

²Institut de Physique et Chimie des Matériaux de Strasbourg (IPCMS), UMR 7504 (CNRS–Université de Strasbourg), 23 rue du Loess, BP 43, 67034 Strasbourg Cedex 2, France.

³Complex Assemblies of Soft Matter Laboratory (COMPASS), UMI 3254 (CNRS–SOLVAY–University of Pennsylvania), CRTB, 350 George Patterson Boulevard, Bristol, PA 19007, USA.

*Author to whom correspondence should be addressed. E-mail: <u>bardaji@qi.uva.es;</u> scoco@qi.uva.es; espinet@qi.uva.es

Abstract

The displacement of a labile ligand from appropriate precursor complexes by 2- or 4- $PPh_2C_6H_4COOH$, yields neutral gold(I) and gold(III) [AuX_n(PPh₂C₆H₄COOH)] (n = 1, X = Cl; n = 3, $X = C_6F_5$), cationic gold(I) [Au(PPh₂C₆H₄COOH)₂](CF₃SO₃), and neutral chromium(0) [Cr(CO)₅(PPh₂C₆H₄COOH)] metallo-organic acids. [AuCl(4-PPh₂C₆H₄COOH)], [Au(C₆F₅)₃(4-PPh₂C₆H₄COOH)] and [Cr(CO)₅(2-PPh₂C₆H₄COOH)] have dimeric structures with typical carboxylic H-bond bridges, whereas [Au(C₆F₅)₃(2-PPh₂C₆H₄COOH)] gives a monomeric species with the carboxylic acid H-bonded to co-crystallized solvent molecules. All the gold-containing acids are emissive at 77 K in the range 404–520 nm, and some of them, also at 298 K with emission maxima from 441 to 485 nm. Reaction of these acid metal complexes with the triazine mesogen $2,4,6-\{(C_{10}H_{21}O)_3C_6H_2NH\}_3C_3N_3$ afford some new hydrogen bonded gold(I) and chromium(0) supramolecular adducts, but the related gold(III) complexes do not form adducts. The 4diphenylphosphinobenzoic adducts display a columnar hexagonal mesophase (Colhex) at roomtemperature, with a random one-dimensional stacking of the pseudo-discoid triazine-metalloorganic adducts into columns, where the metallo-phosphinoacid fragments act as the fourth branch of the trifold triazine–core. The 2–diphenylphosphinobenzoic mixtures do not display mesophases. as they appear in the X-ray studies as mixtures of the triazine and the metallo-phosphinoacid complex. The aggregates are luminescent at 77 K, with emission maxima in the range 419–455 nm.

Keywords: metallomesogens, gold, chromium, hydrogen bonding, columnar liquid crystals, luminescence.

Introduction

Intermolecular hydrogen bonding can promote molecular self–assembly into ordered supramolecular structures, allowing for engineering of soft materials with specific functionalities.¹ This approach has been used successfully in the construction of organic liquid crystalline architectures. Many examples of simple to highly complex molecular self–assemblies have been reported.^{2,3}

There is interest in liquid crystalline systems forming columnar arrangements due to their potential application in opto-electronic devices with some advantageous properties:⁴ high charge-carrier mobility along the stacking axis, long-range self-assembling, self-healing and easy processing due to fluidity, solubility in organic solvents, and added properties such as luminescence, conductivity, or magnetism (for metallomesogens).

Metal-containing H-bonded liquid crystals are still rare, 5,6,7,8,9,10,11 but smectic and columnar mesophases can be produced by judicious combination of the complementary building blocks. 2,4,6-Triarylamino-1,3,5-triazines equipped by 6 or 9 peripheral alkoxy chains are appropriate bricks to form H-bonded discotic adducts with carboxylic acids and self-organize into liquid crystalline columnar mesophases. 12 We recently extended this concept by integrating metal complexes containing carboxylic acid functions, and reported new types of supramolecular metallomesogens, derived from 1:1 association of a triazine and a 4-isocyanobenzoic acid complex of chromium(0), iron(0), molybdenum(0) or tungsten(0). The hexagonal packing into columnar mesophases found for the free triazine was systematically preserved in the metal-containing supramolecular adducts.¹³ In contrast, the corresponding gold(I) isocyanobenzoic acid complexes did not produce such adducts, likely because the weakness of the H-bonding interactions with the triazine and the high insolubility of the starting gold complexes makes adduct formation thermodynamically unfavorable. Using the same self-assembly concept, we could prepare monoand dinuclear thiolatobenzoic gold(I) adducts with the same triazine mesogen, and demonstrated that the corresponding supramolecular adducts also produce a stable Colhex mesophase at room temperature. 14 In all cases, the supramolecular triazine-metallo-organic acid complexes stack in a complementary manner: the metallic thiolatobenzoic/isocyanobenzoic acid fragment acts as a fourth branch of the triazine core, in such a way that the steric crowding is minimized and the interface with the aliphatic continuum is smoothened. In other words, the metal complex moieties are somehow buried into the dominant aliphatic environment, in such a way that each discotic unit of adduct appears externally very similar to the free triazine, a disc with aliphatic chains. The

versatility of this approach is therefore very promising for the design and construction of room-temperature LC mesophases from metal-containing molecules using other carboxylic acid linkers to connect a metallic fragment to the triazine. A potential consequence of linking additional groups (in this case metal complexes) to a regular discotic molecule is that the new adduct, having a substituent protruding from the central core, is less symmetric and this descent of symmetry might produce changes in the properties of the material, as studied in less complex systems.¹⁵

In this study we examine the utility of 2– and 4–diphenylphosphinobenzoic acids (Figure 1). The P– atom is a general donor for any metal fragment, and therefore these ligands can be used as P– ligands in the synthesis of many metal complexes. They have also been used as carboxylate ligands. In line with our previous works on metallo–organic supramolecular assemblies, the carboxylic functional group of these diphenylphosphinobenzoic acids is suitable to produce H–bonds. For instance, 2–diphenylphosphinobenzoic acid is a dimer with typical carboxylic acid–bridges, and gold(I), and copper(I)²⁰ derivatives have been reported also as H–bonded dimers.

Figure 1. Structures of 2– and 4–diphenylphosphinobenzoic acids, and ¹H NMR labels.

P-containing metallomesogens are uncommon because of the unfavorable tetrahedral geometry imposed by the phosphorous atom.²¹ However, we have reported recently that the hexagonal columnar architectures produced by aggregation of isocyano— or thiolato—metallo—organic acids to triazines are able to accommodate some structurally voluminous molecular groups between the branches of the triazine, still preserving the mesogenic behavior.^{13,14} Achieving the same with phosphine groups as linkers looks more challenging, but in the present study we will show that some liquid crystals can be made. Even more challenging is the use of 2—diphenylphosphinobenzoic acid that, compared with its *para* isomer, introduces a violent rigid kink in the supramolecular pursued. Three different metal moieties were chosen that provide different features to the potential metallomesogens: linear Au^I, which is expected to be favorable; octahedral Cr(CO)₅, which has been shown before to be reasonably favorable and is a good reporter of the bonding interaction through v(CO) of the carbonyl groups in IR; and square—planar Au^{III}, which has not been checked before. Some of the metal containing moieties are very demanding sterically and were chosen on purpose to challenge the ability of the triazine to accommodate them into a discotic unit.

Results and discussion

Synthesis and Characterization of diphenylphosphinobenzoic acid metal complexes. The reaction of diphenylphosphinobenzoic acids **1** or **2** with [AuCl(tht)], [Au(C_6F_5)₃(tht)], [Au(tht)₂]CF₃SO₃ (tht = tetrahydrothiophene) or hexacarbonyl chromium(0) leads to the corresponding gold(I), gold(III) or chromium(0) complexes **3–10** (Scheme 1). They are air–stable, white (**3–8**) or yellow (**9–10**) solids at room temperature, and were characterized by CHN analysis, IR and NMR.

Scheme 1. Synthesis and molecular structures of the gold or chromium–organic acids **3–10**: i) [AuCl(tht)]; ii) [Au(C_6F_5)₃(tht)]; iii) ½ [Au(tht)₂]CF₃SO₃; iv) [Cr(CO)₆] + Me₃NO.

All the complexes display one v(C=O) band from the carboxylic group in the range 1719–1685 cm⁻¹. The chromium compounds show also carbonyl bands at 2064, 1987 and 1932 cm⁻¹. In their ¹H NMR spectra, the aromatic protons of the metallo–organic acids are low–field shifted compared to the free phosphine ligand. The largest shifts are about +0.32 ppm for H⁵ in the *ortho* ligand, and +0.40 ppm for H³ for the *para* ligand. The assignments given were confirmed by COSY and ¹H $\{^{31}P\}$ NMR. The ¹⁹F NMR spectra of compounds **5** and **6** show two sets (1:2 ratio) of three resonances (2:1:2 ratio) due to the C₆F₅ groups, in the range –120 and –122 (F_{ortho}), –157 (F_{para}), –160.5 and –161 ppm (F_{meta}). A singlet at around –79 ppm is observed for the triflate anion of compounds **7–8**. The singlet observed in the ³¹P{¹H} NMR spectra is low–field shifted by 23–65 ppm in all complexes, compared to the free phosphine ligand.

X-Ray Crystal Structure Determination of complexes 4, 5, 6 and 9. The crystalline structures of 4, 5, 6 and 9 are shown in Figures 2–3, with selected bond lengths and angles in Tables 1–2. Compounds 4, 6, and 9 are dimers through the carboxylic acid groups (bond lengths and angles in Table 3), regardless of the phosphine *ortho* or *para* substitution pattern. As expected, the gold(I) complex 4 displays a typical linear coordination for gold, and gold(III) derivatives 5 and 6 show slightly distorted square–planar geometries, with standard Au–C, Au–Cl, and Au–P bond distances

somewhat longer for gold(III) than for gold(I). The shortest intermolecular Au–Au distance found for the gold(I) compound **4** is 6.4 Å, which discards any gold–gold interaction. The chromium(0) derivative **9** is also a H–bridged dimer that displays a slightly distorted octahedral geometry for its two independent molecules in the crystal. In contrast to **6**, complex **5** is a monomer with the hydrogen atom of the carboxylic group bonded to the O atom of a co–crystallized diethyl ether molecule. This is due to the high steric requirement of the $Au(C_6F_5)_3$ fragment embedding the acid group, which precludes the *ortho* dimerization but not the *para* dimerization. All the compounds show two different C–O bond lengths in the carboxylic functional group (Table 1). A review in the literature reports that the formation of a carboxylic acid dimer requires the absence of competitors, and in the X–ray structure known only about 29% of the compounds form the classic dimer, whereas the remaining 71% form hydrogen bonds with a large variety of other acceptors. 22

Table 1. Selected Bond Lengths [Å] and Angles [deg] for Complexes 3, 4, 5 and 6.

	3 ^a	4 ^b	4	5	6
Au–P	2.26(1)	2.232(4) 2.225(4) °	2.2249(19)	2.3808(18)	2.3768(13)
Au-Cl	2.29(1)	2.278(4) 2.269(4)	2.271(2)	_	_
Au–C	_	_	_	2.070(7) 2.079(7) 2.109(7)	2.068(5) 2.073(5) 2.077(5)
O=C	1.24(4)	1.24(2) 1.21(2)	1.245(9)	1.211(10)	1.239(6)
O–C	1.34(3)	1.29(2) 1.30(2)	1.283(9)	1.329(9)	1.292(7)
P-Au-Cl	172.9(4)	177.5(1) 178.9(1)	178.75(8)	_	_
P-Au-C	_	_	_	176.2(2) 90.86(19) 94.0(2)	171.50(16) 91.58(14) 93.43(14)
C-Au-C	_	_	_	175.1(3) 87.9(3) 87.2(3)	173.45(19) 87.72(19) 87.95(19)
O-C-O	125(4)	124(1) 125(1)	122.1(8)	124.5(8)	124.4(5)

^a Data from reference 19. ^b Data from reference 18. ^c Two independent molecules.

Table 2. Selected Bond Lengths [Å] and Angles [deg] for Compound **9.**

Cr(1)–P(1)	2.3985(9)	C(2)–Cr(1)–P(1)	176.65(14)
Cr(1)-C(1)	1.894(3)	C(1)– $Cr(1)$ – $C(4)$	177.22(15)
Cr(1)-C(2)	1.861(4)	C(3)– $Cr(1)$ – $C(5)$	176.65(17)
Cr(1)-C(3)	1.888(4)	O(1)-C(1)-Cr(1)	178.0(4)
Cr(1)-C(4)	1.900(3)	O(2)– $C(2)$ – $Cr(1)$	177.7(5)
Cr(1)-C(5)	1.889(4)	O(3)-C(3)-Cr(1)	176.9(4)
C(1)-O(1)	1.128(4)	O(4)-C(4)-Cr(1)	176.8(3)
C(17)-O(6)	1.207(3)	O(5)-C(5)-Cr(1)	176.6(3)
C(17)-O(7)	1.319(3)	O(6)-C(17)-O(7)	123.2(2)

Table 3. Hydrogen Bonds involving the carboxylic group for dimers **4**, **6**, and **9**, and monomer **5** [Å and deg].

D-H A	d(D-H)	d(HA)	d(DA)	<(DHA)	
Compound 4					
O(1)- $H(1)$ - $O(2A)$	0.820	1.808	2.594	160.09	
O(1A)-H(1A)-O(2)	0.820	1.808	2.594	160.09	
Compound 6					
O(2)-H(2)-O(1A)	0.820	1.814	2.631	174.97	
O(2A)-H(2A)-O(1)	0.820	1.814	2.631	174.97	
Compound 9					
O(7)–H(7)···O(13)	0.820	1.857	2.676	175.61	
O(14)–H(14A)···O(6)	0.820	1.878	2.698	179.08	
Compound 5					

O(2)-H(2)···O(3) 0.821 1.825 2.626 164.89

Symmetry transformations used to generate equivalent atoms: for compound 4 are -x+1, -y-1, -z; for compound 6 are -x, -y+2, -z+1.

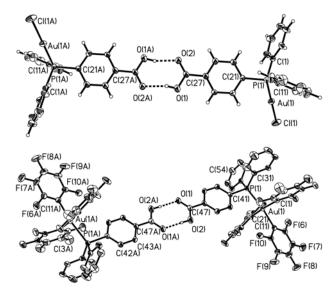


Figure 2. X–ray structures of dimers **4** (above) and **6** (below, H atoms omitted for clarity, except for the carboxylic group). Displacement ellipsoids are at 25% probability level.

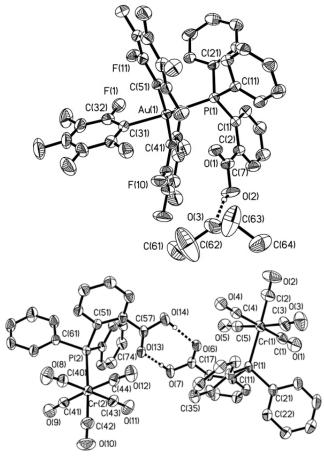


Figure 3. X–ray structure of compound **5** (above), and **9** (below). Displacement ellipsoids are at 30% probability level (H atoms omitted for clarity, except for the carboxylic group).

Hydrogen-bonded triazine-[M] adducts. Triazine (T) was reacted with the diphenylphosphinobenzoic acid ligands 1-2 and the metal complexes 3-10 in THF, in the

appropriate molar ratio (1:1 or 2:1, depending on the number of acid groups in the complex), followed by slow evaporation of the solvent (Scheme 2). This afforded pale brown (free phosphines and gold) or green (chromium) waxy solids, which were then studied to see whether they correspond to defined T^n adducts or not.

Scheme 2. Reactions for the synthesis of supramolecular triazine–metalloacid adducts, \mathbf{T}^n . The H–bonding system is indicated by dashed lines. $R = C_{10}H_{21}$. The attempted syntheses are: i) reactions with compounds 1–6, 9 and 10; ii) the same, with compounds 7 and 8).

The waxy materials obtained in the reactions aimed at producing supramolecular hydrogen bonded adducts were examined by several techniques to find out their nature and thermal properties. They can be classified in three groups: 1) mixtures of the reactants; 2) hydrogen bonded adducts; and 3) uncertain materials. To the first group pertain the gold(III) materials T^5 and T^6 , which show clearly, at room temperature in polarized optical microscopy (POM), a mixture of crystals and liquid, indicating that the corresponding adducts have not been formed. The rest of the compounds apparently show mesophases at room temperature, but with very different thermal behavior. T^2 , T^4 , T^8 and T^{10} resist some heating maintaining the mesophase texture until the clearing point is reached; moreover, as discussed in detail later, small—angle powder X—ray diffraction (SAXS) studies support the formation of columnar mesophases by these hydrogen bonded supramolecular adducts. Finally, whether the triazine forms or not adducts T^1 , T^3 , T^7 , and T^9 is doubtful and their nature is uncertain. Only T^9 displays IR ($v(C\equiv O)$) and SAXS data that might support formation of the adduct: the A_1 mode associated mainly to the CO trans to the phosphine group diminishes clearly in intensity, and shifts +8 (for T^9) or +10 cm $^{-1}$ (for T^{10} , see Fig. S1 in SI). The same behavior was observed in closely related adducts. The fact that T^9 and T^{10}

give quite similar shifts seems to suggest that not only T^{10} but also T^9 might be an adduct.²³ The others (T^1 , T^3 , T^7) quickly decompose under the X-ray observation, with formation of crystals of the starting acid, so their thermal behavior looks uninteresting.

Overall, the results suggest that the stability of the H-bonded adducts versus their separated components is modest and structural variations in the components are critical. Thus, aspects as the size of the metallic moiety (as in T^5 and T^6), or the angle made at the acid ring (2- versus 4-diphenylphosphinobezoic) will determine whether the supramolecular material will be formed or not. The stability of the H-bonded adducts is not very high even for the materials that undoubtedly form adducts and mesophases, and diffusion-ordered NMR spectroscopy (DOSY) shows that, in CDCl₃, acetone-d₆ or in THF-d₈ solution, T^2 , T^4 , T^8 and T^{10} are dissociated into their components. (see Fig. S2 in SI). Thus, the formation of a condensed phase is critical for the formation of adducts.

Thermal behavior. The thermal behavior of the supramolecular adducts was investigated by differential scanning calorimetry (DSC), POM, and SAXS. The triazine used in this work, ²⁴ bearing nine diverging decyloxy chains, displays a columnar hexagonal mesophase (Col_{hex}) from room temperature to 57 °C, when it clears reversibly to the isotropic liquid. ^{13,14} The diphenylphosphinobenzoic acid derivatives 1 and 2 and metallo–organic acid complexes 3–10 are not mesomorphic. Compound 10 and the free phosphines 1 and 2 have melting points in the range 87–175 °C, but complexes 3–9 decompose without melting in the range 162–250 °C. Remarkably, all supramolecular adducts derived from *para*–diphenylphosphinobenzoic acid are liquid crystals at room temperature (Table 4). Fluid and homogenous optical textures could be observed by POM for these adducts: sandy–like textures for the phosphine adduct T² and for the chromium adduct T¹⁰; ill–defined pseudo–fan–shaped texture with some dark (homeotropic) regions for T⁴ and T⁸ (Figure 4). These textures, although non–specific, unambiguously confirm a mesophase for these four adducts that is compatible with a hexagonal columnar arrangement.

Table 4. Optical, thermal and thermodynamic data of triazine (T) and adducts (Tⁿ).

Comp.	Transition ^a	T/ºCb	$\Delta H^b/J~g^{-1}$
T	$Col_{hex} \rightarrow I$	H1: 57.1	2.0
	$I \rightarrow Col_{hex}$	C1: 42.6	1.1
	$Col_{hex} \rightarrow I$	H2: 57.5	1.2
T^1	Dissociated ^c	H1: 37.4	
T ²	$Cr \rightarrow I$	H1: 51	11.2
	$I \rightarrow Col_{hex}$	C1: 29.5	1.7
	$Col_{hex} \rightarrow I$	H2: 35.8	1.7
T^3	Dissociated ^c	H1: 40.7	
T^4	$Col_{hex} \rightarrow I$	H1: 60.0	1.2
	$I \rightarrow Col_{hex}$	C1: 51.6	1.3

	$Col_{hex} \rightarrow I$	H2: 59.6	1.3
\mathbf{T}^7	Dissociated ^c	H1: 40	
T ⁸	$\begin{aligned} & \text{Col}_{\text{hex}} \to \text{I} \\ & \text{I} \to \text{Col}_{\text{hex}} \\ & \text{Col}_{\text{hex}} \to \text{I} \end{aligned}$	H1: 55.6 C1: 29.5 H2: 55.4	1.3 1.0 1.1
T ⁹	Dissociated ^c	H1: 52.5	
T ¹⁰	$\begin{array}{c} \operatorname{Col}_{\operatorname{hex}}^{ d} \to I \\ \operatorname{I} \to \operatorname{Col}_{\operatorname{hex}} \\ \operatorname{Col}_{\operatorname{hex}} \to I \end{array}$	H1: 38.3 C1: 18.1 H2: 35.7	2.5 2.7 3.7

^a Cr, crystalline phase; Col_{hex}, columnar hexagonal phase; I, isotropic liquid. ^b H1, H2, C1: 1st and 2nd heating, 1st cooling; the temperature corresponds to the peak maximum. ^c Dissociated means that the adducts are split into their triazine and metalloacid components upon heating above the temperature mentioned. ^d A lamellar arrangement cannot be fully excluded.

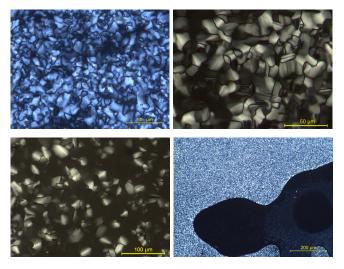


Figure 4. Polarized optical microscopic texture observed for the free triazine T (top left), and for adducts T^4 (top, right), T^8 (bottom left) and T^{10} (bottom right) obtained on cooling from isotropic liquid at room temperature. Enlarged pictures are available in SI Fig. S3.

This thermal behavior was confirmed by DSC measurements (Table 4, in SI Figure S4). T⁴, T⁸ and T¹⁰ behave as classical enantiotropic liquid crystals. For T² the columnar mesophase formed during the first cooling, is maintained at room temperature over several days. With respect to the parent triazine, the mesophase–to–isotropic liquid transition temperature (2nd heating) is very similar for the gold(I) compounds T⁴ (ca. +2 °C) and T⁸ (ca. -2 °C), and lower for compounds T² and the chromium(0) T¹⁰ (about -20 °C). No sign of crystallization or glass transition was detected on cooling the samples to -20 °C, but they became much less fluid and looked frozen, suggesting that a glassy state had been reached. Heating well above the clearing point produced adduct decomposition to give some microcrystals of the starting metallo–organic acids and free triazine. Only a very small difference in transition temperature is observed between the triazine and the corresponding gold adducts (T⁴ and T⁸). The same somewhat unpredicted behavior was found in our previous study with related gold adducts. ¹⁴ We explain this similarity assuming that the metal complex moieties are somehow buried into the dominant aliphatic environment of the azine chains,

in such a way that each discotic unit of adduct appears externally very similar to the triazine discs. As a matter of fact the mesophases of T and T^n (n = 2, 4, 8, 10) mix perfectly in contact experiments. In contrast, addition of additional metal complex to T^n systems does not result in mixing providing further evidence for specific adduct formation.

Further information and the elucidation of the mesophases observed comes from studies of small-angle powder X-ray diffraction as a function of temperature, covering from room temperature up to the isotropic liquid. The supramolecular aggregates show limited stability under prolonged exposure to X-ray beam and temperature. The unambiguous assignment of the mesophases needed, however, access to more small-reflections than visible in the diffractograms acquired with conventional laboratory sources. These missing reflections could be acquired on a synchrotron SAXS line. The diffractograms of the adducts containing 4-diphenylphosphinobenzoic acid as linker, T², T⁴, T⁸, and T¹⁰ exhibit at least two common characteristic features: i) in the small-angle region, one sharp and intense reflection along, in some cases, with additional weaker reflections, which are indicative of long-range ordered low-dimensional lattices; and ii) in the large-angle region, one broad, very strong, scattering halo spreading between 3.5 and 5.5 Å (intensity maximum at about 4.4–4.6 Å), corresponding to the overlap of different, undifferentiated, lateral distances between aliphatic tails and between adduct fragments (undifferentiated h_{ch}+h_{adduct}, Table 5). In all cases, the fundamental reflection dominates over the higher order reflections, and is due to the strong density contrast arising from the alternation of electron-rich columns and electron-poor fluid and continuous zones. This contrast is further enhanced by the presence of the metallic ion within the columns, and logically reduces the higher order reflections (therefore the need to use highly intense source like synchrotron).

The diffractogram of the phosphine adduct T^2 , confirms the formation of a columnar hexagonal mesophase close to 40 °C: it displays the strong and diffuse wide–angle scattering typical of the molten aliphatic chains and cores, along four sharp, small–angle reflections, in the square spacing ratio $1:\sqrt{3}:2:\sqrt{7}$, which were respectively indexed as to the (10), (11), (20) and (21) reflections of a hexagonal lattice, with a parameter of 29.05 Å (Figure 5 and Table 5). On further heating above the isotropization (at T = 65°C), the supramolecular adduct partially dissociates into its elementary components as evidenced by the superposition of the diffraction peaks associated to both the free triazine in its mesophase and the phosphine acid 2 in its crystalline state (SI, Fig. S5). The adduct reforms readily, and recrystallizes on cooling down to 25°C. It shows a reversible behavior only when heated below the clearing transition.

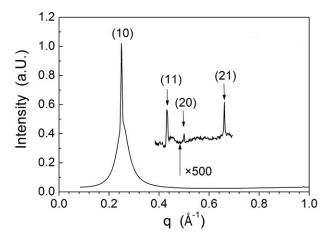


Figure 5. SAXS diffractogram (synchrotron) of adduct **T**² at *ca*. 40 °C, after cooling from isotropic liquid.

The adduct T^4 exhibits a Col_{hex} mesophase at room-temperature, in a temperature range similar to that of T. The diffractograms (Figure 6, SI Fig. S5), recorded at 25°C and 50°C indeed show two or three sharp small-angle reflections of the hexagonal lattice, the broad scattering of the molten chains and cores, as well as an additional diffuse weak halo at mid-angle arising likely from shortrange metal-metal interactions within the columnar structure. Thus, the connection of the [AuCl] fragment onto the phosphine modifies and enhances the mesophase stability with respect to the non-metallic structurally related T² compound. Actually, the presence of the metallic fragment is associated to a slight contraction of the hexagonal cell (Table 5). Similarly, mesomorphism is maintained in the corresponding dimeric adduct (T⁸): T⁸ is mesomorphic at room-temperature and SAXS revealed unequivocally the formation of a Colhex phase, deduced from the presence of the two small-angle reflections indexed as (10) and (11) of an hexagonal lattice (Figure 6, SI Fig. S5). The chromium adduct T^{10} shows mesomorphism, but only in a narrow range around room temperature (Figure 6). Although the nature of the mesophase cannot be unequivocally assigned on the basis of the unique visible reflection, the analogy with the other structurally related adducts T⁴ and T^8 , and the overall similar trends observed with their mesomorphic behavior reasonably support to assign the mesophase as to Colhex too. A lamellar arrangement cannot be fully excluded.

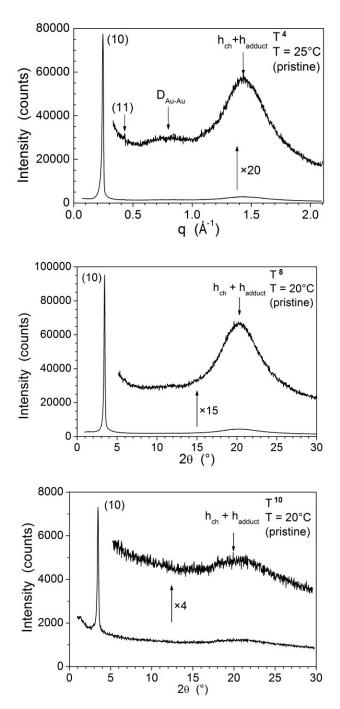


Figure 6. X–ray diffraction patterns for a) T^4 at 25 °C, b) T^8 at 20 °C and c) T^{10} at 20 °C.

As commented above, the reaction between the gold(III)-based acids (**5** or **6**) with triazine do not proceed, and thus do not yield wanted adducts T^5 or T^6 . The diffractograms of the binary mixture T+6 (recorded at 25°C in the pristine state, 55°C and then back at 25°C; see SI, Fig. S5) confirm the non-formation of the H-bonded adduct, as evidenced by the superposition of the distinct signals of each species, namely, the sharp small-angle reflection of T in the Col_{hex} ($T=25^{\circ}C$) which broadens when entering in the isotropic phase ($T=55^{\circ}C$), and the numerous sharp reflections scanning the entire diffraction angle range of **6** in the crystalline state (at all temperatures).

For the materials containing 2-diphenylphosphinobenzoic acid complexes, the results are very different. The material labeled T^3 (T + 3) appears immediately dissociated upon heating, and on beam exposure as shown by SAXS, which reveals phase co-existence between solid free phosphine acid and pure triazine in its mesophase (SI, Fig. S5). T^7 (T + 7) and T^9 (T + 9) (SI, Fig. S5) show a similar behavior.

In summary, mesomorphism is exclusively observed for the analogous para-[M]-phosphine adducts, suggesting that the metallo-organic acids again plays the role of a fourth arm of the triazine thus filling the empty regions between the arms and smoothing the columnar interface.¹⁴ The columnar phase results from the stacking of these pseudo-discotic adducts into columns, with a slight elongation of each unit (disc) when passing from the triazine to the adducts (see hadduct values in Table 5). Unlike other triazine thiolatobenzoic acid systems reported before, ¹⁴ none of the orthosystems exhibits mesomorphic properties, probably because adducts have not been formed. The weakness (T⁴) or absence of the diffuse signal previously observed for the thiolatobenzoic acid compounds at mid-angle, suggests that the metallic ions are essentially camouflaged within the branch of the triazine with little interactions between neighbors and without protruding in the aliphatic continuum. This difference may be ascribed to the different geometry around the P and S atoms, respectively. The tetrahedral geometry around the P atom of the phosphine group will keep the metallic fragment closer to the columnar core due to the bent angle at P, whereas the diverging phenyl entities will be partly mixed with the aromatic parts forming the columnar cores and the aliphatic chains, without dramatically changing the distribution of the electronic density, as it was the case for the thiolatobenzoic acid systems having a closer to linear geometry around the S atom. Obviously, the *ortho* position does not allow for such arrangement, and to the contrary will disrupt the packing of adducts along the columns.

Table 5. Geometrical parameters of mesophases obtained from SAXS for the Tⁿ adducts. [a]

Compound	T/°C	$q/Å^{-1}$	d/Å	hk	I	a/Å	S/Å ²	$V_{mo}l/Å^3$	h _{adduct} /Å
Triazine	30	_	25.83	10	VS(sh)	29.82	770	2966	3.85
T^2	40	0.2498	25.15	10	VS(sh)	29.05	731	3432	4.69
		0.4320	14.54	11	W(sh)				
		0.4997	12.57	20	VW(sh)				
		0.6608	9.51	21	W(sh)				
T^4	25	0.2550	24.64	10	VS(sh)	28.46	701	3845	5.48
		0.4412	14.24	11	W(sh)				
T^8	20	_	25.70	10	VS (sh)	29.7	764	7440	4.87
			14.85	11	VW (sh)				
T^{10}	20	_	26.0	10	VS (sh)	30.1	780	3752	4.81

[a] T = temperature of the experiment; q = wave vector (q = $2\pi/d$); d = d-spacing; hk = Miller indices; I = reflection intensity (VS, very strong; W, weak; VW, very weak; sh: sharp); a = hexagonal lattice parameter; S = cross-columnar section area (S = $A^2\sqrt{3}/2$); V_{mol} = molecular volume (triazine and adducts); h_{adduct} = molecular height per adduct (h_{adduct} = V_{mol}/SN , where N is the number of triazines per complex e.g. N = 1 for monomers, N = 2 for dimers).

Photophysical behavior. The emission and excitation spectra of the free phosphine and metalloorganic acids were recorded in the solid state at 77 K or 298 K, and in CH₂Cl₂ frozen solution at 77 K. None of them emits in solution at 298 K. The emission and excitation spectra of the supramolecular adducts (\mathbf{T}^2 , \mathbf{T}^4 , \mathbf{T}^8 , \mathbf{T}^{10}) were recorded in the solid state at 77 K or 298 K. The spectra of complex 8 and adduct \mathbf{T}^8 at 77 K are shown as representative examples in Figure 7. Details of the excitation and emission spectra are given in Tables S1–S2 in SI.

4–Diphenylphosphinobenzoic acid and all the gold metallo acids are emissive at 77 K in the range 404–520 nm, and some of them also at 298 K with emission maxima from 441 to 485 nm. However, neither the chromium compounds 9–10 nor the free 2–Diphenylphosphinobenzoic acid show any emission in this range. Consequently, this emission is associated to the Au–P(acid) fragment. Many gold(I) compounds are luminescent in the visible region, but luminescent gold(III) compounds are comparatively scarce.

All the adducts emit and show, at 77 K, a structureless broad emission band in the range 419–455 nm, which appears not only for the complexes containing the Au–P(acid) fragment but also for the chromium adduct T^{10} and the free ligand adduct T^2 . Moreover, this emission appears within a narrow range in spite of the modifications in the metallic fragment, and also close to a strong emission of the free triazine, which appears at 423 nm. Thus, the conclusion is that this emission in the adducts is triazine–centered, and the expected phosphine or Au–P centered emissions in T^2 , T^4 and T^8 are of lower intensity and are overlapped by the azine centered emission.

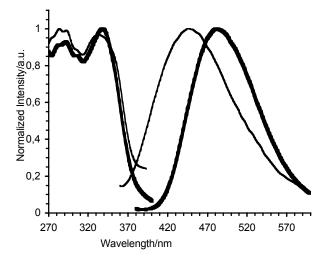


Figure 7. Excitation and emission spectra of **8** (bold line) and T^8 (normal line) dispersed in KBr at 77 K. Note that the plot is in normalized intensity. This produces a deceptive appearance of identical intensity for the two compounds.

Conclusions

2– or 4–Diphenylphosphinobenzoic acids behave towards metal centers as typical monodentate phosphine ligands do. Thus, gold(I) or gold(III), and chromium(0) complexes have been prepared.

The free carboxylic functional groups of these two phosphine acids or their metallo-organic acids produce H-bridged dimers, except for the ortho-phosphine gold(III) complex because of its voluminous substituents at gold. They can also form donor-acceptor adducts with an appropriate triazine, providing some para-phosphine chromium(0) and gold(I) metalloacid-triazine supramolecular adducts that display stable hexagonal columnar mesophases at room temperature. In the columnar stacking of adducts the metallic fragment finds room to accommodate itself as a wedge filling the space between the branches of the trefoil molecular architecture of the triazine units. This is an example showing how the triazine bearing nine lateral alkoxy chains manages to accommodate pretty large metal-organic fragments to produce adducts without losing the mesomorphic behavior. However, the very unfavorable sterics of the *ortho*-phosphine metalloacids is clearly detrimental for the formation of adducts with the triazine. It is doubtful whether they really form at all adducts or simply their adducts do not stand moderate temperatures close to room temperature or X-ray irradiation. The Achilles heel of the supramolecular entities discussed here is the weakness of the connection of the two components, the hydrogen bond. Otherwise it looks that, with heavily alkyl-substituted azines, pretty unfavorable geometries and fairly voluminous groups can be accommodated into discoid products that display mesophases at low temperature with a columnar order.

Experimental Section

General procedures are as reported before. 14 1H, 19F and 31P{1H} NMR chemical shifts are quoted relative to SiMe₄ (external, ¹H), CFCl₃ (external, ¹⁹F) and 85% H₃PO₄ (external, ³¹P). Emission and excitation spectra at 298 K and 77 K were measured in the solid state as finely pulverized KBr mixtures, and in deoxygenated CH₂Cl₂ solutions (about 10⁻³ M) in quartz tubes with a Perkin-Elmer LS-55 spectrofluorimeter. For the characterization of the LC mesophases, in addition to POM and DSC, small-angle X-ray scattering techniques were used. Temperaturevariable small-angle X-ray patterns were obtained using a linear focalized monochromatic Cu- $K\alpha 1$ beam ($\lambda = 1.5405$ Å) using a sealed–tube generator (900 W) equipped with a bent quartz monochromator. In all cases, the crude powder was filled in thin Lindemann capillaries of 1 mm diameter and 10 µm wall thickness in air (corrections for air were made), and then heated to produce the mesophase. An initial set of diffraction patterns was recorded with a curved Inel CPS 120 counter gas-filled detector linked to a data acquisition computer; periodicities up to 70 Å can be measured, and the sample temperature controlled to within ± 0.01 °C from 20 to 200 °C. Alternatively, patterns were also recorded on an image plate; periodicities up to 120 Å can be measured (scanned by STORM 820 from Molecular Dynamics with 50 mm resolution). For some samples, synchrotron patterns were obtained on the SWING synchrotron beamline in the SAXS

configuration at 12 keV energy (proposal 20120951), using a homemade transmission oven of 0.1°C accuracy and filling samples in 1mm Lindemann capillaries.

Synthesis of the precursors

[AuCl(tht)], 27 [Au(C₆F₅)₃(tht)], 28 [Ag(CF₃SO₃)(tht)], 29 and [{(C₁₀H₂₁O)₃C₆H₂NH}₃C₃N₃]¹² were prepared according to literature methods. The other reagents were obtained from commercial sources.

Synthesis of [AuCl(PPh₂C₆H₄CO₂H)] ortho (3), para (4) and [Au(C₆F₅)₃(PPh₂C₆H₄CO₂H)] ortho (5), para (6). To a dichloromethane solution (20 mL) of $[AuX_n(tht)]$ (100 mg; X = Cl, n = 1, 0.31 mmol, for the synthesis of 3 and 4; $X = C_6F_5$, n = 3, 0.13 mmol, for the synthesis of 5 and 6) was added the corresponding diphenylphosphinobenzoic acid 1 or 2 (96 mg, 0.31 mmol, for the synthesis of 3 and 4; 40 mg, 0.13 mmol, for the synthesis of 5 and 6), and the reaction was stirred at room temperature for 90 min. The solution was then concentrated to ca. 5 mL. Addition of hexane afforded compounds 3-6 as white solids. Compound 5 was purified from the starting materials by crystallization from chloroform/diethyl ether mixture. Yield of 3: 134 mg, 80 %. Mp: 205 (dec.). Anal. Calcd (%): C, 42.36; H, 2.81; N, 0. Found: C, 42.55; H, 2.71; N, 0. ¹H NMR (d₆-acetone, 400 MHz): $\delta_{\rm H}$ 7.02 (ddd, $J_{\rm HP}$ = 12.7 Hz, $J_{\rm HH}$ = 7.79 and 1.1 Hz 1H, H³), 7.60–7.53 (m, 10H, H_o and H_p and H_m), 7.69 (tt, J_{HH} = 7.8 and 1.7 Hz, J_{HP} = 1.7 Hz, 1H, H⁴), 7.79 (tt, J_{HH} = 7.7 and 1.5 Hz, J_{HP} = 1.5 Hz, 1H, H⁵), 8.34 (ddd, $J_{HH} = 7.5$ and 1.6 Hz, $J_{HP} = 4.4$ Hz, 1H, H⁶). $^{31}P\{^{1}H\}$ NMR (d₆-acetone, 162) MHz): δ_p 37.49 (s). IR (KBr): 3062 ν (O–H), 1685 ν (C=O) cm⁻¹. Yield of **4**: 140 mg, 84 %. Mp: 200 (dec.). Anal. Calcd (%): C, 42.36; H, 2.81; N, 0. Found: C, 41.97; H, 2.74; N, 0. ¹H NMR (d₆acetone, 400 MHz): δ_H 7.67–7.61 (m, 10H, Ph), 7.73 (dd, J_{HH} = 7.9 and J_{HP} = 12.7 Hz, 2H, H³), 8.20 (dd, $J_{HH} = 7.9$ and $J_{HP} = 2.2$ Hz, 2H, H²). ³¹P{¹H} NMR (d₆-acetone, 162 MHz): δ_P 34.34 (s). IR (KBr): 3062 v(O-H), 1694 v(C=O) cm⁻¹. Yield of 5: 38 mg, 29 %. Mp: 210 (dec.). Anal. Calcd (%): for C, 44.24; H, 1.51; N, 0. Found: C, 44.46; H, 1.98; N, 0. 1 H NMR (CDCl₃, 400 MHz): δ_{H} $6.97 \text{ (dd, } J_{HH} = 7.8 \text{ Hz, } J_{HP} = 13.0 \text{ Hz, } 1H, H^3), 7.34 - 7.63 \text{ (m, } 12H, Ph+ H^4 + H^5), 8.17 \text{ (dd, } J_{HP} = 4.5 \text{ (dd, } J_{HP} =$ Hz, $J_{HH} = 7.2$ Hz, 1H, H⁶). ¹⁹F NMR (CDCl₃, 376 MHz): $\delta_F - 119.5$ (brm, 4F, $F_o - Au$), -121.7 (m, 2F, F_0 -Au), -157.1 (t, N = 18.0 Hz, 3F, F_p -Au), -160.7 (m, 4F, F_m -Au), -161.2 (m, 2F, F_m -Au). ³¹P{¹H} NMR (CDCl₃, 162 MHz): δ_P 23.9 (s). IR (KBr): 3087 ν (O–H), 1689 ν (C=O), 970, 804, 792 (C₆F₅) cm⁻¹. Yield of **6**: 95 mg, 73 %. Mp: 240 (dec.). Anal. Calcd (%): C, 44.24; H, 1.51; N, 0. Found: C, 44.46; H, 1.98; N, 0. 1 H NMR (CDCl₃, 400 MHz): δ_{H} 7.44–7.47 (m, 8H, H m and H o of Ph), 7.53 (dd, $J_{HH} = 8.5$ and $J_{HP} = 11.7$ Hz, 2H, H^3), 7.60 (m, 2H, H^p of Ph), 8.10 (dd, $J_{HH} = 8.5$ and $J_{HP} = 2.5 \text{ Hz}, 2H, H^2$). ¹⁹F NMR (CDCl₃, 376 MHz): $\delta_F - 119.9 \text{ (m, 4F, F}_0 - \text{Au)}, -121.7 \text{ (m, 2F, F}_0 - \text{Au)}$ Au), -156.6 (t, N = 18.8 Hz, 2F, F_p -Au), -156.7 (t, N = 19.4 Hz, 1F, F_p -Au), -160.5 (m, 4F, F_m - Au), -160.8 (m, 2F, F_m-Au). $^{31}P\{^{1}H\}$ NMR (CDCl₃, 162 MHz): δ_{P} 18.1 (s). IR (KBr): 3066 v(O–H), 1702 v(C=O), 969, 804 sh, 795 (C₆F₅) cm⁻¹.

Synthesis of [Au(PPh₂C₆H₄CO₂H)₂](CF₃SO₃): ortho (7), para (8). To an acetone (20 mL) solution of [AuCl(tht)] (50 mg, 0.156 mmol) was added [Ag(CF₃SO₃)(tht)] (54 mg, 0.156 mmol) and the mixture was stirred at room temperature for 1 h protected from the light. Precipitate of AgCl was filtered off. The corresponding diphenylphosphinobenzoic acid (1 or 2: 96 mg, 0.31 mmol) was added to the solution. After stirring for 1 h, the solution was concentrated to ca. 5 mL. Addition of hexanes afforded compounds 7 and 8 as white solids. Yield of 7: 129 mg, 86 %. Mp: 219 (dec.). Anal. Calcd (%): C, 48.86; H, 3.15; N, 0. Found: C, 48.56; H, 3.30; N, 0. ¹H NMR (d₆– acetone, 400 MHz): δ_H 7.07 (ddd, J_{HH} = 7.9 and 1.3, J_{HP} = 12.9 Hz, 1H, H³), 7.62–7.55 (m, 10H, Ph), 7.71 (tt, $J_{HH} = 7.6$ and 1.6, $J_{HP} = 1.6$ Hz, 1H, H^4), 7.81 (tt, $J_{HH} = 7.6$ and 1.5, $J_{HP} = 1.5$ Hz, 1H, H⁵), 8.39 (ddd, $J_{HH} = 7.9$ and 1.4, $J_{HP} = 4.4$ Hz, 1H, H⁶). ¹⁹F NMR (d₆-acetone, 376 MHz): $\delta_F - 79.3$ (s). ${}^{31}P\{{}^{1}H\}$ NMR (d₆-acetone, 162 MHz): δ_{P} 47.4 (s). IR (KBr): 3058 v(O-H), 1702 v(C=O), 1225, 636 (CF₃SO₃) cm⁻¹. Yield of **8**: 72 mg, 48 %. Mp: 162 (dec.). Anal. Calcd (%): C, 48.86; H, 3.15; N, 0. Found: C, 48.80; H, 3.49; N, 0. ¹H NMR (d_6 -acetone, 400 MHz): δ_H 7.61–7.73 (m, 10H, Ph), 7.78 (dd, $J_{HH} = 8.3 \text{ Hz}$, $J_{HP} = 11.7 \text{ Hz}$, 2H, H^3), 8.17 (d, $J_{HH} = 8.3 \text{ Hz}$, 2H, H^2). ¹⁹F NMR (d₆– acetone, 376 MHz): $\delta_F - 79.3$ (s). $^{31}P\{^{1}H\}$ NMR (d₆-acetone, 162 MHz): $\delta_P 45.8$ (s). IR (KBr): 3058 v(O-H), 1719 v(C=O), 1224, 637 (CF₃SO₃) cm⁻¹.

Synthesis of [Cr(CO)₅(PPh₂C₆H₄CO₂H)]: *ortho* (9), *para* (10). To a suspension of [Cr(CO)₆] (110 mg, 0.5 mmol) in 30 mL of acetonitrile was added a solution of Me₃NO (35 mg, 0.5 mmol) in 30 mL of acetonitrile. The mixture was stirred for 3 h under inert atmosphere at room temperature. The solvent was removed under vacuum and the residue was dissolved in tetrahydrofuran (20 mL). Then, a solution of the corresponding diphenylphosphinobenzoic acid (1 or 2: 153 mg, 0.5 mmol) in tetrahydrofuran (20 mL) was added dropwise. After stirring for 2 h, the solvent was removed under vacuum. The dry residue was washed with cold pentane, and recrystallized from diethyl ether to give 9–10 as greenish yellow solids. Yield of 9: 150 mg, 60 %. Mp: 250 (dec.). Anal. Calcd (%): C, 57.84; H, 3.03; N, 0. Found: C, 58.14; H, 3.42; N, 0. ¹H NMR (d₆–acetone, 400 MHz): δ_H 7.08 (dd, $J_{HH} = 8.0$ and $J_{HP} = 11.8$ Hz, 1H, H³), 7.42–7.71(m, 12H, H⁴ + H⁵ + Ph), 8.27 (br, 1H, H⁶). ³¹P{¹H} NMR (d₆–acetone, 162 MHz): δ_P 61.5 (s). IR (KBr): 2064, 1985, 1931 v(CO), 1696 v(C=O) cm⁻¹. Yield of 10: 112 mg, 45 %. Mp: 87. Anal. Calcd (%): C, 57.84; H, 3.03; N, 0. Found: C, 58.11; H, 3.40; N, 0. ¹H NMR (d₆–acetone, 400 MHz): δ_H 7.56–7.61 (m, 10H, Ph), 7.66 (dd, $J_{HH} = 8.3$ and $J_{HP} = 8.3$

= 10.1 Hz, 2H, H³), 8.17 (dd, J_{HH} = 8.3 and J_{HP} = 1.8 Hz, 2H, H²). $^{31}P\{^{1}H\}$ NMR (d₆-acetone, 162 MHz): δ_{P} 56.2 (s). IR (KBr): 2064, 1989, 1934 v(CO), 1702 v(C=O) cm⁻¹.

Reactions to prepare hydrogen-bonded triazine-metallo-organic acid adducts, T^n . The supramolecular complexes were prepared from the pure components (triazine, T and the various acids 1–10). Exact stoichiometric molar amounts of the two compounds were dissolved in dry tetrahydrofuran at room temperature, and the solvent was swept off by passing a stream of gaseous nitrogen, affording the adducts as pale brown (free phosphines and gold) or green (chromium) waxy solids. The corresponding T^n materials where then studied. Only T^2 , T^4 , T^8 , and T^{10} were unambiguously identified as hydrogen bonded adducts.

Single crystal structure determination of metallo-organic acids 4, 5, 6 and 9.

CCDC 1000572–1000575 contain the supplementary crystallographic data for **4**, **5**, **6** and **9**. These data can be obtained free of charge from the Cambridge Crystallographic Data Centre via www.ccdc.cam.ac.uk/data_request/cif. Crystals of **4** and **9** were obtained by slow diffusion of hexanes into an acetone (**4**) or dichloromethane (**9**) solution, at –18°C. Crystals of **5** and **6** were obtained by slow diffusion of diethyl ether into chloroform solutions, at –18°C. The crystals were then mounted on a glass fiber and transferred to the SuperNova Oxford Diffraction diffractometer. Crystal data and details of data collection and structure refinement are given in Table 6. Cell parameters, data reduction and absorption corrections were carried out with the CrysAlis system software. The structure was refined anisotropically on F². All non–hydrogen atomic positions were located in difference Fourier maps and refined anisotropically. The hydrogen atoms were placed in their geometrically generated positions. The structure of **4** contains some disordered solvent molecules, and we were unable to properly model it. Compound **5** crystallizes with incipiently disordered diethyl ether and water molecules. Compound **6** crystallizes with an incipiently disordered chloroform molecule. The four molecules of Cr(0) in the unit cell of **9** crystallize with one highly disordered hexane molecule.

Table 6. Details of Crystallographic Data and Structure Refinement for acids 4, 5, 6 and 9.

Compound	4	$5 \text{ Et}_2\text{OH}_2\text{O}$	6 CHCl ₃	9 0.25 hexane
empirical formula	C ₁₉ H ₁₅ AuClO ₂ P	C ₄₁ H ₁₅ AuF ₁₅ O ₄ P	$C_{38}H_{16}AuCl_3F_{15}O_2P$	$C_{25.50}H_{15}CrO_7P$
fw	538.70	1084.47	1123.79	516.34
temp (K)	293(2)	293(2)	293(2)	293(2)
wavelength (Å)	0.71073	1.54184	0.71073	1.54184
cryst syst	Monoclinic	Monoclinic	Triclinic	Triclinic
space group	P 2(1)/c	P 2(1)/c	<i>P</i> –1	<i>P</i> –1
unit cell dim.: a (Å)	18.9328(5)	14.4299(2)	9.8540(8)	10.9729(5)
b (Å)	7.12915(16)	15.2743(3)	10.4075(4)	14.6769(7)
$c(\mathring{A})$	16.7656(4)	18.6396(4)	19.2765(17)	15.7818(8)

α (deg)	90	90	92.533(5)	78.135(4)
β (deg)	94.008(2)	98.8129(19)	99.200(7)	74.224(4)
χ (deg)	90	90	93.152(5)	88.521(4)
χ (deg) vol. (Å ³)	2257.40(10)	4059.79(14)	1945.7(2)	2392.4(2)
Z	4	4	2	4
density (calc.)	-	1.774	1.918	1.434
(Mg/m^3)				
abs. coeff. (mm ⁻¹)	6.712	8.194	4.135	4.951
F(000)	1024	2088	1080	1052
cryst habit	Needle	Plate	Plate	Plate
cryst size (mm)	$0.32 \ x \ 0.05 \ x$	0.26 x 0.13 x	0.27 x 0.19 x 0.07	0.29 x 0.19 x
	0.05	0.08		0.08
Θ range for data	2.16 to 28.68	3.10 to 75.15	2.10 to 28.76	2.97 to 75.08
colln				
index ranges	$-21 \le h \le 24$,	-17<=h<=16,	-12<=h<=9,	-13<=h<=6,
	$-6 \le k \le 9$,	-18<=k<=12, -23<=l<=22	-7<=k<=13, -23<=l<=22	-18<=k<=18, -19<=l<=18
	-22 <= 1 <= 12			
reflns collected	9039	12575	13316	14476
ind. reflns	4774 [R(int) = 0.0258]	7959 [R(int) = 0.0338]	8046 [R(int) = 0.0260]	9356 [R(int) = 0.0247]
max, and min, trans.	0.752 and 0.525	0.601 and 0.349	0.796 and 0.450	0.720 and 0.480
data/restraints/param.		7959 / 0 / 559	8046 / 0 / 541	9356 / 0 / 622
goodness-of-fit on	1.115	1.021	1.041	1.025
F^2				
final R indices $[I >$	R1 = 0.0447,		R1 = 0.0391, wR2	
2σ(<i>I</i>)]	wR2 = 0.1296	wR2 = 0.1198	0.0869	wR2 = 0.1070
R indices (all data)	R1 = 0.0686,		R1 = 0.0504, wR2	
	wR2 = 0.1421	wR2 = 0.1397	0.0937	wR2 = 0.1215
larg. diff. peak hole	1.429 and	1.089 and-1.470	1.113 and-1.018	0.391 and-0.330
$(e.Å^{-3})$	-0.649			

Acknowledgements. We thank the Spanish Comisión Interministerial de Ciencia y Tecnología (Project CTQ2011–25137) and the Junta de Castilla y León (Project VA302U13) for financial support. The authors acknowledge SOLEIL for provision of synchrotron radiation facilities, particularly Dr. Javier Pérez for assistance in using beamline SWING. B. H. and B. D. thank the CNRS for support.

Supporting Information. X-ray crystallographic details in CIF format. FTIR spectra of triazine, chromium metallo-organic acid 10 and the corresponding aggregate with the triazine T¹⁰ (Figure S1), DOSY spectra of T² and T¹⁰ (Figure S2), polarized optical microscopic texture observed for the free triazine T, aggregate T², T⁴, T⁸ and T¹⁰ obtained on cooling from isotropic liquid at room temperature, (Figure S3), DSC thermograms for the free triazine T, aggregate T², T⁴, T⁸ and T¹⁰. (Figure S4), X-ray diffraction patterns not included in the text (Figure S5), excitation and emission data for all the compounds and adducts (Tables S1–S2). This material is available free of charge via the Internet at http://pubs.acs.org.

References

- (1) (a) Ringsdorf, H.; Schlarb, B.; Venzmer, J. Angew. Chem. Int. Ed. 1988, 27, 113–158. (b) Zeng, F; Zimmerman, S. C. Chem. Rev. 1997, 97, 1681–1712. (c) Kato, T.; Mizoshita, N.; Kishimoto, K. Angew. Chem. Int. Ed. 2006, 45, 38–68. (d) Lehn, J.–M. Chem. Soc. Rev. 2007, 36, 151–161. (e) Lehn, J.–M. Top. Curr. Chem. 2007, 322, 1–32. (f) Rosen, B.M.; Wilson, C.J.; Wilson, D.A.; Peterca, M.; Imam, M.R.; Percec, V. Chem. Rev. 2009, 109, 6275–6540. (g) Lehn, J.M. Angew. Chem. Int. Ed. 2013, 52, 2836–2850. h) Tschierske, C. Angew. Chem. Int. Ed. 2013, 52, 8828–8878. (i) Rosen, B.M.; Roche, C.; Percec, V. Top. Curr. Chem. 2013, 333, 213–253
- (2) (a) Kato, T.; Fréchet, J. M. J. Am. Chem. Soc. 1989, 111, 8533 8534. (b) Brienne, M.–J.; Gabard, J.; Lehn, J.–M.; Stibor, I. J. Chem. Soc. Chem. Commun. 1989, 1868–1870. (c) Willis, K.; Price, D. J.; Adams, H.; Ungar, G.; Bruce, D. W. J. Mater. Chem. 1995, 5, 2195 2199; (d) Suárez, M.; Lehn, J.–L.; Zimmerman, S. C.; Skoulios, A.; Heinrich, B. J. Am. Chem. Soc. 1998, 120, 9526 9532; (e) Grunert, M.; Howie, R. A.; Kaeding, A.; Imrie, C. T. J. Mater. Chem. 1997, 7, 211–214; (f) Würthner, F.; Yao, S.; Heise, B.; Tschierske, C. Chem. Commun. 2001, 2260 2261; (g) Mizoshita, N.; Monobe, H.; Inoue, M.; Ukon, M.; Watanabe, T.; Shimizu, Y.; Hanabusa, K.; Kato, T. Chem. Commun. 2002, 428–429; (h) Jin, S.; Ma, Y.; Zimmerman, S. C.; Cheng, S. Z. D. Chem. Mater. 2004, 16, 2975 2977; (i) Kajitani, T.; Kohmoto, S.; Yamamoto, M.; Kishikawa, K. Chem. Mater. 2004, 16, 2329 2331; (j) McCubbin, J. A.; Tong, X.; Zhao, Y.; Snieckus, V.; Lemieux, R. P. Chem. Mater. 2005, 17, 2574 2581; (k) Barberá, J.; L. Puig, P. Romero, Serrano, J. L.; Sierra, T. J. Am. Chem. Soc. 2006, 128, 4487–4492.
- (3) (a) Tschierske, C. *Prog. Polym. Sci.* **1996**, *21*, 775–852. (b) Paleos, C. M.; Tsiourvas, D. *Liq. Cryst.* **2001**, *28*, 1127 1161. (c) Bruce, D. W. *Adv. Inorg. Chem.* **2001**, *52*, 151–204.
- (4) (a) Kaafarani, Bilal R. *Chem. Mater.* **2011**, *23*, 378–396. (b) Pisula, W.; Kastler, M.; Wasserfallen, D.; Mondeshki, M.; Piris, J.; Schnell, I.; Mullen, K. *Chem. Mater.* **2006**, *18*, 3634–3640. (c) O'Neill, M.; Kelly, S. M. *Adv. Mater.* **2003**, *15*, 1135–1146. (d) Kumar, S. *Chem. Soc. Rev.* **2006**, *35*, 83–109. (e) Laschat, S.; Baro, A.; Steinke, N.; Giesselmann, F.; Hagele, C.; Scalia, G.; Judele, R.; Kapatsina, E.; Sauer, S.; Schreivogel, A.; Tosoni, M. *Angew. Chem. Int. Ed.* **2007**, *46*, 4832–4887. (f) Sergeyev, S.; Pisulab, W.; Geerts, Y. H. *Chem. Soc. Rev.* **2007**, *36*, 1902–1929.
- (5) Donnio, B.; Guillon, D.; Bruce D. W.; Deschenaux, R. *Metallomesogens*, in *Comprehensive Coordination Chemistry II: From Biology to Nanotechnology*, ed. McCleverty, J. A. and Meyer, T. J.; Elsevier, Oxford, UK 2003, vol. 7 (ed. Fujita, M. and Powell, A.), ch. 7.9, pp. 357–627.
- (6) (a) Deschenaux, R.; Monnet, F.; Serrano, E.; Turpin, F.; Levelut, A.-M. *Helv. Chim. Acta* **1998**, *81*, 2072 2077. (b) Massiot, P.; Imperór–Clerc, M.; Veber, M.; Deschenaux, R. *Chem. Mater.* **2005**, *17*, 1946–1951. (c) Donnio, B.; Seddon, J. M.; Deschenaux, R. *Organometallics* **2000**, *19*, 3077 3081.
- (7) Ziessel, R.; Pickaert, G.; Camerel, F.; Donnio, B.; Guillon, D.; Césario, M.; Prange, T. J. Am. Chem. Soc. 2004, 126, 12403 12413.
- (8) Giménez, R.; Elduque, A.; López, J. A.; Barberá, J.; Cavero, E.; Lantero, I.; Oro, L. A.; Serrano, J. L. *Inorg. Chem.* **2006**, *45*, 10363 10370.
- (9) (a) Li, S.-Y.; Chen, C.-J.; Lo, P.-Y.; Sheu, H.-S.; Lee, G.-H.; Lai, C. K. *Tetrahedron* **2010**, *66*, 6101–6112; (b) Wang, Y.J.; Song, J.H.; Lin, Y.S.; Lin, C.; Sheu, H. S.; Lee, G. H.; Lai, C. K. *Chem. Commun.* **2006**, 4912 4914.
- (10) (a) Coco, S.; Espinet, E.; Espinet, P.; Palape, I. *Dalton Trans.* **2007**, 3267–3272. (b) Coco, S.; Cordovilla, C.; Domínguez, C.; Espinet, P. *Dalton Trans.* **2008**, 6894–6900.
- (11) Dechambenoit, P.; Ferlay, S.; Donnio, B.; Guillon, D.; Hosseini, M. W. Chem. Commun. 2011, 47, 734-736.
- (12) (a) Goldmann, D.; Dietel, R.; Janietz, D.; Schmidt, C.; Wendorff, J. H. *Liq. Cryst.* **1998**, *24*, 407–411. (b) Barberá, J.; Puig, L.; Serrano, J. L.; Sierra, T. *Chem. Mater.* **2004**, *16*, 3308–3317. (c) Barberá, J.; Puig, L.; Serrano, J. L.; Sierra, T. *Chem. Mater.* **2005**, *17*, 3763–3771.
- (13) Coco, S.; Cordovilla, C.; Domínguez, C.; Donnio, B.; Espinet, P.; Guillon, D. Chem. Mat. 2009, 21, 3282–3289.
- (14) Domínguez, C.; Heinrich, B.; Donnio, B.; Coco, S.; Espinet, P. Chem. Eur. J. 2013, 19, 5988–5995.
- (15) Chen, H. H.; Lin, H. A.; Chien, S. C.; Wang, T. H.; Hsu, H. F.; Shih, T. L., Wu, C. J. Mater. Chem. 2012, 22, 12718-12722.
- (16) (a) Schumann, H.; H. Hemling, V. Ravindar, Y. Badrieh, J. Blum J. Organomet. Chem. 1994, 469, 213–219. (b) Wong, W.-K.; Zhang, L.; Wong, W.-T. Chem. Commun. 1998, 673–674. (c) Barbaro, P.; Ghilardi, C. A.; Midollini, S.; Orlandini, A.; Ramirez, J. A.; Scapacci G. J. Organomet. Chem. 1998, 555, 255–262. (d) Komon, Z. J. A.; Bu, X.; Bazan G. C. J. Am. Chem. Soc. 2000, 122, 12379–12380. (e) Correia, J. D. G.; Domingos, A.; Santos, I.; Bolzati, C.; Refosco, F.; Tisato F. Inorg. Chim. Acta 2001, 315, 213–219. (f) Kuang, S.-M.; Fanwick, P. E.; Walton, R. A. Inorg. Chem. 2002, 41, 405–412. (g) Kuang, S.-M.; Fanwick, P. E.; Walton, R. A. Inorg. Chem. Commun. 2002, 5, 134–138. (h) Kuang, S.-M.; Fanwick, P. E.; Walton, R. A. Inorg. Chem. 2002, 41, 1036–1038. (i) Kuang, S.-M.; Fanwick, P. E.; Walton, R. A. Inorg. Chim. Acta 2002, 338, 219–227. (j) Sánchez, G.; García, J.; Meseguer, D.; Serrano, J. L.; García, L.; Pérez, J.; López, G. Dalton Trans. 2003, 4709–4717. (k) Schultz, T.; Pfaltz A. Synthesis 2005, 1005–1011. (l) Rueff, J.-M.; Perez, O.; Leclaire, A.; Couthon–Gourves, H.; Jaffres, P.-A. Eur. J. Inorg. Chem. 2009, 4870–4876. (m) Phadnis, P. P.; Dey, S.; Jain, V. K.; Nethaji, M.; Butcher, R. J. Polyhedron 2006, 25, 87–94. (n) Kawatsura, M.; Ata, F.; Wada, S.; Hayase, S.; Uno, H.; Itoh, T. Chem. Commun. 2007, 298–300. (o) Samec, J. S. M.; Grubbs, R. H. Chem. Eur. J. 2008, 14, 2686–2692. (p) Uhl, W.; Bock, H. R.; Hepp, A. Rogel, F.; Voss, M. Z. Anorg. Allg. Chem. 2010, 636, 1255–1262. (q) Uhl, W.; Bock, H. R.; Kosters, J.; Voss, M. Z. Anorg. Allg. Chem. 2010, 636, 1851–1859.
- (17) Chandrasekaran, A.; Day, R. O.; Holmes R. R. Inorg. Chem. 2001, 40, 6229-6238.
- (18) Mohr, F.; Jennings, M. C.; Puddephatt, R. J. Angew. Chem. Int. Ed. 2004, 43, 969 –971.
- (19) Howe, B. P.; Parish, R. V.; Pritchard, R. G. Quim. Nova 1998, 21, 564 568.

- (20) Pellei, M.; Lobbia, G. G.; Santini, C.; Spagna, R.; Camalli, M.; Fedeli, D.; Falcioni, G. Dalton Trans. 2004, 2822–2828.
- (21) (a) Kaharu, T.; Matsubara, H.; Takahashi, S. *J. Mater. Chem.* **1992**, *2*, 43–47. (b) Kaharu, T.; Matsubara, H.; Takahashi, S. *Mol. Cryst. Liq. Cryst.* **1992**, *220*, 191–199. (c) Bruce, D. W.; Lea, M. S.; Marsden, J. R.; Rourke, J. P.; Tajbakhsh, A. R. *J. Mater. Chem.* **1994**, *4*, 1017–1020. (d) Rourke, J. P.; Bruce, D. W.; Marder, T. B. *J. Chem. Soc. Dalton Trans.* **1995**, 317–318. (e) Bruce, D. W.; Lea, M. S.; Marsden, J. R. *Mol. Cryst. Liq. Cryst.* **1996**, 275, 183–194. (f) Tsiourvas, D.; Kardassi, D.; Paleos, C. M.; Gehant, S.; Skoulios A. *Liq. Cryst.* **1997**, *23*, 269–274. (g) Barral, M. C.; Jiménez–Aparicio, R.; Priego, J. L.; Royer, E. C.; Torres, M. R.; Urbanos, F. A. *Inorg. Chem. Commun.* **1999**, *2*, 153–155. (h) Tsiourvas, D.; Kardassi, D.; Paleos, C. M.; Skoulios A. *Liq. Cryst.* **2000**, *27*, 1213–1217. (i) Hatano, T.; Kato, T. *Chem. Commun.* **2006**, 1277–1279. (j) Frein, S.; Auzias, M.; Sondenecker, A.; Vieille–Petit, L.; Guintchin, B.; Maringa, N.; Süss–Fink, G.; Barberá, J.; Deschenaux, R. *Chem. Mater.* **2008**, *20*, 1340–1343. (k) Bottazzi, T.; Cecchi, F.; Zelcer, A.; Heinrich, B.; Donnio, B.; Guillon, D.; Cukiernik F. D. *J. Coord. Chem.* **2013**, *66*, 3380–3390. (22) Steiner, T. *Angew. Chem. Int. Ed.* **2002**, *41*, 48–76.
- (23) Pitifully the IR spectrum in the range of v(C=O) and v(C=N) absorptions does not provide clear cut information on the formation of hydrogen bonds due to low quality of the spectra (arising from the phyical state of the non crystalline samples) and easy overlap of the carboxylic acid and the triazine bands. This also applies to the group of compounds that are adducts.
- (24) For other related non-discotic mesogens with a three-fold symmetry see: (a) Meier, H.; Lehmann, M. *Angew. Chem. Int. Ed.* **1998**, *37*, 643 645; (b) Omenat, A.; Barberá, J.; Serrano, J. L.; Houbrechts, S.; Persoons, A. *Adv. Mater.* **1999**, *11*, 1292 –1295; (c) Meier, H.; Lehmann, M.; Kolb, U. *Chem. Eur. J.* **2000**, *6*, 2462 –2469. (d) Lee, C. H.; Yamamoto, T. *Tetrahedron Lett.* **2001**, *42*, 3993 3996. (e) Attias, A.–J.; Cavalli, C.; Donnio, B.; Guillon, D.; Happiot, P.; Malthête, J. *Chem. Mater.* **2002**, *14*, 375 –384. (f) Meier, H.; Holst H. C.; Oehlhof, A. *Eur. J. Org. Chem.* **2003**, 4173 4180. (g) Gómez-Lor, B.; Alonso, B.; Omenat, A.; Serrano J.–L. *Chem. Commun.* **2006**, 5012–5014. (h) Lehmann, M.; Jahr, M.; Donnio, B.; Graf, R.; Gemming, S.; Popov, I. *Chem. Eur. J.* **2008**, *14*, 3562 –3576. (i) Lehmann, M.; Jahr, M. *Chem. Mater.* **2008**, *20*, 5453–5456. (j) Lehmann, M.; Jahr, M.; Grozema, F. C.; Abellon, R. D.; Siebbeles L. D. A.; Muller, M. *Adv. Mater.* **2008**, *20*, 4414–4418. (k) Kotha, S.; Kashinath, D.; Kumar, S. *Tetrahedron Lett.* **2008**, *49*, 5419–5423. (l) Lehmann, M. *Chem.-Eur. J.* **2009**, *15*, 3638–3651. (m) García–Frutos, E. M.; Pandey, U. K.; Termine, R.; Omenat, A.; Barberá, J.; Serrano, J. L.; Golemme, A.; Gómez–Lor, B. *Angew. Chem. Int. Ed.* **2011**, *50*, 7399 –7402. (n) Achalkumar, A. S.; Hiremath, U. S.; Shankar Rao, D. S.; Krishna Prasad, S.; Yelamaggad C. V. *J. Org. Chem.* **2013**, *78*, 527–544.
- (25) (a) Roundhill, D. M.; Fackler Jr., J. P *Optoelectronic Properties of Inorganic Compounds*; Plenum Press: New York, 1998. (b) Balch, A. L. *Angew. Chem. Int. Ed.* **2009**, 48, 2641–2644. (c) Tiekink, E. R.T.; Kang, J.-G. *Coord. Chem. Rev.* **2009**, 253, 1627–1648; (d) He, X.; Yam, V. W. W. *Coord. Chem. Rev.* **2011**, 255, 2111–2123.
- (26) Herbst, A.; Bronner, C.; Dechambenoit, P.; Wenger, O. S. Organometallics 2013, 32, 1807–1814, and references therein
- (27) Usón, R.; Laguna A.; Laguna, M. Inorg. Synth. 1989, 26, 85–91.
- (28) Usón, R.; Laguna A.; Laguna, M.; Fernández, E.; Jones P. G.; Sheldrick, G. M. J. Chem. Soc. Dalton Trans. 1982, 1971–1976.
- (29) Bardají, M.; Crespo, O.; Laguna, A.; Fischer, A. K. *Inorg. Chim. Acta* **2000**, *304/1*, 7–16.
- (30) CrysAlisPro Software system, Version 1.171.32; Oxford Diffraction, Oxford Ltd., Xcalibur CCD system, 2007.
- (31) SHELXTL program system version 5.1; Bruker Analytical X-ray Instruments Inc.: Madison, WI, 1998.

For Table of Contents Synopsis

Diphenylphosphinobenzoic Acids as Linkers in [2,4,6– $\{(C_{10}H_{21}O)_3C_6H_2NH\}_3C_3N_3$] Triazine Adducts with Metal Complex, which Self–Organize into Room Temperature Hexagonal Columnar Mesophases

Ana B. Miguel–Coello, ¹ Manuel Bardají, ¹,* Silverio Coco, ¹,* Bertrand Donnio, ^{2,3} Benoît Heinrich, ² and Pablo Espinet ¹,*

¹IU CINQUIMA/Química Inorgánica, Facultad de Ciencias, Universidad de Valladolid, E–47071 Valladolid, Spain.

²Institut de Physique et Chimie des Matériaux de Strasbourg (IPCMS), UMR 7504 (CNRS–Université de Strasbourg), 23 rue du Loess, BP 43, 67034 Strasbourg Cedex 2, France.

³Complex Assemblies of Soft Matter Laboratory (COMPASS), UMI 3254 (CNRS–SOLVAY–University of Pennsylvania), CRTB, 350 George Patterson Boulevard, Bristol, PA 19007, USA.

*Author to whom correspondence should be addressed. E-mail: <u>bardaji@qi.uva.es</u>; scoco@qi.uva.es; espinet@qi.uva.es

Table of contents synopsis

Gold(I) or chromium(0) phosphine complexes with 4–diphenylphosphinobenzoic acid react with 2,4,6–triarylamino–1,3,5–triazine affording H–bonded supramolecular adducts display hexagonal columnar (Col_{hex}) mesophases.

Synopsis Artwork:

