

Behaviour of hollow pultruded GFRP square beams with different shear span-to-depth ratios

Journal:	<i>Journal of Composite Materials</i>
Manuscript ID:	Draft
Manuscript Type:	Original Manuscript
Date Submitted by the Author:	n/a
Complete List of Authors:	Muttashar, Majid; University of Southern Queensland, Centre of Excellence in Engineered Fibre Composites Karunasena, Warnu; University of Southern Queensland, Centre of Excellence in Engineered Fibre Composites Manalo, Allan; University of Southern Queensland, Centre of Excellence in Engineered Fibre Composites Lokuge, Weena; University of Southern Queensland, Centre of Excellence in Engineered Fibre Composites
Keywords:	Pultruded sections, fibre composites, elastic properties, characterization, shear span, full-scale testing
Abstract:	It is important to determine accurately the elastic properties of fibre reinforced polymer (FRP) composites material, considering that their member design is often governed by deflection rather than strength. In this study, the elastic properties of the pultruded glass FRP (GFRP) square sections were evaluated firstly using full-scale with different shear span to depth (a/d) ratios and tested under static four-point bending. Back calculation and simultaneous methods were then employed to evaluate the flexural modulus and shear stiffness and were compared with the results of the coupon tests. Secondly, the full-scale beams were tested up to failure to determine their capacity and failure mechanisms. Finally, prediction equations describing the behaviour of the pultruded GFRP square beams were proposed and compared with the experimental results. The results indicate that the back calculation method gives more reliable values of elastic properties of GFRP profiles. In addition, the behaviour of the beams is strongly affected by the a/d ratios. The shear was found to have a significant contribution on the behaviour of beams with lower a/d ratios while the flexural stress played a major part for higher a/d ratios. The proposed equation, which accounts for the combined effect of the shear and flexural stresses, reasonably predicted the failure load of pultruded GFRP square beams.

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60



SCHOLARONE™
Manuscripts

For Peer Review

Research paper

Behaviour of hollow pultruded GFRP square beams with different shear span-to-depth ratios
(Title contains 11 words)

Running headline: Behaviour of Hollow Pultruded GFRP square Beams with Different Shear Span-to-Depth Ratios
(78 characters)

by

Majid Muttashar^{1,2}, Warna Karunasena¹, Allan Manalo^{1,*} and Weena Lokuge¹

¹ Centre of Excellence in Engineered Fibre Composites (CEEFC),

School of Civil Engineering and Surveying, University of Southern Queensland,
Toowoomba, 4350, Australia

² Department of Civil Engineering, College of Engineering, University of Thi Qar, Iraq.

Submitted to

Journal of Composite Materials

Corresponding Author*:

Allan Manalo

Senior Lecturer in Civil Engineering (Structural)
Centre of Excellence in Engineered Fibre Composites (CEEFC),
School of Civil Engineering and Surveying,
University of Southern Queensland,
Toowoomba, Queensland 4350, Australia
E-mail: allan.manalo@usq.edu.au

Manuscript summary:

Total pages 21 (including 1-page cover)
Number of figures 18
Number of tables 7

Behaviour of hollow pultruded GFRP square beams with different shear span-to-depth ratios

Majid Muttashar^{1,2}, Warna Karunasena¹, Allan Manalo^{1,*} and Weena Lokuge¹

Abstract

It is important to determine accurately the elastic properties of fibre reinforced polymer (FRP) composites material, considering that their member design is often governed by deflection rather than strength. In this study, the elastic properties of the pultruded glass FRP (GFRP) square sections were evaluated firstly using full-scale with different shear span to depth (a/d) ratios and tested under static four-point bending. Back calculation and simultaneous methods were then employed to evaluate the flexural modulus and shear stiffness and were compared with the results of the coupon tests. Secondly, the full-scale beams were tested up to failure to determine their capacity and failure mechanisms. Finally, prediction equations describing the behaviour of the pultruded GFRP square beams were proposed and compared with the experimental results. The results indicate that the back calculation method gives more reliable values of elastic properties of GFRP profiles. In addition, the behaviour of the beams is strongly affected by the a/d ratios. The shear was found to have a significant contribution on the behaviour of beams with lower a/d ratios while the flexural stress played a major part for higher a/d ratios. The proposed equation, which accounts for the combined effect of the shear and flexural stresses, reasonably predicted the failure load of pultruded GFRP square beams.

¹ Centre of Excellence in Engineered Fibre Composites (CEEFC), School of Civil Engineering and Surveying, University of Southern Queensland, Toowoomba, 4350, Australia

² Department of Civil Engineering, College of Engineering, University of Thi Qar, Iraq.

*Corresponding author:

Allan Manalo, Centre of Excellence in Engineered Fibre Composites (CEEFC), School of Civil Engineering and Surveying, University of Southern Queensland, Toowoomba, 4350, Australia

Email: allan.manalo@usq.edu.au

Keywords: Elastic properties, characterization, shear, flexural, failure load, GFRP beams

Introduction

Fibre reinforced polymer (FRP) composites emerged as a promising material to satisfy the increasing demand for better performing and more durable civil infrastructures¹. Recently, FRP composites have been used in bridges, because of their high stiffness, strength-to-weight ratios, corrosion resistance and durability². In addition to these superior properties, the process of producing FRP sections allows the designer to specify different material properties for different parts of the cross section³. Nevertheless, the use of these advanced materials in structural applications is constrained due to limited knowledge on their material properties and structural behaviour. Therefore it is of paramount importance to investigate the properties of pultruded FRP sections so that they can be broadly utilised in structural applications.

A number of micromechanical simulations have already been developed to predict the properties of pultruded beams such as flexural and shear modulus⁴⁻⁶. The mechanical properties estimated using these models showed a good correlation with the experimental results. However, the models require accurate information on the processing details of the FRP profiles such as individual properties of fibres and resin, the fibre volume fraction and the composition of the laminates⁷. Therefore, the use of these models as a design tool for structural purposes is likely to complicate the process. Thus, several researchers investigated coupon specimens to determine the effective mechanical properties of the composites and used these properties to predict the behaviour of full scale pultruded FRP profiles^{8, 9}. Manaloet al.¹⁰ mentioned that there are limited test methods and equipment to characterise the properties of thick FRP composites by using the results of coupon tests. Moreover, the limited dimensions in the transverse direction of the majority of the pultruded GFRP sections added a new obstacle to the applicability of available test standards¹¹. The complex internal

1
2
3 structure of composites and/or the variation of its mechanical properties within the element
4
5 itself warrant testing of full scale sections to obtain realistic design properties.
6

7 Guadeset al. ¹² conducted an experimental investigation to characterise the
8
9 mechanical properties of square pultruded sections (100 mm x 100 mm) using both coupon
10
11 and full – scale specimens. Although, there was a good agreement between the coupon and
12
13 full-scale results for single span beams, the effect of shear deformation on the behaviour of
14
15 the pultruded profiles was neglected as the beam considered in sufficiently long. Bank ¹³
16
17 indicated that the effect of shear on thin walled FRP sections is very significant especially for
18
19 shorter beams and should be considered in determining the elastic properties of composite
20
21 material. In support of this, Bank ¹³ and Neto and Rovere ¹⁴ conducted experiments using
22
23 full-scale sections to determine the flexural (E) and shear (G) modulus of FRP composite
24
25 beams. In both situations, three – point bending tests were used to characterise the behaviour
26
27 of beams with different spans. Even though same test procedure and almost similar section
28
29 properties were used in both research, there was a huge difference between the calculated
30
31 E/G ratios as Bank ¹³ determined the elastic modulus based on Timoshenko Beam Theory
32
33 while Neto and Rovere ¹⁴ used the graphical (simultaneous) test method. Mottram ¹⁵ stated
34
35 that the sensitivity of the graphical method in determining the slope (of the regression line
36
37 through the data points) can lead to a significant change in the E and G calculations. As a
38
39 result, there is a need to revisit the graphical method used to find the flexural and shear
40
41 modulus.
42
43
44
45
46

47 To the authors' knowledge, there are very limited experimental studies conducted to
48
49 determine the structural properties of full – scale FRP composite beams made of vinyl ester
50
51 resin with E-glass fibre reinforcement oriented in different directions. In this study, hollow
52
53 pultruded GFRP square beams with different shear span-to-depth (a/d) ratios were tested
54
55 using static four – point bending configuration. Graphical (simultaneous) and back
56
57
58
59
60

1
2
3 calculation methods were used to calculate the E and G and compared with the results of the
4
5 coupon test. In addition, the effect of a/d ratio on the strength and failure behaviour of the
6
7 GFRP beams was analysed. Based on the experimental results of this research, a simplified
8
9 prediction equation to obtain the failure load of the GFRP beams was proposed with due
10
11 consideration given to the effect of a/d ratio. These predicted failure loads are then compared
12
13 with the experimental results.
14
15

16 17 **Determination of flexural and shear modulus (Beam Theory)**

18
19 The relatively low elastic modulus of GFRP leads to designs being governed by deflection
20
21 and buckling limitations, instead of strength^{16, 17}. In addition, the anisotropic nature of the
22
23 FRP composites results in low shear modulus to longitudinal elastic modulus ratio.
24
25 Accordingly, the contribution of shear deformation in the total deformation becomes
26
27 significant and should be considered in designing composite structures^{3, 5, 14}. This shear
28
29 contribution can be theorised by using Timoshenko beam theory. This theory incorporates
30
31 shear deformation of thin walled composite sections in deflection and investigates its effect in
32
33 a quantitative manner in order to reliably determine the E and G for the pultruded FRP
34
35 section. In this method the controlling equations are:
36
37
38

$$39 \quad EI \frac{\partial \phi}{\partial x} = M \quad (1)$$

$$40 \quad \frac{\partial \delta}{\partial x} + \phi = \frac{V}{KGA} \quad (2)$$

41
42 where I is the second moment of area, ϕ is the bending slope, M is the bending moment, δ is
43
44 the total deflection, V is the shear force and A is the cross-sectional area. The shear
45
46 coefficient K is a constant which accounts for the shear distribution over the beam cross
47
48 section. For homogenous box profile, K can be calculated using the equation recommended
49
50 by Bank⁷:
51
52
53
54

$$55 \quad K = \frac{80}{192 + (v^*G/E)(-12)} \quad (3)$$

where ν , G and E refer to the longitudinal Poisson's ratio, shear modulus and elastic modulus, respectively of the section. By solving equations 1 and 2 for the case of four- point load bending with the load applied at a distance (a) from the support point ($a=L/3$ in this case, where L is the beam span), the total deflection can be obtained as follows:

$$\delta = \frac{23 PL^3}{1296 EI} + \frac{PL}{6KGA} \quad (4)$$

where P is the total applied load, EI is the flexural stiffness and KGA is the shear stiffness.

Two techniques are commonly used to calculate EI and KGA by using the above equation. The first technique is called "back calculation method (BCM)" which was based on the Bernoulli equation to determine the EI from the strain readings on the outer flange surfaces at mid-span (in the constant moment region):

$$EI = \frac{Mc}{\varepsilon} \quad (5)$$

where c is the distance from the neutral axis to the outermost fibre, and ε is the measured strain. After EI is calculated, Equation 4 can be used to back calculate KGA .

The second technique is referred to as "simultaneous method (SM)" where at least two different spans should be investigated experimentally. Each test produces a data set for load, deflection and span. These three terms are known in Equation 4 with EI and KGA as two unknowns. For better interpretation of the method, Equation 4 is divided throughout by $PL/6A$ as follows:

$$\frac{6A\delta}{PL} = \frac{23}{216E} \left(\frac{L}{r}\right)^2 + \frac{1}{KG} \quad (6)$$

This represents a straight line, with $(L/r)^2$ being the independent variable on the horizontal axis and $6A\delta/PL$ being the dependent variable on the vertical axis. Herein, r is the radius of gyration of the section defined by $r = \sqrt{I/A}$. By plotting the variable $\frac{6A\delta}{PL}$ against $\left(\frac{L}{r}\right)^2$, the elastic modulus can be found from the slope of the straight line and the shear modulus from the intercept on the vertical axis:

$$E = \frac{23}{216 * slope} \quad (7)$$

$$KG = \frac{1}{intercept} \quad (8)$$

Experiment program

Material properties

Pultruded GFRP square sections (125 mm x 125 mm x 6.5 mm thickness) produced by Wagner's Composite Fibre Technologies (WCFT), Australia were used in this study. These sections are made from vinyl ester resin with E-glass fibre reinforcement. The density of these pultruded profiles is 2050 kg/m³. As per standard ISO 1172¹⁸, the burnout test revealed an overall glass content of 78% by weight in these profiles. The stacking sequence of the plies is [0⁰/+45⁰/0⁰/-45⁰/0⁰/-45⁰/0⁰/+45⁰/0⁰], where the 0⁰ direction aligns with the longitudinal axis of the tube. Table 1 shows the mechanical properties of the pultruded sections determined from coupon tests.

Table 1. Mechanical properties from coupon test

Characterization of elastic properties for pultruded sections

Following the methodology proposed by Bank¹³, GFRP pultruded profiles with three different a/d ratios were tested under static four - point bending. The details of the tested specimens are listed in Table 2. The load was applied at the third points of the span and shear span to total length (a/L) was maintained at 1/3 for all tests. Figure 1 shows the schematic illustration of the test set-up and the tests were conducted according to ASTM D7250¹⁹. A 2000 kN capacity servo hydraulic testing machine was used with a loading rate of 2 mm/min. All specimens were tested only up to approximately 20% of the failure load to ensure that the beams are still in the elastic range. Strain gauges (PFL-20-11-1L-120) of 20 mm length were attached to the bottom face at the mid-span of the specimens. Laser displacement transducer

was used to measure the mid-span deflection. The applied load and the deflection of the loading ram were recorded using the Systems 5000 data acquisition system.

Table 2. Details of the specimens tested for the elastic properties

Figure 1. Experimental set-up for characterisation of elastic properties.

Behaviour of hollow pultruded GFRP composite beams

Hollow GFRP pultruded sections with four different a/d ratios were tested up to failure under static four point bending test. In contrast to section 3.2, the load was applied at the two points with a load span equal to 300 mm. The constant load span was used to keep the upper face of the section under same condition for all specimens and to take account of the limitation on the length of the test frame. Vertical supports were provided to prevent lateral buckling. The details of the tested specimens are listed in Table 3. Figure 2 shows the experimental set up. A 2000 kN capacity universal machine was used for applying the load. Steel plates were provided at the support and loading points to minimise indentation failure.

Table 3. Details of the specimens tested for the behaviour of GFRP beams

Figure 2. Experimental setup for the behaviour of GFRP beams.

Experimental results and observations

The experimental results for the elastic properties and the behaviour of full scale beams are discussed in this section.

Elastic properties of GFRP sections

E and G using back calculation method. The load versus deflection curves for all specimens are shown in Figure 3. Linear elastic behaviour up to 20 kN can be observed from these. The variations of E and KGA with load for all specimens are shown in Figures 4 to 6. From these curves, it can be seen that these parameters start at a high value but reduce with increasing load. In order to minimise the errors that might have occurred due to deflection

1
2
3 measurements in this study, EI and KGA were computed from the average of several points
4 spaced within a range of $L/800$ to $L/600$ deflection as suggested by Hayes and Lesko²⁰. The
5 average calculated values of E and KGA from the BCM are summarized in Table 4. In this
6
7 table, a numerical value for the moment of inertia has been used. The shear modulus G is
8
9 separated from KGA using the k determined from equation (3) and the nominal cross section
10
11 area of the beam. The average value of E was 47.2 GPa which is 20% higher than the coupon
12
13 test results. The higher flexural modulus obtained from the full section compared with the
14
15 coupon specimens can be related to the continuity of $\pm 45^\circ$ fibres along the length of the
16
17 pultruded beams. In addition, the shear modulus value of 4 GPa is comparable with the value
18
19 suggested by Mottram¹⁵ for a standard GFRP pultruded profile.
20
21
22
23
24

25
26 **Figure 3.** Load – deflection relationship for GFRP beams.

27
28 **Figure 4.** Elastic modulus (E) and Shear stiffness (KGA) versus Load for $a/d = 1.6$

29
30 **Figure 5.** Flexural Modulus (E) and Shear Stiffness (KGA) versus Load for $a/d = 2.4$

31
32 **Figure 6.** Flexural Modulus (E) and Shear Stiffness (KGA) versus Load for $a/d = 3.2$

33
34 **Table 4.** Summary of average E and KGA for each span for GFRP beam testing (BCM)

35
36 *E and G using simultaneous method.* In order to determine the elastic properties E and G , a
37
38 graph for $6A\delta/PL$ versus $(L/r)^2$ was plotted as shown in Figure 7. A linear regression was
39
40 used to obtain the slope, intercept and the coefficient of correlation, which are also shown in
41
42 the figure. The E and G values were then calculated using equations 7 and 8, respectively.
43
44 The calculated E in this method is 56.1 GPa which is higher than the coupon test results by
45
46 about 43 %. In contrast, G is 3.3 GPa which is less than the average value for standard
47
48 pultruded profiles by about 17 %.
49
50

51
52 **Figure 7.** Typical graph to determine E and KG using simultaneous method.

53
54
55 *Behaviour of hollow pultruded GFRP composite beams*
56
57
58
59
60

1
2
3 *Load-deflection behaviour.* Figure 8 shows the load - deflection curves for the GFRP
4 pultruded beams, which shows a linear behaviour until failure. There is a non- linear response
5 before the final failure for the beams with a/d ratios of 1.2 and 2.4. This behaviour is possibly
6 due to the crushing of the corners of the specimen at the support and at the loading points
7 which leads to separation of the web – flange junction. This progressive failure results in the
8 web to continue carrying the applied load. The load carrying capacity of the beam is affected
9 by the variation of the a/d ratio whereas a decreasing trend was observed with increasing a/d
10 ratio. All the beams show a brittle failure in both flexural and transverse shear failure modes.
11 Table 5 presents a summary of the test results with respect to failure load, corresponding
12 deflection and failure mode.
13
14
15
16
17
18
19
20
21
22
23
24

25 **Table 5.** Summary of experimental results for GFRP beams
26
27

28 *Stress -strain behaviour.* The strain measurements for the beams at the top and bottom faces
29 in addition to the strain at the shear path are shown in Figures 9 to 11. It can be seen that the
30 tension strain at the bottom face is higher than the top face compression strain (i.e. for a/d
31 ratio of 6 and stress 250 MPa the tension strain reaches 4700 micro strain compared with
32 4000 micro-strain in the compression side). There was a different trend in the strain on the
33 top and bottom sides. The tension strains increased linearly up to failure, whereas the
34 compression strains began to decrease non – linearly as the load exceeded approximately
35 75% of the ultimate failure load. At the top side, the strain was negative demonstrating that
36 the profile is compressed, as expected. With increasing load, however, the values tend to
37 become positive indicating that the top surface is moving from being compressed to
38 tensioned as shown in Figure 9. This behaviour reflects the onset of buckling considering
39 that the flange can be assumed to be simply supported at the loading points. Consequently,
40 the increase in the applied load increased the compression component of the moment which
41 results in a local buckling of the flange. Figure 10 shows that the tensile strain decreases
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3 with decreasing shear span. The bottom side of the tested specimens were subjected to
4
5 extensive tensile straining although failure cannot be observed there even after the
6
7 compression region at the loading zone has failed entirely. Figure 11 shows that shear strain
8
9 increases with decreasing a/d due to the fact that a significant portion of the shear is
10
11 transferred directly to the support by an inclined strut. As a result the amount of the direct
12
13 load transfer increases with decreasing a/d ratio. In summary, the failure initiated at web –
14
15 flange junction and followed by buckling and/or crushing in the web depending on the a/d
16
17 ratio: beams with higher a/d ratio experienced buckling failure whereas beams with lower
18
19 a/d ratio experienced crushing.
20
21

22
23 **Figure 8.** Load – deflection curves for GFRP beams.

24
25 **Figure 9.** Stress versus compression strain.

26
27 **Figure 10.** Stress versus tensile strain.

28
29 **Figure 11.** Stress versus shear strain.

30
31
32 *Failure mode.* The different failure modes of the GFRP beams are shown in Figure 12. The
33
34 observed failure modes can be classified as flexural failure and transverse shear failure. The
35
36 shorter beams (a/d ratios of 1.2 and 2.4) displayed progressive damage accumulation, which
37
38 is indicated by the drops in the load – deflection curves, with the increasing of the applied
39
40 load. It was observed that the specimens had cracked and some twisted away from the centre
41
42 towards one side. The mode of failure observed was transverse shear failure resulting in the
43
44 delamination and cracking of the fibre along the edges of the pultruded beam in addition to
45
46 local buckling on the compression flange as shown in Figures 13(a) and (b). Moreover, it was
47
48 observed that the failure initiated at web-flange junctions and followed by premature
49
50 buckling and crushing in the webs. This failure behaviour is described as a potential failure
51
52 for pultruded GFRP sections under concentrated bearing load conditions ²¹. For beams with
53
54 a/d ratios of 3.6 and 6, the failure occurred at the points of loading and distinct cracks
55
56
57
58
59
60

1
2
3 developed on the top surface and side of the tubes. Furthermore, cracks developed at the
4 intersection between the flange and the web due to the buckling, leading to separation
5 between them. It was also observed that delamination crack happened at the compression
6 surface and later progressed into the sides as a result of local buckling initiation as shown in
7 Figure 13(c) and (d). Similar observation was reported by Guadeset al.¹² and Kumaret al.²²
8 in their investigations on the flexural behaviour of 100 and 76 mm square pultruded FRP
9 tubes. In their studies, however, they reported that the final failure of the specimen occurs
10 mainly due to the effect of the local buckling of the thin wall which results in material
11 delamination and cracking of the fibre along the edges of the beam under the point loads.
12 Shear crack was not observed even for beams with the lowest a/d ratio. The possible reason
13 for this is the presence of the $\pm 45^\circ$ plies in addition to the main fibre on the tube which
14 provides a stronger shear resistance along the transverse direction.
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29

30 **Figure 12.** Failure modes of GFRP beams for different shear span to depth ratios.
31

32 *Discussion*

33
34
35 *Determination of elastic properties.* Table 6 gives a summary of the properties of the GFRP
36 profiles based on the coupon and full scale tests. It can be seen from this table that there is a
37 significant difference between the results determined from coupon and full scale tests. The
38 main reason between the coupon and full scale results is the effect of discontinuity of the
39 fibres (especially the $+45^\circ$) in the small solid coupon of composite material. However, the
40 continuity of the fibres in the full-scale beam results in higher effective elastic properties than
41 the coupon specimens. Using these properties, the load-deflection behaviour of the full-scale
42 pultruded GFRP beams were calculated using equation 4 and compared with the experimental
43 results. Figure 13 displays comparison between the experimental and the predicted deflection
44 calculated by using Timoshenko Beam Theory (equation 4). Elastic properties obtained from
45 full scale test (using BCM and SM) and coupon test have been used to predict the deflection.
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3 It can be seen that the Timoshenko Beam Theory provides a good approximation for the
4
5 curves determined by the experimental tests. It can also be observed from the figure that
6
7 using the elastic properties from BCM to calculate the beam deflection showed a good
8
9 correlation with the experimental results for all a/d ratios. In contrast, analytical results using
10
11 SM underestimated the experimental results and using coupon test results overestimated the
12
13 deflection as shown in Figure 13. SM generally is relatively sensitive to the accuracy of the E
14
15 measurement. When the span is short and for the same applied load, the deflection is in
16
17 minimal. This observation is similar with Roberts and Al-Ubaidi²³ wherein they indicated
18
19 that the measured elastic properties of Pultruded FRP I-profile can change substantially
20
21 depending on the sensitivity of the graphical method. Therefore, it can be concluded that the
22
23 elastic properties (E and G) determined using the BCM can reliably predict the behaviour of
24
25 full scale GFRP beams.
26
27
28
29

30 Figure 14 shows the relationship between the flexural and shear deflection percentage
31
32 of total deflection as a function of a/d ratio. The flexural and shear deflection was calculated
33
34 using the average value obtained in this study ($E/G = 11.6$). It can be seen that the flexural
35
36 deflection constitutes approximately 40% of the total deflection for a/d of 1.2. In contrast,
37
38 shear deflection was 60 % for the same a/d ratio. These observations reflect the significant
39
40 contribution of shear deformation in the total deflection of beams with low shear span to
41
42 depth ratio. From the figure it can also be observed that the percentage of shear deflection is
43
44 less than 10% for a/d of 10 and a ratio of 20 is required to decrease the shear deflection to
45
46 less than 5%. Therefore, for composite beams with a/d equal or less than 10 the effect of
47
48 shear deformation should be accounted in the total deflection calculation.
49
50
51
52

53 **Table 6.** Summary of experimental properties for GFRP beams
54

55 **Figure 13.** Comparison of theoretical and experimental deflection of beams with different a/d
56
57 ratios.
58
59
60

1
2
3 **Figure 14.** Contribution of flexural and shear deflection for beams with different a/d ratios.

4
5 *Effect of a/d ratio on shear stress.* The effects of shear span to depth ratio on the shear stress
6
7 of the GFRP beams were evaluated by calculating the shear stress experienced by the beams
8
9 using equation 9:

$$\tau = \frac{VQ}{2It} \quad (9)$$

10
11
12
13
14
15
16 where V is the shear force, Q is the first moment of area, I is the moment of inertia, and t is
17
18 the wall thickness. The calculated values of shear stress at failure for different a/d ratios of
19
20 the GFRP beams are shown in Figure 15. The results showed that the a/d ratio has a
21
22 significant effect on the shear stress experienced by the pultruded GFRP beams. The reason is
23
24 that the shorter span beams can be subjected to higher failure load which means higher shear
25
26 force resulting in higher shear stress according to Equation 9. As a result, it can be seen that
27
28 the shear stress increases with decreasing a/d ratio. Similar behaviour has been documented
29
30 for composite sandwich beams and timber beams tested with different a/d ratios²⁴⁻²⁶. The
31
32 authors indicated that shorter beam is subjected to a higher shear stress compared with longer
33
34 span beams. They also mentioned that due to the core weakness, the shorter beams failed due
35
36 to shear. In this study, no shear cracks were observed on the tested beams at the region of
37
38 maximum shear even for short span beams.
39
40
41
42

43
44 The relationship between the shear stress and the a/d ratios seems to be linear. Almost
45
46 all the tested sections failed in similar mode by local buckling under the applied load
47
48 followed by cracking at the compression side and the delamination of the plies. Although the
49
50 tensile strain is low for small a/d ratios, the bottom face of the beam displays a crushing of
51
52 fibres at the support without any failure at the mid-span as shown in Figure 12. The reason
53
54 for this is the higher applied load corresponding to lower a/d ratio.
55
56
57
58
59
60

1
2
3 The maximum calculated shear stress of the pultruded GFRP beams with shear span to depth
4 ratio of 1.2 and 6 are 55 and 32 MPa, respectively. These shear stresses are 45% and 27%,
5
6
7 respectively, of the shear strength of the pultruded profile given in Table 1. These lower
8
9 percentages indicated that the shear stress is not only the factor which affected the behaviour
10
11 of the pultruded beams but also the flexural stress. Manaloet al. ¹⁰ mentioned that these
12
13 combined stresses played an important part in understanding the overall behaviour of
14
15 composites and should be considered in the design and analysis of composite materials.
16
17

18
19 **Figure 15.** Shear stress versus shear span to depth ratio for GFRP beam.

20
21 *Effect of a/d ratio on flexural stress.* The flexural behaviour of the GFRP hollow sections
22
23 have been studied by calculating the bending stress using equation 10:
24

$$\sigma = \frac{Mc}{I} \quad (10)$$

25
26
27
28
29
30 The calculated bending stresses for GFRP beams with different a/d ratios are shown in Figure
31
32 16. It can be seen that the bending stress increases with increasing a/d ratio. The maximum
33
34 bending stress with a/d ratios of 1.2 and 6 are 98 and 300 MPa, respectively. These bending
35
36 stress values are 21% and 66% of the compression strength, respectively, and 13% and 41%,
37
38 respectively, of the tensile strength of the pultruded profile as mentioned in Table 1. This
39
40 explains the reason why the failure is happening at the compression side. Furthermore, the
41
42 results indicated that the specimen experiences considerable flexural stresses even at a/d ratio
43
44 of 1.2 which contributed to the failure mechanisms. Similar result was reported by Turvey
45
46 and Zhang ²⁷ in their investigation on the shear failure strength of web – flange junctions in
47
48 pultruded GRP profiles. In their study, however, they reported that failure is a function of
49
50 combined high shear and bending stresses at the interfaces of different plies.
51
52
53

54
55 **Figure 16.** Bending stress versus shear span to depth ratio for GFRP beam.

1
2
3 *Effect of a/d ratio on failure mode.* The GFRP pultruded beams showed a brittle failure mode.
4
5 The failure happened without any reduction in the slope of the load – deflection behaviour.
6
7 The beams with a/d ratio of more than 3 exhibited a flexural mode of failure. The failure of
8
9 those beams was controlled by the buckling under the load points followed by cracks and
10
11 delamination at the compression face in addition to a web – flange junction failure as shown
12
13 in Figures 12(c) and (d). The beams with a/d less than 3 showed a transverse shear failure.
14
15 This type of failure was resulting in the delamination and cracking of the fibre along the
16
17 edges of the pultruded beam in addition to local buckling on the compression flange. This
18
19 failure behaviour was reported by Turvey and Zhang²⁷ and Wu and Bai²¹ as a web – flange
20
21 junction failure which caused mainly by the concentrated bearing load conditions. A change
22
23 in the slope of the load – deflection behaviour has been noticed. In some cases, it can be seen
24
25 that there are some drops in the load at the failure progress stage for the beams with spans
26
27 lower a/d ratios. This failure response is due to the progressive damage accumulation of the
28
29 section. No pure shear failure or shear cracks appeared in all of the tested beams. The main
30
31 reason for that is the stacking sequence of the plies of the GFRP pultruded sections are in the
32
33 form of ± 45 degrees. It was clearly noticed that the failure cracks position was closer to the
34
35 top loading point than to the supports.
36
37
38
39

40 41 **Prediction of failure load for pultruded GFRP beams with different a/d ratio**

42
43
44 The contribution of the shear deformation was clearly observed for all a/d ratios considered in
45
46 this study. Therefore, in order to estimate the failure load of the pultruded GFRP beams, it is
47
48 important to account for the shear and the bending stresses in the prediction equation.
49
50

51 52 *Proposed prediction equation*

53
54 Based on the experimental results, buckling failure occurred at the concentrated load points
55
56 and/or near the support locations. The main reason for this behaviour is the high shear forces
57
58
59
60

that typically develop at those locations. Bank ⁷ stated that, when the beam is subjected to high shear forces and high bending moment, the web is subjected to combined shear stress (τ) and axial compressive or tensile (flexural) stress, (σ). As a result, the combined effect of both stresses is significant and should be accounted for in the prediction of failure load. Structural plastics design manual ASCE ²⁸ recommends using an interaction equation based on the isotropic plate theory to calculate the critical load which takes into account the combined effect of shear and flexural stresses. This equation expressed in the form:

$$\frac{\sigma_{act}}{\sigma_{all}} + \frac{\tau_{act}}{\tau_{all}} \leq 1 \quad (11)$$

where σ_{act} and τ_{act} are the actual flexural and shear stresses, respectively, σ_{all} and τ_{all} are the corresponding material allowable stresses. In this formula the combined effect of the shear and flexure has been suggested and the failure load can be calculated using the following equation:

$$P = \frac{1}{\frac{ac}{2I\sigma_{all}} + \frac{Q}{2I\tau_{all}}} \quad (12)$$

In this study, a linear interaction equation similar to ASCE equation is proposed to predict the failure load of the pultruded GFRP beams which account for the combined effect of shear and flexure. In the proposed equation, buckling stress $\sigma_{buckling}$ calculated according to Bank ¹³ has been used instead of the allowable compressive strength due to the fact that almost all the tested hollow pultruded profiles failed with local buckling. Therefore, the predicted failure load of the pultruded GFRP beams can be calculated as:

$$P = \frac{1}{\frac{ac}{2I\sigma_{buckling}} + \frac{Q}{2I\tau_{all}}} \quad (13)$$

The allowable stresses of the pultruded GFRP material are listed in Table 1.

Comparison between predicted and the experimental failure loads

1
2
3 The predicted failure load of the pultruded GFRP beams tested using 4 – point load and the
4 percentage difference between the predicted and actual (experimental) average failure loads
5 are summarised in Table 7. For clarity, the comparison is also shown in Figure 17.
6
7
8

9
10 It can be seen from Table 7 and Figure 17 that the proposed equation (13) shows a good
11 agreement between the predicted and the actual failure load. For beam with a/d ratio 1.2, the
12 proposed equation overestimates the failure load by 11%. This indicates that the beams are
13 more likely to fail by transverse shear failure and the shear has the higher effect on the
14 section's failure mode. In contrast, the flexural compression stress is the more dominant
15 stress to cause the failure for pultruded beams with a/d ratios of 3.6 – 6. Moreover, it can be
16 clearly noticed that the use of equation (12) to predict the failure load depends on the ultimate
17 flexural stress will overestimate the failure load by as much as 31 to 44 %. Figure 18 shows
18 the percentages of stress contribution from the failure stress of the pultruded beams. As seen
19 from the figure, for beams of a/d ratio 1.2, shear stress contribution (57%) for the failure load
20 is higher than that for the flexural stress (42%). For beams with higher a/d ratio, the flexural
21 stress becomes the dominant stress to cause the failure with 79% of the failure load compared
22 with 21% of shear stress, respectively. These percentages showed that the predicted
23 contributions compare well with the experimental contributions for shear and flexural
24 stresses. In general, the proposed equation 13 provided a conservative but practical estimation
25 of the failure load of the pultruded GFRP beams with different a/d ratios.
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44

45
46 **Table 7.** Predicted failure load compared with the actual failure load
47

48
49 **Figure 17.** Comparison between the predicted and the actual failure loads.
50

51
52 **Figure 18.** Percentages of stress contribution from the total failure stress.
53

54 **Conclusions**

55
56
57
58
59
60

1
2
3 The behaviour of GFRP pultruded square beams with different shear span to depth (a/d)
4 ratios was investigated using the four-point bending test. Similarly, the elastic properties of
5 the beams were determined by testing full-scale specimens. The following conclusions can be
6 drawn based on the results of the investigation:
7
8
9
10

- 11 1. The back calculation method gives more reliable values of effective flexural and shear
12 moduli of pultruded hollow GFRP square sections compared with simultaneous
13 method and coupon test. This method is based on the Bernoulli equation and uses the
14 strain readings at mid-span of the beam. A good correlation between the predicted and
15 the actual load-deflection behaviour was achieved using the elastic properties
16 determined from this method.
17
18
- 19 2. The shear deformation contributes by as much as 50% to the total deflection of beams
20 with low a/d ratio. Thus, it is recommended to account for the shear deflection in the
21 deflection calculation of GFRP beams when (a/d) is less than or equal to 6.
22
23
- 24 3. The shear stress experienced by the beam decreases with increasing a/d . In contrast,
25 the flexural stress increases with increasing a/d ratio.
26
27
- 28 4. The failure of the beam is governed by the buckling under the loading points followed
29 by cracks and delamination at the web-flange junction at the compression face.
30
31
- 32 5. The proposed equation accounting for the combined effect of shear and flexural
33 stresses in pultruded GFRP square beams and accounting for the buckling stress of
34 composites reasonably predicted the failure load of full size pultruded GFRP beams.
35
36
- 37 6. Aside from shear and flexural stresses, it was found that there is a complexity on the
38 overall behaviour of pultruded GFRP square beams with low a/d , which needs further
39 investigation.
40
41
42
43
44
45
46
47
48
49
50
51
52
53

54 55 **Acknowledgement** 56 57 58 59 60


The authors would like to acknowledge the support of Wagner's Composite Fibre Technologies (WCFT) for providing the GFRP pultruded sections. The first author would like to acknowledge the financial support by the Ministry of Higher Education and Scientific Research-Iraq.

References

1. Bakis C, Bank LC, Brown V, et al. Fiber-reinforced polymer composites for construction-state-of-the-art review. *Journal of Composites for Construction*. 2002; 6: 73-87.
2. Hollaway L. A review of the present and future utilisation of FRP composites in the civil infrastructure with reference to their important in-service properties. *Construction and Building Materials*. 2010; 24: 2419-2445.
3. Bank LC. Shear coefficients for thin-walled composite beams. *Composite Structures*. 1987; 8: 47-61.
4. Barbero EJ, Fu S-H and Raftoyiannis I. Ultimate bending strength of composite beams. *Journal of Materials in Civil Engineering*. 1991; 3: 292-306.
5. Omidvar B. Shear coefficient in orthotropic thin-walled composite beams. *Journal of Composites for Construction*. 1998; 2: 46-56.
6. Nagaraj V and GangaRao HV. Static behavior of pultruded GFRP beams. *Journal of Composites for Construction*. 1997; 1: 120-129.
7. Bank LC. *Composite for Construction Structural Design with FRP Materials*. New Jersey: Jone Wiley & Sons, 2006, p.551.
8. Davalos JF, Salim H, Qiao P, Lopez-Anido R and Barbero E. Analysis and design of pultruded FRP shapes under bending. *Composites Part B: Engineering*. 1996; 27: 295-305.
9. Roberts T and Masri H. Section properties and buckling behavior of pultruded FRP profiles. *Journal of reinforced plastics and composites*. 2003; 22: 1305-1317.
10. Manalo A, Mutsuyoshi H and Matsui T. Testing and characterization of thick hybrid fibre composites laminates. *International Journal of Mechanical Sciences*. 2012; 63: 99-109.
11. Cardoso D, Harries K and Batista E. On the Determination of Mechanical Properties for Pultruded GFRP Sections. *International Conference on FRP composites in Civil Engineering*. Vancouver, Canada: International Institute for FRP in Construction 2014.
12. Guades E, Aravinthan T and Islam MM. Characterisation of the mechanical properties of pultruded fibre-reinforced polymer tube. *Materials & Design*. 2014; 63: 305-315.
13. Bank LC. Flexural and shear moduli of full-section fiber reinforced plastic(FRP) pultruded beams. *Journal of Testing and Evaluation*. 1989; 17: 40-45.
14. Neto A and Rovere H. Flexural stiffness characterization of fiber reinforced plastic (FRP) pultruded beams. *Composite structures*. 2007; 81: 274-282.
15. Mottram J. Shear modulus of standard pultruded fiber reinforced plastic material. *Journal of Composites for Construction*. 2004; 8: 141-147.
16. Chambers RE. ASCE design standard for pultruded fiber-reinforced-plastic (FRP) structures. *Journal of Composites for Construction*. 1997; 1: 26-38.
17. Parke G and Hewson N. ICE manual of bridge engineering. *history*. 2008; 6: 3.
18. ISO 1172. Textile-glass-reinforced plastics, prepregs, moulding compounds and laminates: Determination of the textile-glass and mineral-filler content- Calcination methods. 1996.
19. ASTM D7250. ASTM D7250/D7250M-06 Standard practice for determine sandwich beam flexural and shear stiffness. West Conshohocken, (PA): ASTM International, 2006.
20. Hayes M and Lesko J. The effect of non-classical behaviors on the measurement of the Timoshenko shear stiffness. *Proc 2nd Inter Conf FRP Composites in Civil Engineering-CICE*. 2004, p. 873-880.


- 1
2
3 21. Wu C and Bai Y. Web crippling behaviour of pultruded glass fibre reinforced polymer sections.
4 *Composite Structures*. 2014; 108: 789-800.
5 22. Kumar P, Chandrashekhara K and Nanni A. Structural performance of a FRP bridge deck.
6 *Construction and Building Materials*. 2004; 18: 35-47.
7 23. Roberts T and Al-Ubaidi H. Flexural and torsional properties of pultruded fiber reinforced plastic
8 I-profiles. *Journal of Composites for Construction*. 2002; 6: 28-34.
9 24. Dai J and Hahn HT. Flexural behavior of sandwich beams fabricated by vacuum-assisted resin
10 transfer molding. *Composite Structures*. 2003; 61: 247-253.
11 25. Yoshihara H and Furushima T. Shear strengths of wood measured by various short beam shear
12 test methods. *Wood science and technology*. 2003; 37: 189-197.
13 26. Awad ZK, Aravinthan T and Manalo A. Geometry effect on the behaviour of single and glue-
14 laminated glass fibre reinforced polymer composite sandwich beams loaded in four-point bending.
15 *Materials & Design*. 2012; 39: 93-103.
16 27. Turvey GJ and Zhang Y. Shear failure strength of web-flange junctions in pultruded GRP WF
17 profiles. *Construction and Building Materials*. 2006; 20: 81-89.
18 28. ASCE. Structural Plastics Design Manual. *ASCE Manuals and Reports on Engineering Practice*
19 63. Reston, VA: American Society of Civil Engineering, 1984.
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

All Figures

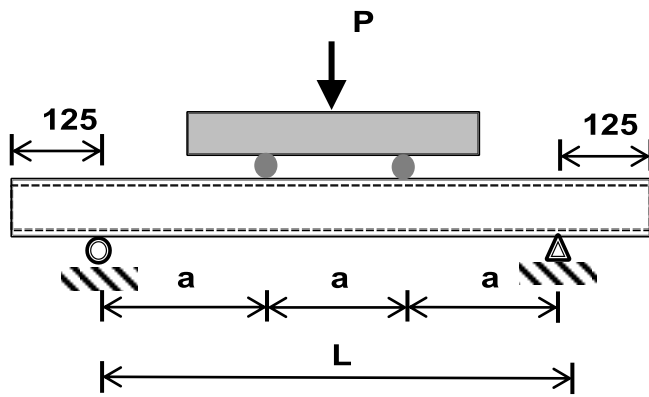

*All dimensions are in mm as per Table 2

Figure 1. Experimental set-up for characterisation of elastic properties

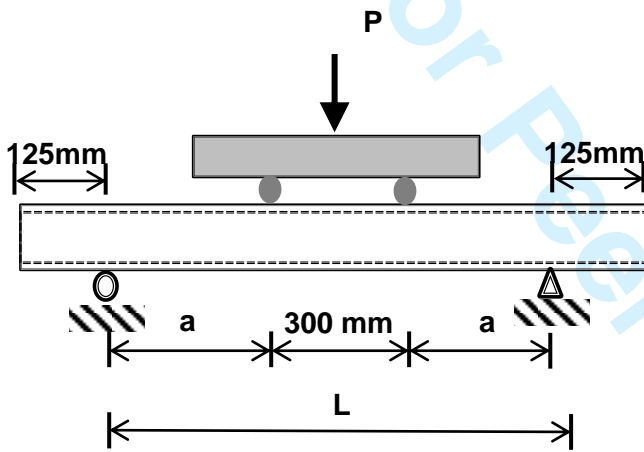

*All dimensions are in mm as per Table 3

Figure 2. Experimental setup for the behaviour of GFRP beams

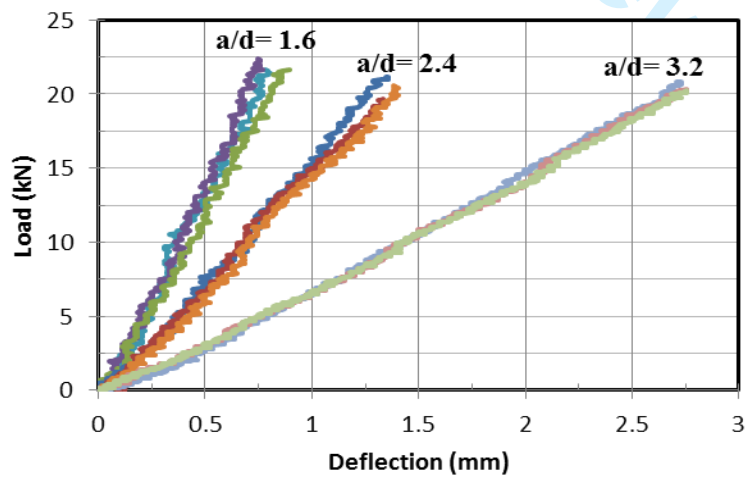


Figure 3. Load – deflection relationship for GFRP beams

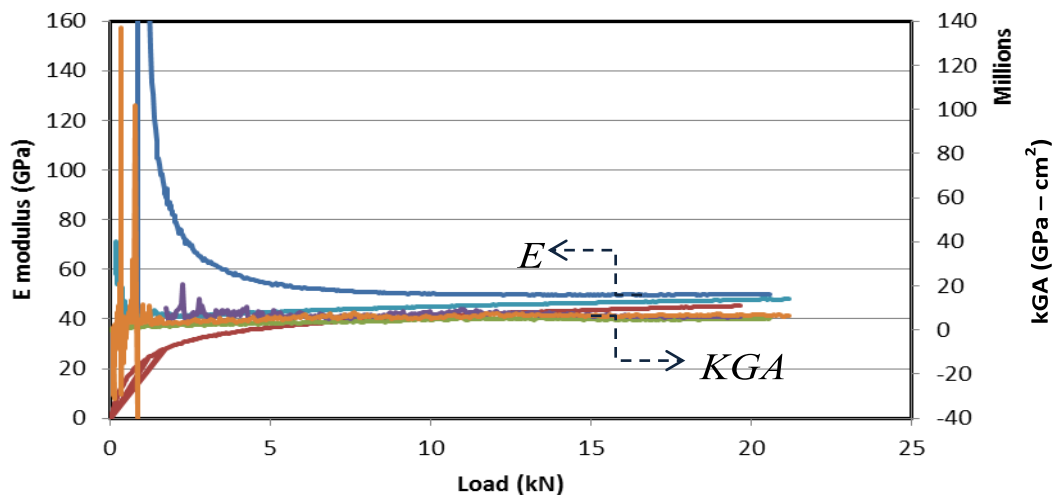


Figure 4. Elastic modulus (E) and shear stiffness (KGA) versus Load for $a/d = 1.6$

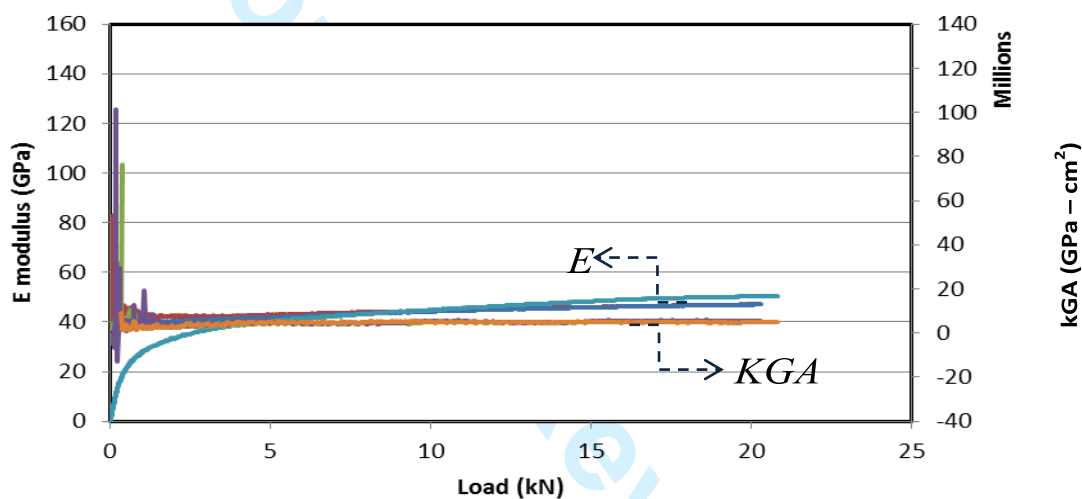


Figure 5. Flexural modulus (E) and shear stiffness (KGA) versus Load for $a/d = 2.4$

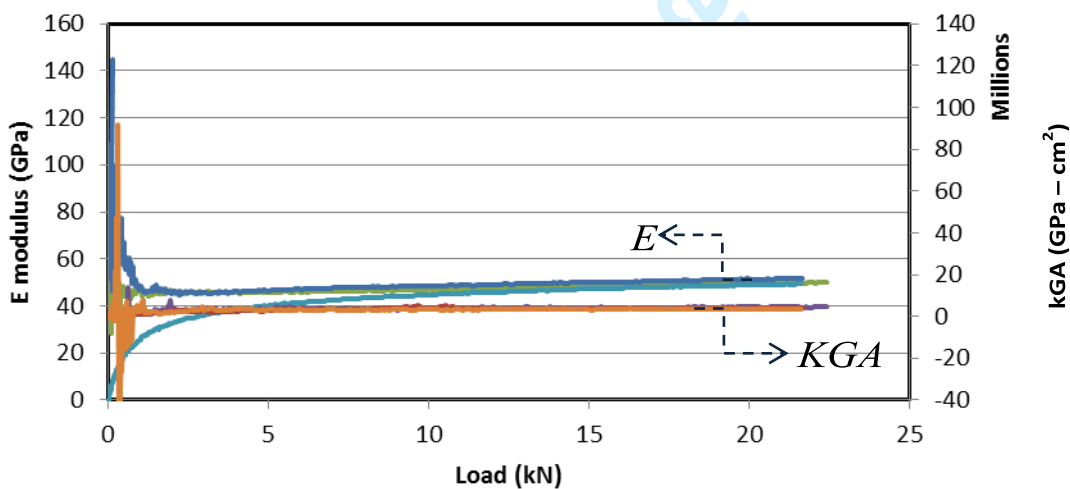


Figure 6. Flexural modulus (E) and shear stiffness (KGA) versus Load for $a/d = 3.2$

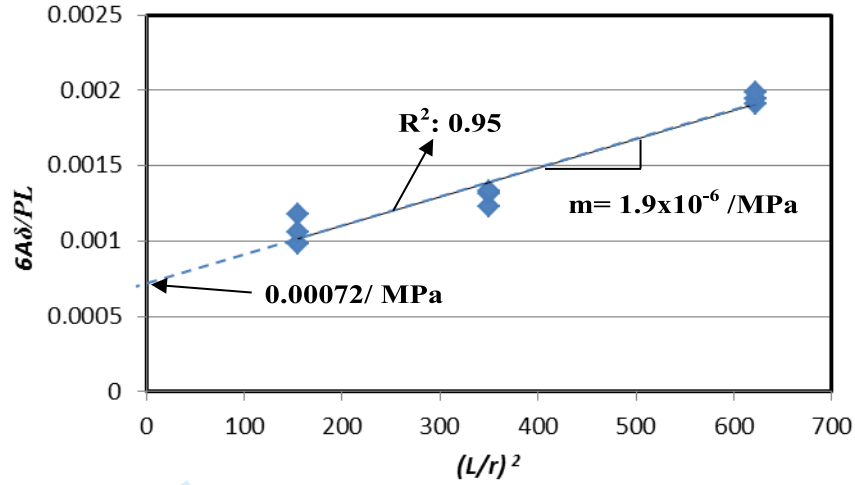


Figure 7. Typical graph to determine E and KG using SM

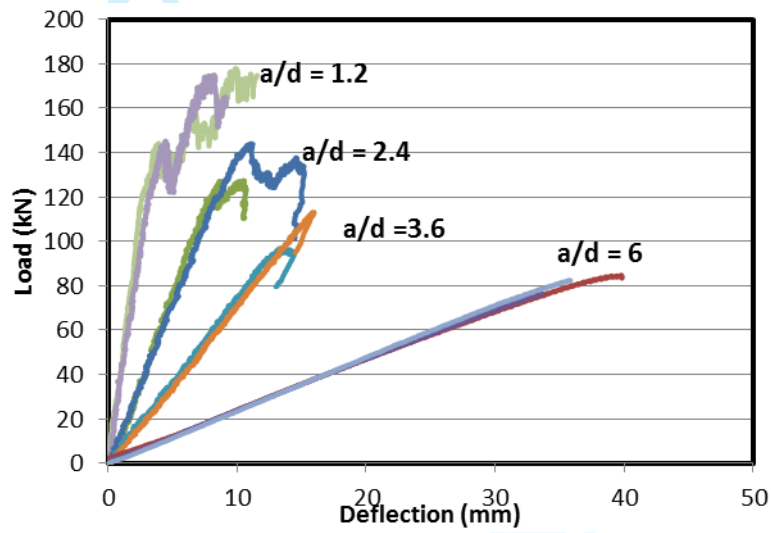


Figure 8. Load – deflection curves for GFRP beams

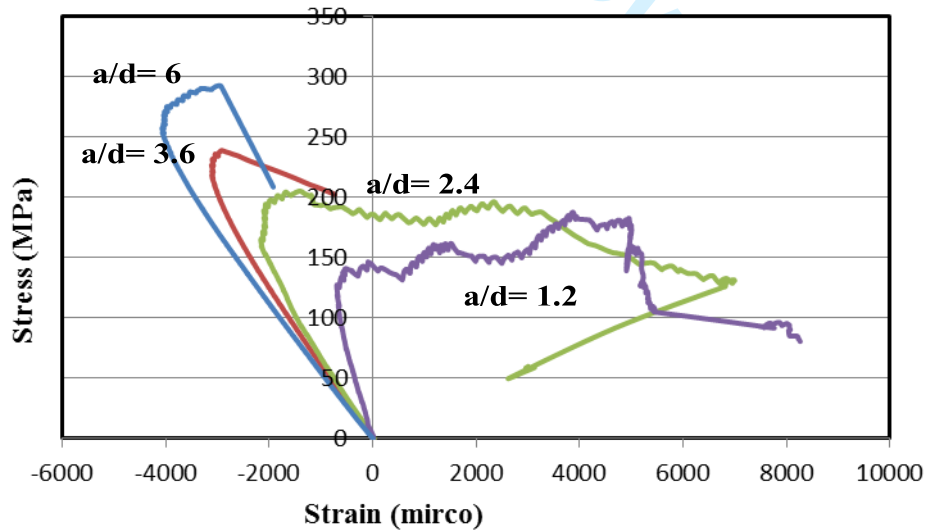


Figure 9. Stress versus compression strain

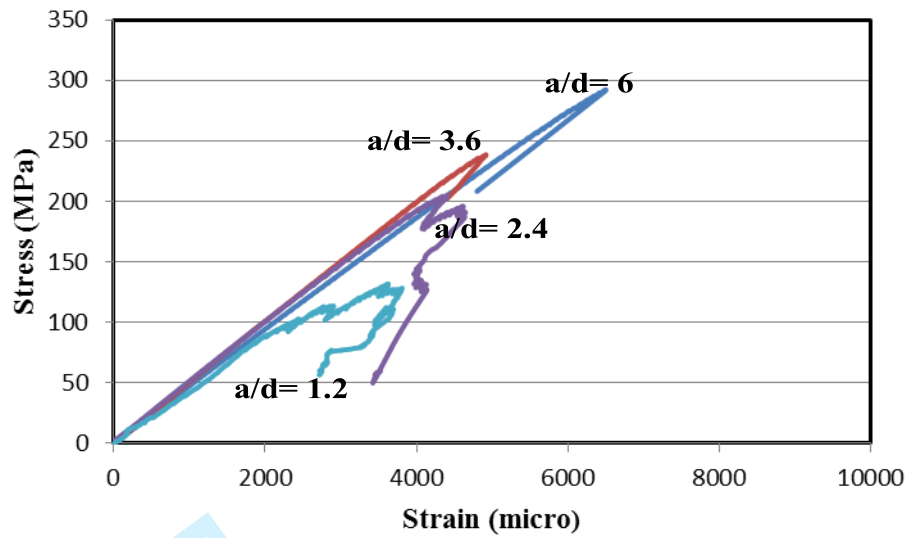


Figure 10. Stress versus tensile strain

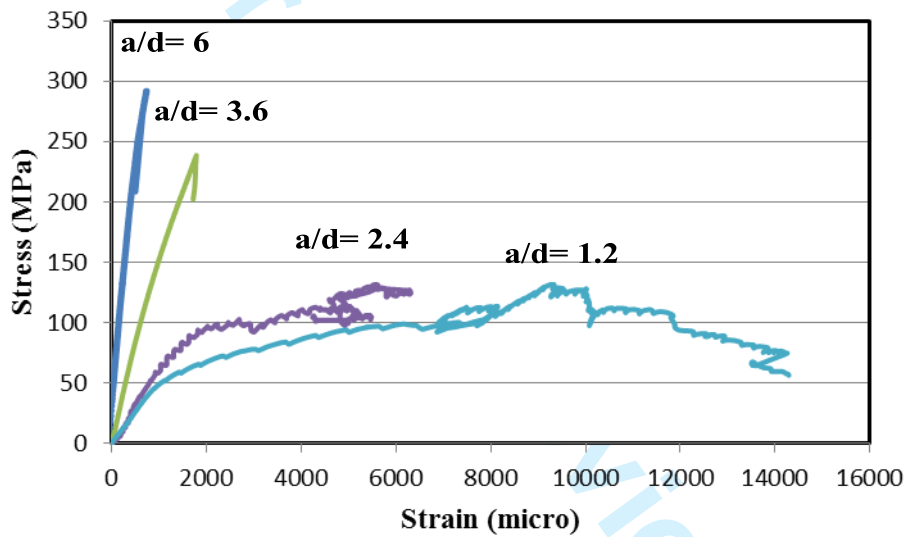


Figure 11. Stress versus shear strain

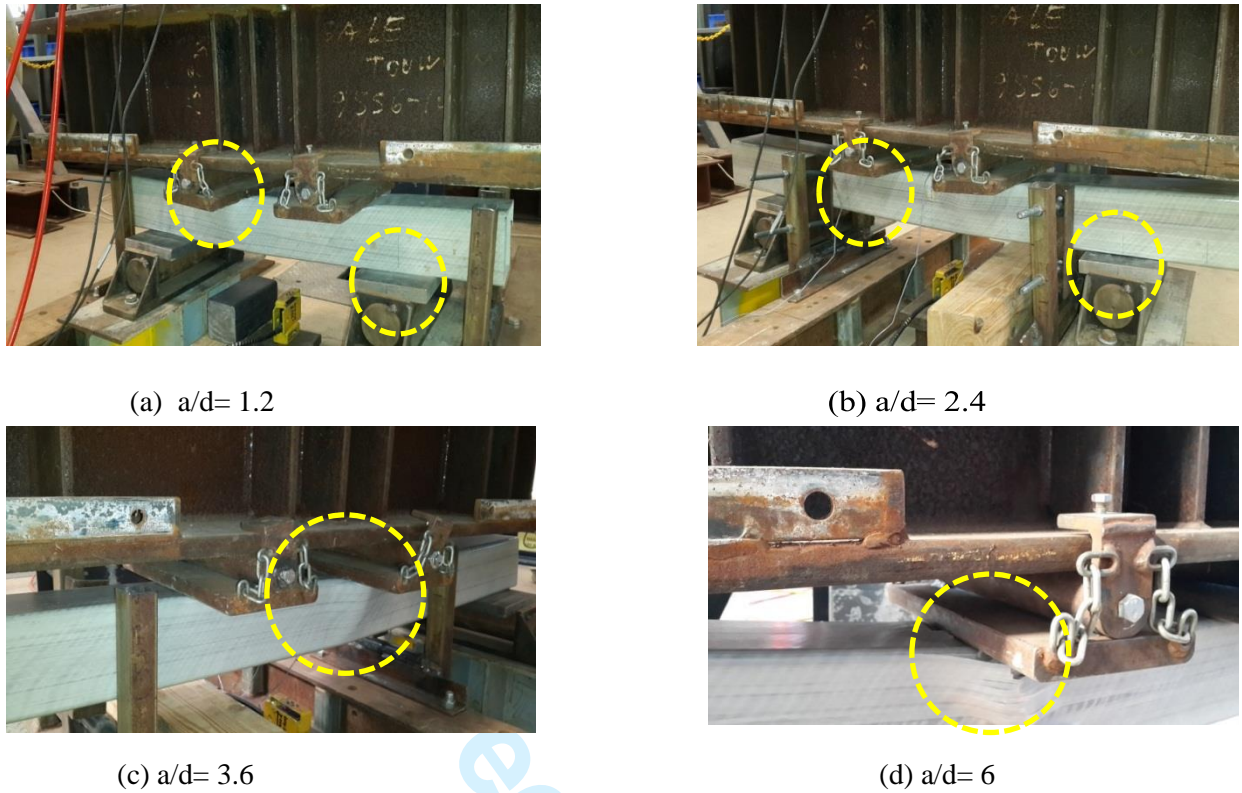


Figure 12. Failure modes of GFRP beams for different shear span to depth ratios

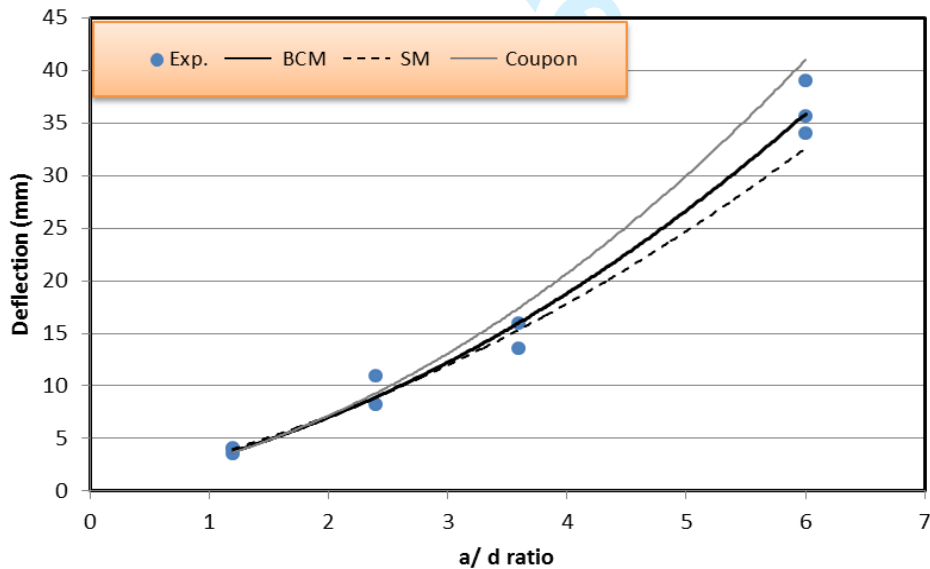


Figure 13. Comparison of theoretical and experimental deflection of beams with different a/d ratios

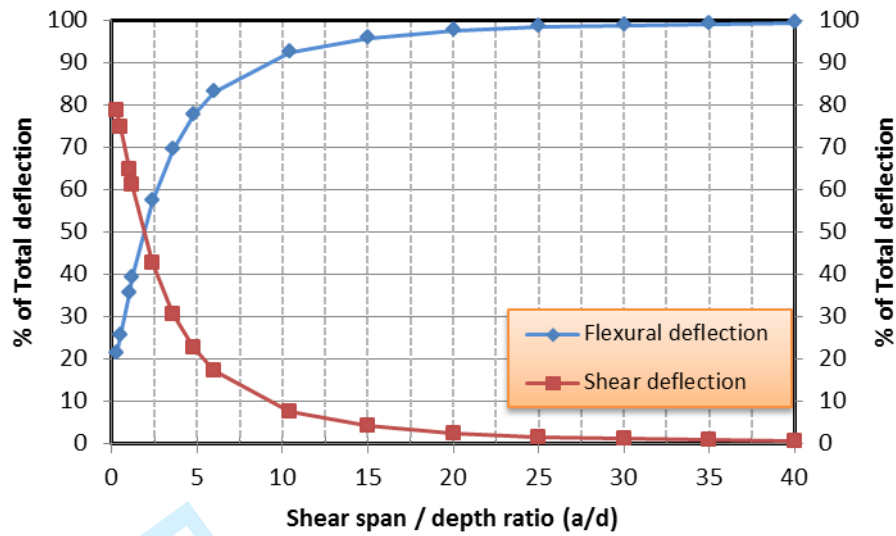


Figure 14. Contribution of flexural and shear deflection for beams with different a/d ratios

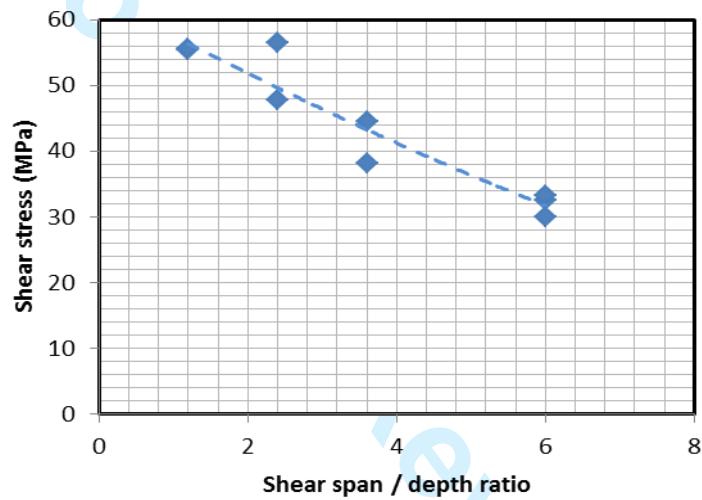


Figure 15. Shear stress versus shear span to depth ratio for GFRP beam

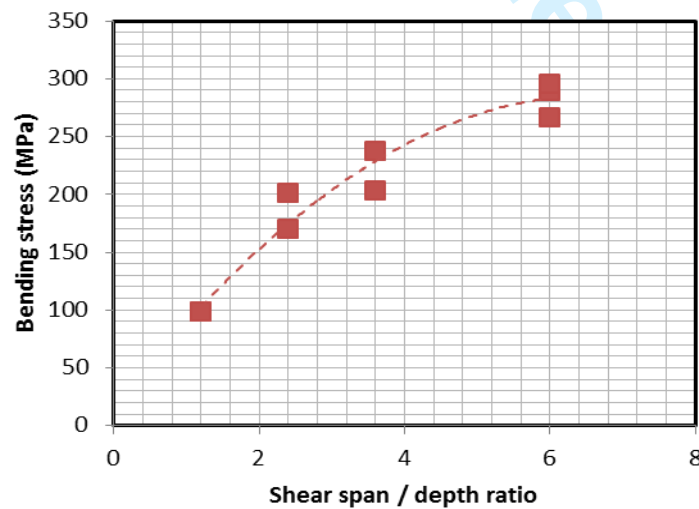


Figure 16. Bending stress versus shear span to depth ratio for GFRP beam

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

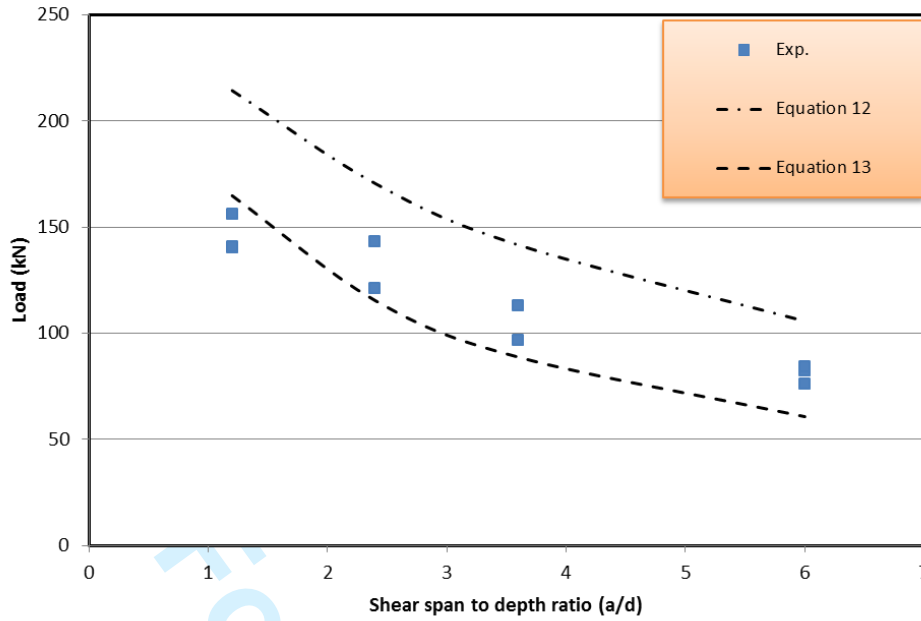


Figure 17. Comparison between the predicted and the actual failure loads

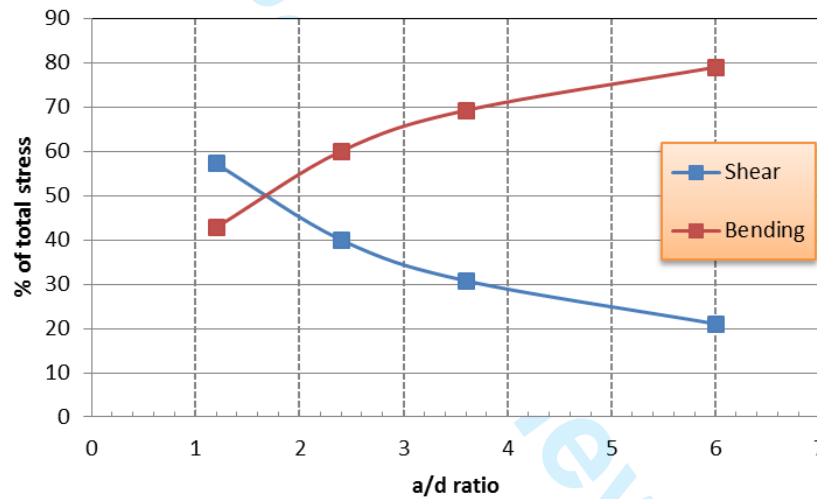


Figure 18. Percentages of stress contribution from the total failure stress

All Tables

Table 1. Mechanical properties from coupon test

Properties	Average value	SD
Compressive modulus (Longitudinal), GPa	38	1.4
Compressive strength, MPa	640	37
Tensile modulus (Longitudinal), GPa	42	2
Tensile Strength (MPa)	741	39
Flexural modulus (Longitudinal) (GPa)	39.3	2.3
Shear modulus (Longitudinal) (GPa)	5.7	0.4
Shear Strength (MPa)	120	14
Inter-laminar shear strength (MPa)	51	2

Table 2. Details of the specimens tested for the elastic properties

Span length mm	Shear span, a mm	a/d
600	200	1.6
900	300	2.4
1200	400	3.2

Table 3. Details of the specimens tested for the behaviour of GFRP beams

Span length mm	Shear span, a mm	a/d
600	150	1.2
900	300	2.4
1200	450	3.6
1800	750	6

Table 4. Summary of average E and KGA for each span for GFRP beam testing (BCM)

a/d	E GPa	C.O.V %	KGA GPa-cm ²	C.O.V %	G GPa
1.6	47.3	4.4	58.5	10	4.8
2.4	46.2	2.4	49.1	9	4.1
3.2	48.1	2.1	39.3	10	3.3
Ave.	47.2				4

Table 5. Summary of experimental results for GFRP beams

Shear span/ depth	Average failure load kN	Deflection mm	Failure mode
1.2	148	8	TS
2.4	132	9	TS
3.6	107.8	14	F
6	80.8	37	F

TS: transverse shear failure

F: flexural failure

Table 6. Summary of experimental properties for GFRP beams

Test type	E modulus GPa	G modulus GPa
Coupon	39.3	5.7
BCM	47.2	4
SM	56.1	3.3

Table 7. Predicted failure load compared with the actual failure load

a/d ratio	Exp. kN	Eq. 12 kN	Eq. 13 kN
1.2	148	214	164
2.4	132	170	115
3.6	107.8	142	88
6	80.8	106	60