

Cleveland State University  
**EngagedScholarship@CSU**



Chemical & Biomedical Engineering Faculty  
Publications

Chemical & Biomedical Engineering Department

5-19-2016

# Methodological Considerations of Electron Spin Resonance Spin Trapping Techniques for Measuring Reactive Oxygen Species generated from metal oxide nanomaterials

Min Sook Jeong  
*Baterials*


Kyeong-Nam Yu  
*Cleveland State University*

Hyun Hoon Chung  
*Seoul National University College of Medicine*

Soo Jin Park  
*Baterials*

Ah Young Lee  
*Seoul National University*

Follow this and additional works at: [https://engagedscholarship.csuohio.edu/encbe\\_facpub](https://engagedscholarship.csuohio.edu/encbe_facpub)

 [next page for additional authors](#)  
Part of the [Biomedical Engineering and Bioengineering Commons](#), and the [Chemical Engineering Commons](#)

**How does access to this work benefit you? Let us know!**

## Original Citation

Jeong MS, Yu K, Chung HH, Park SJ, Lee AY, Song MR, Cho M, Kim JS. Methodological considerations of electron spin resonance spin trapping techniques for measuring reactive oxygen species generated from metal oxide nanomaterials. *Scientific Reports*. 2016;6:26347.

## Repository Citation

Jeong, Min Sook; Yu, Kyeong-Nam; Chung, Hyun Hoon; Park, Soo Jin; Lee, Ah Young; Song, Mi Ryoung; Cho, Myung-Haing; and Kim, Jun Sung, "Methodological Considerations of Electron Spin Resonance Spin Trapping Techniques for Measuring Reactive Oxygen Species generated from metal oxide nanomaterials" (2016). *Chemical & Biomedical Engineering Faculty Publications*. 128.  
[https://engagedscholarship.csuohio.edu/encbe\\_facpub/128](https://engagedscholarship.csuohio.edu/encbe_facpub/128)

This Article is brought to you for free and open access by the Chemical & Biomedical Engineering Department at EngagedScholarship@CSU. It has been accepted for inclusion in Chemical & Biomedical Engineering Faculty Publications by an authorized administrator of EngagedScholarship@CSU. For more information, please contact [library.es@csuohio.edu](mailto:library.es@csuohio.edu).

---

**Authors**

Min Sook Jeong, Kyeong-Nam Yu, Hyun Hoon Chung, Soo Jin Park, Ah Young Lee, Mi Ryoung Song,  
Myung-Haing Cho, and Jun Sung Kim

# SCIENTIFIC REPORTS

OPEN

## Methodological considerations of electron spin resonance spin trapping techniques for measuring reactive oxygen species generated from metal oxide nanomaterials

Received: 16 February 2016

Accepted: 29 April 2016

Published: 19 May 2016


Min Sook Jeong<sup>1</sup>, Kyeong-Nam Yu<sup>2</sup>, Hyun Hoon Chung<sup>3</sup>, Soo Jin Park<sup>1</sup>, Ah Young Lee<sup>4</sup>, Mi Ryoung Song<sup>1</sup>, Myung-Haing Cho<sup>4,5,6,7,8</sup> & Jun Sung Kim<sup>1</sup>

Qualitative and quantitative analyses of reactive oxygen species (ROS) generated on the surfaces of nanomaterials are important for understanding their toxicity and toxic mechanisms, which are in turn beneficial for manufacturing more biocompatible nanomaterials in many industrial fields. Electron spin resonance (ESR) is a useful tool for detecting ROS formation. However, using this technique without first considering the physicochemical properties of nanomaterials and proper conditions of the spin trapping agent (such as incubation time) may lead to misinterpretation of the resulting data. In this report, we suggest methodological considerations for ESR as pertains to magnetism, sample preparation and proper incubation time with spin trapping agents. Based on our results, each spin trapping agent should be given the proper incubation time. For nanomaterials having magnetic properties, it is useful to remove these nanomaterials via centrifugation after reacting with spin trapping agents. Sonication for the purpose of sample dispersion and sample light exposure should be controlled during ESR in order to enhance the obtained ROS signal. This report will allow researchers to better design ESR spin trapping applications involving nanomaterials.

To further promote industries that rely on nanotechnology, it is important to understand not only the characteristics and potentials of such materials, but also their toxicity. The field of toxicology has produced a wealth of information relating to the toxicity or toxic mechanisms of nanomaterials, which have expanded and refined the industrial uses of such materials. In recent decades, these efforts have been highly beneficial to understanding the toxicities and toxic mechanisms of various nanomaterials and to safely and responsibly develop their related technologies. Nevertheless, nanomaterials have many different forms and applications, and this diversity must be considered when studying their toxicity. In particular, in the initial and current state of nanotoxicology, various nanomaterial properties such as size, shape, and charge must be considered due to their pivotal roles in influencing material toxicity. Therefore, determining the physicochemical properties of nanomaterials is critical in evaluating their overall toxicity. In the relevant biological and physicochemical analyses, it is essential to not only produce relevant data but to understand the limitations of existing methods.

Reactive oxygen species (ROS) are highly reactive substances that are potentially toxic to living organisms. They can cause detrimental effects in cells through oxidative damage of biomolecules (proteins, lipids, and nucleic acids) or through disruption of cell signaling pathways<sup>1</sup>. ROS is considered one of the most important sources

<sup>1</sup>R&D Center, Biterials, Goyang-si, Republic of Korea. <sup>2</sup>Department of Chemical & Biomedical Engineering, Cleveland State University, Cleveland, OH, USA. <sup>3</sup>Department of Obstetrics and Gynecology, Seoul National University College of Medicine, Seoul, Republic of Korea. <sup>4</sup>Laboratory of Toxicology, College of Veterinary Medicine, Seoul National University, Seoul, Republic of Korea. <sup>5</sup>Graduate Group of Tumor Biology, Seoul National University, Seoul, Republic of Korea. <sup>6</sup>Advanced Institute of Convergence Technology, Seoul National University, Suwon, Republic of Korea. <sup>7</sup>Graduate School of Convergence Science and Technology, Suwon, Republic of Korea. <sup>8</sup>Institute of GreenBio Science Technology, Seoul National University, Pyeongchang-gun, Republic of Korea. Correspondence and requests for materials should be addressed to M.H.C. (email: mchotox@snu.ac.kr) or J.S.K. (email: lifeisgood@biterials.com)

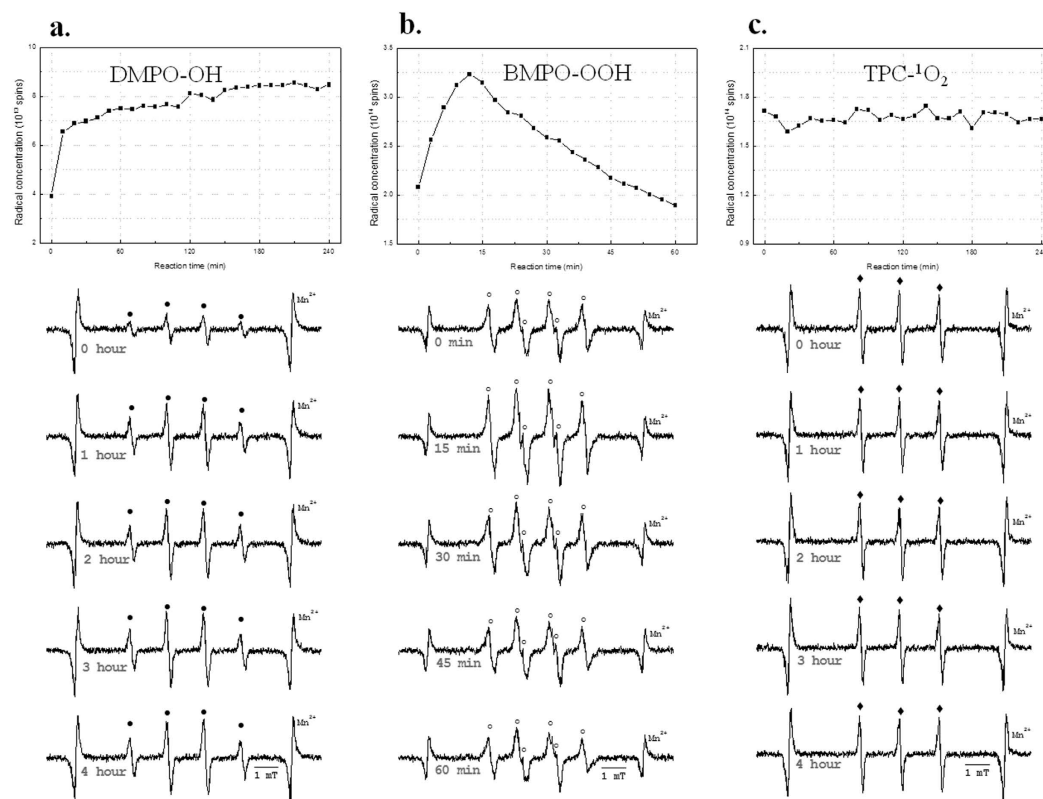


**Figure 1. Stability reviews of each spin adduct according to incubation time in each positive control system.** (a) Stability review of the DMPO-OH adduct generated by the Fenton reaction in the presence of DMPO, (b) Stability review of the BMPO-OOH adduct by the hypoxanthine-xanthine oxidase system in the presence of BMPO, (c) Stability review of the TPC- $^1\text{O}_2$  adduct generated by the Rose Bengal photosensitizer in the presence of TPC.

of toxic mechanisms in various nanomaterials. Many reports suggest that the entrance of nanomaterials into the cell may lead to the formation of ROS. In addition, the formation of ROS in the cell can induce toxicity through a number of complicated pathways<sup>2–4</sup>. Therefore, it is important to measure and quantify ROS formation in order to understand ROS-related toxicity in nanomaterials<sup>5</sup>. ROS typically have a short lifespan, making their direct detection and determination very difficult and often impossible<sup>6,7</sup>. The use of fluorescent probes, such as dichlorodihydrofluorescein and hydroethidine, as well as dihydrorhodamine and chemiluminescent methods, provides simple ways of detecting free radicals and ROS in cellular systems. Nevertheless, these methods have limitations and many sources of artifacts<sup>8–10</sup>.

Electron spin resonance (ESR) (also called electron paramagnetic resonance or EPR) is a powerful technique for studying chemical species that have one or more unpaired electrons. ESR spectroscopy has become a direct and potent (robust-Rev1) method for detecting free radicals that are chemically generated or formed in biological systems, and in nanotoxicology this technique has been employed for detecting ROS<sup>11–13</sup>. ESR techniques with various spin trapping agents are used to detect specific free radicals and to produce a relatively stable and distinct spin adduct that can be identified and quantified by ESR<sup>11</sup>. Although ESR with spin trapping agents is a very robust and valuable method of detecting ROS, selection of the correct specific type of spin trapping agent, sample preparation method, and incubation time between spin trapping agents and target materials must be addressed in greater detail. He *et al.*, for example, contended that light exposure may affect the formation of ROS in metal nanoparticles, and that it also influences the formation of free radicals<sup>10,14</sup>. Moreover, ultrasound was reported by Makino, Mossoba and Riesz to affect overall sample preparation<sup>15</sup>. In this study, we suggest methodological considerations to follow in regards to the magnetism of nanomaterials, incubation time of spin trapping agents, and various other factors that can lead to distortion of ESR signals of nanomaterials such as light exposure and sonication, which are often used carelessly in ESR for measuring the ROS generated from metal oxide nanomaterials.

## Results

**Spin adduct stability as a function of incubation time.** We analyzed the stability of the spin adduct as a function of the incubation time in a positive control system (Fig. 1). In the case of the DMPO-OH adduct, the signal intensity increases until approximately 150 min in the Fenton reaction system. From 150 min to approximately 4 h, the signal intensity is saturated (Fig. 1a). In the case of the BMPO-OOH adduct, the signal intensity increases until approximately 12 min, and then slowly decreases over time in the hypoxanthine-xanthine oxidase system (Fig. 1b). However, the TPC- $^1\text{O}_2$  adduct is very stable until approximately 4 h (Fig. 1c). Based on our

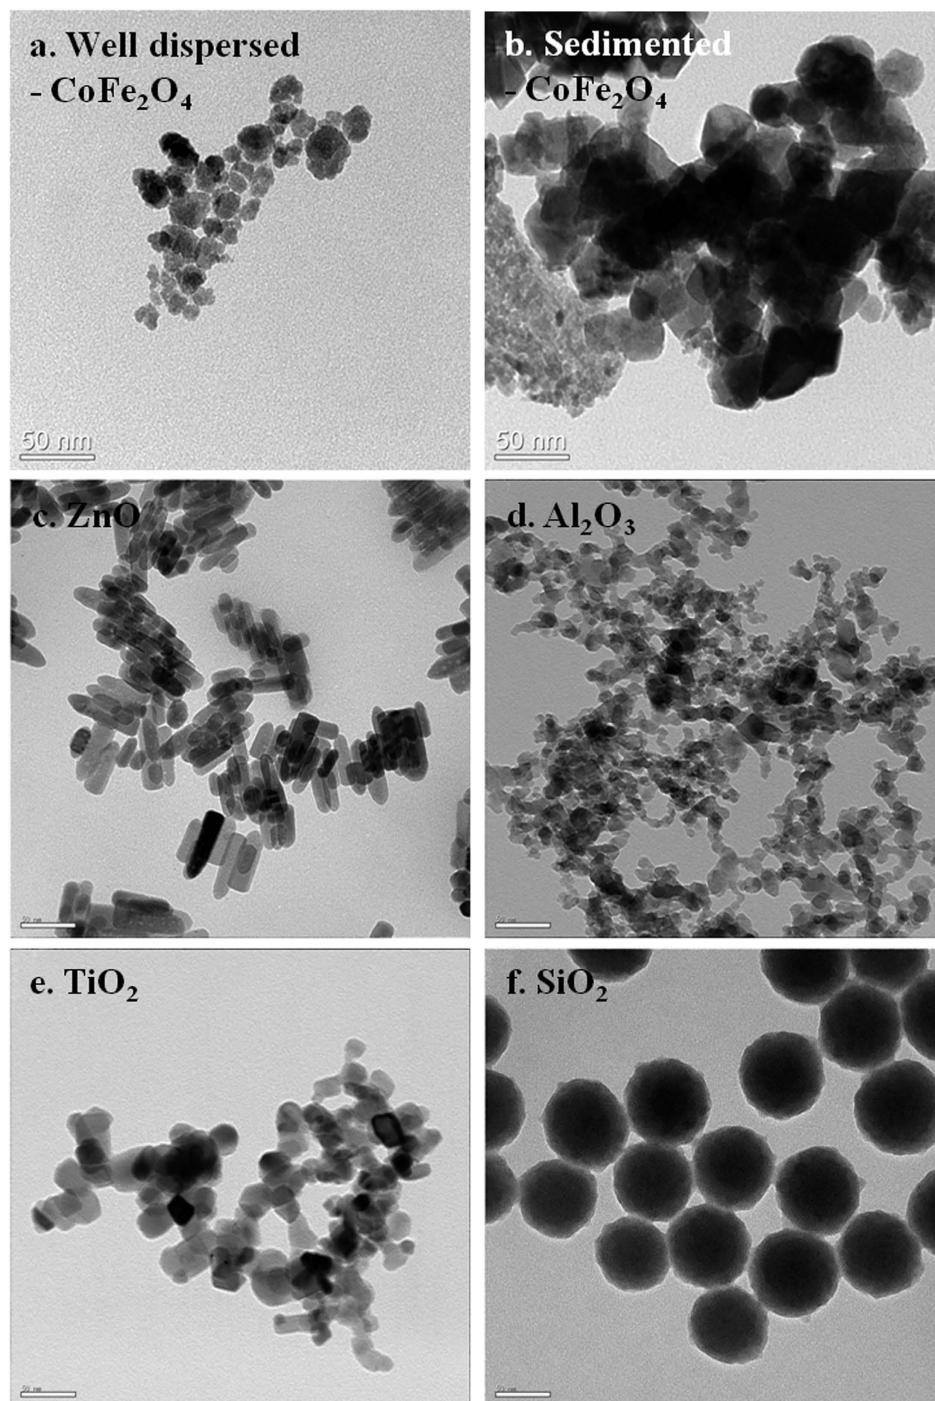


**Figure 2.** TEM images of metal oxide nanomaterials. (a) Well-dispersed  $\text{CoFe}_2\text{O}_4$  ( $20.4 \pm 10.3$  nm), (b) Sedimented  $\text{CoFe}_2\text{O}_4$  ( $48.3 \pm 9.7$  nm), (c) ZnO nanorods (width:  $16.2 \pm 1.3$  nm, length:  $50.8 \pm 11.8$  nm), (d)  $\text{Al}_2\text{O}_3$  ( $15.6 \pm 5.4$  nm), (e)  $\text{TiO}_2$  ( $26.5 \pm 6.7$  nm), (f)  $\text{SiO}_2$  ( $72.9 \pm 4.0$  nm).

results, determination of the incubation time between the spin trapping agent and test materials may be important in future quantitative analysis. These results allow us to determine an optimal reaction time for spin trapping reactions, respectively.


**TEM characterization of test nanomaterials.** Transmission electron microscopy (TEM) analysis was performed to confirm the particle morphology and size of the nanomaterials. As shown in Fig. 2, ZnO nanomaterials have a rod-like shape (width:  $16.2 \pm 1.3$  nm, length:  $50.8 \pm 11.8$  nm),  $\text{SiO}_2$  nanomaterials are spherical ( $72.9 \pm 4.0$  nm), and the shapes of well dispersed- $\text{CoFe}_2\text{O}_4$  ( $20.4 \pm 10.3$  nm), sedimented- $\text{CoFe}_2\text{O}_4$  ( $48.3 \pm 9.7$  nm),  $\text{TiO}_2$  ( $26.5 \pm 6.7$  nm) and  $\text{Al}_2\text{O}_3$  ( $15.6 \pm 5.4$  nm) nanomaterials are polyhedral.




### a. Well dispersed magnetic nanomaterials ( $\text{CoFe}_2\text{O}_4$ )

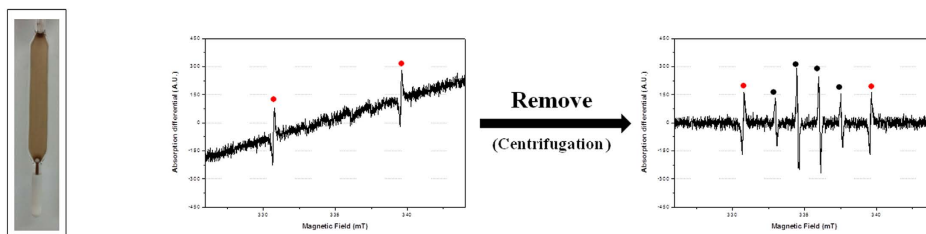


### b. Sedimented magnetic nanomaterials ( $\text{CoFe}_2\text{O}_4$ )

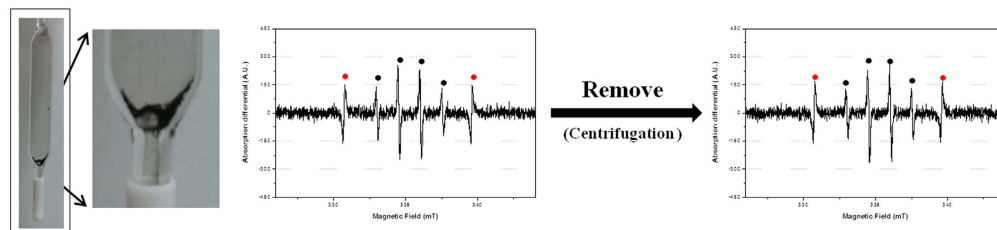

### c. Well dispersed non-magnetic nanomaterials ( $\text{SiO}_2$ )

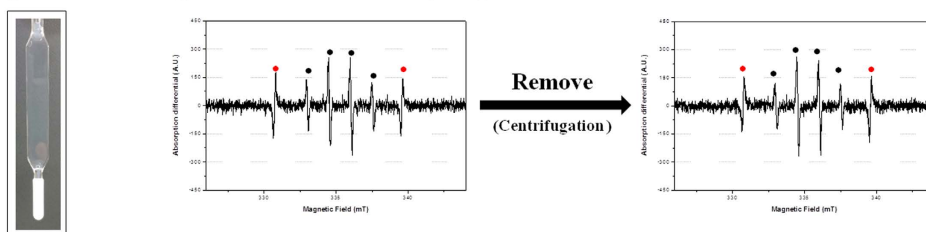


### d. Sedimented non-magnetic nanomaterials ( $\text{ZnO}$ )

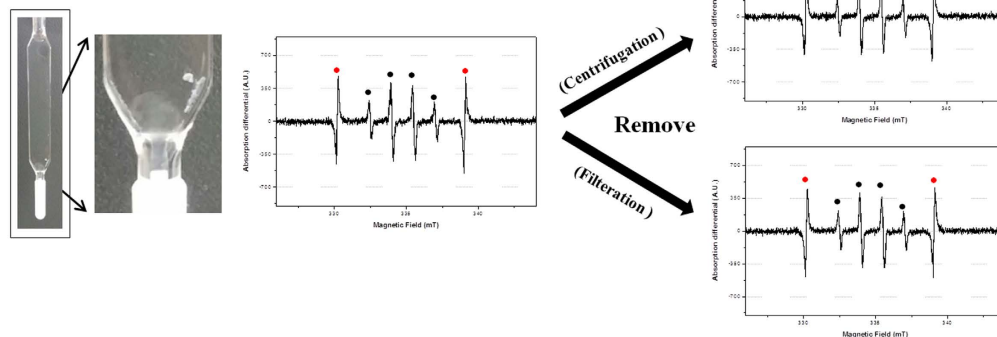

**Figure 3.** ESR spectra confirming the removal effect of nanomaterials on sample preparation. (a) Well-dispersed magnetic nanomaterials ( $\text{CoFe}_2\text{O}_4$ ), (b) Sedimented magnetic nanomaterials ( $\text{CoFe}_2\text{O}_4$ ). (c) Well-dispersed non-magnetic nanomaterials ( $\text{SiO}_2$ ), (d) Sedimented non-magnetic nanomaterials ( $\text{ZnO}$ ).  $\text{CoFe}_2\text{O}_4$  and  $\text{SiO}_2$  nanomaterials were detected in positive control system and  $\text{ZnO}$  nanomaterials were detected without positive control system. The nanomaterials were removed by centrifugation (at  $12700 \times g$  for 10 min) or filtration (with  $0.2 \mu\text{m}$  pore size).

**Magnetic nanomaterials and centrifugation.** Nanomaterials have many physicochemical properties; among them, magnetism can impact the ESR signal of the material. We compared the ESR signal before and after removing nanomaterials by centrifugation or filtration in the case of  $\text{CoFe}_2\text{O}_4$  (a magnetic nanomaterial) in a positive control system. Because ESR signals of  $\text{CoFe}_2\text{O}_4$  samples were not detected based on hydroxyl radical signals (DMPO-OH adducts) after mixing the nanomaterials and spin trapping agent (DMPO) for 3 h (data not shown), samples were detected using a positive control system. ESR signals were distorted in the case of well-dispersed  $\text{CoFe}_2\text{O}_4$  (Fig. 3a). This ESR signal was tilted to one side because of contributions from both the spin adduct spectrum and a small portion ( $335 \pm 10 \text{ mT}$ ) of the very broad (few hundred mT) intrinsic ESR spectrum of the unpaired electrons from  $\text{CoFe}_2\text{O}_4$ . No ESR signal was present for DMPO-OH adducts (Quartet with 1:2:2:1 signal intensity) despite the positive control system. However, after removing the well-dispersed  $\text{CoFe}_2\text{O}_4$  by centrifugation, the ESR signal was not tilted and DMPO-OH adducts were detected.

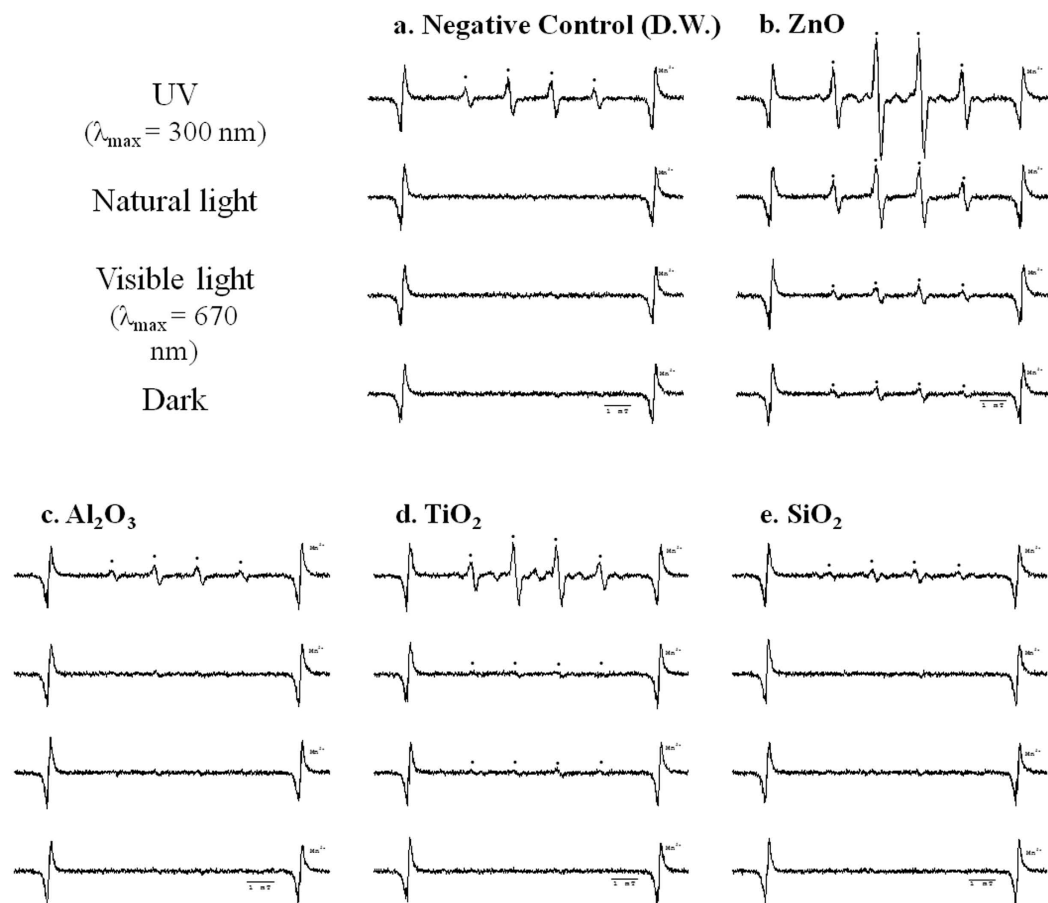

**Figure 4.** ESR spectra confirming the effects of light exposure interference on sample preparation with DMPO (UV, natural light, visible light, and dark conditions from above). (a) ESR spectrum of negative control (DW), (b) ESR spectrum of ZnO, (c) ESR spectrum of  $\text{Al}_2\text{O}_3$ , (d) ESR spectrum of  $\text{TiO}_2$ , (e) ESR spectrum of  $\text{SiO}_2$ .


In the case of sedimented  $\text{CoFe}_2\text{O}_4$ , there is no distortion of the ESR signals (Fig. 3b). Based on this result, we conclude that well-dispersed nanomaterials with magnetic properties should not be directly applied in ESR due to interference issues (Fig. 3a).

To evaluate the interference effects of non-magnetic nanomaterials ( $\text{ZnO}$  and  $\text{SiO}_2$ ), ESR spectra were collected before and after removing the nanomaterials by centrifugation or filtration. Here, there is no difference in ESR signal for samples with and without non-magnetic nanomaterials (Fig. 3c,d). Based on our results, there is no adverse effect of removing nanomaterials after incubating the spin trapping agent; therefore we suggest that removal of well-dispersed nanomaterials having magnetic properties by centrifugation could be applied to ESR analysis.

**Effects of light exposure during sample preparation on ESR spectra.** Each nanomaterial was exposed to various light sources, such as UV, natural light, visible light, and dark conditions in the presence of a spin trapping agent (DMPO). The signal of the associated hydroxyl radical adduct was then recorded to determine if any changes occurred. As shown in Fig. 4, all ESR spectra increase in intensity under UV (280–360 nm) conditions as compared to dark conditions. The ESR spectrum of distilled water (DW) without nanomaterials increases under UV conditions as well. Excited  $\text{H}_2\text{O}^*$  generates hydrogen atoms ( $\text{H}^*$ ) and hydroxyl radicals ( $^*\text{OH}$ )<sup>16</sup>, and these hydroxyl radicals are subsequently trapped by DMPO. For this reason, the ESR spectrum of the DMPO-OH adducts increases in intensity.

In the case of  $\text{TiO}_2$ , the ESR spectrum increases slightly in visible light ( $2.03 \times 10^{13}$  spins) and in natural light ( $2.00 \times 10^{13}$  spins). For ZnO, the ESR spectrum increases in order of dark conditions ( $2.82 \times 10^{13}$  spins) < visible light ( $3.37 \times 10^{13}$  spins) < natural light ( $9.43 \times 10^{13}$  spins) < UV ( $1.84 \times 10^{14}$  spins), and is more strongly sensitized to light compared to other nanomaterials. The ESR spectra of ZnO and  $\text{TiO}_2$  with photocatalytic behavior increase remarkably under UV conditions. Based on our results, exposure to specific light sources can affect ESR spectra not only for nanomaterials, but for DW as well.

**Effects of ultrasound sonication during sample preparation on ESR spectra.** Sonication is commonly used in nanotechnology to evenly disperse nanomaterials in liquid media. As shown in Fig. 5, ESR spectra

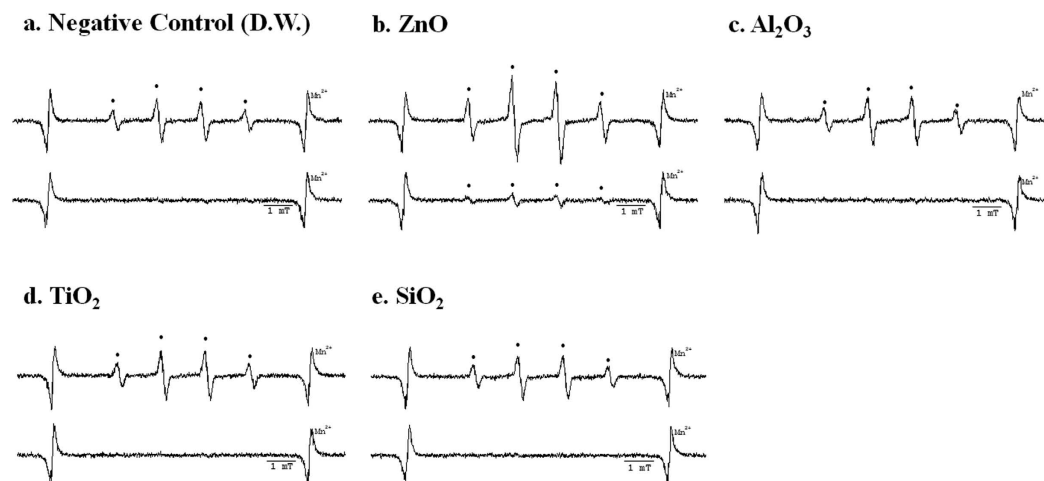

**Figure 5. ESR spectra confirming interference effects of ultrasonic dispersion on sample preparation with DMPO (upper: with sonication; bottom: without sonication). (a) ESR spectrum of negative control (DW), (b) ESR spectrum of ZnO, (c) ESR spectrum of  $\text{Al}_2\text{O}_3$ , (d) ESR spectrum of  $\text{TiO}_2$ , (e) ESR spectrum of  $\text{SiO}_2$ .**

were newly generated after ultrasonic dispersion for D.W, solutions of  $\text{Al}_2\text{O}_3$ ,  $\text{TiO}_2$ , and  $\text{SiO}_2$ . In the case of ZnO, the ESR spectrum increases  $4.8\times$  when prepared by ultrasonic dispersion compared to a solution without sonication ( $1.36 \times 10^{14}$  spins vs.  $2.82 \times 10^{13}$  spins). Therefore, because ROS signals can be generated by ultrasonic dispersion, such dispersion should not be used for detecting ROS generated from the nanomaterial itself.

## Discussion

ROS are a primary source of nanomaterial toxicity that can form after the exposure of nanomaterials to various elements, and are inherent to the surface conditions of the nanomaterials. However, the *in situ* identification and quantification of ROS in nanomaterials has some obstacles, such as their interactions with repair systems and other unknown factors. To avoid these problems, ROS must be analyzed directly during their formation from nanomaterials. In addition, the direct identification and quantification of ROS by ESR is important in understanding the toxic mechanisms of nanomaterials and in product design integrating these nanomaterials. In particular, the various factors that can affect ESR signals must be considered, such as the characteristics of the parent nanomaterial, spin trapping agent incubation time, and sample preparation. In this report, we examine the magnetic properties, photocatalytic activity, and dispersion method of such nanomaterials and how they can impact ESR analysis, as well as examining samples with and without the parent nanomaterials (removed by centrifugation or filtration) (Fig. 3).

Each spin trapping agents should be applied with a proper incubation time when using ESR to quantify ROS from nanomaterials. In this case, the life span of each spin trapping agent should be considered. Based on our results, the ESR signal intensity of the BMPO adduct decreases after the peak value, in contrast with the DMPO and TPC adducts (Fig. 1). In our results, spin trapping agents have different signal intensities depending on their incubation time (Fig. 1), emphasizing the importance of this parameter.

In the ESR analysis of various metal oxide nanomaterials, well-dispersed nanomaterials such as  $\text{CoFe}_2\text{O}_4$  should not be used for ESR directly due to their inherent magnetic properties, which can affect the ESR data. However, removing the nanomaterials after the reaction of the spin trapping agent is very effective in these cases (Fig. 3a). The photocatalytic activity of the nanomaterials should be additionally considered for ESR. In our results and various reports, the ESR signal intensity of nanomaterials with photocatalytic activity differs before and after light exposure (Fig. 4)<sup>10,14</sup>. Based on this result, exposure to various light sources should be also controlled when collecting nanomaterial ESR signals. During sample preparation, ultrasonication can also enhance ESR signals (Fig. 5). Therefore, ultrasonic processes should be carefully applied to ESR, especially in quantitative studies. In our well-documented experimental conditions, only the hydroxyl radical was observed from ZnO nanomaterials. In other cases, there was no observed ROS from nanomaterials (Fig. 6).


## Conclusions

The qualitative and quantitative analyses of ROS generated on nanomaterial surfaces are important for understanding and predicting their toxicity and toxic mechanisms. To this end, ESR spin trapping techniques are very useful tools for detecting ROS formation. However, applying these without considering the physicochemical properties of the nanomaterials and the sampling conditions can lead to data misinterpretation. This study enables researchers to design accurate applications of ESR spin trapping techniques with nanomaterials and to interpret the results of toxicity studies (Fig. 7).

## Materials and Methods

**Materials and instrumental preparation.**  $\text{TiO}_2$  and  $\text{Al}_2\text{O}_3$  were purchased from Evonik Industries (Hanau, Germany). Well-dispersed  $\text{CoFe}_2\text{O}_4$ , ZnO and  $\text{SiO}_2$  were synthesized at Biterials Co., Ltd. The spin



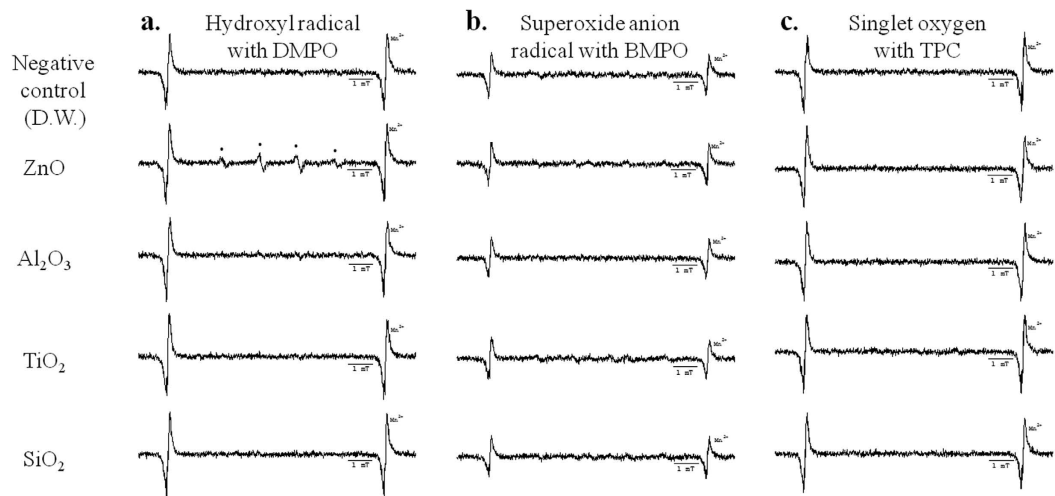

**Figure 6.** ESR spectra in accordance with well-documented methods in the sample preparation of nanomaterials (negative control, ZnO, Al<sub>2</sub>O<sub>3</sub>, TiO<sub>2</sub>, and SiO<sub>2</sub> from above). (a) ESR data of hydroxyl radical ( $\bullet\text{OH}$ ) production in the presence of DMPO with each nanomaterial, (b) ESR data on superoxide anion radical ( $\text{O}_2^{\bullet-}$ ) production in the presence of BMPO with each nanomaterial, (c) ESR data on singlet oxygen ( $^1\text{O}_2$ ) production in the presence of TPC with each nanomaterial.



trapping agents were 5,5-dimethyl-1-pyrroline *N*-oxide (DMPO) for  $\bullet\text{OH}$ , 5-tert-butoxycarbonyl-5-methyl-1-pyrroline-*N*-oxide (BMPO)  $\text{O}_2^{\bullet-}$ , and 2,2,5,5-tetramethyl-3-pyrroline-3-carboxamide (TPC) for  $^1\text{O}_2$ .

The nitron spin-trap reagents 5,5-dimethyl-1-pyrroline *N*-oxide (DMPO, 99.9%) and 5-tert-butoxycarbonyl-5-methyl-1-pyrroline-*N*-oxide (BMPO) were purchased from Dojindo (Tokyo, Japan). Sedimented  $\text{CoFe}_2\text{O}_4$ , 2,2,5,5-tetramethyl-3-pyrroline-3-carboxamide (TPC), iron(II) sulfate ( $\text{FeSO}_4$ ), hydrogen peroxide ( $\text{H}_2\text{O}_2$ ), hypoxanthine (HPX), xanthine oxidase (XOD), diethylenetriaminepentaacetic acid (DTPA), phosphate buffer solution, dimethyl sulfoxide (DMSO) and Rose Bengal were purchased from Sigma-Aldrich (St. Louis, Missouri, USA). 4-hydroxyl-2,2,6,6-tetramethylpiperidine-1-oxyl (TEMPOL) was purchased from JEOL (Tokyo, Japan). Syringe filters (0.20  $\mu\text{m}$  pore size) were purchased from Sartorius (Goettingen, Germany). An ultraviolet (UV)-B lamp (1.6 W, 0.170 A, G8T5E) was purchased from Sankyo Denki (Tokyo, Japan). The visible-light lamp (6 W, 60 mA, SSL-012458) and green lamp (6 W, 60 mA, ST-5030) were purchased from STECH LED (Gyeonggi-do, Korea).

**ESR measurements.** The ESR signals of samples were acquired using a JES-TE200 ESR spectrometer (JEOL, Tokyo, Japan) with an X-band standard frequency of 8.8–9.6 GHz. To identify the peaks, the signal components were analyzed by the ES-IPRITS data system with version 3.00 analysis software installed in the ESR instrument. The following ESR parameters were used: a frequency of 9.42 GHz, center field of  $335 \pm 10$  mT, modulation frequency of 100 kHz, time constant of 0.03 s, and power of 5.00 mW. Aqueous samples were loaded into a LC-12 aqueous quartz flat cell (JEOL)<sup>17</sup>.

**Positive control reactions to evaluate the spin trapping agent in each ROS type.** *Hydroxyl radicals ( $\bullet\text{OH}$ ).* Hydroxyl radicals are generated from the Fenton reaction, which is the oxidation of substrates by iron(II) and hydrogen peroxide. Through this reaction, hydrogen peroxide can produce reactive hydroxyl radicals as Iron(II) is oxidized by hydrogen peroxide to produce iron(III), a hydroxyl radical and hydroxyl ion ( $\text{Fe}^{2+} + \text{H}_2\text{O}_2 \rightarrow \text{Fe}^{3+} + \text{HO} + \text{HO}^-$ )<sup>18</sup>. This reaction mixture contained DW, 0.01 mM  $\text{FeSO}_4$ , 50 mM DMPO, and 0.1 mM  $\text{H}_2\text{O}_2$ , and the reaction began with the addition of  $\text{H}_2\text{O}_2$ . ESR signals were collected every 10 min for 4 h.

*Superoxide anion radicals ( $\text{O}_2^{\bullet-}$ ).* Superoxide anion radicals were generated from a hypoxanthine–xanthine oxidase (HX-XO) system. The hypoxanthine–xanthine oxidase system generates superoxide anions as shown in reactions 1 and 2<sup>19</sup>.



This reaction mixture contained 100 mM phosphate buffer (pH 7.4) with 25  $\mu\text{M}$  DTPA, 0.125 mM hypoxanthine, 50 mM BMPO and 0.125 units/mL of xanthine oxidase. The reaction began with the addition of xanthine oxidase, and ESR signals were collected every 10 min for 4 h.

*Singlet oxygen ( $^1\text{O}_2$ ).* The singlet oxygen was generated from the Rose Bengal photosensitizer. When photoexcited, this photosensitizer transfers its energy to the oxygen-producing singlet oxygen (reactions 3 and 4)<sup>20</sup>.


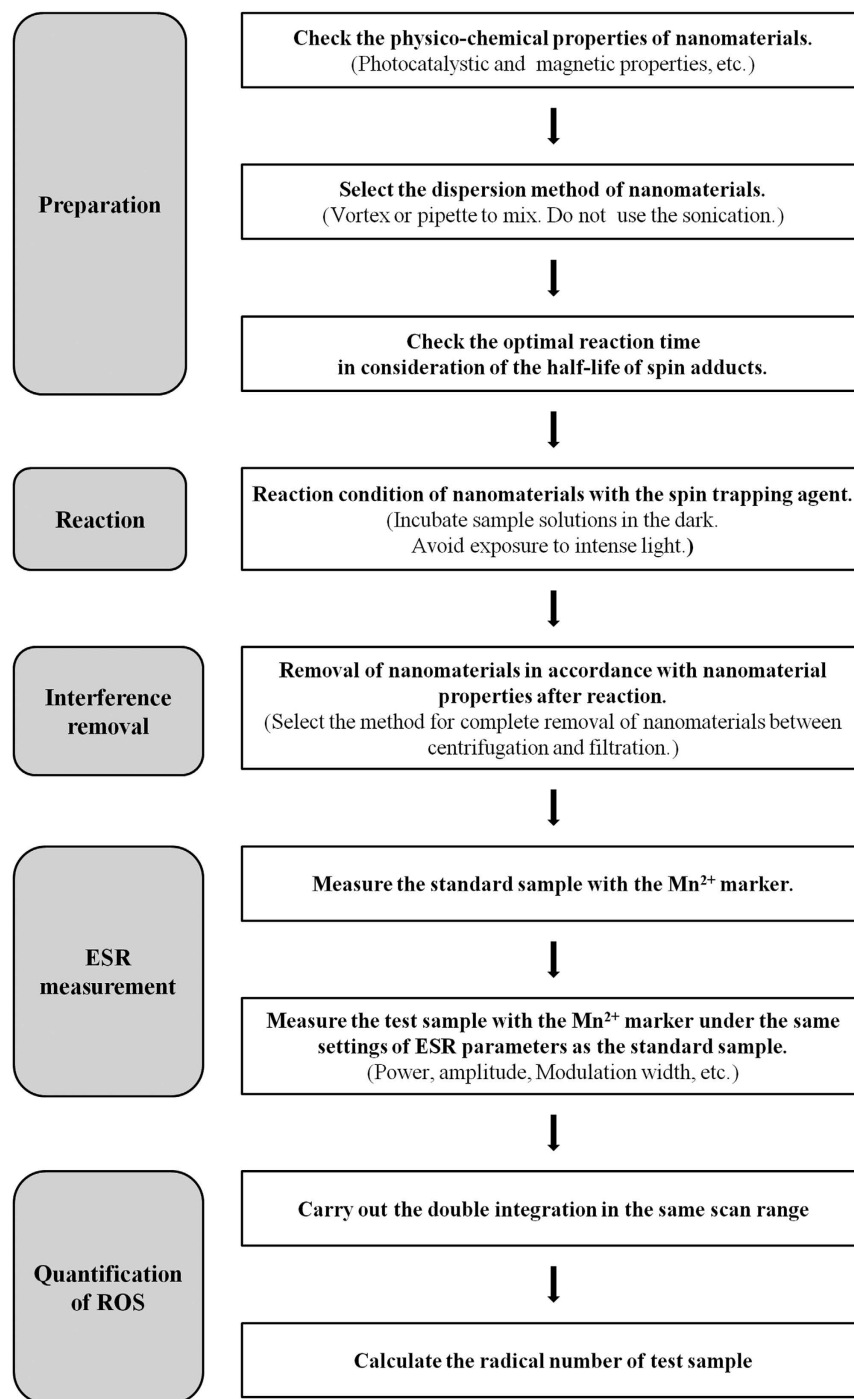


Figure 7. Methodological considerations for using ESR spin-trapping techniques with nanomaterials.



The reaction mixture contained 10 mM TPC and 0.1 mM Rose Bengal in DW; it was illuminated with continuous light ( $\lambda_{\text{max}} =$  approximately 550 nm) using an LED lamp for 10 min. ESR signals were collected every 3 min for 1 h.

**Size and morphology measurements of nanomaterials.** The morphology and nanostructure of CoFe<sub>2</sub>O<sub>4</sub> (well-dispersed and sedimented), ZnO, Al<sub>2</sub>O<sub>3</sub>, TiO<sub>2</sub>, and SiO<sub>2</sub> were characterized by energy-filtering transmission electron microscopy (EF-TEM) using a LIBLA 120 microscope (Carl Zeiss, Oberkochen, Germany)

at an accelerating voltage of 120 kV. The suspension (4 mg/mL) of nanomaterials was prepared in methanol and sonicated for 30 s. A portion of the nanomaterial suspension was deposited on a 300-mesh carbon-coated copper grid and dried at room temperature overnight before examination.

**ESR measurements of magnetic nanomaterials.** To estimate the effect of magnetic properties on the nanomaterials, we prepared two different states of  $\text{CoFe}_2\text{O}_4$ , those being well-dispersed and sedimented materials. Samples were examined by ESR after mixing with a spin trapping agent (DMPO) for 3 h, at which point the hydroxyl radical ( $\bullet\text{OH}$ ) signal was not detected (data not shown). For this reason, samples were detected using a positive control system. After ESR analysis of both samples, we removed the  $\text{CoFe}_2\text{O}_4$  by centrifugation ( $12,700 \times g$  for 10 min), and then re-analyzed with ESR. Then, to evaluate the interference effects of non-magnetic nanomaterials ( $\text{ZnO}$  and  $\text{SiO}_2$ ), ESR spectra were analyzed before and after removing the nanomaterials by centrifugation or filtration. As mentioned above,  $\text{SiO}_2$  was examined with a positive control system, while  $\text{ZnO}$  nanomaterials were detected without this positive control system.

**ESR measurement to identify light source interference.** Each nanomaterial suspension with a spin trapping agent (DMPO) was exposed to UVB ( $\lambda_{\text{max}} = 280\text{--}360$  nm), natural light, visible light ( $\lambda_{\text{max}} = 670$  nm), and dark conditions for 3 h, respectively. The signal of hydroxyl radical adduct was recorded to observe and changes compared to dark conditions.

**ESR measurements to identify interference by using ultrasonic dispersion.** Mixtures with nanomaterials and spin trapping agent were immersed in an ultrasonic bath (42 kHz, 135 W) for 10 min after reaction for 3 h. All steps were performed in dark conditions. For each mixture, the signal of the hydroxyl radical adduct was recorded to verify if the ultrasonic bath had any effects compared to the unapplied mixture.

**Quantification of ROS.** The radical concentrations in the samples were determined by comparing the area of the absorption peak with that of a standard sample (TEMPOL), with  $3.0 \times 10^{14}$  spins in  $1.0 \times 10^{-3}$  mM TEMPOL as a reference point. Spin counts were calculated from the area of the absorption peak of the  $\text{Mn}^{2+}$  marker and the signal by double integration of the ESR spectrum. The radical number of the test sample could be calculated relative the area of the standard sample<sup>21–23</sup>. In summary, the standard sample (St) and test sample (T) should be measured with the same ESR spectrometer parameters, respectively. I Double integrating the spectra over the same scan range allows for the quantification of the test sample as

$$N_T = (A_T/A_{St}) \times (M_T/M_{St}) \times (3.0 \times 10^{14} \text{ spins})$$

$A_{St}$ : The area of absorption peak with a standard sample ( $1.0 \times 10^{-3}$  mM TEMPOL)

$A_T$ : The area of absorption peak with a test sample

$M_{St}$ : The area of absorption peak of  $\text{Mn}^{2+}$  marker with a standard sample

$M_T$ : The area of absorption peak of  $\text{Mn}^{2+}$  marker with a test sample

$N_T$ : The radical number of test sample.

## References

1. Ray, P. D., Huang, B. W. & Tsuji, Y. Reactive oxygen species (ROS) homeostasis and redox regulation in cellular signaling. *Cell Signal.* **24**, 981–990 (2012).
2. Ahamed, M., Ali, D., Alhadlaq, H. A. & Akhtar, M. J. Nickel oxide nanoparticles exert cytotoxicity via oxidative stress and induce apoptotic response in human liver cells (HepG2). *Chemosphere.* **93**, 2514–2522 (2013).
3. Lee, Y. H. *et al.* Cytotoxicity, oxidative stress, apoptosis and the autophagic effects of silver nanoparticles in mouse embryonic fibroblasts. *Biomaterials.* **35**, 4706–4715 (2014).
4. Hamzeh, M. & Sunahara, G. I. *In vitro* cytotoxicity and genotoxicity studies of titanium dioxide ( $\text{TiO}_2$ ) nanoparticles in Chinese hamster lung fibroblast cells. *Toxicol In Vitro.* **27**, 864–873 (2013).
5. Fu, P. P., Xia, Q., Hwang, H. M., Ray, P. C. & Yu, H. Mechanisms of nanotoxicity: generation of reactive oxygen species. *J Food Drug Anal.* **22**, 64–75 (2014).
6. Isaksen, I. S. A. & Dalsoren, S. B. Getting a better estimate of an atmospheric radical. *Science.* **6013**, 38–39 (2011).
7. Li, M., Yin, J. J., Wamer, W. G. & Lo, Y. M. Mechanistic characterization of titanium dioxide nanoparticle-induced toxicity using electron spin resonance. *J Food Drug Anal.* **22**, 76–85 (2014).
8. Chen, X., Tian, X., Shin, I. & Yoon, J. Fluorescent and luminescent probes for detection of reactive oxygen and nitrogen species. *Chem Soc Rev.* **40**, 4783–4804 (2011).
9. Kobayashi, H. *et al.* Quality control of reactive oxygen species measurement by luminol-dependent chemiluminescence assay. *J Androl.* **22**, 568–574 (2001).
10. He, W. *et al.* Photogenerated charge carriers and reactive oxygen species in  $\text{ZnO}/\text{Au}$  hybrid nanostructures with enhanced photocatalytic and antibacterial activity. *J Am Chem Soc.* **15**, 750–757 (2014).
11. Yin, J. J. *et al.* Phototoxicity of nano titanium dioxides in HaCaT keratinocytes—generation of reactive oxygen species and cell damage. *Toxicol Appl Pharmacol.* **15**, 81–88 (2012).
12. Lipovsky, A., Gedanken, A., Nitzan, Y. & Lubart, R. Enhanced inactivation of bacteria by metal-oxide nanoparticles combined with visible light irradiation. *Lasers Surg Med.* **43**, 236–240 (2011).
13. Dunnick, K. M. *et al.* The effect of tungstate nanoparticles on reactive oxygen species and cytotoxicity in raw 264.7 mouse monocyte macrophage cells. *J Toxicol Environ Health A.* **77**, 1251–1268 (2014).
14. He, W., Liu, Y., Wamer, W. G. & Yin, J. J. Electron spin resonance spectroscopy for the study of nanomaterial-mediated generation of reactive oxygen species. *J Food Drug Anal.* **22**, 49–63 (2014).
15. Makino, K., Mossoba, M. M. & Riesz, P. Chemical effects of ultrasound on aqueous solutions. Evidence for hydroxyl and hydrogen free radicals (.cndot.OH and .cndot.H) by spin trapping. *J Am Chem Soc.* **104**, 3537–3539 (1982).
16. Attri, P. *et al.* Generation mechanism of hydroxyl radical species and its lifetime prediction during the plasma-initiated ultraviolet (UV) photolysis. *Sci Rep.* **20**, 1–8 (2015).
17. Park, S. J. *et al.* Comparing the toxic mechanism of synthesized zinc oxide nanomaterials by physicochemical characterization and reactive oxygen species properties. *Toxicol Lett.* **15**, 197–203 (2011).
18. Prousek, P. Fenton chemistry in biology and medicine. *Pure Appl Chem.* **79**, 2325–2338 (2007).

19. Okuno, T., Kawai, H., Hasegawa, T., Ueno, H. & Nakamura, K. Enhancement of hydroxyl radical formation from superoxide anion radical in the presence of organic selenium compounds. *J Health Sci.* **47**, 240–247 (2001).
20. Yadav, D. K., Kruk, J., Sinha, R. K. & Pospíšil, P. Singlet oxygen scavenging activity of plastoquinol in photosystem II of higher plants: electron paramagnetic resonance spin-trapping study. *Biochim Biophys Acta.* **1797**, 1807–1811 (2010).
21. Weihua, L., Mouhua, W., Zhe, X. & Guozhong, W. The free radical species in polyacrylonitrile fibers induced by  $\gamma$ -radiation and their decay behaviors. *Radiat Phys Chem.* **81**, 835–839 (2012).
22. Keiichi, M., Yukio, M., Masahiro, K., Midori, H. & Akitane, M. The application of ESR spin-trapping technique to the evaluation of SOD-like activity of biological substances. *Bull Chem Soc Jpn.* **63**, 187–191 (1990).
23. Nam, S. N., Han, S. K., Kang, J. W. & Choi, H. Kinetics and mechanisms of the sonolytic destruction of non-volatile organic compounds: investigation of the sonochemical reaction zone using several OH $\cdot$  monitoring techniques. *Ultrason Sonochem.* **10**, 139–147 (2003).

## Acknowledgements

This research was supported by the Nano R&D Program through the National Research Foundation of Korea (NRF), funded by the Ministry of Science, ICT & Future Planning (NRF-2014M3A7A1052846) and grant no. 3420130200 (2013-0362), grant no. 0320140270 (2014-1040) from the Seoul National University Hospital Research Fund.

## Author Contributions

M.S.J. and K.N.Y. are considered as equal contributors to this work. M.S.J. performed the ESR analysis. K.N.Y. conceived the idea and conducted the design. H.H.C., S.J.P. and A.Y.L. coordinated the project. M.R.S. performed the TEM analysis and synthesis of nanomaterials. M.H.C. and J.S.K. supervised the work, analyzed the data and wrote the manuscript. All of the authors reviewed the manuscript.

## Additional Information

**Competing financial interests:** The authors declare no competing financial interests.

**How to cite this article:** Jeong, M. S. *et al.* Methodological considerations of electron spin resonance spin trapping techniques for measuring reactive oxygen species generated from metal oxide nanomaterials. *Sci. Rep.* **6**, 26347; doi: 10.1038/srep26347 (2016).



This work is licensed under a Creative Commons Attribution 4.0 International License. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in the credit line; if the material is not included under the Creative Commons license, users will need to obtain permission from the license holder to reproduce the material. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>