

## Old Dominion University ODU Digital Commons

Electrical & Computer Engineering Faculty  
Publications

Electrical & Computer Engineering

2002

# High-Efficiency Solar Cells Based on Cu(InAl)Se<sub>2</sub> Thin Films

S. Marsillac

Old Dominion University, [Smarsill@odu.edu](mailto:Smarsill@odu.edu)


P.D. Paulson

M. W. Haimbodi

R. W. Birkmire

W. N. Shafarman

Follow this and additional works at: [https://digitalcommons.odu.edu/ece\\_fac\\_pubs](https://digitalcommons.odu.edu/ece_fac_pubs)

 Part of the [Engineering Physics Commons](#), [Materials Science and Engineering Commons](#), and the [Power and Energy Commons](#)

### Repository Citation

Marsillac, S.; Paulson, P. D.; Haimbodi, M. W.; Birkmire, R. W.; and Shafarman, W. N., "High-Efficiency Solar Cells Based on Cu(InAl)Se<sub>2</sub> Thin Films" (2002). *Electrical & Computer Engineering Faculty Publications*. 22.  
[https://digitalcommons.odu.edu/ece\\_fac\\_pubs/22](https://digitalcommons.odu.edu/ece_fac_pubs/22)

### Original Publication Citation

Marsillac, S., Paulson, P.D., Haimbodi, M.W., Birkmire, R.W., & Shafarman, W.N. (2002). High-efficiency solar cells based on Cu(InAl)Se<sub>2</sub> thin films. *Applied Physics Letters*, 81(7), 1350-1352. doi: 10.1063/1.1499990



## High-efficiency solar cells based on Cu ( InAl ) Se 2 thin films

S. Marsillac, P. D. Paulson, M. W. Haimbodi, R. W. Birkmire, and W. N. Shafarman

Citation: [Applied Physics Letters](#) **81**, 1350 (2002); doi: 10.1063/1.1499990

View online: <http://dx.doi.org/10.1063/1.1499990>

View Table of Contents: <http://scitation.aip.org/content/aip/journal/apl/81/7?ver=pdfcov>

Published by the [AIP Publishing](#)

---

### Articles you may be interested in

[Reliable wet-chemical cleaning of natively oxidized high-efficiency Cu\(In,Ga\)Se<sub>2</sub> thin-film solar cell absorbers](#)  
J. Appl. Phys. **116**, 233502 (2014); 10.1063/1.4903976

[Structure and interface chemistry of MoO<sub>3</sub> back contacts in Cu\(In,Ga\)Se<sub>2</sub> thin film solar cells](#)  
J. Appl. Phys. **115**, 033514 (2014); 10.1063/1.4862404

[Study of molybdenum back contact layer to achieve adherent and efficient CIGS<sub>2</sub> absorber thin-film solar cells](#)  
J. Vac. Sci. Technol. A **23**, 1197 (2005); 10.1116/1.1889440

[Cathodoluminescence of Cu\(In,Ga\)Se<sub>2</sub> thin films used in high-efficiency solar cells](#)  
Appl. Phys. Lett. **83**, 4770 (2003); 10.1063/1.1631083

[CuIn<sub>1-x</sub>Al<sub>x</sub>Se<sub>2</sub> thin films and solar cells](#)  
J. Appl. Phys. **91**, 10153 (2002); 10.1063/1.1476966

---

The image shows the cover of an Applied Physics Reviews journal issue. It features a blue and orange color scheme with a molecular structure background. The text 'NEW Special Topic Sections' is prominently displayed in white. Below it, 'NOW ONLINE' is written in orange, followed by the title 'Lithium Niobate Properties and Applications: Reviews of Emerging Trends' in white. The AIP Applied Physics Reviews logo is in the bottom right corner.

**NEW Special Topic Sections**

**NOW ONLINE**  
Lithium Niobate Properties and Applications:  
Reviews of Emerging Trends

**AIP** Applied Physics Reviews

## High-efficiency solar cells based on Cu(InAl)Se<sub>2</sub> thin films

S. Marsillac,<sup>a)</sup> P. D. Paulson, M. W. Haimbodi, R. W. Birkmire, and W. N. Shafarman<sup>b)</sup>  
*Institute of Energy Conversion, University of Delaware, Newark, Delaware 19716*

(Received 28 May 2002; accepted for publication 17 June 2002)

A Cu(InAl)Se<sub>2</sub> solar cell with 16.9% efficiency is demonstrated using a Cu(InAl)Se<sub>2</sub> thin film deposited by four-source elemental evaporation and a device structure of glass/Mo/Cu(InAl)Se<sub>2</sub>/CdS/ZnO/indium tin oxide/(Ni/Algrid)/MgF<sub>2</sub>. A key to high efficiency is improved adhesion between the Cu(InAl)Se<sub>2</sub> and the Mo back contact layer, provided by a 5-nm-thick Ga interlayer, which enabled the Cu(InAl)Se<sub>2</sub> to be deposited at a 530 °C substrate temperature. Film and device properties are compared to Cu(InGa)Se<sub>2</sub> with the same band gap of 1.16 eV. The solar cells have similar behavior, with performance limited by recombination through trap states in the space charge region in the Cu(InAl)Se<sub>2</sub> or Cu(InGa)Se<sub>2</sub> layer. © 2002 American Institute of Physics. [DOI: 10.1063/1.1499990]

The Cu(InGa)Se<sub>2</sub> thin films in high efficiency solar cells typically have Ga/(In+Ga) ≈ 0.1–0.3 giving a band gap ( $E_g$ ) = 1.1–1.2 eV. Significant effort has been made to develop high efficiency solar cells based on wider band gap CuInSe<sub>2</sub> alloys by replacing In with Ga, or Se with S. The goal is improved module performance resulting from the tradeoff between higher voltage and lower current at maximum power which can allow fewer scribes for monolithic integration or reduced losses in the transparent conducting oxide layer. Further, wider band gaps could be used to develop multijunction devices with even higher efficiency. However, with band gaps greater than 1.3 eV, the efficiency of Cu(InGa)Se<sub>2</sub> devices is limited by a degradation of the electronic properties of the Cu(InGa)Se<sub>2</sub> layer leading to losses in fill factor (FF) and open circuit voltage ( $V_{OC}$ ).<sup>1,2</sup>

We have recently reported on Cu(InAl)Se<sub>2</sub> films deposited by multisource elemental evaporation, in which the band gap can be varied from 1.0 to 2.7 eV.<sup>3,4</sup> Solar cells with 11% efficiency were fabricated, but poor adhesion limited the substrate temperature ( $T_{SS}$ ) used for the growth of the Cu(InAl)Se<sub>2</sub> film which restricted the cell efficiency. In this letter, a method to improve the adhesion, allowing higher  $T_{SS}$ , is presented and a Cu(InAl)Se<sub>2</sub> based solar cell with 16.9% efficiency is demonstrated. Film and device properties are compared to Cu(InGa)Se<sub>2</sub> with the same band gap of 1.16 eV.

Cu(InAl)Se<sub>2</sub> and Cu(InGa)Se<sub>2</sub> films were deposited by elemental evaporation on Mo-coated soda lime glass at  $T_{SS}$  = 530 and 550 °C, respectively. The films were 2.0–2.5 μm thick. The ratio of Al or Ga to In was adjusted so that the films had the same band gap. Delivery rates of all metals were constant during the 60 min film growth and secondary ion mass spectroscopy (SIMS) depth profile measurements confirmed that the films have uniform composition and, therefore, band gap. At substrate temperatures greater than 450 °C, the Cu(InAl)Se<sub>2</sub> did not adhere well to the glass/Mo

substrate. It has been previously shown that the addition of Ga to CuInSe<sub>2</sub> films improves their adhesion to Mo.<sup>5</sup> Therefore, a 5-nm-thick Ga film was sputtered onto the Mo prior to the growth of Cu(InAl)Se<sub>2</sub>. This resulted in improved adhesion and allowed films to be deposited at  $T_{SS}$  = 530 °C. SIMS measurements showed that the Ga is distributed through the Cu(InAl)Se<sub>2</sub> film, but it accounts for only 0.3 at. % of the Cu(InAl)Se<sub>2</sub>. All Cu(InGa)Se<sub>2</sub> films exhibited good adhesion.

The compositions of Cu(InAl)Se<sub>2</sub> and Cu(InGa)Se<sub>2</sub> films were determined by energy dispersive x-ray spectroscopy (EDS) and are shown in Table I. The ratios  $x \equiv \text{Al}/(\text{In} + \text{Al})$  and  $\text{Ga}/(\text{In} + \text{Ga})$  were 0.13 and 0.26, respectively, for films with  $E_g$  = 1.16 eV. For the Cu(InAl)Se<sub>2</sub>, the optical absorption coefficient ( $\alpha$ ) was determined by spectroscopic ellipsometry<sup>4</sup> and  $E_g$  was obtained from the intercept of  $(\alpha E)^2$  plotted versus  $E$ . The band gap for Cu(InGa)Se<sub>2</sub> was determined from the composition as in previous work.<sup>1</sup> Scanning electron microscopy characterization of the surface and the cross section of the films shows similar surface morphology with columnar grains for both films, and cross-sectional grain width in the range of ~1 μm.

X-ray diffraction (XRD) measurements with Bragg–Brentano ( $\theta$ – $2\theta$  configuration) focusing geometry and Cu  $K\alpha$  radiation show that the Cu(InAl)Se<sub>2</sub> and Cu(InGa)Se<sub>2</sub> films are single phase and nearly randomly oriented. Figure 1 compares the (112) reflections for CuInSe<sub>2</sub>, Cu(InAl)Se<sub>2</sub>, and Cu(InGa)Se<sub>2</sub>. The lattice spacing  $d(112)$  and full width at half maximum (FWHM) are included in Table I. In each case, the variation in lattice spacing with Al and Ga content follows Vegards law,<sup>4</sup> but the shift in  $d(112)$  from CuInSe<sub>2</sub>,

TABLE I. Results of EDS and XRD measurements on Cu(InAl)Se<sub>2</sub> and Cu(InGa)Se<sub>2</sub> films.

Sample	Cu	In	Al or Ga	Se	$x$	$d(112)$ (Å)	FWHM (°)
Cu(InAl)Se <sub>2</sub>	23.5	23.0	3.5	50.0	0.13	3.324	0.14
Cu(InGa)Se <sub>2</sub>	24.1	19.7	6.9	49.3	0.26	3.312	0.13

<sup>a)</sup>Permanent address: Equipe de Physique des Solides pour l'Electronique, FSTN, BP 92208, 2 Rue de la Houssinière, 44322 Nantes Cedex 03, France.

<sup>b)</sup>Electronic mail: wns@udel.edu

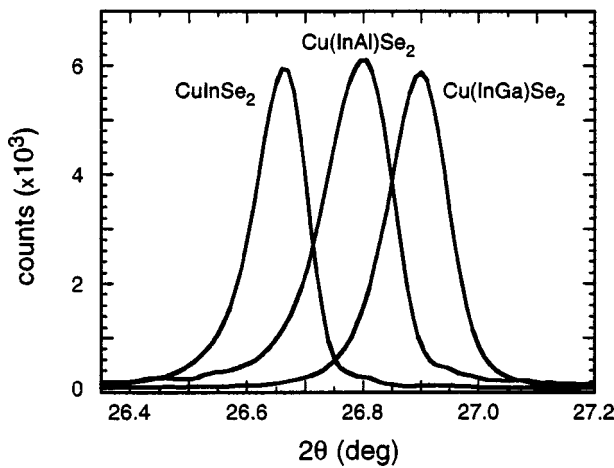


FIG. 1. XRD scans of the (112) peaks of the Cu(InAl)Se<sub>2</sub> and Cu(InGa)Se<sub>2</sub> films and a CuInSe<sub>2</sub> film for comparison.

with  $d(112) = 3.343 \text{ \AA}$ , is smaller for the Cu(InAl)Se<sub>2</sub> film than for the Cu(InGa)Se<sub>2</sub>. This shows that alloying with Al allows the band gap to be increased with less variation in lattice spacing than with Ga. The FWHM for all films is comparable to the instrumental broadening of  $0.11^\circ$  which indicates that compositional variations are small, with a maximum variation in  $x$  of  $\pm 2\%$ .

Solar cells were fabricated with the structure glass/Mo/[Cu(InAl)Se<sub>2</sub> or Cu(InGa)Se<sub>2</sub>]/CdS/ZnO/indium tin oxide (ITO)/MgF<sub>2</sub> with a Ni/Al collection grid. The CdS was deposited with a thickness of  $\sim 40 \text{ nm}$  by chemical bath deposition. ZnO and ITO were deposited by rf sputtering, with the ITO having a sheet resistance of  $25 \Omega/\square$ . The MgF<sub>2</sub> antireflection layers and grids were deposited by electron-beam evaporation. Current–voltage ( $J$ – $V$ ) characteristics were measured at the National Renewable Energy Laboratory (NREL) under standard conditions ( $100 \text{ mW/cm}^2$ ,  $25^\circ\text{C}$ ; ASTM: E 892 Global). The open circuit voltage ( $V_{OC}$ ), short circuit current ( $J_{SC}$ ), and efficiency ( $\eta$ ) are listed in Table II. The  $J$ – $V$  and quantum efficiency (QE) curves, also measured at NREL, are shown in Figs. 2 and 3. The cells have comparable efficiency with slightly higher  $V_{OC}$  and lower FF for the Cu(InAl)Se<sub>2</sub> device. The QE curves are nearly indistinguishable, in agreement with the cells having the same band gap and  $J_{SC}$ .

The  $J$ – $V$  data were analyzed using a standard diode equation

$$J = J_0 \exp\left[\frac{q}{AkT}(V - R_s J)\right] - J_0 - J_L + GV, \quad (1)$$

where  $J_0$  is the forward current,  $A$  is the diode quality factor,  $J_L$  is the light generated current,  $R_s$  is the series resistance, and  $G$  is the shunt conductance. For the devices in this work,  $G < 1 \text{ mS/cm}^2$  and can be neglected.  $R_s$  was determined

TABLE II. Solar cell parameters and results of diode analysis.

Film	$\eta$ (%)	$V_{OC}$ (mV)	$J_{SC}$ (mA/cm <sup>2</sup> )	FF (%)	$R_s$ ( $\Omega \text{ cm}^2$ )	$A$	$J_0$ (mA/cm <sup>2</sup> )
Cu(InAl)Se <sub>2</sub>	16.9	621	36.0	75.5	0.5	1.5	$1 \times 10^{-5}$
Cu(InGa)Se <sub>2</sub>	16.5	593	35.8	77.7	0.1	1.4	$2 \times 10^{-6}$

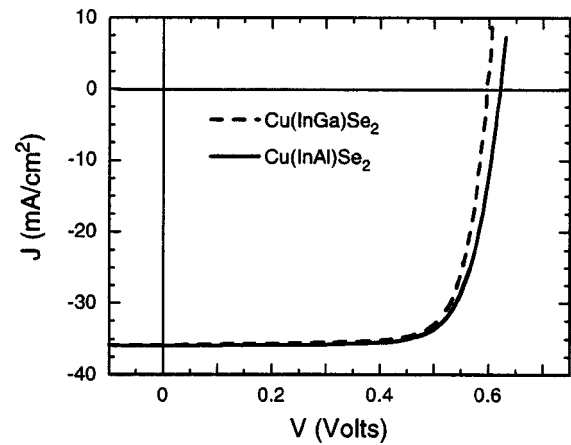


FIG. 2. Current–voltage curves for the Cu(InAl)Se<sub>2</sub> and Cu(InGa)Se<sub>2</sub> devices.

from the intercept of a plot of the derivative  $dV/dJ$  vs  $(J + J_{SC})^{-1}$ , since, according to Eq. (1) with  $J_L = J_{SC}$ :

$$\frac{dV}{dJ} = R_s + \frac{AkT}{q} (J + J_{sc})^{-1}. \quad (2)$$

Using the value of  $R_s$ , listed in Table II, the semi-logarithmic plot of  $J + J_{SC}$  vs  $V - R_s J$  is shown for the two cells in Fig. 4. In each case the data is linear over more than an order of magnitude demonstrating a good fit to Eq. (1) with no significant loss due to voltage dependent collection of the light generated current. The slope and intercept in Fig. 4 give  $A$  and  $J_0$ , also listed in Table II. In addition, the temperature dependence of  $V_{OC}$  was measured at 10 K intervals from 218 to 318 K. For both cells,  $V_{OC}$  varied linearly with  $T$  and extrapolation to  $T = 0$  gave the band gap of 1.16 V. This shows that the recombination is in the absorber layer. Thus, the diode behavior of both devices is consistent with the forward diode current limited by Shockley–Read–Hall recombination through trap states within the space-charge region of the absorber.<sup>6,7</sup> The Cu(InAl)Se<sub>2</sub> device has larger  $A$  and smaller  $J_0$  than the Cu(InGa)Se<sub>2</sub> which suggest differences in the defect distributions which control the recombination.

In conclusion, the adhesion of Cu(InAl)Se<sub>2</sub> films was improved by the addition of a 5-nm-thick Ga film on the glass/Mo substrate which allowed the films to be deposited at

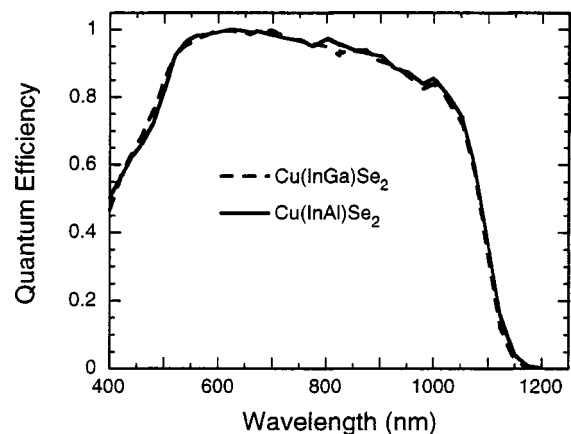


FIG. 3. Normalized quantum efficiency curves for the Cu(InAl)Se<sub>2</sub> and Cu(InGa)Se<sub>2</sub> devices.

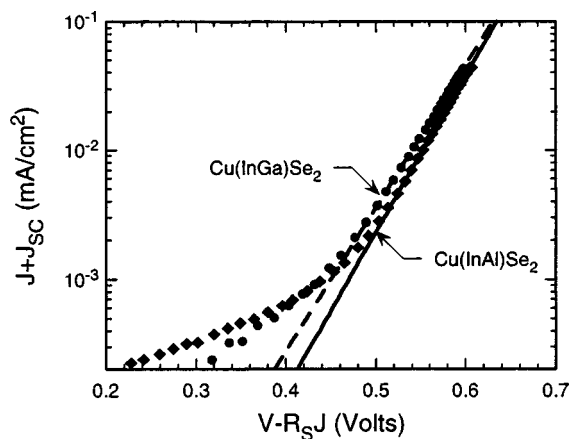


FIG. 4. Semi-logarithmic plot of  $J + J_{SC}$  vs  $V - R_S J$  under illumination for the  $\text{Cu}(\text{InAl})\text{Se}_2$  and  $\text{Cu}(\text{InGa})\text{Se}_2$  devices.

a substrate temperature of 530 °C. The higher substrate temperature resulted in  $\text{Cu}(\text{InAl})\text{Se}_2$  with improved electronic properties and a solar cell with 16.9% efficiency was fabricated. The  $\text{Cu}(\text{InAl})\text{Se}_2$  solar cells diode characteristics are similar to  $\text{Cu}(\text{InGa})\text{Se}_2$  with the same band gap, limited by recombination through defect states in the absorber layer.

The authors thank T. Lampros, K. Hart, T. Minemoto, and S. Hegedus at IEC for technical assistance, and C. Perkins, S. Asher, and T. Moriarty at NREL for film and device measurements. This work was supported, in part, by NREL under Subcontract No. ADJ-1-30630-12 and by NIST under an Advanced Technology Program in collaboration with ITN Energy Systems and Global Solar Energy.

<sup>1</sup>W. N. Shafarman, R. Klenk, and B. E. McCandless, *J. Appl. Phys.* **79**, 7324 (1996).

<sup>2</sup>U. Rau, M. Schmidt, A. Jasenek, G. Hanna, and H. W. Schock, *Sol. Energy Mater. Sol. Cells* **67**, 137 (2001).

<sup>3</sup>M. W. Haimbodi, E. Gourmelon, P. D. Paulson, R. W. Birkmire, and W. N. Shafarman, *Proc. 28th IEEE Photovoltaic Specialists Conference, Anchorage, AL* (IEEE, New York, 2001), p. 454.

<sup>4</sup>P. D. Paulson, M. W. Haimbodi, S. Marsillac, W. N. Shafarman, and R. W. Birkmire, *J. Appl. Phys.* **91**, 10153 (2002).

<sup>5</sup>C. Jensen, D. Tarrant, J. Ermer, and G. Pollock, *Proc. 23rd IEEE Photovoltaic Specialists Conference, Louisville, KY* (IEEE, New York, 1993), p. 577.

<sup>6</sup>M. Roy, S. Damaskinos, and J. E. Phillips, *Proc. 20th IEEE Photovoltaic Specialists Conference, Las Vegas, NV* (IEEE, New York, 1988), p. 1618.

<sup>7</sup>U. Rau and H. Schock, *Appl. Phys. A: Mater. Sci. Process.* **A69**, 131 (1999).