

Fermi- to non-Fermi-liquid crossover and Kondo behavior in two-dimensional $(\text{Cu } 2/3 \text{ V } 1/3)\text{V}_2\text{S}_4$

A. Gauzzi, H. Moutaabbid, Y. Klein, G. Loupiau, Vincent Hardy

► **To cite this version:**

A. Gauzzi, H. Moutaabbid, Y. Klein, G. Loupiau, Vincent Hardy. Fermi- to non-Fermi-liquid crossover and Kondo behavior in two-dimensional $(\text{Cu } 2/3 \text{ V } 1/3)\text{V}_2\text{S}_4$. *Journal of Physics: Condensed Matter*, IOP Publishing, 2019, 31 (31), pp.31LT01. 10.1088/1361-648X/ab1d9b . hal-02161160

HAL Id: hal-02161160

<https://hal.archives-ouvertes.fr/hal-02161160>

Submitted on 12 Jul 2019

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

Fermi- to non-Fermi-liquid crossover and Kondo behavior in two-dimensional $(\text{Cu}_{2/3}\text{V}_{1/3})\text{V}_2\text{S}_4$

Andrea Gauzzi¹, Hicham Moutaabbid¹, Yannick Klein¹, Geneviève Loupiau¹, Vincent Hardy²

E-mail: andrea.gauzzi@upmc.fr

¹Institut de Minéralogie, de Physique des Matériaux et de Cosmochimie (IMPMC)
UMR7590, Sorbonne Université/CNRS/MNHN, 4 place Jussieu, 75005 Paris, France

²Laboratoire CRISMAT UMR 6508, CNRS/ENSICAEN/UCBN, Caen, France

Abstract.

By means of a specific heat (C) and electrical resistivity (ρ) study, we give evidence of a pronounced Fermi liquid (FL) behavior with sizable mass renormalization, $m^*/m = 30$, up to unusually high temperatures ~ 70 K in the layered system $(\text{Cu}_{2/3}\text{V}_{1/3})\text{V}_2\text{S}_4$. At low temperature, a marked upturn of both C and ρ is suppressed by magnetic field, which suggests a picture of Kondo coupling between conduction electrons in the VS_2 layers and impurity spins of the V^{3+} ions located between layers. This picture opens the possibility of controlling electronic correlations and the FL to non-FL crossover in simple layered materials. For instance, we envisage that the coupling between layers provided by the impurity spins may realize a two-channel Kondo state.

Keywords: Fermi liquids, Kondo effect, Transition metal chalcogenides

The solid state chemistry of layered transition metal chalcogenides (LTMC) displays ideal characteristics for tuning or even radically changing the electronic and transport properties of two-dimensional systems, which is promising for the development of novel materials in view of electronic, photonic and thermoelectric applications [1]. Chemical intercalation has been widely used to electronically dope the conducting layers in a variety of LTMCs, such as 1T-TaS₂ [2] and 1T-TiSe₂ [3], which has unveiled an interesting interplay between charge density wave (CDW) orders and superconductivity (SC). Novel capabilities enabling the control of thickness down to the atomic limit and electronic doping *via* ionic gating have led to striking discoveries, such as a modification from indirect to direct band gap in MoS₂ in the monolayer limit [4] and high temperature SC in the FeSe system, where the critical temperature dramatically increases from 30 K in the bulk [5] up to 100 K in monolayers [6].

In order to master the above properties, it is important to know to which extent band theory is applicable to LTMCs. In principle, one expects weaker electronic correlations in LTMCs than in transition metal (TM) oxides, considering the reduced ionicity of S and Se and the comparatively large bandwidth of hybrid S(3*p*) or Se(4*p*) - (TM)*d* states. In practice, the question remains controversial even for well-studied compounds, such as the aforementioned 1T-TiSe₂ and 1T-TaS₂ systems. In Cu-intercalated 1T-TiSe₂, first-principles calculations within density functional theory explain the SC and CDW phases without invoking many-body effects [7], while photoemission experiments suggest that the Coulomb electron-hole interaction is required to stabilize the CDW phase [8]. In 1T-TaS₂, it has been established that Mott localization controls the stability of a complex sequence of CDW and SC transitions [2, 9], as originally proposed by Fazekas and Tosatti [10] and confirmed experimentally by various authors [11, 12]. However, in spite of an intense research effort for more than forty years, the microscopic mechanism of these transitions remains elusive due to a complex interplay between electronic and lattice degrees of freedom [13].

Here, we report on the observation of Fermi-liquid (FL) behavior with sizable mass renormalization preceding a Kondo effect [14, 15] in the LTMC system $(\text{Cu}_{2/3}\text{V}_{1/3})\text{V}_2\text{S}_4$ (CVS). To the best of our knowledge, this result has never been observed before in LTMCs. As shown in Figure 1, CVS is characterized by a defect NiAs structure consisting of a stacking of 1T-VS₂ layers and of chains of edge-sharing $(\text{Cu}_{1-x}\text{V}_x)\text{S}_6$ octahedra [16]. As

compared to previous LTMCs, CVS displays no CDW or SC instabilities and no indications of strong electron-lattice coupling, which may explain why the FL to non-FL (NFL) crossover is clearly observed experimentally.

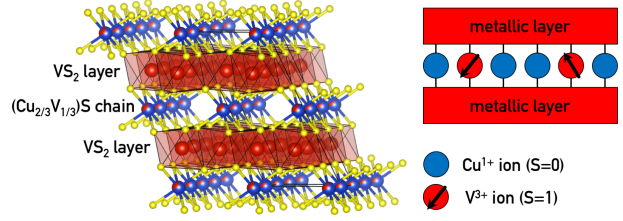


Figure 1. (Color online) Left: layered crystal structure of $(\text{Cu}_{2/3}\text{V}_{1/3})\text{V}_2\text{S}_4$ showing the stacking of 1T-type VS₂ layers (red octahedra) and of $(\text{Cu}_{2/3}\text{V}_{1/3})\text{S}$ chains. Yellow and red/blue spheres indicate the S and Cu/V atoms, respectively. Right: schematic representation of the structure showing the presence of magnetic ($S = 1$) V³⁺ and nonmagnetic ($S = 0$) Cu¹⁺ ions in the chains between metallic VS₂ layers.

The present finding is attributed to the peculiar properties of the above crystal structure enabling a coupling between conduction electrons in the layers and magnetic ($S = 1$) V³⁺ impurities in the chains. This coupling is the essential ingredient of the Kondo effect [14] which gives rise to a singlet state with NFL properties. If confirmed, the picture proposed here would open the possibility of tuning the FL to NFL crossover in the regime of moderate electronic correlations characteristic of TM sulfides, a convenient regime for first-principles calculations. This would be a step towards a better understanding of correlated materials and their functionalization.

Our original motivation was to verify the expectation of metallic transport in CVS, suggested by previous magnetic susceptibility data [16] showing an enhanced Pauli-like term attributed to electronic correlations and no long-range magnetic order. For the present study, we have measured single crystals synthesized under high pressure, as described elsewhere [16]. Typical crystal dimensions are $0.4 \times 0.15 \text{ mm}^2$ in the *ab*-plane and 0.03 - 0.08 mm thickness along the *c*-axis. A few crystals were selected for dc resistivity measurements in a four-contact bar configuration using a commercial Quantum Design Physical Properties measurement system (PPMS). Specific heat measurements were carried out in the PPMS on a bunch of crystals from the same batch using a $2-\tau$ relaxation method. Both types of measurements were carried out in the 2-300 K range by varying magnetic field up to 9 T. The reproducibility of the results was checked by measuring

two batches of crystals grown under the same synthesis conditions.

Figure 2 summarizes the results of the in-plane resistivity measurements. Note the following: (i) a metallic behavior with room temperature resistivity $\rho_{300\text{K}}=0.44$ m Ω cm and a modest residual resistivity ratio, $RRR = \rho_{300\text{K}}/\rho_{2\text{K}} \sim 2$; (ii) a pronounced upturn below ~ 20 K completely suppressed by a magnetic field of 9 T. Feature (i) is characteristic of bad metals and common in 2D sulfides, such as V_5S_8 [17, 18], which shares with CVS a similar layered structure except it contains only 1/2 - instead of one - interstitial metal atom per VS_2 layer. (iii) In the temperature region between the upturn and 70 K, the $\rho(T)$ curve displays a marked quadratic dependence, a signature of Fermi-liquid behavior arising from electron-electron scattering.

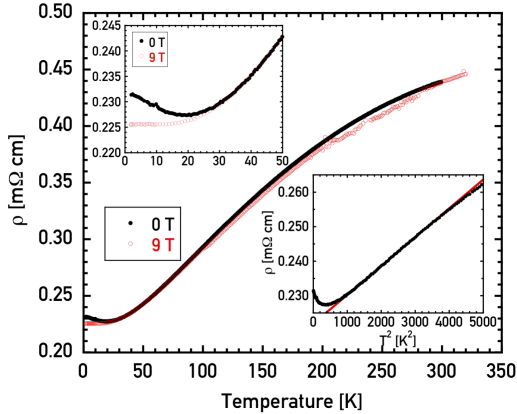


Figure 2. (Color online) In-plane resistivity curves of a representative $(\text{Cu}_{2/3}\text{V}_{1/3})\text{V}_2\text{S}_4$ single crystal taken at zero-field and at 9 T. Top inset: enlarged view of the minimum at ~ 20 K suppressed by the field. Bottom inset: the linearity of the ρ vs. T^2 plot in the 30-70 K range gives evidence of Fermi-liquid behavior. The red solid line is a linear fit in this range. The results of the fit are given in the text.

A quadratic dependence of $\rho(T)$ has been previously reported in transition metals [19], intermetallic compounds, such as A15 superconductors [20], TM oxides like V_2O_3 [21], SrTiO_3 [22] and Sr_2RuO_4 [23], and heavy-fermions [24, 25, 15], but never in LTMCs. A caveat concerns a similar dependence reported in $\text{Ti}_{1+x}\text{S}_2$ [26], which shares with CVS a 1T-type layered structure with x interstitial Ti atoms between TiS_2 layers. A subsequent study showed that the power-law of $\rho(T)$ strongly varies with x - hence with carrier concentration - and that the dominant scattering mechanism is phononic [27]. It is not common that this quadratic dependence extends to high temperatures, as observed here. To the best of our knowledge, a similar finding concerns a few other d -electron systems like the aforementioned SrTiO_3 and Sr_2RuO_4 . This unusual feature is ascribed to the small carrier density of CVS and/or to a large electron-electron scattering cross-section, so that the quadratic term dominates the other (*e.g.* electron-

phonon) terms. The observation of a FL-like quadratic term up to high temperatures ~ 70 K further indicates that coherent quasiparticles survive at these temperatures [28]. A high coherence temperature for the quasiparticles in CVS is compatible with the comparatively weak electron-electron correlations in d -electron systems, as compared to f -electron heavy fermions, where the quadratic term is rarely observed and, in any case, limited to much lower temperatures ~ 0.1 -1 K [25, 15].

Assuming a FL scenario for CVS, we quantify the strength of the electron-electron scattering by analyzing the curve of Figure 2 using the FL expression $\rho(T) = \rho_0 + AT^2$. A linear fit of the curve in the 30-70 K region above the upturn yields $A = 8.4 \times 10^{-3} \mu\Omega\text{cm K}^{-2}$, two orders of magnitude larger than typical values for transition metals [19] and comparable to the values reported on the aforementioned TM oxides V_2O_3 [21], Sr_2RuO_4 [23] or LiV_2O_4 [29], which are established Fermi liquids. We conclude that CVS exhibits intermediate heavy-fermion properties. This conclusion is confirmed by the large electronic contribution to the specific heat, γ , obtained from a C/T vs. T^2 plot (see Figure 3). A linear fit yields $\gamma = 60 \pm 4$ mJ mol $^{-1}$ K $^{-2}$ and a Debye temperature $\Theta_D = 294 \pm 5$ K \ddagger . Remarkably, Figure 4 shows that the experimental A and γ values nicely fall onto the universal curve $A/\gamma^2 = 1.0 \times 10^{-5} \mu\Omega\text{cm} (\text{mol K mJ}^{-1})^2$ found by Kadowaki and Woods for heavy fermions [24] \S in the regime of intermediate mass renormalization, $m^*/m = 30$.

The scenario of correlated metal is confirmed by the universal prediction for the Sommerfeld-Wilson ratio, $R_W = \frac{4}{3} \left(\frac{\pi k_B}{g\mu_B} \right)^2 \frac{\chi_0}{\gamma}$, where g is the gyromagnetic ratio of the electron, μ_B is the Bohr magneton and χ_0 is the Pauli susceptibility. Within a FL picture, both χ_0 and γ are proportional to the density of states at the Fermi level, hence $R_W = 1$. On the other hand, in the Kondo impurity problem, R_W increases up to 2 according to a robust result of renormalization group theory [33, 34]. In our case, by taking the experimental value $\chi_0 = 1.02 \times 10^{-3}$ cm 3 mol $^{-1}$ from [16], we obtain $R_W = 2$ within the experimental error (see Figure 4), which surprisingly suggests that CVS is a correlated Kondo metal. Further Kondo signatures are the resistivity upturn at low temperature and a similar upturn of the C/T curve at ~ 6 K, both suppressed by a 9 T field (see Figs. 1-2). The $\sim 2\%$ increase of the resistivity is comparable with that of AuFe [35] and about ten times smaller than that of CuMn [36].

In order to check the validity of the Kondo picture, we analyze the temperature dependence of the upturn of the resistivity in Figure 2. In the limit of diluted impurities, following the well-established result of Kondo's perturbative theory [14] confirmed by subsequent studies that include a self-consistent treatment by Nagaoka [37],

\ddagger The statistical uncertainty in the γ and β values arises from the choice of the region of the C/T vs. T^2 plot for the linear fit.

\S We consider the γ value per mole of planar V ions because each formula unit contains two V ions in the conducting VS_2 planes.

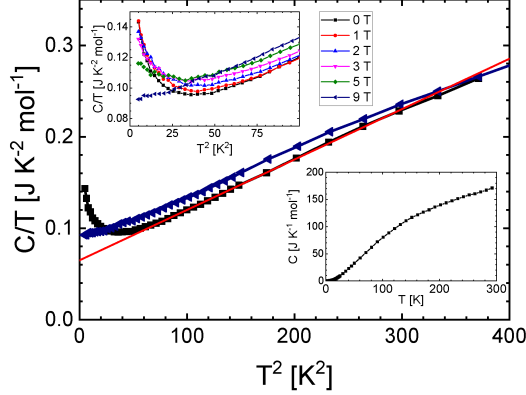


Figure 3. (Color online) Temperature and magnetic field dependence of the constant-pressure specific heat, C , measured on a bunch of $(\text{Cu}_{2/3}\text{V}_{1/3})\text{V}_2\text{S}_4$ single-crystals. The main panel shows the zero-field and 9 T curves and a fit of the former curve (red solid line) in the 10-20 K region using the linear dependence, $C/T = \gamma + \beta T^2$, expected from band theory at low temperatures. Note a marked upturn of the zero-field curve suppressed by the 9 T field. Top inset: enlarged view of the low-temperature behavior of the C/T vs. T^2 curves at various fields in the 0-9 T range. Bottom inset: zero-field C vs. T curve in the whole temperature range measured.

one finds that the excess resistivity $\Delta\rho(T)$ describing the upturn diverges logarithmically as:

$$\Delta\rho(T) = -c \frac{3\pi m^* J}{16 ne^2 \hbar} \ln \frac{T}{0.68 T_K} \quad (1)$$

where c is the impurity concentration, m^* and n are the effective mass and density of conduction electrons, respectively and J is the exchange energy between conduction electron and magnetic impurity. J is related to the characteristic Kondo energy, T_K , via the BCS-like expressions $\Delta_0 = 1.14 k_B T_K$ and $\Delta_0 = D \exp[-1/Jg(\epsilon_F)]$, where Δ_0 is the zero-temperature Kondo energy, D is the bandwidth and $g(\epsilon_F)$ is the density of states at the Fermi level, ϵ_F . This perturbative result is valid only in the high temperature limit, $T \gg T_K$. In the opposite limit, various authors found that the logarithmic divergence is removed as electron-electron interactions become unimportant [37, 38, 39, 33]. The system then recovers a FL regime that manifests itself as a saturation of the resistivity described by a Lorentzian dependence [37]:

$$\Delta\rho(T) = \Delta\rho(0) \left[1 + \frac{\pi^2}{3} \left(\frac{k_B T}{\Delta} \right)^2 \right]^{-1} \quad (2)$$

A straightforward data fit shows that the $\rho(T)$ curve of Figure 2 is very well explained in a wide 2-70 K range by adding the $\Delta\rho(T)$ term of eq. (2) to the Fermi liquid contribution $\rho_0 + AT^2$. In Figure 5, we plot the $\rho(T)$ curve together with the best fit that yields $T_K = 27.6 \pm 0.2$ K, consistent with the rule of thumb that T_K corresponds to the resistivity minimum. The high quality of the agreement does not even require using eq. (1), instead of eq. (2), in

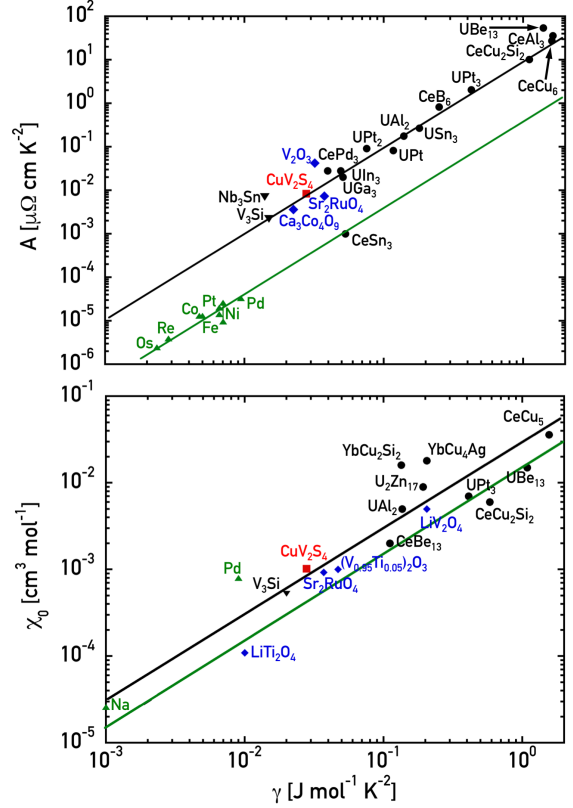


Figure 4. Upper panel: Kadowaki-Woods plot of the T^2 resistivity coefficient, A , vs. Sommerfeld constant, γ , where the present result for $(\text{Cu}_{2/3}\text{V}_{1/3})\text{V}_2\text{S}_4$ (red square) is compared with previous data for heavy-fermions (black circles) [24], 3d TM oxides (blue diamonds) [21, 23], A15 superconductors (black triangles) [20] and simple metals (green triangles) [19]. Black and green solid lines indicate the universal predictions including [20] or neglecting [19] many-body effects, respectively. Lower panel: the same as above for the Sommerfeld-Wilson plot of the Pauli susceptibility, χ_0 vs. γ . Black and green solid lines indicate the universal predictions for free-electron systems and heavy fermions [30], respectively. The χ_0 value for $(\text{Cu}_{2/3}\text{V}_{1/3})\text{V}_2\text{S}_4$ (red square) is taken from [16]. Data include heavy-fermions (black circles) [30], 3d-metal oxides (blue diamonds) [31, 23, 32], A15 superconductors (black triangles) [30] and simple metals (green triangles) [30].

the high temperature region $T \gg T_K$ where, in principle, eq. (1) would be more suitable. Note that the saturation of the resistivity upturn at low temperature, visible in Figure 5 and explained quantitatively by eq. (2), rules out a weak-localization scenario, according to which the resistivity should diverge in the $T \rightarrow 0$ K limit. Other Kondo systems like CuFe and CuMn display a similar saturation of the resistivity upturn [40].

The analysis of the specific heat data of Figure 3 further supports a picture of Kondo system. We determine the Kondo contribution, $\Delta C(T)$, associated with the upturn of the experimental C/T vs T^2 curve, by subtracting from this curve the conventional dependence $C_0/T = \gamma + \beta T^2$ that describes well the data above the upturn (see linear fit in Figure 3). Figure 5 shows that $\Delta C(T)$ displays a linear

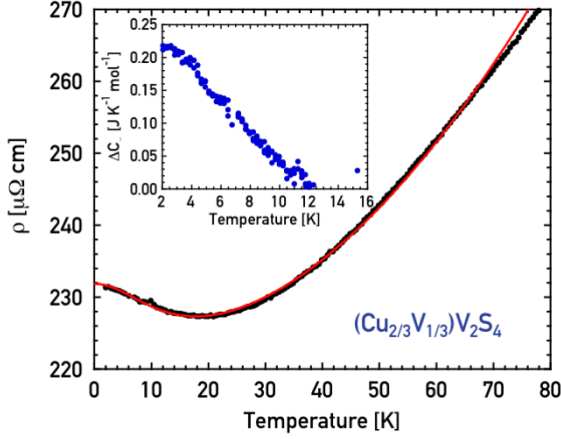


Figure 5. (Color online) Comparison between the experimental resistivity at low temperatures (full black circles) and Nagaoka's prediction [37] for a dilute Kondo model (red solid line), described by eq. (2). Top inset: temperature dependence of the excess specific heat, ΔC , extracted from the linear fit of the C/T vs T^2 plot in Figure 3, as explained in the text. The linear dependence of ΔC is again consistent with Nagaosa's theory in the low-temperature limit (see text).

increase with decreasing temperature which levels off at ~ 2 K. This behavior is again consistent with Nagaoka's prediction [37] of domelike dependence of $\Delta C(T)$ for a dilute Kondo system. This dependence, which has no analytic form, is approximated by a linear dependence $\Delta C(T) = -K(T - T_K)$ for $T \sim T_K$, where K is a positive constant, and by $C(T) \sim T$ in the zero-temperature limit. In the present case, according to eq. (3), the linear behavior of Figure 5 yields an estimate of $T_K \approx 12$ K, somehow lower than the T_K estimated from the resistivity. The discrepancy is ascribed to an inaccurate determination of the electronic specific heat from the dominant lattice contribution or to the limitations of current nonperturbative theories of the Kondo effect [41, 42]. A further analysis of this point goes beyond the scope of the present paper.

We should compare the present upturns of the resistivity and of the specific heat at low temperature with similar features previously reported in d - [43, 44] and f -compounds [25]. These upturns have been the object of controversial interpretations and an alternative scenario of Schottky anomaly has been put forward for compounds like the Heusler alloy Fe_2VAl [44]. We verified this alternative scenario by analyzing the field-dependence of the excess specific heat, ΔC , determined as above. According to a Schottky multi-level model [45], the low-temperature dependence of ΔC is expected to exhibit a hump which shifts toward high temperatures with increasing field. This prediction differs markedly from the behavior of Figure 3. The model further predicts a hump for the field dependence of ΔC at constant temperature as well, for the magnetic contribution ΔC depends on the adimensional variable $x = \frac{g\mu_B H}{k_B T}$. Again, the behavior of Figure 6 differs qualitatively

from this prediction: at 2 K, the ΔC curve exhibits a linear decrease with field while, at this temperature and for a $S = 1/2$ ($S = 1$) impurity, a hump is predicted at $H = 3.5$ T (2.5 T). Thus, we can rule out the Schottky scenario in our case.

We finally propose an intuitive explanation of the Kondo scenario suggested here. This scenario would be unique for a d -system, as the Kondo effect requires either localized magnetic impurities or narrow-bands characteristic of f - rather than d -systems [44]. The peculiarity of the present d -system is the stacking of metallic VS_2 layers with $(\text{Cu},\text{V})\text{S}$ chains containing one magnetic V^{3+} ion every two nonmagnetic Cu^{1+} ions (see Figure 1). We argue that the $3d$ electrons of these ions are localized due to the reduced dimension of the chain, so the V^{3+} ions behave as diluted $S = 1$ magnetic impurities interacting with the metallic layers. This explanation is supported by a previous analysis of the magnetic susceptibility [16], which indicates that only the V^{3+} ions in the chain contribute to the Curie behavior. A further argument in favor of the proposed scenario is the evidence of Kondo lattice behavior reported recently in the parent compound V_5S_8 [46], which shares with the present compound a similar structure made of a stacking of VS_2 layers and of VS chains. The difference between the two structures is that, in the latter case, the chain sites are all occupied by magnetic V^{3+} ions, which may explain the Kondo lattice picture. In our case, these ions occupy only 1/3 of the available sites, which rather suggests a dilute Kondo impurity picture. Suitable probes, such as angular resolved photoemission spectroscopy on both compounds, may confirm experimentally the above scenario of onedimensional band associated with the $(\text{Cu},\text{V})\text{S}$ chains.

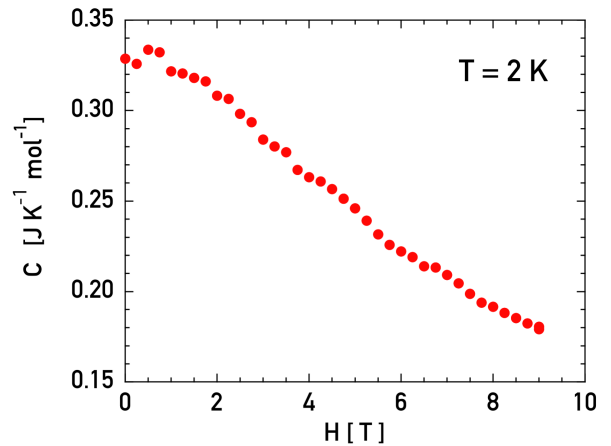


Figure 6. (Color online) Magnetic field dependence of the specific heat of $(\text{Cu}_{2/3}\text{V}_{1/3})\text{V}_2\text{S}_4$ at 2 K.

In conclusion, we have given experimental evidence of a FL to NFL crossover induced by a Kondo interaction

in the twodimensional system $(\text{Cu}_{2/3}\text{V}_{1/3})\text{V}_2\text{S}_4$ (CVS). To the best of our knowledge, this is a unique example of correlated electron system exhibiting the signatures of both heavy-fermions in a broad 30–70 K temperature range and of Kondo effect. We therefore think that CVS constitutes a playground for studying the above crossover in a regime of intermediate electronic correlations accessible to first-principles calculations. For instance, one interesting possibility may be that CVS and related compounds constitute a simple realization of the two-channel Kondo state [34, 47, 48]. Indeed, the coupling between adjacent layers is typically very weak in layered transition metal disulfides $M\text{S}_2$ owing to the van der Waals gap between them. Hence, it is plausible that, in CVS, each metallic VS_2 layer screens independently the impurity spin in the chain site, as schematically illustrated in Figure 1. The verification of this scenario awaits further studies at very low temperatures and as a function of the separation between adjacent layers.

The authors acknowledge stimulating discussions with M. Calandra, M. Casula, P. Coleman and M. Hellgren.

- [1] Wang H, Yuan H, Sae Hong S, Li Y and Cui Y 2015 *Chem. Soc. Rev.* **44**(9) 2664–2680
- [2] Wilson J, Salvo F D and Mahajan S 1975 *Advances in Physics* **24** 117–201
- [3] Morosan E, Zandbergen H W, Dennis B S, Bos J W G, Onose Y, Klimczuk T, Ramirez A P, Ong N P and Cava R J 2006 *Nature Physics* **2** 544 EP –
- [4] Mak K F, Lee C, Hone J, Shan J and Heinz T F 2010 *Phys. Rev. Lett.* **105**(13) 136805
- [5] Guo J, Jin S, Wang G, Wang S, Zhu K, Zhou T, He M and Chen X 2010 *Phys. Rev. B* **82**(18) 180520
- [6] Ge J F, Liu Z L, Liu C, Gao C L, Qian D, Xue Q K, Liu Y and Jia J F 2014 *Nature Materials* **14** 285 EP –
- [7] Calandra M and Mauri F 2011 *Phys. Rev. Lett.* **106**(19) 196406
- [8] Cercellier H, Monney C, Clerc F, Battaglia C, Despont L, Garnier M G, Beck H, Aebi P, Patthey L, Berger H and Forró L 2007 *Phys. Rev. Lett.* **99**(14) 146403
- [9] Thomson R E, Burk B, Zettl A and Clarke J 1994 *Phys. Rev. B* **49**(24) 16899–16916
- [10] Fazekas P and Tosatti E 1979 *Philosophical Magazine B* **39** 229–244
- [11] Perfetti L, Loukakos P A, Lisowski M, Bovensiepen U, Berger H, Biermann S, Cornaglia P S, Georges A and Wolf M 2006 *Phys. Rev. Lett.* **97**(6) 067402
- [12] Sipos B, Kusmartseva A F, Akrap A, Berger H, Forró L and Tutiš E 2008 *Nature Materials* **7** 960 EP –
- [13] Yi S, Zhang Z and Cho J H 2018 *Phys. Rev. B* **97**(4) 041413
- [14] Kondo J 1964 *Progress of Theoretical Physics* 0033-068X, 1347-4081 02860
- [15] Stewart G R 2001 *Reviews of Modern Physics* **73** 797–855 01041
- [16] Klein Y, Moutaabbid H, Soyer A, D’Astuto M, Rousse G, Vigneron J, Etcheberry A and Gauzzi A 2011 *Journal of Solid State Chemistry* 0022-4596
- [17] Kawada I, Nakano-Onoda M, Ishii M, Saeki M and Nakahira M 1975 *Journal of Solid State Chemistry* 0022-4596
- [18] Nozaki H, Ishizawa Y, Saeki M and Nakahira M 1975 *Physics Letters A* 0375-9601
- [19] Rice M J 1968 *Phys. Rev. Lett.* **20**(25) 1439–1441
- [20] Miyake K, Matsuura T and Varma C 1989 *Solid State Communications* 0038-1098
- [21] McWhan D B and Rice T M 1969 *Physical Review Letters* **22** 887–890
- [22] Tokura Y, Taguchi Y, Okada Y, Fujishima Y, Arima T, Kumagai K and Iye Y 1993 *Phys. Rev. Lett.* **70**(14) 2126–2129
- [23] Maeno Y, Yoshida K, Hashimoto H, Nishizaki S, Ikeda S i, Nohara M, Fujita T, Mackenzie A P, Hussey N E, Bednorz J G and Lichtenberg F 1997 *Journal of the Physical Society of Japan* 0031-9015
- [24] Kadowaki K and Woods S B 1986 *Solid State Communications* 0038-1098 00787
- [25] Stewart G R 1984 *Rev. Mod. Phys.* **56**(4) 755–787
- [26] Thompson A H 1975 *Physical Review Letters* **35** 1786–1789
- [27] Klipstein P C, Bagnall A G, Liang W Y, Marseglia E A and Friend R H 1981 *Journal of Physics C: Solid State Physics* **14** 4067
- [28] Amaricci A, de’ Medici L, Sordi G, Rozenberg M J and Capone M 2012 *Phys. Rev. B* **85**(23) 235110
- [29] Kondo S, Johnston D C, Swenson C A, Borsa F, Mahajan A V, Miller L L, Gu T, Goldman A I, Maple M B, Gajewski D A, Freeman E J, Dilley N R, Dickey R P, Merrin J, Kojima K, Luke G M, Uemura Y J, Chmaissem O and Jorgensen J D 1997 *Physical Review Letters* **78** 3729–3732
- [30] Lee P A, Rice T M, Serene J W, Sham L J and Wilkins J W 1986 *Comments on Condensed Matter Physics* **12** 99–161
- [31] Menth A and Remeika J P 1970 *Physical Review B* **2** 3756–3762
- [32] Johnston D C, Swenson C A and Kondo S 1999 *Physical Review B* **59** 2627–2641
- [33] Wilson K G 1975 *Rev. Mod. Phys.* **47**(4) 773–840
- [34] Nozières P and Blandin A 1980 *J. Phys. France* **41** 193–211
- [35] Ford P J, Whall T E and Loram J W 1970 *Phys. Rev. B* **2**(6) 1547–1553
- [36] Haen P, Souletie J and Teixeira J 1976 *Journal of Low Temperature Physics* 1573-7357
- [37] Nagaoka Y 1965 *Phys. Rev.* **138**(4A) A1112–A1120
- [38] Anderson P W 1970 *Journal of Physics C: Solid State Physics* **3** 2436
- [39] Nozières P 1974 *Journal of Low Temperature Physics* **17** 31–42
- [40] Rizzuto C 1974 *Reports on Progress in Physics* **37** 147
- [41] Andrei N, Furuya K and Lowenstein J H 1983 *Rev. Mod. Phys.* **55**(2) 331–402
- [42] Tsvetick A and Wiegmann P 1983 *Advances in Physics* **32** 453–713
- [43] Nishino Y, Kato M, Asano S, Soda K, Hayasaki M and Mizutani U 1997 *Phys. Rev. Lett.* **79**(10) 1909–1912
- [44] Lue C S, Ross J H, Chang C F and Yang H D 1999 *Phys. Rev. B* **60**(20) R13941–R13945
- [45] Falge R L and Wolcott N M 1971 *Journal of Low Temperature Physics* 1573-7357
- [46] Niu J and et al 2018 *arXiv:1809.04213*
- [47] Zawadowski A 1980 *Phys. Rev. Lett.* **45**(3) 211–214
- [48] Potok R M, Rau I G, Shtrikman H, Oreg Y and Goldhaber-Gordon D 2007 *Nature* **446** 167–171