

Elsevier Editorial System(tm) for Microchemical Journal
Manuscript Draft

Manuscript Number: MICROC-D-14-00298R1

Title: Chemical safety of children's play paints: focus on selected heavy metals

Article Type: Original Research Paper

Keywords: toys; children; artist paints; face paints; heavy metals

Corresponding Author: Dr. Edgar Pinto,

Corresponding Author's Institution:

First Author: Andreia Rebelo, MsD

Order of Authors: Andreia Rebelo, MsD; Edgar Pinto; Manuela V. Silva, MsD; Agostinho A. Almeida, PhD

Abstract: Children's play paints are widely used as didactic products in preschool activities. Besides direct skin contact, a great risk of oral exposure exists during its normal and foreseeable use. Due to the ubiquitous nature of most metals, their presence as impurities in all products is recognized as unavoidable. However, the toxic potential of most of them requires that their levels are kept as low as possible.

The present study aimed to assess the content of selected heavy metals (Pb, Cd, Cr, Co, Ni, Mn, Cu and Zn) in "artist paints" (n=54) and "face paints" (n=12) commonly used in preschool establishments and available at low cost stores. Determinations were carried out by GFAAS (for Pb, Cd, Co, Cr and Ni) and FAAS (for Mn, Cu and Zn).

The levels obtained [mean±SD (maximum)] were: 0.48±0.44 (1.98) µg g⁻¹ for Pb; 0.04±0.04 (0.30) µg g⁻¹ for Cd; 0.17±0.20 (1.47) µg g⁻¹ for Co; 1.36±2.18 (9.40) µg g⁻¹ for Cr; 0.63±0.56 (3.10) µg g⁻¹ for Ni; 19.8±88.2 (718) µg g⁻¹ for Mn; 108±260 (1458) µg g⁻¹ for Cu; 130±564 (3478) µg g⁻¹ for Zn.

A safety assessment considering the estimated potential exposure and health-based limits (tolerable daily intakes) was performed. Overall, the results showed no reasons for safety concerns regarding the studied elements.

Dear Editor,

I am submitting the article titled: "Chemical safety of children's play paints: focus on selected heavy metals" for publication in Microchemical Journal.

The corresponding author of this article is Edgar Pinto. The address is Rua Valente Perfeito, 322, 4400-330, Vila Nova de Gaia, Portugal, Portugal; Tel: +351 222 061 000; Fax: +351 222 061 001; Email: ecp@estsp.ipp.pt.

Looking forward that it is accepted for publication.

Best regards

Edgar Pinto

Response to reviewers' comments

Reviewers' main comment: *The paper presents a study about the levels of metals in different types of toys, and their possible toxic effects on children. The aim of the paper is interesting but my principal objection is that the number of samples studied are very short in order to obtain a general conclusion. About the analytical method there is not nothing new, the only new is the samples analyzed, then it is necessary a bigger samples number before the acceptance of the paper.*

- The authors agree with reviewers about the number of samples analyzed. We add 35 more samples, now reaching a total of 66 paints analyzed regarding their metal content. It is fully representative of the Portuguese market. A new type of paint was also included (fingerpaint) in order to give more relevance and comprehensiveness to the study.

1 - More information about the quality control of the results must be enclosed, for example, what type of Certified Reference Material was used to check the accuracy of the methods?

- (Lines 133-138) A new section was introduced "2.3 Quality Control" and the results from the analysis of the certified reference material ISE918 (sandy soil) are presented in a new table (Table 1).

2 - What about the blank values?

- (Lines 145-147) A new sentence was included to address the question of blank values: "In each batch of microwave-assisted acid digestion (i.e., 10 vessels) one sample blank was included. In total, 23 sample blanks were performed. The obtained mean values were subtracted from the sample values."

3 - Had you problems about matrix effects?

- (Lines 139-144) A new sentence was included to clarify how the evaluation of matrix effects was carried out: "The effect of the sample matrix on the accuracy of the analytical determinations was assessed through a matrix-matched calibration

approach. Standard solutions were added to the matrix (i.e., paint), calibration curves were built and slopes were compared with those obtained for simple aqueous standard solutions. No significant differences ($p > 0.05$) were observed between the obtained slopes. Thus, the analytical procedures were considered free from matrix effects.”

4 - Why the number of samples is low?, authors say in the conclusion section, lines 348-352, that it is not possible to obtain a general conclusion because the number of samples is low and then that more work is necessary. Can you explain then why did not include more samples?

- (Lines 362-375) The samples analyzed were representative of the main products and brands found in the Portuguese market and preschool establishments. However, as abovementioned, more samples were analyzed. The conclusion section was rewrite to demonstrate the main achievements of the present study: “The data obtained in this study provide useful information about the content of selected heavy metals in children paints and related potential risk of exposure to these elements. In general, the content of heavy metals in the studied samples were well below the migrations limits set by the TSD and levels (for Pb and Cd) considered as technically achievable for cosmetics using good manufacturing practices. However, given the fact that the content of heavy metals in finished products strongly depends on the quality of raw-materials and manufacturing process, it is difficult to extrapolate to other contexts (other lots, other brands, other countries/markets). Therefore, further studies and periodic monitoring are needed for a full safety characterization of this kind of products. The differences in metal content between the different categories of paints are related with manufacturing processes and their specific composition. However, it was not possible to associate the higher metal levels with specific ingredients, particularly pigments, since these products do not have label information about its composition.”

Highlights

- Heavy metals can be present in children's play paints due to their ubiquitous and persistent nature.
- Eight heavy metals (Pb, Cd, Cr, Co, Ni, Mn, Cu and Zn) were determined in several products types, colors, brands and country of manufacture.
- Overall, the results showed no reasons for safety concerns regarding the studied elements
- Heavy metals in finished products strongly depends on the quality of raw-materials and manufacturing process
- A close monitoring is needed for a full safety characterization of this kind of products

18 **Abstract**

19 Children's play paints are widely used as didactic products in preschool activities.
20 Besides direct skin contact, a great risk of oral exposure exists during its normal and
21 foreseeable use. Due to the ubiquitous nature of most metals, their presence as
22 impurities in all products is recognized as unavoidable. However, the toxic potential of
23 most of them requires that their levels are kept as low as possible.

24 The present study aimed to assess the content of selected heavy metals (Pb, Cd, Cr, Co,
25 Ni, Mn, Cu and Zn) in "artist paints" (n=54) and "face paints" (n=12) commonly used
26 in preschool establishments and available at low cost stores. Determinations were
27 carried out by GFAAS (for Pb, Cd, Co, Cr and Ni) and FAAS (for Mn, Cu and Zn).

28 The levels obtained [mean±SD (maximum)] were: 0.48±0.44 (1.98) $\mu\text{g g}^{-1}$ for Pb;
29 0.04±0.04 (0.30) $\mu\text{g g}^{-1}$ for Cd; 0.17±0.20 (1.47) $\mu\text{g g}^{-1}$ for Co; 1.36±2.18 (9.40) $\mu\text{g g}^{-1}$
30 for Cr; 0.63±0.56 (3.10) $\mu\text{g g}^{-1}$ for Ni; 19.8±88.2 (718) $\mu\text{g g}^{-1}$ for Mn; 108±260 (1458)
31 $\mu\text{g g}^{-1}$ for Cu; 130±564 (3478) $\mu\text{g g}^{-1}$ for Zn.

32 A safety assessment considering the estimated potential exposure and health-based
33 limits (tolerable daily intakes) was performed. Overall, the results showed no reasons
34 for safety concerns regarding the studied elements.

35

36 **Keywords:** toys, children, artist paints, face paints, heavy metals

37

38 **1. Introduction**

39 In early childhood education, activities such as drawing and painting help children to
40 develop self-expression skills, and significantly contribute to their physical and
41 psychological development [1]. According to Arda [2], painting is a stronger form of
42 expression than words in early years, which makes play paints an attractive tool for
43 preschool activities. These paints can be divided into two main groups: “artist paints”
44 (e.g., gouaches, watercolors, acrylic paints) and the “face paints”.

45 Given its purpose, *artist paints* fall within the concept of toy («a product designed or
46 intended, whether or not exclusively, for use in play by children under 14 years of age») and their safety in the European Union is regulated under the Directive 2009/48/EC on
47 the safety of toys (hereinafter the “Toy Safety Directive” will be designated as TSD)
48 [3]. This category of toys is susceptible of easy ingestion in significant quantities and
49 they should comply with maximum acceptable levels for the migration of toxic
50 elements [4]. Metals may be released from toys by different mechanisms such as the
51 action of saliva during mouthing, sweat during dermal contact or gastric fluid after
52 ingestion [5]. Therefore, high amounts of metals may become bioavailable, reach the
53 systemic circulation and exert their toxicological effects on target organs. Severity of
54 the exposure depends on the content, physiological parameters, behavioral patterns and
55 bioavailability of the metal [5]. The TSD lays down migration limits for 18 different
56 elements, including the heavy metals Pb, Cd, Co, Cr, Ni, Mn, Cu and Zn.

58 As regards to *face paints*, they have to be considered as cosmetic products [«any
59 substance or mixture intended to be placed in contact with the external parts of the
60 human body (...) with a view exclusively or mainly to (...) changing their
61 appearance...»], according to the EU Regulation (EC) no. 1223/2009 on cosmetics
62 products (hereinafter “Cosmetics Regulation”) [6]. The Cosmetics Regulation states that

63 “products should be safe under normal or reasonable foreseeable conditions of use. In
64 particular, a risk-benefit reasoning should not justify a risk to human health” [6].
65 Children’s face paints are directly applied to skin, and mainly produce local exposure to
66 ingredients. However, the use of these products by children is of particular concern
67 mainly because of the potential for exposure through ingestion [7].
68 The dermal contact with chemical substances, natural or synthetic, will always involve
69 some risk of irritation and sensitization (particularly allergic contact dermatitis) [8-10].
70 Although topical exposure usually does not result in significant penetration through the
71 skin, the human systemic exposure can rarely be completely excluded [8]. The risk of
72 percutaneous absorption is variable depending on the site of application of the product
73 (e.g., products applied directly to mucous membranes pose a greater risk). When
74 children play with paints, skin contact and potential absorption through the skin is
75 almost unavoidable.
76 Due to their ubiquitous and persistent nature, the presence of metals as impurities in all
77 products is recognized as unavoidable (trace amounts arising from both the ingredients
78 and manufacturing practices) [11]. However, for safety reasons, their levels should be
79 kept at the lowest levels that are technically feasible or are of no toxicological concern.
80 Based on this background, the aim of our work was to determine the content of Pb, Cd,
81 Cr (total), Co, Ni, Mn, Cu and Zn in artist paints and face paints used by children in
82 preschool establishments and widely available in low cost stores. Results were
83 compared with legal limits and values obtained in similar studies. It was also evaluated
84 whether there were significant differences between metals content in the different types
85 of products (gouaches, acrylics, watercolors, fingerpaints and face paints). In order to
86 assess the safety of the products, the potential metal intake was evaluated and compared
87 with tolerable daily intakes.

88 **2. Material and methods**

89 **2.1. Sample collection**

90 Using a convenience sampling procedure, samples of artist paints (n=54) and face paints
91 (n=12) were collected in 8 preschool establishments (20 products) and purchased in 7
92 low cost stores (46 products) from Porto (Portugal). All the selected paints were
93 specifically designed for children use, representing 17 popular brands. The paints
94 collected in preschool establishments were mainly used by children aged between 3 and
95 6 years old. The general information about the samples (brand, type, color and country
96 of manufacture) and the local of acquisition (school or store) is provided in Table 2. An
97 identification code consisting of a combination of a letter and a number was assigned to
98 each sample. For the artist paints the letters indicate the type of product: G-gouache; A-
99 acrylic; W-watercolor; FP-fingerpaint. Face paints are indicated by the letter “F”. The
100 brand is also indicated by a code consisting of a combination of a letter (“B”, for brand)
101 and a number. A different number was attributed to each sampling site too.

102

103 **2.2. Sample analysis**

104 The samples were solubilized by closed-vessel microwave-assisted acid digestion in a
105 MLS-1200 Mega (Soriso, Italy) microwave oven equipped with an HPR-1000/10 S
106 rotor. A sample mass between 0.3-0.5 g was directly weighted into the microwave oven
107 polytetrafluorethylene (PTFE) vessels and 4 mL of high-purity concentrated nitric acid
108 (HNO₃) (65% w/w, *TraceSELECT*[®] Ultra, from Fluka, L’Isle d’Abeau Chesnes, France)
109 plus 1 mL of high-purity hydrogen peroxide (H₂O₂) (30% v/v, *TraceSELECT*[®], from
110 Fluka, Seelze, Germany) was added. Then, the sample digestion was performed using
111 the following microwave oven program (power [W]/time [min]): 250/2, 0/2, 600/5,
112 500/5, 400/5. After cooling, sample solutions were transferred into a 50 mL

113 decontaminated polypropylene volumetric flask and the volume was adjusted with ultra-
114 pure water ($> 18.2 \text{ M}\Omega\cdot\text{cm}$ at $25 \text{ }^\circ\text{C}$) obtained from a Milli-Q (Millipore, Billerica, MA)
115 RG water purification system. Sample blanks were obtained using the same procedure.
116 The obtained solutions (blanks and digested samples) were stored in tightly closed
117 decontaminated polypropylene tubes in the refrigerator at $4 \text{ }^\circ\text{C}$ until analysis.
118 Each sample was analyzed in triplicate. The metals determinations were carried out
119 using graphite furnace atomic absorption spectrometry (GFAAS) for Pb, Cd, Co, Cr and
120 Ni, and flame-atomic absorption spectrometry (FAAS) for Mn, Cu and Zn.
121 For GFAAS determinations, a Perkin Elmer (Überlingen, Germany) model 4100 ZL
122 instrument (longitudinal Zeeman-effect background correction), equipped with a
123 transverse heated graphite atomizer (THGA) and an AS-70 auto-sampler was used. For
124 FAAS determinations, a Perkin Elmer model 3100 instrument (air/acetylene flame) was
125 used. Calibration standards were prepared by adequate dilution with HNO_3 0.2% (v/v)
126 of a multi-element (Pb, Cd, Co, Cr, Ni, Mn, Cu and Zn) standard stock solution. This
127 was prepared from single-element 1000 mg L^{-1} commercial standard solutions (Sigma,
128 St. Louis, MO). The limits of detection (LoD) were calculated as the concentration
129 corresponding to 3 times the standard deviation of a series of 10 replicate measurements
130 of the calibration blank (HNO_3 0.2% v/v).

131

132 ***2.3 Quality Control***

133 Since paints are not available as a certified reference material (CRM) for metal analysis,
134 a sandy soil (ISE 918) supplied by WEPAL (Wageningen, The Netherlands) was used
135 for analytical quality control purposes. The CRM was subjected to the same sample
136 pretreatment as the studied paints. The values obtained proved the adequacy of the
137 analytical procedure (Table 1).

138 The effect of the sample matrix on the accuracy of the analytical determinations was
139 assessed through a matrix-matched calibration approach. Standard solutions were added
140 to the matrix (i.e., paint), calibration curves were built and slopes were compared with
141 those obtained for simple aqueous standard solutions. No significant differences ($p >$
142 0.05) were observed between the obtained slopes. Thus, the analytical procedures were
143 considered free from matrix effects.

144 In each batch of microwave-assisted acid digestion (i.e., 10 vessels) one sample blank
145 was included. In total, 23 sample blanks were performed. The obtained mean values
146 were subtracted from the sample values.

147

148 ***2.4. Data analysis***

149 Statistical analysis was performed using IBM (New York, NY) SPSS Statistics 20
150 software. For the statistics calculation, results that fall below the LoD were assumed as
151 the LoD divided by the square root of 2, a commonly used procedure for data
152 imputation [12]. Descriptive statistics was used to summarize the results for artist paints
153 and face paints separately. Student's t-test was performed to evaluate the matrix effects.
154 The difference in metal content between the different types of paints was tested with the
155 non-parametric Kruskal-Wallis test followed by a multi comparison analysis using the
156 Dunnet's T3 test. Statistical significance was considered for $p < 0.05$.

157

158 ***2.5. Safety assessment***

159 Measured metals content was used to assess the safety of the products using the
160 methodology for assessment of chemical safety of toys, option 2 (use of product
161 composition data), as proposed by the National Institute for Public Health and the
162 Environment (RIVM) [13]. The exposure scenario considered was the direct ingestion,

163 mostly associated to hand-to-mouth (HTM) contact. Hand-to-mouth contact is a child
164 specific behavior that can lead to a relevant exposure [14], especially in children under
165 3 years of age. This methodology is based on the calculation of the amount of element
166 released from the estimated amount of product ingested, i.e., the estimated daily intake
167 (EDI) divided by the mean body weight of the children. This value should be lower than
168 a defined fraction (usually 5, 10 or 20%) of the tolerable daily intake (TDI, in mg kg^{-1}
169 bw day^{-1}) for the element of interest [13]. This is a two-step calculation that involves:

170

171 1) Calculation of the EDI, as follows:

$$EDI (\mu\text{g}/\text{kg bw}/\text{day}) = \frac{\text{element content in product } (\mu\text{g}/\text{g}) \times \text{weight of product ingested } (\text{g}/\text{day})}{\text{body weight } (\text{kg})}$$

172

173 For this purpose, it was assumed that the maximum daily intake of artist paints and face
174 paints (i.e., the maximum amount of product that can be ingested by children) is 400 mg
175 day^{-1} and 210 mg day^{-1} , respectively, as proposed by RIVM [13,14], and the total
176 amount of the element in the product is released at once and becomes readily available
177 for gastrointestinal absorption (i.e., bioaccessibility is 100%). The children body weight
178 was set at 12 kg, as proposed by EFSA (a default value for children under 3 years old)
179 [15].

180

181 2) Calculation of the relative intake indices (RII), as follows:

$$RII (\%) = \frac{EDI}{TDI} \times 100$$

182

183 **3. Results and discussion**

184 A total of 66 samples were analyzed, 54 artist paints and 12 face paints, representing 17
185 different brands (see Table 2). All the products had a package label providing

186 information about the product and country of manufacture. China was the predominant
187 country of origin (42.4%), followed by Italy (28.8%), France (15.2%), UK (10.6%) and
188 Spain (3.0%). The samples purchased in low cost stores were mostly from China
189 (58.7%). Watercolors were the most available artist paint, representing the highest
190 percentage of the samples analyzed (34.8%), followed by gouaches (30.3%), face paints
191 (18.2%), fingerpaints (9.1%) and acrylics (7.6%). The colors most analyzed were
192 yellow (16.7%), red (15.2%), and white and green (13.6% each).

193 The results of metal content in the studied products are summarized in Table 3.
194 Considering that artist paints and face paints are covered by different regulations (toys
195 and cosmetics, respectively), data analysis was performed separately. It must be noted
196 that the total element content was determined by performing a complete solubilization
197 (microwave-assisted acid digestion) of the samples, a different extraction procedure
198 from that described in the standard for the determination of migration limits, which
199 simply simulates the material contact with the stomach acid for a defined period of time
200 after swallowing. Results obtained therefore represent what may be considered as the
201 worst case scenario regarding the exposure to the elements.

202

203 ***3.1. Metal content in artist paints***

204 The average content of Pb in artist paints (gouaches, acrylics, watercolors and
205 fingerpaints) was $0.52 \pm 0.48 \mu\text{g g}^{-1}$. Gouaches presented the highest content of Pb
206 ($0.65 \pm 0.48 \mu\text{g g}^{-1}$) while fingerpaints presented the lowest (all results were below the
207 LOD), a significant statistical difference. The migration limit for Pb set by the TSD
208 ($3.4 \mu\text{g g}^{-1}$) was not exceeded in any of the samples analyzed, even assuming that the
209 total Pb content is susceptible to be released. Germany continues to apply,
210 provisionally, its own national limits for certain heavy metals in toys, including Pb,

211 which are stricter than the EU standards, defining a maximum daily bioavailability of
212 0.7 μg for Pb [16]. As regards the requirements in countries outside de EU, the
213 Canadian Hazardous Products Act limits to 90 $\mu\text{g g}^{-1}$ the total content of Pb in surface
214 coating materials of toys for children younger than 3 years old [17]. Similarly, in the
215 USA, the Consumer Product Safety Improvement Act (CPSIA) of 2008 also sets the
216 concentration of Pb in paint to a limit of 90 $\mu\text{g g}^{-1}$ [18].

217 Cadmium presented the lowest average content among the studied metals: $0.04\pm 0.05 \mu\text{g g}^{-1}$
218 g^{-1} . The highest levels were found in gouaches ($0.05\pm 0.07 \mu\text{g g}^{-1}$) and the lowest in
219 fingerpaints ($0.02\pm 0.01 \mu\text{g g}^{-1}$). None of the samples exceeded the migration limit
220 imposed by the TSD ($0.5 \mu\text{g g}^{-1}$).

221 For the transitions metals Cr, Co and Ni, the average content in artist paints was
222 $1.36\pm 2.64 \mu\text{g g}^{-1}$, $0.17\pm 0.22 \mu\text{g g}^{-1}$ and $0.69\pm 0.55 \mu\text{g g}^{-1}$, respectively. The highest Cr
223 levels were found in watercolors ($2.43\pm 3.28 \mu\text{g g}^{-1}$), which were significantly higher
224 than the levels in fingerpaints. Five of the samples presenting the highest values (W₂₈,
225 W₂₉, W₃₀, W₃₁ and W₃₂) were purchased in low cost stores, with maximum Cr content
226 reaching $9.4 \mu\text{g g}^{-1}$. The TSD sets different migration limits to Cr(III) and Cr(VI): 9.4
227 $\mu\text{g g}^{-1}$ and $0.005 \mu\text{g g}^{-1}$, respectively. Therefore, no definite conclusion can be drawn,
228 because our value corresponds to the total Cr content. For Co and Ni, none of the artist
229 paints has exceeded the migration limits set by the TSD: $2.6 \mu\text{g g}^{-1}$ for Co and $18.8 \mu\text{g g}^{-1}$
230 g^{-1} for Ni.

231 As regards Mn, the mean content was $9.65\pm 14.38 \mu\text{g g}^{-1}$. Gouaches presented a
232 significantly higher content ($20.5\pm 19.4 \mu\text{g g}^{-1}$) than other artist paints. However, none
233 of the samples reached the TSD migration limit of $300 \mu\text{g g}^{-1}$.

234 Copper was present at very different levels, with 12 samples (G₁, G₁₃, G₁₅, G₁₇, G₂₀,
235 A₂₁, W₃₁, W₃₂, W₃₆, W₄₂, FP₅₀ and FP₅₄) exceeding the TSD migration limit ($156 \mu\text{g g}^{-1}$

236 ¹). The same was observed for Zn, with two samples (A₂₃ and A₂₅) also exceeding the
237 migration limit (938 µg g⁻¹). The average content of these elements in artist paints was
238 131±283 µg g⁻¹ for Cu and 156±621 µg g⁻¹ for Zn. However, it is worth mentioning
239 again that these values correspond to the total content in the product and not the actual
240 content susceptible to migration.

241

242 ***3.2. Metal content in face paints***

243 The average content of Pb in face paints (0.29±0.17 µg g⁻¹) was quite similar to the
244 results obtained in the CSC study [19] on children's face paints of the USA market,
245 with Pb levels ranging from 0.054 µg g⁻¹ to 0.65 µg g⁻¹. Several studies had also
246 determined the Pb content in other cosmetic products, mainly in eye shadows and lip
247 products [20-23]. In a large survey of the US market (n=400 lipsticks), a mean Pb
248 content of 1.11 µg g⁻¹ (maximum 7.19 µg g⁻¹) was found [21]. Recently, the European
249 Commission's Joint Research Centre conducted a survey of the Pb content in lip
250 products of the European market (products purchased 15 different EU countries), and a
251 mean Pb content of 0.75±0.64 µg g⁻¹ was found (maximum 3.75 µg g⁻¹) [23].

252 According to the Cosmetics Regulation, Pb and its compounds are substances
253 prohibited in cosmetic products. Nevertheless, trace amounts of this and other heavy
254 metals are unavoidably found as impurities in all the products due to the persistent
255 nature of these elements and the fact that they are found in the natural environment [24].

256 There are currently no international standards for impurities in cosmetics. The German
257 authorities conducted studies to determine the background levels of heavy metal in
258 cosmetic products, including toothpaste. Based on these studies, it was set that levels of
259 Pb in cosmetic products above 20 µg g⁻¹ were technically avoidable [25]. For
260 toothpastes the maximum concentration was set at 1 µg g⁻¹. Health Canada, the federal

261 department responsible for public health, considers that Pb levels in cosmetic products
262 lower than $10 \mu\text{g g}^{-1}$ is technically feasible. Although these limits were based on levels
263 that can be technically avoided and not in a risk-based approach [26], it is considered
264 that they provide a high level of protection to susceptible subpopulations of consumers
265 (namely children) when weighted against established tolerable intakes for this metal
266 [24]. In our study, none of the samples exceeded this “limit” ($10 \mu\text{g g}^{-1}$).

267 Cadmium and its compounds are also forbidden in cosmetic products in EU [6]. The
268 average content of Cd was $0.02 \pm 0.02 \mu\text{g g}^{-1}$, well below the limits set by Health Canada
269 ($3 \mu\text{g g}^{-1}$) and German authorities ($5 \mu\text{g g}^{-1}$) for this element in cosmetics. Similar
270 results have been obtained in others studies regarding Cd in eye shadows and lip
271 products [20,22].

272 For the transitions metals Co and Ni, the content in face paints was typically lower than
273 $1 \mu\text{g g}^{-1}$, a recommended limit value in consumer products for very sensitive individuals
274 [27]. Chromium exceeded this value in 6 samples. Copper content was below the LoD
275 in all the analyzed face paints. As regards Mn and Zn, the average content was
276 $65.6 \pm 205.5 \mu\text{g g}^{-1}$ and $15.4 \pm 42.5 \mu\text{g g}^{-1}$, respectively. The maximum Mn content was
277 found in the sample F₆₆ ($717 \mu\text{g g}^{-1}$) while the maximum Zn content was found in the
278 same sample F₅₈ ($149 \mu\text{g g}^{-1}$). Several Zn compounds are allowed in cosmetic products,
279 mainly as white coloring agents, and others are allowed with some restrictions laid
280 down in Cosmetic Regulation [e.g., $\text{Zn}(\text{C}_2\text{H}_3\text{O}_2)_2$ and ZnCl_2 are water-soluble zinc salts
281 allowed in cosmetic products but restricted to a maximum concentration of 1% in ready
282 for use preparations].

283

284 **3.3. Safety assessment**

285 The metal content determined in the studied samples (Table 3) was used for a safety
286 assessment of the products. We used the methodology proposed by RIVM, option 2,
287 which involves the use of product composition data [13] (for details, see Material and
288 Methods section). The estimated daily intake was calculated assuming 400 mg day^{-1}
289 (210 mg day^{-1} for face paints) as the amount of product ingested by the children. Data
290 from RIVM [13] were used as tolerable daily intake (Table 4). A relative intake index
291 (RII) for each element was calculated. This represents the fraction of the tolerable daily
292 intake corresponding to the amount of metal ingested from the exposure to the products.
293 Results are summarized in Table 5.

294 Lead and Cadmium – Pb and Cd are two highly toxic metals. The main route of Pb
295 exposure is through the gastrointestinal tract. Children are particularly susceptible, since
296 they absorb a higher amount of Pb than adults (up to 50% of ingested amount *versus*
297 10% in adults) [28]. Lead can also enter the body through dermal absorption, although
298 this is less significant [28]. However, the cutaneous absorption of Pb may be increased
299 when the skin is damaged (by scratches and wounds, for example). Under conditions of
300 continued exposure, not all the Pb entering the body will be eliminated, and this results
301 in accumulation in body tissues, especially in the bone [28]. The exposure to low levels
302 of Pb in children is common and is particularly insidious because of the lack of
303 diagnostically definitive physical signs [29]. Even at very low blood levels ($5 \mu\text{g dL}^{-1}$
304 and even lower), Pb can result in neurotoxic effects and lasting effects on
305 neurobehavioral functioning in children [29,30].

306 Cadmium accumulates in the human body, especially in the kidneys [31]. However,
307 there is still limited data on the renal toxicity of Cd in children [32]. Since this is a
308 cumulative element (Cd has a very long biological half-time), children exposure, even at
309 very low levels, may have long-term adverse consequences [32], particularly in the

310 nervous system, such as learning disabilities and hyperactivity [20]. Data from Table 5
311 shows that exposure to Pb and Cd resulting from the exposure to the studied products is
312 very low (RII: $0.42 \pm 0.42\%$ and $0.23 \pm 0.30\%$, respectively), with a RII lower than 2% in
313 the worst case.

314 Nickel, chromium and cobalt – These transition metals are among the most common
315 contact sensitizing chemicals (Table 4). Some authors have proposed that consumer
316 products must contain less than $5 \mu\text{g g}^{-1}$ of Ni, Cr and Co, or preferably less than $1 \mu\text{g g}^{-1}$,
317 in order to minimize the risk for very sensitive individuals [27]. Table 6 shows the
318 number of samples containing Cr, Co and Ni above $5 \mu\text{g g}^{-1}$, between $1 \mu\text{g g}^{-1}$ and $5 \mu\text{g g}^{-1}$
319 and below $1 \mu\text{g g}^{-1}$. The threshold of $1 \mu\text{g g}^{-1}$ was only exceeded for Ni, Cr and Co in
320 9, 16 and 1 samples, respectively. The threshold of $5 \mu\text{g g}^{-1}$ was only exceeded in 5
321 watercolor samples, which showed Cr contents between 7.4 and $9.4 \mu\text{g g}^{-1}$. Samples
322 purchased in low cost stores showed the worst results.

323 Nickel and its water soluble salts are of particular concern. Following sensitization,
324 dermal exposure to even small amounts of Ni can cause outbreaks of dermatitis [33].
325 According to ATSDR, approximately 10-20% of the population is sensitive to Ni,
326 developing dermal problems, even when exposed to low concentrations, either by
327 ingestion or skin contact [34]. A Ni mass loading of $0.5 \mu\text{g}$ per cm^2 of skin area has
328 been suggested as a no-effect level for sensitization, based on a wide range of studies
329 [35]. According to RIVM [36], an exposure of about 3 mg/cm^2 of skin surface may be
330 assumed as typical for face paint use. Thus, even in the *worst scenario* (i.e., for the
331 maximum Ni level found: $3.10 \mu\text{g g}^{-1}$), the exposure to Ni would represent only about
332 $0.0093 \mu\text{g/cm}^2$, approximately 50 fold lower than the no-effect level of $0.5 \mu\text{g/cm}^2$,
333 suggesting that an important margin of safety exists.

334 The chemical and toxicological properties of Cr are very different depending on the
335 valence state of the element, Cr(VI) presenting a much higher toxicity than Cr(III),
336 which is even an essential trace element [37]. As abovementioned, some people are very
337 sensitive to dermal exposure Cr. In this study, no speciation analysis was carried out.
338 However, even assuming that all the Cr present in the samples was Cr(VI), and taking
339 into account only the non-carcinogenic effects by Cr(VI), very low RII ($0.83 \pm 1.43\%$;
340 maximum 6.27%) were obtained. For Co and Ni, RII were $0.37 \pm 0.49\%$ (maximum
341 3.50%) and $0.20 \pm 0.18\%$ (maximum 1.03%).

342 Manganese, copper and zinc – In adequate amounts, Mn is an essential nutrient for
343 humans, however, in excessive concentrations it becomes a very toxic element [38,39].
344 Some authors have associated the exposure to high levels of Mn with hyperactivity and
345 a decrease of development and intellectual function in children [38,40], like the ability
346 of learn and remember [41]. *In vitro* studies suggest that Cu is poorly absorbed through
347 intact skin [42], though some Cu compounds appear to be better absorbed than others.
348 In addition, a very small percentage of infants and children are unusually sensitive to Cu
349 [42]. Zn plays an important role in the growth and development of children. However,
350 in excessive amounts it can also adversely affect human health. The ingestion of large
351 doses of Zn (10-15 times higher than the Recommended Dietary Allowance – RDA),
352 even for a short period, can cause stomach cramps, nausea and vomiting [43].
353 Furthermore, studies in animals indicate that low levels of certain Zn compounds (e.g.,
354 $Zn(C_2H_3O_2)_2$ and $ZnCl_2$) can cause skin irritation [43].

355 The results obtained show that for most samples the exposure to Mn, Cu and Zn is low
356 (Table 5), with a RII $0.29 \pm 0.98\%$ (max 7.85%) for Mn, and lower than 5% in 53/66
357 samples for Cu and 64/66 for Zn. The main exception was one acrylic paint (A₂₁)

358 purchased in a low cost store, for which the estimated Cu intake was more than half the
359 TDI (RII = 58.6%).

360

361 **4. Conclusions**

362 The data obtained in this study provide useful information about the content of selected
363 heavy metals in children paints and related potential risk of exposure to these elements.

364 In general, the content of heavy metals in the studied samples were well below the
365 migrations limits set by the TSD and levels (for Pb and Cd) considered as technically
366 achievable for cosmetics using good manufacturing practices. However, given the fact
367 that the content of heavy metals in finished products strongly depends on the quality of
368 raw-materials and manufacturing process, it is difficult to extrapolate to other contexts
369 (other lots, other brands, other countries/markets). Therefore, further studies and
370 periodic monitoring are needed for a full safety characterization of this kind of products.

371 The differences in metal content between the different categories of paints are related
372 with manufacturing processes and their specific composition. However, it was not
373 possible to associate the higher metal levels with specific ingredients, particularly
374 pigments, since these products do not have label information about its composition.

375

376 **Figure Caption**

377 **Fig. 1.** Box and whiskers plot showing the distributions of the metals content.

378 Corresponding numeric data are provided in Table 3 for all samples ($n = 66$). Boxes

379 extend from the 25th to the 75th percentile, horizontal bars inside the boxes represent

380 the median, whiskers extend to maximum and minimum observations within 2 times the

381 length of the interquartile range above and below the 75th and 25th percentiles,

382 respectively, and outliers are represented as rhombus.

383

384 **References**

- 385 [1] V. Oğuz, The factors influencing childrens' drawings, *Procedia Soc. Behav. Sci.* 2
386 (2010) 3003 – 3007.
- 387 [2] Z. Arda, Art instruction in pre-school education, *Procedia Soc. Behav. Sci.* 1 (2009)
388 150-153.
- 389 [3] Directive 2009/48/EC of the European Parliament and of the Council of 18 June
390 2009 on the safety of toys, *Off. J. Eur. Commun. L* 170 (30.06.2009) 1-37,
391 Available from: [http://eur-](http://eur-lex.europa.eu/LexUriServ/LexUriServ.do?uri=OJ:L:2009:170:0001:0037:en:PDF)
392 [lex.europa.eu/LexUriServ/LexUriServ.do?uri=OJ:L:2009:170:0001:0037:en:PDF](http://eur-lex.europa.eu/LexUriServ/LexUriServ.do?uri=OJ:L:2009:170:0001:0037:en:PDF)
- 393 [4] ISO 8124-3:2010(E), Safety of Toys – Part 3: Migration of Certain ingredients.
394 Available from: http://www.iso.org/iso/catalogue_detail?csnumber=43471
- 395 [5] M. Guney & G.J. Zagury, Heavy Metals in Toys and Low-Cost Jewelry: Critical
396 Review of U.S. and Canadian Legislations and Recommendations for Testing.
397 *Environ. Sci. Technol.* 46 (2012) 4265-4274.
- 398 [6] Regulation (EC) no. 1223/2009 of the European Parliament and of the Council of 30
399 November 2009 on cosmetic products, *Off. J. Eur. Commun. L* 342 (22.12.2009),
400 Available from: [http://eur-](http://eur-lex.europa.eu/LexUriServ/LexUriServ.do?uri=CONSLEG:2009R1223:20130711:en:PDF)
401 [lex.europa.eu/LexUriServ/LexUriServ.do?uri=CONSLEG:2009R1223:20130711:e](http://eur-lex.europa.eu/LexUriServ/LexUriServ.do?uri=CONSLEG:2009R1223:20130711:en:PDF)
402 [n:PDF](http://eur-lex.europa.eu/LexUriServ/LexUriServ.do?uri=CONSLEG:2009R1223:20130711:en:PDF)
- 403 [7] I. Baer, J. van de Kreeke, T.P.J. Linsinger, P. Robouch, F.C. Raposo, B. de la Calle,
404 IMEP-24 analysis of eight trace elements in toys, *Trends Analyt. Chem.* 30 (2011)
405 313-323.
- 406 [8] G.J. Nohynek, E. Antignac, T. Re, H. Toutain, Safety assessment of personal care
407 products/cosmetics and their ingredients, *Toxicol. Appl. Pharmacol.* 243 (2010)
408 239-259.

- 409 [9] R.F. Davies, G.A. Johnston, New and emerging cosmetic allergens, Clin. Dermatol.
410 29 (2011) 311-315.
- 411 [10] C. Laguna, J. de la Cuadra, B. Martín-González, V. Zaragoza, L. Martínez-
412 Casimiro, V. Alegre, Allergic Contact Dermatitis to Cosmetics, Actas
413 Dermosifiliogr 100 (2009) 53-60.
- 414 [11] I. Al-Saleh, S. Al-Enazi, N. Shinwari, Assessment of lead in cosmetic products,
415 Regul. Toxicol. Pharmacol. 54 (2009) 105-113.
- 416 [12] P.A. Succop, S. Clark, M. Chen & W. Galke, Imputation of Data Values That are
417 Less Than a Detection Limit, J. Occup. Environ. Hyg. 1 (2004) 436-441.
- 418 [13] J.G.M. Van Engelen, M.V.D.Z. Park, P.J.C.M. Janssen, A.G. Oomen, E.F.A.
419 Brandon, K. Bouma, A.J.A.M. Sips, M.T.M. Van Raaij, Chemicals in Toys: A
420 general methodology for assessment of chemical safety of toys with a focus on
421 elements, National Institute for Public Health and the Environment (the
422 Netherlands) report 320003001 (2008).
- 423 [14] W. ter Burg, H.J. Bremmer, J.G.M. van Engelen, Oral exposure of children to
424 chemicals via hand-to-mouth contact, National Institute for Public Health and the
425 Environment report 320005004 (2007).
- 426 [15] EFSA, Guidance on selected default values to be used by the EFSA Scientific
427 Committee, Scientific Panels and Units in the absence of actual measured data,
428 Available from: <http://www.efsa.europa.eu/en/efsajournal/doc/2579.pdf> 2012.
- 429 [16] Commission Decision 2011/510/EU of 4 August 2011 extending the period
430 referred to in Article 114(6) of the Treaty on the Functioning of the European
431 Union in relation to national provisions maintaining the limit values for lead,
432 barium, arsenic, antimony, mercury and nitrosamines and nitrosatable substances
433 in toys notified by Germany pursuant to Article 114(4), Off. J. Eur. Commun. L

434 214 (19.08.2011) 15-18, Available from: [http://eur-lex.europa.eu/legal-](http://eur-lex.europa.eu/legal-content/EN/TXT/PDF/?uri=CELEX:32011D0510&rid=1)
435 [content/EN/TXT/PDF/?uri=CELEX:32011D0510&rid=1](http://eur-lex.europa.eu/legal-content/EN/TXT/PDF/?uri=CELEX:32011D0510&rid=1)

436 [17] Government of Canada, Consolidated Acts, Hazardous Products Act (R.S.C., 1985,
437 c. H-3), Available from: <http://laws-lois.justice.gc.ca/eng/acts/H-3/>

438 [18] US CPSC, US Consumer Product Safety Commission, FAQs: Lead In Paint (And
439 Other Surface Coatings), Available from: [https://www.cpsc.gov/en/Business--](https://www.cpsc.gov/en/Business--Manufacturing/Business-Education/Lead/FAQs-Lead-In-Paint-And-Other-Surface-Coatings)
440 [Manufacturing/Business-Education/Lead/FAQs-Lead-In-Paint-And-Other-](https://www.cpsc.gov/en/Business--Manufacturing/Business-Education/Lead/FAQs-Lead-In-Paint-And-Other-Surface-Coatings)
441 [Surface-Coatings](https://www.cpsc.gov/en/Business--Manufacturing/Business-Education/Lead/FAQs-Lead-In-Paint-And-Other-Surface-Coatings).

442 [19] CSC, The Campaign for safe Cosmetics, Pretty Scary: Could Halloween face paint
443 cause lifelong health problems? Available from:
444 http://www.safecosmetics.org/downloads/PrettyScary_Oct2709.pdf, 2009.

445 [20] M.G. Volpe, M. Nazzaro, R. Coppola, F. Rapuano, R.P. Aquino, Determination
446 and assessments of selected heavy metals in eye shadow cosmetics from China,
447 Italy, and USA, *Microchem. J.* 101 (2012) 65-69.

448 [21] N.M. Hepp, Determination of total lead in 400 lipsticks on the U.S. market using a
449 validated microwave-assisted digestion, inductively coupled plasma-mass
450 spectrometric method, *J. Cosmet. Sci.* 63 (2012) 159-176.

451 [22] S. Liu, S.K. Hammond & A. Rojas-Cheatham, Concentrations and Potential Health
452 Risks of Metals in Lip Products, *Environ. Health Perspect.* 121 (2013) 705-710.

453 [23] P. Piccinini, M. Piecha & S.F. Torrent, European survey on the content of lead in
454 lip products, *J. Pharm. Biomed. Anal.* 76 (2013) 225-233.

455 [24] Health Canada, Consumer Product Safety, Guidance on Heavy Metal Impurities in
456 Cosmetics, Available from: [http://www.hc-sc.gc.ca/cps-](http://www.hc-sc.gc.ca/cps-spcc/pubs/indust/heavy_metals-metiaux_lourds/index-eng.php)
457 [spc/pubs/indust/heavy_metals-metiaux_lourds/index-eng.php](http://www.hc-sc.gc.ca/cps-spcc/pubs/indust/heavy_metals-metiaux_lourds/index-eng.php) 2012.

- 458 [25] Bundesgesundheitsblatt (Federal Health Journal, Germany) 28 (1985) 216.
459 Available from:
460 [http://www.bfr.bund.de/cm/343/kosmetische_mittel_bfr_empfiehl_schwermetallg](http://www.bfr.bund.de/cm/343/kosmetische_mittel_bfr_empfiehl_schwermetalle_ueber.pdf)
461 [ehalte_ueber.pdf](http://www.bfr.bund.de/cm/343/kosmetische_mittel_bfr_empfiehl_schwermetalle_ueber.pdf) 2006.
- 462 [26] O. Al-Dayel, J. Hefne & T. Al-Ajyan, Human Exposure to Heavy Metals from
463 Cosmetics, Oriental Journal of Chemistry, 27 (2011) 01-11.
- 464 [27] D.A. Basketter, G. Briatico-Vangosa, W. Kaestner, C. Lally, W.J. Bontinck,
465 Nickel, cobalt and chromium in consumer products: a role in allergic contact
466 dermatitis?, Contact Dermat. 28 (1993) 15-25.
- 467 [28] US ATSDR, United States Agency for Toxic Substances and Disease Registry,
468 Department of Health and Human Services, Toxicological Profile for Lead,
469 Available from: <http://www.atsdr.cdc.gov/toxprofiles/tp13.pdf> 2007.
- 470 [29] T.I. Lidsky, J.S. Schneider, Lead neurotoxicity in children: basic mechanisms and
471 clinical correlates. Brain 126 (2003) 5-19.
- 472 [30] WHO, World Health Organization, Childhood lead poisoning, Available from:
473 <http://www.who.int/ceh/publications/leadguidance.pdf> 2010
- 474 [31] Nordic Council of Ministers, Cadmium Review, Available from:
475 http://www.who.int/ifcs/documents/forums/forum5/nmr_cadmium.pdf 2003.
- 476 [32] US ATSDR, United States Agency for Toxic Substances and Disease Registry,
477 Department of Health and Human Services, Toxicological Profile for Cadmium,
478 Available from: <http://www.atsdr.cdc.gov/toxprofiles/tp5.pdf> 2012.
- 479 [33] International Programme on Chemical Safety (IPCS) (1991). Chemical.
480 Environmental Health Criteria 108: Nickel. WHO. Geneva

- 481 [34] US ATSDR, United States Agency for Toxic Substances and Disease Registry,
482 Division of Toxicology and Human Health Sciences, Nickel: ToxFAQs, Available
483 from: <http://www.atsdr.cdc.gov/tfacts15.pdf> 2012.
- 484 [35] J.H.E Arts, C. Mommers, C. de Heer, Dose-response relationships and threshold
485 levels in skin and respiratory allergy, *Crit Rev Toxicol.* 36 (2006) 219-251.
- 486 [36] H.J. Bremmer, L.C.H. Prud'homme de Lodder, J.G.M. van Engelen, Cosmetics
487 Fact Sheet: To assess the risks for the consumer (updated version for ConsExpo 4),
488 National Institute for Public Health and the Environment (the Netherlands) report
489 320104001/2006.
- 490 [37] US ATSDR, United States Agency for Toxic Substances and Disease Registry,
491 Division of Toxicology and Human Health Sciences, Chromium: ToxFAQs,
492 Available from: <http://www.atsdr.cdc.gov/toxfaqs/tfacts7.pdf> 2012.
- 493 [38] G.A. Wasserman, X. Liu, F. Parvez, P. Factor-Litvak, H. Ahsan, D. Levy, J. Kline,
494 A. van Geen, J. Mey, V. Slavkovich, A.B. Siddique, T. Islam, J.H. Graziano,
495 Arsenic and manganese exposure and children's intellectual function,
496 *NeuroToxicology* 32 (2011) 450-457.
- 497 [39] E. Hodgson, *A Textbook of Modern Toxicology*, third ed., John Wiley & Sons,
498 Inc., Hoboken, New Jersey, 2004.
- 499 [40] H. Riojas-Rodríguez, R. Solís-Vivanco, A. Schilman, S. Montes, S. Rodríguez, C.
500 Ríos, Y. Rodríguez-Agudelo, Intellectual Function in Mexican Children Living in
501 a Mining Area and Environmentally Exposed to Manganese, *Environ. Health*
502 *Perspect.* 118 (2010) 1465-1470.
- 503 [41] US ATSDR, United States Agency for Toxic Substances and Disease Registry,
504 Division of Toxicology and Human Health Sciences, Manganese: Public Health

505 Statement, Available from: <http://www.atsdr.cdc.gov/ToxProfiles/tp151-c1-b.pdf>
506 2012.

507 [42] US ATSDR, United States Agency for Toxic Substances and Disease Registry,
508 Department of Health and Human Services, Toxicological Profile for Copper,
509 Available from: <http://www.atsdr.cdc.gov/toxprofiles/tp132.pdf> 2004.

510 [43] US ATSDR, United States Agency for Toxic Substances and Disease Registry,
511 Division of Toxicology, Zinc: Public Health Statement, Available from:
512 <http://www.atsdr.cdc.gov/ToxProfiles/tp60-c1-b.pdf> 2005.

Figure 1
[Click here to download high resolution image](#)

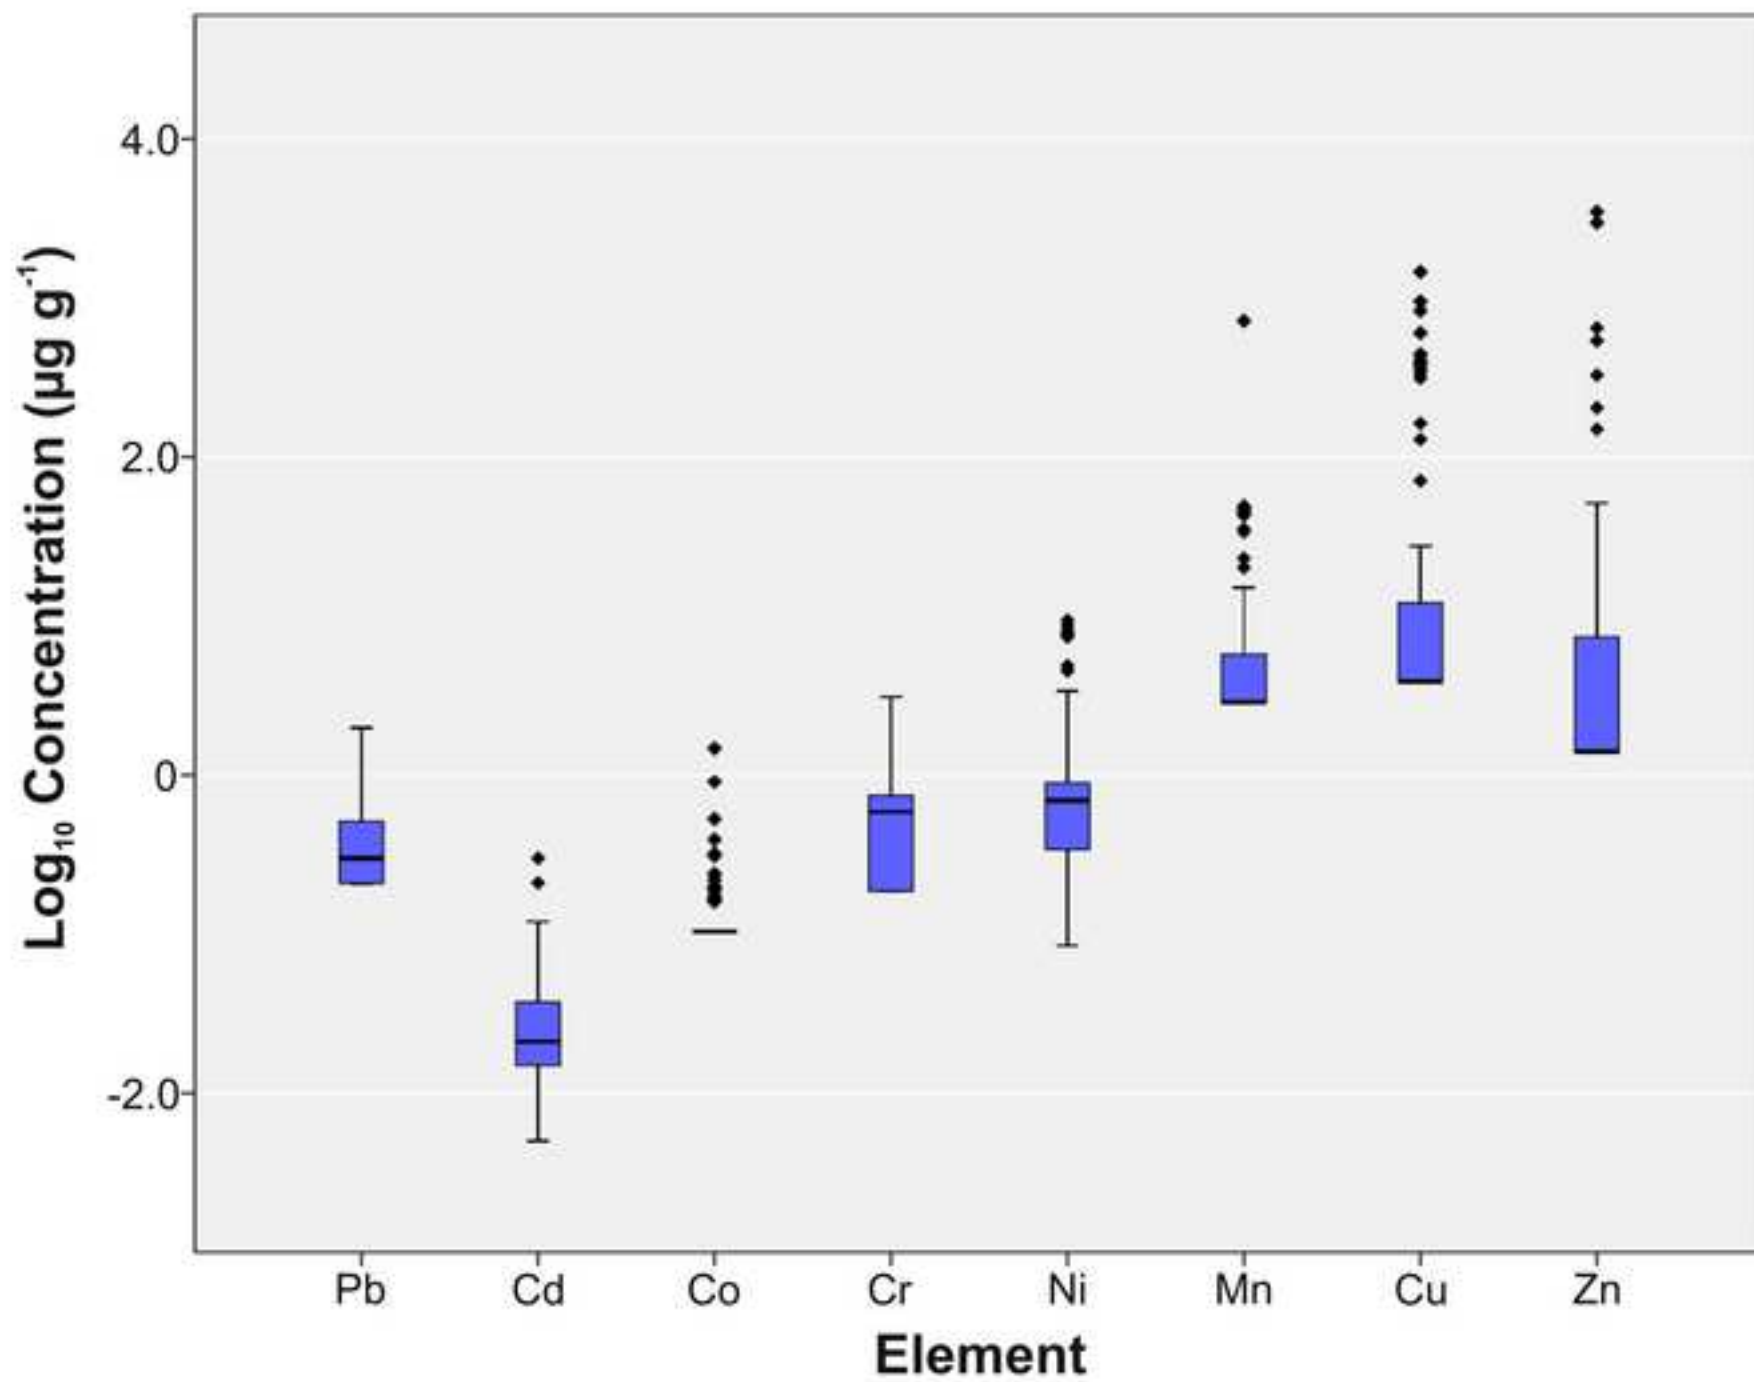


Table 1 – Results obtained from the CRM (sandy soil) analysis (mean \pm SD; n = 3).

Element	Certified value ($\mu\text{g g}^{-1}$)	Analytical value ($\mu\text{g g}^{-1}$)	Recovery (%)
Cd	0.250 ± 0.030	0.237 ± 0.016	94.8 ± 6.4
Co	1.25 ± 0.20	1.23 ± 0.04	98.5 ± 3.3
Cr	25.3 ± 3.0	24.0 ± 0.8	95.0 ± 3.1
Cu	16.8 ± 0.8	16.0 ± 0.3	94.2 ± 4.7
Mn	173 ± 12.8	175.3 ± 2.3	101.4 ± 1.3
Ni	7.65 ± 0.70	8.00 ± 0.03	104.5 ± 3.9
Pb	21.6 ± 1.2	20.3 ± 1.0	94.2 ± 4.7
Zn	44.1 ± 3.3	43.6 ± 0.8	98.8 ± 1.8

Table 2 – General information about the samples

Sample no.	Collected/ Purchased in	Product Type	Color	Brand	Country of manufacture
G1	School #1	Gouache	Blue	B1	Italy
G2	School #1	Gouache	Yellow	B1	Italy
G3	School #1	Gouache	White	B1	Italy
G4	School #2	Gouache	Yellow	B2	France
G5	School #3	Gouache	Red	B1	Italy
G6	School #3	Gouache	Yellow	B3	Italy
G7	School #4	Gouache	Orange	B4	Spain
G8	School #5	Gouache	Red	B5	Italy
G9	School #5	Gouache	Orange	B5	Italy
G10	School #6	Gouache	Purple	B5	Italy
G11	School #7	Gouache	Red	B5	Italy
G12	School #7	Gouache	Pink	B5	Italy
G13	School #7	Gouache	Green	B2	France
G14	Store #1	Gouache	Yellow	B6	Italy
G15	Store #2	Gouache	Green	B7	China
G16	Store #3	Gouache	Green	B8	France
G17	Store #3	Gouache	Magenta	B8	France
G18	Store #3	Gouache	White	B8	France
G19	Store #3	Gouache	Blue	B8	France
G20	Store #3	Gouache	Yellow	B8	France
A21	School #4	Acrylic	Blue	B1	Italy
A22	School #5	Acrylic	White	B2	France
A23	Store #1	Acrylic	Red	B9	China
A24	Store #1	Acrylic	Red (Scarlet)	B9	China
A25	Store #1	Acrylic	White	B9	China
W26	School #8	Watercolor	Golden	B2	France
W27	School #8	Watercolor	Green	B5	Italy
W28	Store #4	Watercolor	Red	B10	China
W29	Store #4	Watercolor	Orange	B10	China
W30	Store #4	Watercolor	Purple	B10	China
W31	Store #4	Watercolor	Green	B10	China
W32	Store #4	Watercolor	Blue	B10	China
W33	Store #2	Watercolor	Yellow	B11	China
W34	Store #2	Watercolor	Red	B11	China
W35	Store #2	Watercolor	White	B11	China

W36	Store #2	Watercolor	Green	B11	China
W37	Store #2	Watercolor	Yellow(lemon)	B12	China
W38	Store #2	Watercolor	Orange	B12	China
W39	Store #2	Watercolor	Blue	B12	China
W40	Store #2	Watercolor	Black	B12	China
W41	Store #2	Watercolor	Brown	B12	China
W42	Store #2	Watercolor	Blue (navy)	B12	China
W43	Store #2	Watercolor	White	B12	China
W44	Store #2	Watercolor	Yellow	B12	China
W45	Store #2	Watercolor	Purple	B12	China
W46	Store #2	Watercolor	Pink	B12	China
W47	Store #2	Watercolor	Green	B12	China
W48	Store #2	Watercolor	Red	B12	China
FP49	Store #5	Fingerpaint	Black	B1	Italy
FP50	Store #5	Fingerpaint	Green	B1	Italy
FP51	Store #5	Fingerpaint	Red	B1	Italy
FP52	Store #5	Fingerpaint	White	B1	Italy
FP53	Store #5	Fingerpaint	Yellow	B1	Italy
FP54	Store #5	Fingerpaint	Blue	B1	Italy
F55	School #2	Face paint	White	B13	France
F56	School #6	Face paint	Pink	B14	Spain
F57	School #7	Face paint	Silver	B15	China
F58	Store #6	Face paint	Pink	B16	China
F59	Store #6	Face paint	Yellow	B16	China
F60	Store #7	Face paint	White	B17	U.K
F61	Store #7	Face paint	Yellow	B17	U.K
F62	Store #7	Face paint	Blue	B17	U.K
F63	Store #7	Face paint	Purple	B17	U.K
F64	Store #7	Face paint	Green	B17	U.K
F65	Store #7	Face paint	Red	B17	U.K
F66	Store #7	Face paint	Black	B17	U.K

Table 3 – Metals content in samples (mean value of n=3 determinations; $\mu\text{g g}^{-1}$ wet weight) and summary statistics

Sample ID	Pb	Cd	Co	Cr	Ni	Mn	Cu	Zn
<i>Gouaches</i> (n=20)								
G1	<LoD	0.04	<LoD	0.67	0.34	35.2	400	4.22
G2	0.30	0.03	0.17	0.52	0.42	33.8	<LoD	2.81
G3	<LoD	0.04	<LoD	0.45	<LoD	5.75	<LoD	2.46
G4	0.79	0.03	<LoD	0.39	<LoD	<LoD	<LoD	3.16
G5	0.48	0.03	<LoD	1.22	0.50	46.7	<LoD	3.16
G6	<LoD	0.02	<LoD	0.16	<LoD	<LoD	<LoD	<LoD
G7	1.69	0.21	<LoD	1.07	<LoD	23.0	<LoD	3.86
G8	1.94	<LoD	<LoD	0.73	0.78	43.1	<LoD	9.84
G9	0.75	0.03	<LoD	0.49	0.51	45.3	<LoD	7.38
G10	1.14	0.04	0.32	0.52	0.78	45.3	13.1	10.2
G11	0.68	0.03	0.16	0.46	0.60	43.1	<LoD	6.32
G12	0.90	0.03	0.17	0.46	0.71	48.9	<LoD	7.38
G13	0.79	<LoD	<LoD	0.44	<LoD	5.75	361	2.81
G14	0.41	0.30	<LoD	2.39	0.27	10.8	<LoD	4.22
G15	<LoD	0.02	<LoD	0.62	0.85	<LoD	439	11.6
G16	0.39	<LoD	<LoD	0.17	0.80	<LoD	<LoD	<LoD
G17	0.51	<LoD	<LoD	0.17	0.74	<LoD	602	<LoD
G18	0.38	<LoD	<LoD	0.20	0.78	<LoD	<LoD	<LoD
G19	0.48	0.07	0.16	0.65	1.00	<LoD	<LoD	<LoD
G20	0.52	0.02	0.19	0.26	1.16	<LoD	384	<LoD
Mean (median)*	0.65 (0.50)	0.05 (0.03)	0.13 (0.10)	0.60 (0.48)	0.56 (0.56)	20.5 (8.3)	112.7 (3.9)	4.39 (3.16)
SD	0.48	0.07	0.05	0.50	0.30	19.4	197	3.26
Max.	1.94	0.30	0.32	2.39	1.16	48.9	602	11.6
<i>Acrylics</i> (n=5)								

A21	<LoD	0.03	<LoD	0.73	<LoD	10.8	1458	2.81
A22	0.42	<LoD	<LoD	0.10	<LoD	<LoD	<LoD	<LoD
A23	<LoD	<LoD	0.24	0.36	<LoD	<LoD	<LoD	3478
A24	<LoD	<LoD	<LoD	2.12	1.69	<LoD	<LoD	34.4
A25	0.39	<LoD	1.47	0.79	0.77	<LoD	<LoD	2968
Mean (median)*	0.29 (0.21)	0.02 (0.01)	0.40 (0.10)	0.82 (0.73)	0.60 (0.19)	4.45 (2.87)	295 (3.86)	1297 (34.4)
SD	0.11	0.01	0.60	0.78	0.66	3.54	650	1768
Max.	0.42	0.03	1.47	2.12	1.69	10.8	1458	3478

Watercolors (n=23)

W26	0.35	<LoD	<LoD	4.88	<LoD	<LoD	7.05	9.13
W27	<LoD	<LoD	<LoD	0.21	<LoD	<LoD	12.1	327
W28	1.67	0.07	0.91	8.71	3.10	2.88	<LoD	646
W29	1.16	0.09	0.31	7.67	1.66	2.87	<LoD	538
W30	0.81	<LoD	0.22	7.40	1.39	<LoD	8.24	16.5
W31	1.71	0.12	0.53	8.01	1.34	2.88	831	204
W32	1.98	0.07	0.20	9.40	2.32	3.59	952	51.3
W33	<LoD	<LoD	<LoD	0.16	<LoD	<LoD	<LoD	<LoD
W34	<LoD	<LoD	<LoD	0.09	<LoD	<LoD	<LoD	<LoD
W35	<LoD	<LoD	<LoD	0.09	<LoD	<LoD	<LoD	13.1
W36	<LoD	<LoD	<LoD	0.16	<LoD	<LoD	441	<LoD
W37	0.30	0.03	<LoD	0.72	0.61	<LoD	<LoD	<LoD
W38	0.31	0.04	<LoD	0.76	0.63	<LoD	<LoD	<LoD
W39	0.30	0.04	<LoD	0.75	0.62	5.86	129	<LoD
W40	0.33	0.04	<LoD	0.89	0.67	4.24	<LoD	<LoD
W41	0.32	0.04	<LoD	0.76	0.63	<LoD	27.5	<LoD
W42	<LoD	0.04	<LoD	0.78	0.62	<LoD	313	<LoD
W43	0.38	0.04	<LoD	0.76	0.61	<LoD	<LoD	<LoD
W44	0.30	0.04	<LoD	0.71	0.58	<LoD	<LoD	<LoD

W45	0.30	0.04	<LoD	0.76	0.57	<LoD	<LoD	<LoD
W46	0.36	0.05	<LoD	0.84	0.72	4.62	<LoD	<LoD
W47	0.31	0.03	<LoD	0.73	0.60	<LoD	70.9	<LoD
W48	0.29	0.04	<LoD	0.73	0.58	<LoD	<LoD	<LoD
Mean (median)*	0.54 (0.31)	0.04 (0.04)	0.18 (0.10)	2.43 (0.76)	0.80 (0.61)	3.13 (2.87)	124 (3.86)	79.4 (1.40)
SD	0.54	0.03	0.19	3.28	0.73	0.75	266	180
Max.	1.98	0.12	0.91	9.40	3.10	5.86	952	646
<i>Fingerprints</i> (n=6)								
FP49	<LoD	<LoD	<LoD	0.21	0.70	<LoD	<LoD	<LoD
FP50	<LoD	<LoD	<LoD	0.20	0.71	<LoD	163	<LoD
FP51	<LoD	<LoD	<LoD	0.23	0.70	<LoD	<LoD	<LoD
FP52	<LoD	0.03	0.19	0.42	1.22	<LoD	<LoD	<LoD
FP53	<LoD	<LoD	<LoD	0.19	0.71	<LoD	<LoD	<LoD
FP54	<LoD	<LoD	<LoD	0.28	0.70	<LoD	338	<LoD
Mean (median)*	<LoD	0.02 (0.01)	0.12 (0.10)	0.25 (0.22)	0.79 (0.70)	<LoD	86.0 (3.9)	<LoD
SD	-	0.01	0.04	0.09	0.21	-	139	-
Max.	-	0.03	0.19	0.42	1.22	-	338	-
<i>Face paints</i> (n=12)								
F55	0.71	<LoD	<LoD	0.34	<LoD	<LoD	<LoD	2.11
F56	0.55	0.08	<LoD	3.38	0.28	9.34	<LoD	3.51
F57	<LoD	<LoD	<LoD	0.35	<LoD	4.31	<LoD	<LoD
F58	<LoD	<LoD	<LoD	1.50	<LoD	20.1	<LoD	149
F59	0.32	<LoD	<LoD	0.76	<LoD	15.1	<LoD	18.3
F60	<LoD	<LoD	<LoD	0.66	<LoD	<LoD	<LoD	<LoD
F61	<LoD	<LoD	<LoD	1.24	<LoD	<LoD	<LoD	<LoD
F62	<LoD	<LoD	<LoD	1.18	<LoD	<LoD	<LoD	<LoD
F63	<LoD	<LoD	<LoD	1.28	<LoD	<LoD	<LoD	<LoD
F64	<LoD	<LoD	<LoD	0.42	<LoD	<LoD	<LoD	<LoD

F65	<LoD	<LoD	<LoD	0.73	<LoD	<LoD	<LoD	<LoD
F66	<LoD	<LoD	0.39	4.51	2.12	718	<LoD	<LoD
Mean (median)*	0.29 (0.21)	0.02 (0.01)	0.13 (0.10)	1.36 (0.97)	0.36 (0.19)	65.6 (2.9)	<LoD	15.4 (1.4)
SD	0.17	0.02	0.08	1.29	0.56	205.5	-	42.5
Max.	0.71	0.08	0.39	4.51	2.12	718	-	149

LoD (Limit of Detection) – Pb: 0.29 $\mu\text{g g}^{-1}$; Cd: 0.02 $\mu\text{g g}^{-1}$; Co: 0.15 $\mu\text{g g}^{-1}$; Cr: 0.04 $\mu\text{g g}^{-1}$; Ni: 0.26 $\mu\text{g g}^{-1}$; Mn: 4 $\mu\text{g g}^{-1}$; Cu: 5.5 $\mu\text{g g}^{-1}$; Zn: 2 $\mu\text{g g}^{-1}$.

*For median and mean calculation, results <LoD were imputed as $\text{LoD}/\sqrt{2}$ [12].

Table 4 – Tolerable daily intake (TDI), background exposure and skin irritation/sensitization risk for the elements studied [13].

Element	TDI ($\mu\text{g kg}^{-1} \text{ bw day}^{-1}$)	Skin irritation and sensitization contact risk (qualitative indication)
Cd	0.5	Low
Cr(VI)	5*	High
Co	1.4	Medium
Cu	83	Low
Pb	3.6	Low
Mn	160	Unknown
Ni	10	High
Zn	500	Low

*This value only takes into account non-carcinogenic effects by Cr(VI).

Table 5 – Summary of the relative intake indices (%)* for the different paint types

	Pb	Cd	Co	Cr	Ni	Mn	Cu	Zn
<i>Gouaches</i> (n=20)								
Mean	0.60	0.34	0.31	0.40	0.19	0.43	4.52	0.03
Median	0.46	0.20	0.25	0.32	0.19	0.17	0.16	0.02
SD	0.44	0.49	0.13	0.34	0.10	0.40	7.92	0.02
Max.	1.80	2.00	0.76	1.59	0.39	1.02	24.2	0.08
<i>Acrylics</i> (n=5)								
Mean	0.27	0.12	0.96	0.55	0.20	0.09	11.9	8.65
Median	0.19	0.10	0.25	0.49	0.06	0.06	0.16	0.23
SD	0.10	0.04	1.43	0.52	0.22	0.07	26.1	11.8
Max.	0.39	0.20	3.50	1.41	0.56	0.22	58.6	23.2
<i>Watercolors</i> (n=23)								
Mean	0.50	0.26	0.42	1.62	0.27	0.07	4.96	0.53
Median	0.29	0.25	0.25	0.51	0.20	0.06	0.16	0.01
SD	0.50	0.18	0.45	2.19	0.24	0.02	10.7	1.20
Max.	1.83	0.80	2.17	6.27	1.03	0.12	38.2	4.31
<i>Fingerpaints</i> (n=6)								
Mean	-	0.11	0.28	0.17	0.26	-	3.46	-
Median	-	0.10	0.25	0.15	0.23	-	0.16	-
SD	-	0.03	0.08	0.06	0.07	-	5.58	-
Max.	-	0.18	0.46	0.28	0.41	-	13.6	-
<i>Face paints</i> (n=12)								
Mean	0.14	0.07	0.16	0.48	0.06	0.72	-	0.05
Median	0.10	0.05	0.13	0.34	0.03	0.03	-	0.01

SD	0.08	0.07	0.10	0.45	0.10	2.25	-	0.15
Max.	0.35	0.28	0.49	1.58	0.37	7.85	-	0.52

* Relative intake indices (RII%) – the percentage of the *tolerable daily intake* (TDI) represented by the *estimated daily intake* (EDI), resulting from exposure to the products.

Table 6 – Number of samples containing levels of Cr, Co and Ni above $5 \mu\text{g g}^{-1}$, between 1 and $5 \mu\text{g g}^{-1}$ and below $1 \mu\text{g g}^{-1}$.

	$>5 \mu\text{g g}^{-1}$			$1-5 \mu\text{g g}^{-1}$			$<1 \mu\text{g g}^{-1}$		
	Cr	Co	Ni	Cr	Co	Ni	Cr	Co	Ni
Gouaches (n=20)	0	0	0	3	0	1	17	20	19
Acrylics (n=5)	0	0	0	1	1	1	4	4	4
Watercolors (n=23)	5	0	0	1	0	5	17	23	18
Fingerpaints (n=6)	0	0	0	0	0	1	6	6	5
Face paints (n=12)	0	0	0	6	0	1	6	12	11