

## Nonunitary Spin-Triplet Superconductivity in $\text{UPt}_3$ : Evidence from $^{195}\text{Pt}$ Knight Shift Study

H. Tou,<sup>1,\*</sup> Y. Kitaoka,<sup>1</sup> K. Ishida,<sup>1</sup> K. Asayama,<sup>1</sup> N. Kimura,<sup>2,†</sup> Y. Ōnuki,<sup>2,3</sup> E. Yamamoto,<sup>3</sup>  
Y. Haga,<sup>3</sup> and K. Maezawa<sup>4</sup>

<sup>1</sup>Department of Physical Science, Graduate School of Engineering Science, Osaka University, Toyonaka, Osaka 560-8531, Japan

<sup>2</sup>Department of Physics, Graduate School of Science, Osaka University, Toyonaka, Osaka 560-0043, Japan

<sup>3</sup>Advanced Science Research Center, Japan Atomic Energy Research Institute, Tokai, Ibaraki 319-1195, Japan

<sup>4</sup>Faculty of Engineering, Toyama Prefectural University, Toyama 939-0398, Japan

(Received 4 September 1997)

$^{195}\text{Pt}$  Knight shift (KS) measurements covering the superconducting multiple phases for major field ( $H$ ) orientations have been carried out on the high-quality single crystal  $\text{UPt}_3$ . For  $H > 5$  kOe, the KS does not change below the superconducting transition temperature  $T_c$  down to 28 mK, regardless of major crystal orientations, which provides evidence that the odd-parity superconductivity with the *parallel spin pairing* is realized. By contrast, the KS *decreases* below  $T_c$  for  $H_b \parallel b$  axis and  $H_b < 5$  kOe and for  $H_c \parallel c$  axis and  $H_c < 2.3$  kOe, whereas the KS for  $H_a \parallel a$  axis is  $T$  independent across  $T_c$  down to  $H_a \sim 1.764$  kOe. These novel findings entitle  $\text{UPt}_3$  as the first spin-triplet odd-parity superconductor including a *nonunitary* pairing characterized by the two-component  $\mathbf{d}$  vector like  $\mathbf{d}_b + i\mathbf{d}_c$  at low  $T$  and low  $H$ . [S0031-9007(98)05803-7]

PACS numbers: 74.70.Tx, 71.28.+d, 75.40.Cx, 76.60.Cq

Extensive experiments have provided convincing evidence for the unconventional nature of the superconducting (SC) state in  $\text{UPt}_3$  [1]. Especially, the SC double transition and multiple phases ( $A$ ,  $B$ ,  $C$  phases) in the  $H$  (magnetic field)- $T$  (temperature) plane point to internal degrees of freedom in a Cooper pair [2]. Several scenarios to explain the multiple phases in  $\text{UPt}_3$  have been put forth. A controversy, however, lies in whether the nearly degenerate SC transition temperatures ( $T_{c1}$ ,  $T_{c2}$ ) arise either from the pseudospin part (spin scenario) [3,4] or the orbital part (orbital scenario) [5,6] of the Cooper pair. All scenarios have assumed that the degeneracy is broken by the antiferromagnetic (AF) ordering detected by the neutron scattering experiment [7].

A possibility of the odd parity of the Cooper pair was suggested from the NMR [8] and the  $\mu\text{SR}$  [9] experiments, which pointed to  $T$ -independent Pt and  $\mu^+$  Knight shifts below  $T_c$ . In our previous paper [10], we reported the precise  $^{195}\text{Pt}$  Knight shift (KS) measurements on the high-quality single crystalline  $\text{UPt}_3$  as follows: No NMR anomalies associated with the AF ordering were observed near and below  $T_N = 5$  K, suggesting that it is not a static order but AF spin fluctuations. In the SC state, the KS above 5 kOe does not change across  $T_c$  down to  $T = 28$  mK regardless of the field orientations and the SC multiple phases. These novel results have revealed that  $\text{UPt}_3$  is the odd-parity superconductor with the *parallel spin pairing* and the pinning of the order parameter does not take place above  $\sim 5$  kOe.

In the anisotropic superfluid state in  $^3\text{He}$ , the triplet order parameter is described by  $\hat{\Delta}(\mathbf{k}) = i[\mathbf{d}(\mathbf{k}) \cdot \boldsymbol{\sigma}] \sigma_y$  in terms of the  $\mathbf{d}$  vector [11]. The magnetic field forces to align the  $\mathbf{d}$  vector perpendicularly to  $H$  and even stabilize the nonunitary triplet state, i.e.,  $A_1$  phase characterized by the  $\mathbf{d}_x + i\mathbf{d}_y$  for  $H \parallel z$  axis. By contrast, in heavy fermion

superconductors (HFS), the spin-orbit coupling (SOC) felt by the Cooper pair have been believed to be strong enough to lock a  $\mathbf{d}$  vector to the crystal lattice. In a quantitative level, the previous experiment clarified that the strength of the SOC is relatively weaker than  $\sim 5$  kOe in a measure of the field. It was, however, kept in our mind that a  $\mathbf{d}$  vector may be locked to the lattice at lower fields.

In spite of many experimental and theoretical efforts, it is still an underlying issue to identify possible spin-triplet states, e.g.,  $\mathbf{d}$  vectors corresponding to the multiple  $A$ ,  $B$ , and  $C$  phases. In order to complete the understanding for the odd-parity pairing state in  $\text{UPt}_3$ , further accurate Knight shift experiments at low fields are repeatedly required on a high-quality single crystal.

In this Letter, we report further precise measurements of the  $^{195}\text{Pt}$  Knight shift in the SC state down to the lowest field of  $\sim 1.764$  kOe and temperature of 28 mK. Two single crystals with typical dimensions of  $2 \times 2 \times 5$  mm<sup>3</sup> (#3s) and  $1 \times 1 \times 4$  mm<sup>3</sup> (#4) with their lengths parallel to the hexagonal [0001] and [1 $\bar{1}$ 00] axes, respectively, were used. Hereafter, the hexagonal [11 $\bar{2}$ 0], [1 $\bar{1}$ 00], and [0001] axes are denoted as  $a$ ,  $b$ , and  $c$  axes [see Fig. 5(d)], and field orientations, Knight shifts, and the components of  $\mathbf{d}$  vector are denoted as  $H_i$ ,  $K_i$ , and  $\mathbf{d}_i$  with  $i = a, b$ , and  $c$ , respectively. We emphasize that the present samples are in a clean limit with the residual resistivity ratio of  $RRR \sim 510$  and the transport mean free path of  $l_{tr} \geq 2000$  Å [12]. Therefore, the *spin-orbit scattering* due to impurity was, in fact, ruled out [10].

Figures 1(a) and 1(b) show the  $T$  dependence of  $^{195}\text{Pt}$  NMR spectra for  $H_a \sim 1.764$  and  $H_b \sim 1.943$  kOe, respectively. In the normal state, the full width at half maximum of the spectrum is as narrow as  $\sim 5.9$  Oe being the narrowest to date in the HFS's. As seen in the figure, a peak in the spectrum shifts below  $T_c$  to a

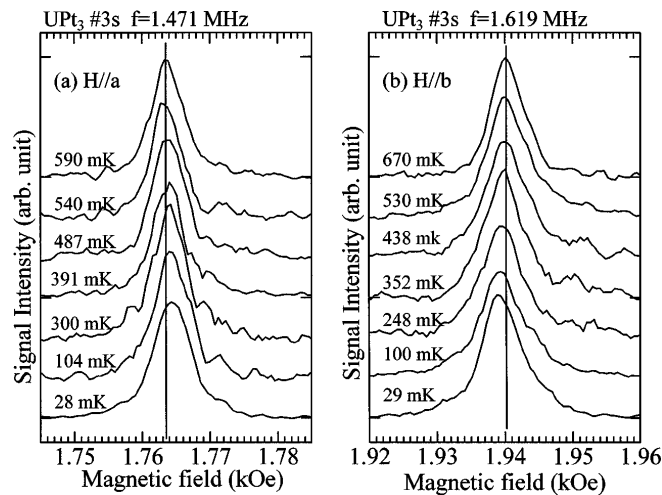


FIG. 1.  $T$  dependence of the  $^{195}\text{Pt}$  NMR spectra for (a)  $H_a \sim 1.764$  kOe at  $f = 1.471$  MHz and (b)  $H_b \sim 1.943$  kOe at  $f = 1.619$  MHz.

high field by  $\sim 1$  Oe for  $H_a$ , whereas to a lower field by  $\sim 1.8$  Oe for  $H_b$  and  $H_c$ , respectively. Noting that the hyperfine coupling constant is negative irrespective of crystal orientations [10], it turns out that the shift for  $H_a$  is dominated by the SC diamagnetic field,  $H_{\text{dia}}$ . Contrary to this, the significant decrease of the spin part in the KS is observed for  $H_b$  and  $H_c$ . Even at the lowest  $T$  and  $H$ , the obtained spectrum remains slightly asymmetric with an increase by  $\sim 1.5$  Oe in the linewidth, suggesting that the magnetic field penetrates uniformly.

Under  $H_{c2} \sim 20$  kOe  $\gg H \gg H_{c1} \sim 10$  Oe and a vortex spacing ( $d \sim 1050$  Å at  $H \sim 2$  kOe) extremely smaller than the London penetration depth ( $\lambda > \sim 7000$ – $11000$  Å [9,13]), the square root of the second moment,  $\sqrt{\Delta H^2}$ , of the NMR spectrum, which is a good measure of the SC diamagnetic contribution, is estimated as  $\sqrt{\Delta H^2} = (B/\sqrt{4\pi})(d/\lambda)[1 + (2\pi\lambda)^2]^{-1/2} \sim \phi_0/(\lambda^2\sqrt{16\pi^3}) \leq 1.9$  Oe by using  $\lambda > 7000$  Å, where  $\phi_0 = hc/2e$  is the flux quantum [14]. This is comparable with the increase by  $\sim 1.5$  Oe in the linewidth for  $H_a$ ,  $H_b$ , and  $H_c$  at the lowest  $T$  and  $H$ . Furthermore, a direct calculation by using the relation of  $H_{\text{dia}} = -H_{c1} \ln(\beta e^{-1/2} d/\xi)/\ln \kappa$  [15] yields  $H_{\text{dia}} \sim -1.9$  Oe. Here we used the value of  $H_{c1} \sim 1$  mT,  $\beta = 0.381$  for the triangular lattice,  $d \sim 1050$  Å, and  $\kappa \sim 100$  [16]. These considerations allow us to estimate  $H_{\text{dia}}$  to be as small as  $\sim -1.5$  Oe at respective lowest field from the increase in the linewidth below  $T_c$ .

Figures 2, 3, and 4 display the  $T$  dependence of the KS for  $H_a$  ( $K_a$ ),  $H_b$  ( $K_b$ ), and  $H_c$  ( $K_c$ ), respectively. Here, the KS is defined by the first moment of each spectrum without any correction arising from the SC diamagnetic shift. Figure 5 indicates schematically the multiple phase diagram obtained from other measurements on the same single crystals [17] and the  $H$  and  $T$  region where the KS does decrease as mapped by the shadow area. The spin part in the KS decreases to zero at  $T = 0$  and is unchanged across  $T_c$  in the case of  $\mathbf{d} \parallel H$  and  $\mathbf{d} \perp H$ , respectively, in

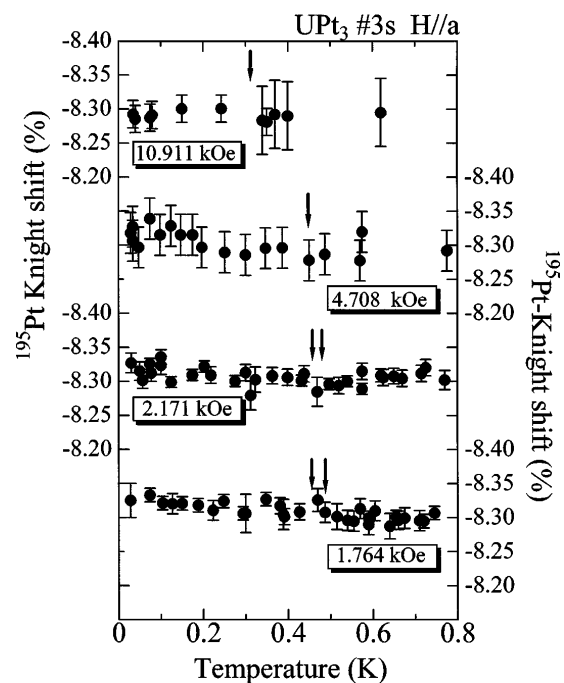


FIG. 2.  $T$  dependence of the  $^{195}\text{Pt}$   $K_a$  at the various magnetic fields for  $H_a \parallel a$  axis. Arrows ( $\downarrow$ ) show  $T_{c1}$  and  $T_{c2}$ .

the analogy with the superfluid  $^3\text{He}$ . To determine the spin structure in the Cooper pair, hence, enables us to identify respective  $\mathbf{d}$  vectors in the multiple phases as follows:

(1)  $K_a$ ,  $K_b$ , and  $K_c$  do not change below  $T_c$  in the field range of 5–15.6 kOe regardless of crystal orientations. In the  $C$  phase for  $H_a$  and  $H_b$  and the  $B$  and  $C$  phases for  $H_c$ , the spin susceptibility due to the Cooper pair is the same as that in the normal state, namely, the  $\mathbf{d}$  vector rotates so that  $\mathbf{d} \perp H$  or it is kept as  $\mathbf{d} \perp H$ .

(2)  $|K_b|$  decreases below  $T_{c1}$  for  $H_b < 5$  kOe, but  $|K_a|$  increases for  $H_a < 5$  kOe by an amount comparable to  $H_{\text{dia}}$ . The latter means that the spin part in  $K_a$  is almost unchanged across  $T_c$  for  $H_a$ . Since  $\mathbf{d} \parallel b$  axis in the  $A$  and  $B$  phases, the Cooper pair spin vector is in the  $a$ - $c$  plane perpendicular to the  $b$  axis.

(3)  $K_c$  is unchanged across  $T_{c1}$  for  $H_c < 2.3$  kOe. This result and (2) mean that the spin vector in the  $A$  phase follows the field in the  $a$ - $c$  plane perpendicular to the  $b$  axis. The  $A$  phase is hence characterized by the single component  $\mathbf{d}_b$  vector.

(4) The decrease in  $|K_c|$  occurs below  $T_{c2}$  for  $H_c < 2.3$  kOe:  $|K_c|$  decreases markedly by a slight field reduction for  $H_c$  from 2.299 to 2.141 kOe. This means that the spin vector rotates from the  $c$  axis to the  $a$  axis in the  $B$  phase in fields lower than  $H_{c,\text{pin}} \sim 2.3$  kOe. By incorporating that  $K_a$  is almost unchanged across  $T_c$ , whereas both  $|K_b|$  and  $|K_c|$  decrease, it is concluded that the Cooper pair spin vector is spontaneously pinned to the  $a$  axis at low  $T$  and  $H$ . It turns out that the  $B$  phase at low  $T$  and low  $H$  is a *nonunitary state* characterized by the two-component  $\mathbf{d}$  vector whose relative phase is  $\pi/2$ , e.g.,  $\mathbf{d}_b + i\mathbf{d}_c$  locked to the  $b$  and  $c$  axes.

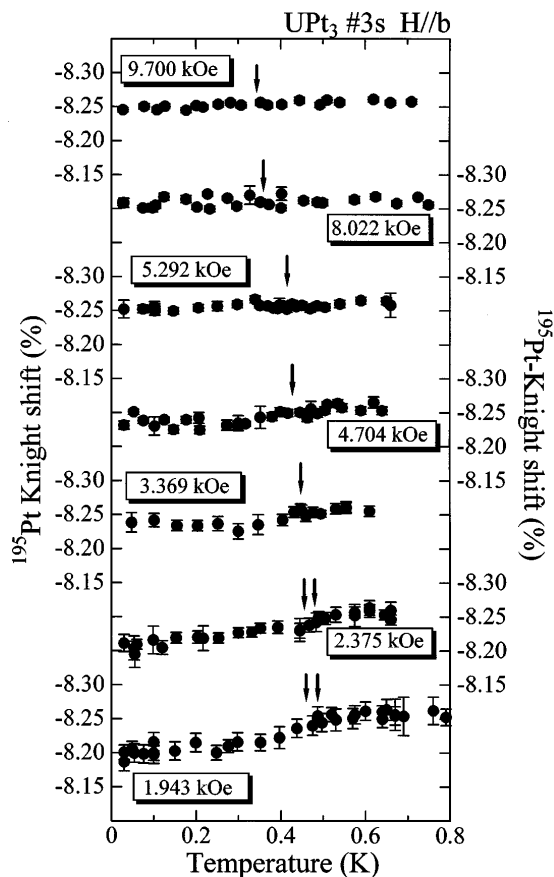


FIG. 3.  $T$  dependence of the  $^{195}\text{Pt}$   $K_b$  at the various magnetic fields for  $H_b \parallel b$  axis. Arrows ( $\downarrow$ ) show  $T_{c1}$  and  $T_{c2}$ .

(5) As a result, it is reasonable that the  $C$  phase possesses a single component  $\mathbf{d}_c$  ( $\mathbf{d}_a$ ) vector for  $H_{a,b}$  ( $H_c$ ).

(6) As indicated in Fig. 5(b) for  $H_b$ , the decrease in  $|K_b|$  almost tunes to the  $C \rightarrow B$  transition in the  $H$  variation and the normal to  $A$  phase transition in the  $T$  variation.

(7) As in Fig. 5(c) for  $H_c$ , although the decrease in  $|K_c|$  tunes qualitatively to the  $A \rightarrow B$  transition in the  $T$  variation, but it does not to the  $C \rightarrow B$  transition [ $H_c(CB)$ ] in the  $H$  variation, taking place at  $H_{c,\text{pin}} \sim 2.3$  kOe much lower than  $H_c(CB)$ .

Contributing insights are obtained from a comparison of the above rich variety of the Knight shift results with the proposed scenarios for the order parameter symmetry in  $\text{UPt}_3$  so far as follows:

(A) The spin-singlet  $E_{1g}$  scenario [6] is ruled out because it predicts an isotropic decrease in the KS which should be independent of the field.

(B) The two dimensional  $E_{1u}$  [4] and  $E_{2u}$  [5] scenarios for the strong SOC are excluded because the KS in  $E_{1u}$  and  $E_{2u}$  is predicted to decrease below  $T_c$  in the basal plane (in both the  $a$  and  $b$  axes) and only along the  $c$  axis, respectively. From the results of (1) and (7), since the vector rotation from the  $\mathbf{d}_c$  to the  $\mathbf{d}_a$  in the  $B$  phase takes place for  $H_c > H_{c,\text{pin}} \sim 2.3$  kOe which is a relatively

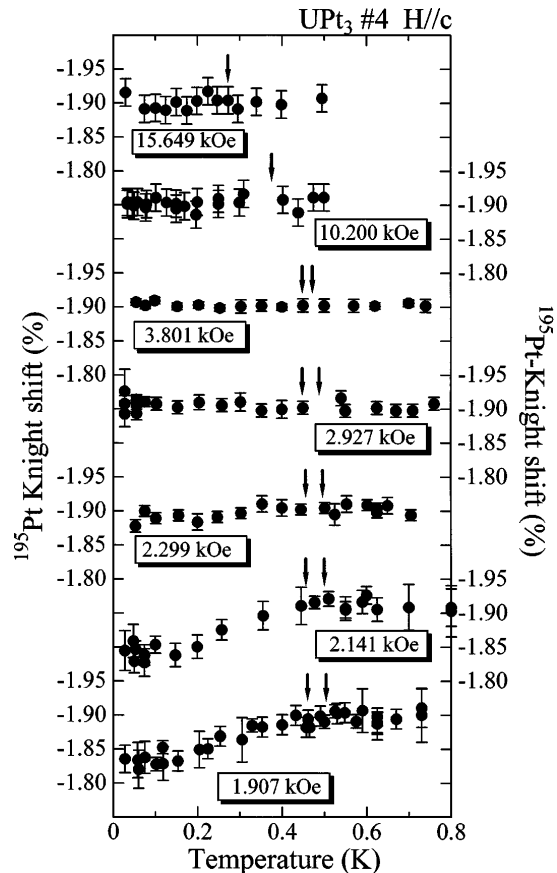


FIG. 4.  $T$  dependence of the  $^{195}\text{Pt}$   $K_c$  at various magnetic fields for  $H_c \parallel c$  axis. Arrows ( $\downarrow$ ) show  $T_{c1}$  and  $T_{c2}$ .

weak field, any scenario based on the strong SOC fails to interpret the present experiment.

(C) The first proposed spin scenario [3] for the weak SOC seems to be consistent with the result for  $H > 5$  kOe [8–10], but is not in accord with the present results below 5 kOe since no decrease in the KS was predicted along any crystal direction.

Ohmi and Machida have recently put forward a renewed spin scenario, which is successful in assigning the  $\mathbf{d}$  vector structure to describe the multiple phases of superconductivity and in identifying the  $B$  phase as the *nonunitary spin-triplet* state at low  $T$  and low  $H$  [18]. Furthermore, they have pointed out that the cause that the  $\mathbf{d}$  vector in the  $A$  and  $B$  phases is locked to the  $b$  axis is not due to the SOC, but to the symmetry breaking field associated with the quasielastic AF fluctuations with the staggered polarization vector,  $\mathbf{M}_Q$  along the  $b$  axis. In order to match the Knight shift results for  $H_c$  to the phase diagram, a phenomenological pinning field,  $H_{c,\text{pin}}$  along  $H_c$  is taken into account so as to reproduce the rotation of the  $\mathbf{d}_c$  vector found experimentally. A possible explanation for a microscopic origin of the small pinning field along  $H_{c,\text{pin}} \sim 2.3$  kOe should, however, be addressed in future theoretical works.

Finally, we comment on the quasiparticle spin susceptibility. The fraction of the decrease in the KS's,  $\delta K_b$ ,

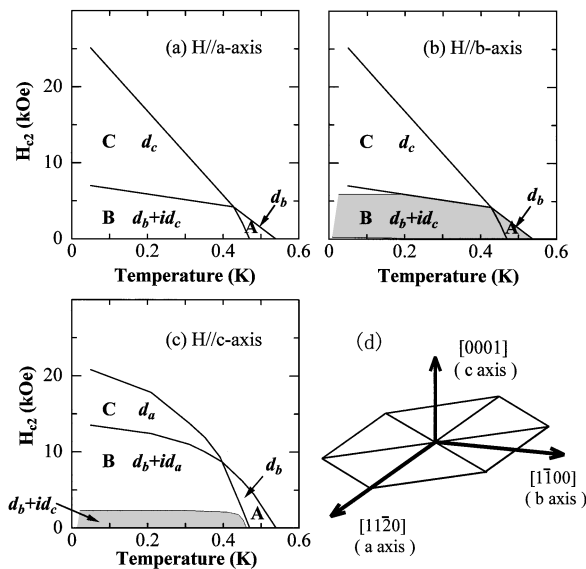


FIG. 5. (a), (b), and (c) indicate respective superconducting multiple phase diagram in  $\text{UPT}_3$  for  $H_a$ ,  $H_b$ , and  $H_c$  obtained from other measurements on the same single crystals. The shadow areas show  $H$  and  $T$  regions where the KS does decrease. Notice that these areas are not new phases associated with other SC transitions. (d) shows the definition of the hexagonal crystal axes in the present experiment.

and  $\delta K_c$  are nearly isotropic with  $\sim 0.07\%$  and  $\sim 0.08\%$ , respectively, at the lowest  $H$  and  $T$ . When  $H_{\text{dia}} \sim -1.5$  Oe ( $\sim -0.08\%$ ) is taken into account, the spin susceptibility  $\chi_s$  as  $\delta\chi = \chi_s$  is estimated to be ( $\sim 0.99$  and  $\sim 1.26$ )  $\times 10^{-4}$  emu/mole for respective directions perpendicular and parallel to the  $c$  axis from the relation of  $\delta K = A\delta\chi/(N_A\mu_B)$  with the hyperfine coupling constants of  $A_{\perp} \sim -84.9$  and  $A_c \sim -70.8$  kOe/ $\mu_B$  [10]. These values are by an order of magnitude smaller than the values of measured susceptibility. This anomalously small (pseudo) spin part in the quasiparticle susceptibility may be relevant to the realization of the *nonunitary* spin-triplet pairing in which the *ferromagnetic* spin polarization is spontaneously induced to the  $a$  axis.

In conclusion, a complete set of the  $^{195}\text{Pt}$  Knight shift data on the high-quality single crystal  $\text{UPT}_3$  have identified the spin structure of the Cooper pair. From the detailed dependences of the Knight shift on the temperature, magnetic field, and crystal orientation, it has been established that the  $A$  and  $B$  phases belong to a class of *unitary* and *nonunitary* triplet pairing states characterized by the  $\mathbf{d}_b$  and  $\mathbf{d}_b + i\mathbf{d}_c$  vectors, respectively, and the  $C$  phase may be the *unitary* state described as the  $\mathbf{d}_c$  ( $\mathbf{d}_a$ ) vector for  $H_{a,b}$  ( $H_c$ ). The vector rotation from the  $\mathbf{d}_c$  to the  $\mathbf{d}_a$  for  $H_c > 2.3$  kOe has experimentally verified that the spin-orbit coupling felt by the Cooper pair is weak.  $\text{UPT}_3$  is thus concluded to be

the first *spin-triplet odd-parity superconductor* in charged many body systems.

We gratefully acknowledge K. Machida, T. Ohmi, and K. Miyake for valuable discussions and theoretical comments. H. T. and Y. K. thank J. Flouquet, T. Sakakibara, H. Ikeda, and A. Huxley for useful comments. This work was supported by the *Priority Areas Grants from the Ministry of Education, Sport, Science and Culture in Japan*. H. T. was supported by *Research Aid of Inoue Foundation for Science*.

\*Present address: Department of Physics, Tokyo Metropolitan University, Minami-osawa, Hachi-oji, Tokyo 192-0397, Japan.

†Present address: Center for Low Temperature Science, Tohoku University, Sendai 980-0845, Japan.

- [1] J. Flouquet *et al.*, *Physica (Amsterdam)* **185C**, 372 (1991); L. Taillefer *et al.*, *Physica (Amsterdam)* **169B**, 257 (1991), and references therein.
- [2] R. A. Fischer *et al.*, *Phys. Rev. Lett.* **62**, 1411 (1989); K. Hasselbach *et al.*, *Phys. Rev. Lett.* **63**, 93 (1989); G. Bruls *et al.*, *Phys. Rev. Lett.* **65**, 2294 (1990); S. Adenwalla *et al.*, *Phys. Rev. Lett.* **65**, 2298 (1990).
- [3] K. Machida and M. Ozaki, *Phys. Rev. Lett.* **66**, 3293 (1991); T. Ohmi and K. Machida, *Phys. Rev. Lett.* **71**, 625 (1993); K. Machida *et al.*, *J. Phys. Soc. Jpn.* **62**, 3216 (1993).
- [4] K. Machida *et al.*, *J. Phys. Soc. Jpn.* **64**, 1067 (1995).
- [5] C. H. Choi and J. A. Sauls, *Phys. Rev. Lett.* **66**, 484 (1991); J. A. Sauls, *J. Low Temp. Phys.* **95**, 153 (1994); *Adv. Phys.* **43**, 113 (1994).
- [6] K. A. Park and R. Joynt, *Phys. Rev. Lett.* **74**, 4734 (1995).
- [7] G. Aeppli *et al.*, *Phys. Rev. Lett.* **63**, 676 (1989).
- [8] Y. Kohori *et al.*, *J. Phys. Soc. Jpn.* **56**, 2263 (1987); *J. Magn. Magn. Mater.* **76&77**, 478 (1988).
- [9] G. M. Luke *et al.*, *Phys. Lett. A* **157**, 173 (1991).
- [10] H. Tou *et al.*, *Phys. Rev. Lett.* **77**, 1374 (1996).
- [11] A. J. Leggett, *Rev. Mod. Phys.* **47**, 331 (1975).
- [12] N. Kimura *et al.*, *J. Phys. Soc. Jpn.* **64**, 3881 (1995).
- [13] C. B. Broholm *et al.*, *Phys. Rev. Lett.* **65**, 2062 (1990).
- [14] P. Pincus *et al.*, *Phys. Lett.* **13**, 22 (1964); analytic form for the second moment was reported as for the square lattice, but its magnitude for the triangular is expected to be not so much different.
- [15] P. G. de Dennes, in *Superconductivity of Metals and Alloys*, translated by P. A. Pincus (W. A. Benjamin, Inc., New York, Amsterdam, 1966).
- [16] This diamagnetic shift is smaller than the value estimated in the previous paper,  $\sim 6.4$  Oe at  $H \sim 4.7$  kOe. This is because a different set of parameters is used, covering a possible broad range in estimations from various experiments.
- [17] K. Tenya *et al.*, *Phys. Rev. Lett.* **77**, 3193 (1996).
- [18] T. Ohmi and K. Machida, *J. Phys. Soc. Jpn.* **65**, 4018 (1996); **65**, 3456 (1996); report.